

REPORT SUGGESTIONS O ADVICES BRISTILE 2023

(300123 to 030223) DANDENONG

SLURRY PREPARATION AND APPLICATOR

* A reference dosage in the slurry, depending on the sand used, could be as follows.


CONCRETE TILES		CONTROL AND ANALYSIS SAND / CEMENT					
REPORT		MONTH	YEAR		FACTORY		
Sand Tests		GRANULOMETRY				WASHED	OTROS

RIVER	%Retenido	SLURRY SAND		0,2	2,1	2,6	53,9	38,5	2,5	0,3				
	%Acum			0,2	2,3	4,8	58,7	97,2	99,7	100,0	1,6		96,2	

MODEL	Nº	PARAMETER	NOMINAL VALUE
ALL MODELS AND COLOURS	1	Process development times:	
		Cycle start	0
		Discharge of water and A/C load	120
		Pigment discharge manual	5
		Mixer time	120
		Total cycle time	240
		DOSAGES	
RED COLOUR	1	Sand	56
	2	Cement	70
	3	Pigment	3,27
	4	Waterproofing (Plasticiser to be used temperature > 25°C)	0,35
	5	Water	34
	6	Total weight (approx.)	159,62

SLURRY PREPARATION

***The preparation of slurry, which takes place inside the factory in front of the slurry applicator, is actually a source of dirt and contamination in its Cutting system and extruder head environment.**

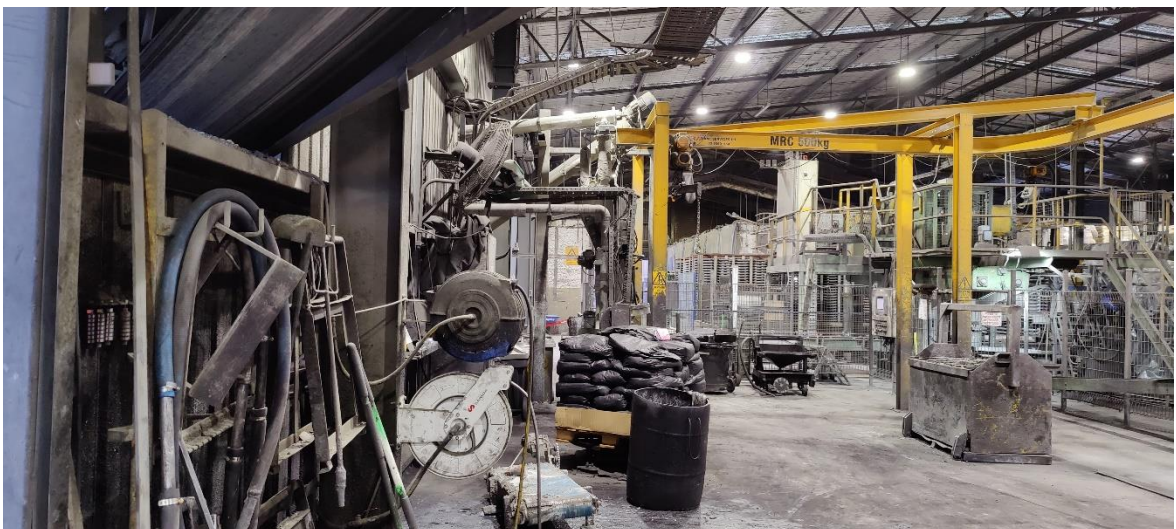

SLURRY APPLICATOR

***The slurry application consists of 2 applicators, with the main applicator running 92 % of the production, the second applicator only running 5 % of the total production.**



***It has a 260mm belt with a central lower rib, which picks up the tile in the Cutter and takes it to the Racker.**



***It generates a lot of slurry residue, accumulated in the 2 lower containers, when applying the slurry to the whole band between the tiles and when there is no tile underneath.**




***In my opinion the slurry preparation should go next to the concrete mixer, which is the point where the machinery that generates most pollution and dirt should be "concentrated".**

***That is why in the future it could be considered to move the slurry preparation.**



***The operator in this area adds pigment to the mixer or prepares slurry.**

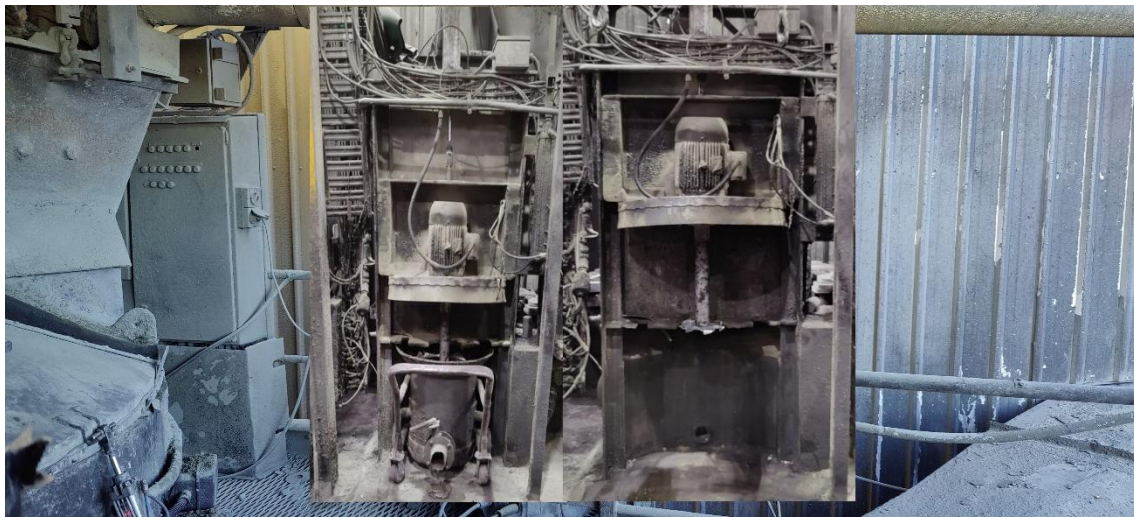

***It would not be necessary to raise and remove the beaker from the mixer because it would pass to a lower container, which with a peristaltic pump would send the slurry to the applicator.**

***A pneumatic valve could be fitted at the bottom, which works very well with the slurry.**



*The lower part of the mixer should be the cleaning point for the mixers and their lower containers, for which this area should be delimited to channel the waste and water generated.

*Also the water generated by the cleaning of the mixer and its hopper with high pressure water.



*An accessible channelling system would have to be built from the final mixer area to the settling tanks

*The slurry application assembly should also be modified, from receipt of the pallet at the Cutter to delivery to the Racker, with a set of mobile applicators and conveyors..

*It could be approached in 2 PHASES.

PHASE I

*. The current belt conveyor is transformed into 2 belt conveyors and one polycorrugated conveyor

*The belt is not contaminated, as it is the side polycorres that are contaminated.



PHASE II

*In this second phase, the applicators are made mobile and a central agitator tank is installed to prevent the slurry from settling and to collect the slurry left over from the application.

***This allows the cleaning and maintenance of the assembly to be carried out outside the factory.**

* The conveyor of the main applicator can be made with a polycor or TC guide bench section in which the pallets go without space between them and driven by the belt conveyor at the exit of the cutting system.

