



Quality Assurance Report 샘플

CUSTOMER(고객명)	DESCRIPTION(품명)	LOT NO(로트번호)	ISSUED DATE(발행일자)
캠텍	0.1778*19.05	20260331 -01	2026-03-31
규격(재질)	LOT SIZE(수량)		
0.1778*19.05 STS305 BA	Au 0.254 μ m~	Ni 0.1 μ m	27.8 Kg

I. VISUAL INSPECTION (Sampling Plan : n=100mm/Reel, 5Reel/Shipping or n=50ea/Shipping, c=0)

NO	INSPECTION ITEMS	Ac/Re	RESULT	NO	INSPECTION ITEMS	Ac/Re	RESULT
1	DISCOLORATION(변색)	0/1	OK	6	NO PLATING(미도금)	0/1	OK
2	STAIN(얼룩)	0/1	OK	7	PEELING(도금 벗겨짐)	0/1	OK
3	RUST(부식)	0/1	OK	8	LUMP(도금뭉침)	0/1	OK
4	CONTAMINATION(오염)	0/1	OK	9	CAMBER(휨)	0/1	OK
5	BENT(변형)	0/1	OK	10	PLATING BURR (도금버)	0/1	OK

II. DIMENSION INSPECTION (Sampling Plan : n=100mm/Reel, 5Reel/Shipping or n=50ea/Shipping, c=0)

NO	항목/구분	SPEC			검사주기	우리하이피		고객		판정
		규격	하한(-)	상한(+)		1차	2차	1차	2차	
1	전폭	19.05	-0.127	0.127	Reel/Lot	18.950				OK
2	간격	5.08	-0.152	0.1524	Reel/Lot	5.067				OK
3	도금폭	1.52	-0.152	0.1524	Reel/Lot	1.814				-
4										
5										
6										
7										
8										
9										
10										

III. PLATING THICKNESS(도금두께) (Sampling Plan : 1y)

NO	SPECIFICATION		Measurement Data	RESULT
1	X-Ray 측정	Au 0.254 μ m~	첨부 : 도금성적서	OK
		Ni 0.1 μ m	첨부 : 도금성적서	

IV. FUNCTIONAL TEST (Sampling Plan : n=100mm/EA, 2EA/Shipping, c=0)

NO	INSPECTION ITEMS	SPECIFICATION	TEST SAMPLE	RESULT
1	ADHESION TEST (밀착성 시험)	1.세품을 스카치 Tape에 완전 밀착후 45도 각도로 순간적으로 떼어낸다.(들뜸 및 벗겨짐) 2.테이프 시험이 안되는 제품은 니퍼로 90도로 상,하각은후 도금들뜸이나 벗겨짐이 없을것.		OK
2	Chemical Deburring Test	1.Chemicals Phosphoric acid (85%) 20%, Nitric acid (60%) 5%, Hydrochloric acid (35%) 10%, DI Water 65% 2.Immersion time: 10 minutes 3.After immersion: Treated in an ultrasonic cleaner at 68-132 kHz for 20 minutes.		OK

제품도면		우리하이피	작성	승인	종합판정	
			김영란	조승현		
		고객	작성	승인	종합판정	

업체명 : 캠텍

품명 : 0.1778x19.05

LOT NO : 260331-01 (ST)


DATE : 26.03.31.

No	μm Au	μm Ni	Au tolerance
1	0.308	0.093	0.305 0.312 0.319
2	0.313	0.072	
3	0.312	0.094	
4	0.319	0.096	
5	0.309	0.082	
Mean	0.312	0.087	
S.Dev	0.004	0.010	

FUNC: MEASURE
COL : 0.100 mm


Au
Ni
SS

SEC : 15 Sec

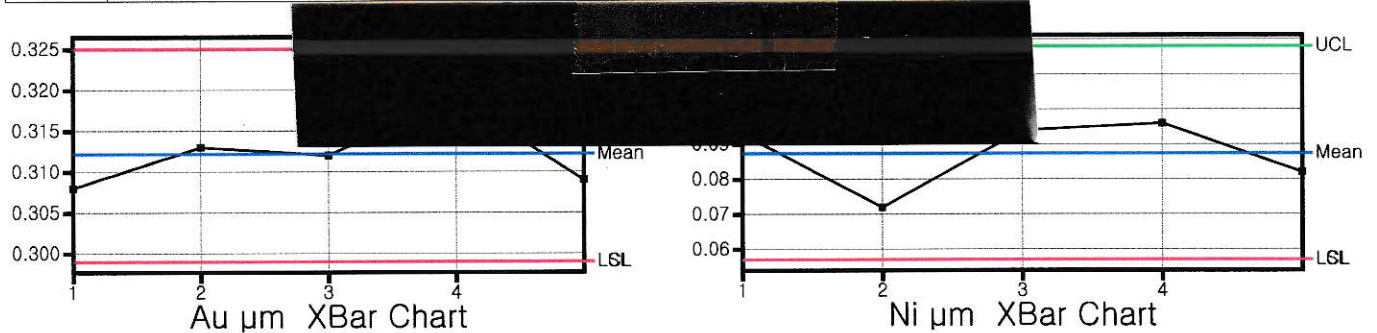

도금원소 : Au/Ni//SS

측정값 개수	5	5
최대값	0.319	0.096
최소값	0.308	0.072
범위	0.011	0.024
평균값	0.312	0.087
표준편차	0.004	0.010
변동계수	1.385	11.657

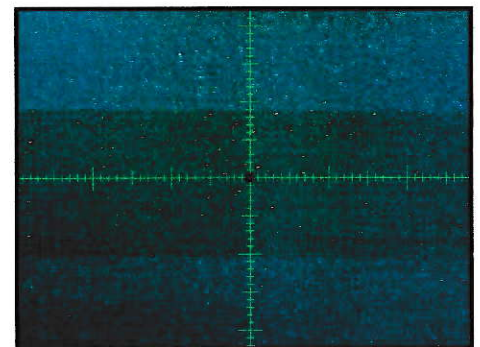

우리하이피

업체명 : 캠텍

품명 : 0.1778x19.05

LOT NO : 260331-01 (END)



DATE : 26.03.31.

No	μm Au	μm Ni	Au tolerance
1	0.308	0.088	0.298 0.305 0.312
2	0.311	0.070	
3	0.298	0.091	
4	0.302	0.071	
5	0.305	0.086	
Mean	0.305	0.081	
S.Dev	0.005	0.010	

FUNC: MEASURE
COL : 0.100 mm

Au
Ni
SS

SEC : 15 Sec

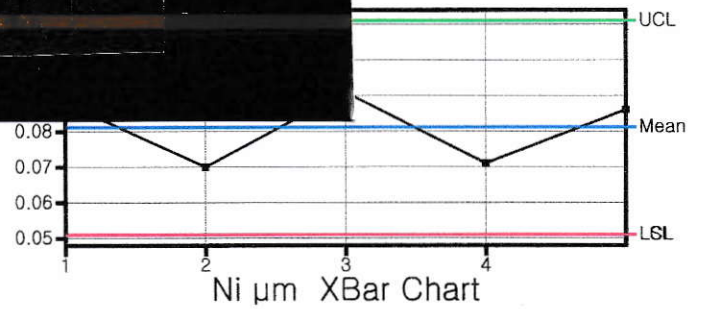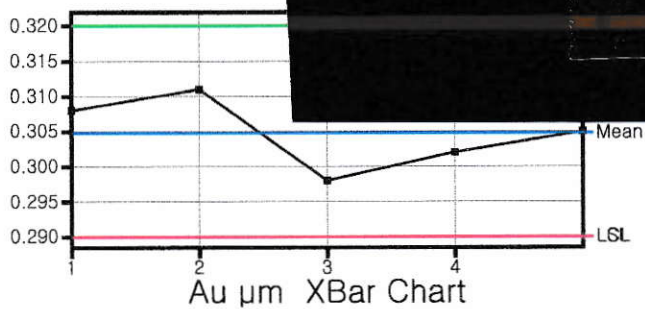

도금원소 : Au/Ni//SS

측정값 개수	5	5
최대값	0.311	0.091
최소값	0.298	0.070
범위	0.013	0.021
평균값	0.305	0.081
표준편차	0.005	0.010
변동계수	1.663	12.235

우리하이피

