



Quality Assurance Report

CUSTOMER(고객명)	DESCRIPTION(품명)	LOT NO(로트번호)	ISSUED DATE(발행일자)
신흥 SEC	0.4*26	20260511 -01 ~16	2026-05-11
규격(재질)		LOT SIZE(수량)	
0.4*26 AL	Ni 1.5μm ~	836 Kg	

I. VISUAL INSPECTION (Sampling Plan : n=100mm/Reel, 5Reel/Shipping or n=50ea/5

NO	INSPECTION ITEMS	Ac/Re	RESULT	NO	INSPECTION
1	DISCOLORATION(변색)	0/1	OK	6	NO PLATING(미도금)
2	STAIN(일록)	0/1	OK	7	PEELING(도금 벗겨짐)
3	RUST(부식)	0/1	OK	8	LUMP(도금뭉침)
4	CONTAMINATION(오염)	0/1	OK	9	CAMBER(휨)
5	BENT(변형)	0/1	OK	10	PLATING BURR (도금)

II. DIMENSION INSPECTION (Sampling Plan : n=100mm/Reel, 5Reel/Shipping or n=50ea/5

NO	항목/구분	SPEC			검사주기	우리하이피	
		규격	하한(-)	상한(+)		1차	2차
1	전폭	26.0	-0.1		Reel/Lot	25.993	0.402
2						25.984	0.402
3						25.913	0.403
4						25.978	0.403
5						25.961	0.402
6						25.976	0.403
7						25.937	0.403
8						25.984	0.402
9						25.956	0.402
10						25.989	0.401

5/11
0.4x26
① 53 ⑤ 53 ⑨ 53 ⑬ 51
② 53 ⑥ 53 ⑩ 53 ⑭ 51
③ 53 ⑦ 53 ⑪ 51 ⑮ 51
④ 53 ⑧ 53 ⑫ 51 ⑯ 51
총 836kg
25.986 0.403

III. PLATING THICKNESS(도금두께) (Sampling Plan : 1y

NO	SPECIFICATION	Measurement Data	RESULT
1	X-Ray 측정 Ni 1.5μm ~	첨부 : 도금성적서 첨부 : 도금성적서	OK

IV. FUNCTIONAL TEST (Sampling Plan : n=100mm/EA, 2EA/Shipping, c=0)

NO	INSPECTION ITEMS	SPECIFICATION	TEST SAMPLE	RESULT
1	ADHESION TEST (밀착성 시험)	1.제품을 스카치 Tape에 완전 밀착후 45도 각도로 순간적으로 떼어낸다.(들뜸 및 벗겨짐) 2.테이프 시험이 안되는 제품은 니퍼로 90도로 상하각은후 도금들뜸이나 벗겨짐이 없을것.		OK

제품도면		우리하이피	작성	승인	종합판정	
		김영란	조승현			
고객		작성	승인		종합판정	

업체명 : 신흥SEC


품명 : 0.4x26 초물 LOT NO : 260511-01 DATE : 26.05.11.

No	μm Ni	Ni tolerance
1	2.070	2.046 2.069 2.093
2	2.067	
3	2.091	
4	2.054	
5	2.046	
6	2.088	
Mean	2.069	
S.Dev	0.018	

FUNC: MEASURE
COL : 0.100 mm

Ni
—
Al


SEC : 15 Sec

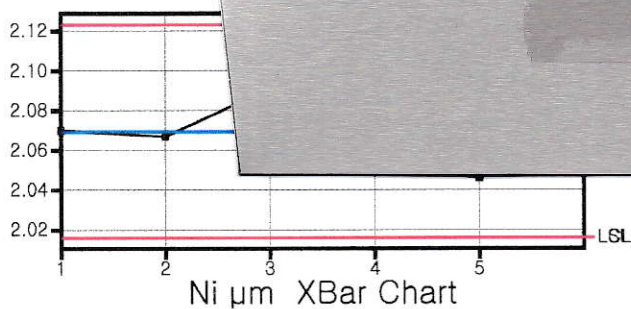

도금원소 : Ni//Al

측정값 개수 6
 최대값 2.091
 최소값 2.046
 범위 0.045
 평균값 2.069
 표준편차 0.018
 변동계수 0.865

우리하이피

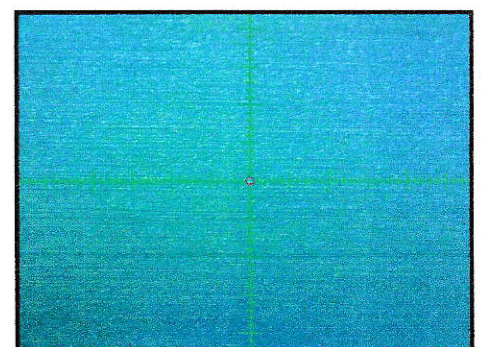

업체명 : 신흥SEC


품명 : 0.4x26 초물 LOT NO : 260511-16 DATE : 26.05.11.

No	μm Ni	Ni tolerance
1	2.046	2.018 2.050 2.083
2	2.068	
3	2.052	
4	2.083	
5	2.031	
6	2.022	
Mean	2.050	
S.Dev	0.023	

FUNC: MEASURE
COL : 0.100 mm

Ni
—
Al

SEC : 15 Sec

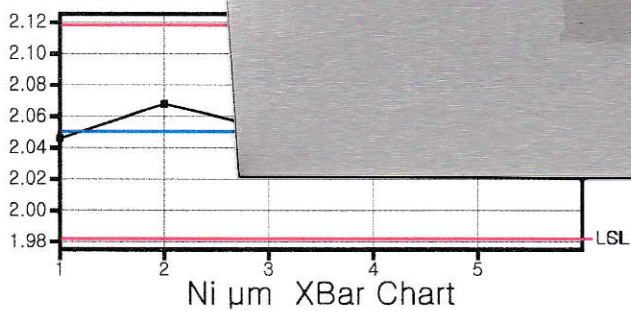

도금원소 : Ni//Al
측정값 개수 6
최대값 2.083
최소값 2.022
범위 0.061
평균값 2.050
표준편차 0.023
변동계수 1.107

우리하이피

