

구분	작성 (Prepared)			검토 (Checked)			승인 (Approved)			구분	작성 (Prepared)			검토 (Checked)			승인 (Approved)		
	재			재			재				재			재			재		
검 사 성 적 서 Inspection Report																			
고객명 (Customer)				한빛티앤아이				품명 (Part Name)				Heat Spreader				납품서NO (Order No.)			
모델 (Model)				27mm Body				모델 NO. (Model NO.)				0850618HS				관리번호 (Report NO.)			
재질 (Material)								도면 REV.NO											
검사 단계				수입검사				구분 (Classification)				□개발신설 (Development) ■양산중 (Production) □설변 (Design Change) □금형재제작 (Mold Rebuilt) □기타 (Etc)							
										특기 사항 (Comments) 중합 판정 (Judgement) ☒ 적합품 (OK Part) ☐ 부적합품 (NG Part) LOT 크기 (Quantity) 54,770 pcs 검사 일자 (Date of Inspection) 2026.08.27. 검사 원 (Inspector) 우리하이피 김영란									
측정 단위 : mm (Measuring Unit : mm) 하단은 고객 기록란										측정기명 (Measuring Instrument) TM Toolmakers Microscope DC Digimatic Calipers PG Pin Gauge RD reflection densitometer MM Micro Meter HG Height Gauge TC Thickness&Coating Measurement System DP Dyne pen									
순번 (NO)	검사 항목 (Inspection Method)			규격 (Specification)			측정기 (Measuring Instrument)			x1 (Sample 1)	x2 (Sample 2)	x3 (Sample 3)	x4 (Sample 4)	x5 (Sample 5)	Sample SIZE	판정 (Judgement)			
1	외관			압록, 변색, 이물 없을것 KS A ISO 2859-1 일반검사 수준 G-2 AQL=0.1			육안			OK	OK	OK	OK	OK	500	OK			
2	도금두께			3.0 ~ 6.0 μm			TC			3.255	3.261	3.307	3.272	3.282	5	OK			
3	Reflection Density			0.65 ~ 0.95			RD			0.82	0.83	0.84	0.81	0.79	5	OK			
4	에너지펜 TEST NO.36			끊김, 뭉침 없을것			DP			OK	OK	OK	OK	OK	5	OK			
5	CROSS Cutting			개별 격자 1mm 이 내 20% 이하일것			육안			OK	OK	OK	OK	OK	5	OK			
6																			
7																			
8																			

고객명: 한빛티앤아이


품명 : Heat Spreader 27mm LOT NO : 260827-01 DATE : 26.08.27.

No	μm Ni	Ni	tolerance
1	3.255	3.244	3.275 3.307
2	3.261		
3	3.307		
4	3.272		
5	3.282		
Mean	3.275		
S.Dev	0.020		



FUNC: MEASURE
COL : 0.100 mm

$\frac{\text{Ni}}{\text{Cu}}$

SEC : 20 Sec

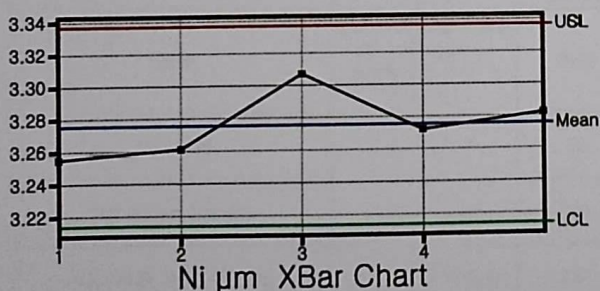

도금원소 : Ni//Cu
측정값 개수 5
최대값 3.307
최소값 3.255
범위 0.052
평균값 3.275
표준편차 0.020
변동계수 0.625

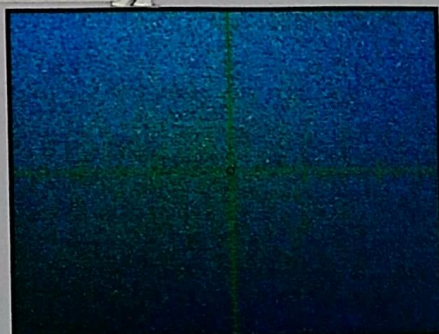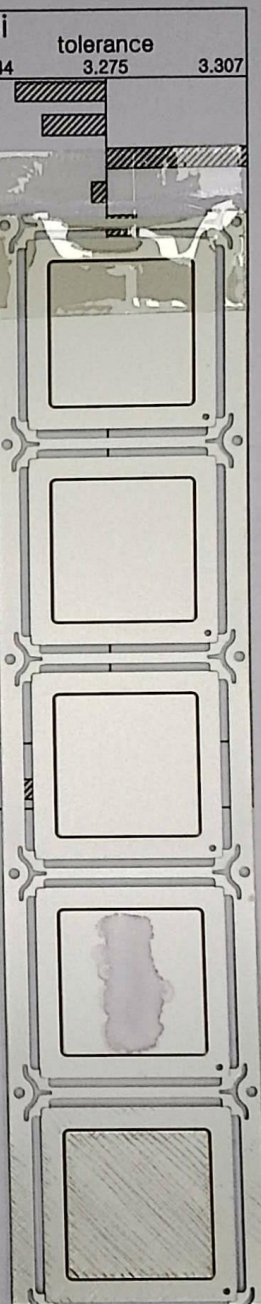

우리하이피(주)