

Temperature-density dependent hidden order of amorphous carbon

Yutao Liu, Tinghong Gao*, Qingquan Xiao, Yunjun Ruan, Qian Chen, Bei Wang, Jin Huang

Industry and Education Combination Innovation Platform of Intelligent Manufacturing and Graduate Joint Training Base, College of Big Data and Information Engineering, Guizhou University, Guiyang 550025, China

***Corresponding author Email: gaotinghong@sina.com**

Abstract:

The microscopic structure of amorphous carbon is often extremely complex, and its underlying topological order has long remained unclear. In this study, we constructed a high-precision machine learning-based neuroevolution potential and performed large-scale molecular dynamics simulations of the annealing process of amorphous carbon under various temperature and density conditions. We systematically proposed and validated nine representative amorphous carbon structures. By calculating X-ray diffraction patterns and structure factors, we analyzed in detail the topological differences among these structures. Based on these results, a temperature–density phase diagram of amorphous carbon was constructed, clearly identifying two topological phase boundaries with discontinuous structural transitions, thereby revealing hidden order obscured by structural disorder. The phase diagram reveals that temperature serves as an independent topological order parameter, challenging the traditional view that density alone governs phase transitions in amorphous carbon. Moreover, the critical temperature increases approximately linearly with increasing density. Furthermore, the diagram uncovers two distinct transformation pathways, with high-density disordered graphene network and paracrystalline diamond structures serving as intermediate states. Additionally, pressure-controlled simulations reveal asymmetric nucleation behavior during the formation and decomposition of the diamond phase. These findings offer a new theoretical perspective on the hidden order and microstructural features of amorphous carbon.

Keywords: amorphous carbon, machine learning potential, molecular dynamics, topological structure, phase diagram

1. Introduction

Amorphous solids are materials that lack the long-range periodic order characteristic of crystals^{1, 2}. Consequently, clear Bragg peaks are seldom observed in their diffraction patterns, making precise identification of their microscopic structure extremely challenging³. As a member of this class, amorphous carbon exhibits even more complex and elusive structural features because carbon atoms can simultaneously adopt sp , sp^2 , and sp^3 hybridizations^{4, 5}. In the 1940s, Franklin's discovery of glassy carbon while studying coal carbonization products ignited widespread interest in amorphous carbon research⁶. Even today, however, structural characterization techniques remain limited: commonly used Raman spectroscopy, X-ray diffraction (XRD), and nuclear magnetic resonance (NMR) cannot directly resolve the atomic arrangement inside amorphous carbon. Although high-resolution transmission electron microscopy (HRTEM) can reveal locally ordered domains—such as diamond-like lattices on the ~ 1 nm scale—the overall atomic-scale arrangement and its underlying principles have yet to be clearly elucidated⁷.

In recent years, the successful synthesis of various amorphous carbon structures has significantly advanced research in the field. For example, Tian et al. fabricated amorphous monolayer carbon (AMC) using a laser-assisted deposition method, elucidating the relationship between its microscopic structure and electrical conductivity⁸. The development of high-pressure techniques has also confirmed the transformation of tetrahedral amorphous carbon (rich in sp^3 bonding) and sp^2 glassy carbon into sp^2 – sp^3 hybrid amorphous carbon^{9, 10}. Tang et al. successfully synthesized paracrystalline diamond (p-D) using face-centered cubic C_{60} as a precursor, providing important evidence for structural continuity between crystalline and amorphous carbon phases¹¹. In addition, Hu et al. developed an onion-like amorphous carbon structure embedded within a disordered graphene network (DGN), which exhibited excellent electrical conductivity¹². Shang et al. synthesized bulk amorphous carbon composed almost entirely of sp^3 bonds under high-temperature and high-pressure conditions, yielding a material with exceptional properties comparable to diamond¹³.

The highly disordered nature of amorphous carbon arises from topological variations at the atomic scale, formed by different crystalline allotropes of carbon^{4, 14–16}. Although both short-

range and medium-range order have been commonly observed, the fundamental laws underlying atomic arrangements remain an unresolved scientific challenge¹⁷⁻¹⁹. Recently, Zhu et al. performed molecular dynamics (MD) simulations using the traditional empirical EDIP potential and established a density-dependent topological phase diagram of amorphous carbon., revealing for the first time the possible existence of hidden topological order in these materials²⁰. However, due to the limited accuracy of empirical potentials in predicting experimentally observed sp^3/sp^2 ratios, the reliability of such results remains uncertain. Moreover, temperature plays a crucial role in the formation of amorphous carbon structures²¹⁻²⁵, and constructing phase diagrams based solely on density while neglecting temperature effects clearly omits key information. Therefore, exploring the hidden topological order in amorphous carbon from the two physical dimensions of temperature and density is of great significance for comprehensively understanding this complex system.

In this study, we developed a machine learning-based neuroevolution potential (NEP) and employed molecular dynamics (MD) simulations to investigate the annealing of amorphous carbon under varying temperature and density conditions. A total of nine representative amorphous carbon structures were identified, and their microscopic topological features were systematically analyzed through calculations of X-ray diffraction (XRD) patterns and structure factors. More importantly, we constructed a temperature–density topological phase diagram of amorphous carbon, uncovering the underlying principles governing structural formation under different thermodynamic conditions. A clear linear relationship was observed between critical temperature and density. Furthermore, we thoroughly examined the structural transitions of amorphous carbon under high-temperature and high-pressure conditions, providing valuable theoretical support for the synthesis, property tuning, and broader application of amorphous carbon materials.

2. Results and Discussion

Machine learning potentials (MLPs) is an emerging and powerful approach for accurately simulating material properties that are consistent with those observed in experiments²⁶⁻²⁸. The core idea behind this method is to train machine learning (ML) models on large datasets of atomic configurations, which are typically labeled with energies, atomic forces, and virials calculated using first-principles methods such as density functional theory (DFT)²⁹. Once

trained, MLPs can perform MD simulations with computational efficiency comparable to empirical potentials while achieving the predictive accuracy of DFT. However, constructing high-quality and highly diverse training datasets remains one of the major challenges in MLP development. We constructed a dataset for carbon annealing simulations, comprising a total of 7,889 structures. The distribution of the dataset after dimensionality reduction using t-distributed stochastic neighbor embedding (t-SNE)³⁰ is shown in Fig. 1a, with detailed construction procedures provided in Table S1. Each point represents an individual atomic structure, whose position is determined by structural descriptors of its local atomic environment. The Fig.1a clearly shows that structurally similar data points exhibit obvious clustering, while dissimilar structures are well-separated, indicating that the dataset possesses good diversity and high-quality structural descriptors.

The NEP framework was employed to train the dataset and develop a MLP specifically designed for simulating the annealing process of amorphous carbon^{31, 32}. The accuracy of the NEP framework has been well demonstrated in previous studies on complex systems such as short-range order in amorphous alloys³³, lattice thermal conductivity³⁴, thermodynamic properties of water and ice³⁵, and structural stability of gold nanoclusters confined in zeolites³⁶. The training results are shown in Fig. 1b. The final root mean square errors (RMSE) for energy and forces on the training set reached 49.02 meV/atom and 565.5 meV/Å, respectively, while the corresponding values on the test set were 46.82 meV/atom and 561.32 meV/Å. These errors are comparable to, or even lower than, those reported for previous carbon-related MLPs³⁷⁻³⁹, indicating that the NEP achieves a level of accuracy highly consistent with DFT calculations. The dataset also covers a wide range of energies and forces, ensuring the stability of NEP-based MD simulations under diverse conditions. Moreover, the achieved fitting accuracy is comparable to existing studies, validating the choice of hyperparameters used in training (see Table S2). The evolution of the loss functions over training steps and the virial fitting performance are shown in Figs. S1, respectively.

To further assess the accuracy of the trained NEP, we performed a 15 ps relaxation simulation of an amorphous carbon system with a density of 3 g/cm³ at 4000 K, and calculated the radial distribution function (RDF)⁴⁰, as shown in Fig. 1c. The NEP-simulated RDF closely matches the DFT results, confirming that NEP-driven MD simulations can reliably reproduce structural features consistent with DFT. In addition, we conducted structural optimizations and static energy calculations for diamond structures with a range of lattice constants, generating

energy–volume (E – V) curves (Fig. 1d). The results show that NEP and DFT exhibit excellent agreement in describing the strain behavior of diamond structures. Fig. 1e further compares the sp^3 content at different densities calculated using various methods. The NEP-predicted sp^3 fractions at 4000 K not only align well with experimental values^{22, 41, 42} but are also very close to DFT predictions, whereas traditional empirical potentials⁴³ (e.g., EDIP, Tersoff, and Brenner) significantly underestimate the experimentally observed sp^3 content. Therefore, the NEP developed in this study demonstrates high accuracy and reliability in simulating the annealing behavior of amorphous carbon.

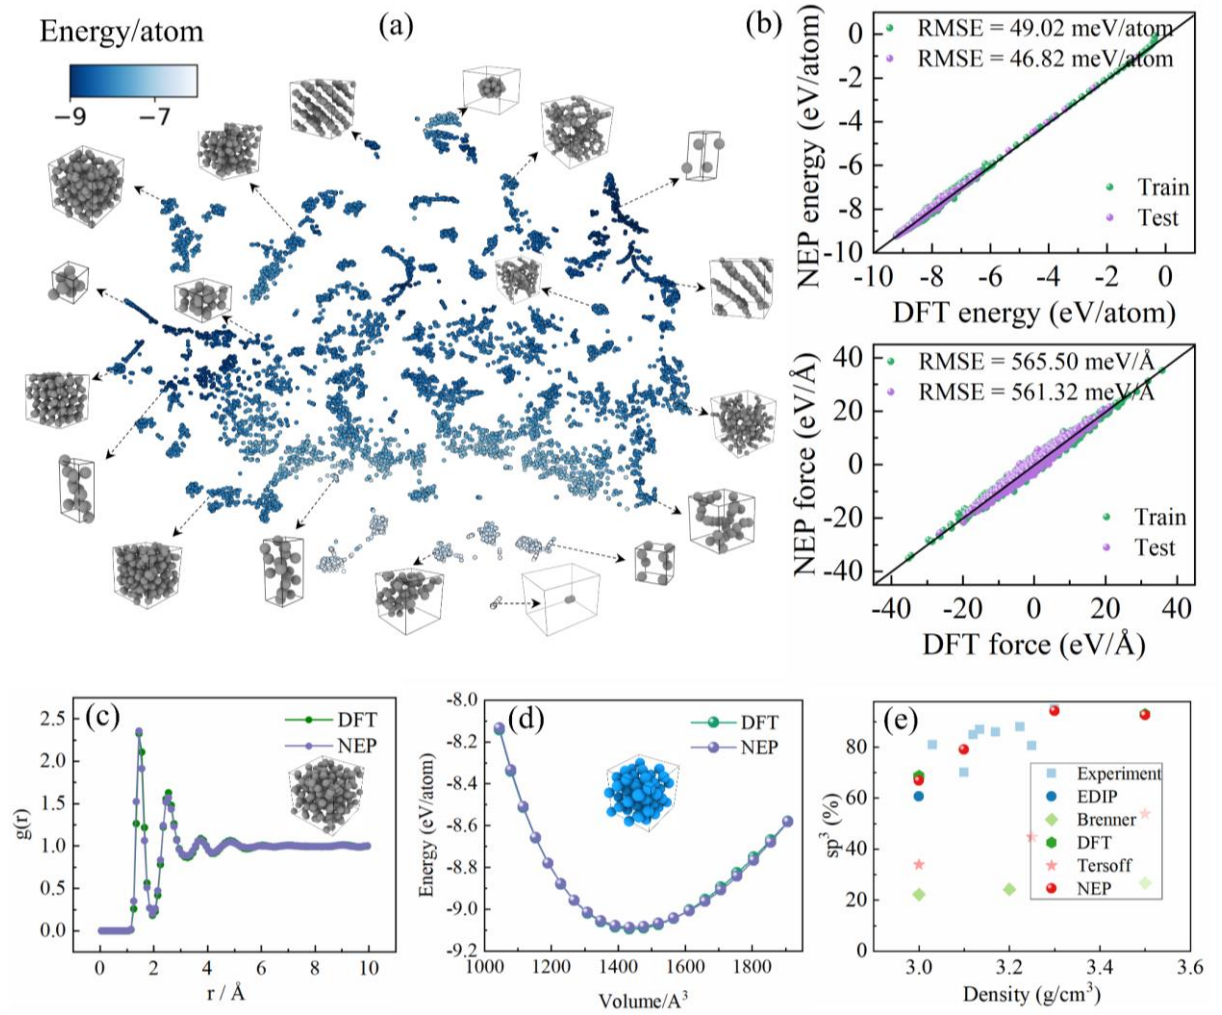


Fig. 1 Training and validation results of the NEP. (a) A schematic visualization of the dataset, where each point represents a carbon structure and is colored based on its average atomic energy. (b) Training results for energy (top) and forces (bottom). (c) Comparison of RDF obtained from 15 ps isothermal simulations at 4000 K for a 216-atom amorphous carbon system, driven by DFT and the NEP, respectively. (d) E – V curves of diamond structures under different strain conditions. (e) Comparison of the sp^3 fraction in amorphous carbon calculated by different methods, showing good agreement between NEP, experimental data, and DFT results.

Using the trained NEP, we performed systematic large-scale annealing MD simulations of amorphous carbon by adjusting temperature and density. Fig. 2 presents nine representative amorphous carbon structures obtained from different conditions. In Fig. 2a, a widely distributed DGN forms a three-dimensional, disordered, and porous carbon framework. Graphene sheets are connected via folding, stacking, or covalent bonding to form a non-periodic pore network, exhibiting a high degree of topological randomness. Previous studies have shown that the pore size of this structure decreases monotonically with increasing density³⁹. Due to the folding of graphene sheets, a large number of voids are formed experimentally, with porosity reaching up to 99.7 % and a specific surface area as high as 850 m²/g⁴⁴. We performed a statistical analysis of the ring structures in several typical DGN models (Fig. S2). The results indicate that the carbon rings predominantly consist of 5-, 6-, 7-, and 8-membered rings, with 6-membered rings being the most abundant. This suggests that the short-range order originates from hexagonal honeycomb-like configurations, in agreement with previous literature²⁰. Martin et al. have pointed out that the topology of DGNs is mainly composed of saddle-shaped graphene nanoflakes with negative curvature, rich in out-of-plane topological defects⁴⁵. Our simulations further show that all DGN structures have a sp² bonding fraction exceeding 96% (see Fig. S2), which is in excellent agreement with experimental results obtained via electron energy loss spectroscopy (EELS)⁴⁶.

With increasing density, the graphene sheets formed under high-temperature conditions become compressed, resulting in high-density DGN (HD DGN, Fig. 2b). These structures are characterized by graphene sheets folded and stacked along specific directions, partially exhibiting parallel alignment, but still dominated by large, continuous folded regions. At slightly lower temperatures, some graphene sheets appear as fragmented domains, which we define as discontinuous DGN (Fig. 2c). In this structure, each nanoscale fragment can be viewed as a structural unit composed of several carbon rings, and the local microstructure is significantly distorted due to sp²–sp³ hybridization. The formation of discontinuous DGNs is attributed to the inability of graphene sheets in multiple orientations to overcome energy barriers and rearrange into a unified low-energy structure at lower temperatures. In Fig. S3, we show the specific distribution of carbon ring types in this structure, which exhibits a significantly higher proportion of non-hexagonal rings compared to the 6-membered-ring-

dominated configuration in conventional DGN. These short and partially aligned graphene sheets can be regarded as graphitic nuclei in the formation process of glassy carbon, making them an ideal structural model for this material^{47, 48}. At even higher temperatures and densities, a large number of more or less parallel graphene sheets begin to form within the system. Although some overlapping still exists, the structure as a whole lacks long-range three-dimensional order. We define this structure as amorphous graphite (a-G, Fig. 2d). The formation mechanism of a-G originates from the system's ability to overcome energy barriers at elevated temperatures, enabling the development of locally larger graphitic domains.

When the system density increases to approximately 2.9 g/cm³, the proportion of sp³ bonds rises significantly. At lower temperatures, an amorphous Diaphite (a-DG) structure is formed (Fig. 2e), while at higher temperatures, crystalline Diaphite is generated (Fig. 2f). Diaphite was first discovered in meteorites and consists of intergrown diamond domains and graphitic layers⁴⁹. Notably, traditional empirical potentials (such as EDIP⁵⁰) have previously failed to reproduce Diaphite in simulations, whereas the NEP developed in this study successfully captures this experimentally observed structure, highlighting its superior descriptive capability. Diaphite exhibits excellent fracture toughness and ductility due to the coexistence of sp² and sp³ bonds⁴⁹. As the density further increases to the range of 3.3–3.5 g/cm³, the sp³ content rises sharply under extreme compression, and three types of diamond-like structures emerge in different temperature regimes: p-D (Fig. 2g), amorphous diamond (a-D, Fig. 2h), and nano-polycrystalline diamond (NPD, Fig. 2i). Recent experiments have successfully synthesized atomically a-D materials with densities exceeding 3 g/cm³, and p-D has been obtained from C₆₀ precursors within specific temperature windows under high-pressure conditions¹¹. Unlike crystalline or fully a-D, p-D exhibits pronounced medium-range order, extending across several atomic shells. The NEP approach proposed in this study is unified and easy to implement, capable of producing both a-D and p-D without the need to switch between different potential models. At sufficiently high temperatures and densities, diamond nuclei with various orientations continue to grow and eventually evolve into NPD.

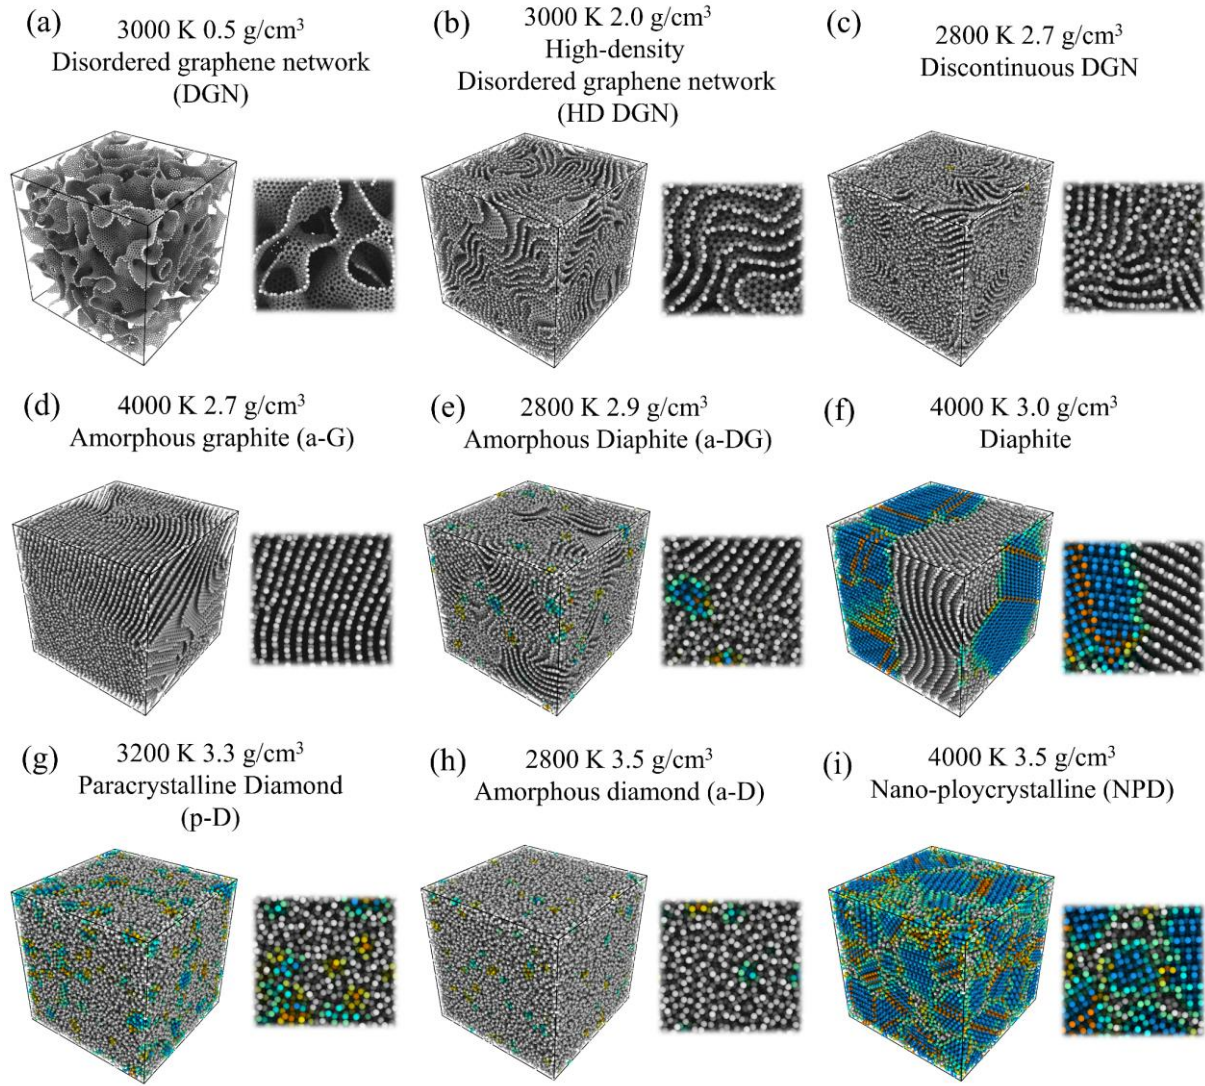


Fig. 2 Nine representative amorphous carbon structures formed under different temperature and density conditions. (a) DGN; (b) HD DGN; (c) Discontinuous DGN; (d) a-G; (e) a-DG; (f) Diaphite; (g) p-D; (h) a-D; (i) NPD. Atomic coloring is based on the “Identify Diamond Structure” function in OVITO⁵¹, with local magnified views shown alongside each structure. Detailed color classification is illustrated in Fig. S4.

To reveal the subtle differences among the nine amorphous carbon structures obtained, we calculated their XRD patterns and structure factors. Fig. 3a shows the XRD results for the different structures. Although DGN, HD DGN, Discontinuous DGN, and a-G all exhibit graphitic characteristics, their diffraction curves display significant variations. DGN shows no distinct peaks, consistent with previously reported simulation results⁴⁵. HD DGN presents a clear peak around $1.7 \text{ \AA}^{-1}$, closely matching the experimental XRD pattern of glassy carbon. Discontinuous DGN and a-G exhibit characteristic peaks at $2.07 \text{ \AA}^{-1}$ and $2.16 \text{ \AA}^{-1}$, respectively. It is noteworthy that the theoretical density of standard graphite is 2.26 g/cm^3 , with a

corresponding peak at $1.88 \text{ \AA}^{-1}$, whereas both Discontinuous DGN and a-G in our simulations reach densities of 2.7 g/cm^3 , significantly higher than graphite. This indicates that the material undergoes volumetric compression, resulting in reduced interlayer spacing between graphene sheets (see Fig. S5). Moreover, the broadened peak at $2.07 \text{ \AA}^{-1}$ in the Discontinuous DGN indicates a higher degree of disorder, similar to the a-DG structure, which exhibits extreme disorder due to the absence of diamond nuclei, showing only a weak diamond-related peak near $3.1 \text{ \AA}^{-1}$. Both Diaphite and NPD display characteristic diffraction peaks of crystalline diamond, including the (111), (220), and (311) planes¹¹. In NPD, the (220) and (311) peaks shift due to its higher density (3.5 g/cm^3); this shift is absent in NPD formed at a lower density of 3.3 g/cm^3 , as shown in Fig. S6. In the XRD pattern of Diaphite, a distinct peak splitting appears around $3.0 \text{ \AA}^{-1}$, attributed to the presence of large hexagonal diamond domains accompanied by twinning and defect-induced nucleation behavior⁵².

Furthermore, we performed Fourier transforms of the RDF to obtain structure factors⁵³, allowing for a deeper comparison of short-range order among the different structures (Fig. 3b). In the upper panel of Fig. 3b, DGN, HD DGN, and Discontinuous DGN exhibit clear differences in the low-Q region ($Q < 4 \text{ \AA}^{-1}$), indicating fundamental distinctions in their degrees of short-range order. The sharper peaks observed for HD DGN and Discontinuous DGN suggest more locally ordered structures. The middle panel of Fig. 3b shows the structure factor of Diaphite, which features significantly enhanced peaks at positions I_1 and I_2 , reflecting the formation of diamond-like structures with a high proportion of sp^3 bonding. In contrast, a-G and a-DG lack underlying crystalline frameworks, and their structure factor curves flatten beyond I_2 without distinct peaks, exhibiting typical amorphous characteristics. NPD displays pronounced features at both I_1 and I_2 , indicative of diamond nucleation. Notably, p-D and a-D have historically been difficult to distinguish due to their subtle structural differences. However, in this study, the high-precision MLP enables clear differentiation: p-D shows a slightly higher I_1 peak than I_2 , whereas a-D exhibits the opposite trend (lower panel of Fig. 3b). This observation is in excellent agreement with experimental results¹¹, further validating the accuracy of the potential in identifying microstructural features.

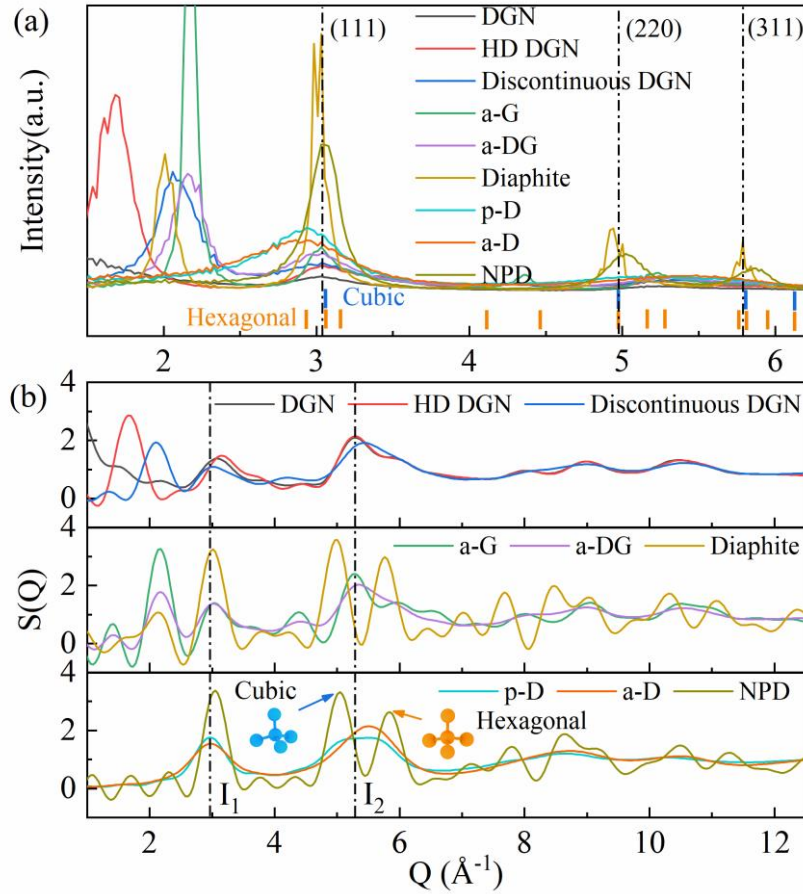


Fig. 3 Identification of nine different amorphous carbon structures. (a) Calculated XRD patterns, with short vertical lines below the curves indicating the diffraction peak positions of cubic and hexagonal diamond. (b) Structure factor.

To comprehensively illustrate the structural evolution of amorphous carbon under different temperature–density conditions, we constructed a **phase diagram** based on large-scale simulation results (Fig. 4a). Each symbol and its corresponding shaded area in the diagram represent a specific atomic topological structure. Overall, the phase diagram can be divided into three main regions: (I) graphite region, (II) transition region, and (III) diamond region. The simulation results indicate that the primary topological boundaries lie between $\rho \approx 2.8 \text{ g/cm}^3$ and $\rho \approx 3.2 \text{ g/cm}^3$, **which is in excellent agreement with experimentally reported⁵⁴**. Within the range of $\rho = 0.5\text{--}1.8 \text{ g/cm}^3$ and $T = 1500\text{--}4200 \text{ K}$, the phase diagram is dominated by the DGN structure; lower densities favor the folding of carbon atoms into graphene networks. These structures are characterized by abundant sp^2 bonds and large carbon rings, resulting in an overall porous morphology^{55, 56}. When $\rho < 2.7 \text{ g/cm}^3$ and $T < 2800 \text{ K}$, the annealed structures are primarily Discontinuous DGN, corresponding to the trapezoidal region in the diagram. As

temperature increases within the range of $\rho = 2.0\text{--}2.9 \text{ g/cm}^3$, the structural evolution follows a sequence from Discontinuous DGN $\rightarrow$ HD DGN $\rightarrow$ a-G. These findings indicate that temperature is the primary driving force for phase transitions, while changes in density reflect the macroscopic manifestation of topological ordering.

Therefore, two graphitization pathways (blue dashed line) can be identified in the phase diagram. Graphitization path 1 represents the direct transition from DGN to a-G, highlighting the density-driven effect: when $T \geq 2800 \text{ K}$ and $\rho > 1.8 \text{ g/cm}^3$, the structure evolves into a-G without intermediate states. Graphitization path 2 occurs in the $\rho \approx 2.0\text{--}2.7 \text{ g/cm}^3$ region, where, with increasing temperature, the system undergoes a sequential ordering process: Discontinuous DGN $\rightarrow$ HD DGN $\rightarrow$ a-G, revealing a temperature-induced stepwise transformation. When ρ lies between 2.8 and 3.1 g/cm^3 (Region II), the system exhibits a mixed graphitic/diamond-like topology. At lower temperatures ($\sim 3000 \text{ K}$), a-DG forms, and upon heating, the amorphous diamond domains crystallize into nanodiamonds, resulting in Diaphite. Further increasing the density to 2.9–3.5 g/cm^3 (Region III), a-D is formed at low temperatures ($\sim 3000 \text{ K}$); continued heating leads to the emergence of a p-D intermediate state, which eventually transforms into NPD. There are also two diamondization pathways in the diamond region (black dotted line): diamondization path 1 involves a direct Diaphite $\rightarrow$ NPD transition driven by increasing density at high temperatures, a path commonly observed in high-pressure experiments⁵⁷. Diamondization path 2 occurs at constant density through temperature elevation, following the sequence a-D $\rightarrow$ p-D $\rightarrow$ NPD, highlighting the role of p-D as a transitional phase, this crystallization pathway is also commonly seen in previous studies^{20, 39}. Fig. 4c shows the temperature–density distribution of the sp^3/sp^2 ratio: in the $\rho < 2.8 \text{ g/cm}^3$ region, deep blue indicates a very low sp^3 fraction, while for $\rho > 2.8 \text{ g/cm}^3$, the sharp increase in sp^3 bonding results in a gradual shift toward deep red, consistent with the structural analysis. It is expected that more precise physical parameters will be proposed in the future to distinguish between the nine types of amorphous carbon structures and to achieve a more accurate description of the phase diagram.

Nevertheless, this phase diagram reveals in detail correspondence between temperature–density conditions and the topological structures of amorphous carbon, prompting deeper reflection on the underlying physical principles. First, within specific density ranges—for

example, at a density of 2.7 g/cm^3 —Discontinuous DGN forms at 2800 K, while a-G forms at 4000 K. This indicates that temperature acts as a topological order parameter independent of density, which contrasts sharply with previously established density-dominated phase transition mechanisms^{20, 39}. Second, we observed that at each given density, the critical temperature separating two phases exhibits an approximately linear increase with increasing density (indicated by the red dashed lines in the Fig. 4(a)). Moreover, the slopes of these critical temperature curves appear to be similar. Since the slope reflects the topological reconstruction energy barrier, this suggests that higher densities require higher temperatures to induce phase transitions. This interpretation is supported by our calculations of atomic root mean square displacement (RMSD) for samples annealed at 3000 K across the density range of $0.5\text{--}3.5 \text{ g/cm}^3$. As shown in Fig. 4(c), at the same temperature, lower-density structures exhibit larger atomic RMSD due to more available free volume, whereas higher-density structures restrict atomic motion. Therefore, it can be inferred that higher temperatures are required at higher densities to drive atomic rearrangement in confined spaces. Additionally, the graphitization and diamondization paths appear to share structural similarities. In both cases, path 1 is driven by density, while path 2 is governed by temperature. Notably, both path 2 transformations involve intermediate phases—HD DGN and p-D, respectively. Finally, at 3.3 g/cm^3 and 3200 K, p-D forms at a unique triple point where a-DG, Diaphite, and NPD coexist. This special condition marks a topological three-phase equilibrium. Previous metadynamics simulations have also suggested that p-D formation occurs within a temperature window of 3000–4000 K²¹, aligning closely with experimentally observed values when interpreted within the Arrhenius framework⁵⁸; temperatures outside this range tend to yield either a-D or NPD. By decoding the phase transformation mechanisms of amorphous carbon in the temperature–density space, this study opens up further questions about how amorphous carbon structures dynamically evolve under realistic pressure-driven conditions.

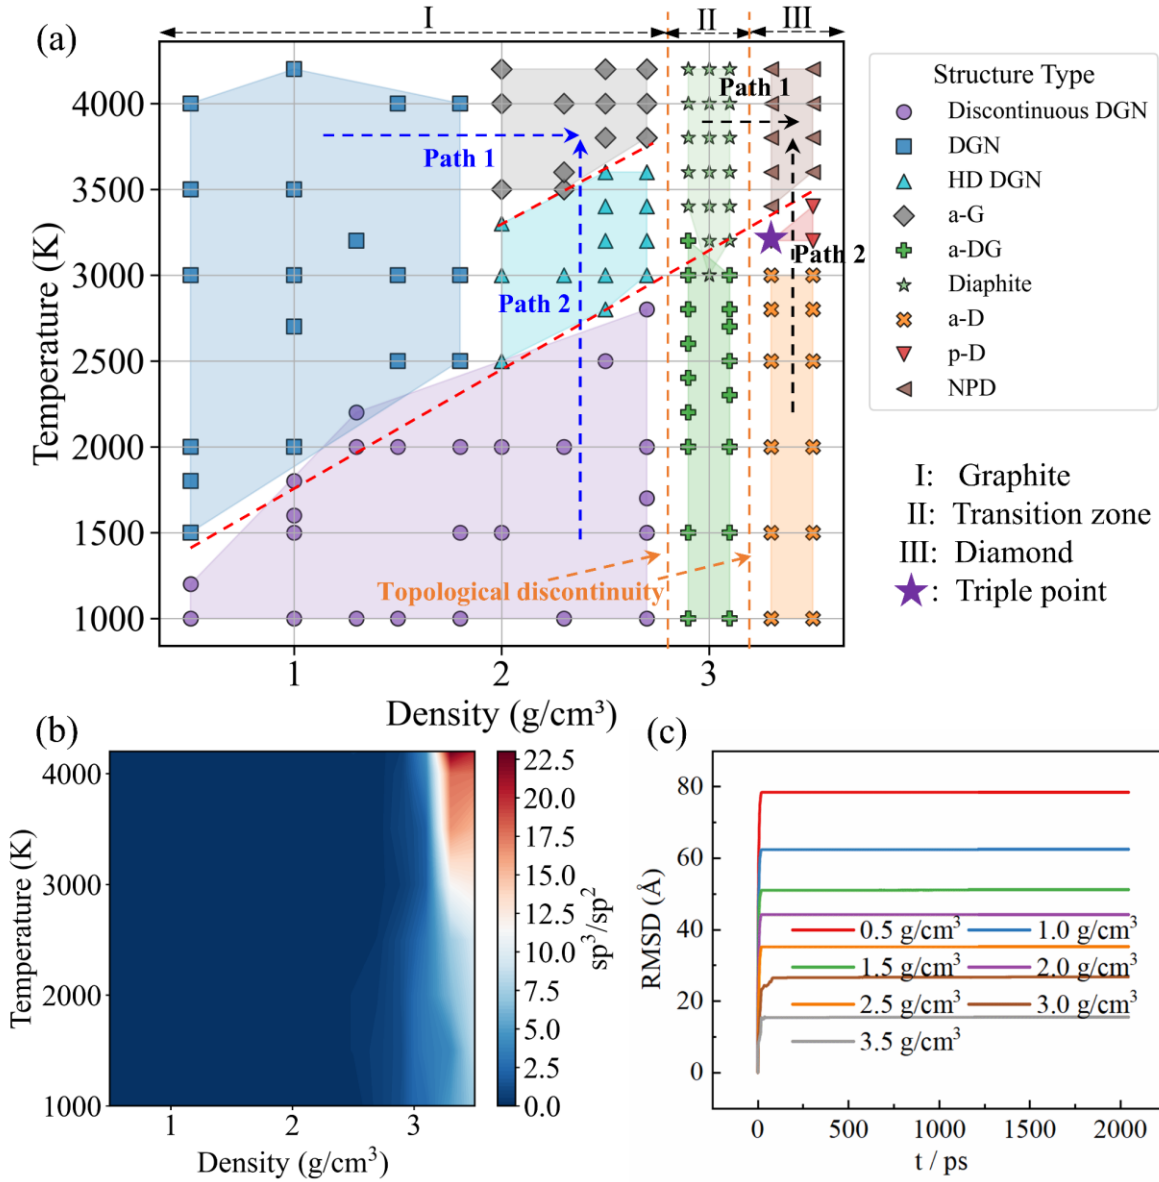


Fig. 4 (a) Temperature–density phase diagram of amorphous carbon. (b) Distribution map of the sp^3/sp^2 ratio formed under different temperature and density conditions. (c) Time evolution of the RMSD during isothermal annealing at 3000 K for amorphous carbon structures with varying densities.

As shown in Fig. 5, we achieved phase transitions between different amorphous carbon structures by tuning the applied pressure. The initial configuration was a DGN structure annealed at 3000 K with a density of 0.5 g/cm³. Fig. 5a presents the evolution of sp^2 and sp^3 atomic fractions, as well as crystalline atoms, under two target pressures: 40 GPa and 60 GPa. Since the evolution trends under both conditions are largely consistent, our analysis focuses on the results at 40 GPa. Based on the simulation settings, we can divide it into five stages.

In stage I, under an initial high temperature of 4000 K, no significant changes in physical

parameters were observed, indicating that the DGN structure exhibits excellent thermal stability under high-temperature conditions—consistent with experimental findings that carbon materials possess high-temperature resistance²⁵. Entering stage II, as the pressure gradually increases, the system undergoes complex structural evolution. Before 700 ps, the atomic fractions of sp^2 and sp^3 remain nearly unchanged (Fig. 5a, upper panel), with sp^2 bonds dominating. Although the pressure at this point has reached approximately 20 GPa and the density about 2.5 g/cm³ (Fig. 5b), the structure primarily transforms into HD DGN (Fig. 5c①). As the pressure continues to rise, the sp^2 fraction decreases sharply while the sp^3 fraction increases rapidly. By 882 ps, the system evolves into a mixed structure of graphitic fragments and amorphous tetrahedral carbon—a-DG (Fig. 5c②). The graphitic domains gradually collapse under further volumetric compression, and by 1000 ps, the system transitions into an a-D state, predominantly composed of tetrahedral structures (Fig. 5c③), with the sp^3 content reaching approximately 63 %. In stage III, crystalline atoms begin to appear, marking the onset of diamond nucleation. A p-D emerges at 1154 ps (Fig. 5c④), though it exists only briefly before rapidly crystallizing under thermal activation, eventually forming a stable NPD (Fig. 5c⑤). The system remains in this stable state for an extended period until entering stage IV. In stage IV, as the pressure is reduced while maintaining high temperature, the previously stable NPD nuclei begin to dissociate. The structure transforms into layered graphitic configurations, with a transient Diaphite phase appearing at 3004 ps (Fig. 5c⑥). This intermediate phase also exists for a short time before evolving into a Discontinuous DGN structure at 3013 ps (Fig. 5c⑦). Detailed descriptions of this transition process are provided in Fig. S7. Finally, in stage V, the system stabilizes into a DGN structure with a density of approximately 1.5 g/cm³ at 3750 ps (Fig. 5c⑧), which is slightly higher than the initial density of 0.5 g/cm³. The densities of all typical structures found in Fig. 5c are consistent with those shown in the phase diagram (Fig. 4a).

Throughout the entire phase transition process, all of the previously discussed eight structures were observed, except for a-G. This absence is mainly attributed to the initial structure being DGN: although some partially folded graphene sheets may align into parallel layered structures under pressure, their lifetime is too short to evolve into large-scale a-G domains. By tuning the applied pressure, we achieved a controllable phase transition from DGN

to diamond-dominated structures (p-D and NPD), highlighting the critical role of pressure in the topological reconstruction of amorphous carbon. A comparison between the 40 GPa and 60 GPa results reveals that during stage II, sp^3 atoms reach their peak concentration more quickly under 60 GPa (Fig. 5a, lower panel). However, the crystalline atom content in later stages is actually lower than that at 40 GPa—approximately 52 % versus 63 %. This suggests that high pressure alone is insufficient to overcome the nucleation barrier of amorphous carbon; additional thermal activation is required. Notably, although the applied pressure is symmetric, the processes of diamond nucleation and dissociation exhibit significant asymmetry. The system first undergoes a fully a-D before gradually crystallizing into diamond structures under the influence of temperature—a process corresponding to diamondization path 2 in Fig. 4a. Interestingly, along this path, the system's density remains nearly unchanged, which aligns well with the “temperature-dominated” nucleation mechanism discussed earlier in Fig. 4a. Previous studies have indicated that the transformation from graphite to diamond requires the assistance of nanoscale coherent interfaces to consume remaining graphite and complete the transition⁵⁷(i.e., Diamondization Path 1). This pathway was not observed in our simulations, likely due to the absence of a-G in the system. Under high temperatures, the short-timescale compression renders the DGNs unstable, making it prone to directly transform into an a-D structure. As a result, the phase transition pathway a-D → p-D → NPD emerges as the optimal crystallization route for the system. Upon pressure release and volume expansion, diamond tends to dissociate into graphitic layered structures under continued high-temperature conditions. This behavior is attributed to the lower free energy of graphite compared to diamond⁵⁹.

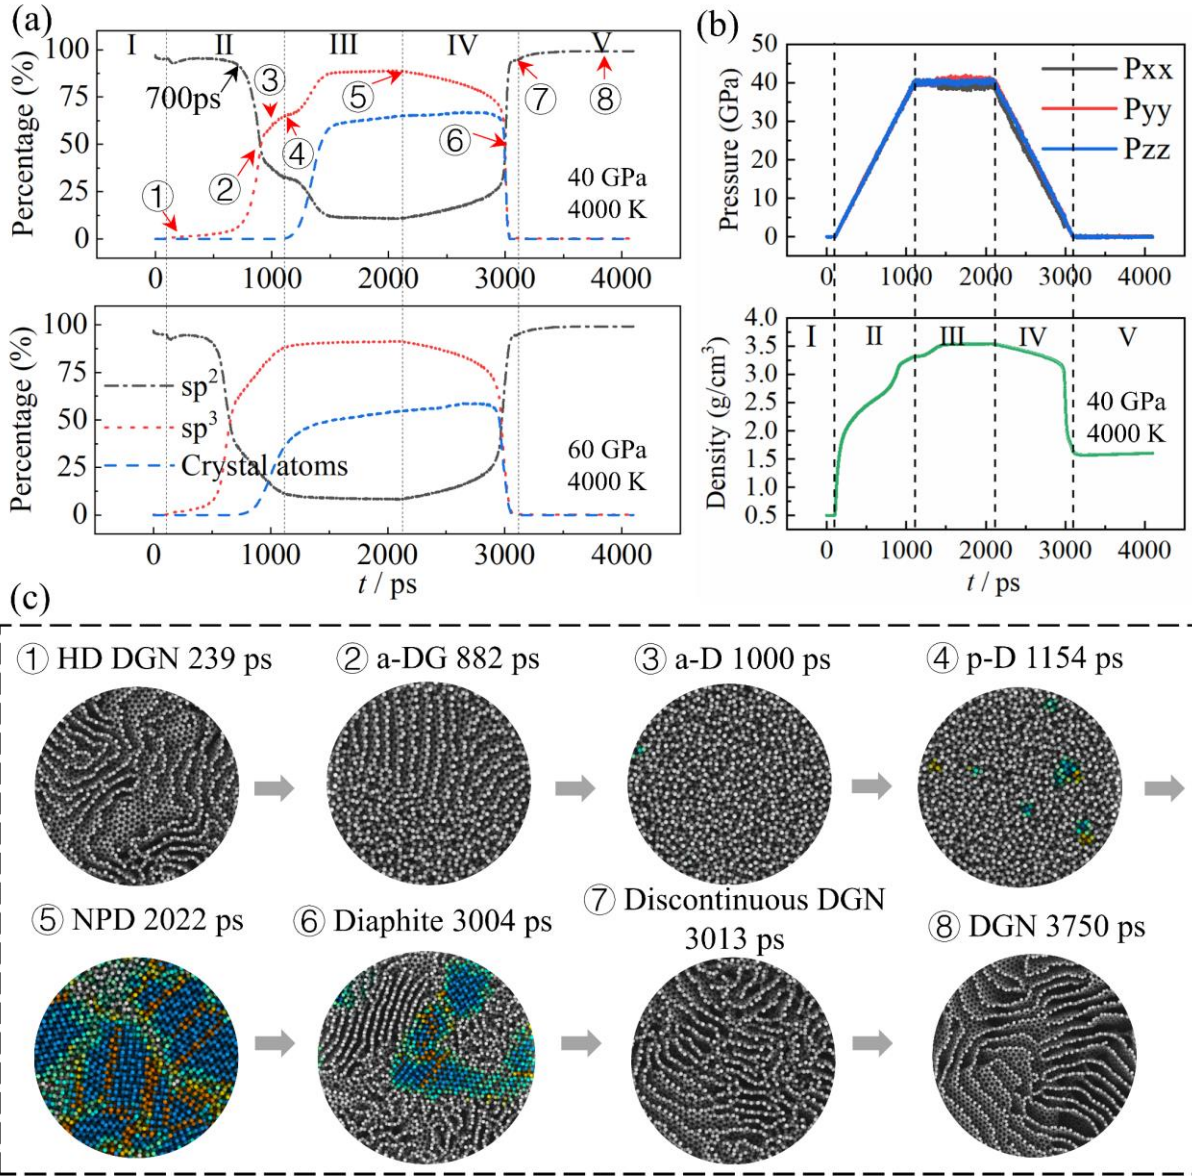


Fig. 5 Phase transitions between different amorphous carbon. (a) Evolution of sp^2 , sp^3 , and crystalline atom fractions during annealing under two target pressures, 40 GPa and 60 GPa. Crystalline atoms are defined as the sum of cubic and hexagonal diamond atoms, excluding first and second nearest neighbors. Stage I: Initial relaxation of the DGN structure at 4000 K for 100 ps; Stage II: Temperature held at 4000 K while pressure is gradually increased to 40 GPa over 1000 ps; Stage III: System relaxed at 4000 K and 40 GPa for an additional 1000 ps; Stage IV: Temperature maintained at 4000 K while pressure is released to 0 GPa; Stage V: Temperature reduced to 300 K under 0 GPa. (b) Time evolution of system pressure and density under the 40 GPa target pressure. (c) Structural snapshots at key time points during the phase transition, corresponding to the 40 GPa, 4000 K conditions shown in (a).

3. Conclusions

In summary, we employed the constructed NEP to accurately simulate the annealing process of carbon across a broad temperature range (1000–4200 K) and density range (0.5–3.5 g/cm³). Through these simulations, we identified nine representative amorphous carbon structures: DGN, HD DGN, Discontinuous DGN, a-G, a-DG, Diaphite, p-D, a-D, and NPD. By calculating the XRD patterns and structure factors of these structures and comparing them with experimental data, we observed strong agreement. Based on these results, we systematically analyzed the topological differences among the nine structures and further constructed a comprehensive amorphous carbon phase diagram. The phase diagram reveals two topologically discontinuous phase boundaries, indicating the existence of **hidden order** within amorphous carbon. The main findings include: (1) temperature serves as a topological **order** parameter independent of density, which **contrasts significantly with the previously held view that phase transitions are primarily density-driven**; (2) at specific densities, the critical temperature between two phases increases approximately linearly with density, and the critical temperature curves exhibit similar slopes across different densities; (3) in both the graphitic and diamond-like regions, there exist two distinct phase transition pathways, each involving an intermediate phase—HD DGN and p-D, respectively. We further propose that p-D acts as a critical point at the intersection of three phases, providing theoretical guidance for experimental synthesis routes. Based on the phase diagram, we investigated the transformation processes between different structures by tuning the system pressure and discovered asymmetric nucleation behavior during the formation and decomposition of diamond. These findings offer a theoretical foundation and practical guidance for the controlled synthesis of amorphous carbon materials.

4. Methods

All MD simulations were performed using the open-source GPUMD code⁶⁰. The initial models were constructed by randomly placing 100,000 carbon atoms into simulation boxes of varying volumes to achieve system densities ranging from 0.5 to 3.5 g/cm³. The systems were then equilibrated at 6000 K for 50 ps under isothermal conditions to ensure sufficient mixing and structural relaxation. After equilibration, the **system was rapidly quenched** to a specific target temperature within the range of 1000–4200 K, followed by 2000 ps of isothermal

annealing at that temperature. Subsequently, the systems were rapidly cooled to 300 K within 10 ps and further equilibrated at 300 K for 50 ps to obtain the final stable carbon structures. All simulations without pressure variation were conducted in the NVT ensemble⁶¹. For the pressure-induced structural transitions, the initial configuration was taken from the final structure annealed at 3000 K with a density of 0.5 g/cm³. The structure was first equilibrated at 4000 K for 20 ps, after which the pressure was gradually increased to 40 or 60 GPa over 1000 ps. The system was then held at the target pressure and 4000 K for an additional 1000 ps of isothermal relaxation. Afterward, the pressure was gradually released to 0 GPa over 1000 ps. Finally, the temperature was decreased from 4000 K to 300 K within another 1000 ps. The entire pressure-varying simulation was carried out using the Martyna–Tuckerman–Tobias–Klein (MTTK) ensemble^{62, 63}.

Acknowledgements

This paper was supported by the the National Natural Science Foundation of China (Grant Nos. 52262021, and 51761004), Industry and Education Combination Innovation Platform of Intelligent Manufacturing and Graduate Joint Training Base at Guizhou University (Grant No. 2020-520000-83-01-324061), the Guizhou Province Science and Technology Fund, China (Grant Nos. ZK[2021]051, ZK[2023]013), High-level Creative Talent Training Program in Guizhou Province of China (Grant No. [2015]4015), and Guizhou Engineering Research Center for smart services (Grant No. 2203-520102-04-04-298868).

Conflict of Interest

The authors declare no conflict of interest.

Data Availability Statement

To ensure the reproducibility of the machine learning-based NEP in this study, the dataset and potential function files will be made publicly available through an open-access repository: <https://github.com/lytgz/Annealing-of-amorphous-carbon/tree/master>.

References

- [1] Berthier, L., Biroli, G., Manning, L., Zamponi, F. Yielding and plasticity in amorphous solids. *Nat. Rev. Phys.*, 1-18 (2025).
- [2] He, P., Liu, J.-X., Wu, H., Wang, Z. Floquet amorphous topological orders in a one-dimensional Rydberg glass. *Commun. Phys.* **8**, 1-7 (2025).
- [3] Elliott, S.R. Medium-range structural order in covalent amorphous solids. *Nature* **354**, 445-452 (1991).
- [4] Robertson, J. Amorphous carbon. *Adv. Phys.* **35**, 317-374 (1986).
- [5] Kim, I.S., Shim, C.E., Kim, S.W., Lee, C.S., Kwon, J., Byun, K.E., Jeong, U. Amorphous carbon films for electronic applications. *Adv. Mater.* **35**, 2204912 (2023).
- [6] Bangham, D., Franklin, R.E. Thermal expansion of coals and carbonised coals. *Trans. Faraday Soc.* **42**, B289-B294 (1946).
- [7] Ooe, K., Seki, T., Yoshida, K., Kohno, Y., Ikuhara, Y., Shibata, N. Direct imaging of local atomic structures in zeolite using optimum bright-field scanning transmission electron microscopy. *Sci. Adv.* **9**, eadf6865 (2023).
- [8] Tian, H., Ma, Y., Li, Z., Cheng, M., Ning, S., Han, E., Xu, M., Zhang, P.-F., Zhao, K., Li, R. Disorder-tuned conductivity in amorphous monolayer carbon. *Nature* **615**, 56-61 (2023).
- [9] McMillan, P.F. New materials from high-pressure experiments. *Nat. Mater.* **1**, 19-25 (2002).
- [10] Lin, Y., Zhang, L., Mao, H.-k., Chow, P., Xiao, Y., Baldini, M., Shu, J., Mao, W.L. Amorphous diamond: a high-pressure superhard carbon allotrope. *Phys. Rev. Lett.* **107**, 175504 (2011).
- [11] Tang, H., Yuan, X., Cheng, Y., Fei, H., Liu, F., Liang, T., Zeng, Z., Ishii, T., Wang, M.-S., Katsura, T. Synthesis of paracrystalline diamond. *Nature* **599**, 605-610 (2021).
- [12] Hu, M., Pang, J., Tang, Y., Ma, M., Huang, J., Li, P., Shi, L., Zhong, Y., He, J., Ding, J. Bulk Amorphous Carbon with Lightweight, High Strength, and Electrical Conductivity: Onion-Like Carbon Structures Embedded in Disordered Graphene Networks. *Inorg. Chem.*, **64**, 11786-11795 (2025).
- [13] Shang, Y., Liu, Z., Dong, J., Yao, M., Yang, Z., Li, Q., Zhai, C., Shen, F., Hou, X., Wang, L. Ultrahard bulk amorphous carbon from collapsed fullerene. *Nature* **599**, 599-604 (2021).
- [14] Kelires, P.C. Structural properties and energetics of amorphous forms of carbon. *Physical Review B* **47**, 1829 (1993).
- [15] Deringer, V.L., Csányi, G., Proserpio, D.M. Extracting crystal chemistry from amorphous carbon structures. *ChemPhysChem* **18**, 873-877 (2017).
- [16] Banerjee, D., Mukherjee, S., Chattopadhyay, K. Controlling the surface topology and hence the hydrophobicity of amorphous carbon thin films. *Carbon* **48**, 1025-1031 (2010).
- [17] Joo, W.-J., Lee, J.-H., Jang, Y., Kang, S.-G., Kwon, Y.-N., Chung, J., Lee, S., Kim, C., Kim, T.-H., Yang, C.-W. Realization of continuous Zachariasen carbon monolayer. *Sci. Adv.* **3**, e1601821 (2017).
- [18] Toh, C.-T., Zhang, H., Lin, J., Mayorov, A.S., Wang, Y.-P., Orofeo, C.M., Ferry, D.B., Andersen, H., Kakenov, N., Guo, Z. Synthesis and properties of free-standing monolayer amorphous carbon. *Nature* **577**, 199-203 (2020).
- [19] Zhang, D., Peng, L., Li, X., Yi, P., Lai, X. Controlling the nucleation and growth orientation of nanocrystalline carbon films during plasma-assisted deposition: a reactive molecular dynamics/Monte Carlo study. *J. Am. Chem. Soc.* **142**, 2617-2627 (2020).
- [20] Zhu, Y., Fang, Z., Zhang, Z., Wu, H. Discontinuous phase diagram of amorphous carbons. *Natl. Sci. Rev.* **11**, nwae051 (2024).
- [21] Zhang, Z., Fang, Z., Wu, H., Zhu, Y. Temperature-dependent paracrystalline nucleation in atomically

disordered diamonds. *Nano Lett.* **24**, 312-318 (2023).

[22] Zeng, Z., Yang, L., Zeng, Q., Lou, H., Sheng, H., Wen, J., Miller, D.J., Meng, Y., Yang, W., Mao, W.L. Synthesis of quenchable amorphous diamond. *Nat. Commun.* **8**, 322 (2017).

[23] Zhang, S., Jiang, G., Yang, Y., Li, H., Yan, F., Yan, M., Zhang, Y. Annealing effect on microstructure of novel Ti doped DLC multilayer films. *Coatings* **13**, 833 (2023).

[24] Kim, J.-H., Lee, J.-H., Kang, Y.-S., Jang, K.-T., Im, J., Seong, M.-J. Evolution of amorphous carbon films into nano-crystalline graphite with increasing growth temperature in plasma-enhanced chemical vapor deposition. *Curr. Appl Phys.* **23**, 52-56 (2021).

[25] Rouhani, M., Hong, F.C.-N., Jeng, Y.-R. In-situ thermal stability analysis of amorphous carbon films with different sp³ content. *Carbon* **130**, 401-409 (2018).

[26] Omranpour, A., Elsner, J., Lausch, K.N., Behler, J. Machine learning potentials for heterogeneous catalysis. *ACS Catal.* **15**, 1616-1634 (2025).

[27] Liu, Y., Meng, H., Zhu, Z., Yu, H., Zhuang, L., Chu, Y. Predicting Mechanical and Thermal Properties of High-Entropy Ceramics via Transferable Machine-Learning-Potential-Based Molecular Dynamics. *Adv. Funct. Mater.* **35**, 2418802 (2025).

[28] Loew, A., Sun, D., Wang, H.-C., Botti, S., Marques, M.A. Universal machine learning interatomic potentials are ready for phonons. *npj Comput. Mater.* **11**, 1-8 (2025).

[29] Orio, M., Pantazis, D.A., Neese, F. Density functional theory. *Photosynth. Res.* **102**, 443-453 (2009).

[30] Belkina, A.C., Ciccolella, C.O., Anno, R., Halpert, R., Spidlen, J., Snyder-Cappione, J.E. Automated optimized parameters for T-distributed stochastic neighbor embedding improve visualization and analysis of large datasets. *Nat. Commun.* **10**, 5415 (2019).

[31] Fan, Z., Zeng, Z., Zhang, C., Wang, Y., Song, K., Dong, H., Chen, Y., Ala-Nissila, T. Neuroevolution machine learning potentials: Combining high accuracy and low cost in atomistic simulations and application to heat transport. *Physical Review B* **104**, 104309 (2021).

[32] Fan, Z. Improving the accuracy of the neuroevolution machine learning potential for multi-component systems. *J. Phys.: Condens. Matter* **34**, 125902 (2022).

[33] Zhao, R., Wang, S., Kong, Z., Xu, Y., Fu, K., Peng, P., Wu, C. Development of a neuroevolution machine learning potential of Pd-Cu-Ni-P alloys. *Mater. Des.* **231**, 112012 (2023).

[34] Folkner, D.A., Chen, Z., Barbalinardo, G., Knoop, F., Donadio, D. Elastic moduli and thermal conductivity of quantum materials at finite temperature. *J. Appl. Phys.* **136**, (2024).

[35] Chen, Z., Berrens, M.L., Chan, K.-T., Fan, Z., Donadio, D. Thermodynamics of water and ice from a fast and scalable first-principles neuroevolution potential. *Journal of Chemical & Engineering Data* **69**, 128-140 (2023).

[36] Sonti, S., Sun, C., Chen, Z., Kowalski, R.M., Kowalski, J.S., Donadio, D., Ahn, S.-H., Kulkarni, A.R. Stability and Dynamics of Zeolite-Confined Gold Nanoclusters. *J. Chem. Theory Comput.* **20**, 8261-8269 (2024).

[37] Fan, Z., Xiao, Y., Wang, Y., Ying, P., Chen, S., Dong, H. Combining linear-scaling quantum transport and machine-learning molecular dynamics to study thermal and electronic transports in complex materials. *J. Phys.: Condens. Matter* **36**, 245901 (2024).

[38] Dong, H., Cao, C., Ying, P., Fan, Z., Qian, P., Su, Y. Anisotropic and high thermal conductivity in monolayer quasi-hexagonal fullerene: A comparative study against bulk phase fullerene. *Int. J. Heat Mass Transfer* **206**, 123943 (2023).

[39] Wang, Y., Fan, Z., Qian, P., Caro, M.A., Ala-Nissila, T. Density dependence of thermal conductivity in nanoporous and amorphous carbon with machine-learned molecular dynamics. *Physical Review B* **111**,

094205 (2025).

[40] Kirkwood, J.G., Boggs, E.M. The radial distribution function in liquids. *J. Chem. Phys.* **10**, 394-402 (1942).

[41] LiBassi, A., Ferrari, A., Stolojan, V., Tanner, B., Robertson, J., Brown, L. Density, sp³ content and internal layering of DLC films by X-ray reflectivity and electron energy loss spectroscopy. *Diamond Relat. Mater.* **9**, 771-776 (2000).

[42] Li, Z., Wang, Y., Ma, M., Ma, H., Hu, W., Zhang, X., Zhuge, Z., Zhang, S., Luo, K., Gao, Y. Ultrastrong conductive in situ composite composed of nanodiamond incoherently embedded in disordered multilayer graphene. *Nat. Mater.* **22**, 42-49 (2023).

[43] Moon, J., Tian, Z. Crystal-like thermal transport in amorphous carbon. *npj Comput. Mater.* **11**, 1-8 (2025).

[44] Chen, Z., Ren, W., Gao, L., Liu, B., Pei, S., Cheng, H.-M. Three-dimensional flexible and conductive interconnected graphene networks grown by chemical vapour deposition. *Nat. Mater.* **10**, 424-428 (2011).

[45] Martin, J.W., de Tomas, C., Suarez-Martinez, I., Kraft, M., Marks, N.A. Topology of disordered 3D graphene networks. *Phys. Rev. Lett.* **123**, 116105 (2019).

[46] Zhang, X., Zhong, L., Mateos, A., Kudo, A., Vyatskikh, A., Gao, H., Greer, J.R., Li, X. Theoretical strength and rubber-like behaviour in micro-sized pyrolytic carbon. *Nat. Nanotechnol.* **14**, 762-769 (2019).

[47] Uskoković, V. A historical review of glassy carbon: Synthesis, structure, properties and applications. *Carbon Trends* **5**, 100116 (2021).

[48] Hu, M., He, J., Zhao, Z., Strobel, T.A., Hu, W., Yu, D., Sun, H., Liu, L., Li, Z., Ma, M. Compressed glassy carbon: An ultrastrong and elastic interpenetrating graphene network. *Sci. Adv.* **3**, e1603213 (2017).

[49] Németh, P.t., McColl, K., Smith, R.L., Murri, M., Garvie, L.A., Alvaro, M., Pécz, B.I., Jones, A.P., Corà, F., Salzmann, C.G. Diamond-graphene composite nanostructures. *Nano Lett.* **20**, 3611-3619 (2020).

[50] Marks, N.A. Generalizing the environment-dependent interaction potential for carbon. *Physical Review B* **63**, 035401 (2000).

[51] Stukowski, A. Visualization and analysis of atomistic simulation data with OVITO—the Open Visualization Tool. *Modell. Simul. Mater. Sci. Eng.* **18**, 015012 (2009).

[52] Zhu, S.-c., Yan, X.-z., Liu, J., Oganov, A.R., Zhu, Q. A revisited mechanism of the graphite-to-diamond transition at high temperature. *Matter* **3**, 864-878 (2020).

[53] Coppins, P., The structure factor, in: *International Tables for Crystallography Volume B: Reciprocal space*, Springer, 2006, pp. 10-24.

[54] Muchlisha, N., Widjonarko, D.M., Saraswati, T.E. Sintesis Carbon Nanofoam dan Karakteristiknya. *ALCHEMY Jurnal Penelitian Kimia* **19**, 108-122 (2023).

[55] Zhang, L., Yang, X., Zhang, F., Long, G., Zhang, T., Leng, K., Zhang, Y., Huang, Y., Ma, Y., Zhang, M. Controlling the effective surface area and pore size distribution of sp² carbon materials and their impact on the capacitance performance of these materials. *J. Am. Chem. Soc.* **135**, 5921-5929 (2013).

[56] Kiciński, W., Szala, M., Bystrzejewski, M. Sulfur-doped porous carbons: Synthesis and applications. *Carbon* **68**, 1-32 (2014).

[57] Luo, K., Liu, B., Hu, W., Dong, X., Wang, Y., Huang, Q., Gao, Y., Sun, L., Zhao, Z., Wu, Y. Coherent interfaces govern direct transformation from graphite to diamond. *Nature* **607**, 486-491 (2022).

[58] de Tomas, C., Suarez-Martinez, I., Vallejos-Burgos, F., Lopez, M.J., Kaneko, K., Marks, N.A. Structural prediction of graphitization and porosity in carbide-derived carbons. *Carbon* **119**, 1-9 (2017).

[59] Fried, L.E., Howard, W.M. Explicit Gibbs free energy equation of state applied to the carbon phase diagram. *Physical Review B* **61**, 8734 (2000).

[60] Fan, Z., Wang, Y., Ying, P., Song, K., Wang, J., Wang, Y., Zeng, Z., Xu, K., Lindgren, E., Rahm, J.M.

GPUMD: A package for constructing accurate machine-learned potentials and performing highly efficient atomistic simulations. *J. Chem. Phys.* **157**, 114801 (2022).

[61] Tan, S.J., Do, D., Nicholson, D. Consistency of NVT, NPT, μ VT and Gibbs (NV2T and NPT) with kinetic Monte Carlo schemes. *Chem. Eng. J.* **401**, 126056 (2020).

[62] Martyna, G.J., Tuckerman, M.E., Tobias, D.J., Klein, M.L. Explicit reversible integrators for extended systems dynamics. *Mol. Phys.* **87**, 1117-1157 (1996).

[63] Martyna, G.J., Tobias, D.J., Klein, M.L. Constant pressure molecular dynamics algorithms. *J. chem. Phys* **101**, 10.1063 (1994).