

भारतीय मानक
Indian Standard

IS 4151 : 2015
(Reaffirmed 2020)

दुपहिया वाहन चालकों के लिए
संरक्षी हेलमेट — विशिष्टि
(चौथा पुनरीक्षण)

Protective Helmet for Two Wheeler
Riders — Specification
(*Fourth Revision*)

ICS 13.340.20

© BIS 2015



भारतीय मानक ब्यूरो
BUREAU OF INDIAN STANDARDS
मानक भवन, 9 बहादुरशाह ज़फर मार्ग, नई दिल्ली-110002
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI-110002
www.bis.org.in www.standardsbis.in

December 2015

Price Group 12

Fire Fighting Sectional Committee, CED 22

FOREWORD

This Indian Standard (Fourth Revision) was adopted by the Bureau of Indian Standards, after the draft finalized by the Fire Fighting Sectional Committee had been approved by the Civil Engineering Division Council.

Helmet is one of the most important items of personal protective equipment used by two wheeler riders for protection against the hazards connected with driving on roads. This standard has been framed to cover provisions of protective helmets for everyday use by the two wheeler riders.

The protection given by wearing of the helmet for which requirements have been laid in this standard is not complete and wearing of the helmet may not prevent injury and/or death in severe accidents.

This standard was first issued as an emergency Indian Standard in 1967 (made as firm in 1968) and subsequently revised in 1976, 1982 and 1993. This revision has been taken up on the basis of experience gained during these years and to bring in line with latest developments at international level. The standard has been aligned with ECE Regulation No. 22, Revision 4 incorporating 05 series of amendments to the maximum extent possible, keeping in view the Indian climatic and road conditions.

The major changes incorporated in this revision are given below:

- a) The title of the standard has been modified from 'Protective Helmets for Motorcycle Riders — Specification' to 'Protective Helmets for Two Wheeler Riders — Specification';
- b) Impact absorption test has been modified with number of additional impact points, use of kerb stone anvil, increased impact velocity and head injury criteria etc;
- c) New tests to simulate the abrasion of helmet during the accident, chin guard and for effectiveness of the retention system;
- d) Inclusion of side impact tests under various conditions of temperature and humidity.; and
- e) Allowance for ventilation for the head, while wearing the helmet.

The composition of the Committee responsible for the formulation of this standard is given in Annex P.

For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated, expressing the result of a test or analysis, shall be rounded off in accordance with IS 2 : 1960 'Rules for rounding off numerical values (*revised*)'. The number of significant places retained in the rounded off value should be the same as that of the specified value in this standard.

Indian Standard

**PROTECTIVE HELMETS FOR TWO WHEELER
RIDERS — SPECIFICATION**

(Fourth Revision)

1 SCOPE

1.1 This standard covers the requirements regarding the material, construction, workmanship, finish, mass and performance for protective helmet (with or without lower face cover) for everyday use by two wheeler riders.

1.2 The helmets covered by this standard are not intended for high-speed competitive events.

2 REFERENCES

The following standards contain provisions which, through reference in this text, constitute provisions of this standard. At the time of publication, the editions indicated were valid. All standards are subject to revision and parties to agreements based on this standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below:

<i>IS No.</i>	<i>Title</i>
1884 : 1993	Automotive vehicles: Electric horns — Specification (<i>third revision</i>)
9695 : 1980	Methods for sampling of helmets
9844 : 1981	Methods of testing corrosion resistance of electroplated and anodized aluminium coatings by neutral salt spray test
9973 : 1981	Specification for visor for scooter helmets
15575	Electro acoustics — Sound level meters:
(Part 1) : 2005	Specification
(Part 2) : 2005	Pattern evaluation tests

3 TERMINOLOGY

For the purpose of this standard, the following definitions shall apply (*see* Fig. 1 and Annex A).

3.1 Two Wheeler — Any two wheeled motor vehicle with or without detachable side car.

3.2 Protective Helmet — A helmet primarily intended to protect the wearer's head against impact.

3.3 Shell — The hard part of the protective helmet which gives it its general shape.

3.4 Protective Padding — A material used to absorb impact energy.

3.5 Comfort Padding — A material provided for the wearer's comfort.

3.6 Retention System — The complete assembly by means of which the helmet is maintained in position on the head, including any devices for adjustments of the system or to enhance the wearer's comfort.

3.6.1 Chin Strap — A part of the retention system consisting of a strap that passes under the wearer's jaws to keep the helmet in position.

3.6.2 Chin Cup — It is an accessory of the chinstrap that fits round the point of the wearer's chin.

3.7 Peak — It is an extension of the shell above the eyes (detachable).

3.8 Lower Face Cover — A detachable, movable or integral (permanently fixed) part of the helmet covering the lower part of the face.

3.8.1 Protective Lower Face Cover — A detachable, movable or integral (permanently fixed) part of the helmet covering the lower part of the face and intended to protect the chin of the user against impacts.

3.8.2 Non-protective Lower Face Cover — A detachable, movable or integral (permanently fixed) part of the helmet covering the lower part of the face that does not protect the chin of user against impact.

3.9 Visor — A transparent protective screen extending over the eyes and covering all or part of the face.

3.10 Basic Plane of the Human Head — A plane at the level of the opening of the external auditory meatus (external ear opening) and the lower edge of the orbits (lower edge of the eye sockets).

3.11 Basic Plane of the Headform — A plane, which corresponds to the basic plane of the human head.

3.12 Central Vertical Axis — The line relative to human head or headform or helmet that lies in the plane of symmetry, and that is normal to the basic plane at a point equidistant from the front and back of the head or the headform or helmet.

3.13 Reference Plane — A construction plane parallel to the basic plane of the headform at a distance from it, which is a function of the size of the headform.

IS 4151 : 2015

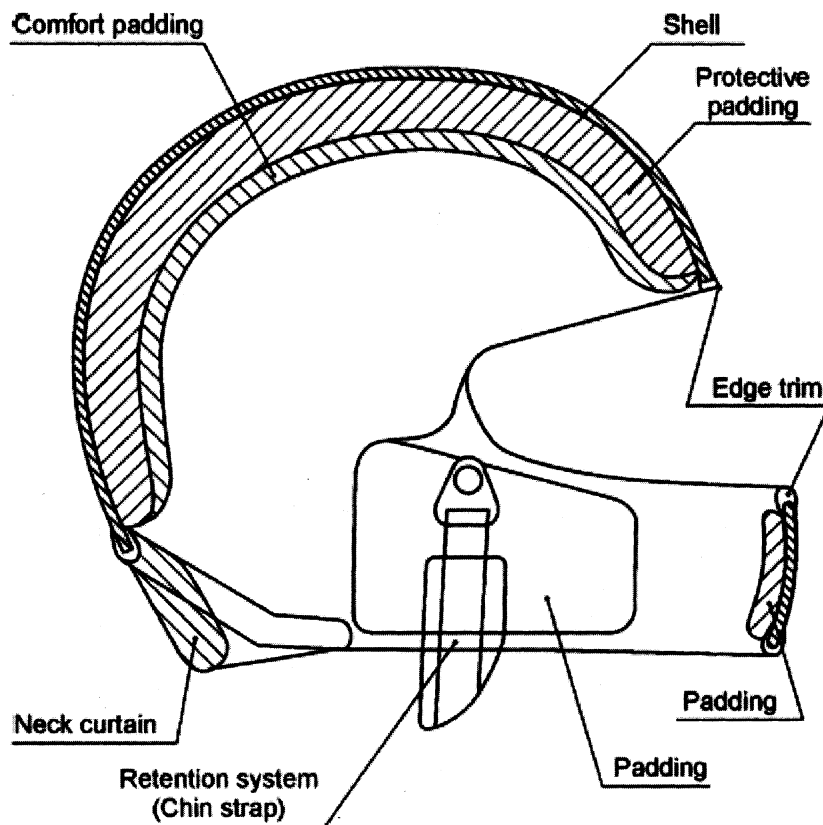


FIG. 1 TYPICAL SKETCH SHOWING INTERNAL COMPONENTS OF HELMET

3.14 Neck Curtain — A part of the helmet attached to the lower edge of the helmet designed to protect against adverse weather conditions, dirt and small stones.

4 MATERIAL

4.1 Shell

The shell of the helmet shall be of metallic or non-metallic materials conforming to the test requirements.

4.2 Protective Padding

It may be of expanded polystyrene or any other material having similar properties.

4.3 Comfort Padding

It may be of expanded polyurethane foam, polyethylene or any other suitable material having similar properties.

4.4 Retention System

The criteria for selection of material for chin strap and comfort padding shall be sweat-resistant, non-irritant and shall not be known to cause any skin disease.

4.5 Metal Parts

The metal parts in helmet shall be either inherently corrosion resistant or shall have been treated for corrosion resistance. Such parts shall show no sign of corrosion when subjected to test as specified in IS 9844.

4.6 Visor

If provided, it shall conform to IS 9973.

5 SIZES

Helmets shall be of the sizes matching to the sizes of headform of 500, 520, 540, 560, 570, 580, 600 and 620 mm.

6 CONSTRUCTIONAL REQUIREMENTS

6.1 General

6.1.1 The basic construction of the helmet shall be in the form of a hard outer shell containing additional means of absorbing impact energy and a retention system.

6.1.2 The protective helmet may be fitted with earflaps and a neck curtain. It may also have a detachable peak, a visor and a lower face cover. Visor, if fitted, shall

meet the requirements of IS 9973. If fitted with a non protective lower face cover the outer surface of the cover shall be marked "Does not provide any additional protection to chin from impacts".

6.1.3 No component or device shall be fitted to or incorporated in the protective helmet unless it is designed in such a way that it shall not cause injury and that, when it is fitted to or incorporated in the protective helmet, the helmet still complies with the performance requirements of this standard.

6.2 Shell

The extent of the protection provided shall be as given in **6.2.1** to **6.2.7**.

6.2.1 The shell shall cover all areas above plane AA' and shall extend downwards at least as far as the lines CDEF on both sides on the headform (*see* Fig. 2).

6.2.2 At the rear, the rigid parts and, in particular, the shell shall not be within a cylinder of diameter 100 mm and with axis situated at the intersection of the medium plane of symmetry of the headform and of a plane parallel to and 110 mm below the reference plane (*see* Fig. 2).

6.2.3 The helmet shall not dangerously affect the wearer's ability to hear and shall conform to the requirements laid down in **7.6**.

6.2.4 The temperature in the space between the head and the shell shall not rise inordinately. To prevent this ventilation holes may be provided in the shell. Ventilation may be provided for increasing the comfort of the rider

6.2.5 Above the reference plane, the shape shall be in the form of continuous, convex curve, except where shaping is provided for functional purposes. Below the reference plane, irregularities in the curve shall be smoothly faired. The shell shall not incorporate an integral peak, but may incorporate an integral lower face cover. Where means for attaching a visor are not provided, the profile at the front edge shall not prevent the wearing of goggles.

6.2.6 All projections from or irregularities in the outer surface of the shell greater than 2 mm shall be tested for shear assessment according to test for projections and surface friction as per **7.4**. The outer surface of the helmet shall be tested for friction assessment according to test for projections and surface friction.

6.2.7 All external projection shall be radiused and any external projections other than press fasteners shall be smooth and adequately faired. Rivet heads shall be radiused and shall not project more than 2 mm above the outer surface of the shell and shall have a radius of minimum of 1 mm. All external projections more

than 2 mm above the outer surface of the shell shall have a radius of minimum of 2 mm. The later specific requirements shall not apply if a projection satisfies the requirement in **7.4.1** or **7.4.2**.

6.2.8 There shall be no inward-facing sharp edges on the inside of the helmet. Rigid projecting internal parts shall be covered with padding so that any stresses transmitted to the head are not highly concentrated.

6.2.9 The various components of the protective helmets shall be so assembled that they are not liable to become easily detached as a result of an impact.

6.3 Protective Padding

The protective padding shall cover all the areas defined in **6.2.1** taking into account the requirements given in **6.2.3** and **6.2.4**.

6.4 Retention System

The helmet shall be held in place on the wearer's head by means of a retention system which may be in the form of chin strap with buckle or double-D ring or sliding bar or any other similar locking device, which is secured under the lower jaw. All parts of the retention system shall be permanently attached to the system or to the helmet/shell.

6.4.1 If the retention system includes a chinstrap, the strap shall not be less than 20 mm wide under a load of $150\text{ N} \pm 5\text{ N}$ applied under the conditions given in **F-1.2** and **F-1.3**.

6.4.2 The chin strap shall not include a chin-cup.

6.4.3 Chinstraps shall be fitted with a device to adjust and maintain tension in the strap.

6.4.4 Chin strap fastening and tensioning devices shall be positioned on the straps either so that there are no rigid parts extending more than 130 mm vertically below the headform reference plane with the helmet mounted on the appropriate sized headform, or so that the whole of the device is between the bony projections of the underside of the lower jaw.

6.4.5 If the retention system includes either a double-D ring or sliding bar fastening device then means shall be provided to prevent the retention system being completely undone and also to retain the free end of the strap when the retention system is adjusted.

6.4.6 Sliding bar/double-D ring fastening devices shall be fitted with a pulling type flap to be used for releasing the retention system. Its colour shall be red and its minimum dimensions shall be 10mm × 20 mm.

6.4.7 If a retention system includes a quick-release mechanism, then the method of release of this mechanism shall be self-evident. Any levers, tabs,

IS 4151 : 2015

buttons or other components which need to be operated to release the mechanism shall be coloured red, those parts of the rest of the system which are visible when closed shall not be similarly coloured, and the mode of operation shall be permanently indicated.

6.4.8 The retention system shall remain closed when the tests (Impact absorption test, dynamic test of retention system and retention test) as described in 7.2, 7.5 and 7.7 are carried out.

6.4.9 The buckle of the retention system shall be designed so as to preclude any possibility of incorrect manipulation. This means, *inter-alia*, that it shall not be possible for the buckle to be left in a partially closed position.

6.5 The characteristics or the materials used in the manufacture of helmets shall be known not to undergo appreciable alteration under the influence of ageing, or of the circumstances of use to which the helmet is normally subjected, such as exposure to sun, extremes of temperature and rain. For the parts of the helmet coming into contact with the skin, the materials used shall be known not to undergo appreciable alteration through the effect of perspiration or of toilet preparations. The manufacturer shall not use materials known to cause skin troubles.

6.6 After the performance of one of the above prescribed test, the protective helmet shall not exhibit any breakage or deformation dangerous to the wearer.

6.7 Peripheral Vision

6.7.1 The helmet shall be placed on the head form corresponding to its size of a helmet type by the procedure specified in Annex B.

6.7.2 In the condition mentioned in 6.7.1, there shall be no occultation in the field of vision bounded by planes as shown in Fig. 3A, 3B and 3C and shall satisfy the requirements as given in 6.7.2.1, 6.7.2.2 and 6.7.2.3.

6.7.2.1 Horizontally

Two segments of dihedral angles symmetrical in relation to the median longitudinal vertical plane of the headform and situated between the reference and the basic planes. Each of these dihedral angles is defined by longitudinal vertical median plane of the headform and the vertical plane forming an angle of not less than 105° with the median longitudinal vertical plane and whose edge is the straight line LK (see Fig. 3A and 3C).

6.7.2.2 Upwards

A dihedral angle defined by the reference plane of the headform and a plane forming an angle of not less than 7° with the reference plane and whose edge is the straight line L_1, L_2 ; the points L_1 and L_2 representing the eyes (see Fig. 3A and 3B).

6.7.2.3 Downwards

A dihedral angle defined by the basic plane of the headform and a plane forming an angle of not less than 45° with the basic plane and whose edge is the straight line K_1, K_2 (see Fig. 3A and 3B).

6.8 Workmanship and Finish

6.8.1 All edges shall be smooth and rounded. Any external or internal projection permitted under 6.2.6 and 6.2.7 shall be smooth and adequately faired to other surfaces.

6.9 Mass

The protective helmets with lesser mass are preferred and may be available with the increasing availability of more advanced composites and materials. However, mass of the complete helmet (without peak, visor and detachable lower face cover, if provided) shall not exceed 1 500 g.

7 TESTS FOR HELMETS

7.1 Each helmet type shall be conditioned as shown below:

Test	Number of Helmets to be Conditioned				Total
	Solvent + Ambient Temperature and Hygrometry Conditioning	Solvent + Heat Conditioning	Solvent + Low Temperature Conditioning	Solvent Ultra violet Radiation Conditioning and Moisture Conditioning	
Impact absorption	2	1	1	1	5
Rigidity	2				2
Retention system	1				1

The largest size of each helmet type shall be tested for impact absorption and rigidity. For tests of the retention system, helmet size shall be chosen such that the helmet to be tested shall be that offering the least favourable conditions (such as thickest padding, etc).

Additionally, for each smaller headform size within the size range of the helmet type two helmets shall undergo the impact absorption test. One helmet shall be heat conditioned, and the other low temperature conditioned. The conditioned helmets shall be impacted against either anvil, in equal numbers as far as possible.

7.1.1 Types of Conditioning

7.1.1.1 Solvent conditioning

Take a cotton cloth approximately 150 mm square and a quantity approximately 25 ml of a solvent consisting of test liquid with (70 percent octane and 30 percent toluene). Using the cloth soaked in the solvent, apply the solvent to all those regions of the outside surface of the helmet shell within 50 mm of the chin strap fixings and keep these regions wet within the solvent for 7.5 ± 2.5 s. Repeat the procedure on the remainder of the external surface including any chin guard, keeping these regions wet for 12.5 ± 2.5 s. No further conditioning or testing be done during the following 30 min.

7.1.1.2 Ambient temperature and hygrometry conditioning

The helmet shall be exposed to a temperature of $25 \pm 5^\circ\text{C}$ and a relative humidity of 65 ± 5 percent for at least 4 h.

7.1.1.3 Heat conditioning

The helmet shall be exposed to a temperature of $50 \pm 2^\circ\text{C}$ for not less than 4 h and not more than 6 h.

7.1.1.4 Low-temperature conditioning

The helmet shall be exposed to a temperature of $-20 \pm 2^\circ\text{C}$ for not less than 4 h and not more than 6 h.

7.1.1.5 Ultraviolet-radiation conditioning and moisture conditioning

The outer surface of the protective helmet shall be exposed successively to ultraviolet irradiation by a 125 W xenon filled quartz lamp for 48 h at a range of 25 cm, followed by spraying for 4 to 6 h with water at ambient temperature at the rate of 1 litre/min.

7.2 Impact Absorption Test

The helmet shall be tested by the method prescribed in Annex C and shall meet the requirements given in 7.2.1 and 7.2.2.

7.2.1 The absorption efficiency shall be considered sufficient where the resultant acceleration measured at the centre of gravity of the headform at no time exceeds 275 g, and the head injury criterion does not exceed 2 400.

7.2.2 The helmet shall not become detached from the headform.

7.3 Rigidity Test

The helmet shall be tested by the method prescribed in Annex D and shall meet the requirements given in 7.3.1 and 7.3.2.

7.3.1 Along each axis, the deformation measured under the 630 N load shall not exceed by more than 40 mm than that measured under the initial 30 N load.

7.3.2 After restoration of the 30 N load, the deformation measured shall not exceed by more than 15 mm than that measured under the initial 30 N load.

7.4 Test for Projections and Surface Friction

An appropriate size of helmet shall be subjected to the test either by method A or by method B as prescribed in Annex E and shall meet the requirements given in 7.4.1 or 7.4.2.

7.4.1 Test for Projections and Surface Friction (Method A)

7.4.1.1 When tested against the bar anvil the helmet shall satisfy the following requirement:

The peak longitudinal force measured on the anvil shall not exceed 2 500 N nor shall its integral with respect to time over the duration of the impact exceed 12.5 Ns for any of the selected impact points.

7.4.1.2 When tested against the abrasive anvil, a second helmet shall satisfy the following requirement:

The peak longitudinal force measured on the anvil shall not exceed 3 500 N, nor shall its integral with respect to time over the duration of the impact exceed 25 Ns for any of the selected impact points.

7.4.2 Test for Projections and Surface Friction (Method B)

7.4.2.1 For shear assessment the tested projection, shall shear away, shall be detached or alternatively shall not prevent the assessment bar from sliding past the projection. In all cases the bar on the horizontal carriage shall travel past the projection.

7.4.2.2 For friction assessment the abrasive carriage shall not be brought to rest by the helmet.

7.5 Dynamic Test of Retention System

The helmet shall be tested for their retention system

IS 4151 : 2015

by the method prescribed in Annex F and shall meet the requirements given in 7.5.1 and 7.5.2.

7.5.1 During the test, the dynamic displacement of the point of application of the force shall not exceed 35 mm.

7.5.2 After 2 min, the residual displacement of the point of application of the force, as measured under a mass of $15\text{ kg} \pm 0.5\text{ kg}$ shall not exceed 25 mm.

7.5.3 Damage to the retention system shall be accepted provided that it is still possible to take the helmet easily off the headform and that the requirements given in 7.5.1 and 7.5.2 above are met.

7.5.4 In the case of retention system fitted with quick release mechanism it shall be possible to release the mechanism in accordance with 7.10.2.

7.6 Audibility Test

The helmet shall be tested for their sound attenuation properties by the method prescribed in Annex G and shall meet the requirements given in 7.6.1.

7.6.1 The sound transmission loss shall not be more than 10 dB over the frequency range 250 to 2 000 Hz.

7.7 Retention (Detaching) Test of Helmet

The helmet shall be tested by the method prescribed in Annex H and shall meet the requirements given in 7.7.1.

7.7.1 After the test the angle between the reference line situated on the shell of the helmet and the reference plane of the headform shall not exceed 30° .

7.8 Micro-slip Test of the Chin Strap

It shall be tested by the method prescribed in Annex J and shall meet the requirements given in 7.8.1.

7.8.1 The total slippage through the grip shall not exceed 10 mm.

7.9 Test for Resistance to Abrasion of the Chin Strap

The test shall be performed by the method prescribed in Annex K on every device in which the strap slides through a rigid part of the retention system, with the following exceptions as mentioned in 7.9.1 and 7.9.2. It shall meet the requirements given in 7.9.3.

7.9.1 Where the micro-slip test described in 7.8, shows that the strap slips less than half the prescribed value; or

7.9.2 Where the composition of the material used, or the information already available, renders the test superfluous in the judgment of the technical service.

7.9.3 After the test described in K-1.3 the strap shall withstand a tension of 3 kN without breaking when tested as per K-1.4.

7.10 Tests for Retention Systems Relying on Quick-Release Mechanisms

7.10.1 Inadvertent Release by Pressure

7.10.1.1 If the retention system is designed to be

released by pressure on a certain part, the system shall not release when a rigid sphere of diameter 100 mm is pressed with a force of $100 \pm 5\text{ N}$ directly in the line of movement of the part.

7.10.1.2 If such a system incorporates more than one quick-release mechanism, or one such mechanism requiring more than one operation to release it, the system shall be deemed not to comply with this requirement if sufficient opening of the system is caused by the pressure of the sphere on only one quick-release mechanism or for only one operation, whichever is appropriate, to allow the release of the appropriate headform.

7.10.2 Ease of Release

After the additional force has been removed, the opening system shall be capable of being operated by a force not exceeding 30 N. However, if the quick release mechanism is incorporated in the helmet shell, the opening system shall be capable of being operated by a force not exceeding 60 N.

7.10.2.1 The helmet shall be mounted on the test machine as shown in Fig. 8 as described in F-1.3 such that a static force of $150 \pm 5\text{ N}$ is applied to the retention system. An additional static force of $350 \pm 5\text{ N}$ shall be applied to the retention system for at least 30 seconds and then removed.

7.10.2.2 The buckle opening force shall be applied using a dynamometer or similar device in the manner and direction of normal use. In the case of a push button the contact end shall be a polished metal hemisphere with radius $2.5 \pm 0.1\text{ mm}$. The opening force shall be applied on the geometric centre of the push button or respective application areas.

7.10.3 Durability of Quick-Release Mechanisms

The quick release mechanism shall not fracture nor disengage when a tensile force of $2.0\text{ kN} \pm 50\text{ N}$ is progressively applied to the retention system in the direction in which the mechanism is designed to bear load. Following the application and removal of the force the quick release mechanism shall still be capable of operation.

7.10.3.1 Procedure

7.10.3.1.1 Subject the quick-release mechanism to the following procedures in the order given:

Using apparatus appropriate to the particular design of mechanism carry out the following procedure. Close and lock the mechanism. Apply a loading force of $20 \pm 1\text{ N}$ in the direction in which the mechanism is designed to bear load, then unlock and disengage the mechanism under load. Complete this cycle in not less than 2 s. Repeat for a total of 5 000 cycles.

IS 4151 : 2015

7.10.3.1.2 If the quick-release mechanism incorporates metal components carry out the following procedure:

Place the complete mechanism in a closed cabinet so that the mechanism can be continuously wetted by a spray while still allowing free access of air to all parts of the mechanism. Subject the mechanism to a spray of a solution consisting of $5\% \pm 1\%$ (*m/m*) of reagent grade sodium chloride in distilled or de-ionized water for a period of 48 ± 1 h at a temperature of $35^\circ\text{C} \pm 5^\circ\text{C}$. Rinse the mechanism thoroughly in clean running water to remove salt deposits and allow it to dry for 24 ± 1 h.

Repeat the procedure given in **7.10.3.1.1**.

8 SAMPLING AND CRITERIA FOR CONFORMITY

The method of sampling and criteria for conformity shall be as per IS 9695.

9 MARKING

9.1 Each helmet shall be clearly and indelibly marked with the following information in a readily accessible places:

- a) Manufacturer's name or trade-mark;
- b) Batch No.;

- c) Month and year of manufacturing;
- d) Size;
- e) Mass of the helmet to the nearest 50 g. (*For information to the consumer only*)

NOTE — The maximum mass quoted should include all the accessories that are supplied with the helmets, with the packaging, as it is placed on the market, whether or not those accessories have actually been fitted to the helmet".

- f) Name of the country of manufacturing; and
- g) To be marked as "Does not provide any additional protection to chin from impacts", if applicable (*see 6.1.2*)

9.1.1 The marking shall not be in the main field of vision.

9.2 BIS Certification Marking

The helmet may also be marked with the Standard Mark.


9.2.1 The use of the Standard Mark is governed by the provisions of the *Bureau of Indian Standards Act, 1986* and the Rules and Regulations made thereunder. The details of conditions under which the license for the use of the Standard Mark may be granted to manufacturers or producers may be obtained from the Bureau of Indian Standards.

IS 4151 : 2015

ANNEX A

(Clauses 3 and 6.2)

HEADFORMS

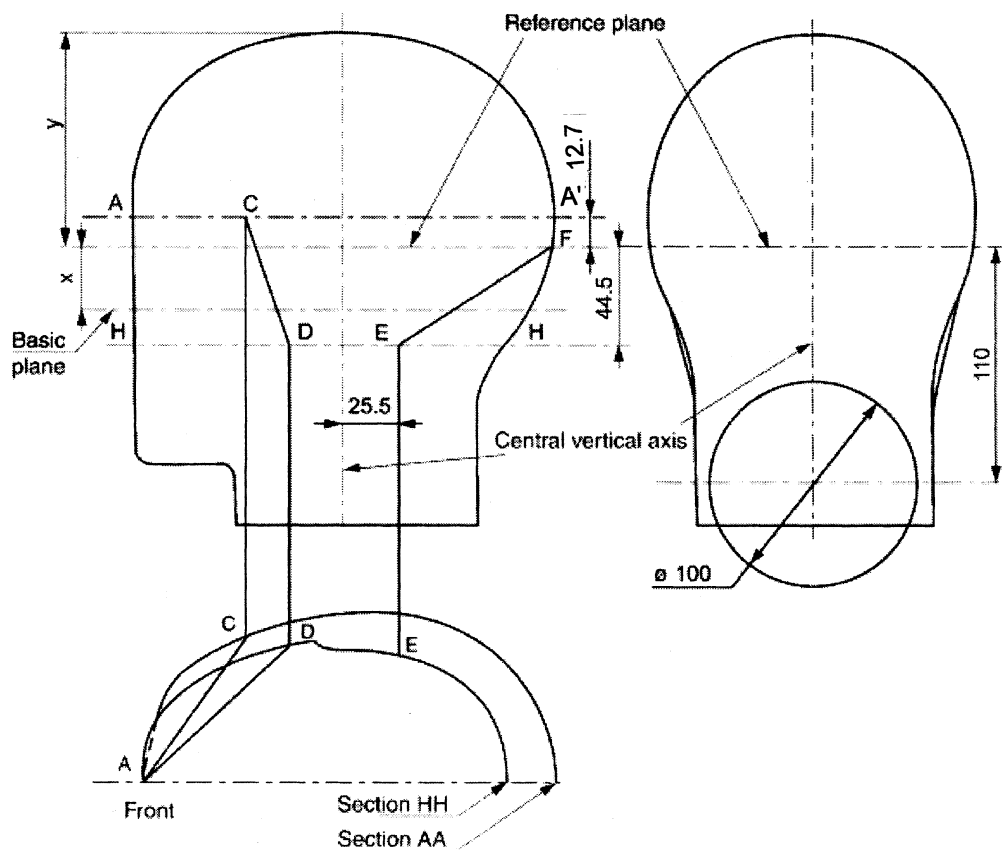

Headforms	Size	X	Y	AC	HD
A	500	24	90	80	88
C	520	25	93	82	90
E	540	26	96	84	92
G	560	27	99	86	94
J	570	27.5	102.5	87	95
K	580	28	104	88	96
M	600	29	107	90	98
O	620	30	110	92	100

NOTE — For details see Annex M and Annex N.

All dimensions in millimetres.
FIG. 2 MINIMUM EXTENT OF PROTECTION

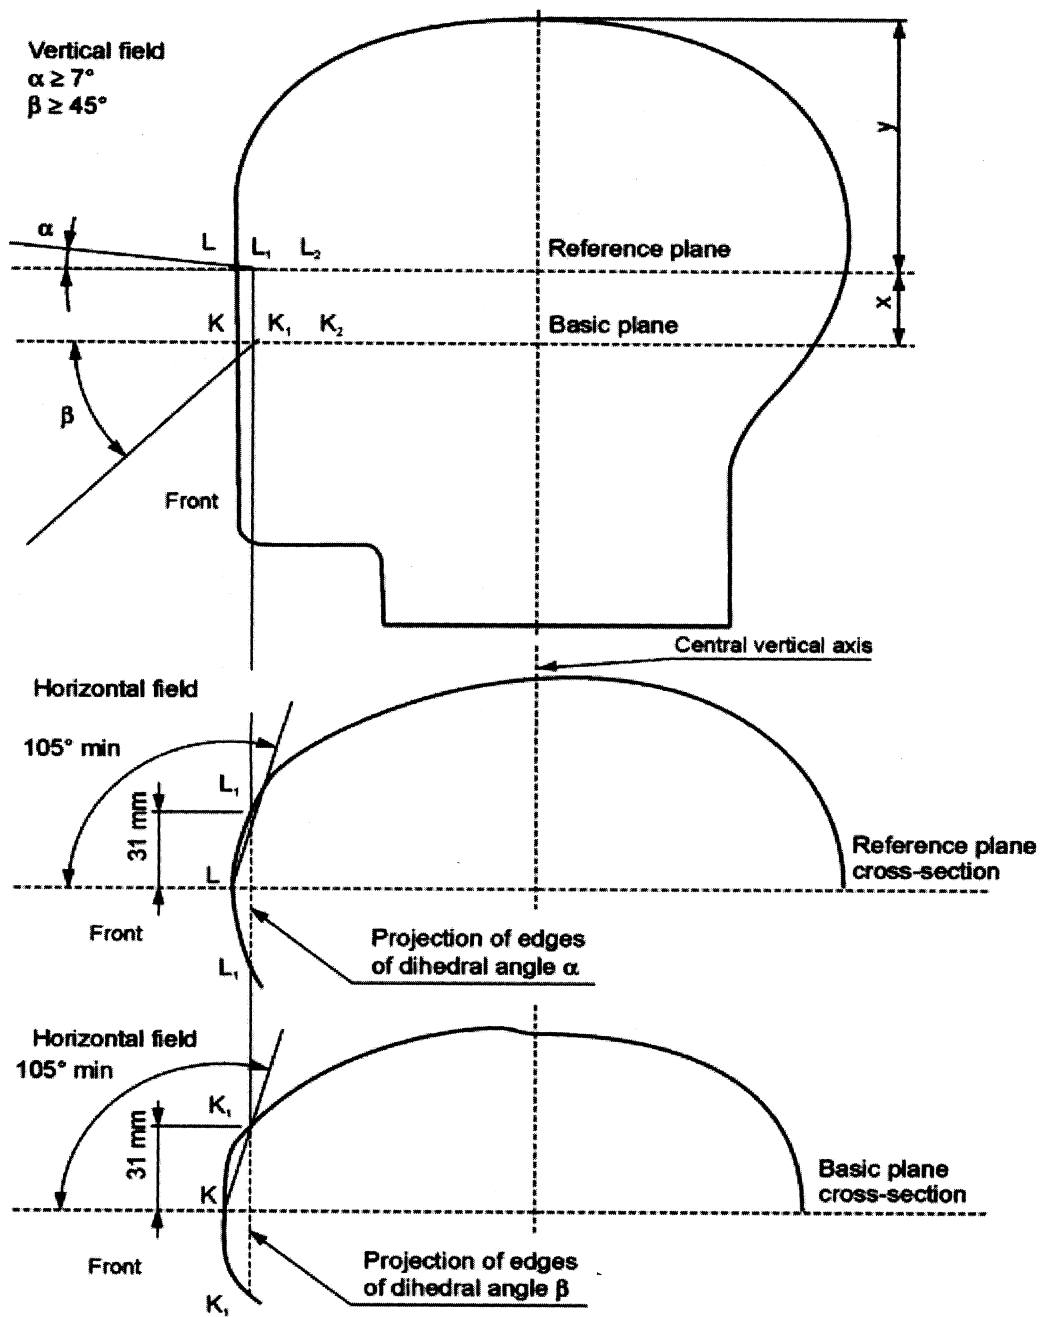


FIG. 3A PERIPHERAL VISION

IS 4151 : 2015

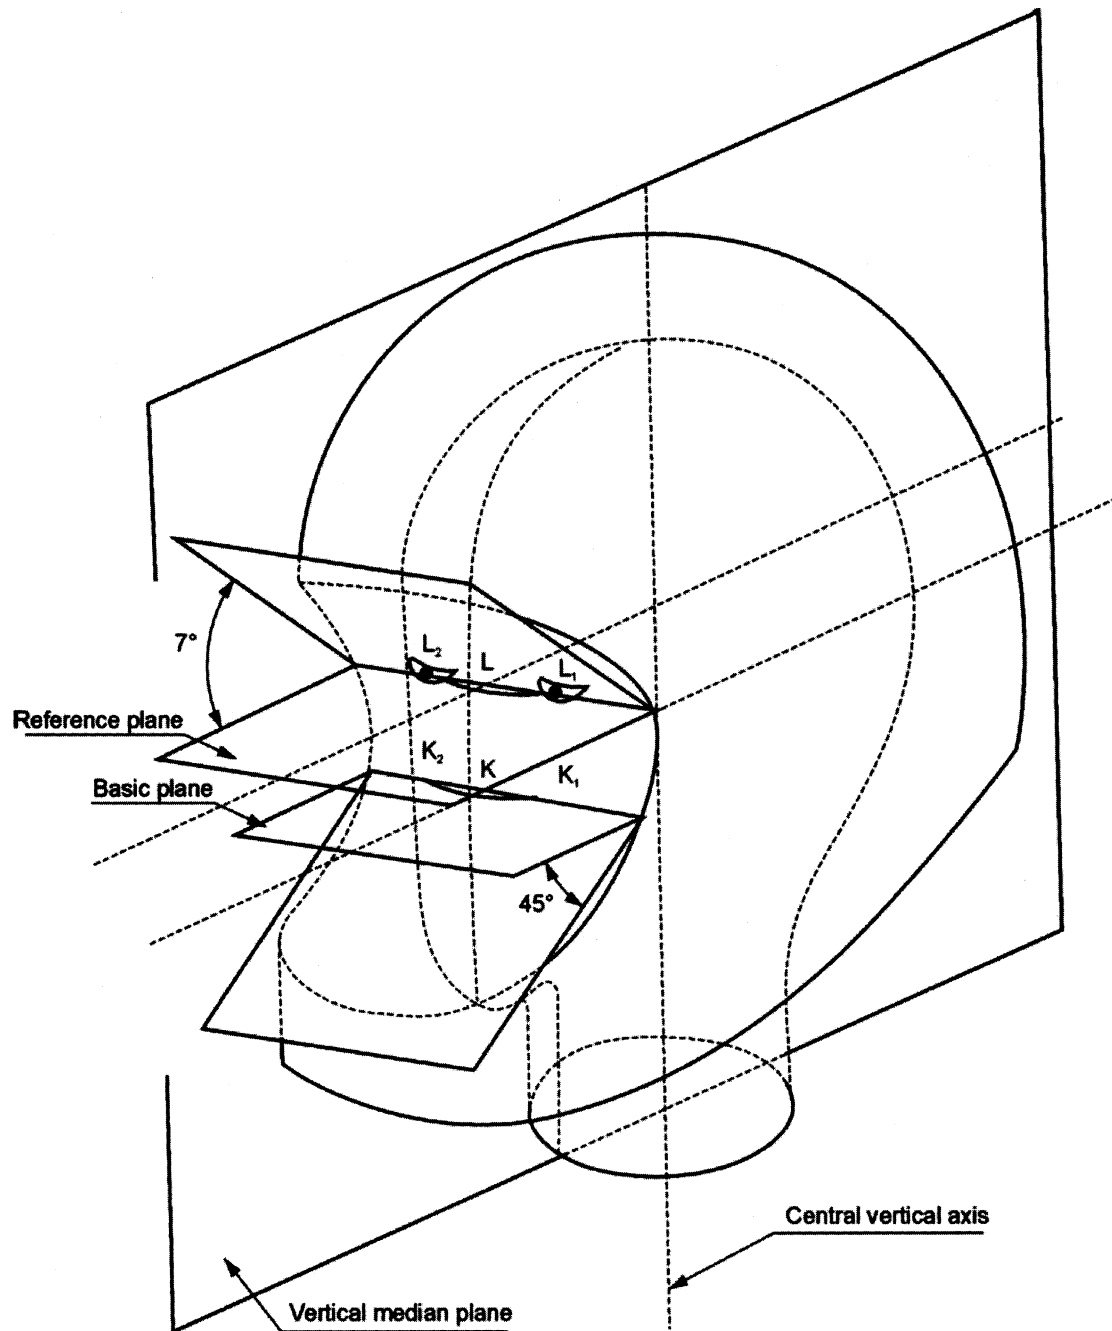


FIG. 3B PERIPHERAL VISION — VERTICAL FIELD

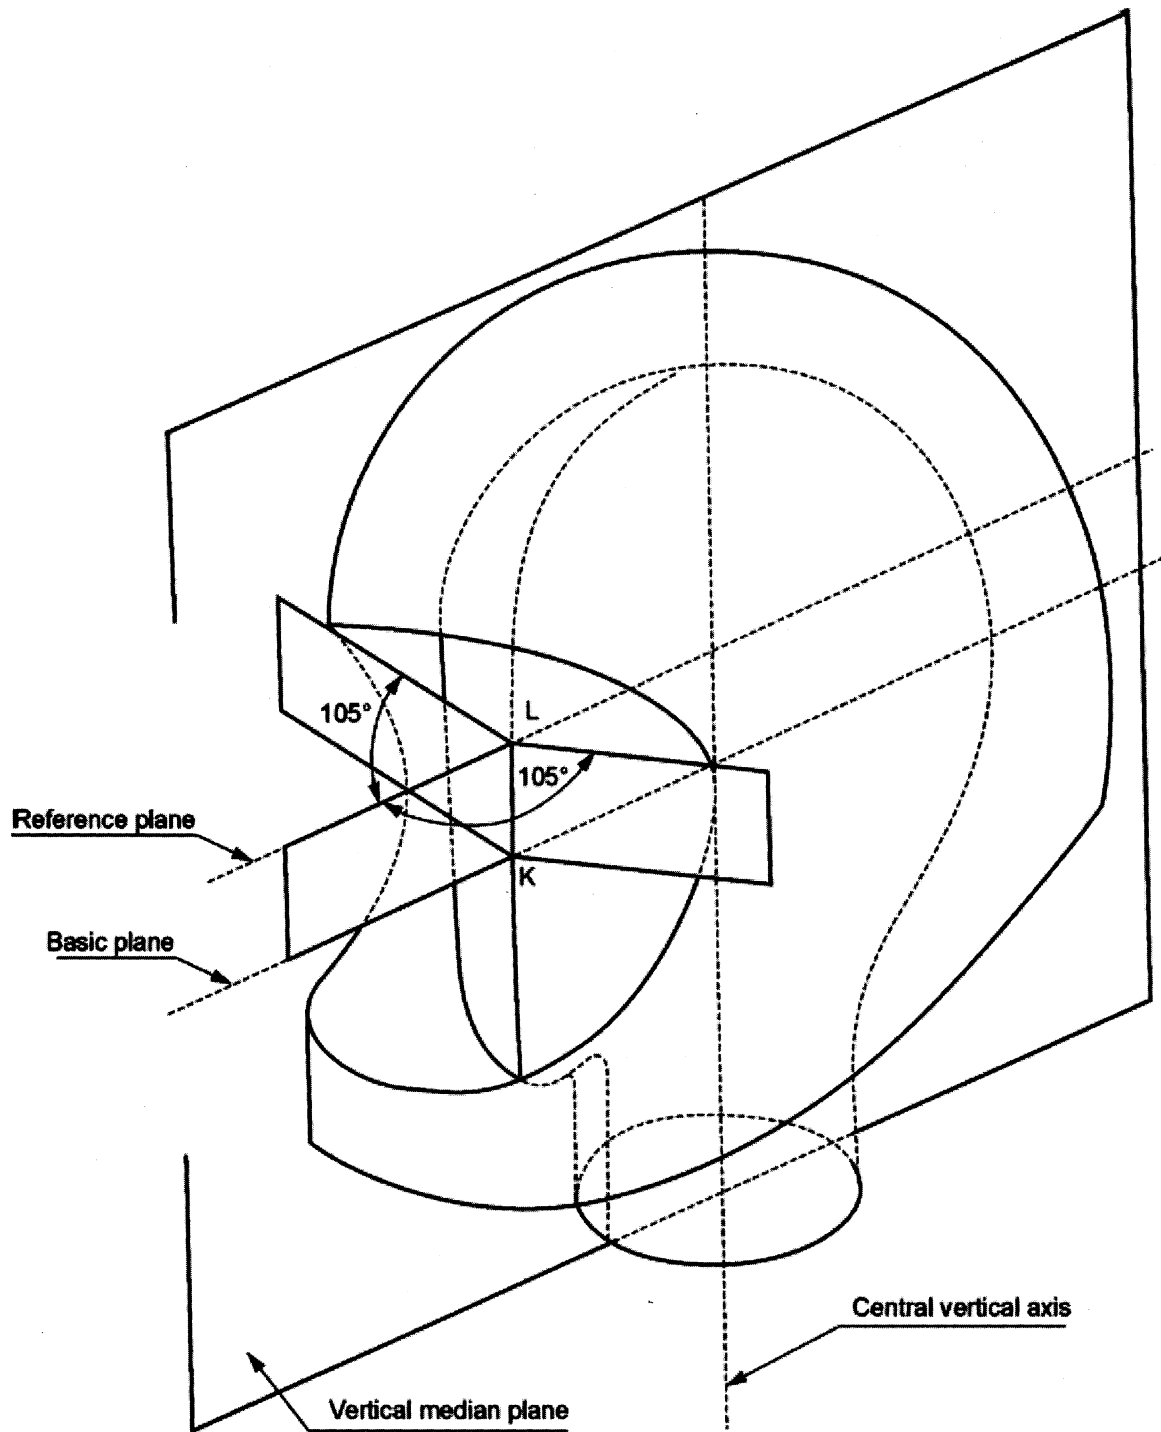


FIG. 3C PERIPHERAL VISION — HORIZONTAL FIELD

IS 4151 : 2015

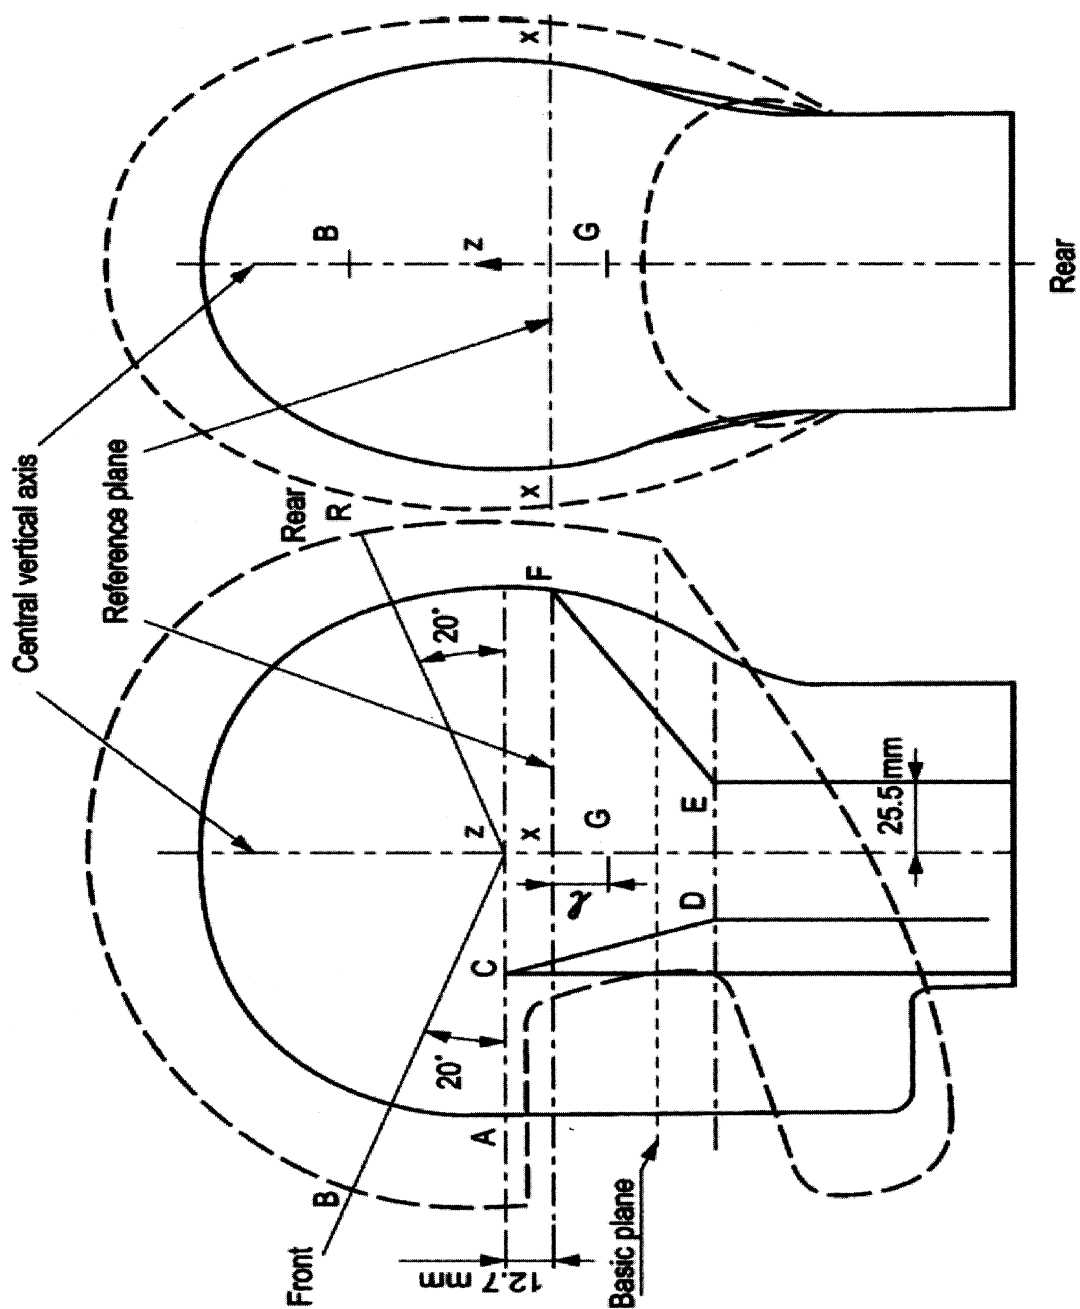


FIG. 4 IDENTIFICATION OF IMPACT POINTS

ANNEX B

(Clause 6.7.1)

POSITIONING OF THE HELMET ON THE HEADFORM

B-1 The helmet is placed on a headform of appropriate size. A load of 50 N is applied on the crown of the helmet in order to adjust the helmet on the headform. It shall be ascertained that the vertical median plane of the helmet coincides with the median vertical plane of the headform.

B-2 The front edge of the helmet is placed against a gauge to check the minimum angle for the upward field of vision. The following points are then checked.

B-2.1 That the line *AC* and the *ACDEF* zone are covered by the shell (*see* Fig. 2)

B-2.2 That the requirements for the minimum downward angle and the horizontal field of vision are satisfied.

B-2.3 Requirements mentioned in 6.2.2 relating to the rear projection shall be met.

B-3 If one of the above conditions is not met, the helmet is moved slightly from front to rear to seek a position where all the requirements are met. Once such a position is determined, a horizontal line is drawn on the shell at the level of the *AA'* plane. This horizontal line shall determine the reference plane for the positioning of the helmet during the tests.

ANNEX C

(Clause 7.2)

IMPACT ABSORPTION TEST

C-1 PRINCIPLE

Impact absorption capacity is determined by recording against time, the acceleration imparted to a headform fitted with the helmet, when dropped in guided free fall at a specified impact velocity upon a fixed steel anvil.

C-2 APPARATUS (*see* Fig. 5)

The test apparatus shall comprise of the following:

- a) A base;
- b) An anvil rigidly fixed to a base;
- c) A free fall guidance system;
- d) A mobile system supporting the helmeted headform;
- e) A metal headform fitted with a tri-directional accelerometer and a measuring assembly; and
- f) A system by which the point of impact may be brought into correspondence with the centre of the anvil.

C-2.1 Base

C-2.1.1 The base shall be made of steel or concrete or a combination of these materials and have mass of at least 500 kg. It shall be so constructed that there is no significant deformation of surface under the test load.

C-2.1.2 No part of the base or anvil shall have a resonance frequency liable to affect the measurements.

C-2.2 Anvils

C-2.2.1 The flat steel anvil shall have a circular impact face of $130 \text{ mm} \pm 3 \text{ mm}$ diameter.

C-2.2.2 The kerbstone anvil shall have two sides forming an angle of $105^\circ \pm 5^\circ$, each of them with a slope of $52.5^\circ \pm 2.5^\circ$ towards the vertical and meeting along a striking edge with a radius of $15 \text{ mm} \pm 0.5 \text{ mm}$. The height shall be at least 50 mm and the length not less than 125 mm. The orientation is 45° to the longitudinal vertical plane at Points *B*, *P* and *R*, and 45° to the base plane at Point *X* (front low, back up).

C-2.3 Mobile System and Guides

The mobile system supporting the headform shall be such that its characteristics do not affect the measurement of acceleration at the centre of gravity of the headform. It shall also be such that any point in the area *ACDEF* can be positioned vertically above the centre of the anvil. The guides shall be such that the impact velocity is not less than 95 percent of the theoretical velocity.

C-2.4 Accelerometer and Measuring Assembly

C-2.4.1 The accelerometer shall be capable of withstanding a maximum acceleration of 2 000 g without damage. Its maximum mass shall be 50 g. The measuring system including the drop assembly shall

IS 4151 : 2015

have a frequency response in accordance with channel frequency class (CFC) 1 000 (*see* ISO 6487).

C-2.4.2 The HIC shall be calculated as the maximum (depending from t_1 and t_2 of the equation):

$$HIC = \left[\frac{1}{t_2 - t_1} \int_{t_1}^{t_2} a(t) dt \right]^{2.5} (t_2 - t_1)$$

where 'a' is the resultant acceleration as a multiple of 'g' and t_1 and t_2 are any two points in time(s) during the impact. The acceleration data has to be sampled at a frequency of at least 8 000 Hz and filtered (CFC 1 000) (*see* ISO 6487).

C-2.5 Headforms

C-2.5.1 The headform to be used for the impact absorption test shall be made of a metal of characteristics such that the headform present no resonance frequency below 3 000 Hz. The general characteristics of the test headform shall be used shall be as given in Table 1.

Table 1 General Characteristics of Test Headforms

SI No. (1)	Symbols (2)	Size mm (3)	Mass kg (4)
i)	A	500	3.1 ± 0.10
ii)	E	540	4.1 ± 0.12
iii)	J	570	4.7 ± 0.14
iv)	M	600	5.6 ± 0.16
v)	O	620	6.1 ± 0.18

NOTE — Headform of sizes not listed in this table shall be tested with the next smaller headform size given in Fig. 2.

C-2.5.2 The shape of the test headforms shall be:

- Above the reference plane, in conformity with the detailed dimensions of the test headforms shown in Annex M;
- Below the reference plane, in conformity with the detailed dimensions of the test headforms shown in Annex N;

C-2.5.3 The centre of gravity of the headform shall be near the Point G on the central vertical axis at 1 mm below the reference plane, as defined in Annex N. The headform shall contain, near its centre of gravity, a housing for a tri-directional accelerometer.

C-2.5.4 For tests other than those of impact absorption, headforms complying only with the geometrical provisions of C-2.5.2 may be used.

C-3 PROCEDURE

C-3.1 Marking of Points of Impact

Before conditioning, the points and areas of impact are marked as indicated in C-3.4.3 and Fig. 4.

C-3.2 Positioning of the Helmet after Conditioning

C-3.2.1 The helmet shall be positioned in accordance

with the requirements of Annex B on a headform of appropriate size selected from among those listed in C-2.5.1 when testing impact Points B, X, P, R. The helmet shall then be tipped towards the rear so that the front edge of the helmet in the median plane is displaced by 25 mm; the retention system shall then be adjusted under the chin of the headform; if the system includes an adjustable chinstrap, the strap is tightened as for normal use.

C-3.2.2 When testing impact Point 'S' on a helmet with a protective lower face cover, the helmeted headform is tipped forwards so that the central vertical axis of the headform is inclined at an angle of $65 \pm 3^\circ$ to the vertical with the vertical longitudinal plane of symmetry of the helmeted head form in the vertical position. If the impact point would be within 15 mm of the rim, the helmeted headform shall be re-positioned so that the impact point is not less than 15 mm from the rim.

C-3.2.3 The test headform shall be so positioned that the designated point on the helmet is vertically above the centre of the anvil. The plane tangential to the point of impact shall be horizontal. This prescription does not apply to S impact point.

C-3.2.4 The protective helmets placed on the market with a visor shall be tested with the visor and without peak in the closed position.

C-3.3 Impact Velocity

C-3.3.1 The test shall be completed not more than five minutes after the helmet is taken from the conditioning chamber. If the test does not complete within the stipulated time the same shall be kept for reconditioning for not less than 1 h. Tests at Point S shall be carried out after tests as Points B, X, P and R. The drop height shall be such that the unit constituted by the headform and helmet falls on the test anvil at a velocity, which, immediately before impact, is equal to:

$$7.5^{+0.15}_{-0} \text{ m/s for both anvils specified in C-2.2.}$$

$$5.5^{+0.15}_{-0} \text{ m/s for tests at Point S.}$$

C-3.3.2 The velocity of the moving mass is measured between 1 cm and 6 cm before impact, to an accuracy of 1 percent. The acceleration against time at the centre of gravity of the headform is measured and recorded and the Head Injury Criterion (HIC) as prescribed in C-2.4.2 shall be calculated.

C-3.4 Selection of Points of Impact

C-3.4.1 Each test shall be carried out with 4 impacts on one helmet on the points B, X, P, and R, in this sequence. When a helmet with a protective lower face cover is being tested then an additional Point S shall

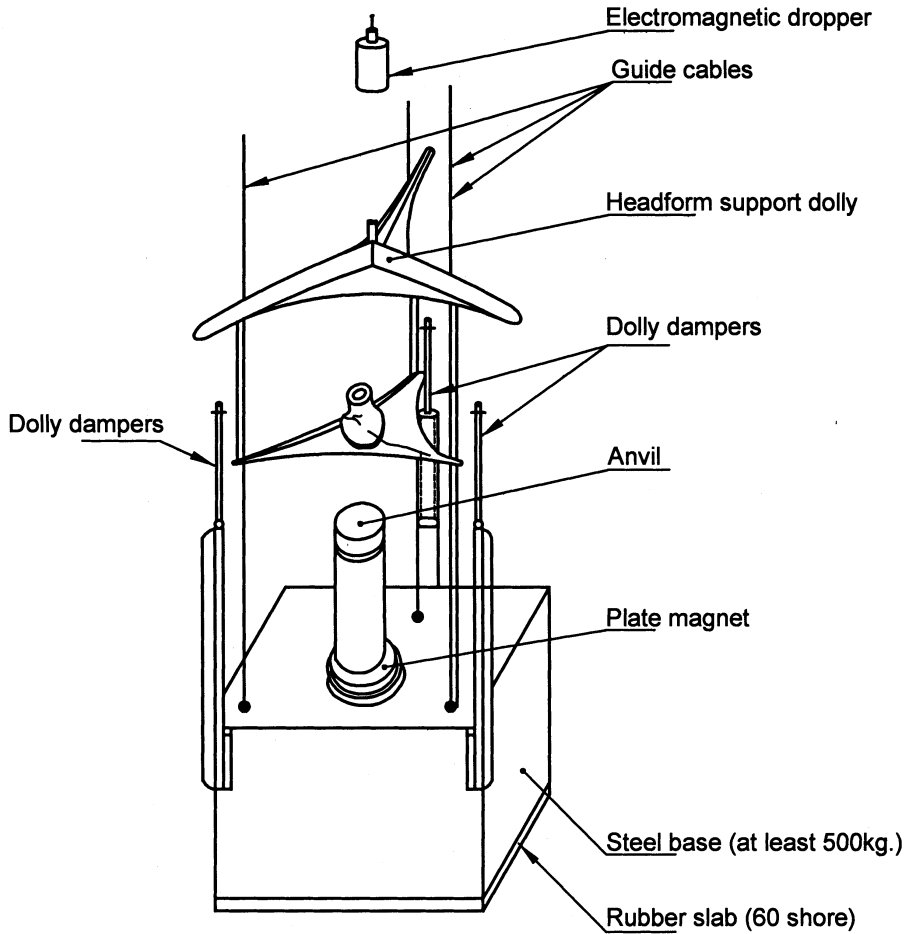


FIG. 5 TEST MACHINE HEAD FORM DROP ASSEMBLY

be impacted after the four other points, but only against the anvil specified in C-2.2.1.

C-3.4.2 After each impact the helmet shall be re-positioned correctly on the headform prior to the next impact, without interfering with the adjustment of the retention system. Before each impact on the Point *S* the helmet shall be re-positioned correctly on the headform and the retention system adjusted under the chin of the headform; if the system includes an adjustable chin strap, the strap is tightened as much as possible.

C-3.4.3 The points of impact are defined for each helmet (Fig. 4).

B, in the frontal area, situated in the vertical longitudinal plane of symmetry of the helmet and at an angle of 20° measured from *Z* above the 'AA' Plane.

X, in either the left or right lateral area, situated in the central transverse vertical plane and 12.7 mm below the 'AA' Plane.

R, in the rear area, situated in the vertical longitudinal plane of symmetry of the helmet and at an angle of 20° measured from *Z* above the 'AA' Plane.

P, in the area with a radius of 50 mm and a centre at the intersection of the central vertical axis and the outer surface of the helmet shell.

S, in the lower face cover area, situated within an area bounded by a sector of 20° divided symmetrically by the vertical longitudinal plane of symmetry of the helmet.

Impacts at Points *B*, *X* and *R* should be within 10 mm radius of the defined point.

C-3.5 Combination of Conditioning and Anvils

Conditioning: Solvent Plus	Anvils ¹⁾
Ambient	Flat and kerbstone
Heat	Kerbstone ²⁾
Low temperature ³⁾	Flat ²⁾
Ultraviolet radiation and moisture	Flat or kerbstone (to be selected by the laboratory)

¹⁾ Point 'S' shall only be impacted against the flat anvil.
²⁾ Only for the largest helmet size. For smaller headforms in the size range of the helmet type either anvil may be used.
³⁾ Only for each helmet size subjected to low temperature conditioning shall undergo the impact test at Point 'S'.

IS 4151 : 2015

ANNEX D

(Clause 7.3)

RIGIDITY TEST

D-1 PROCEDURE

D-1.1 The helmet, after undergoing ambient temperature and humidity conditioning shall be placed between two parallel plates by means of which a known load can be applied along the longitudinal axis¹⁾ (line *LL* in Fig. 6) or the transverse axis (line *TT* in Fig. 6). The surface of the plates shall be large enough to contain a circle of at least 65 mm in diameter. An initial load of 30 N shall be applied at a minimum plates speed of 20 mm/min, and after 2 min the distance between the plates shall be measured. The load shall then be increased by 100 N at a minimum plate speed of 20 mm/min and then wait for 2 min. This procedure shall be repeated until the application of a load of 630 N.

D-1.2 The load applied to the plates shall then be reduced to 30 N at a minimum plate speed of 20 mm/min, the distance between the plates shall then be measured.

D-1.3 The helmet used for the test along the longitudinal

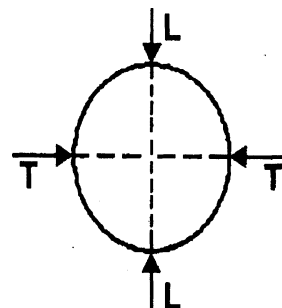


FIG. 6 REPRESENTATIVE FIGURE INDICATING
LONGITUDINAL AND TRANSVERSE AXIS

axis shall be a new helmet and another new helmet shall be used for the test along the transverse axis.

¹⁾ During the test along the longitudinal axis the contact point between the helmet and one of the two plates shall be the 'B' impact point.

ANNEX E

(Clause 7.4)

TEST FOR PROJECTIONS AND SURFACE FRICTION

E-1 TEST FOR PROJECTIONS AND SURFACE FRICTION (METHOD A)

E-1.1 Principle

The rotation-inducing forces caused by projections on the helmet and friction against the outer surface of the helmet which occur when a helmeted headform is dropped vertically on to an inclined anvil are measured in the longitudinal axis of the anvil. The peak force and its integral with respect to time over the duration of the positive impulse are used as performance criteria.

E-1.2 Apparatus (see Fig. 7)

The test apparatus shall comprise:

- a) an anvil rigidly fixed to a base,

- b) a free fall guidance system,
- c) a mobile system supporting the helmeted headform,
- d) a headform conforming to that referred to in E-1.2.5,
- e) a system which may be adjusted such that the point of impact can be brought into correspondence with the upper part of the face of the anvil,
- f) a means of recording the continuously changing transmitted anvil force during the impact, and
- g) a suitable energy absorbing base and catch net to prevent damage to the helmet after the impact.

E-1.2.1 Base

This shall conform to the requirements specified in **C-2.1**.

E-1.2.2 Anvil

E-1.2.2.1 The anvil is mounted securely at an angle of 15° to the vertical with provision for fore-and-aft adjustment. The anvil has a minimum width of 200 mm and is adaptable to carry either of two different impact surfaces as follows.

E-1.2.2.2 The bar anvil consists of a series of at least 5 horizontal bars at 40 mm centres. Each bar is made from a steel strip of height 6 mm and width 25 mm with its uppermost edge machined to a 1 mm radius and the lower 15 mm of its face chamfered at an angle of 15° so that, as mounted, the upper edge of each bar is fully exposed from vertically above. The bars are casehardened to a depth of approximately 0.5 mm.

E-1.2.2.3 The bar anvil should be used to assess the tangential forces and their integrals with time caused by projections on the helmet, for example visor fittings, screws, press studs and steps in the shell surface, etc.

E-1.2.2.4 The abrasive anvil is a sheet of grade 80 closed-coat aluminum oxide abrasive paper with a minimum supported length of 225 mm and is securely clamped to the base of the anvil to prevent slippage.

E-1.2.2.5 The abrasive anvil should be used to assess the tangential forces and their integrals with time caused by friction against the outer surface of the helmet. This is particularly applicable to selected areas of helmets, the outer surface of which either have significant variations of curvature or are made of more than one material.

E-1.2.2.6 The anvil is fitted with force transducer(s) connected to recording apparatus so that the transmitted longitudinal force component can be measured and continuously recorded with an accuracy of ± 5 percent during a glancing blow to any part of its exposed surface.

E-1.2.3 Mobile System and Guides

The mobile system supporting the headform shall be such that its characteristics do not affect the measurement of force in the anvil. It shall also be such that any point on the helmet can be positioned vertically above the anvil. The guides shall be such that the impact velocity is not less than 95 percent of the theoretical velocity.

E-1.2.4 Force and Measuring Assembly

The force transducers fitted to the anvil shall be capable of withstanding a maximum force of 20 000 N without damage. The measuring system including the anvil assembly shall have a frequency response in

accordance with channel frequency class (CFC) 1 000 (see ISO 6487).

E-1.2.5 Headform

The headform shall be that referred to in **C-2.5.1** characterized by the Symbol J.

E-1.3 Procedure

E-1.3.1 The drop height shall be such that the unit constituted by the headform and helmet falls on the test anvil at a velocity, which, immediately before impact, is equal to $8.5^{+0.15}_{-0}$ m/s.

E-1.3.2 Selection and Positioning of the Helmet

E-1.3.2.1 An appropriate size helmet shall be selected to fit the headform referred to in **C-2.5.1**. The horizontal axis of the helmet shall be determined by placing the helmet on a headform, of a type referred to in **C-2.5**, according to the requirements of Annex B. The helmet shall then be removed from that headform and placed on a headform of a type referred to in **C-2.5.1**. A load of 50 N is applied to the crown of the helmet in order to adjust the helmet on the headform such that there is contact between the crown of the headform and the inner surface of the helmet. The horizontal plane of the helmet shall then be adjusted to be within $90^\circ \pm 5^\circ$ of vertical axis of the headform. The retention system is then adjusted under the chin of the headform: if the system includes an adjustable chin strap, the strap is tightened as much as possible.

E-1.3.2.2 The test headform shall be so positioned that the chosen impact point on the helmet is vertically above the upper part of the face of the anvil.

E-1.3.2.3 The helmet shall be tested in any condition in which it may be placed on the market, that is both with and without accessories if they are supplied as original equipment. Helmets placed on the market with a visor shall be tested with the visor in the closed position.

E-1.3.3 Selection of Impact Points

E-1.3.3.1 Any point on the helmet shell may be selected. The impact point should be selected with regard to the anvil against which the helmet is to be tested, taking into account the function of the anvils given in **E-1.2.2.2** and **E-1.2.2.4**. The helmet shall be tested as many times as necessary to ensure that all notable features are evaluated.

When the abrasive anvil is used, evaluate the front, rear, sides and crown areas of the helmet, selecting within the general areas, sites on the outer surface which are likely to produce the greatest force and/or the greatest impulse where impulse is the integral of force with respect to time over the duration of the

IS 4151 : 2015

impact. Examples of such areas are those having the greatest radius of curvature (that is the flattest surface) or areas having more than one type of surface, for example a visor fixing cover plate or a painted shell partially overlaid by a fabric cover.

NOTE — The primary impact site on any projection is likely to be opposite to the site where the projection receives maximum support. For example, the primary impact site on a visor cover plate assembly is opposite to the area where the visor and cover plate locates in a recess in the shell.

E-1.3.3.2 The rim of the shell and the upper and lower edge of the visor situated within an area bounded by a sector of 120° divided symmetrically by the vertical longitudinal plane of symmetry of the helmet do not constitute a projection for the purpose of this test.

E-2 TEST FOR PROJECTIONS AND SURFACE FRICTION (METHOD B)

E-2.1 Principle

The rotation-inducing forces caused by projections on the helmets and friction against the outer surface of the helmets are assessed firstly by a shear impact on the projections using a shear edge against which the projections shall shear away, be detached, or permit the shear edge to slide past the projections. The friction is assessed by the displacement of a carriage abrading the outer surface of the helmet. The shear impact and abrading carriage displacement are generated by a drop weight device.

E-2.2 Apparatus (see Fig. 8)

The test apparatus shall comprise:

- a horizontal guided carriage with interchangeable attachments for abrasive paper or a shear edge.
- a horizontal guide and support for this carriage.
- a roller with a wire rope or a strap or a similar-flexible connection.
- lever connecting the headform to the test apparatus with a hinge.
- an adjustable system supporting the headform.
- a drop weight to load the lower end support of the wire rope, or a strap, after the weight is released.
- a system to support a headform and to apply a force to the helmet normal to the carriage.

E-2.2.1 Carriage

E-2.2.1.1 For friction assessment the carriage bears a sheet of grade 80 closed-coat aluminium oxide abrasive paper with a supported length of 300.0 (−0.0/+3.0) mm and securely clamped to the carriage to prevent

slippage. At its end towards the drop weight and in this direction the carriage has a 80 mm ± 1 mm long smooth steel area not being covered by the abrasive paper and higher than the rest of the carriage by the thickness of the abrasive paper plus 0.5 ± 0.1 mm.

E-2.2.1.2 For shear assessment the carriage is provided in the middle, with a bar made from a steel strip of height 6 mm and width 25 mm with its uppermost edges machined to a 1 mm radius. The bar is casehardened to a minimum depth of 0.5 mm.

E-2.2.1.3 The carriage and either attachment shall have a total mass of 5.0⁺⁰_{−0.2} kg.

E-2.2.2 Horizontal Guide

The horizontal guide, which guides and supports the carriage, may consist of two cylindrical bars on which the ball bearings of the carriage may freely travel.

E-2.2.3 Roller with a Wire Rope or Strap

The rollers shall have a diameter of at least 60 mm and lead the wire rope or strap from the horizontal into the vertical direction. The horizontal end of the wire rope or strap is fixed to the carriage; the vertical end is fixed to the drop weight.

E-2.2.4 Drop Weight

The drop weight shall have a mass of 15.0^{+0.5}_{−0} kg. For shear assessment the free drop height shall be 500.0^{+0.5}_{−0} mm with provision for further possible travel of at least 400 mm. For testing the friction assessment the free drop height shall be 500.0^{+0.5}_{−0} mm with provision for further possible travel of at least 400 mm.

E-2.2.5 Headform Support

The system supporting the headform shall be such that any point on the helmet can be positioned in contact with the upper surface of the carriage.

E-2.2.6 Lever and Hinge

A rigid lever shall connect the headform support of the test apparatus with a hinge. The height of the hinge pivot above the upper surface of the carriage shall not be greater than 150 mm.

E-2.2.7 Loading Mass

A loading system is used to generate a force of 400.0⁺¹⁰_{−0} N on the helmet normal to the surface of the carriage. This force shall be measured before each test.

E-2.2.8 Verification of the Test Apparatus

With the unloaded carriage and a drop height of 450 mm the velocity of the carriage after 250 mm of travel shall be 4.0 ± 0.1 m/s. The requirements shall be verified after every 500 helmet tests or once every 6 months whichever is sooner.

E-2.3 Procedure

E-2.3.1 Positioning of the Helmets

E-2.3.1.1 The helmet is placed on a headform of appropriate size in accordance with the requirements of Annex B. The helmet is tipped towards the rear so that the front edge of the helmet in the median plane is displaced by 25 mm; if the helmet includes an adjustable chin strap, the strap shall be tightened as much as possible. The headform shall be so positioned that the chosen location on the helmet can be positioned in contact with the upper surface of the horizontal carriage.

E-2.3.1.2 The helmet shall be tested in any condition in which it may be placed on the market, that is both with and without accessories if they are supplied as original equipment. Helmets placed on the market with a visor shall be tested with the visor in the closed position.

E-2.3.2 Test of Projection

The headform is adjusted in order to have the chosen projection on the carriage so that the shear edge is positioned 50 mm from the projection and makes lateral contact with the projection after the drop weight is released from its upper position.

E-2.3.3 Test of Outer-surface

The abrasive paper is mounted on the carriage in the position specified in E-2.2.1. The chosen outer surface of the helmet is lowered on to the abrading carriage at the centre of the flat surface without abrasive paper. A loading mass is applied in accordance with E-2.2.7.

The drop weight is released from its upper position in accordance with E-2.2.4. The abrasive paper shall be changed after every test.

E-2.3.4 Selection of Test Points

E-2.3.4.1 Any point on the helmet may be selected for friction and/or shear assessment. A helmet shall be tested as many times as necessary to ensure that all notable features are evaluated with one test only per feature. Re-orientate the helmet as necessary to allow every feature to be tested. For shear assessment evaluate all different external projections greater than 2 mm above the outer surface of the shell. For friction assessment, evaluate areas of the outer surface that are likely to produce the greatest friction.

E-2.3.4.2 The rim of the shell and the upper and lower edge of the visor situated within an area bounded by a sector of 120° divided symmetrically by the vertical longitudinal plane of symmetry of the helmet do not constitute a projection for the purpose of this test.

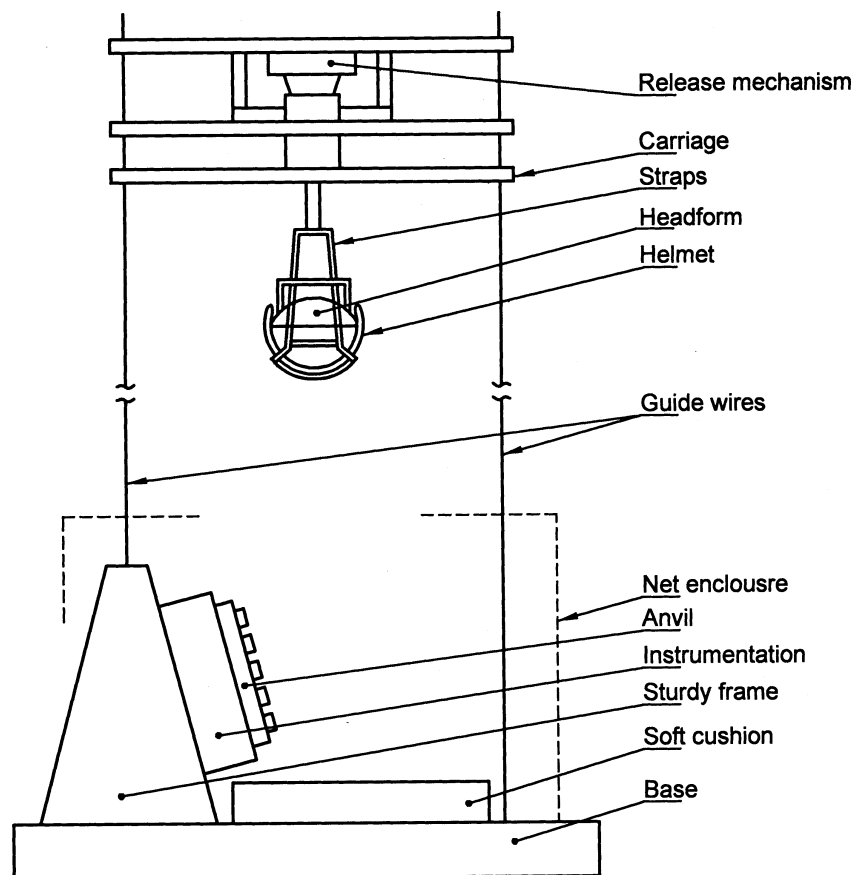


FIG. 7 EXAMPLE OF A SUITABLE TEST APPARATUS FOR PROJECTIONS AND SURFACE FRICTION (METHOD A)

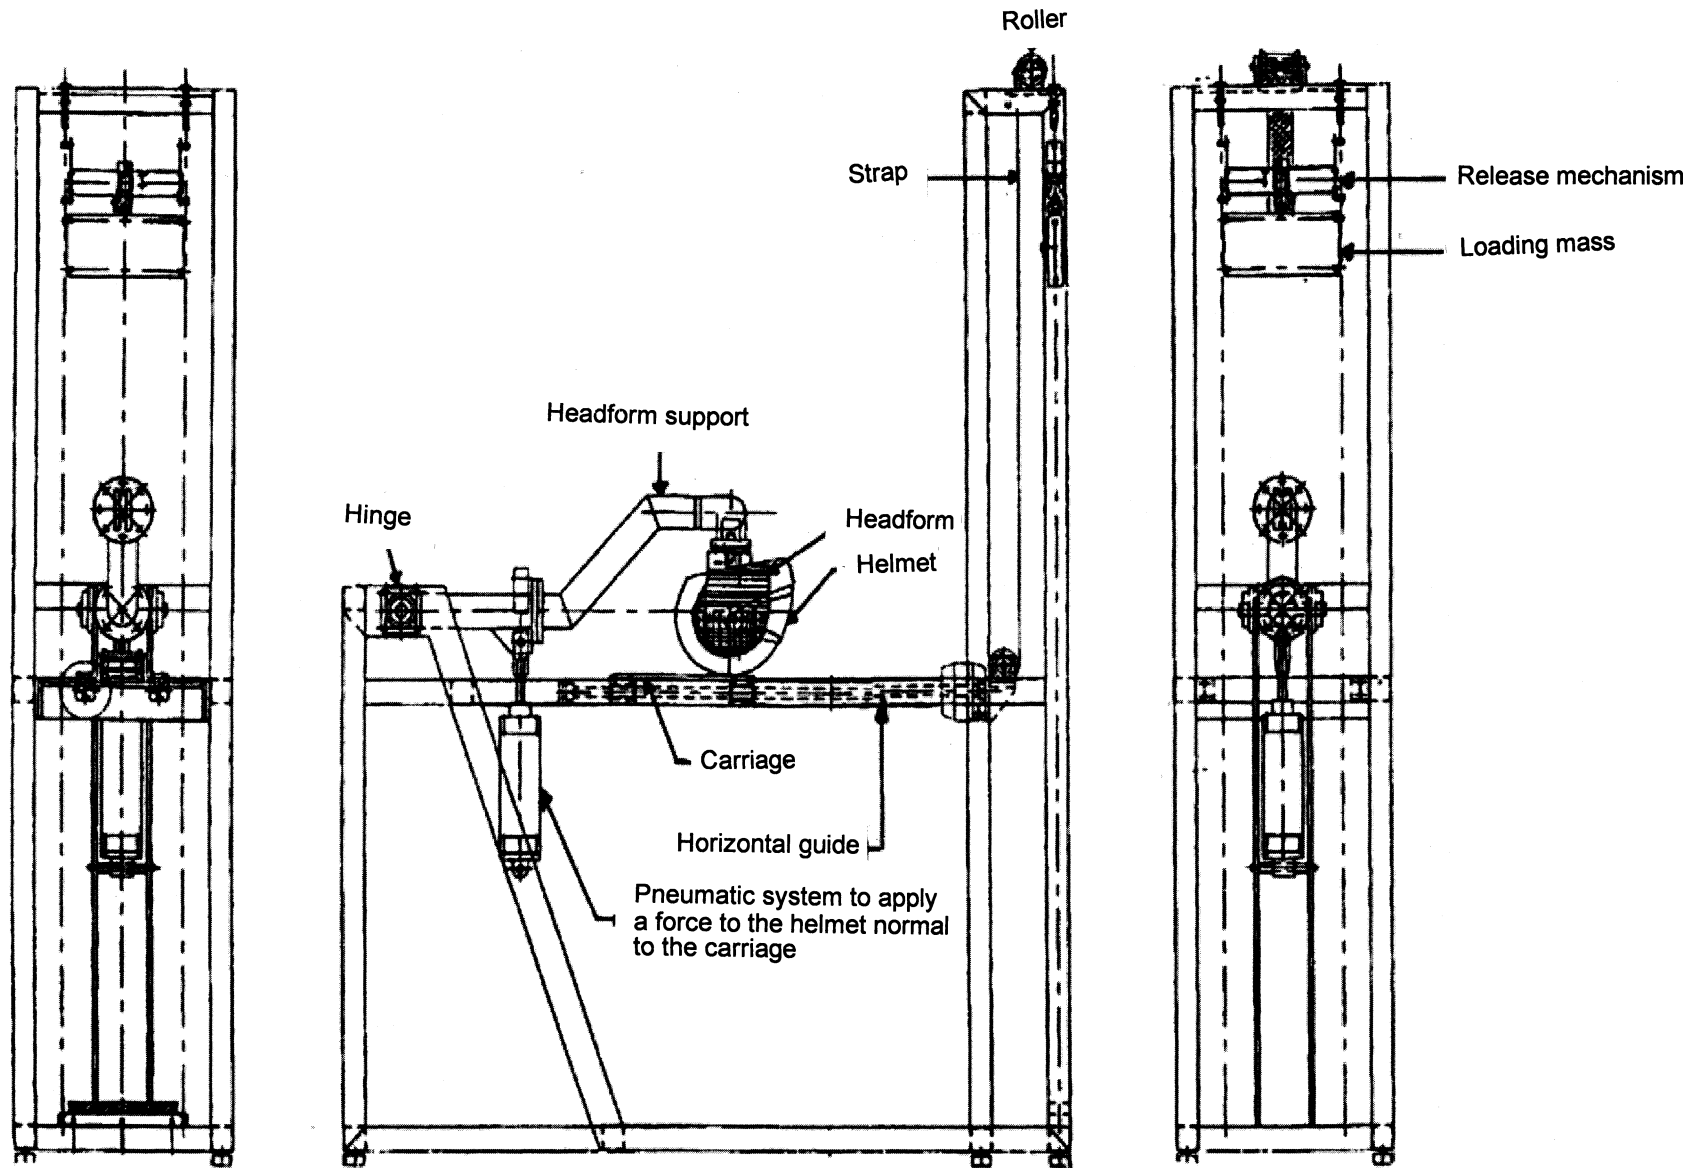


FIG. 8 EXAMPLE OF A SUITABLE TEST APPARATUS FOR PROJECTIONS AND SURFACE FRICTION (METHOD B)

ANNEX F

(Clauses 6.4.1 and 7.5)

DYNAMIC TEST OF RETENTION SYSTEM

F-1 PROCEDURE

F-1.1 The helmet shall be positioned as prescribed in Annex B.

F-1.2 In this position the helmet shall be held by the shell (see Fig. 9) at a point traversed by the vertical axis passing through the centre of gravity of the headform. The headform is equipped with a load-bearing device aligned with the vertical axis passing through the centre of gravity of the headform and with a device to measure the vertical displacement of the point of application of the force.

F-1.3 A guide and arrest device for a falling mass shall then be attached below the headform. The mass of the headform so equipped in this way shall be 15 ± 0.5 kg; this produces the preloading on the retention system for determining the position from which the vertical displacement of the point of application of the force shall be measured.

F-1.4 The falling mass of $10 \text{ kg} \pm 0.1 \text{ kg}$ shall then be released and shall drop in a guided free fall from a height of $750 \text{ mm} \pm 5 \text{ mm}$.

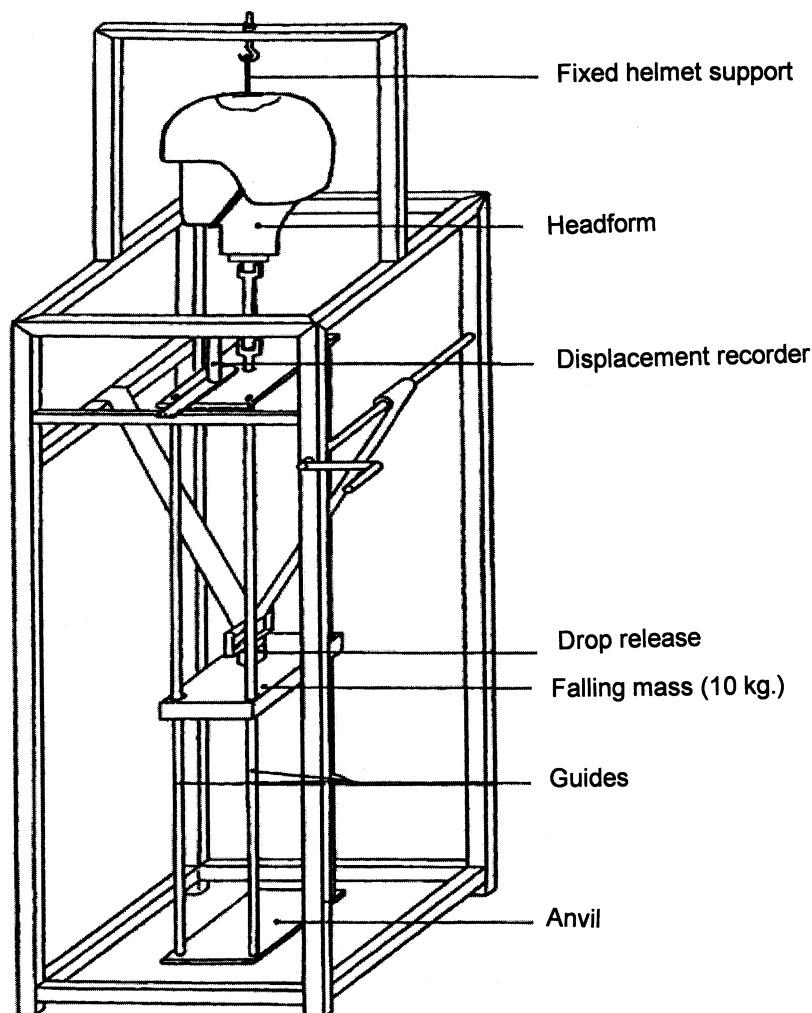


FIG. 9 DYNAMIC TEST OF RETENTION SYSTEM

IS 4151 : 2015

ANNEX G

(Clause 7.6)

AUDIBILITY TEST

G-1 APPARATUS

G-1.1 Measuring Apparatus

Measuring apparatus shall consist of a headform and sound level meter in accordance with IS 15575. The microphone of sound level meter shall be fitted at a place corresponding to the right or left human ear's location.

G-1.2 Sound Source

The sound surface shall be a horn conforming to Type 2A of IS 1884 [which has sound pressure level range of 90 to 115 dB(A)]. The sound source shall be located so that sound is incident from back of the headform.

G-2 PROCEDURE

G-2.1 This test shall be carried out under the prevailing

atmospheric conditions and the back-ground noise level shall be such that the reading indicated on the sound level meter by the noise is at least 10 dB of below that of the horn sound level.

This test shall be carried out in an open space in which there is no obstacle within a radius of 12 m and no acoustical focusing affects or nearby parallel walls.

G-2.2 The horn shall be mounted 1.2 m above the ground and shall be fixed in a rigid manner on a base whose mass shall be at least 10 times that of the horn and not less than 15 kg and shall be adjustable sideways and up and down. The sound waves are emitted from the horn by using suitable 12 V dc power supply and are directed towards the rear of the headform at the distance of 2 m. The two readings are taken with and without helmet. The difference shall be recorded to the nearest dB.

ANNEX H

(Clause 7.7)

RETENTION (DETACHING) TEST


H-1 PROCEDURE

H-1.1 The helmet previously conditioned at ambient temperature and hygrometry, shall be placed on and secured to the appropriate headform, selected from those listed in Fig. 2 in accordance with the requirements of C-3.2.1.

H-1.2 A device to guide and release a falling mass (the

total mass being $3 \text{ kg} \pm 0.1 \text{ kg}$) is hooked on to the rear part of the shell in the median vertical plane of the helmet, as shown in Fig. 10.

H-1.3 The falling mass of $10 \text{ kg} \pm 0.01 \text{ kg}$ is then released and dropped in a guided free fall from a height of $0.50 \text{ m} \pm 0.01 \text{ m}$. The guiding device shall be such as to ensure that the impact speed is not less than 95 percent of the theoretical speed.

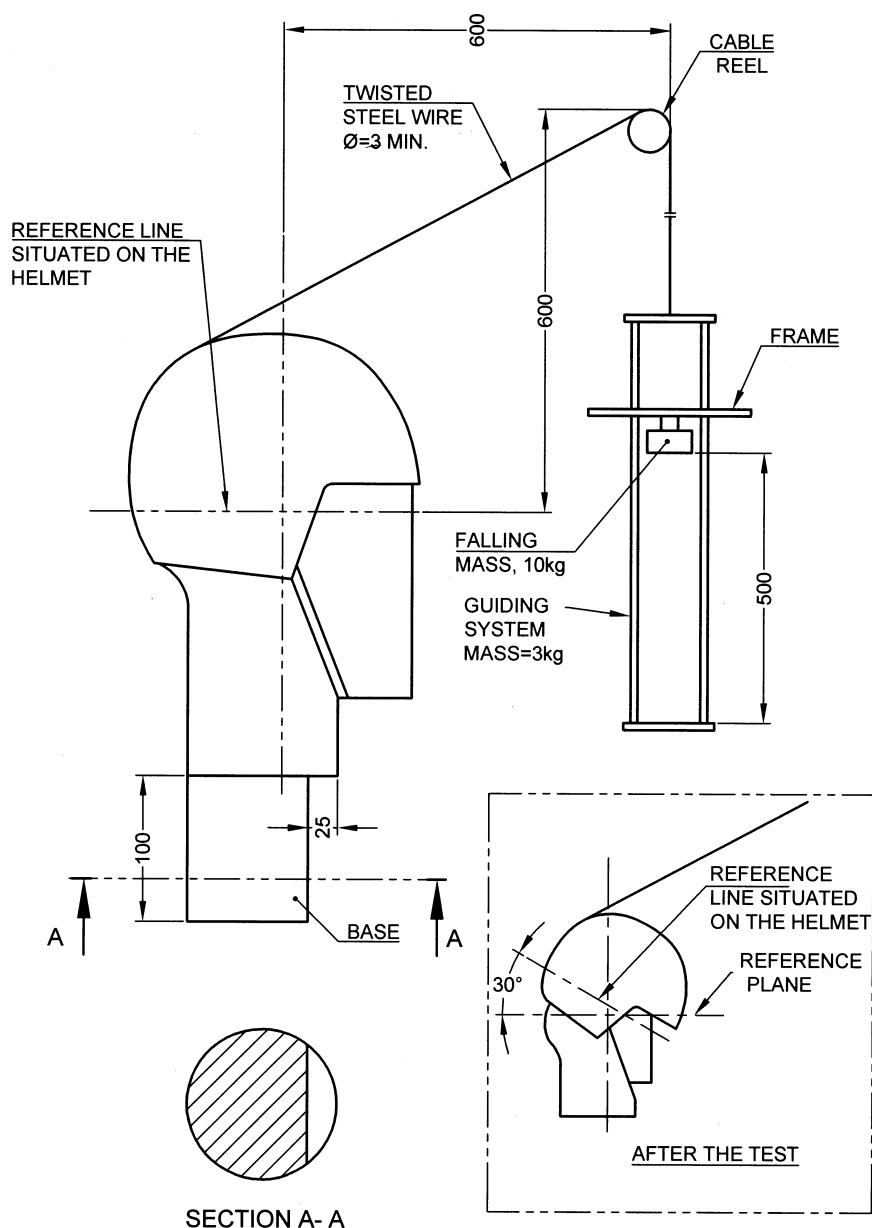

All dimensions in millimetres.

FIG. 10 RETENTION (DETACHING) TEST APPARATUS

IS 4151 : 2015

ANNEX J

(Clause 7.8)

MICRO-SLIP TEST OF THE CHIN STRAP

J-1 PROCEDURE

J-1.1 The test rig consists of a flat horizontal robust base, a weight for applying a load, a freely rotatable horizontal roller of diameter not less than 20 mm, and in the same horizontal plane as the top of the roller a clamp capable of reciprocating horizontal motion at right angles to the axis of the roller with a total amplitude of 50 ± 5 mm at a frequency between 0.5 Hz and 2 Hz. A typical test machine is shown in Fig. 11.

J-1.2 Take a sample of the strap at least 300 mm long, including the tensioning and adjusting device and any additional strap fastening. Fix the upper end of the strap to the reciprocating clamp level with the top of the

roller and drape the strap over the roller. Attach a weight to the lower end of the strap so that when the weight is lifted by the strap it imposes a tensile force of 20 ± 1 N. Adjust the apparatus so that when the reciprocating clamp is at the centre of its motion the weight is just resting on the base with the strap barely in tension and the strap buckle is between the clamp and roller and will not touch the roller during reciprocation.

J-1.3 Operate the reciprocating clamp for 20 cycles. Note the position of the components on the strap. Operate the reciprocating clamp for 500 cycles then record the distance through which the components have slipped along the strap.

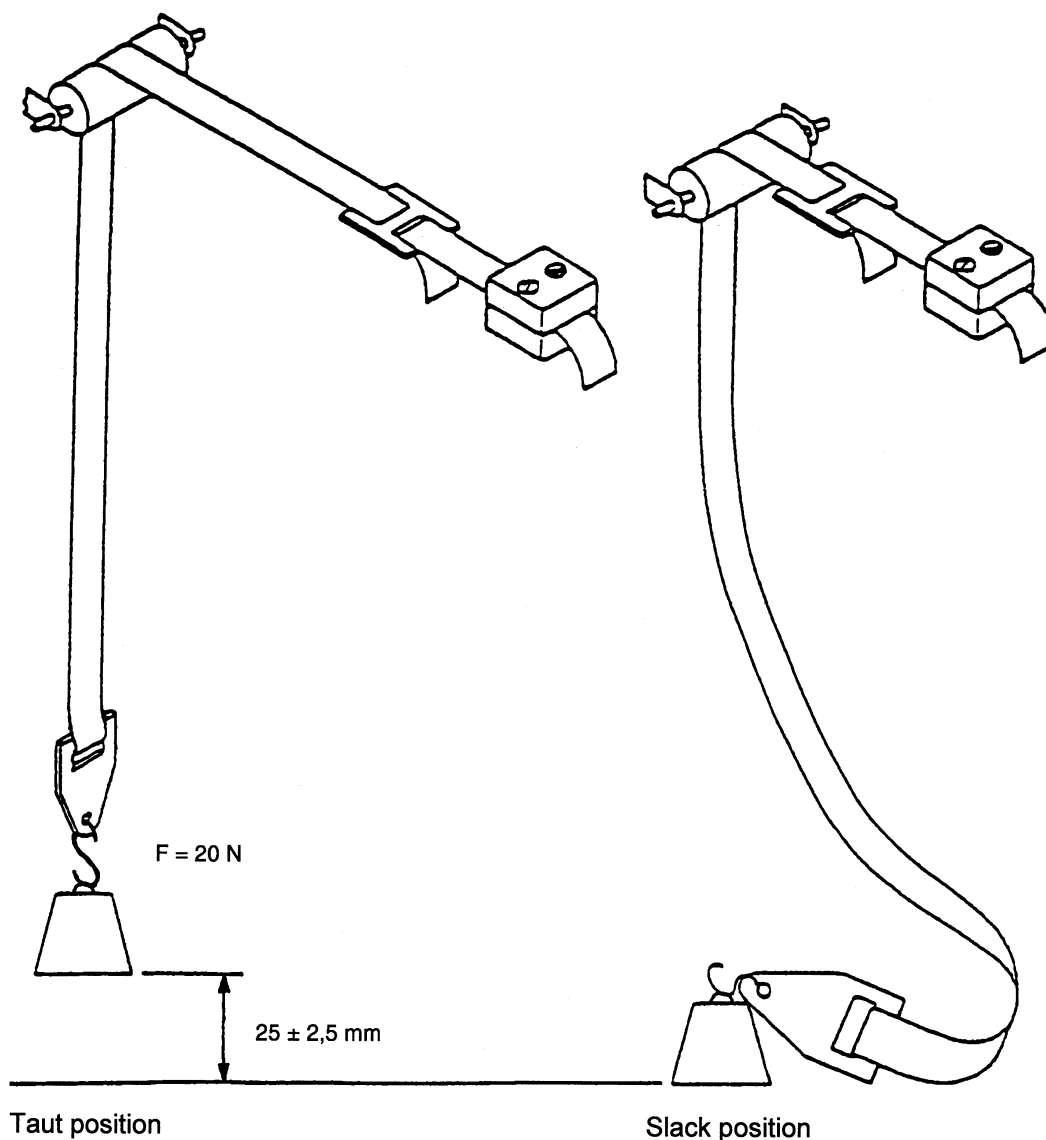


FIG. 11 APPARATUS FOR TESTING SLIPPAGE OF THE CHIN STRAP

ANNEX K

(Clauses 7.9)

TEST FOR RESISTANCE TO ABRASION OF THE CHIN STRAP

K-1 PROCEDURE

K-1.1 The test rig as mentioned is similar to that described in **J-1.1** except that the amplitude is $100 \text{ mm} \pm 10 \text{ mm}$ and the strap passes over a representative surface of the associated adjuster or other strap fitting through an appropriate angle. The typical test machine is shown in Fig. 12.

K-1.2 Select an arrangement of the apparatus appropriate for the particular design of both the strap and the fitting likely to cause abrasion. Grip one end of the strap in the oscillating clamp, arrange the strap to be threaded through the fitting as designed and hang a weight on the end to tension the strap with a force of

$20 \pm 1 \text{ N}$. Mount or otherwise steady the fitting in such a position that movement of the oscillating clamp slides the strap through the fitting, in a manner simulating slippage of the fitting on the strap when the helmet is on the head.

K-1.3 Oscillate the clamp for a total of 5 000 cycles at a frequency between 0.5 and 2 Hz.

K-1.4 Mount the abraded strap in a tensile testing machine using clamps which avoid local breakage of the strap, and so that there is a length of $150 \pm 15 \text{ mm}$ of strap, including the abraded portion, between the clamps. Operate the machine to stretch the strap at a speed of $100 \text{ mm} \pm 20 \text{ mm per min}$.

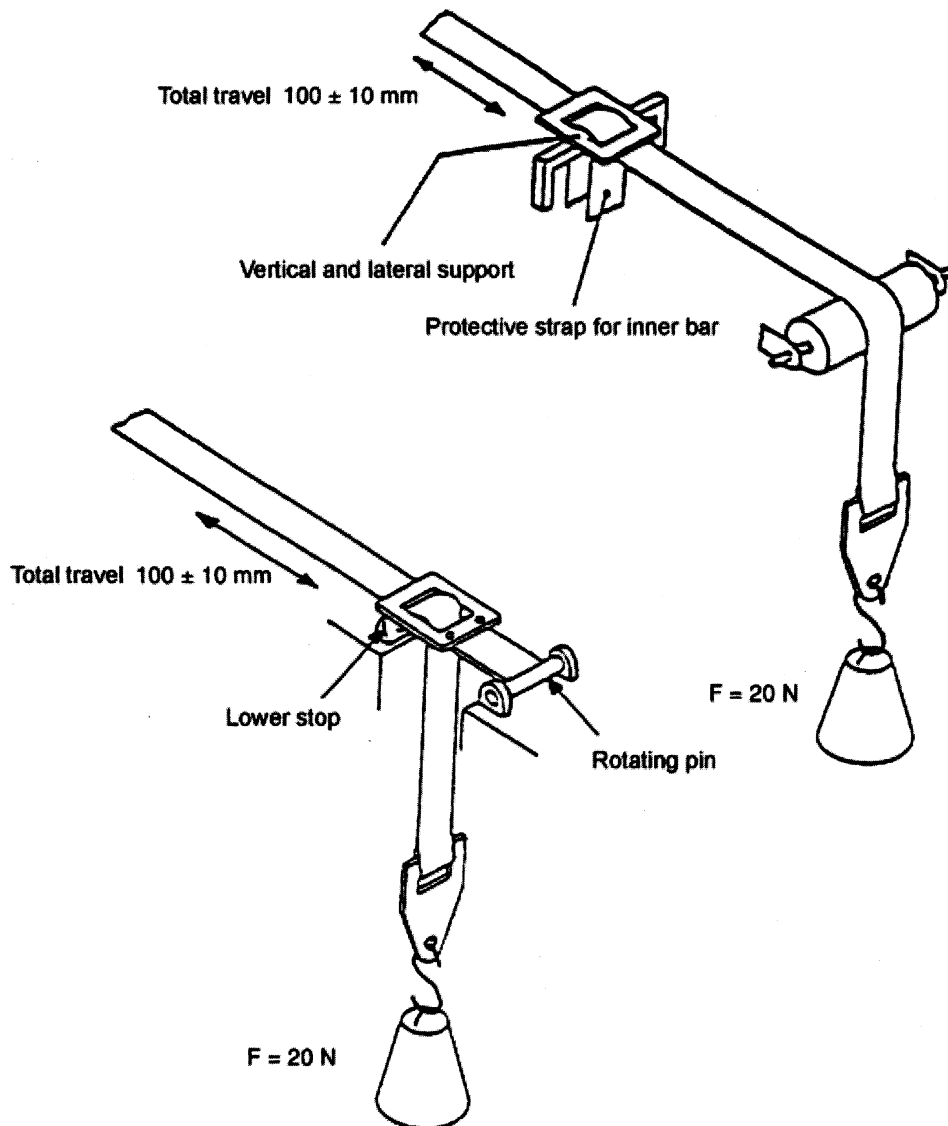


FIG. 12 APPARATUS FOR TESTING ABRASION OF THE CHIN STRAP


IS 4151 : 2015

ANNEX M

[Clause C-2.5.2 (a)]

REFERENCE HEADFORMS

(Above Reference Plane)

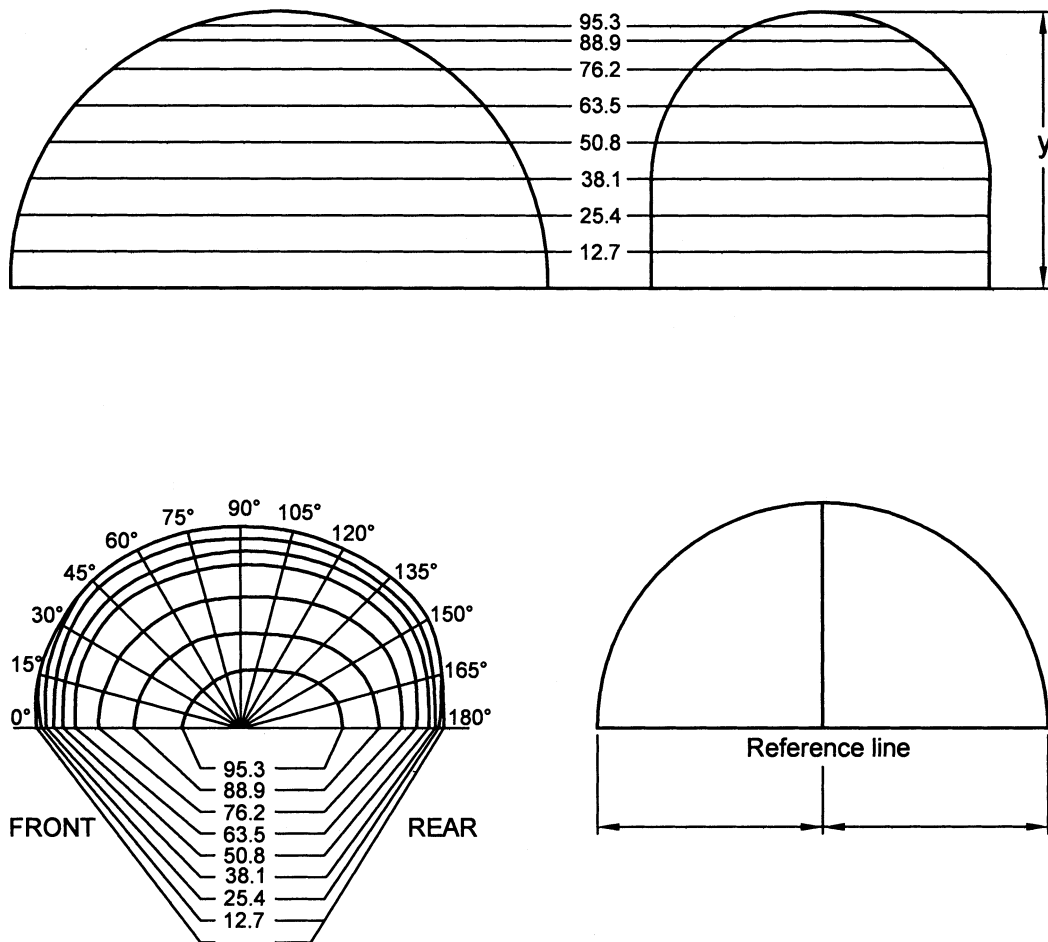

All dimensions in millimetres.

FIG. 13 REFERENCE HEADFORMS
(SHAPE, DIMENSIONS ABOVE REFERENCE PLANE)

Headform A										(Dimensions in millimetres.)			
Height Above Reference Line	0° Front	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	88.1	86.4	83.1	75.4	69.9	66.8	66.5	69.3	73.4	78.8	84.1	87.6	88.1
12.7	86.9	85.3	83.1	75.4	69.9	66.8	66.5	69.3	73.4	78.8	84.1	87.6	88.1
25.4	84.6	83.6	82.3	75.4	69.9	66.8	66.5	69.3	73.4	78.8	84.1	86.1	86.1
38.1	80.8	80.3	79.5	72.9	67.6	65.3	65.0	67.6	71.6	76.5	81.3	82.8	82.8
50.8	74.7	74.4	74.0	68.1	63.2	61.0	60.7	63.2	66.8	71.6	73.7	76.7	76.7
63.5	64.8	64.8	64.8	59.9	55.6	53.3	53.1	55.4	59.2	63.5	67.6	67.6	67.6
76.2	45.7	45.7	45.5	43.4	41.4	40.4	40.4	42.4	46.2	50.5	54.6	54.6	54.6
82.6	31.0	31.2	31.2	31.0	30.0	29.7	30.2	32.5	36.1	40.4	43.9	44.5	44.5
Dimension: Y : 89.7 mm – Head circumference : 500 mm													

IS 4151 : 2015

Headform C													(Dimensions in millimetres.)	
Height Above Reference Line	0° Front	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear	
0	91.2	89.7	86.1	78.7	72.6	69.9	69.6	72.4	76.7	82.0	87.4	90.4	91.2	
12.7	89.9	88.6	86.1	78.7	72.6	69.9	69.6	72.4	76.7	82.0	87.4	90.4	91.2	
25.4	87.6	87.1	85.3	78.7	72.6	69.9	69.6	72.4	76.7	82.0	87.4	89.2	89.9	
38.1	84.6	83.8	82.3	76.5	70.6	68.1	68.1	70.6	74.7	79.8	84.3	85.6	86.4	
50.8	78.5	78.2	77.5	72.4	66.5	64.3	64.3	66.5	70.4	75.4	79.5	80.3	80.8	
63.5	69.3	69.1	69.1	64.5	59.4	57.2	57.4	59.7	63.5	68.3	71.9	71.9	71.9	
76.2	52.3	52.3	52.3	49.3	46.2	45.2	45.7	48.0	51.6	56.1	59.4	59.7	59.9	
82.6	39.9	39.9	39.9	38.1	37.1	36.6	36.8	38.6	41.9	46.2	50.5	51.1	51.3	
88.9	20.6	20.6	20.6	21.3	22.1	22.9	23.9	25.4	28.2	31.8	34.3	34.5	34.5	
Dimension: Y : 92.7 mm – Head circumference : 520 mm														

Headform E (Dimensions in millimetres.)													
Height Above Reference Line	0° Front	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	94.5	93.0	89.7	82.0	76.2	73.2	72.9	75.7	79.8	84.8	90.7	93.7	94.5
12.7	93.2	91.9	89.7	82.0	76.2	73.2	72.9	75.7	79.8	84.8	90.7	93.7	94.5
25.4	91.2	90.7	88.9	82.0	76.2	73.2	72.9	75.7	79.8	84.8	90.7	92.7	93.0
38.1	87.6	87.9	85.9	80.0	74.7	71.6	71.4	74.2	77.7	82.6	88.6	89.2	89.2
50.8	82.0	82.3	81.0	75.4	70.4	67.8	67.6	70.4	73.9	79.0	83.8	84.3	84.3
63.5	73.4	73.7	73.4	68.6	64.0	61.5	61.2	63.5	67.1	71.9	76.5	76.5	76.5
76.2	57.7	57.9	58.2	55.9	52.6	50.5	50.3	52.1	55.1	59.7	64.5	64.8	64.8
82.6	46.5	46.5	46.5	45.2	43.2	42.4	42.9	44.4	47.5	52.3	56.4	56.9	56.6
88.9	30.5	30.5	30.7	31.0	31.2	31.2	31.8	33.8	36.8	40.4	43.9	44.2	44.2
Dimension: Y : 96 mm – Head circumference : 540 mm													

Headform G													(Dimensions in millimetres.)	
Height Above Reference Line	0° Front	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear	
0	97.5	95.8	93.0	85.1	79.5	76.2	75.9	78.5	83.1	88.4	94.0	97.0	97.5	
12.7	96.3	95.3	92.7	85.1	79.5	76.2	75.9	78.5	83.1	88.4	94.0	97.0	97.5	
25.4	93.7	92.7	91.4	85.1	79.5	76.2	75.9	78.5	83.1	88.4	94.0	95.8	96.3	
38.1	90.4	89.7	88.9	83.3	77.7	75.2	74.9	77.0	81.3	86.6	91.7	92.7	93.0	
50.8	86.1	85.6	84.6	79.0	73.7	71.1	70.9	73.2	78.0	82.8	87.1	87.9	88.1	
63.5	77.5	77.2	76.5	72.1	67.3	64.5	64.3	66.5	70.9	75.9	79.0	79.0	80.0	
76.2	63.8	63.8	64.0	61.2	57.4	54.9	54.9	56.9	61.5	66.5	68.8	69.1	69.1	
88.9	39.9	39.6	39.6	39.1	38.4	37.8	38.4	40.4	44.2	49.8	52.8	53.1	53.1	
95.3	20.6	20.6	20.6	21.3	22.4	23.4	23.9	25.4	28.7	33.6	37.8	39.1	39.1	
Dimension: Y : 99.1 mm – Head circumference : 560 mm														

Headform J													(Dimensions in millimetres.)	
Height above reference line	0° Front	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear	
0	100.8	98.8	96.3	88.1	82.0	79.5	79.2	82.0	85.9	91.7	96.8	100.1	100.8	
12.7	99.6	98.0	95.8	88.1	82.0	79.5	79.2	82.0	85.9	91.7	96.8	100.1	100.8	
25.4	96.8	95.8	94.5	88.1	82.0	79.5	79.2	82.0	85.9	91.7	96.5	98.3	98.8	
38.1	93.7	92.7	91.9	86.1	80.0	77.2	77.7	80.0	83.8	89.4	94.5	95.8	96.0	
50.8	89.2	88.6	87.9	82.0	76.2	73.9	74.4	77.0	80.5	85.9	90.4	90.9	90.9	
63.5	81.5	80.8	81.0	75.9	70.6	68.1	68.3	71.1	71.4	79.5	83.8	84.1	84.1	
76.2	69.3	69.1	69.3	65.3	61.2	58.9	59.2	61.7	65.0	69.3	73.2	73.4	73.4	
88.9	47.2	47.5	48.0	46.2	44.4	43.7	44.2	46.2	50.0	54.1	58.2	58.4	58.4	
95.3	32.8	32.8	33.3	32.5	32.0	32.3	33.0	35.1	38.1	42.2	46.5	47.2	47.2	
Dimension: Y : 102.4 mm – Head circumference : 570 mm														

IS 4151 : 2015

<i>Headform K</i> (Dimensions in millimetres.)													
<i>Height Above Reference Line</i>	0° Front	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	102.4	101.1	97.0	89.7	84.1	81.3	80.8	83.3	87.9	92.7	98.3	101.6	102.4
12.7	101.1	100.1	97.0	89.7	84.1	81.3	80.8	83.3	87.9	92.7	98.3	101.6	102.4
25.4	98.8	98.3	96.3	89.7	84.1	81.3	80.8	83.3	87.9	92.7	98.3	99.8	100.6
38.1	95.5	95.2	93.7	87.4	82.0	79.5	79.5	81.5	85.9	90.4	95.5	97.0	97.7
50.8	90.9	90.4	89.7	83.6	78.5	76.2	76.2	78.5	83.1	87.4	91.9	92.5	93.2
63.5	83.1	82.8	82.0	77.2	72.1	69.9	70.4	72.4	76.7	80.8	84.6	85.1	85.6
76.2	71.1	71.1	71.4	68.1	63.8	61.2	61.2	63.0	67.1	71.6	74.9	75.2	75.2
88.9	51.8	51.8	51.8	50.8	48.5	46.7	47.2	49.3	52.1	56.9	60.7	60.7	60.7
95.3	37.6	37.3	37.3	37.3	36.8	36.6	37.1	38.9	42.2	47.0	51.1	51.8	51.3
101.6	18.3	17.8	17.8	18.0	18.5	19.3	20.1	21.8	24.9	29.0	33.8	36.1	36.6
Dimension: Y : 102.4 mm – Head circumference : 570 mm													



<i>Headform M</i> (Dimensions in millimetres.)													
<i>Height Above Reference Line</i>	0° Front	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	105.7	103.9	100.6	92.7	86.9	84.1	83.8	86.4	90.7	96.0	102.1	105.7	105.7
12.7	104.4	103.4	100.3	92.7	86.9	84.1	83.8	86.4	90.7	96.0	102.1	105.7	105.7
25.4	102.1	101.6	99.8	92.7	86.9	84.1	83.8	86.4	90.7	96.0	102.1	104.4	104.4
38.1	99.3	98.8	97.8	90.9	85.3	82.6	82.3	84.6	88.9	94.0	99.8	100.8	101.1
50.8	95.0	94.7	93.5	86.9	81.3	79.0	78.7	81.0	85.3	90.4	96.0	96.5	96.3
63.5	87.1	87.1	86.9	80.8	75.4	73.2	73.2	75.4	79.5	84.8	89.4	89.7	89.4
76.2	75.9	76.2	76.2	71.6	67.1	64.8	64.8	66.5	70.6	75.4	80.0	80.0	79.3
88.9	58.2	58.2	58.2	56.6	54.6	52.3	52.3	53.8	56.9	61.7	66.8	67.1	66.8
95.3	45.5	45.7	46.0	46.0	44.5	43.4	43.2	44.5	47.2	52.1	57.7	58.2	57.9
101.6	26.4	26.2	26.7	27.7	28.7	29.5	30.0	31.2	34.0	38.6	42.7	43.2	42.7
Dimension: Y : 107.2 mm – Head circumference : 600 mm													

<i>Headform O</i> (Dimensions in millimetres.)													
<i>Height Above Reference Line</i>	0° Front	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	108.7	107.4	103.4	95.8	90.4	87.6	87.1	90.2	94.2	99.8	105.4	108.0	108.7
12.7	107.7	106.4	103.4	95.8	90.4	87.6	87.1	90.2	94.2	99.8	105.4	108.0	108.7
25.4	105.2	104.4	102.9	95.8	90.4	87.6	87.1	90.2	94.2	99.8	105.4	106.7	106.9
38.1	102.4	102.1	101.1	94.2	88.9	86.1	85.9	88.9	93.0	98.6	103.4	104.1	104.1
50.8	97.8	97.5	96.5	90.2	85.1	82.3	82.6	85.3	89.9	94.7	99.6	100.3	100.3
63.5	91.2	91.2	90.4	84.3	79.2	76.7	77.0	79.8	83.8	88.4	93.0	93.2	93.2
76.2	81.0	81.3	80.8	76.2	71.6	69.3	69.6	71.9	75.7	80.5	84.6	84.6	84.6
88.9	64.5	64.5	64.5	61.5	58.4	57.2	57.7	60.2	63.5	68.1	71.9	71.4	71.9
95.3	54.1	53.8	54.1	52.6	50.3	49.0	49.5	51.6	55.4	60.5	64.3	64.0	64.0
101.6	37.6	37.6	38.1	38.4	38.1	37.8	38.4	40.4	43.4	48.0	51.3	51.3	51.1
Dimension: Y : 110.2 mm – Head circumference : 620 mm													

ANNEX N

[Clause C-2.5.2 (b) and C-2.5.3]


REFERENCE HEADFORMS (Below Reference Plane)

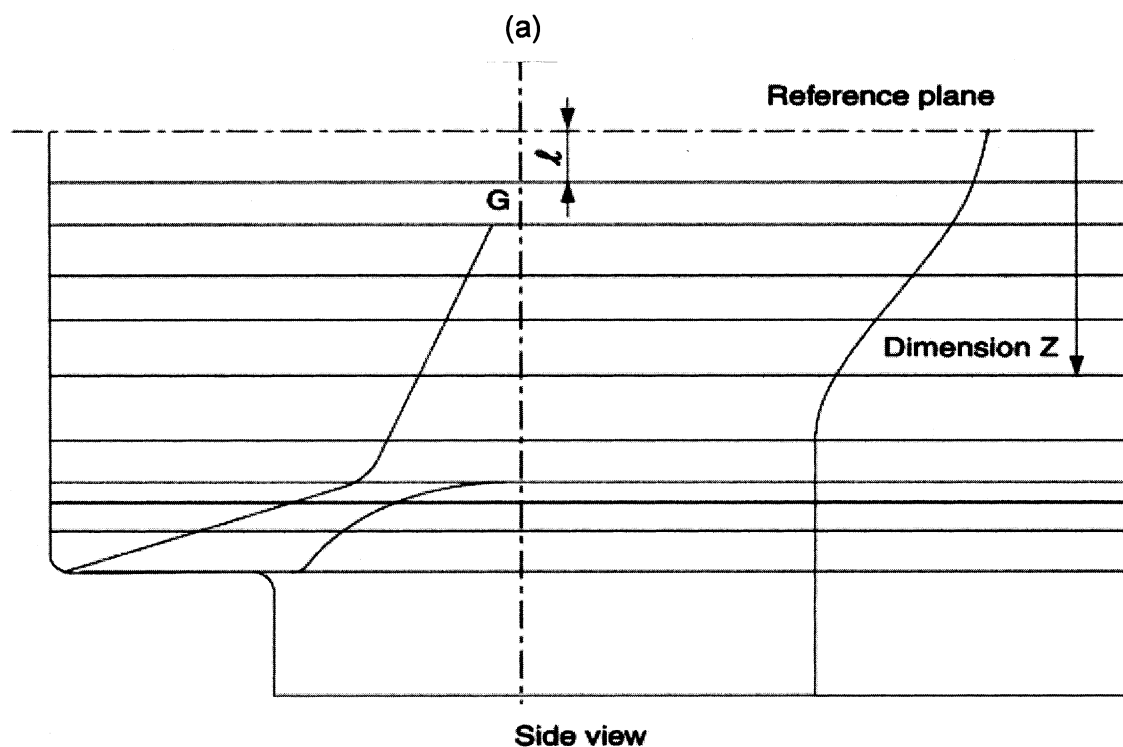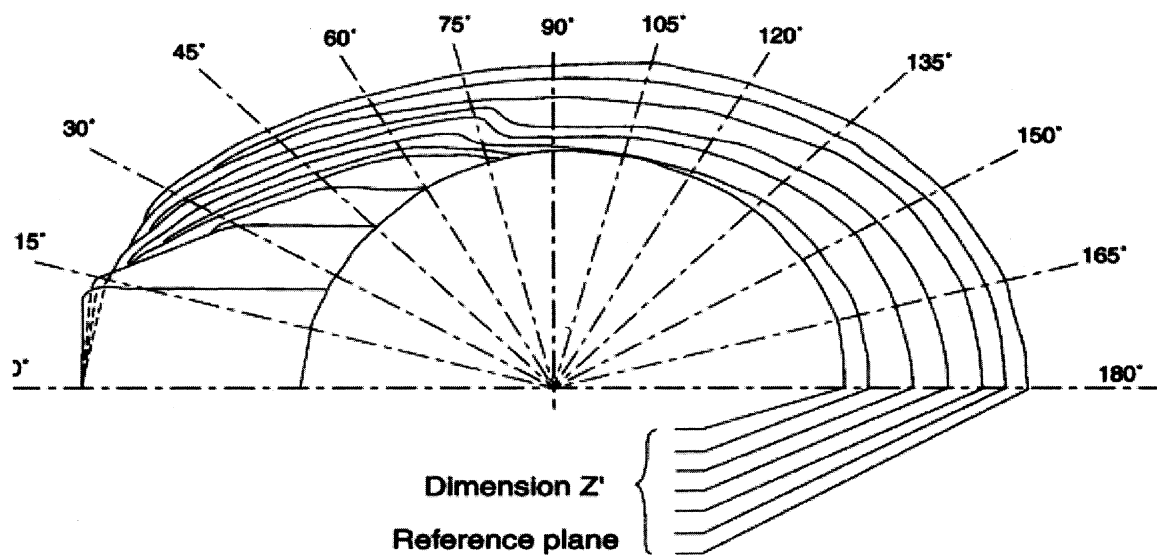

(b)

FIG. 14 REFERENCE HEADFORMS (*Continued*)
(SHAPE, DIMENSIONS BELOW REFERENCE PLANE)

IS 4151 : 2015

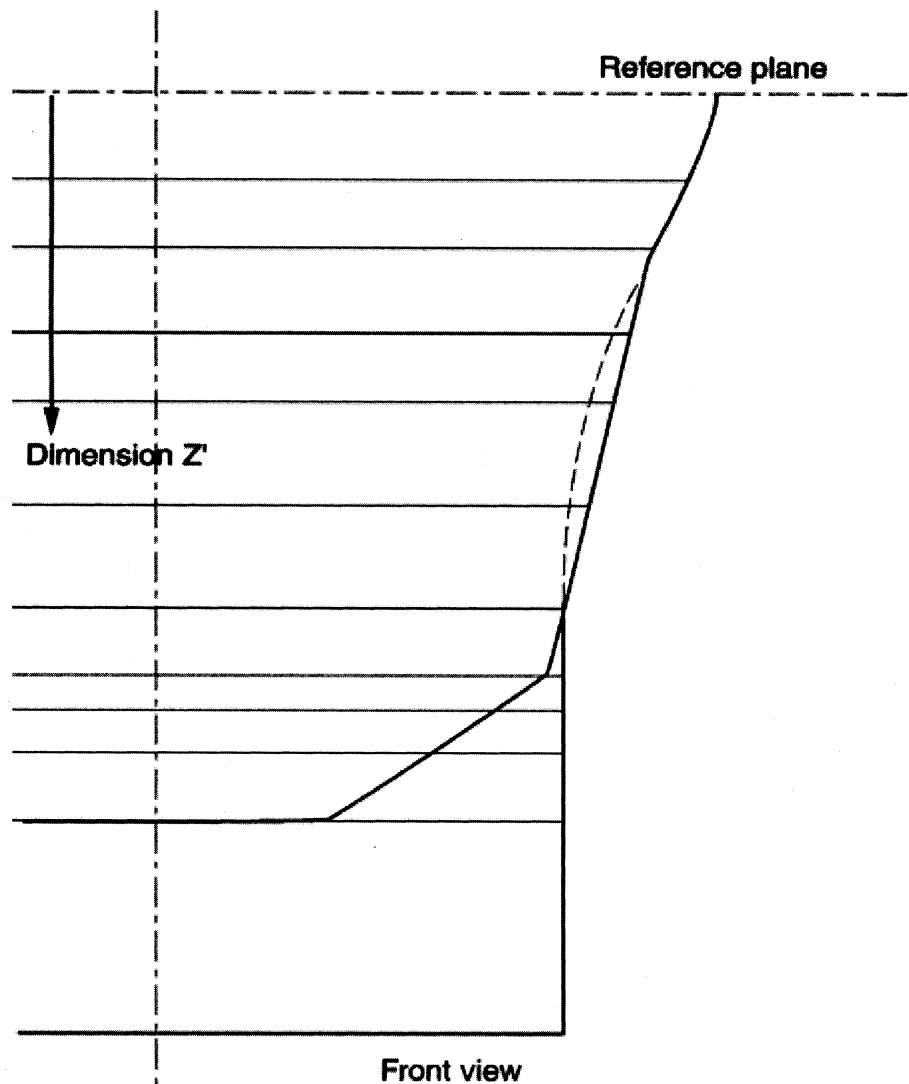

(c)

FIG. 14 REFERENCE HEADFORMS
(SHAPE, DIMENSIONS BELOW REFERENCE PLANE)

Headform A													(Dimensions in millimetres.)
Dimension Z'	0°	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	88.0	86.5	83.0	75.5	70.0	67.0	66.5	69.5	73.5	78.5	84.0	87.0	88.0
-11.1	88.0	86.5	82.5	74.5	68.5	66.0	66.0	68.5	72.0	77.0	81.5	84.5	85.0
-19.9	88.0	88.0	82.5	74.0	66.5	63.0	61.5	64.5	67.5	72.5	77.0	80.0	80.5
-30.6	88.0	89.5	81.0	71.5	65.0	62.0	56.0	58.0	61.5	66.5	71.0	73.5	74.0
-39.4	88.0	89.5	79.0	69.0	63.0	60.0	54.0	55.0	58.0	61.5	65.0	67.5	67.0
-52.5	88.0	89.5	77.0	67.0	60.5	54.0	51.5	52.0	53.5	56.5	59.0	60.0	58.5
-65.6	88.0	89.5	75.5	65.0	58.5	52.5	50.5	51.0	51.5	52.5	53.0	54.0	54.5
-74.4	88.0	89.5	73.5	62.5	58.0	51.0	50.5	51.0	51.5	52.5	53.0	54.0	54.5
-78.8	88.0	89.5	71.5	60.5	49.5	50.0	50.5	51.0	51.5	52.5	53.0	54.0	54.5
-84.4	88.0	89.5	69.5	47.5	49.5	50.0	50.5	51.0	51.5	52.5	53.0	54.0	54.5
-92.8	88.0	92.0	47.5	47.5	49.5	50.0	50.5	51.0	51.5	52.5	53.0	54.0	54.5
-119.0	47.0	47.0	47.5	47.5	49.5	50.0	50.5	51.0	51.5	52.5	53.0	54.0	54.5
Dimension I : 11.1 mm – Head circumference : 500 mm													

IS 4151 : 2015

Headform C										(Dimensions in millimetres.)			
Dimension Z'	0°	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	91.5	89.5	86.0	79.0	72.5	70.0	69.5	72.5	77.0	82.0	87.5	90.5	91.5
−11.5	91.5	89.5	85.5	77.0	71.0	68.5	68.5	71.0	74.5	80.0	84.5	87.5	88.0
−20.6	91.5	91.0	85.5	76.5	69.0	65.5	64.0	66.5	70.0	75.5	80.0	83.0	83.5
−31.8	91.5	92.5	84.0	74.0	67.0	64.5	58.0	60.5	64.0	69.0	73.5	76.0	76.5
−40.8	91.5	92.5	81.5	71.5	65.5	62.0	56.0	57.0	60.0	64.0	67.5	70.0	69.5
−54.4	91.5	92.5	80.0	69.5	62.5	56.0	53.5	54.0	55.5	58.5	61.0	62.0	61.0
−68.0	91.5	92.5	78.0	67.0	61.0	54.5	52.0	53.0	53.5	54.5	55.0	56.0	56.5
−77.1	91.5	92.5	76.0	65.0	60.0	52.5	52.0	53.0	53.5	54.5	55.0	56.0	56.5
−81.7	91.5	92.5	74.0	62.5	51.0	51.5	52.0	53.0	53.5	54.5	55.0	56.0	56.5
−87.6	91.5	92.5	72.0	49.5	51.0	51.5	52.0	53.0	53.5	54.5	55.0	56.0	56.5
−96.2	91.5	95.5	49.0	49.5	51.0	51.5	52.0	53.0	53.5	54.5	55.0	56.0	56.5
−123.4	48.5	48.5	49.0	49.5	51.0	51.5	52.0	53.0	53.5	54.5	55.0	56.0	56.5
Dimension I : 11.5 mm – Head circumference : 520 mm													

Headform E										(Dimensions in millimetres.)			
Dimension Z'	0°	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	94.5	93.0	90.0	82.0	76.5	73.5	73.0	76.0	80.0	85.0	91.0	94.0	94.5
−11.9	94.5	93.0	88.5	79.5	73.0	70.5	70.5	73.0	77.0	82.5	87.0	90.5	91.0
−21.3	94.5	94.0	88.5	79.0	71.0	67.5	66.0	69.0	72.0	77.5	82.5	85.5	86.0
−32.8	94.5	95.5	86.5	76.5	69.5	66.5	60.0	62.5	66.0	71.0	76.0	78.5	79.0
−42.1	94.5	95.5	84.5	74.0	67.5	64.0	57.5	59.0	62.0	66.0	70.0	72.0	71.5
−56.2	94.5	95.5	82.5	71.5	64.5	57.5	55.5	55.5	57.0	60.5	63.0	64.0	63.0
−70.2	94.5	95.5	80.5	69.5	62.5	56.0	54.0	55.0	55.5	56.0	56.5	57.5	58.0
−79.6	94.5	95.5	78.5	67.0	62.0	54.5	54.0	55.0	55.5	56.0	56.5	57.5	58.0
−84.3	94.5	95.5	76.5	64.5	53.0	53.5	54.0	55.0	55.5	56.0	56.5	57.5	58.0
−90.4	94.5	95.5	74.5	51.0	53.0	53.5	54.0	55.0	55.5	56.0	56.5	57.5	58.0
−99.3	94.5	98.5	50.5	51.0	53.0	53.5	54.0	55.0	55.5	56.0	56.5	57.5	58.0
−127.4	50.0	50.0	50.5	51.0	53.0	53.5	54.0	55.0	55.5	56.0	56.5	57.5	58.0
Dimension I : 11.9 mm – Head circumference : 540 mm													

Headform G													(Dimensions in millimetres.)	
Dimension Z'	0°	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear	
0	97.5	95.5	93.0	85.5	79.5	76.0	76.0	78,5	83.0	88.5	94.0	97.0	97.5	
−12.3	97.5	95.5	91.5	82.0	75.5	73.0	73.0	75.5	79.0	85.0	90.0	93.0	93.5	
−21.9	97.5	97.0	91.5	81.5	73.5	69.5	68.0	71.0	74.5	80.0	85.0	88.5	89.0	
−33.8	97.5	98.5	89.5	78.5	71.5	68.5	62.0	64.0	68.0	73.5	78.0	81.0	81.5	
−43.5	97.5	98.5	87.0	76.5	69.5	66.0	59.5	61.0	63.5	68.0	72.0	74.5	74.0	
−58.0	97.5	98.5	85.0	74.0	66.5	59.5	57.0	57.5	59.0	62.5	65.0	66.0	64.5	
−72.4	97.5	98.5	83.0	71.5	64.5	58.0	55.5	56.5	57.0	58.0	58.5	59.5	60.0	
−82.1	97.5	98.5	81.0	69.0	63.5	56.0	55.5	56.5	57.0	58.0	58.5	59.5	60.0	
−86.9	97.5	98.5	78.5	66.5	54.5	55.0	55.5	56.5	57.0	58.0	58.5	59.5	60.0	
−93.2	97.5	98.5	77.0	52.5	54.5	55.0	55.5	56.5	57.0	58.0	58.5	59.5	60.0	
−102.4	97.5	101.5	52.0	52.5	54.5	55.0	55.5	56.5	57.0	58.0	58.5	59.5	60.0	
−131.4	51.5	51.5	52.0	52.5	54.5	55.0	55.5	56.5	57.0	58.0	58.5	59.5	60.0	
Dimension I : 12.3 mm — Head circumference : 560 mm														

IS 4151 : 2015

Headform J (Dimensions in millimetres.)													
Dimension Z'	0°	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	101.0	99.5	95.5	88.5	82.5	79.5	79.5	82.0	86.0	92.0	97.0	100.5	101.0
−12.7	101.0	99.5	94.5	85.0	78.0	75.5	75.5	78.0	82.0	88.0	93.0	96.5	97.0
−22.7	101.0	100.5	94.5	84.5	76.0	72.0	70.5	73.5	77.0	83.0	88.0	91.5	92.0
−35.0	101.0	102.0	92.5	81.5	74.0	71.0	64.0	66.5	70.5	76.0	81.0	84.0	84.5
−45.0	101.0	102.0	90.0	79.0	72.0	68.5	61.5	63.0	66.0	70.5	74.5	77.0	76.5
−60.0	101.0	102.0	88.0	76.5	69.0	61.5	59.0	59.5	61.0	64.5	67.5	68.5	67.0
−75.0	101.0	102.0	86.0	74.0	67.0	60.0	57.5	58.5	59.0	60.0	60.5	61.5	62.0
−85.0	101.0	102.0	84.0	71.5	66.0	58.0	57.5	58.5	59.0	60.0	60.5	61.5	62.0
−90.0	101.0	102.0	81.5	69.0	56.5	57.0	57.5	58.5	59.0	60.0	60.5	61.5	62.0
−96.5	101.0	102.0	79.5	54.5	56.5	57.0	57.5	58.5	59.0	60.0	60.5	61.5	62.0
−106.0	101.0	105.0	54.0	54.5	56.5	57.0	57.5	58.5	59.0	60.0	60.5	61.5	62.0
−136.0	53.5	53.5	54.0	54.5	56.5	57.0	57.5	58.5	59.0	60.0	60.5	61.5	62.0
Dimension I : 12.7 mm – Head circumference : 570 mm													

Headform K													(Dimensions in millimetres.)	
Dimension Z'	0°	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear	
0	102.5	101.0	97.0	90.0	84.0	81.5	81.0	83.5	88.0	93.0	98.5	101.5	102.5	
−12.9	102.5	101.0	96.0	86.0	79.0	76.5	76.5	79.0	83.0	89.5	94.5	98.0	98.5	
−23.0	102.5	102.0	96.0	86.0	77.0	73.0	71.5	74.5	78.0	84.0	89.5	93.0	93.5	
−35.5	102.5	103.5	94.0	82.5	75.0	72.0	65.0	67.5	71.5	77.0	82.0	85.0	85.5	
−45.7	102.5	103.5	91.5	80.0	73.0	63.5	62.5	64.0	67.0	71.5	75.5	78.0	77.5	
−60.9	102.5	103.5	89.5	77.5	70.0	62.5	60.0	60.5	62.0	65.5	68.5	69.5	68.0	
−76.1	102.5	103.5	87.5	75.0	68.0	61.0	58.5	59.5	60.0	61.0	61.5	62.5	63.0	
−86.2	102.5	103.5	85.5	72.5	67.0	59.0	58.5	59.5	60.0	61.0	61.5	62.5	63.0	
−91.3	102.5	103.5	82.5	70.0	57.5	58.0	58.5	59.5	60.0	61.0	61.5	62.5	63.0	
−97.9	102.5	103.5	80.5	55.5	57.5	58.0	58.5	59.5	60.0	61.0	61.5	62.5	63.0	
−107.6	102.5	106.5	54.5	55.5	57.5	58.0	58.5	59.5	60.0	61.0	61.5	62.5	63.0	
−138.0	54.5	54.5	54.5	55.5	57.5	58.0	58.5	59.5	60.0	61.0	61.5	62.5	63.0	
Dimension I : 12.9 mm – Head circumference : 580 mm														

Headform M (Dimensions in millimetres.)													
Dimension Z'	0°	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	106.0	104.0	101.0	93.5	87.0	84.5	84.0	86.5	91.0	96.0	102.0	106.0	106.0
−13.3	106.0	104.0	98.5	88.5	81.5	79.0	79.0	81.5	85.5	92.0	97.0	100.5	101.5
−23.7	106.0	105.0	98.5	88.0	79.5	75.0	73.5	76.5	80.5	86.5	92.0	95.5	96.0
−36.5	106.0	106.5	96.5	85.0	77.5	74.0	67.0	69.5	73.5	79.5	84.5	87.5	88.0
−47.0	106.0	106.5	94.0	82.5	75.0	71.5	64.0	66.0	69.0	73.5	78.0	80.5	80.0
−62.6	106.0	106.5	92.0	80.0	72.0	64.0	61.5	62.0	63.5	67.5	70.5	71.5	70.0
−78.3	106.0	106.5	90.0	77.0	70.0	62.5	60.0	61.0	61.5	62.5	63.0	64.0	64.5
−88.7	106.0	106.5	87.5	74.5	69.0	60.5	60.0	61.0	61.5	62.5	63.0	64.0	64.5
−94.0	106.0	106.5	85.0	72.0	59.0	59.5	60.0	61.0	61.5	62.5	63.0	64.0	64.5
−100.7	106.0	106.5	83.0	57.0	59.0	59.5	60.0	61.0	61.5	62.5	63.0	64.0	64.5
−110.7	106.0	109.5	56.5	57.0	59.0	59.5	60.0	61.0	61.5	62.5	63.0	64.0	64.5
−142.0	56.0	56.0	56.5	57.0	59.0	59.5	60.0	61.0	61.5	62.5	63.0	64.0	64.5
Dimension I : 13.3 mm — Head circumference : 600 mm													

IS 4151 : 2015

Headform O (Dimensions in millimetres.)													
Dimension Z'	0°	15°	30°	45°	60°	75°	90°	105°	120°	135°	150°	165°	180° Rear
0	108.5	107.5	103.5	96.0	90.5	87.5	87.0	90.0	94.5	100.0	105.0	108.0	108.5
−13.7	108.5	107.5	101.5	91.5	84.0	81.0	81.0	84.0	88.0	94.5	100.0	103.5	104.5
−24.4	108.5	108.0	101.5	91.0	81.5	77.5	76.0	79.0	83.0	89.0	94.5	98.5	99.0
−37.6	108.5	109.5	99.5	87.5	79.5	76.5	63.0	71.5	76.0	81.5	87.0	90.5	91.0
−48.4	108.5	109.5	97.0	85.0	77.5	73.5	66.0	67.5	71.0	76.0	80.0	83.5	82.0
−64.5	108.5	109.5	94.5	82.0	74.0	66.0	63.5	64.0	65.5	69.5	72.5	73.5	72.0
−80.6	108.5	109.5	92.5	79.5	72.0	64.5	62.0	63.0	63.5	64.5	65.0	66.0	66.5
−91.4	108.5	109.5	90.5	77.0	71.0	62.5	62.0	63.0	63.5	64.5	65.0	66.0	66.5
−96.8	108.5	109.5	87.5	74.0	60.5	61.0	62.0	63.0	63.5	64.5	65.0	66.0	66.5
−103.8	108.5	109.5	85.5	58.5	60.5	61.0	62.0	63.0	63.5	64.5	65.0	66.0	66.5
−114.0	108.5	113.0	58.0	58.5	60.5	61.0	62.0	63.0	63.5	64.5	65.0	66.0	66.5
−146.2	57.5	57.5	58.0	58.5	60.5	61.0	62.0	63.0	63.5	64.5	65.0	66.0	66.5
Dimension I : 13.7 mm – Head circumference : 620 mm													

IS 4151 : 2015

ANNEX P

(Foreword)

COMMITTEE COMPOSITION

Fire Fighting Sectional Committee, CED 22

<i>Organization</i>	<i>Representative(s)</i>
Ministry of Home Affairs, New Delhi	SHRI D. K. SHAMI (Chairman) DEPUTY FIRE ADVISOR (<i>Alternate</i>)
Aerostar Helmets Limited, New Delhi	SHRI KULJIT S. ARORA
Agni Controls, Chennai	SHRI D. BALACHANDRAN
Airport Authority of India, New Delhi	SHRI SUBHASH KUMAR SHRI P. K. DESHMUKH (<i>Alternate</i>)
Bhabha Atomic Research Centre, Mumbai	CHIEF FIRE OFFICER
Brijbasi Hitech Udyog Ltd, New Delhi	SHRI MAHESH C. AGGARWAL SHRI RAJESH K. AGGARWAL (<i>Alternate</i>)
Building Fire Research Centre, Mysore	DR N. SURESH SHRI Y. M. MANJUNATH (<i>Alternate</i>)
Central Building Research Institute, Roorkee	DR M. P. SINGH SHRI SURVIR SINGH (<i>Alternate</i>)
Central Public Works Department, New Delhi	SHRI CHAITANYA KUMAR VERMA SHRI SHAM SUNDER GARG (<i>Alternate</i>)
Centre for Fire & Explosive Environment Safety (DIFR), Delhi	SHRI V. K. SHARMA SHRI M. K. JAIN (<i>Alternate</i>)
Chennai Petroleum Corporation Ltd, Chennai	SHRI J. P. K. HEPAT
Chhatariya Rubber & Chemicals Industries, Mumbai	SHRI S. A. HAVELIWALA SHRI H. S. HAVELIWALA (<i>Alternate</i>)
Controllorate of Quality Assurance, Pune	COL S. M. HARIDAS LT COL R. K. TIWARI (<i>Alternate</i>)
Council of Architecture, New Delhi	PRESIDENT
Delhi Development Authority, New Delhi	SHRI M. K. KASHYAP
Delhi Fire Services, New Delhi	SHRI A. K. SHARMA SHRI G. C. MISHRA (<i>Alternate</i>)
Directorate of Fire and Emergency Services, Goa	SHRI ASHOK MENON SHRI RAJENDRA A. HALDANKAR (<i>Alternate</i>)
Engineer-in-Chief's Branch, New Delhi	DR RAM VERMA SHRI V. K. GULATI (<i>Alternate</i>)
Engineers India Ltd, New Delhi	SHRI R. B. BHUTDA SHRI VIPAN GOEL (<i>Alternate</i>)
F. M. Engineering International India Branch, Bangalore	SHRI SUMIT KHANNA SHRI PRASAD KULKARNI (<i>Alternate</i>)
Fire & Emergency Services J&K, Srinagar	DR. G. A. BHAT
Fire Protection Association of India, Mumbai	PRESIDENT
GAIL (India) Limited, New Delhi	SHRI S. P. GARG SHRI SANJEEV KUMAR KALKAL (<i>Alternate</i>)
Gunnebo India Pvt Limited, Chennai	SHRI K. ARUL PRAKASH SHRI RAJESH SHARMA (<i>Alternate</i>)
H. D. Fire Protect Co, Thane	SHRI HARISH N. DHARAMSHI SHRI K. T. CHAUDHARI (<i>Alternate</i>)
Indian Oil Corporation Limited, Noida	SHRI T. K. KUMAR
Institution of Fire Engineers, New Delhi	PRESIDENT GENERAL SECRETARY (<i>Alternate</i>)
K. V. Fire Chemicals (India) Pvt Ltd, Navi Mumbai	SHRI RAJESH H. SABADRA SHRI UDAY K. SHROFF (<i>Alternate</i>)

IS 4151 : 2015

<i>Organization</i>	<i>Representative(s)</i>
Karnataka State Fire and Emergency Services, Bangalore	SHRI B. G. CHANGAPPA SHRI B. K. HAMPAGOL (<i>Alternate</i>)
Maharashtra Fire Services, Mumbai	SHRI M. V. DESHMUKH SHRI S. S. WARICK (<i>Alternate</i>)
Mumbai Fire Brigade, Mumbai	SHRI S. V. JOSHI SHRI S. H. NESRIKAR (<i>Alternate</i>)
National Fire Service College, Nagpur	DIRECTOR
National Institute of Engineering, Mysore	DR N. SURESH
National Thermal Power Corporation, New Delhi	SHRI S. K. JHA SHRI SANJAY VERMA (<i>Alternate</i>)
Newage Industries, Mumbai	SHRI ASHOK M. SHAH SHRI SHETUL A. SHAH (<i>Alternate</i>)
Oil Industry Safety Directorate, New Delhi	SHRI S. K. NANDY
Prakash Suraksha Devices, Delhi	SHRI PRAMOD PRAKASH SHRI AMOD PRAKASH (<i>Alternate</i>)
Reliance Industries Limited, Jamnagar	SHRI VARADENDRA KOTI SHRI UMESH KHANDALKAR (<i>Alternate</i>)
RESQ Technologies, Ahmedabad	SHRI ROHIT V. SHAH
Safex Fire Services Limited, Mumbai	SHRI JITENDRA SHAH SHRI SANDIP SHAH (<i>Alternate</i>)
Shah Bhogilal Jethalal & Bros, Ahmedabad	SHRI MUKESH M. SHAH SHRI. ABHAY D. PURANDARE (<i>Alternate</i>)
State Bank of India, Mumbai	SHRI VIJAY S. NALHE
Surex Production and Sales Private Limited, Kolkata	SHRI DEBASHIS NEOGI
Swastik Synergy Engineering Pvt Ltd, Mumbai	SHRI MUKESH D. SHAH SHRI KUNAL ZATAKIA (<i>Alternate</i>)
Tamil Nadu Fire and Rescue Services Department, Chennai	SHRI S. VIJAYASEKAR SMT N. PRIYA (<i>Alternate</i>)
Tyco Fire & Security India Pvt Ltd, Mumbai	SHRI AJIT RAGHAVAN SHRI MANOJ SHENOY (<i>Alternate</i>)
UL India Pvt Limited, Bangalore	SHRI SANTOSH MAZUMDAR SHRI DILBAGH SINGH (<i>Alternate</i>)
Uttar Pradesh Fire Services, Lucknow	SHRI P. K. RAO SHRI AMAN SHARMA (<i>Alternate</i>)
Wadia Body Builders, Ahmedabad	REPRESENTATIVE
West Bengal Fire and Emergency Service, Kolkata	SHRI D. P. BISWAS SHRI G.K. BHATTACHARYA (<i>Alternate</i>)
Zenith Fire Services (India) Pvt Ltd, Mumbai	SHRI B. C. SHAH SHRI D. C. SHAH (<i>Alternate</i>)
In personal capacity (<i>B-152, 1st Floor, East of Kailash, New Delhi</i>)	SHRI HEMANT KUMAR
In personal capacity (<i>K-33-A, Green Park, New Delhi</i>)	SHRI S. K. DHERI
In personal capacity (<i>P/4, Belgacuta Villa, Kolkata</i>)	SHRI S. N. KUNDU
In personal capacity (<i>A-45, Sector-70, Noida</i>)	DR H. S. KAPRWAN
In personal capacity (<i>A-347, Defence Colony, New Delhi</i>)	SHRI R. C. SHARMA
In personal capacity (<i>SJR Verity, VIVA-305, Amrita College Road, Bangalore</i>)	SHRI T. R. A. KRISHNAN
Directorate General, Bureau of Indian Standards	SHRI J. ROY CHOWDHURY, Scientist 'F' & Head (Civil Engg) Representing Director General (<i>Ex-officio</i>)

Member Secretary
SHRI SRIKANTH YAJJALA
Scientist 'B' (Civil Engg), BIS

IS 4151 : 2015

Helmet Subcommittee, CED 22:5

<i>Organization</i>	<i>Representative(s)</i>
In personal capacity (<i>B-152, 1st Floor, East of Kailash, New Delhi</i>)	SHRI HEMANT KUMAR (<i>Convener</i>)
Aerostar Helmets Limited, New Delhi	SHRI KULJIT S. ARORA
All India Helmet Manufacturer's Association, Faridabad	SHRI MADHU BHUSHAN KHURANA SHRI AMIT DESAI (<i>Alternate</i>)
Automotive Research Association of India, Pune	SHRI A. V. MANNIKAR SHRI S. G. SAROF (<i>Alternate</i>)
Bureau of Police Research and Development, New Delhi	SMT VANITA YADAV SHRI M. M. GOSAL (<i>Alternate</i>)
Central Institute of Mining and Fuel Research, Dhanbad	DR H. SINGH
Coal India Limited, Ranchi	SHRI G. C. SHARMA SHRI A. B. W. HUSSAIN (<i>Alternate</i>)
CONCERT Trust, Chennai	SHRI M. MOHAN SHRI G. RAJAN (<i>Alternate</i>)
Concord Arai Pvt Limited, Chennai	SHRI R. RAMAKRISHNAN SHRI A. R. D. RAMACHANDRA RAJA (<i>Alternate</i>)
Defence Bio-Engg & Electro Medical Lab, Bangalore	SHRI A. S. K. PRASAD DR V. C. PADAKI (<i>Alternate</i>)
Defence Material Stores Research & Development, DRDO, Kanpur	DR R. K. TIWARI SHRI ARUN KUMAR SINGH (<i>Alternate</i>)
Directorate General of Mines Safety, Dhanbad	SHRI C. B. PRASAD SHRI N. P. DEORI (<i>Alternate</i>)
ERGO Auto Limited, Faridabad	SHRI R. B. KHURANA SHRI O. P. ADLAKHA (<i>Alternate</i>)
Helmet Manufacturer's Association, Noida	REPRESENTATIVE
Hero Moto Corp Ltd, Dharuhera	SHRI SUMIT BANSAL SHRI MANISH KESWANI (<i>Alternate</i>)
Indian Institute of Technology, New Delhi	DR PUNEET MAHAJAN
Mines Safety Appliances Limited, Kolkata	SHRI K. SANYAL MR S. BHATTACHARYA (<i>Alternate</i>)
Ministry of Home Affairs, New Delhi	FIRE ADVISER DEPUTY FIRE ADVISOR (<i>Alternate</i>)
Ministry of Road Transport and Highways, New Delhi	SHRI S. P. GUPTA
Safety Engineering Department, Bokaro	SHRI D. MAHATA SHRI R. K. OJHA (<i>Alternate</i>)
Society of Indian Automobile Manufacturers (SIAM), New Delhi	PRESIDENT
Steelbird Hi-Tech India Ltd, New Delhi	SHRI RAJEEV KAPUR SHRI ARUN KUMAR (<i>Alternate</i>)
STUDS Accessories Limited, Faridabad	SHRI MADHU BHUSHAN KHURANA SHRI SIDHARTH BHUSHAN KHURANA (<i>Alternate</i>)
VOICE Society, New Delhi	SHRI M. A. U. KHAN SHRI H. WADHWA (<i>Alternate</i>)
In personal capacity (<i>A-347, Defence Colony, New Delhi</i>)	SHRI R. C. SHARMA

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act*, 1986 to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Director (Publications), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the latest issue of 'BIS Catalogue' and 'Standards : Monthly Additions'.

This Indian Standard has been developed from Doc No.: CED 22 (7887).

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

Telephones : 2323 0131, 2323 3375, 2323 9402

Website: www.bis.org.in

Regional Offices:

Telephones

Central : Manak Bhavan, 9 Bahadur Shah Zafar Marg
NEW DELHI 110002

{ 2323 7617
2323 3841

Eastern : 1/14 C.I.T. Scheme VII M, V. I. P. Road, Kankurgachi
KOLKATA 700054

{ 2337 8499, 2337 8561
2337 8626, 2337 9120

Northern : SCO 335-336, Sector 34-A, CHANDIGARH 160022

{ 260 3843
260 9285

Southern : C.I.T. Campus, IV Cross Road, CHENNAI 600113

{ 2254 1216, 2254 1442
2254 2519, 2254 2315

Western : Manakalaya, E9 MIDC, Marol, Andheri (East)
MUMBAI 400093

{ 2832 9295, 2832 7858
2832 7891, 2832 7892

Branches: AHMEDABAD. BENGALURU. BHOPAL. BHUBANESHWAR. COIMBATORE. DEHRADUN.
FARIDABAD. GHAZIABAD. GUWAHATI. HYDERABAD. JAIPUR. KOCHI. LUCKNOW.
NAGPUR. PARWANOO. PATNA. PUNE. RAJKOT. VISAKHAPATNAM.

AMENDMENT NO. 1 JUNE 2018
TO
IS 4151 : 2015 PROTECTIVE HELMET FOR TWO
WHEELER RIDERS — SPECIFICATION

(Fourth Revision)

(First cover page, Hindi Title) — Substitute ‘सवारों’ for ‘चालकों’.

(Page 1, clause 2) — Substitute the following for the entry for IS 15575:

<i>IS No.</i>	<i>Title</i>
15575 (Part 1) : 2016/ IEC 61672-1 : 2013	Electro acoustics — Sound level meters: Part 1 Specifications (<i>first revision</i>)

(Page 4, clause 6.9, line 6) — Substitute '1 200 g' for '1 500 g'.

(Page 5, clause 7.2.1) — Substitute the following for the existing clause:

‘7.2.1 The absorption efficiency shall be considered sufficient where the resultant acceleration measured at the centre of gravity of the head form meets the following requirements:

- a) Peak acceleration does not exceed 400g;
- b) Accelerations in excess of 200g does not exceed a cumulative duration of 2.0 millisecond; and
- c) Accelerations in excess of 150g does not exceed a cumulative duration of 4.0 millisecond.’

[Page 7, clause 9.1(g)] — Insert the following at the end:

‘h) The words ‘Two Wheeler Helmet’ on outer surface of the helmet.’

(Page 14, clause C-2.4.2) — Delete.

(Page 14, clause C-3.3.1, line 10) — Substitute ‘ $6.00 \pm_{-0}^{+0.15}$ m/s’ for ‘ $7.5 \pm_{-0}^{+0.15}$ m/s’.

Amendment No. 1 to IS 4151 : 2015

(Page 14, clause **C-3.3.1**, line 11) — Substitute ' $5.50^{+0.15}_{-0}$ m/s' for ' $5.5^{+0.15}_{-0}$ m/s'.

(Page 14, clause **C-3.3.2**, second sentence) — Substitute the following for the existing sentence:

'The acceleration against time at the centre of gravity of the headform is measured and recorded.'

(Page 17, clause **E-1.3.1**, line 4) — Substitute ' $8.50^{+0.15}_{-0}$ m/s' for ' $8.5^{+0.15}_{-0}$ m/s'.

(Page 22, clause **G-1.1**, line 2) — Substitute 'IS 15575 (Part 1)' for 'IS 15575'.