



LABORATORY REPORT

Gerab System Technology.
Dubai, UAE

Report No : WLPR15-8007
Sample No : WSP15-8321
Report Date: 04/06/2015


Introduction: Further to the request received from **M/s. Gerab System Technology** dated 28TH May 2015, a sample of Fibre FTTH Cable was tested using with Standard **IEC 60794**.

Sample description : 2 Fibre FTTH Cable
Made : Datacom
Fibre Type : LSZH
Cable Colour : Yellow
Test Method : IEC 60794
Sample received : 28/05/2015
Date of Test : 01/06/2015-04/06/2015
Tested by : SJV

RESULTS

Impact Test

Diameter of Punch : 12mm
Radius of surface : 75 mm
Mass of cylinder : 0.978 kg

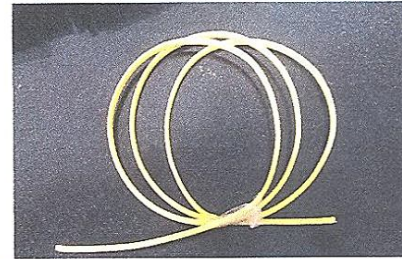

Impact Height	Impact Energy	Result
150 mm	1.431 Joule	Visually examined on the tested area, no physical damage appear.

Crush Test

Applied Force	Duration	Results
196 N	10 min	No physical damage and cracks were observed during the test.

Tensile Test

Length & Width	Test	Tensile Strength(N)	Avg. Tensile Strength(N)
3mm x 2.2 mm	Test1	78	76
	Test2	75	
	Test3	76	

Bending Test

Mandrel Diameter	Length of Specimen	Mass of Weight	No of Turns	Result
25 mm	1 Meter	1000 g	15	Indentation without any crack was observed

Page 01 of 02

**Torsion Test**

Tensile Load	No. of Cycles	Distance between two clamp	Results
49.03 N	10	250 mm	No physical damage and twisting were observed during the test

Kink Test

Minimum Loop Diameter	Results
30 mm	Pass (No Kink Occurred)

Buffer Movement under Compression

Compression Distance: 7 mm

Results
Compression force at 0.4 mm movement $\leq$ 1 N.

Sheath Pull off Force

Strip Force	Strip Length	Rate of Separation
5 N	50 mm	$\leq$ 200 mm/min

Temperature Cycling

Type of Winding	Winding Radius	Temperature	Duration	Result
Free, supported horizontally in an climatic chamber	75 mm	-10°C / 70°C	1 hr	No attenuation were observed during the test

Sheath Shrinkage

Temperature	Duration	Shrinkage
70°C	1 hr	$\leq$ 0,5 %

Remarks: The above tested product (Fibre FTTH Cable) complies with the specification of IEC 60794.**Signed for and on behalf of Wimpey Laboratories****Binu K Babu****In Charge -Technical & Marketing**

Test results relate only to the samples tested.

This report shall not be reproduced except in full, without the written approval of the Laboratory.

-End of text-

WLPR15-8007

Page 02 of 02