

PT. IMC TEKNO INDONESIA

INJECTION MOLDING CONDITION STANDARD

DATE : 21 MEI 2026

STATUS :

V

 TRIAL MASS PRO

PART NAME : BRACKET (5P45V)

PART NO. : A3994-635-00

CUSTOMER : PT. MAPI

QUALITY CONTROL	ENGINEERING	PRODUCTION	PREPARED BY
	WAHYU J		NURRONI

INJECTION MACHINE

MC no/Ton.: 31/110T SCREW Ø: 45 mm

MODEL : FN2000-25A

CONTROLLER : NC 9000

MATERIAL

NAME : PP ELPRO

GRADE : P640J

COLOUR : NATURAL

DRY UP TM : 2 H

DRY UP TMP : 80 °C

REGRIND : - %

MASTER BATCH : - %

PART

CAVITY : 2/2

TOTAL WEIGHT : 35,432 g

PART WEIGHT :

1

 15,659 g g g g

RUNNER WEIGHT : 4,185 g

ANNEALING STANDARD :

:

2

 15,588 g g g g

MOLD

MTC SETTING : - °C

MTC ACTUAL TEMP. : - °C

CHILLER TMP : °C

MOLD ACTUAL TEMPERATURE (± 5)°C

CAVITY SIDE : 35 °C

CORE SIDE : 35 °C

< INJ / MTG >

1. INJ TM : 8 sec

2. COOL TM : 25 sec

3. CYC ST TM : 0,2 sec

4. MTG ST. TM : - sec

5. NOZZLE BWD TM : - sec

6. V5 : 8 %

7. V4 : 10 %

8. V3 : 10 %

9. V2 : - %

10. V1 : - %

11. TP2 : 2 sec

12. S5 : 8 mm

13. S4 : 10 mm

14. S3 : 25 mm

15. S2 : - mm

16. S1 : - mm

17. SM : 40 mm

18. SD : 5 mm

19. P3 : 35 %

20. P2 : 25 %

21. P1 : 65 %

22. VS : 65 %

23. BACK PRESSURE : 20 kgf

BARREL TEMPERATURE (± 10) °C

NOZZLE

Set 190 °C

Act 190 °C

FRONT

Set 195 °C

Act 195 °C

MIDDLE

Set 190 °C

Act 190 °C

REAR

Set 185 °C

Act 185 °C

< OPEN CLOSE >

1. HI MILD CLS V : 20 %

2. CLAMP SLOW V : 25 %

3. LOW MLD CLS P : 12 %

3. HI MLD CLS P : 95 %

5. OPEN SLOW : 30 %

6. HI MLD OPEN V : 35 %

7. PRI OPEN V : 20 %

8 PRI OPEN TM : 0,2 %

< EJECTOR >

1. EJECT PRES : 20 %

2. FWD EV1 : 10 %

3. COUNT : 1 %

4. START TM : 0,5 %

5. MOMENT STOP : 1ST ~~LAST~~

6. BWD EV 4 : 85 %

7. BWD PRES : 65 %

8. STOP TM : 1 %

9. REPEAT EJECT EV 3 : 55 %

FEEDER TEMPERATURE (± 10) °C

°C

Limit Switch			Rev.No	Date	Description	Prod	PE	QC
LS 5	Eject forward stop	mm	△					
LS 14	Eject backward stop	mm						
LS 3	High Pressure Selection	mm	△					
LS 2	Low pressure mold clamping	mm						
LS 8	Mold opening slow down	mm	△					
LS 4	Mold opening stop	mm						

INJECTION MOLDING CONDITION STANDARD

*Referensi Pengisian Std. & Act. MCS

* DATA STATISTIC


NO	DESCRIPTION	UNIT	STD	TOLERANSI
	MOLD			
01 a	MTC No.		-	
b	MTC Temp. Oli / Water *	°C	-	±10
02	Chiller Temp.	°C	-	±5
03	Core Temp.	°C	35	±5
04	Cavity Temp.	°C	35	±5
	TIMING			
05	Injection TM	Sec	8	±0
06	Cooling TM	Sec	25	±0
07	TP2	Sec	2	±1
	SPEED			
08	V1	%	-	±10
09	V2	%	-	±10
10	V3	%	10	±10
11	V4	%	10	±5
12	V5	%	8	±5
	PRESSURE			
13	P1 / PV1 *	%	65	±10
14	PV2	%	-	±10
15	PV3	%	-	±10
	HOLD			
16	P2 / Pp1 *	%	25	±10
17	P3 / Pp2 *	%	35	±10
	INJECTION DISTANCE			
18	SD	mm	5	±5
19	SM	mm	40	±5
20	S1 / SV1 *	mm	-	±5
21	S2 / SV2 *	mm	-	±5
22	S3 / SV3 *	mm	25	±5
23	S4 / SV4 *	mm	10	±5
24	S5 / SV5 *	mm	8	±5
25	BACK PRESS	Kgf/cm ²	20	±5
	BAREL TEMP			
26	NOZZLE	°C	190	±10
27	*HEAD *FRONT	°C	-	±10
28	*FRONT *MIDDLE	°C	195	±10
29	*MIDDLE *REAR 1	°C	190	±10
30	*REAR *REAR 2	°C	185	±10
	HOPPER DRYER			
31	TEMPERATURE	°C	80	±10
	PART			
32	Cav.No	Pcs	2/2	
33	Part Weight / Shoot	Gr	31,247	
34	Runner Weight / Shoot	Gr	4,185	
35	Total Weight / Shoot	Gr	35,432	

LIMIT MATERIAL STAY IN HOPPER

	Kg
--	----

[illegible]

FLOW COOLING SYSTEM

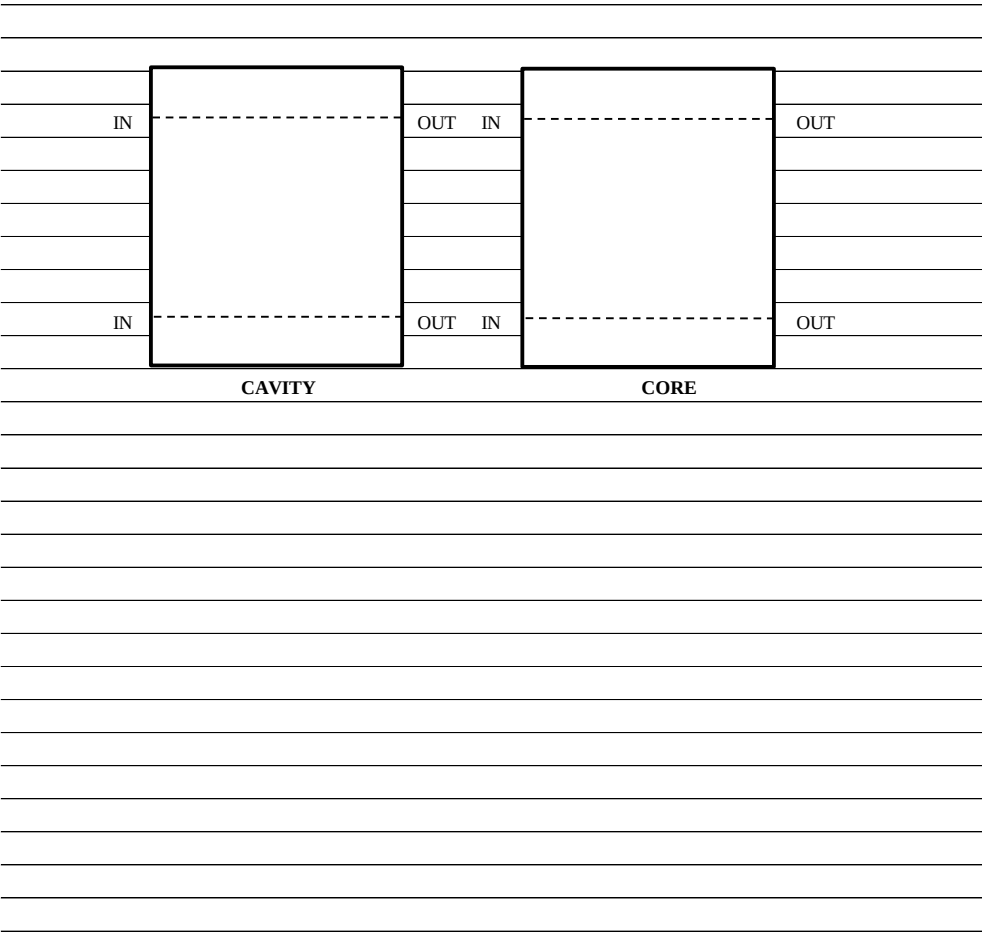

✓	ROBOT RUNNER SETTING	
✓	RE- TRACK	
	USE ROBOT RUNNER	
	NOT USE ROBOT RUNNER	
	RE- TRACK	
	NO RE-TRACK	
	EJECTOR OPERATING	
	NORMAL	☐ OVERRIDE
	MONITOR	
	COUNTER	
	NOZZLE NOT LEAKING	