

CONFIDENTIAL

**TEST REPORT ON DETERMINATION OF  
RANDOM INCIDENCE SOUND ABSORPTION OF NEXUS ACOUSTIC PENDANT**

ULR-TC508522050000146F  
NVH/3100013318/2022-23/0146

15<sup>th</sup> June 2022

- 1.0 CUSTOMER NAME :** Senses Akustik Private Limited  
Plot No. 102, New GIDC, Gundlav,  
Valsad- 396 035, Gujarat
- 2.0 LETTER REF. :** E-mail dated 10<sup>th</sup> MAY 2022
- 3.0 TEST COMPONENT DETAILS :** Test sample details given by customer is as follows:
- 3.1 Product Name : Nexus acoustic pendant
- 3.2 Acoustic material specification : Consist of 100%PET (60% Recycled),
- 3.3 Dimension : 800 mm diameter, 200 mm height
- 3.4 Weight of one sample : 3.0 Kg
- 3.5 Samples used for testing : 6 samples used for testing

**4.0 TEST REQUIREMENTS :**

Measurement of equivalent sound absorption and per sample equivalent sound absorption on above mentioned test sample as per ASTM C-423 / ISO 354 in reverberation chamber.

**5.0 TEST PROCEDURE :**

Equivalent sound absorption and per sample equivalent sound absorption was computed by hanging 6 nos. of above mentioned test sample at a height of 1 m from ceiling as per ASTM C-423 / ISO 354 in reverberation chamber. Please refer figure 1 for test set up and test component details. Total three sets of measurement were taken and average value is reported. The measurement was carried out at temperature 25<sup>o</sup>C  $\pm$ 1<sup>o</sup>C, humidity 57% and barometric pressure 938 mbar.

**6.0 DATE OF EVALUATION :**

The Random incidence sound absorption measurement was carried out on above mentioned test sample on 14<sup>th</sup> June 2022.

Page 1 of 5

ULR-TC508522050000146F  
NVH/3100013318/2022-23/0146

15<sup>th</sup> June 2022

## 7.0 INSTRUMENTATION :

Sr. No	Instrument Name	Type / Model No	Make	Calibrated on	Calibration due on
1	Multi-channel Data Acquisition System	3560 D	Brüel & Kjær, Denmark	03-Aug-21	03-Aug-22
2	½" Random Incidence Microphone	378B20	PCB, USA	03-Aug-21	03-Aug-22
3	Power Amplifier	2716	Brüel & Kjær, Denmark	Does not require separate calibration as it is driven by data acquisition system	
4	Omni directional Sound source	Omni power 4296	Brüel & Kjær, Denmark		
5	Reverberation room	80 m³ and 110 m³	-	-	-

## 8.0 TEST RESULTS :

- 8.1 Table 1 and figure 2 show the values and plot for Equivalent Sound Absorption Area in Sabine m² of Nexus Acoustic Pendant consist of 100% PET (60% Recycled) of measured 800 mm diameter, 200 mm height, 3 kg weight and 6 samples tested in hanging condition in the frequency range of 100 Hz to 5000 Hz
- 8.2 Table 2 and figure 3 show the values and plot per Sample Equivalent Sound Absorption Area in Sabine m² of Nexus Acoustic Pendant consist of 100% PET (60% Recycled) of measured 800 mm diameter, 200 mm height, 3 kg weight and 6 samples tested in hanging condition in the frequency range of 100 Hz to 5000 Hz.

## 9.0 CONCLUSIONS :

Average value of per sample sound absorption of Nexus Acoustic Pendant sample calculated in the frequency range 100 Hz to 5000 Hz.

Nexus Acoustic Pendant consist of 100% PET (60% Recycled) of measured 800 mm diameter, 200 mm height, 3 kg weight	
Average value of per sample sound absorption of Nexus Acoustic Pendant, Sabine's m²	0.58

Tested and Report Prepared By:



P. P. Kamble  
Engineer

Reviewed By:



M. P. Joshi  
Dy. General Manager

Reviewed By:



S. K. Jain  
General Manager

Approved By:



Dr. N. H. Walke  
Deputy Director

This test report pertains only to the samples actually tested at ARAI in the presented condition. The issuing of this test report does not indicate any measure of approval, certification, supervision, control of quality surveillance by ARAI of any product. No extract, abridgement or abstraction from this test report be published or used to advertise the product without the written consent of the Director, ARAI, who reserves the absolute right to agree or reject all or any of the details of any items of publicity for which consent may be sought.



TC-5085

ULR-TC508522050000146F  
NVH/3100013318/2022-23/0146

15<sup>th</sup> June 2022

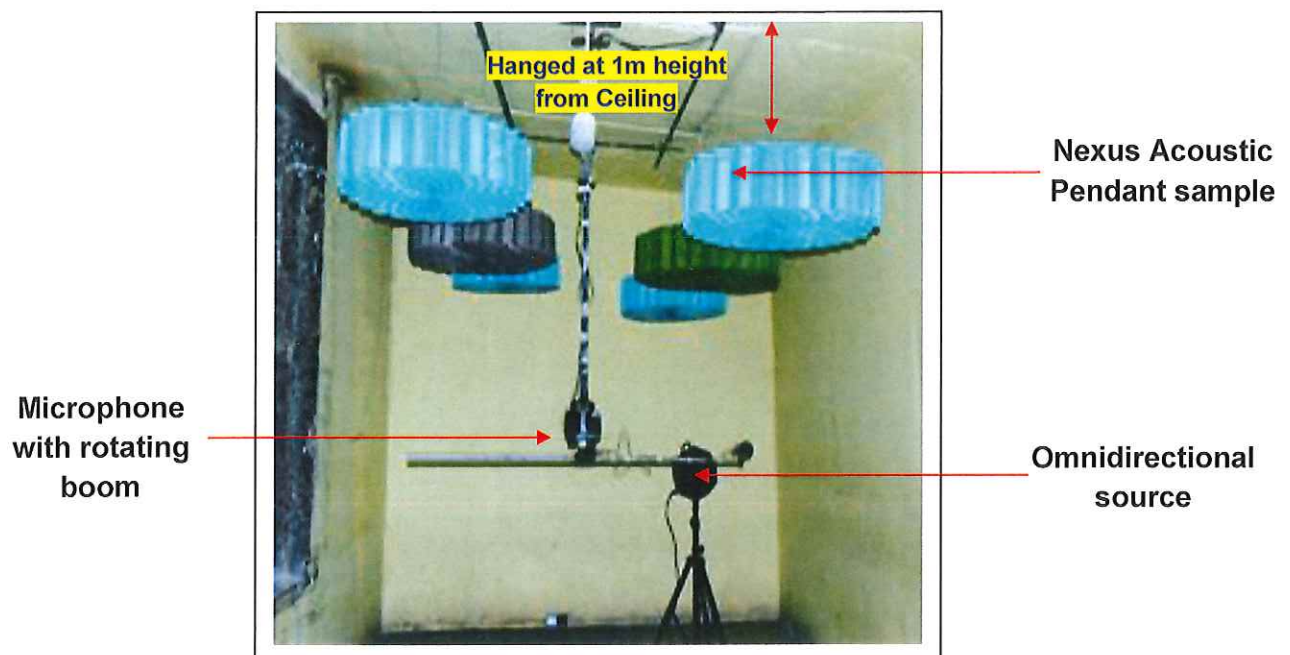



Figure 1: Test set up for mounting and testing of Nexus Acoustic Pendant sample in reverberation chamber



15th June 2022

Table 1 and Figure 2: Values and Plot for Equivalent Sound Absorption Area in Sabine m<sup>2</sup> of Nexus Acoustic Pendant consist of 100% PET (60% Recycled) of measured 800 mm diameter, 200 mm height, 3 kg weight and 6 samples tested in hanging condition at one third octave frequencies

One third octave frequency, Hz	Equivalent Sound Absorption Area, Sabine m <sup>2</sup>	Standard Deviation
100	0.12	0.00
125	0.89	0.12
160	1.11	0.05
200	1.21	0.07
250	1.89	0.10
315	2.38	0.17
400	2.95	0.05
500	3.39	0.05
630	3.62	0.15
800	4.02	0.01
1000	4.33	0.03
1250	4.45	0.04
1600	4.77	0.12
2000	5.11	0.07
2500	5.39	0.01
3150	5.61	0.08
4000	5.74	0.05
5000	5.94	0.09

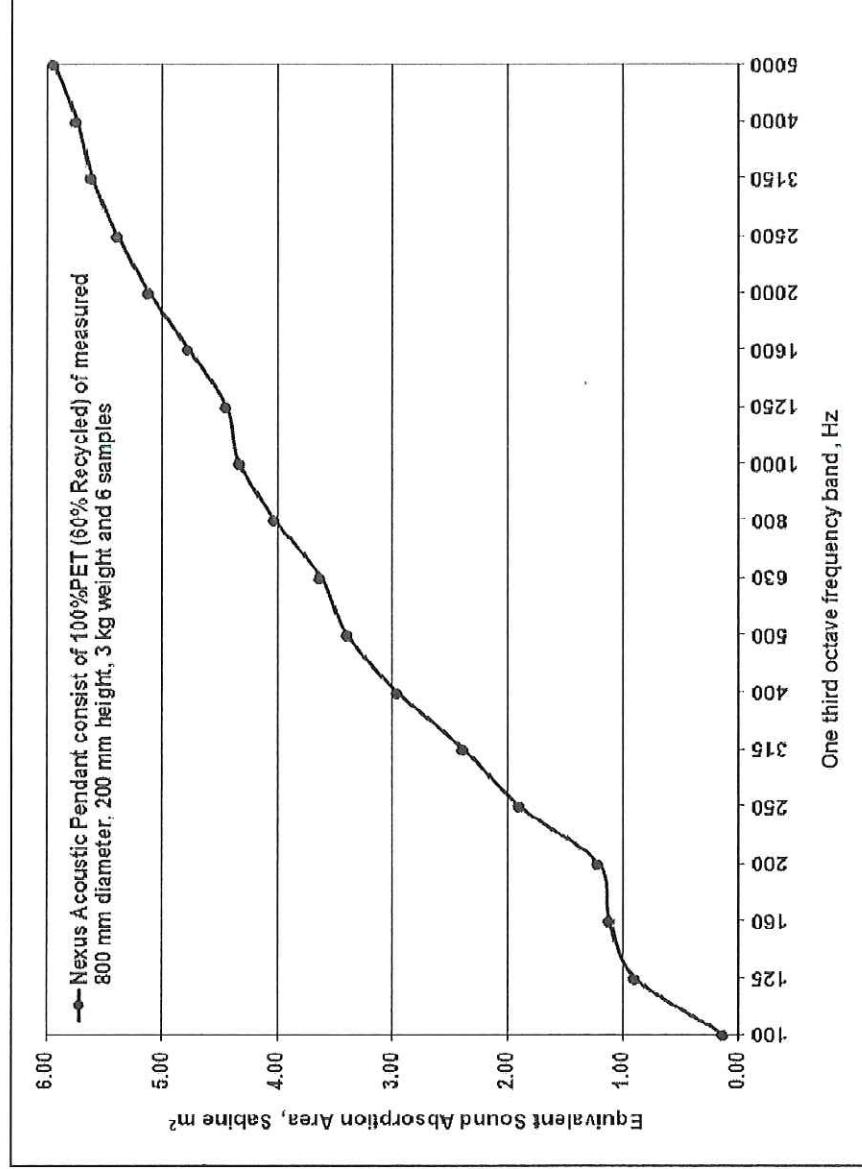

15th June 2022

Table 2 and Figure 3: Values and Plot for Per Sample Equivalent Sound Absorption Area in Sabine m<sup>2</sup> of Nexus Acoustic Pendant consist of 100%PET (60% Recycled) of measured 800 mm diameter, 200 mm height, 3 kg weight and 6 samples tested in hanging condition at one third octave frequencies

One third octave frequency, Hz	Per Sample Equivalent Sound Absorption Area, Sabine m <sup>2</sup>	Standard Deviation
100	0.02	0.00
125	0.15	0.02
160	0.19	0.01
200	0.20	0.01
250	0.32	0.02
315	0.40	0.03
400	0.49	0.01
500	0.56	0.01
630	0.60	0.02
800	0.67	0.00
1000	0.72	0.00
1250	0.74	0.01
1600	0.80	0.02
2000	0.85	0.01
2500	0.90	0.00
3150	0.93	0.01
4000	0.96	0.01
5000	0.99	0.01

