

实验计划

2026 年 3 月 14 日

目录

第一章 电磁吸收材料研究现状	1
1.1 其他研究者的工作成果	1
1.2 学界目前在本材料体系内为了提高吸波性能做出的努力与尝试	1
1.2.1 学界在吸波材料方面的努力	1
1.2.2 学界目前对于纳米纤维在静电纺织中的演化行为的研究	2
第二章 一阶段实验总结	3
2.1 可控参数	3
2.2 实验条件改良	3
2.3 实验计划	3
2.4 0321 改良效果	4
2.5 0401 效果	4
2.6 材料性能对比	11

第一章 电磁吸收材料研究现状

1.1 其他研究者的工作成果

Material	Thickness (nm)	Minimum RL(dB)	EAB(GHz)	Ref.
Fe/SiC/PCS	2.25	-46.3	4.6(<-20dB)	[1]
MXene	2.7/2.1	-54.1(2.7)	7.76(2.1)	[2]
Fe/Co@C-CNFs	1.08/1.22	-18.66(1.08)	4.2(1.22)	[3]
PAN/Fe ₃ O ₄	4	-11.3	7	[4]
TiN/carbon-paraffin composites	1.9	-41.8	3.9	[5]
SiC	1.9	-57.8	12	[5]
ZnO/Co	3.0/2.6	-68.4(3.0)	5.9(2.6)	[6]
P-CNF/Fe	4.1	-44.86	3.28	[7]
CeO ₂ /NC	2.5	-42.95	8.48	[8]
Zr/SiC	3.5	-48.6	3.2	[9]
ZrC	1.25/1.0	-25.77(1.25)	3.04(1.0)	[10]
ZrO ₂ /ZrC/ZrB ₂	2.4	-21	8.64	[11]
ZrO ₂ /ZrB ₂ /C	4.0	-54	3.1	[12]
ZS-HNFA-x	2.4	-53.2	6.4	[13]
ZrO ₂ /CF-rGO	3.14	-62.99	8.19	[14]
ZrO ₂ /C	2.5	-36	7.3	[15]

1.2 学界目前在本材料体系内为了提高吸波性能做出的努力与尝试

1.2.1 学界在吸波材料方面的努力

Zhao 等^[16]通过在碳化硅材料表面镀银, 形成导电网络通路, 提高其电磁损耗; 增强界面极化, 提高其衰减常数和阻抗匹配, 从而增强其吸波性能。Liu 等^[17]通过超快高温烧结的方式制备了三种新型 HEP 材料, 通过调整组分并触发多种电磁损耗机制, 该体系的电磁吸收性能得到了显著提升。Zhou 等^[18]通过化学气相渗透法构建了 SiC_f/Si₃N₄ 复合材料, 实现了在宽温度范围 (25-600°C) 内 X 和 Ku 波段对温度不敏感的电磁波吸收。Lan 和 Wang 等^[19]通过在碳化硅晶须组成的轻质多孔骨架中掺入碳纳米线, 热还原以实现碳化硅纳米线网络以产生强界面极化和多重反射, 提高电导率。Cai 等^[20]通过在 1500 摄氏度、氮气气氛下烧结碳化硅晶须的方式实现了碳化硅/氮化硅复合气凝胶, 将 Si₃N₄ 纳米带引入碳化硅纳米线网络, 增强了阻抗匹配、界面极化和偶极极化。

1.2.2 学界目前对于纳米纤维在静电纺织中的演化行为的研究

第二章 一阶段实验总结

短期实验目标 通过“二分法”不断迭代寻找合适的参数

2.1 可控参数

电压、喷射距离、滚筒转速、挤出速率、滑台移速、nZr: PVP 配比

需要注意的是，电压和喷射距离本质上是服务于同一个参数：胶液飞行速度。这两个参数应当整体调节。

预想机理 通过控制胶液飞行速率避免胶液在飞行途中聚团，从而减少附着纤维中的聚团现象；挤出速率：避免在飞行速率过慢时挤出较多导致胶液束过粗；滑台移动速率：减少滑台变速抖动，抑制胶液偏聚；配比：控制纤维的分布；滚筒转速：尽快分离前后附着胶液的空间分布。

2.2 实验条件改良


铝箔纸换硅油纸、提高箱体气密性

2.3 实验计划


次序	参数	最初预设调参节点
1	nZr: PVP	1.5、2.5
2	滚筒转速	200+n40rpm
3	滑台移速	10mm/h

电压与喷射距离（喷射速率）的调节需要进行数学计算

2.4 0321 改良效果

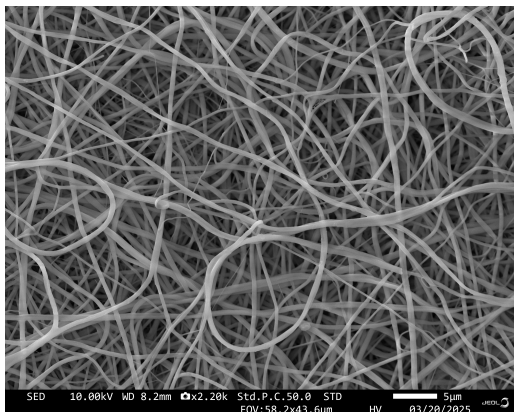

(a) 标准参数：修正为 nZr: PVP=2: 0.6

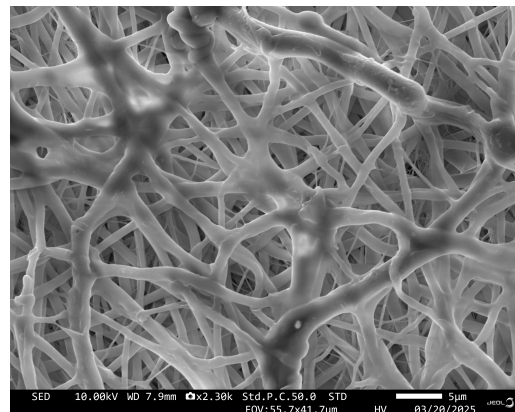

(b) 标准参数

图 2.1a 可以发现此时纤维均匀度大幅提高，但纤维束与纤维束之间的直径差距开始显现明显，目测在十纳米和数百纳米之间波动，纤维束之间较之图 2.1b 更疏松。图 2.1b 可以发现此时纤维不均匀，单条纤维束上直径差距大，在 1 微米到 3 微米之间波动，而纤维束之间出现了粘连成块状的区域，多条纤维束之间存在并列粘连，较之图 2.1a 更密集，密度更高，预测密度较之图 2.1a 更低。

2.5 0401 效果

将图 2.2c 与图 2.1a 对比，我们可以发现，图 2.2c 的纤维相对不光滑，对高温下力学性能来说可能会有影响。形成原因来看，不太可能是因为挤出速率更慢与 PVP: Zr 的含量配比，根据同行的经验来看，有可能是因为封箱的问题：封箱了箱子里湿度更低，失去了水汽的电场均匀化作用，导致胶液在飞行过程中精细拉伸较弱，因而形成的纤维束不太均匀。需要实现湿度的可控化。



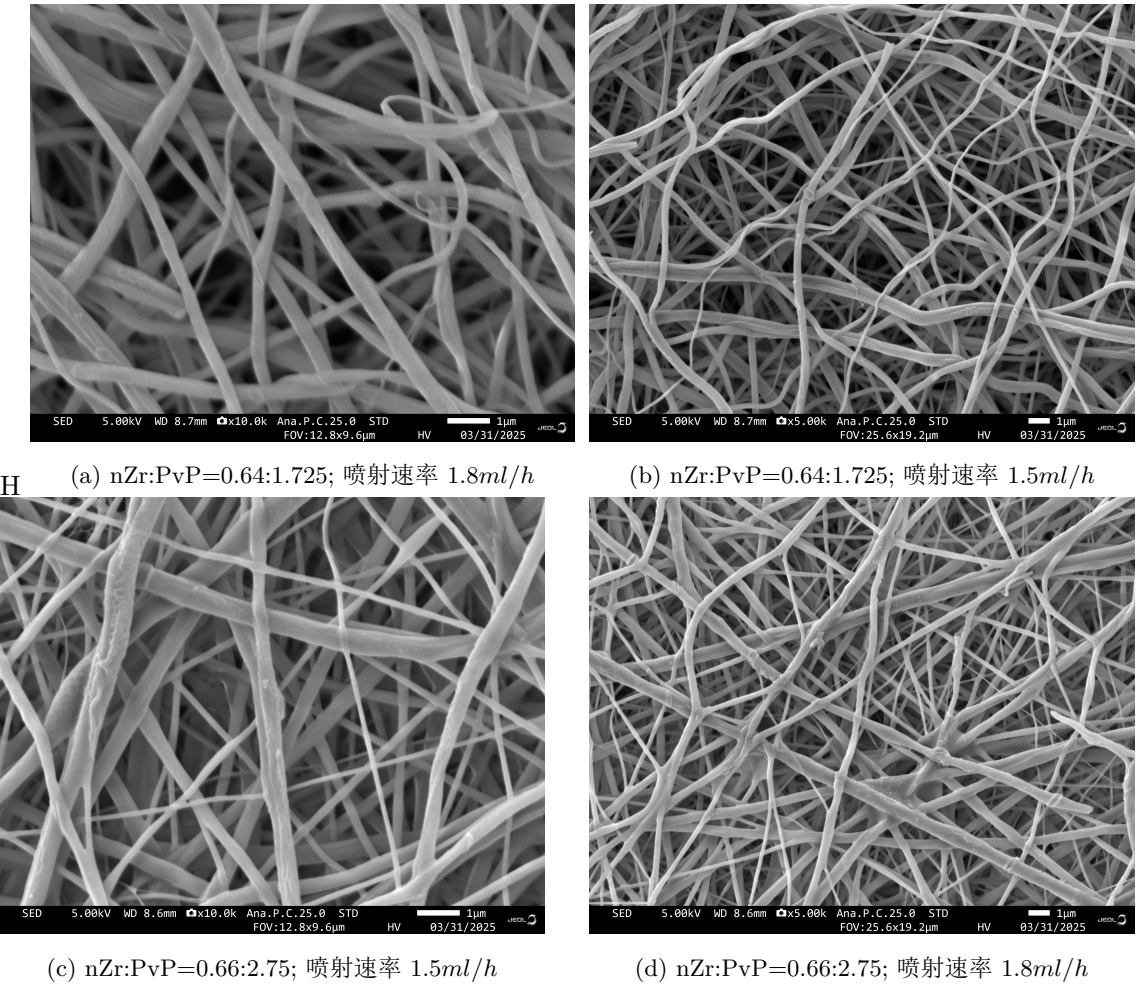



图 2.2: 三月三十一日四份样品 sem 图

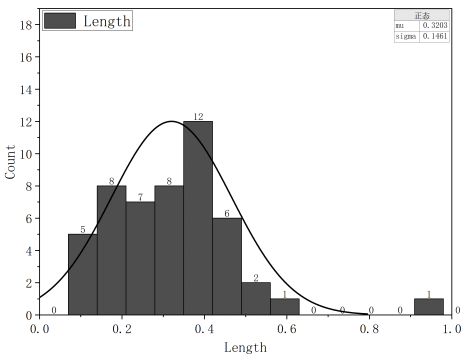


(a) 图 2.2c纤维直径分布

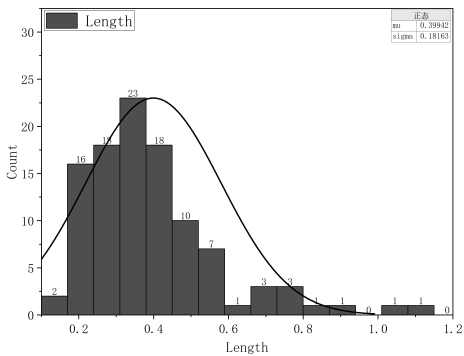

(b) 图 2.2d纤维直径分布

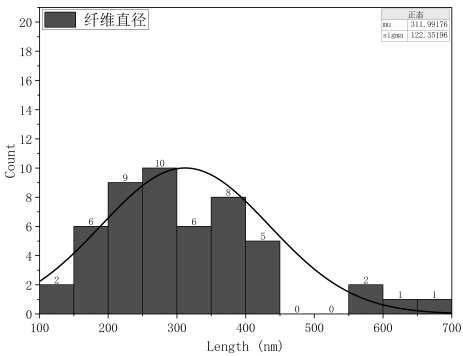

(c) 图 2.2a纤维直径分布

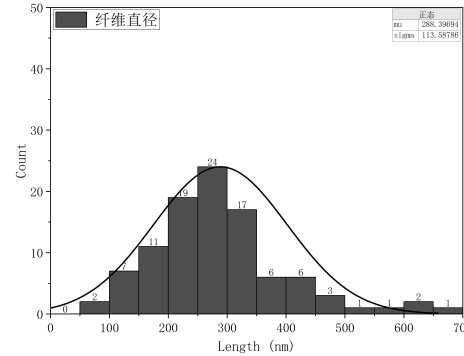

(d) 图 2.2b纤维直径分布

图 2.3: 图 2.2纤维直径分布图

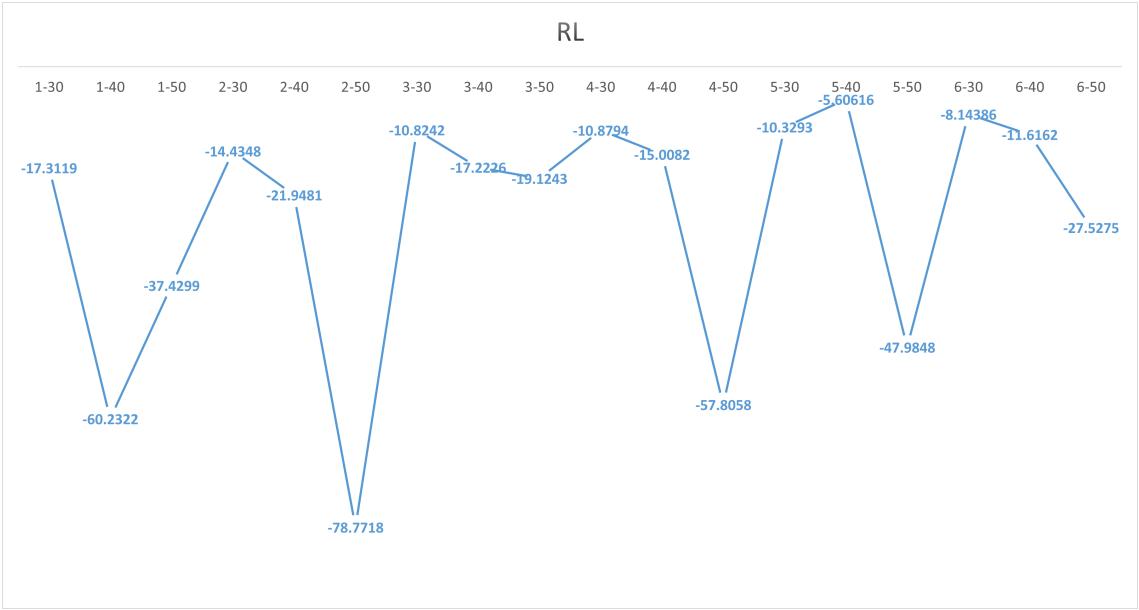


图 2.4: 四月一号样品 RL 系数

可以看到，1、2、4 的样品的 RL 非常不错，有继续研究的价值，当然导师希望我们先复现十多份二号样先好准备后续研究。

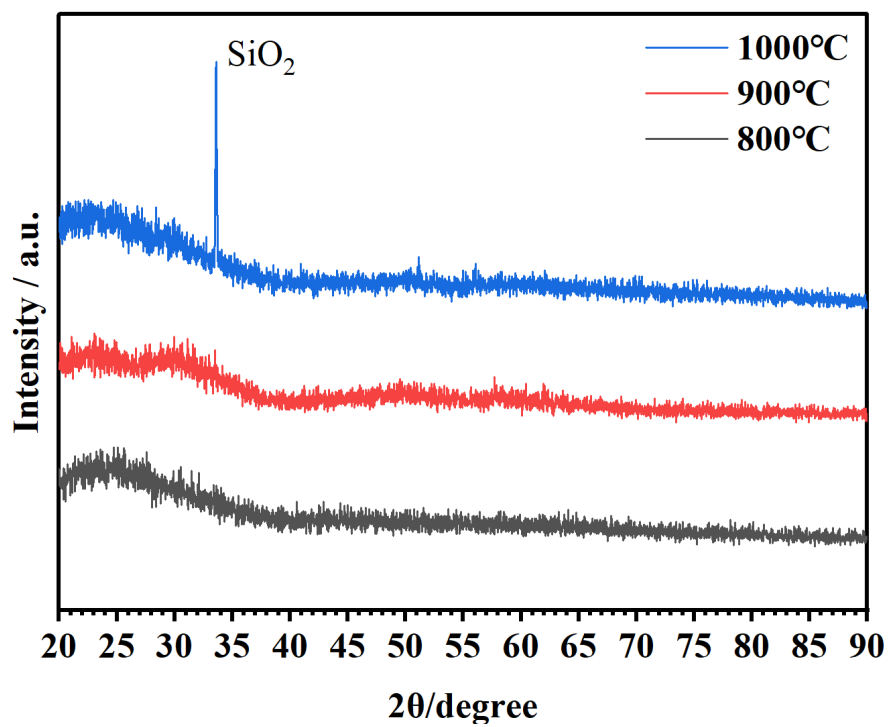
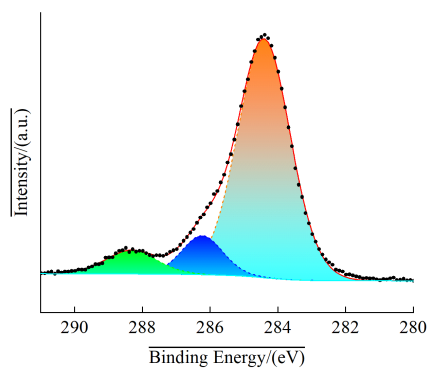
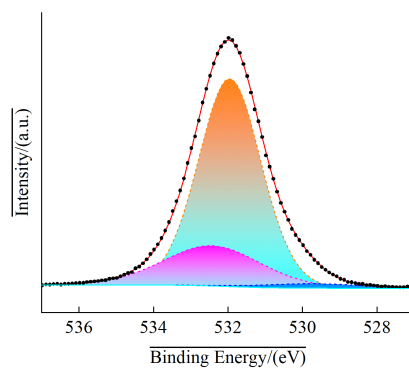
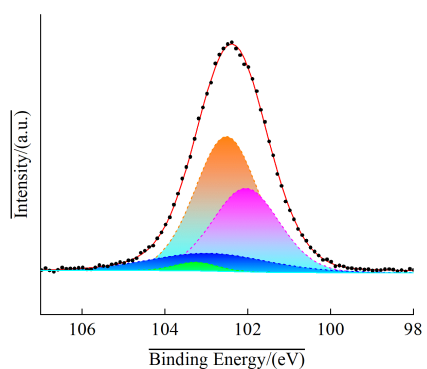
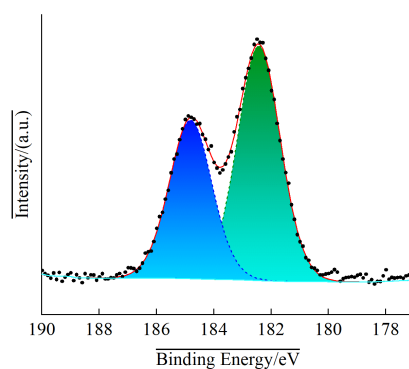
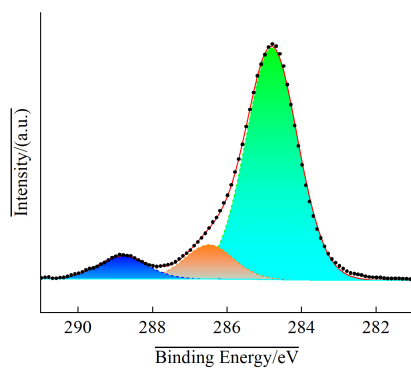
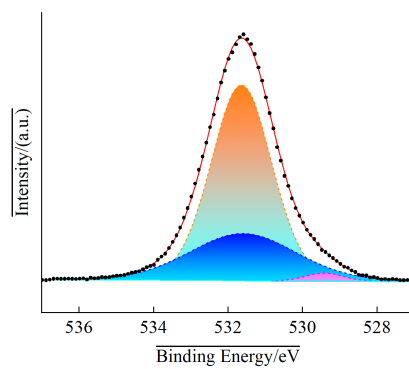
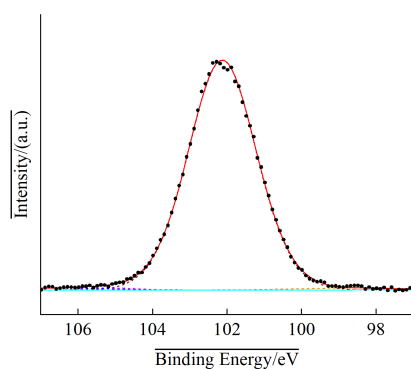
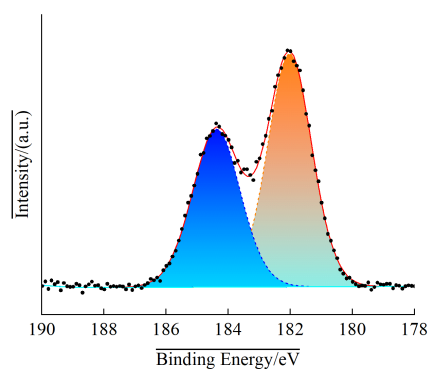


图 2.5: 从上至下 nZr=0.64/0.78/0.64

6 月 10 日回传 xps 数据一份：

(a) $n\text{Zr}=0.78/\text{PvP}=1.725$, 800°C , C1s (b) $n\text{Zr}=0.78/\text{PvP}=1.725, 800^\circ\text{C}$, O1s (c) $n\text{Zr}=0.78/\text{PvP}=1.725$, 800°C , Si2p (d) $n\text{Zr}=0.78/\text{PvP}=1.725, 800^\circ\text{C}$, Zr3d 图 2.6: $n\text{Zr}=0.78, 800^\circ\text{C}$ 组

(a) $n\text{Zr}=0.78/\text{PvP}=1.725, 900^\circ\text{C}$, C1s(b) $n\text{Zr}=0.78/\text{PvP}=1.725, 900^\circ\text{C}$, O1s(c) $n\text{Zr}=0.78/\text{PvP}=1.725, 900^\circ\text{C}$, Si2p(d) $n\text{Zr}=0.78/\text{PvP}=1.725, 900^\circ\text{C}$, Zr3d图 2.7: $n\text{Zr}=0.78, 900^\circ\text{C}$ 组

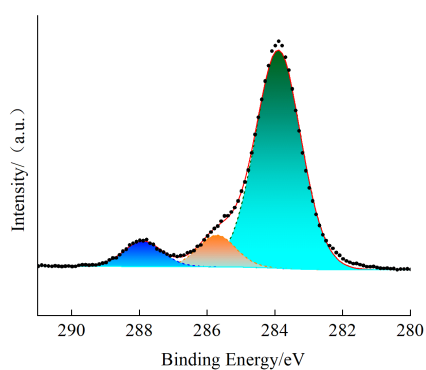
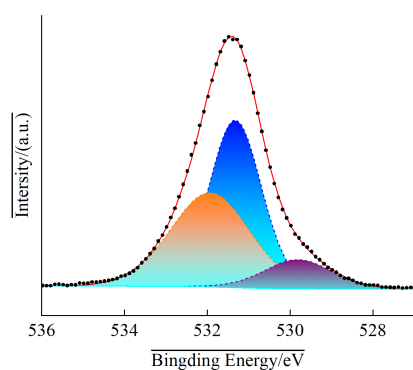
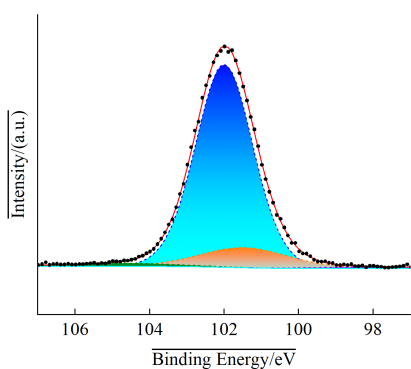
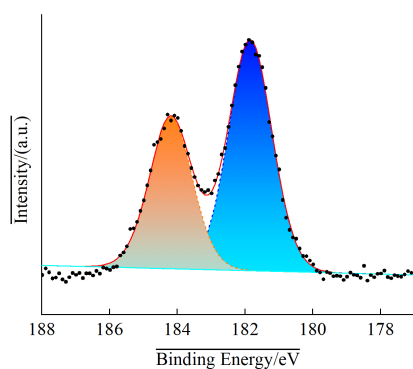
(a) $n\text{Zr}=0.64/\text{PvP}=1.725, 1000^\circ\text{C}$, C1s(b) $n\text{Zr}=0.64/\text{PvP}=1.725, 1000^\circ\text{C}$, O1s(c) $n\text{Zr}=0.64/\text{PvP}=1.725, 1000^\circ\text{C}$, Si2p(d) $n\text{Zr}=0.64/\text{PvP}=1.725, 1000^\circ\text{C}$, Zr3d图 2.8: $n\text{Zr}=0.64, 1000^\circ\text{C}$ 组

图 2.6c 与图 2.7c 对比发现图 2.7c 并没有四个子峰，这是比较奇怪的一个事情，与此同时，图 2.8c 的子峰之间的结合能区别也不显著 e；

2.6 材料性能对比

Material	Thickness (nm)	Minimum RL(dB)	EAB(GHz)	Ref.
Fe/SiC/PCS	2.25	-46.3	4.6(<-20dB)	[1]
MXene	2.7/2.1	-54.1(2.7)	7.76(2.1)	[2]
Fe/Co@C-CNFs	1.08/1.22	-18.66(1.08)	4.2(1.22)	[3]
PAN/Fe ₃ O ₄	4	-11.3	7	[4]
TiN/carbon-paraffin composites	1.9	-41.8	3.9	[5]
SiC	1.9	-57.8	12	[5]
ZnO/Co	3.0/2.6	-68.4(3.0)	5.9(2.6)	[6]
P-CNF/Fe	4.1	-44.86	3.28	[7]
CeO ₂ /NC	2.5	-42.95	8.48	[8]
Zr/SiC	3.5	-48.6	3.2	[9]
ZrC	1.25/1.0	-25.77(1.25)	3.04(1.0)	[10]
ZrO ₂ /ZrC/ZrB ₂	2.4	-21	8.64	[11]
ZrO ₂ /ZrB ₂ /C	4.0	-54	3.1	[12]
ZS-HNFA-x	2.4	-53.2	6.4	[13]
ZrO ₂ /CF-rGO	3.14	-62.99	8.19	[14]
ZrO ₂ /C	2.5	-36	7.3	[15]

参考文献

- [1] HOU Y, CHENG L, ZHANG Y, et al. Electrospinning of fe/sic hybrid fibers for highly efficient microwave absorption[J]. ACS applied materials & interfaces, 2017, 9(8): 7265-7271.
- [2] ZHANG S, JIA Z, ZHANG Y, et al. Electrospun fe_{0.64}ni_{0.36}/mxene/cnfs nanofibrous membranes with multicomponent heterostructures as flexible electromagnetic wave absorbers[J]. Nano Research, 2023, 16(2): 3395-3407.
- [3] CAI W J, JIANG J G, ZHANG Z D, et al. Carbon nanofibers embedded with fe-co alloy nanoparticles via electrospinning as lightweight high-performance electromagnetic wave absorbers[J/OL]. Rare Metals, 2024, 43(6): 2769-2783. <https://doi.org/10.1007/s12598-023-02592-7>.
- [4] YANG Y, GUO Z, ZHANG H, et al. Electrospun magnetic carbon composite fibers: Synthesis and electromagnetic wave absorption characteristics[J/OL]. Journal of Applied Polymer Science, 2013, 127(6): 4288-4295. <https://onlinelibrary.wiley.com/doi/abs/10.1002/app.38027>. DOI: <https://doi.org/10.1002/app.38027>.
- [5] WEI Y, ZHANG L, GONG C, et al. Fabrication of tin/carbon nanofibers by electrospinning and their electromagnetic wave absorption properties[J/OL]. Journal of Alloys and Compounds, 2018, 735: 1488-1493. <https://www.sciencedirect.com/science/article/pii/S092583881734077X>. DOI: <https://doi.org/10.1016/j.jallcom.2017.11.295>.
- [6] QIAO J, XU D, LV L, et al. Self-assembled zno/co hybrid nanotubes prepared by electrospinning for lightweight and high-performance electromagnetic wave absorption[J/OL]. ACS Applied Nano Materials, 2018, 1(9): 5297-5306. <https://doi.org/10.1021/acsanm.8b01303>.
- [7] ZUO X, XU P, ZHANG C, et al. Porous magnetic carbon nanofibers (p-cnf/fe) for low-frequency electromagnetic wave absorption synthesized by electrospinning[J/OL]. Ceramics International, 2019, 45(4): 4474-4481. <https://www.sciencedirect.com/science/article/pii/S0272884218332425>. DOI: <https://doi.org/10.1016/j.ceramint.2018.11.127>.
- [8] ZHAO P Y, WANG H Y, CAI B, et al. Electrospinning fabrication and ultra-wideband electromagnetic wave absorption properties of ceo₂/n-doped carbon nanofibers[J/OL]. Nano Research, 2022, 15(9): 7788-7796. <https://doi.org/10.1007/s12274-022-4675-x>.

- [9] ZHANG B, LIU Y, LI X, et al. Closed-cell zro2/sic-based composite nanofibers with efficient electromagnetic wave absorption and thermal insulation properties[J/OL]. *Journal of Alloys and Compounds*, 2022, 927: 167036. <https://www.sciencedirect.com/science/article/pii/S0925838822034272>. DOI: <https://doi.org/10.1016/j.jallcom.2022.167036>.
- [10] GUO Y, SONG Q, ZHANG L, et al. High-aspect-ratio zrc whiskers: Synthesis, growth mechanism and electromagnetic wave absorption properties[J/OL]. *Journal of Materiomics*, 2023, 9(2): 235-243. <https://www.sciencedirect.com/science/article/pii/S2352847822001460>. DOI: <https://doi.org/10.1016/j.jmat.2022.11.001>.
- [11] WANG Q, QI L, JIA Y, et al. Flexible zro2/zrc/zrb2 ceramic nanofiber mats by electrospinning with broadband electromagnetic absorption and high-temperature oxidation resistance[J/OL]. *Materials Letters*, 2024, 365: 136442. <https://www.sciencedirect.com/science/article/pii/S0167577X24005809>. DOI: <https://doi.org/10.1016/j.matlet.2024.136442>.
- [12] YANG C, LI K, HU M, et al. Flexible zro2/zrb2/c nanofiber felt with enhanced microwave absorption and ultralow thermal conductivity[J/OL]. *Journal of Materiomics*, 2025, 11(4): 100988. <https://www.sciencedirect.com/science/article/pii/S2352847824002272>. DOI: <https://doi.org/10.1016/j.jmat.2024.100988>.
- [13] ZHU H, WENG X, LIAO M, et al. Zro2-interface-engineered sic nanofiber aerogel with integrated hydrophobicity, thermal insulation, and broadband electromagnetic wave absorption[J/OL]. *Applied Surface Science*, 2025, 711: 164079. <https://www.sciencedirect.com/science/article/pii/S0169433225017945>. DOI: <https://doi.org/10.1016/j.apsusc.2025.164079>.
- [14] YIN X, WANG Y, PANG N, et al. Ultralight, highly elastic zro2/carbon fiber reinforced reduced graphene oxide aerogels with radar and infrared stealth capabilities[J/OL]. *Composites Part B: Engineering*, 2025, 303: 112628. <https://www.sciencedirect.com/science/article/pii/S1359836825005293>. DOI: <https://doi.org/10.1016/j.compositesb.2025.112628>.
- [15] WANG X, LIU L, WANG X, et al. Joule heat induced ultrafine zro2/c composites for enhanced microwave absorption[J/OL]. *Surfaces and Interfaces*, 2024, 51: 104818. <https://www.sciencedirect.com/science/article/pii/S2468023024009751>. DOI: <https://doi.org/10.1016/j.surfin.2024.104818>.
- [16] ZHAO P Y, WANG H Y, CAI B, et al. Electrospinning fabrication and ultra-wideband electromagnetic wave absorption properties of CeO2/N-doped carbon nanofibers[J/OL]. *Nano Research*, 2022, 15(9): 7788-7796. DOI: [10.1007/s12274-022-4675-x](https://doi.org/10.1007/s12274-022-4675-x).
- [17] LIU C, CHEN Q, SUN P, et al. Synthesis of novel high-entropy diborides with high-efficiency electromagnetic wave absorption and excellent thermal stability[J/OL]. *Journal of Advanced Ceramics*, 2025, 14(2): 9221030. DOI: [10.26599/JAC.2025.9221030](https://doi.org/10.26599/JAC.2025.9221030).

- [18] ZHOU Q, YIN X, YE F, et al. High temperature electromagnetic wave absorption properties of SiCf/Si₃N₄ composite induced by different SiC fibers[J/OL]. *Ceramics International*, 2019, 45(5): 6514-6522. DOI: [10.1016/j.ceramint.2018.12.142](https://doi.org/10.1016/j.ceramint.2018.12.142).
- [19] LAN X, WANG Z. Efficient high-temperature electromagnetic wave absorption enabled by structuring binary porous SiC with multiple interfaces[J/OL]. *Carbon*, 2020, 170: 517-526. DOI: [10.1016/j.carbon.2020.08.052](https://doi.org/10.1016/j.carbon.2020.08.052).
- [20] CAI W J, JIANG J G, ZHANG Z D, et al. Carbon nanofibers embedded with Fe–Co alloy nanoparticles via electrospinning as lightweight high-performance electromagnetic wave absorbers[J/OL]. *Rare Metals*, 2024, 43(6): 2769-2783. DOI: [10.1007/s12598-023-02592-7](https://doi.org/10.1007/s12598-023-02592-7).