



Radiation Tests: SIHFS9N60A MOSFET

- SEE tests performed at a flux of 3.5×10^8 p/cm²/s
 - The chips were biased and monitored for SEEs, and no events observed up to 3.4×10^{11} p/cm²), **passing the SEE tests**
 - The chips were characterized at CERN after irradiation and a shift of 2.5 V were observed in gate-source threshold voltage after 200 Gy (a very small effect in brick's performance)
- Performed at 3 Gy/h followed by annealing, **TID tests showed a smaller shift in gate-source threshold voltage, and were passed**
- **NIEL tests showed very small deviation in characterization** (due to gamma radiation in reactor)

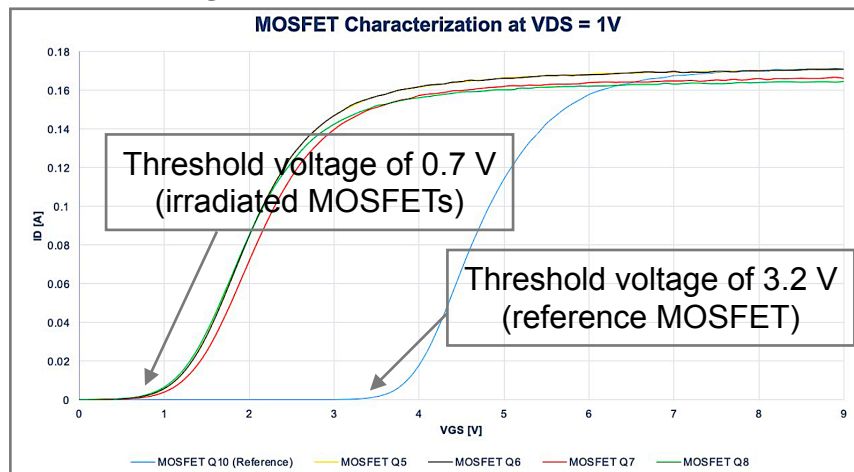

MOSFET characterization after TID of 200 Gy

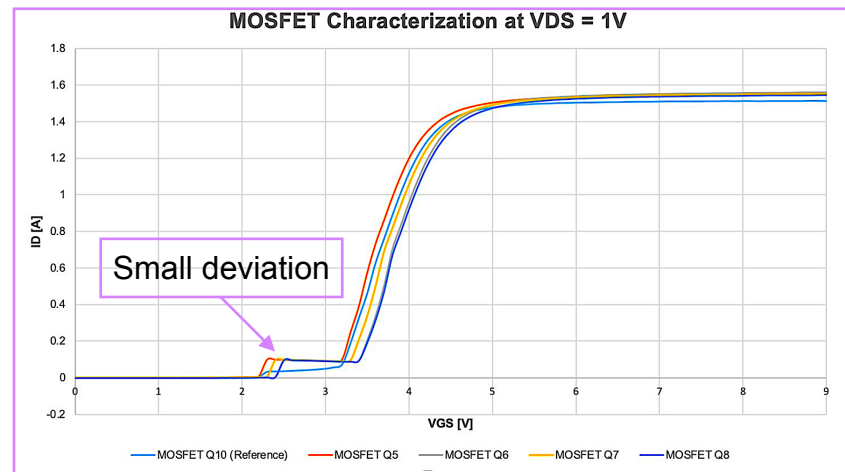

MOSFET characterization after NIEL tests