

Length Gauge Theory of Surface Second Harmonic Generation

Sean M. Anderson and Bernardo S. Mendoza¹

¹*Centro de Investigaciones en Optica,
León, Guanajuato, México, bms@cio.mx*

Abstract

We present a theoretical review of surface second harmonic generation (SHG) from semiconductor surfaces based on the longitudinal gauge. This layer-by-layer analysis is carefully presented in order to show how a surface SHG calculation can be readily evaluated. The nonlinear susceptibility tensor for a surface, $\chi^S(-2\omega; \omega, \omega)$ is split into two terms relating to inter-band and intra-band one-electron transitions.

Contents

I. Introduction	3
II. Non-linear Surface Susceptibility	4
III. Length Gauge	6
IV. Time-dependent Perturbation Theory	9
V. Layered Current Density	13
VI. Microscopic surface susceptibility	16
VII. Conclusions	19
A. \mathbf{r}_e and \mathbf{r}_i	19
B. Matrix elements of $\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k})$ and $\mathcal{V}_{nm}^{\text{nl},\ell}(\mathbf{k})$	22
C. $V_{nm}^{\sigma,\mathbf{a},\ell}$ and $(\mathcal{V}_{nm}^{\sigma,\mathbf{a},\ell})_{;k^b}$	26
D. Generalized derivative $(\omega_n(\mathbf{k}))_{;\mathbf{k}}$	29
E. Expressions for χ_{abc}^S in terms of $\mathcal{V}_{mn}^{\sigma,\mathbf{a},\ell}$	30
1. Intraband Contributions	30
2. Interband Contributions	34
F. Matrix elements of $\tau_{nm}^{\text{ab}}(\mathbf{k})$	34
G. Explicit expressions for $\mathcal{V}_{nm}^{a,\ell}(\mathbf{k})$ and $\mathcal{C}_{nm}^\ell(\mathbf{k})$	35
1. Time-reversal relations	36
H. Generalized derivative $(\mathbf{r}_{nm}(\mathbf{k}))_{;\mathbf{k}}$ for non-local potentials	37
1. Layer Case	39
I. Coding	40
1. Coding for $\mathcal{V}_{nm}^{\sigma,\mathbf{a},\ell}(\mathbf{k})$	45
2. $\Delta_{nm}^{\sigma,\mathbf{a},\ell}(\mathbf{k})$	45
3. Coding for $(\mathcal{V}_{nm}^{\text{LDA},\mathbf{a},\ell}(\mathbf{k}))_{;k^b}$	46

4. Summary	46
5. Bulk expressions	47
6. Layer or Bulk calculation	47
7. \mathcal{V} vs \mathcal{R}	48
8. Other responses	49
9. Consistency check-up 1	50
10. Consistency check-up 2	50
11. Consistency check-up 3	51
12. Consistency check-up 4	52
13. Consistency check-up 5	52
14. Subroutines	54
References	55

I. INTRODUCTION

Second harmonic generation (SHG) is a powerful spectroscopic tool for studying the optical properties of surfaces and interfaces since it has the advantage of being surface sensitive. Within the dipole approximation, inversion symmetry forbids SHG from the bulk of centrosymmetric materials. SHG is allowed at the surface of these materials where the inversion symmetry is broken and should necessarily come from the localized surface region. SHG allows the study of the structural atomic arrangement and phase transitions of clean and adsorbate covered surfaces. Since it is also an optical probe it can be used out of UHV conditions and is non-invasive and non-destructive. Experimentally, new tunable high intensity laser systems have made SHG spectroscopy readily accessible and applicable to a wide range of systems.^{1,2}

However, theoretical development of the field is still an ongoing subject of research. Some recent advances for the cases of semiconducting and metallic systems have appeared in the literature, where the use of theoretical models with experimental results have yielded correct physical interpretations for observed SHG spectra.^{1,3–10}

In a previous article¹¹ we reviewed some of the recent results in the study of SHG using the velocity gauge for the coupling between the electromagnetic field and the electron. In particular, we demonstrated a method to systematically analyze the different contributions to the observed SHG peaks.¹² This approach consists of separating the different contributions to the nonlinear

susceptibility according to 1ω and 2ω transitions, and the surface or bulk nature of the states among which the transitions take place.

To compliment those results, in this article we review the calculation of the nonlinear susceptibility using the longitudinal gauge. We show that it is possible to clearly obtain the “layer-by-layer” contribution for a slab scheme used for surface calculations.

II. NON-LINEAR SURFACE SUSCEPTIBILITY

In this section we outline the general procedure to obtain the surface susceptibility tensor for second harmonic generation. We start with the non-linear polarization \mathbf{P} written as

$$P_a(2\omega) = \chi_{abc}(-2\omega; \omega, \omega) E_b(\omega) E_c(\omega) + \chi_{abcl}(-2\omega; \omega, \omega) E_b(\omega) \nabla_c E_l(\omega) + \dots, \quad (1)$$

where $\chi_{abc}(-2\omega; \omega, \omega)$ and $\chi_{abcl}(-2\omega; \omega, \omega)$ correspond to the dipolar and quadrupolar susceptibilities. We drop the $(-2\omega; \omega, \omega)$ argument to ease on the notation. The sum continues with higher multipolar terms. If we consider a semi-infinite system with a centrosymmetric bulk, the equation above can be separated into two contributions from symmetry considerations alone; one from the surface of the system and the other from the bulk of the system. We take

$$P_a(\mathbf{r}) = \chi_{abc} E_b(\mathbf{r}) E_c(\mathbf{r}) + \chi_{abcl} E_b(\mathbf{r}) \frac{\partial}{\partial \mathbf{r}_c} E_l(\mathbf{r}) + \dots, \quad (2)$$

as the polarization with respect to the original coordinate system, and

$$P_a(-\mathbf{r}) = \chi_{abc} E_b(-\mathbf{r}) E_c(-\mathbf{r}) + \chi_{abcl} E_b(-\mathbf{r}) \frac{\partial}{\partial (-\mathbf{r}_c)} E_l(-\mathbf{r}) + \dots, \quad (3)$$

as the polarization in the coordinate system where inversion is taken, i.e. $\mathbf{r} \rightarrow -\mathbf{r}$. Note that we have kept the same susceptibility tensors, and they must be invariant under $\mathbf{r} \rightarrow -\mathbf{r}$ since the system is centrosymmetric. Recalling that $\mathbf{P}(\mathbf{r})$ and $\mathbf{E}(\mathbf{r})$ are polar vectors¹³, we have that Eq. (3) reduces to

$$\begin{aligned} -P_a(\mathbf{r}) &= \chi_{abc}(-E_b(\mathbf{r}))(-E_c(\mathbf{r})) - \chi_{abcl}(-E_b(\mathbf{r}))\left(-\frac{\partial}{\partial \mathbf{r}_c}\right)(-E_l(\mathbf{r})) + \dots, \\ P_a(\mathbf{r}) &= -\chi_{abc} E_b(\mathbf{r}) E_c(\mathbf{r}) + \chi_{abcl} E_b(\mathbf{r}) \frac{\partial}{\partial \mathbf{r}_c} E_l(\mathbf{r}) + \dots, \end{aligned} \quad (4)$$

that when compared with Eq. (2) leads to the conclusion that

$$\chi_{abc} = 0 \quad (5)$$

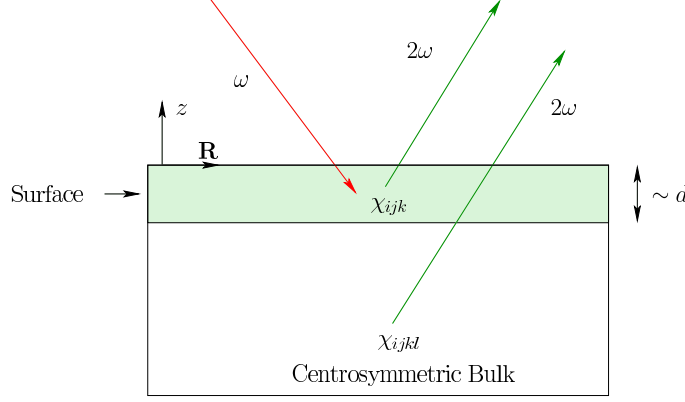


FIG. 1: (Color Online) Sketch of the semi-infinite system with a centrosymmetric bulk. The surface region is of width $\sim d$. The incoming photon of frequency ω is represented by a downward red arrow, whereas both the surface and bulk created second harmonic photons of frequency 2ω are represented by upward green arrows. The red color suggests an incoming infrared photon with a green second harmonic photon. The dipolar (χ_{abc}), and quadrupolar (χ_{abcl}) susceptibility tensors are shown in the regions where they are different from zero. The axis has z perpendicular to the surface and \mathbf{R} parallel to it.

for a centrosymmetric bulk.

If we move to the surface of the semi-infinite system our assumption of centrosymmetry breaks down, and there is no restriction in χ_{abc} . We conclude that the leading term of the polarization in a surface region is given by

$$\int dz P_a(\mathbf{R}, z) \approx dP_a \equiv P_a^S \equiv \chi_{abc}^S E_b E_c, \quad (6)$$

where d is the surface region from which the dipolar signal of \mathbf{P} is different from zero (see Fig. 1), and $\mathbf{P}^S \equiv d\mathbf{P}$ is the surface SH polarization. Then, from Eq. (1) we obtain that

$$\chi_{abc}^S = d\chi_{abc} \quad (7)$$

is the SH surface susceptibility. On the other hand,

$$P_a^b(\mathbf{r}) = \chi_{abcl} E_b(\mathbf{r}) \nabla_c E_l(\mathbf{r}), \quad (8)$$

gives the bulk polarization. We immediately recognize that the surface polarization is of dipolar order while the bulk polarization is of quadrupolar order. The surface, χ_{abc}^S , and bulk, χ_{abcl} , susceptibility tensor ranks are three and four, respectively. We will only concentrate on surface SHG in this article even though bulk generated SH is also a very important optical phenomenon. Also, we leave out of this article other interesting surface SH phenomena like, electric field induced second harmonic (EFISH), which would be represented by a surface susceptibility tensor of quadrupolar

origin. In centrosymmetric systems for which the quadrupolar bulk response is much smaller than the dipolar surface response, SH is readily used as a very useful and powerful optical surface probe.¹

In the following sections we present the theoretical approach to derive the expressions for the surface susceptibility tensor χ_{abc}^S .

III. LENGTH GAUGE

We follow the article by Aversa and Sipe¹⁴ to calculate the optical properties of a given system within the longitudinal gauge. More recent derivations can also be found in Refs. 15,16. Assuming the long-wavelength approximation which implies a position independent electric field, $\mathbf{E}(t)$, the Hamiltonian in the length gauge approximation is given by

$$\hat{H} = \hat{H}_0^\sigma - e\hat{\mathbf{r}} \cdot \mathbf{E}, \quad (9)$$

with

$$\hat{H}_0^\sigma = \hat{H}_0^{\text{LDA}} + \mathcal{S}(\mathbf{r}, \mathbf{p}), \quad (10)$$

as the unperturbed Hamiltonian. The LDA Hamiltonian can be expressed as follows,

$$\begin{aligned} \hat{H}_0^{\text{LDA}} &= \frac{\hat{p}^2}{2m_e} + \hat{V}^{\text{ps}} \\ \hat{V}^{\text{ps}} &= \hat{V}^l(\hat{\mathbf{r}}) + \hat{V}^{\text{nl}}, \end{aligned} \quad (11)$$

where $\hat{V}^l(\hat{\mathbf{r}})$ and \hat{V}^{nl} are the local and the non-local parts of the crystal pseudopotential \hat{V}^{ps} . For the latter, we have that

$$V^{\text{nl}}(\mathbf{r}, \mathbf{r}') \equiv \langle \mathbf{r} | \hat{V}^{\text{nl}} | \mathbf{r}' \rangle \neq 0 \quad \text{for} \quad \mathbf{r} \neq \mathbf{r}', \quad (12)$$

where $V^{\text{nl}}(\mathbf{r}, \mathbf{r}')$ is a function of \mathbf{r} and \mathbf{r}' representing the non-local contribution of the pseudopotential. The Schrödinger equation reads

$$\left(\frac{-\hbar^2}{2m_e} \nabla^2 + \hat{V}^l(\mathbf{r}) \right) \psi_{n\mathbf{k}}(\mathbf{r}) + \int d\mathbf{r}' \hat{V}^{\text{nl}}(\mathbf{r}, \mathbf{r}') \psi_{n\mathbf{k}}(\mathbf{r}') = E_i \psi_{n\mathbf{k}}(\mathbf{r}), \quad (13)$$

where $\psi_{n\mathbf{k}}(\mathbf{r}) = \langle \mathbf{r} | n\mathbf{k} \rangle = e^{i\mathbf{k} \cdot \mathbf{r}} u_{n\mathbf{k}}(\mathbf{r})$, are the real space representations of the Bloch states $|n\mathbf{k}\rangle$ labelled by the band index n and the crystal momentum \mathbf{k} , and $u_{n\mathbf{k}}(\mathbf{r})$ is cell periodic. m_e is the bare mass of the electron and Ω is the unit cell volume. The nonlocal scissors operator is given by

$$\mathcal{S}(\mathbf{r}, \mathbf{p}) = \hbar \Sigma \sum_n \int d^3k' (1 - f_n(\mathbf{k})) |n\mathbf{k}'\rangle \langle n\mathbf{k}'|, \quad (14)$$

where $f_n(\mathbf{k})$ is the occupation number, that for $T = 0$ K, is independent of \mathbf{k} , and is one for filled bands and zero for unoccupied bands. For semiconductors the filled bands correspond to valence bands ($n = v$) and the unoccupied bands to conduction bands ($n = c$). We have that

$$\begin{aligned} H_0^{\text{LDA}}|n\mathbf{k}\rangle &= \hbar\omega_n^{\text{LDA}}(\mathbf{k})|n\mathbf{k}\rangle \\ H_0^\sigma|n\mathbf{k}\rangle &= \hbar\omega_n^\sigma(\mathbf{k})|n\mathbf{k}\rangle, \end{aligned} \quad (15)$$

where

$$\hbar\omega_n^\sigma(\mathbf{k}) = \hbar\omega_n^{\text{LDA}}(\mathbf{k}) + \hbar\Sigma(1 - f_n), \quad (16)$$

is the scissored energy. Here, $\hbar\Sigma$ is the value by which the conduction bands are rigidly (\mathbf{k} -independent) shifted upwards in energy, also known as the scissors shift. Σ could be taken to be \mathbf{k} dependent, but for most calculations (like the ones presented here), a rigid shift is sufficient. We can take $\hbar\Sigma = E_g - E_g^{\text{LDA}}$ where E_g could be the experimental band gap or GW band gap taken at the Γ point, i.e. $\mathbf{k} = 0$. We used the fact that $|n\mathbf{k}\rangle^{\text{LDA}} \approx |n\mathbf{k}\rangle^\sigma$, thus negating the need to label the Bloch states with the LDA or σ superscripts. The matrix elements of \mathbf{r} are split between the *intraband* (\mathbf{r}_i) and *interband* (\mathbf{r}_e) parts, where $\mathbf{r} = \mathbf{r}_i + \mathbf{r}_e$ and ^{14,17,18}

$$\langle n\mathbf{k}|\hat{\mathbf{r}}_i|m\mathbf{k}'\rangle = \delta_{nm} [\delta(\mathbf{k} - \mathbf{k}')\boldsymbol{\xi}_{nm}(\mathbf{k}) + i\nabla_{\mathbf{k}}\delta(\mathbf{k} - \mathbf{k}')], \quad (17)$$

$$\langle n\mathbf{k}|\hat{\mathbf{r}}_e|m\mathbf{k}'\rangle = (1 - \delta_{nm})\delta(\mathbf{k} - \mathbf{k}')\boldsymbol{\xi}_{nm}(\mathbf{k}), \quad (18)$$

and

$$\boldsymbol{\xi}_{nm}(\mathbf{k}) \equiv i\frac{(2\pi)^3}{\Omega} \int_{\Omega} d\mathbf{r} u_{n\mathbf{k}}^*(\mathbf{r}) \nabla_{\mathbf{k}} u_{m\mathbf{k}}(\mathbf{r}). \quad (19)$$

The interband part \mathbf{r}_e can be obtained as follows. We start by introducing the velocity operator

$$\hat{\mathbf{v}}^\sigma = \frac{1}{i\hbar}[\hat{\mathbf{r}}, \hat{H}_0^\sigma], \quad (20)$$

and calculating its matrix elements

$$i\hbar\langle n\mathbf{k}|\hat{\mathbf{v}}^\sigma|m\mathbf{k}\rangle = \langle n\mathbf{k}|[\hat{\mathbf{r}}, \hat{H}_0^\sigma]|m\mathbf{k}\rangle = \langle n\mathbf{k}|\hat{\mathbf{r}}\hat{H}_0^\sigma - \hat{H}_0^\sigma\hat{\mathbf{r}}|m\mathbf{k}\rangle = (\hbar\omega_m^\sigma(\mathbf{k}) - \hbar\omega_n^\sigma(\mathbf{k}))\langle n\mathbf{k}|\hat{\mathbf{r}}|m\mathbf{k}\rangle, \quad (21)$$

thus defining $\omega_{nm}^\sigma(\mathbf{k}) = \omega_n^\sigma(\mathbf{k}) - \omega_m^\sigma(\mathbf{k})$ we get

$$\mathbf{r}_{nm}(\mathbf{k}) = \frac{\mathbf{v}_{nm}^\sigma(\mathbf{k})}{i\omega_{nm}^\sigma(\mathbf{k})} \quad n \notin D_m, \quad (22)$$

which can be identified as $\mathbf{r}_{nm} = (1 - \delta_{nm})\boldsymbol{\xi}_{nm} \rightarrow \mathbf{r}_{e,nm}$. Here, D_m are all the possible degenerate m -states. When \mathbf{r}_i appears in commutators we use ¹⁴

$$\langle n\mathbf{k}|[\hat{\mathbf{r}}_i, \hat{\mathcal{O}}]|m\mathbf{k}'\rangle = i\delta(\mathbf{k} - \mathbf{k}')(\mathcal{O}_{nm})_{;\mathbf{k}}, \quad (23)$$

with

$$(\mathcal{O}_{nm})_{;\mathbf{k}} = \nabla_{\mathbf{k}} \mathcal{O}_{nm}(\mathbf{k}) - i \mathcal{O}_{nm}(\mathbf{k}) (\xi_{nn}(\mathbf{k}) - \xi_{mm}(\mathbf{k})), \quad (24)$$

where “; \mathbf{k} ” denotes the generalized derivative (see Appendix A).

As can be seen from Eq. (10) and (11), both \hat{S} and \hat{V}^{nl} are nonlocal potentials. Their contribution in the calculation of the optical response has to be taken in order to get reliable results.¹⁹

We proceed as follows; from Eqs. (20), (10) and (11) we find

$$\begin{aligned} \hat{\mathbf{v}}^\sigma &= \frac{\hat{\mathbf{p}}}{m_e} + \frac{1}{i\hbar} [\hat{\mathbf{r}}, \hat{V}^{\text{nl}}(\mathbf{r}, \mathbf{r}')] + \frac{1}{i\hbar} [\hat{\mathbf{r}}, \hat{S}(\mathbf{r}, \mathbf{p})] \\ &\equiv \hat{\mathbf{v}} + \hat{\mathbf{v}}^{\text{nl}} + \hat{\mathbf{v}}^{\mathcal{S}} = \hat{\mathbf{v}}^{\text{LDA}} + \hat{\mathbf{v}}^{\mathcal{S}}, \end{aligned} \quad (25)$$

where we have defined

$$\begin{aligned} \hat{\mathbf{v}} &= \frac{\hat{\mathbf{p}}}{m_e} \\ \hat{\mathbf{v}}^{\text{nl}} &= \frac{1}{i\hbar} [\hat{\mathbf{r}}, \hat{V}^{\text{nl}}] \\ \hat{\mathbf{v}}^{\mathcal{S}} &= \frac{1}{i\hbar} [\hat{\mathbf{r}}, \hat{S}(\mathbf{r}, \mathbf{p})] \\ \hat{\mathbf{v}}^{\text{LDA}} &= \hat{\mathbf{v}} + \hat{\mathbf{v}}^{\text{nl}} \end{aligned} \quad (26)$$

with $\hat{\mathbf{p}} = -i\hbar \nabla$ the momentum operator. Using Eq. (14), we obtain that the matrix elements of $\hat{\mathbf{v}}^{\mathcal{S}}$ are given by

$$\mathbf{v}_{nm}^{\mathcal{S}} = i \Sigma f_{mn} \mathbf{r}_{nm}, \quad (27)$$

with $f_{nm} = f_n - f_m$, where we see that $\mathbf{v}_{nn}^{\mathcal{S}} = 0$, then

$$\begin{aligned} \mathbf{v}_{nm}^\sigma &= \mathbf{v}_{nm}^{\text{LDA}} + i \Sigma f_{mn} \mathbf{r}_{nm} \\ &= \mathbf{v}_{nm}^{\text{LDA}} + i \Sigma f_{mn} \frac{\mathbf{v}_{nm}^\sigma(\mathbf{k})}{i \omega_{nm}^\sigma(\mathbf{k})} \\ \mathbf{v}_{nm}^\sigma \frac{\omega_{nm}^\sigma - \Sigma f_{mn}}{\omega_{nm}^\sigma} &= \mathbf{v}_{nm}^{\text{LDA}} \\ \mathbf{v}_{nm}^\sigma \frac{\omega_{nm}^{\text{LDA}}}{\omega_{nm}^\sigma} &= \mathbf{v}_{nm}^{\text{LDA}} \\ \frac{\mathbf{v}_{nm}^\sigma}{\omega_{nm}^\sigma} &= \frac{\mathbf{v}_{nm}^{\text{LDA}}}{\omega_{nm}^{\text{LDA}}}, \end{aligned} \quad (28)$$

since $\omega_{nm}^\sigma - \Sigma f_{mn} = \omega_{nm}^{\text{LDA}}$. Therefore,

$$\begin{aligned} \mathbf{v}_{nm}^\sigma(\mathbf{k}) &= \frac{\omega_{nm}^\sigma}{\omega_{nm}^{\text{LDA}}} \mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k}) = \left(1 + \frac{\Sigma}{\omega_c(\mathbf{k}) - \omega_v(\mathbf{k})} \right) \mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k}) \quad n \notin D_m \\ \mathbf{v}_{nn}^\sigma(\mathbf{k}) &= \mathbf{v}_{nn}^{\text{LDA}}(\mathbf{k}), \end{aligned} \quad (29)$$

and Eq. (22) gives

$$\mathbf{r}_{nm}(\mathbf{k}) = \frac{\mathbf{v}_{nm}^\sigma(\mathbf{k})}{i\omega_{nm}^\sigma(\mathbf{k})} = \frac{\mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k})}{i\omega_{nm}^{\text{LDA}}(\mathbf{k})} \quad n \notin D_m. \quad (30)$$

The matrix elements of \mathbf{r}_e are the same whether we use the LDA or the scissored Hamiltonian and there is no need to label them with either LDA or S superscripts. Thus, we can write

$$\mathbf{r}_{e,nm} \rightarrow \mathbf{r}_{nm}(\mathbf{k}) = \frac{\mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k})}{i\omega_{nm}^{\text{LDA}}(\mathbf{k})} \quad n \notin D_m, \quad (31)$$

which gives the interband matrix elements of the position operator in terms of the matrix elements of $\hat{\mathbf{v}}^{\text{LDA}}$. These matrix elements include the matrix elements of $\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k})$ which can be readily calculated²⁰ for fully separable nonlocal pseudopotentials in the Kleinman-Bylander form.^{21–23} In Appendix B we outline how this can be accomplished.

IV. TIME-DEPENDENT PERTURBATION THEORY

In the independent particle approximation, we use the electron density operator $\hat{\rho}$ to obtain the expectation value of any observable \mathcal{O} as

$$\mathcal{O} = \text{Tr}(\hat{\mathcal{O}}\hat{\rho}) = \text{Tr}(\hat{\rho}\hat{\mathcal{O}}), \quad (32)$$

where Tr is the trace and is invariant under cyclic permutations. The dynamic equation of motion for ρ is given by

$$i\hbar \frac{d\hat{\rho}}{dt} = [\hat{H}, \hat{\rho}], \quad (33)$$

where it is more convenient to work in the interaction picture. We transform all operators according to

$$\hat{\mathcal{O}}_I = \hat{U}\hat{\mathcal{O}}\hat{U}^\dagger, \quad (34)$$

where

$$\hat{U} = e^{i\hat{H}_0 t/\hbar}, \quad (35)$$

is the unitary operator that shifts us to the interaction picture. Note that $\hat{\mathcal{O}}_I$ depends on time even if $\hat{\mathcal{O}}$ does not. Then, we transform Eq. (33) into

$$i\hbar \frac{d\hat{\rho}_I(t)}{dt} = [-e\hat{\mathbf{r}}_I(t) \cdot \mathbf{E}(t), \hat{\rho}_I(t)], \quad (36)$$

that leads to

$$\hat{\rho}_I(t) = \hat{\rho}_I(t = -\infty) + \frac{ie}{\hbar} \int_{-\infty}^t dt' [\hat{\mathbf{r}}_I(t') \cdot \mathbf{E}(t'), \hat{\rho}_I(t')]. \quad (37)$$

We assume that the interaction is switched-on adiabatically and choose a time-periodic perturbing field, to write

$$\mathbf{E}(t) = \mathbf{E} e^{-i\omega t} e^{\eta t} = \mathbf{E} e^{-i\tilde{\omega} t}, \quad (38)$$

with

$$\tilde{\omega} = \omega + i\eta, \quad (39)$$

where $\eta > 0$ assures that at $t = -\infty$ the interaction is zero and has its full strength \mathbf{E} at $t = 0$. After computing the required time integrals one takes $\eta \rightarrow 0$. Also, $\hat{\rho}_I(t = -\infty)$ should be time independent and thus $[\hat{H}, \hat{\rho}]_{t=-\infty} = 0$. This implies that $\hat{\rho}_I(t = -\infty) = \hat{\rho}(t = -\infty) \equiv \hat{\rho}_0$, where $\hat{\rho}_0$ is the density matrix of the unperturbed ground state, such that

$$\langle n\mathbf{k} | \hat{\rho}_0 | m\mathbf{k}' \rangle = f_n(\hbar\omega_n^\sigma(\mathbf{k})) \delta_{nm} \delta(\mathbf{k} - \mathbf{k}'), \quad (40)$$

with $f_n(\hbar\omega_n^\sigma(\mathbf{k})) = f_{n\mathbf{k}}$ as the Fermi-Dirac distribution function.

We solve Eq. (37) using the standard iterative solution, for which we write

$$\hat{\rho}_I = \hat{\rho}_I^{(0)} + \hat{\rho}_I^{(1)} + \hat{\rho}_I^{(2)} + \dots, \quad (41)$$

where $\hat{\rho}_I^{(N)}$ is the density operator to order N in $\mathbf{E}(t)$. Then, Eq. (37) reads

$$\hat{\rho}_I^{(0)} + \hat{\rho}_I^{(1)} + \hat{\rho}_I^{(2)} + \dots = \hat{\rho}_0 + \frac{ie}{\hbar} \int_{-\infty}^t dt' [\hat{\mathbf{r}}_I(t') \cdot \mathbf{E}(t'), \hat{\rho}_I^{(0)} + \hat{\rho}_I^{(1)} + \hat{\rho}_I^{(2)} + \dots], \quad (42)$$

where, by equating equal orders in the perturbation, we find

$$\hat{\rho}_I^{(0)} \equiv \hat{\rho}_0, \quad (43)$$

and

$$\hat{\rho}_I^{(N)}(t) = \frac{ie}{\hbar} \int_{-\infty}^t dt' [\hat{\mathbf{r}}_I(t') \cdot \mathbf{E}(t'), \hat{\rho}_I^{(N-1)}(t')]. \quad (44)$$

It is simple to show that matrix elements of Eq. (44) satisfy $\langle n\mathbf{k} | \hat{\rho}_I^{(N+1)}(t) | m\mathbf{k}' \rangle = \rho_{I,nm}^{(N+1)}(\mathbf{k}) \delta(\mathbf{k} - \mathbf{k}')$, with

$$\rho_{I,nm}^{(N+1)}(\mathbf{k}; t) = \frac{ie}{\hbar} \int_{-\infty}^t dt' \langle n\mathbf{k} | [\hat{\mathbf{r}}_I(t'), \hat{\rho}_I^{(N)}(t')] | m\mathbf{k} \rangle \cdot \mathbf{E}(t'). \quad (45)$$

We now work out the commutator of Eq. (45). Then,

$$\begin{aligned}
\langle n\mathbf{k} | [\hat{\mathbf{r}}_I(t), \hat{\rho}_I^{(N)}(t)] | m\mathbf{k} \rangle &= \langle n\mathbf{k} | [\hat{U}\hat{\mathbf{r}}\hat{U}^\dagger, \hat{U}\hat{\rho}^{(N)}(t)\hat{U}^\dagger] | m\mathbf{k} \rangle \\
&= \langle n\mathbf{k} | \hat{U}[\hat{\mathbf{r}}, \hat{\rho}^{(N)}(t)]\hat{U}^\dagger | m\mathbf{k} \rangle \\
&= e^{i\omega_{nm}^\sigma t} \left(\langle n\mathbf{k} | [\hat{\mathbf{r}}_e, \hat{\rho}^{(N)}(t)] + [\hat{\mathbf{r}}_i, \hat{\rho}^{(N)}(t)] | m\mathbf{k} \rangle \right).
\end{aligned} \tag{46}$$

We calculate the interband term first, so using Eq. (31) we obtain

$$\begin{aligned}
\langle n\mathbf{k} | [\hat{\mathbf{r}}_e, \hat{\rho}^{(N)}(t)] | m\mathbf{k} \rangle &= \sum_{\ell} \left(\langle n\mathbf{k} | \hat{\mathbf{r}}_e | \ell\mathbf{k} \rangle \langle \ell\mathbf{k} | \hat{\rho}^{(N)}(t) | m\mathbf{k} \rangle \right. \\
&\quad \left. - \langle n\mathbf{k} | \hat{\rho}^{(N)}(t) | \ell\mathbf{k} \rangle \langle \ell\mathbf{k} | \hat{\mathbf{r}}_e | m\mathbf{k} \rangle \right) \\
&= \sum_{\ell \neq n, m} \left(\mathbf{r}_{n\ell}(\mathbf{k}) \rho_{\ell m}^{(N)}(\mathbf{k}; t) - \rho_{n\ell}^{(N)}(\mathbf{k}; t) \mathbf{r}_{\ell m}(\mathbf{k}) \right) \\
&\equiv \mathbf{R}_e^{(N)}(\mathbf{k}; t),
\end{aligned} \tag{47}$$

and from Eq. (23),

$$\langle n\mathbf{k} | [\hat{\mathbf{r}}_i, \hat{\rho}^{(N)}(t)] | m\mathbf{k}' \rangle = i\delta(\mathbf{k} - \mathbf{k}')(\rho_{nm}^{(N)}(t))_{;\mathbf{k}} \equiv \delta(\mathbf{k} - \mathbf{k}')\mathbf{R}_i^{(N)}(\mathbf{k}; t). \tag{48}$$

Then Eq. (45) becomes

$$\rho_{I, nm}^{(N+1)}(\mathbf{k}; t) = \frac{ie}{\hbar} \int_{-\infty}^t dt' e^{i(\omega_{nm}^\sigma - \tilde{\omega})t'} \left[R_e^{b(N)}(\mathbf{k}; t') + R_i^{b(N)}(\mathbf{k}; t') \right] E^b, \tag{49}$$

where the roman superindices a, b, c denote Cartesian components that are summed over if repeated. Starting from the linear response and proceeding from Eq. (40) and (47),

$$\begin{aligned}
R_e^{b(0)}(\mathbf{k}; t) &= \sum_{\ell} \left(r_{n\ell}^b(\mathbf{k}) \rho_{\ell m}^{(0)}(\mathbf{k}) - \rho_{n\ell}^{(0)}(\mathbf{k}) r_{\ell m}^b(\mathbf{k}) \right) \\
&= \sum_{\ell} \left(r_{n\ell}^b(\mathbf{k}) \delta_{\ell m} f_m(\hbar\omega_m^\sigma(\mathbf{k})) - \delta_{n\ell} f_n(\hbar\omega_n^\sigma(\mathbf{k})) r_{\ell m}^b(\mathbf{k}) \right) \\
&= f_{mn\mathbf{k}} r_{nm}^b(\mathbf{k}),
\end{aligned} \tag{50}$$

where $f_{mn\mathbf{k}} = f_{m\mathbf{k}} - f_{n\mathbf{k}}$. From now on, it should be clear that the matrix elements of \mathbf{r}_{nm} imply $n \notin D_m$. We also have from Eq. (48) and Eq. (24) that

$$R_i^{b(0)}(\mathbf{k}) = i(\rho_{nm}^{(0)})_{;\mathbf{k}^b} = i\delta_{nm}(f_{n\mathbf{k}})_{;\mathbf{k}^b} = i\delta_{nm} \nabla_{\mathbf{k}^b} f_{n\mathbf{k}}. \tag{51}$$

For a semiconductor at $T = 0$, $f_{n\mathbf{k}}$ is one if the state $|n\mathbf{k}\rangle$ is a valence state and zero if it is a conduction state; thus $\nabla_{\mathbf{k}} f_{n\mathbf{k}} = 0$ and $\mathbf{R}_i^{(0)} = 0$ and the linear response has no contribution from

intraband transitions. Then,

$$\begin{aligned}
\rho_{I,nm}^{(1)}(\mathbf{k}; t) &= \frac{ie}{\hbar} f_{mn\mathbf{k}} r_{nm}^b(\mathbf{k}) E^b \int_{-\infty}^t dt' e^{i(\omega_{nm\mathbf{k}}^\sigma - \tilde{\omega})t'} \\
&= \frac{e}{\hbar} f_{mn\mathbf{k}} r_{nm}^b(\mathbf{k}) E^b \frac{e^{i(\omega_{nm\mathbf{k}}^\sigma - \tilde{\omega})t}}{\omega_{nm\mathbf{k}}^\sigma - \tilde{\omega}} \\
&= e^{i\omega_{nm\mathbf{k}}^\sigma t} B_{mn}^b(\mathbf{k}) E^b(t) \\
&= e^{i\omega_{nm\mathbf{k}}^\sigma t} \rho_{nm}^{(1)}(\mathbf{k}; t),
\end{aligned} \tag{52}$$

with

$$B_{nm}^b(\mathbf{k}, \omega) = \frac{e}{\hbar} \frac{f_{mn\mathbf{k}} r_{nm}^b(\mathbf{k})}{\omega_{nm\mathbf{k}}^\sigma - \tilde{\omega}}, \tag{53}$$

and

$$\rho_{nm}^{(1)}(\mathbf{k}; t) = B_{mn}^b(\mathbf{k}, \omega) E^b(\omega) e^{-i\tilde{\omega}t}. \tag{54}$$

Now, we calculate the second-order response. Then, from Eq. (47)

$$\begin{aligned}
R_e^{b(1)}(\mathbf{k}; t) &= \sum_{\ell} \left(r_{n\ell}^b(\mathbf{k}) \rho_{\ell m}^{(1)}(\mathbf{k}; t) - \rho_{n\ell}^{(1)}(\mathbf{k}; t) r_{\ell m}^b(\mathbf{k}) \right) \\
&= \sum_{\ell} \left(r_{n\ell}^b(\mathbf{k}) B_{\ell m}^c(\mathbf{k}, \omega) - B_{n\ell}^c(\mathbf{k}, \omega) r_{\ell m}^b(\mathbf{k}) \right) E^c(t),
\end{aligned} \tag{55}$$

and from Eq. (48)

$$R_i^{b(1)}(\mathbf{k}; t) = i(\rho_{nm}^{(1)}(t))_{;k^b} = iE^c(t)(B_{nm}^c(\mathbf{k}, \omega))_{;k^b}. \tag{56}$$

Using Eqs. (55) and (56) in Eq. (49), we obtain

$$\begin{aligned}
\rho_{I,nm}^{(2)}(\mathbf{k}; t) &= \frac{ie}{\hbar} \left[\sum_{\ell} \left(r_{n\ell}^b(\mathbf{k}) B_{\ell m}^c(\mathbf{k}, \omega) - B_{n\ell}^c(\mathbf{k}, \omega) r_{\ell m}^b(\mathbf{k}) \right) \right. \\
&\quad \left. + i(B_{nm}^c(\mathbf{k}, \omega))_{;k^b} \right] E_{\omega}^b E_{\omega}^c \int_{-\infty}^t dt' e^{i(\omega_{nm\mathbf{k}}^\sigma - 2\tilde{\omega})t'} \\
&= \frac{e}{\hbar} \left[\sum_{\ell} \left(r_{n\ell}^b(\mathbf{k}) B_{\ell m}^c(\mathbf{k}, \omega) - B_{n\ell}^c(\mathbf{k}, \omega) r_{\ell m}^b(\mathbf{k}) \right) \right. \\
&\quad \left. + i(B_{nm}^c(\mathbf{k}, \omega))_{;k^b} \right] E_{\omega}^b E_{\omega}^c \frac{e^{i(\omega_{nm\mathbf{k}}^\sigma - 2\tilde{\omega})t}}{\omega_{nm\mathbf{k}}^\sigma - 2\tilde{\omega}} \\
&= e^{i\omega_{nm\mathbf{k}}^\sigma t} \rho_{nm}^{(2)}(\mathbf{k}; t).
\end{aligned} \tag{57}$$

Now, we write $\rho_{nm}^{(2)}(\mathbf{k}; t) = \rho_{nm}^{(2)}(\mathbf{k}; 2\omega) e^{-i2\tilde{\omega}t}$, with

$$\begin{aligned}
\rho_{nm}^{(2)}(\mathbf{k}; 2\omega) &= \frac{e}{i\hbar} \frac{1}{\omega_{nm\mathbf{k}}^\sigma - 2\tilde{\omega}} \left[- (B_{nm}^c(\mathbf{k}, \omega))_{;k^b} \right. \\
&\quad \left. + i \sum_{\ell} \left(r_{n\ell}^b B_{\ell m}^c(\mathbf{k}, \omega) - B_{n\ell}^c(\mathbf{k}, \omega) r_{\ell m}^b \right) \right] E^b(\omega) E^c(\omega)
\end{aligned} \tag{58}$$

where $B_{\ell m}^a(\mathbf{k}, \omega)$ are given by Eq. (53). We remark that $\mathbf{r}_{nm}(\mathbf{k})$ are the same whether calculated with the LDA or the scissored Hamiltonian. We chose the former in this article.

V. LAYERED CURRENT DENSITY

In this section, we derive the expressions for the microscopic current density of a given layer in the unit cell of the system. The approach we use to study the surface of a semi-infinite semiconductor crystal is as follows. Instead of using a semi-infinite system, we replace it by a slab (see Fig. 2). The slab consists of a front and back surface, and in between these two surfaces is the bulk of the system. In general the surface of a crystal reconstructs or relaxes as the atoms move to find equilibrium positions. This is due to the fact that the otherwise balanced forces are disrupted when the surface atoms do not find their partner atoms that are now absent at the surface of the slab.

To take the reconstruction or relaxation into account, we take “surface” to mean the true surface of the first layer of atoms, and some of the atomic sub-layers adjacent to it. Since the front and the back surfaces of the slab are usually identical the total slab is centrosymmetric. This implies that $\chi_{\text{abc}}^{\text{slab}} = 0$, and thus we must find a way to bypass this characteristic of a centrosymmetric slab in order to have a finite χ_{abc}^s representative of the surface. Even if the front and back surfaces of the slab are different, breaking the centrosymmetry and therefore giving an overall $\chi_{\text{abc}}^{\text{slab}} \neq 0$, we still need a procedure to extract the front surface χ_{abc}^f and the back surface χ_{abc}^b from the non-linear susceptibility $\chi_{\text{abc}}^{\text{slab}} = \chi_{\text{abc}}^f - \chi_{\text{abc}}^b$ of the entire slab.

A convenient way to accomplish the separation of the SH signal of either surface is to introduce a “cut function”, $\mathcal{C}(z)$, which is usually taken to be unity over one half of the slab and zero over the other half.²⁴ In this case $\mathcal{C}(z)$ will give the contribution of the side of the slab for which $\mathcal{C}(z) = 1$. We can generalize this simple choice for $\mathcal{C}(z)$ by a top-hat cut function $\mathcal{C}^\ell(z)$ that selects a given layer,

$$\mathcal{C}^\ell(z) = \Theta(z - z_\ell + \Delta_\ell^b)\Theta(z_\ell - z + \Delta_\ell^f), \quad (59)$$

where Θ is the Heaviside function. Here, $\Delta_\ell^{f/b}$ is the distance that the ℓ -th layer extends towards the front (f) or back (b) from its z_ℓ position. $\Delta_\ell^f + \Delta_\ell^b$ is the thickness of layer ℓ (see Fig. 2).

Now, we show how this “cut function” $\mathcal{C}^\ell(z)$ is introduced in the calculation of χ_{abc} . The microscopic current density is given by

$$\mathbf{j}(\mathbf{r}, t) = \text{Tr}(\hat{\mathbf{j}}(\mathbf{r})\hat{\rho}(t)), \quad (60)$$

where the operator for the electron's current is

$$\hat{\mathbf{j}}(\mathbf{r}) = \frac{e}{2} (\hat{\mathbf{v}}^\sigma |\mathbf{r}\rangle \langle \mathbf{r}| + |\mathbf{r}\rangle \langle \mathbf{r}| \hat{\mathbf{v}}^\sigma), \quad (61)$$

where $\hat{\mathbf{v}}^\sigma$ is the electron's velocity operator to be dealt with below. We define $\hat{\mu} \equiv |\mathbf{r}\rangle \langle \mathbf{r}|$ and use the cyclic invariance of the trace to write

$$\begin{aligned} \text{Tr}(\hat{\mathbf{j}}(\mathbf{r})\hat{\rho}(t)) &= \text{Tr}(\hat{\rho}(t)\hat{\mathbf{j}}(\mathbf{r})) = \frac{e}{2} (\text{Tr}(\hat{\rho}\hat{\mathbf{v}}^\sigma\hat{\mu}) + \text{Tr}(\hat{\rho}\hat{\mu}\hat{\mathbf{v}}^\sigma)) \\ &= \frac{e}{2} \sum_{n\mathbf{k}} (\langle n\mathbf{k}|\hat{\rho}\hat{\mathbf{v}}^\sigma\hat{\mu}|n\mathbf{k}\rangle + \langle n\mathbf{k}|\hat{\rho}\hat{\mu}\hat{\mathbf{v}}^\sigma|n\mathbf{k}\rangle) \\ &= \frac{e}{2} \sum_{nm\mathbf{k}} \langle n\mathbf{k}|\hat{\rho}|m\mathbf{k}\rangle (\langle m\mathbf{k}|\hat{\mathbf{v}}^\sigma|\mathbf{r}\rangle \langle \mathbf{r}|n\mathbf{k}\rangle + \langle m\mathbf{k}|\mathbf{r}\rangle \langle \mathbf{r}|\hat{\mathbf{v}}^\sigma|n\mathbf{k}\rangle) \\ \mathbf{j}(\mathbf{r}, t) &= \sum_{nm\mathbf{k}} \rho_{nm}(\mathbf{k}; t) \mathbf{j}_{mn}(\mathbf{k}; \mathbf{r}), \end{aligned} \quad (62)$$

where

$$\mathbf{j}_{mn}(\mathbf{k}; \mathbf{r}) = \frac{e}{2} (\langle m\mathbf{k}|\hat{\mathbf{v}}^\sigma|\mathbf{r}\rangle \langle \mathbf{r}|n\mathbf{k}\rangle + \langle m\mathbf{k}|\mathbf{r}\rangle \langle \mathbf{r}|\hat{\mathbf{v}}^\sigma|n\mathbf{k}\rangle), \quad (63)$$

are the matrix elements of the microscopic current operator, and we have used the fact that the matrix elements between states $|n\mathbf{k}\rangle$ are diagonal in \mathbf{k} , i.e. proportional to $\delta(\mathbf{k} - \mathbf{k}')$.

Integrating the microscopic current $\mathbf{j}(\mathbf{r}, t)$ over the entire slab gives the averaged microscopic current density. If we want the contribution from only one region of the unit cell towards the total current, we can integrate $\mathbf{j}(\mathbf{r}, t)$ over the desired region. The contribution to the current density from the ℓ -th layer of the slab is given by

$$\frac{1}{\Omega} \int d^3r \mathcal{C}^\ell(z) \mathbf{j}(\mathbf{r}, t) \equiv \mathbf{J}^\ell(t), \quad (64)$$

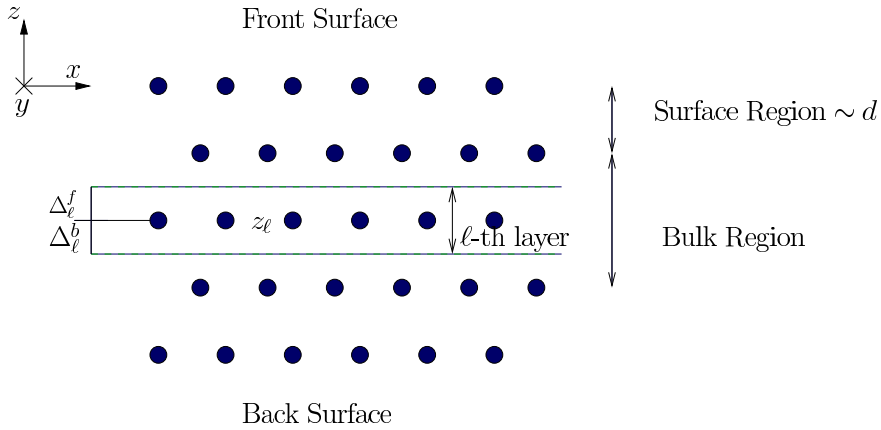


FIG. 2: A sketch of a slab where the circles represent atoms.

where $\mathbf{J}^\ell(t)$ is the microscopic current in the ℓ -th layer. Therefore we define

$$e\mathbf{v}_{mn}^{\sigma,\ell}(\mathbf{k}) \equiv \int d^3r \mathcal{C}^\ell(z) \mathbf{j}_{mn}(\mathbf{k}; \mathbf{r}), \quad (65)$$

to write

$$J_a^{(N,\ell)}(t) = \frac{e}{\Omega} \sum_{mn\mathbf{k}} \mathcal{V}_{mn}^{\sigma,a,\ell}(\mathbf{k}) \rho_{nm}^{(N)}(\mathbf{k}; t), \quad (66)$$

as the induced microscopic current of the ℓ -th layer, to order N in the external perturbation. The matrix elements of the density operator for $N = 1, 2$ are given by Eqs. (53) and (58) respectively. The Fourier component of microscopic current of Eq. (66) is given by

$$J_a^{(N,\ell)}(\omega_3) = \frac{e}{\Omega} \sum_{mn\mathbf{k}} \mathcal{V}_{mn}^{\sigma,a,\ell}(\mathbf{k}) \rho_{nm}^{(N)}(\mathbf{k}; \omega_3). \quad (67)$$

We proceed to give an explicit expression of $\mathcal{V}_{mn}^{\sigma,\ell}(\mathbf{k})$. From Eqs. (65) and (63) we obtain

$$\mathcal{V}_{mn}^{\sigma,\ell}(\mathbf{k}) = \frac{1}{2} \int d^3r \mathcal{C}^\ell(z) \left[\langle m\mathbf{k} | \mathbf{v}^\sigma | \mathbf{r} \rangle \langle \mathbf{r} | n\mathbf{k} \rangle + \langle m\mathbf{k} | \mathbf{r} \rangle \langle \mathbf{r} | \mathbf{v}^\sigma | n\mathbf{k} \rangle \right], \quad (68)$$

and using the following property

$$\langle \mathbf{r} | \hat{\mathbf{v}}^\sigma(\mathbf{r}, \mathbf{r}') | n\mathbf{k} \rangle = \int d^3r'' \langle \mathbf{r} | \hat{\mathbf{v}}^\sigma(\mathbf{r}, \mathbf{r}') | \mathbf{r}'' \rangle \langle \mathbf{r}'' | n\mathbf{k} \rangle = \hat{\mathbf{v}}^\sigma(\mathbf{r}, \mathbf{r}'') \int d^3r'' \langle \mathbf{r} | \mathbf{r}'' \rangle \langle \mathbf{r}'' | n\mathbf{k} \rangle = \hat{\mathbf{v}}^\sigma(\mathbf{r}, \mathbf{r}') \psi_{n\mathbf{k}}(\mathbf{r}), \quad (69)$$

that stems from the fact that the operator $\mathbf{v}^\sigma(\mathbf{r}, \mathbf{r}')$ does not act on \mathbf{r}'' , we can write

$$\begin{aligned} \mathcal{V}_{mn}^{\sigma,\ell}(\mathbf{k}) &= \frac{1}{2} \int d^3r \mathcal{C}^\ell(z) \left[\psi_{n\mathbf{k}}(\mathbf{r}) \hat{\mathbf{v}}^{\sigma*} \psi_{m\mathbf{k}}^*(\mathbf{r}) + \psi_{m\mathbf{k}}^*(\mathbf{r}) \hat{\mathbf{v}}^\sigma \psi_{n\mathbf{k}}(\mathbf{r}) \right] \\ &= \int d^3r \psi_{m\mathbf{k}}^*(\mathbf{r}) \left[\frac{\mathcal{C}^\ell(z) \mathbf{v}^\sigma + \mathbf{v}^\sigma \mathcal{C}^\ell(z)}{2} \right] \psi_{n\mathbf{k}}(\mathbf{r}) \\ &= \int d^3r \psi_{m\mathbf{k}}^*(\mathbf{r}) \mathcal{V}^{\sigma,\ell} \psi_{n\mathbf{k}}(\mathbf{r}). \end{aligned} \quad (70)$$

We used the hermitian property of \mathbf{v}^σ and defined

$$\mathcal{V}^{\sigma,\ell} = \frac{\mathcal{C}^\ell(z) \mathbf{v}^\sigma + \mathbf{v}^\sigma \mathcal{C}^\ell(z)}{2}, \quad (71)$$

where the superscript ℓ is inherited from $\mathcal{C}^\ell(z)$ and we suppress the dependance on z from the increasingly crowded notation. We see that the replacement

$$\hat{\mathbf{v}}^\sigma \rightarrow \hat{\mathcal{V}}^{\sigma,\ell} = \left[\frac{\mathcal{C}^\ell(z) \hat{\mathbf{v}}^\sigma + \hat{\mathbf{v}}^\sigma \mathcal{C}^\ell(z)}{2} \right], \quad (72)$$

is all that is needed to change the velocity operator of the electron $\hat{\mathbf{v}}^\sigma$ to the new velocity operator $\mathcal{V}^{\sigma,\ell}$ that implicitly takes into account the contribution of the region of the slab given by $\mathcal{C}^\ell(z)$.

From Eq. (25),

$$\begin{aligned}\mathbf{v}^{\sigma,\ell} &= \mathbf{v}^{\text{LDA},\ell} + \mathbf{v}^{\mathcal{S},\ell} \\ \mathbf{v}^{\text{LDA},\ell} &= \mathbf{v}^\ell + \mathbf{v}^{\text{nl},\ell} = \frac{1}{m_e} \mathcal{P}^\ell + \mathbf{v}^{\text{nl},\ell}.\end{aligned}\quad (73)$$

We remark that the simple relationship between $\mathbf{v}_{nm}^\sigma(\mathbf{k})$ and $\mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k})$, given in Eq. (29), does not hold between $\mathbf{v}_{nm}^{\sigma,\ell}(\mathbf{k})$ and $\mathbf{v}_{nm}^{\text{LDA},\ell}(\mathbf{k})$, i.e. $\mathbf{v}_{nm}^{\sigma,\ell}(\mathbf{k}) \neq (\omega_{nm}^\sigma/\omega_{nm})\mathbf{v}_{nm}^{\text{LDA},\ell}(\mathbf{k})$ and $\mathbf{v}_{nn}^{\sigma,\ell}(\mathbf{k}) \neq \mathbf{v}_{nn}^{\text{LDA},\ell}(\mathbf{k})$, and thus, to calculate $\mathbf{v}_{nm}^{\sigma,\ell}(\mathbf{k})$ we must calculate the matrix elements of $\mathbf{v}^{\mathcal{S},\ell}$ and $\mathbf{v}^{\text{LDA},\ell}$ (separately) according to the expressions of Appendix C.

To limit the response to one surface, the equivalent of Eq. (71) for $\mathbf{v}^\ell = \mathcal{P}^\ell/m_e$ was proposed in Ref. 24 and later used in Refs. 7, 3, 25, and 26 also in the context of SHG. The layer-by-layer analysis of Refs. 27 and 28 used Eq. (59), limiting the current response to a particular layer of the slab and used to obtain the anisotropic linear optical response of semiconductor surfaces. However, the first formal derivation of this scheme is presented in Ref. 29 for the linear response, and here in this article, for the second harmonic optical response of semiconductors.

VI. MICROSCOPIC SURFACE SUSCEPTIBILITY

In this section we obtain the expressions for the surface susceptibility tensor $\chi_{\text{abc}}^{\mathcal{S}}$. We start with the basic relation $\mathbf{J} = d\mathbf{P}/dt$ with \mathbf{J} the current calculated in Sec. V. From Eq. (67) we obtain

$$J_{\text{a}}^{(2,\ell)}(2\omega) = -i2\tilde{\omega}P_{\text{a}}(2\omega) = \frac{e}{\Omega} \sum_{mn\mathbf{k}} \mathcal{V}_{mn}^{\sigma,\text{a},\ell}(\mathbf{k}) \rho_{nm}^{(2)}(\mathbf{k}; 2\omega), \quad (74)$$

and using Eqs. (58) and (7) leads to

$$\begin{aligned}\chi_{\text{abc}}^{S,\ell} &= \frac{ie}{AE_1^{\text{b}}E_2^{\text{c}}2\tilde{\omega}} \sum_{mn\mathbf{k}} \mathcal{V}_{mn}^{\sigma,\text{a},\ell}(\mathbf{k}) \rho_{nm}^{(2)}(\mathbf{k}; 2\tilde{\omega}) \\ &= \frac{e^2}{A\hbar 2\tilde{\omega}} \sum_{mn\mathbf{k}} \frac{\mathcal{V}_{mn}^{\sigma,\text{a},\ell}(\mathbf{k})}{\omega_{nm}^\sigma - 2\tilde{\omega}} \left[- (B_{nm}^{\text{c}}(\mathbf{k}, \omega))_{;k^{\text{b}}} \right. \\ &\quad \left. + i \sum_{\ell} \left(r_{n\ell}^{\text{b}} B_{\ell m}^{\text{c}}(\mathbf{k}, \omega) - B_{n\ell}^{\text{c}}(\mathbf{k}, \omega) r_{\ell m}^{\text{b}} \right) \right],\end{aligned}\quad (75)$$

which gives the surface-like susceptibility of ℓ -th layer, where \mathbf{v}^σ is given in Eq. (73), where $A = \Omega/d$ is the surface area of the unit cell that characterizes the surface of the system. Using Eq. (53) we split this equation into two contributions from the first and second terms on the right hand side,

$$\chi_{i,\text{abc}}^{S,\ell} = -\frac{e^3}{A\hbar^2 2\tilde{\omega}} \sum_{mn\mathbf{k}} \frac{\mathcal{V}_{mn}^{\sigma,\text{a},\ell}}{\omega_{nm}^\sigma - 2\tilde{\omega}} \left(\frac{f_{mn} r_{nm}^{\text{b}}}{\omega_{nm}^\sigma - \tilde{\omega}} \right)_{;k^{\text{c}}}, \quad (76)$$

and

$$\chi_{e,abc}^{S,\ell} = \frac{ie^3}{A\hbar^2 2\tilde{\omega}} \sum_{\ell mn\mathbf{k}} \frac{\mathcal{V}_{mn}^{\sigma,a,\ell}}{\omega_{nm}^\sigma - 2\tilde{\omega}} \left(\frac{r_{n\ell}^c r_{\ell m}^b f_{m\ell}}{\omega_{\ell m}^\sigma - \tilde{\omega}} - \frac{r_{n\ell}^b r_{\ell m}^c f_{\ell n}}{\omega_{n\ell}^\sigma - \tilde{\omega}} \right), \quad (77)$$

where $\chi_i^{S,\ell}$ is related to intraband transitions and $\chi_e^{S,\ell}$ to interband transitions. For the generalized derivative in Eq. (76) we use the chain rule

$$\left(\frac{f_{mn} r_{nm}^b}{\omega_{nm}^\sigma - \tilde{\omega}} \right)_{;k^c} = \frac{f_{mn}}{\omega_{nm}^\sigma - \tilde{\omega}} (r_{nm}^b)_{;k^c} - \frac{f_{mn} r_{nm}^b \Delta_{nm}^c}{(\omega_{nm}^\sigma - \tilde{\omega})^2}, \quad (78)$$

and the following result shown in Appendix D,

$$(\omega_{nm}^\sigma)_{;k^a} = (\omega_{nm}^{\text{LDA}})_{;k^a} = v_{nn}^{\text{LDA},a} - v_{mm}^{\text{LDA},a} \equiv \Delta_{nm}^a. \quad (79)$$

In order to calculate the nonlinear susceptibility of any given layer ℓ we simply add the above terms $\chi^{S,\ell} = \chi_e^{S,\ell} + \chi_i^{S,\ell}$ and then calculate the surface susceptibility as

$$\chi^S \equiv \sum_{\ell=1}^N \chi^{S,\ell}, \quad (80)$$

where $\ell = 1$ is the first layer right at the surface, and $\ell = N$ is the bulk-like layer (at a distance $\sim d$ from the surface as seen in Fig. 1), such that

$$\chi^{S,\ell=N} = 0, \quad (81)$$

in accordance to Eq. (5) valid for a centrosymmetric environment. We note that the value of N is not universal. This means that the slab needs to have enough atomic layers for Eq. (81) to be satisfied and to give converged results for χ^S . We can use Eq. (80) for either the front or the back surface.

We can see from the prefactors of Eqs. (76) and (77) that they diverge as $\tilde{\omega} \rightarrow 0$. To remove this apparent divergence of $\chi^{S,\ell}$, we perform a partial fraction expansion over $\tilde{\omega}$. As shown in Appendix E, we use time-reversal invariance to remove these divergences and obtain the following expressions for χ^S ,

$$\text{Im}[\chi_{e,abc,\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{c}\mathbf{k}} \sum_{l \neq (v,c)} \frac{1}{\omega_{cv}^\sigma} \left[\frac{\text{Im}[\mathcal{V}_{lc}^{\sigma,a,\ell} \{r_{cv}^b r_{vl}^c\}]}{(2\omega_{cv}^\sigma - \omega_{cl}^\sigma)} - \frac{\text{Im}[\mathcal{V}_{vl}^{\sigma,a,\ell} \{r_{lc}^c r_{cv}^b\}]}{(2\omega_{cv}^\sigma - \omega_{lv}^\sigma)} \right] \delta(\omega_{cv}^\sigma - \omega), \quad (82)$$

$$\text{Im}[\chi_{i,abc,\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{c\mathbf{v}\mathbf{k}} \frac{1}{(\omega_{cv}^\sigma)^2} \left[\text{Re} \left[\left\{ r_{cv}^b (\mathcal{V}_{vc}^{\sigma,a,\ell})_{;k^c} \right\} \right] + \frac{\text{Re} [\mathcal{V}_{vc}^{\sigma,a,\ell} \{r_{cv}^b \Delta_{cv}^c\}]}{\omega_{cv}^\sigma} \right] \delta(\omega_{cv}^\sigma - \omega), \quad (83)$$

$$\text{Im}[\chi_{e,\text{abc},2\omega}^{s,\ell}] = -\frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{k}} \frac{4}{\omega_{cv}^\sigma} \left[\sum_{v' \neq v} \frac{\text{Im}[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \{r_{cv'}^b r_{v'v}^c\}]}{2\omega_{cv'}^\sigma - \omega_{cv}^\sigma} - \sum_{c' \neq c} \frac{\text{Im}[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \{r_{cc'}^c r_{c'v}^b\}]}{2\omega_{c'v}^\sigma - \omega_{cv}^\sigma} \right] \delta(\omega_{cv}^\sigma - 2\omega), \quad (84)$$

and

$$\text{Im}[\chi_{i,\text{abc},2\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{k}} \frac{4}{(\omega_{cv}^\sigma)^2} \left[\text{Re} \left[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \left\{ \left(r_{cv}^b \right)_{;k^c} \right\} \right] - \frac{2\text{Re} \left[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \{ r_{cv}^b \Delta_{cv}^c \} \right]}{\omega_{cv}^\sigma} \right] \delta(\omega_{cv}^\sigma - 2\omega), \quad (85)$$

where the limit of $\eta \rightarrow 0$ has been taken. We have split the interband and intraband 1ω and 2ω contributions. The real part of each contribution can be obtained through a Kramers-Kronig transformation,³⁰ and then $\chi_{\text{abc}}^{S,\ell} = \chi_{e,\text{abc},\omega}^{S,\ell} + \chi_{e,\text{abc},2\omega}^{S,\ell} + \chi_{i,\text{abc},\omega}^{S,\ell} + \chi_{i,\text{abc},2\omega}^{S,\ell}$. To fulfill the required intrinsic permutation symmetry,³¹ the $\{\}$ notation symmetrizes the bc Cartesian indices, i.e. $\{u^b s^c\} = (u^b s^c + u^c s^b)/2$, and thus $\chi_{\text{abc}}^{S,\ell} = \chi_{\text{acb}}^{S,\ell}$. In Appendices H and C we demonstrate how to calculate the generalized derivatives of $\mathbf{r}_{nm;\mathbf{k}}$ and $\mathcal{V}_{nm;\mathbf{k}}^{\sigma,\text{a},\ell}$. We find that

$$(r_{nm}^b)_{;k^a} = -i\mathcal{T}_{nm}^{\text{ab}} + \frac{r_{nm}^a \Delta_{mn}^b + r_{nm}^b \Delta_{mn}^a}{\omega_{nm}^{\text{LDA}}} + \frac{i}{\omega_{nm}^{\text{LDA}}} \sum_{\ell} \left(\omega_{\ell m}^{\text{LDA}} r_{n\ell}^a r_{\ell m}^b - \omega_{n\ell}^{\text{LDA}} r_{n\ell}^b r_{\ell m}^a \right), \quad (86)$$

where

$$\mathcal{T}_{nm}^{\text{ab}} = [r^a, v^{\text{LDA},b}] = \frac{i\hbar}{m_e} \delta_{ab} \delta_{nm} + \mathcal{L}_{nm}^{\text{ab}}, \quad (87)$$

and

$$\mathcal{L}_{nm}^{\text{ab}} = \frac{1}{i\hbar} [r^a, v^{\text{nl},b}]_{nm}, \quad (88)$$

is the contribution to the generalized derivative of \mathbf{r}_{nm} coming from the nonlocal part of the pseudopotential. In Appendix F we calculate $\mathcal{L}_{nm}^{\text{ab}}$, that is a term with very small numerical value but with a computational time at least an order of magnitude larger than for all the other terms involved in the expressions for $\chi_{\text{abc}}^{s,\ell}$.³² Therefore, we neglect it throughout this article and take

$$\mathcal{T}_{nm}^{\text{ab}} \approx \frac{i\hbar}{m_e} \delta_{ab} \delta_{nm}. \quad (89)$$

Finally, we also need the following term (Eq. (H10))

$$\begin{aligned} (v_{nn}^{\text{LDA},a})_{;k^b} &= \nabla_{k^a} v_{nn}^{\text{LDA},b}(\mathbf{k}) = -i\mathcal{T}_{nn}^{\text{ab}} - \sum_{\ell \neq n} \omega_{\ell n}^{\text{LDA}} \left(r_{n\ell}^a r_{\ell n}^b + r_{n\ell}^b r_{\ell n}^a \right) \\ &\approx \frac{\hbar}{m_e} \delta_{ab} - \sum_{\ell \neq n} \omega_{\ell n}^{\text{LDA}} \left(r_{n\ell}^a r_{\ell n}^b + r_{n\ell}^b r_{\ell n}^a \right), \end{aligned} \quad (90)$$

among other quantities for $\mathcal{V}_{nm;\mathbf{k}}^{\sigma,\text{a},\ell}$, where we also use Eq. (89). Above is the standard effective-mass sum rule.³³

VII. CONCLUSIONS

We have presented a complete derivation of the required elements to calculate in the independent particle approach (IPA) the microscopic surface second harmonic susceptibility tensor $\chi^S(-2\omega; \omega, \omega)$ using a layer-by-layer approach. We have done so for semiconductors using the length gauge for the coupling of the external electric field to the electron.

Appendix A: \mathbf{r}_e and \mathbf{r}_i

In this Appendix, we derive the expressions for the matrix elements of the electron position operator \mathbf{r} . The r representation of the Bloch states is given by

$$\psi_{n\mathbf{k}}(\mathbf{r}) = \langle \mathbf{r} | n\mathbf{k} \rangle = \sqrt{\frac{\Omega}{8\pi^3}} e^{i\mathbf{k} \cdot \mathbf{r}} u_{n\mathbf{k}}(\mathbf{r}), \quad (\text{A1})$$

where $u_{n\mathbf{k}}(\mathbf{r}) = u_{n\mathbf{k}}(\mathbf{r} + \mathbf{R})$ is cell periodic, and

$$\int_{\Omega} d^3r u_{n\mathbf{k}}^*(\mathbf{r}) u_{m\mathbf{k}'}(\mathbf{r}) = \delta_{nm} \delta_{\mathbf{k}, \mathbf{k}'}, \quad (\text{A2})$$

with Ω the volume of the unit cell.

The key ingredient in the calculation are the matrix elements of the position operator \mathbf{r} , so we start from the basic relation

$$\langle n\mathbf{k} | m\mathbf{k}' \rangle = \delta_{nm} \delta(\mathbf{k} - \mathbf{k}'), \quad (\text{A3})$$

and take its derivative with respect to \mathbf{k} as follows. On one hand,

$$\frac{\partial}{\partial \mathbf{k}} \langle n\mathbf{k} | m\mathbf{k}' \rangle = \delta_{nm} \frac{\partial}{\partial \mathbf{k}} \delta(\mathbf{k} - \mathbf{k}'), \quad (\text{A4})$$

on the other,

$$\begin{aligned} \frac{\partial}{\partial \mathbf{k}} \langle n\mathbf{k} | m\mathbf{k}' \rangle &= \frac{\partial}{\partial \mathbf{k}} \int d\mathbf{r} \langle n\mathbf{k} | \mathbf{r} \rangle \langle \mathbf{r} | m\mathbf{k}' \rangle \\ &= \int d\mathbf{r} \left(\frac{\partial}{\partial \mathbf{k}} \psi_{n\mathbf{k}}^*(\mathbf{r}) \right) \psi_{m\mathbf{k}'}(\mathbf{r}), \end{aligned} \quad (\text{A5})$$

the derivative of the wavefunction is simply given by

$$\frac{\partial}{\partial \mathbf{k}} \psi_{n\mathbf{k}}^*(\mathbf{r}) = \sqrt{\frac{\Omega}{8\pi^3}} \left(\frac{\partial}{\partial \mathbf{k}} u_{n\mathbf{k}}^*(\mathbf{r}) \right) e^{-i\mathbf{k} \cdot \mathbf{r}} - i\mathbf{r} \psi_{n\mathbf{k}}^*(\mathbf{r}). \quad (\text{A6})$$

We take this back into Eq. (A5), to obtain

$$\begin{aligned}
\frac{\partial}{\partial \mathbf{k}} \langle n\mathbf{k} | m\mathbf{k}' \rangle &= \sqrt{\frac{\Omega}{8\pi^3}} \int d\mathbf{r} \left(\frac{\partial}{\partial \mathbf{k}} u_{n\mathbf{k}}^*(\mathbf{r}) \right) e^{-i\mathbf{k} \cdot \mathbf{r}} \psi_{m\mathbf{k}'}(\mathbf{r}) \\
&\quad - i \int d\mathbf{r} \psi_{n\mathbf{k}}^*(\mathbf{r}) \mathbf{r} \psi_{m\mathbf{k}'}(\mathbf{r}) \\
&= \frac{\Omega}{8\pi^3} \int d\mathbf{r} e^{-i(\mathbf{k}-\mathbf{k}') \cdot \mathbf{r}} \left(\frac{\partial}{\partial \mathbf{k}} u_{n\mathbf{k}}^*(\mathbf{r}) \right) u_{m\mathbf{k}'}(\mathbf{r}) \\
&\quad - i \langle n\mathbf{k} | \hat{\mathbf{r}} | m\mathbf{k}' \rangle.
\end{aligned} \tag{A7}$$

Restricting \mathbf{k} and \mathbf{k}' to the first Brillouin zone, we use the following result valid for any periodic function $f(\mathbf{r}) = f(\mathbf{r} + \mathbf{R})$,

$$\int d^3r e^{i(\mathbf{q}-\mathbf{k}) \cdot \mathbf{r}} f(\mathbf{r}) = \frac{8\pi^3}{\Omega} \delta(\mathbf{q} - \mathbf{k}) \int_{\Omega} d^3r f(\mathbf{r}), \tag{A8}$$

to finally write,¹⁸

$$\begin{aligned}
\frac{\partial}{\partial \mathbf{k}} \langle n\mathbf{k} | m\mathbf{k}' \rangle &= \delta(\mathbf{k} - \mathbf{k}') \int_{\Omega} d\mathbf{r} \left(\frac{\partial}{\partial \mathbf{k}} u_{n\mathbf{k}}^*(\mathbf{r}) \right) u_{m\mathbf{k}}(\mathbf{r}) \\
&\quad - i \langle n\mathbf{k} | \hat{\mathbf{r}} | m\mathbf{k}' \rangle.
\end{aligned} \tag{A9}$$

where Ω is the volume of the unit cell. From

$$\int_{\Omega} u_{m\mathbf{k}} u_{n\mathbf{k}}^* d\mathbf{r} = \delta_{nm}, \tag{A10}$$

we easily find that

$$\int_{\Omega} d\mathbf{r} \left(\frac{\partial}{\partial \mathbf{k}} u_{m\mathbf{k}}(\mathbf{r}) \right) u_{n\mathbf{k}}^*(\mathbf{r}) = - \int_{\Omega} d\mathbf{r} u_{m\mathbf{k}}(\mathbf{r}) \left(\frac{\partial}{\partial \mathbf{k}} u_{n\mathbf{k}}^*(\mathbf{r}) \right). \tag{A11}$$

Therefore, we define

$$\xi_{nm}(\mathbf{k}) \equiv i \int_{\Omega} d\mathbf{r} u_{n\mathbf{k}}^*(\mathbf{r}) \nabla_{\mathbf{k}} u_{m\mathbf{k}}(\mathbf{r}), \tag{A12}$$

with $\partial/\partial \mathbf{k} = \nabla_{\mathbf{k}}$. Now, from Eqs. (A4), (A7), and (A12), we have that the matrix elements of the position operator of the electron are given by

$$\langle n\mathbf{k} | \hat{\mathbf{r}} | m\mathbf{k}' \rangle = \delta(\mathbf{k} - \mathbf{k}') \xi_{nm}(\mathbf{k}) + i \delta_{nm} \nabla_{\mathbf{k}} \delta(\mathbf{k} - \mathbf{k}'), \tag{A13}$$

Then, from Eq. (A13), and writing $\hat{\mathbf{r}} = \hat{\mathbf{r}}_e + \hat{\mathbf{r}}_i$, with $\hat{\mathbf{r}}_e$ ($\hat{\mathbf{r}}_i$) the interband (intraband) part, we obtain that

$$\langle n\mathbf{k} | \hat{\mathbf{r}}_i | m\mathbf{k}' \rangle = \delta_{nm} [\delta(\mathbf{k} - \mathbf{k}') \xi_{nn}(\mathbf{k}) + i \nabla_{\mathbf{k}} \delta(\mathbf{k} - \mathbf{k}')], \tag{A14}$$

$$\langle n\mathbf{k} | \hat{\mathbf{r}}_e | m\mathbf{k}' \rangle = (1 - \delta_{nm}) \delta(\mathbf{k} - \mathbf{k}') \xi_{nm}(\mathbf{k}). \tag{A15}$$

To proceed, we relate Eq. (A15) to the matrix elements of the momentum operator as follows.

For the intraband part, we derive the following general result,

$$\begin{aligned}
\langle n\mathbf{k} | [\hat{\mathbf{r}}_i, \hat{\mathcal{O}}] | m\mathbf{k}' \rangle &= \sum_{\ell, \mathbf{k}''} \left(\langle n\mathbf{k} | \hat{\mathbf{r}}_i | \ell\mathbf{k}'' \rangle \langle \ell\mathbf{k}'' | \hat{\mathcal{O}} | m\mathbf{k}' \rangle \right. \\
&\quad \left. - \langle n\mathbf{k} | \hat{\mathcal{O}} | \ell\mathbf{k}'' \rangle \langle \ell\mathbf{k}'' | \hat{\mathbf{r}}_i | m\mathbf{k}' \rangle \right) \\
&= \sum_{\ell} \left(\langle n\mathbf{k} | \hat{\mathbf{r}}_i | \ell\mathbf{k}' \rangle \mathcal{O}_{\ell m}(\mathbf{k}') \right. \\
&\quad \left. - \mathcal{O}_{n\ell}(\mathbf{k}) | \ell\mathbf{k} \rangle \langle \ell\mathbf{k} | \hat{\mathbf{r}}_i | m\mathbf{k}' \rangle \right), \tag{A16}
\end{aligned}$$

where we have taken $\langle n\mathbf{k} | \hat{\mathcal{O}} | \ell\mathbf{k}'' \rangle = \delta(\mathbf{k} - \mathbf{k}'') \mathcal{O}_{n\ell}(\mathbf{k})$. We substitute Eq. (A14), to obtain

$$\begin{aligned}
&\sum_{\ell} \left(\delta_{n\ell} [\delta(\mathbf{k} - \mathbf{k}') \boldsymbol{\xi}_{nn}(\mathbf{k}) + i \nabla_{\mathbf{k}} \delta(\mathbf{k} - \mathbf{k}')] \mathcal{O}_{\ell m}(\mathbf{k}') \right. \\
&\quad \left. - \mathcal{O}_{n\ell}(\mathbf{k}) \delta_{\ell m} [\delta(\mathbf{k} - \mathbf{k}') \boldsymbol{\xi}_{mm}(\mathbf{k}) + i \nabla_{\mathbf{k}} \delta(\mathbf{k} - \mathbf{k}')] \right) \\
&= \left([\delta(\mathbf{k} - \mathbf{k}') \boldsymbol{\xi}_{nn}(\mathbf{k}) + i \nabla_{\mathbf{k}} \delta(\mathbf{k} - \mathbf{k}')] \mathcal{O}_{nm}(\mathbf{k}') \right. \\
&\quad \left. - \mathcal{O}_{nm}(\mathbf{k}) [\delta(\mathbf{k} - \mathbf{k}') \boldsymbol{\xi}_{mm}(\mathbf{k}) + i \nabla_{\mathbf{k}} \delta(\mathbf{k} - \mathbf{k}')] \right) \\
&= \delta(\mathbf{k} - \mathbf{k}') \mathcal{O}_{nm}(\mathbf{k}) (\boldsymbol{\xi}_{nn}(\mathbf{k}) - \boldsymbol{\xi}_{mm}(\mathbf{k})) + i \mathcal{O}_{nm}(\mathbf{k}') \nabla_{\mathbf{k}} \delta(\mathbf{k} - \mathbf{k}') \\
&\quad + i \delta(\mathbf{k} - \mathbf{k}') \nabla_{\mathbf{k}} \mathcal{O}_{nm}(\mathbf{k}) - i \mathcal{O}_{nm}(\mathbf{k}') \nabla_{\mathbf{k}} \delta(\mathbf{k} - \mathbf{k}') \\
&= i \delta(\mathbf{k} - \mathbf{k}') \left(\nabla_{\mathbf{k}} \mathcal{O}_{nm}(\mathbf{k}) - i \mathcal{O}_{nm}(\mathbf{k}) (\boldsymbol{\xi}_{nn}(\mathbf{k}) - \boldsymbol{\xi}_{mm}(\mathbf{k})) \right) \\
&\equiv i \delta(\mathbf{k} - \mathbf{k}') (\mathcal{O}_{nm})_{;\mathbf{k}}. \tag{A17}
\end{aligned}$$

Then,

$$\langle n\mathbf{k} | [\hat{\mathbf{r}}_i, \hat{\mathcal{O}}] | m\mathbf{k}' \rangle = i \delta(\mathbf{k} - \mathbf{k}') (\mathcal{O}_{nm})_{;\mathbf{k}}, \tag{A18}$$

with

$$(\mathcal{O}_{nm})_{;\mathbf{k}} = \nabla_{\mathbf{k}} \mathcal{O}_{nm}(\mathbf{k}) - i \mathcal{O}_{nm}(\mathbf{k}) (\boldsymbol{\xi}_{nn}(\mathbf{k}) - \boldsymbol{\xi}_{mm}(\mathbf{k})), \tag{A19}$$

the generalized derivative of \mathcal{O}_{nm} with respect to \mathbf{k} . Note that the highly singular term $\nabla_{\mathbf{k}} \delta(\mathbf{k} - \mathbf{k}')$ cancels in Eq. (A17), thus giving a well defined commutator of the intraband position operator with an arbitrary operator $\hat{\mathcal{O}}$. We use Eq. (31) and (A18) in the next section.

Appendix B: Matrix elements of $\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k})$ and $\mathbf{V}_{nm}^{\text{nl},\ell}(\mathbf{k})$

From Eq. (26), we have that

$$\begin{aligned}\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k}) &= \langle n\mathbf{k}|\hat{\mathbf{v}}^{\text{nl}}|m\mathbf{k}'\rangle = \frac{i}{\hbar}\langle n\mathbf{k}|[\hat{V}^{\text{nl}}, \hat{\mathbf{r}}]|m\mathbf{k}'\rangle \\ &= \frac{i}{\hbar}\int d\mathbf{r}d\mathbf{r}'\langle n\mathbf{k}|\mathbf{r}\rangle\langle\mathbf{r}|[\hat{V}^{\text{nl}}, \hat{\mathbf{r}}]|\mathbf{r}'\rangle\langle\mathbf{r}'|m\mathbf{k}'\rangle \\ &= \frac{i}{\hbar}\delta(\mathbf{k}-\mathbf{k}')\int d\mathbf{r}d\mathbf{r}'\psi_{n\mathbf{k}}^*(\mathbf{r})\langle\mathbf{r}|[\hat{V}^{\text{nl}}, \hat{\mathbf{r}}]|\mathbf{r}'\rangle\psi_{m\mathbf{k}'}(\mathbf{r}'),\end{aligned}\quad (\text{B1})$$

where due to the fact that the integrand is periodic in real space, $\mathbf{k} = \mathbf{k}'$ where \mathbf{k} is restricted to the Brillouin Zone. Now,

$$\begin{aligned}\langle\mathbf{r}|[\hat{V}^{\text{nl}}, \hat{\mathbf{r}}]|\mathbf{r}'\rangle &= \langle\mathbf{r}|\hat{V}^{\text{nl}}\hat{\mathbf{r}} - \hat{\mathbf{r}}\hat{V}^{\text{nl}}|\mathbf{r}'\rangle = \langle\mathbf{r}|\hat{V}^{\text{nl}}\hat{\mathbf{r}}|\mathbf{r}'\rangle - \langle\mathbf{r}|\hat{\mathbf{r}}\hat{V}^{\text{nl}}|\mathbf{r}'\rangle \\ &= \langle\mathbf{r}|\hat{V}^{\text{nl}}\mathbf{r}'|\mathbf{r}'\rangle - \langle\mathbf{r}|\mathbf{r}\hat{V}^{\text{nl}}|\mathbf{r}'\rangle = \langle\mathbf{r}|\hat{V}^{\text{nl}}|\mathbf{r}'\rangle(\mathbf{r}' - \mathbf{r}) = V^{\text{nl}}(\mathbf{r}, \mathbf{r}')(\mathbf{r}' - \mathbf{r}),\end{aligned}\quad (\text{B2})$$

where we use $\hat{\mathbf{r}}|\mathbf{r}\rangle = r|\mathbf{r}\rangle$, $\langle\mathbf{r}'|\hat{\mathbf{r}} = \langle\mathbf{r}|r'$, and $V^{\text{nl}}(\mathbf{r}, \mathbf{r}') = \langle\mathbf{r}|\hat{V}^{\text{nl}}|\mathbf{r}'\rangle$ (Eq. (12)). Also, we have the following identity which will be used shortly,

$$\begin{aligned}(\nabla_{\mathbf{K}} + \nabla_{\mathbf{K}'})\frac{1}{\Omega}\int e^{-i\mathbf{K}\cdot\mathbf{r}}V^{\text{nl}}(\mathbf{r}, \mathbf{r}')e^{i\mathbf{K}'\cdot\mathbf{r}'}d\mathbf{r}d\mathbf{r}' &= -i\frac{1}{\Omega}\int e^{-i\mathbf{K}\cdot\mathbf{r}}\left(\mathbf{r}V^{\text{nl}}(\mathbf{r}, \mathbf{r}') - V^{\text{nl}}(\mathbf{r}, \mathbf{r}')\mathbf{r}'\right)e^{i\mathbf{K}'\cdot\mathbf{r}'}d\mathbf{r}d\mathbf{r}' \\ (\nabla_{\mathbf{K}} + \nabla_{\mathbf{K}'})\langle\mathbf{K}|V^{\text{nl}}|\mathbf{K}'\rangle &= \frac{i}{\Omega}\int e^{-i\mathbf{K}\cdot\mathbf{r}}V^{\text{nl}}(\mathbf{r}, \mathbf{r}')(\mathbf{r}' - \mathbf{r})e^{i\mathbf{K}'\cdot\mathbf{r}'}d\mathbf{r}d\mathbf{r}',\end{aligned}\quad (\text{B3})$$

where Ω is the volume of the unit cell, and we defined

$$V^{\text{nl}}(\mathbf{K}, \mathbf{K}') \equiv \langle\mathbf{K}|V^{\text{nl}}|\mathbf{K}'\rangle = \frac{1}{\Omega}\int e^{-i\mathbf{K}\cdot\mathbf{r}}V^{\text{nl}}(\mathbf{r}, \mathbf{r}')e^{i\mathbf{K}'\cdot\mathbf{r}'}d\mathbf{r}d\mathbf{r}',\quad (\text{B4})$$

where $V^{\text{nl}}(\mathbf{K}', \mathbf{K}) = V^{\text{nl}*}(\mathbf{K}, \mathbf{K}')$, since $V^{\text{nl}}(\mathbf{r}', \mathbf{r}) = V^{\text{nl}*}(\mathbf{r}, \mathbf{r}')$ due to the fact that \hat{V}^{nl} is a hermitian operator. Using the plane wave expansion

$$\langle\mathbf{r}|n\mathbf{k}\rangle = \psi_{n\mathbf{k}}(\mathbf{r}) = \frac{1}{\sqrt{\Omega}}\sum_{\mathbf{G}}A_{n\mathbf{k}}(\mathbf{G})e^{i\mathbf{K}\cdot\mathbf{r}},\quad (\text{B5})$$

with $\mathbf{K} = \mathbf{k} + \mathbf{G}$, we obtain from Eq. (B1) and Eq. (B3), that

$$\begin{aligned}\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k}) &= \frac{i}{\hbar}\delta(\mathbf{k}-\mathbf{k}')\sum_{\mathbf{G}, \mathbf{G}'}A_{n\mathbf{k}}^*(\mathbf{G})A_{m\mathbf{k}'}(\mathbf{G}')\frac{1}{\Omega}\int d\mathbf{r}d\mathbf{r}'e^{-i\mathbf{K}\cdot\mathbf{r}}\langle\mathbf{r}|[\hat{V}^{\text{nl}}, \hat{\mathbf{r}}]|\mathbf{r}'\rangle e^{i\mathbf{K}'\cdot\mathbf{r}'} \\ &= \frac{i}{\hbar}\delta(\mathbf{k}-\mathbf{k}')\sum_{\mathbf{G}, \mathbf{G}'}A_{n\mathbf{k}}^*(\mathbf{G})A_{m\mathbf{k}'}(\mathbf{G}')\frac{i}{\Omega}\int d\mathbf{r}d\mathbf{r}'e^{-i\mathbf{K}\cdot\mathbf{r}}V^{\text{nl}}(\mathbf{r}, \mathbf{r}')(\mathbf{r}' - \mathbf{r})e^{i\mathbf{K}'\cdot\mathbf{r}'} \\ &= \frac{1}{\hbar}\delta(\mathbf{k}-\mathbf{k}')\sum_{\mathbf{G}, \mathbf{G}'}A_{n\mathbf{k}}^*(\mathbf{G})A_{m\mathbf{k}'}(\mathbf{G}')(\nabla_{\mathbf{K}} + \nabla_{\mathbf{K}'}V^{\text{nl}}(\mathbf{K}, \mathbf{K}')).\end{aligned}\quad (\text{B6})$$

For fully separable pseudopotentials in the Kleinman-Bylander (KB) form,^{21–23} the matrix elements $\langle \mathbf{K} | V^{\text{nl}} | \mathbf{K}' \rangle = V^{\text{nl}}(\mathbf{K}, \mathbf{K}')$ can be readily calculated.²¹ Indeed, the Fourier representation assumes the form,^{23,34,35}

$$\begin{aligned} V_{\text{KB}}^{\text{nl}}(\mathbf{K}, \mathbf{K}') &= \sum_s e^{i(\mathbf{K}-\mathbf{K}') \cdot \boldsymbol{\tau}_s} \sum_{l=0}^{l_s} \sum_{m=-l}^l E_l F_{lm}^s(\mathbf{K}) F_{lm}^{s*}(\mathbf{K}') \\ &= \sum_s \sum_{l=0}^{l_s} \sum_{m=-l}^l E_l f_{lm}^s(\mathbf{K}) f_{lm}^{s*}(\mathbf{K}'), \end{aligned} \quad (\text{B7})$$

with $f_{lm}^s(\mathbf{K}) = e^{i\mathbf{K} \cdot \boldsymbol{\tau}_s} F_{lm}^s(\mathbf{K})$, and

$$F_{lm}^s(\mathbf{K}) = \int d\mathbf{r} e^{-i\mathbf{K} \cdot \mathbf{r}} \delta V_l^S(\mathbf{r}) \Phi_{lm}^{\text{ps}}(\mathbf{r}). \quad (\text{B8})$$

Here $\delta V_l^S(\mathbf{r})$ is the non-local contribution of the ionic pseudopotential centered at the atomic position $\boldsymbol{\tau}_s$ located in the unit cell, $\Phi_{lm}^{\text{ps}}(\mathbf{r})$ is the pseudo-wavefunction of the corresponding atom, while E_l is the so called Kleinman-Bylander energy. Further details can be found in Ref. 35. From Eq. (B7) we find

$$\begin{aligned} (\nabla_{\mathbf{K}} + \nabla_{\mathbf{K}'}) V_{\text{KB}}^{\text{nl}}(\mathbf{K}, \mathbf{K}') &= \sum_s \sum_{l=0}^{l_s} \sum_{m=-l}^l E_l (\nabla_{\mathbf{K}} + \nabla_{\mathbf{K}'}) f_{lm}^s(\mathbf{K}) f_{lm}^{s*}(\mathbf{K}') \\ &= \sum_s \sum_{l=0}^{l_s} \sum_{m=-l}^l E_l ([\nabla_{\mathbf{K}} f_{lm}^s(\mathbf{K})] f_{lm}^{s*}(\mathbf{K}') + f_{lm}^s(\mathbf{K}) [\nabla_{\mathbf{K}'} f_{lm}^{s*}(\mathbf{K}')]) , \end{aligned} \quad (\text{B9})$$

and using this in Eq. (B6) leads to

$$\begin{aligned} \mathbf{v}_{nm}^{\text{nl}}(\mathbf{k}) &= \frac{1}{\hbar} \sum_s \sum_{l=0}^{l_s} \sum_{m=-l}^l E_l \sum_{\mathbf{G}, \mathbf{G}'} A_{n,\vec{k}}^*(\mathbf{G}) A_{n',\vec{k}}(\mathbf{G}') \\ &\quad \times (\nabla_{\mathbf{K}} f_{lm}^s(\mathbf{K}) f_{lm}^{s*}(\mathbf{K}') + f_{lm}^s(\mathbf{K}) \nabla_{\mathbf{K}'} f_{lm}^{s*}(\mathbf{K}')) \\ &= \frac{1}{\hbar} \sum_s \sum_{l=0}^{l_s} \sum_{m=-l}^l E_l \left[\left(\sum_{\mathbf{G}} A_{n,\vec{k}}^*(\mathbf{G}) \nabla_{\mathbf{K}} f_{lm}^s(\mathbf{K}) \right) \left(\sum_{\mathbf{G}'} A_{n',\vec{k}}(\mathbf{G}') f_{lm}^{s*}(\mathbf{K}') \right) \right. \\ &\quad \left. + \left(\sum_{\mathbf{G}} A_{n,\vec{k}}^*(\mathbf{G}) f_{lm}^s(\mathbf{K}) \right) \left(\sum_{\mathbf{G}'} A_{n',\vec{k}}(\mathbf{G}') \nabla_{\mathbf{K}'} f_{lm}^{s*}(\mathbf{K}') \right) \right], \end{aligned} \quad (\text{B10})$$

where there are only single sums over \mathbf{G} . Above is implemented in the DPTM code.²⁰

Indeed, in DPTM `calcolacommutatore.F90` above expansion coefficients are called $E_l f_{lm}^s(\mathbf{K}) \rightarrow \text{fnlkslm}$ and $E_l \nabla_{\mathbf{K}} f_{lm}^s(\mathbf{K}) \rightarrow \text{fnldkslm}$, where `fnlkslm` is an array indexed by $\mathbf{k} + \mathbf{G}$, and `fnldkslm` is vector array indexed by $\mathbf{k} + \mathbf{G}$.

Now we derive $\mathbf{v}_{nm}^{\text{nl},\ell}(\mathbf{k})$. First we prove that

$$\sum_{\mathbf{G}} |\mathbf{k} + \mathbf{G}\rangle \langle \mathbf{k} + \mathbf{G}| = 1. \quad (\text{B11})$$

Proof:

$$\langle n\mathbf{k}|1|n'\mathbf{k}\rangle = \delta_{nn'}, \quad (\text{B12})$$

take

$$\begin{aligned} \sum_{\mathbf{G}} \langle n\mathbf{k}|\mathbf{k} + \mathbf{G}\rangle \langle \mathbf{k} + \mathbf{G}|n'\mathbf{k}\rangle &= \int d\mathbf{r}d\mathbf{r}' \sum_{\mathbf{G}} \langle n\mathbf{k}|\mathbf{r}\rangle \langle \mathbf{r}|\mathbf{k} + \mathbf{G}\rangle \langle \mathbf{k} + \mathbf{G}|\mathbf{r}'\rangle \langle \mathbf{r}'|n'\mathbf{k}\rangle \\ &= \int d\mathbf{r}d\mathbf{r}' \sum_{\mathbf{G}} \psi_{n\mathbf{k}}^*(\mathbf{r}) \frac{1}{\sqrt{\Omega}} e^{i(\mathbf{k}+\mathbf{G})\cdot\mathbf{r}} \frac{1}{\sqrt{\Omega}} e^{-i(\mathbf{k}+\mathbf{G})\cdot\mathbf{r}'} \psi_{m\mathbf{k}}(\mathbf{r}') \\ &= \int d\mathbf{r}d\mathbf{r}' \psi_{n\mathbf{k}}^*(\mathbf{r}) \psi_{m\mathbf{k}}(\mathbf{r}') \frac{1}{V} \sum_{\mathbf{G}} e^{i(\mathbf{k}+\mathbf{G})\cdot(\mathbf{r}-\mathbf{r}')} \\ &= \int d\mathbf{r}d\mathbf{r}' \psi_{n\mathbf{k}}^*(\mathbf{r}) \psi_{m\mathbf{k}}(\mathbf{r}') \delta(\mathbf{r} - \mathbf{r}') = \int d\mathbf{r} \psi_{n\mathbf{k}}^*(\mathbf{r}) \psi_{m\mathbf{k}}(\mathbf{r}) = \delta_{nn'}, \end{aligned} \quad (\text{B13})$$

and thus Eq. (B11) follows. Q.E.D. We used

$$\langle \mathbf{r}|\mathbf{k} + \mathbf{G}\rangle = \frac{1}{\sqrt{\Omega}} e^{i(\mathbf{k}+\mathbf{G})\cdot\mathbf{r}}. \quad (\text{B14})$$

From Eq. (71), we would like to calculate

$$\mathcal{V}_{nm}^{\text{nl},\ell}(\mathbf{k}) = \frac{1}{2} \langle n\mathbf{k}|C^\ell(z)\mathbf{v}^{\text{nl}} + \mathbf{v}^{\text{nl}}C^\ell(z)|m\mathbf{k}\rangle. \quad (\text{B15})$$

We work out the first term in the r.h.s,

$$\begin{aligned} \langle n\mathbf{k}|C^\ell(z)\mathbf{v}^{\text{nl}}|m\mathbf{k}\rangle &= \sum_{\mathbf{G}} \langle n\mathbf{k}|C^\ell(z)|\mathbf{k} + \mathbf{G}\rangle \langle \mathbf{k} + \mathbf{G}|\mathbf{v}^{\text{nl}}|m\mathbf{k}\rangle \\ &= \sum_{\mathbf{G}} \int d\mathbf{r} \int d\mathbf{r}' \langle n\mathbf{k}|\mathbf{r}\rangle \langle \mathbf{r}|C^\ell(z)|\mathbf{r}'\rangle \langle \mathbf{r}'|\mathbf{k} + \mathbf{G}\rangle \\ &\quad \times \int d\mathbf{r}'' \int d\mathbf{r}''' \langle \mathbf{k} + \mathbf{G}|\mathbf{r}''\rangle \langle \mathbf{r}''|\mathbf{v}^{\text{nl}}|\mathbf{r}'''\rangle \langle \mathbf{r}'''|m\mathbf{k}\rangle \\ &= \sum_{\mathbf{G}} \int d\mathbf{r} \int d\mathbf{r}' \langle n\mathbf{k}|\mathbf{r}\rangle C^\ell(z) \delta(\mathbf{r} - \mathbf{r}') \langle \mathbf{r}'|\mathbf{k} + \mathbf{G}\rangle \\ &\quad \times \int d\mathbf{r}'' \int d\mathbf{r}''' \langle \mathbf{k} + \mathbf{G}|\mathbf{r}''\rangle \langle \mathbf{r}''|\mathbf{v}^{\text{nl}}|\mathbf{r}'''\rangle \langle \mathbf{r}'''|m\mathbf{k}\rangle \\ &= \sum_{\mathbf{G}} \int d\mathbf{r} \langle n\mathbf{k}|\mathbf{r}\rangle C^\ell(z) \langle \mathbf{r}|\mathbf{k} + \mathbf{G}\rangle \\ &\quad \times \frac{i}{\hbar} \int d\mathbf{r}'' \int d\mathbf{r}''' \langle \mathbf{k} + \mathbf{G}|\mathbf{r}''\rangle V^{\text{nl}}(\mathbf{r}'', \mathbf{r}''') (\mathbf{r}''' - \mathbf{r}'') \langle \mathbf{r}'''|m\mathbf{k}\rangle, \end{aligned} \quad (\text{B16})$$

where we used Eq. (B2) and (26). We use Eq. (B5), (B14) and (B3) to obtain

$$\begin{aligned}
\langle n\mathbf{k}|C^\ell(z)|\mathbf{v}^{\text{nl}}|m\mathbf{k}\rangle &= \sum_{\mathbf{G}} \sum_{\mathbf{G}'} A_{n\mathbf{k}}^*(\mathbf{G}') \frac{1}{\Omega} \int d\mathbf{r} e^{-i(\mathbf{k}+\mathbf{G}')\cdot\mathbf{r}} C^\ell(z) e^{i(\mathbf{k}+\mathbf{G})\cdot\mathbf{r}} \\
&\times \sum_{\mathbf{G}''} A_{m\mathbf{k}}(\mathbf{G}'') \frac{i}{\hbar\Omega} \int d\mathbf{r}'' \int d\mathbf{r}''' e^{-i(\mathbf{k}+\mathbf{G})\cdot\mathbf{r}''} V^{\text{nl}}(\mathbf{r}'', \mathbf{r}''') (\mathbf{r}''' - \mathbf{r}'') e^{i(\mathbf{k}+\mathbf{G}'')\cdot\mathbf{r}'''} \\
&= \frac{1}{\hbar} \sum_{\mathbf{G}} \sum_{\mathbf{G}'} A_{n\mathbf{k}}^*(\mathbf{G}') \delta_{\mathbf{G}_{\parallel}\mathbf{G}'_{\parallel}} f_\ell(\mathbf{G}_\perp - \mathbf{G}'_\perp) \sum_{\mathbf{G}''} A_{m\mathbf{k}}(\mathbf{G}'') (\nabla_{\mathbf{K}} + \nabla_{\mathbf{K}''}) V^{\text{nl}}(\mathbf{K}, \mathbf{K}''),
\end{aligned} \tag{B17}$$

where

$$\frac{1}{\Omega} \int d\mathbf{r} C^\ell(z) e^{i(\mathbf{G}-\mathbf{G}')\cdot\mathbf{r}} = \delta_{\mathbf{G}_{\parallel}\mathbf{G}'_{\parallel}} f_\ell(\mathbf{G}_\perp - \mathbf{G}'_\perp), \tag{B18}$$

and

$$f_\ell(g) = \frac{1}{L} \int_{z_\ell - \Delta_\ell^b}^{z_\ell + \Delta_\ell^f} e^{igz} dz, \tag{B19}$$

where $f^*(g) = f(-g)$. We define

$$\mathcal{F}_{n\mathbf{k}}^\ell(\mathbf{G}) = \sum_{\mathbf{G}'} A_{n\mathbf{k}}(\mathbf{G}') \delta_{\mathbf{G}_{\parallel}\mathbf{G}'_{\parallel}} f_\ell(\mathbf{G}'_\perp - \mathbf{G}_\perp), \tag{B20}$$

and

$$\mathcal{H}_{n\mathbf{k}}(\mathbf{G}) = \sum_{\mathbf{G}'} A_{n\mathbf{k}}(\mathbf{G}') (\nabla_{\mathbf{K}} + \nabla_{\mathbf{K}'}) V^{\text{nl}}(\mathbf{K}, \mathbf{K}'), \tag{B21}$$

thus we can compactly write,

$$\langle n\mathbf{k}|C^\ell(z)|\mathbf{v}^{\text{nl}}|m\mathbf{k}\rangle = \frac{1}{\hbar} \sum_{\mathbf{G}} \mathcal{F}_{n\mathbf{k}}^{\ell*}(\mathbf{G}) \mathcal{H}_{m\mathbf{k}}(\mathbf{G}). \tag{B22}$$

Now, the second term of Eq. (B15)

$$\begin{aligned}
\langle n\mathbf{k}|\mathbf{v}^{\text{nl}}C^\ell(z)|m\mathbf{k}\rangle &= \sum_{\mathbf{G}} \langle n\mathbf{k}|\mathbf{v}^{\text{nl}}|\mathbf{k} + \mathbf{G}\rangle \langle \mathbf{k} + \mathbf{G}|C^\ell(z)|m\mathbf{k}\rangle \\
&= \sum_{\mathbf{G}} \int d\mathbf{r}'' \int d\mathbf{r}''' \langle n\mathbf{k}|\mathbf{r}''\rangle \langle \mathbf{r}''|\mathbf{v}^{\text{nl}}|\mathbf{r}'''\rangle \langle \mathbf{r}'''|\mathbf{k} + \mathbf{G}\rangle \\
&\times \int d\mathbf{r} \int d\mathbf{r}' \langle \mathbf{k} + \mathbf{G}|\mathbf{r}\rangle \langle \mathbf{r}|C^\ell(z)|\mathbf{r}'\rangle \langle \mathbf{r}'|m\mathbf{k}\rangle \\
&= \sum_{\mathbf{G}} \frac{i}{\hbar} \int d\mathbf{r}'' \int d\mathbf{r}''' \langle n\mathbf{k}|\mathbf{r}''\rangle V^{\text{nl}}(\mathbf{r}'', \mathbf{r}''') (\mathbf{r}''' - \mathbf{r}'') \langle \mathbf{r}'''|\mathbf{k} + \mathbf{G}\rangle \\
&\times \int d\mathbf{r} \langle \mathbf{k} + \mathbf{G}|\mathbf{r}\rangle C^\ell(z) \langle \mathbf{r}|m\mathbf{k}\rangle \\
&= \sum_{\mathbf{G}} \sum_{\mathbf{G}'} A_{n\mathbf{k}}^*(\mathbf{G}') \frac{i}{\hbar\Omega} \int d\mathbf{r}'' \int d\mathbf{r}''' e^{-i(\mathbf{k}+\mathbf{G}')\cdot\mathbf{r}''} V^{\text{nl}}(\mathbf{r}'', \mathbf{r}''') (\mathbf{r}''' - \mathbf{r}'') e^{i(\mathbf{k}+\mathbf{G})\cdot\mathbf{r}'''}
\end{aligned}$$

$$\begin{aligned}
& \times \sum_{\mathbf{G}''} A_{m\mathbf{k}}(\mathbf{G}'') \frac{1}{\Omega} \int d\mathbf{r} e^{-i(\mathbf{k}+\mathbf{G})\cdot\mathbf{r}} C^\ell(z) e^{i(\mathbf{k}+\mathbf{G}'')\cdot\mathbf{r}} \\
& = \frac{1}{\hbar} \sum_{\mathbf{G}} \sum_{\mathbf{G}'} A_{n\mathbf{k}}^*(\mathbf{G}') (\nabla_{\mathbf{K}} + \nabla_{\mathbf{K}'}) V^{\text{nl}}(\mathbf{K}', \mathbf{K}) \\
& \times \sum_{\mathbf{G}''} A_{m\mathbf{k}}(\mathbf{G}'') \delta_{\mathbf{G}_{\parallel}\mathbf{G}''_{\parallel}} f_\ell(\mathbf{G}''_{\perp} - \mathbf{G}_{\perp}) \\
& = \frac{1}{\hbar} \sum_{\mathbf{G}} \mathcal{H}_{n\mathbf{k}}^*(\mathbf{G}) \mathcal{F}_{m\mathbf{k}}^\ell(\mathbf{G}).
\end{aligned} \tag{B23}$$

Therefore Eq. (B15) is compactly given by

$$\mathbf{v}_{nm}^{\text{nl},\ell}(\mathbf{k}) = \frac{1}{2\hbar} \sum_{\mathbf{G}} \left(\mathcal{F}_{n\mathbf{k}}^{\ell*}(\mathbf{G}) \mathcal{H}_{m\mathbf{k}}(\mathbf{G}) + \mathcal{H}_{n\mathbf{k}}^*(\mathbf{G}) \mathcal{F}_{m\mathbf{k}}^\ell(\mathbf{G}) \right). \tag{B24}$$

For fully separable pseudopotentials in the Kleinman-Bylander (KB) form,^{21–23} we can use Eq. (B9) and evaluate above expression, that we have implemented in the DPTM code.²⁰ Explicitly,

$$\begin{aligned}
\mathbf{v}_{nm}^{\text{nl},\ell}(\mathbf{k}) &= \frac{1}{2\hbar} \sum_s \sum_{l=0}^{l_s} \sum_{m=-l}^l E_l \\
& \left[\left(\sum_{\mathbf{G}''} \nabla_{\mathbf{G}''} f_{lm}^s(\mathbf{G}'') \sum_{\mathbf{G}} A_{n\mathbf{k}}^*(\mathbf{G}) \delta_{\mathbf{G}_{\parallel}\mathbf{G}''_{\parallel}} f_\ell(G_z - G'_z) \right) \left(\sum_{\mathbf{G}'} A_{m\mathbf{k}}(\mathbf{G}') f_{lm}^{s*}(\mathbf{K}') \right) \right. \\
& + \left(\sum_{\mathbf{G}''} f_{lm}^s(\mathbf{G}'') \sum_{\mathbf{G}} A_{n\mathbf{k}}^*(\mathbf{G}) \delta_{\mathbf{G}_{\parallel}\mathbf{G}''_{\parallel}} f_\ell(G_z - G'_z) \right) \left(\sum_{\mathbf{G}'} A_{m\mathbf{k}}(\mathbf{G}') \nabla_{\mathbf{K}'} f_{lm}^{s*}(\mathbf{K}') \right) \\
& + \left(\sum_{\mathbf{G}} A_{n\mathbf{k}}^*(\mathbf{G}) \nabla_{\mathbf{G}} f_{lm}^s(\mathbf{G}) \right) \left(\sum_{\mathbf{G}''} f_{lm}^{s*}(\mathbf{G}'') \sum_{\mathbf{G}'} A_{m\mathbf{k}}(\mathbf{G}') \delta_{\mathbf{G}'_{\parallel}\mathbf{G}''_{\parallel}} f_\ell(G'_z - G''_z) \right) \\
& \left. + \left(\sum_{\mathbf{G}} A_{n\mathbf{k}}^*(\mathbf{G}) f_{lm}^s(\mathbf{G}) \right) \left(\sum_{\mathbf{G}''} \nabla_{\mathbf{G}''} f_{lm}^{s*}(\mathbf{G}'') \sum_{\mathbf{G}'} A_{m\mathbf{k}}(\mathbf{G}') \delta_{\mathbf{G}'_{\parallel}\mathbf{G}''_{\parallel}} f_\ell(G'_z - G''_z) \right) \right].
\end{aligned} \tag{B25}$$

For a full slab calculation, equivalent to a bulk calculation, $C^\ell(z) = 1$ and then $f_\ell(g) = \delta_{g0}$, and Eq. (B25) reduces to Eq. (B10).

Appendix C: $V_{nm}^{\sigma,\text{a},\ell}$ and $(\mathcal{V}_{nm}^{\sigma,\text{a},\ell})_{;k^b}$

From Eq. (73)

$$(\mathcal{V}_{nm}^{\sigma,\text{a},\ell})_{;k^b} = (\mathcal{V}_{nm}^{\text{LDA},\text{a},\ell})_{;k^b} + (\mathcal{V}_{nm}^{\mathcal{S},\text{a},\ell})_{;k^b}. \tag{C1}$$

For the LDA term we have

$$\begin{aligned}
\mathcal{V}_{nm}^{\text{LDA,a},\ell} &= \frac{1}{2} \left(v_{nm}^{\text{LDA,a}} \mathcal{C}^\ell + \mathcal{C}^\ell v_{nm}^{\text{LDA,a}} \right)_{nm} \\
&= \frac{1}{2} \sum_q \left(v_{nq}^{\text{LDA,a}} \mathcal{C}_{qm}^\ell + \mathcal{C}_{nq}^\ell v_{qm}^{\text{LDA,a}} \right) \\
(\mathcal{V}_{nm}^{\text{LDA,a}})_{;k^b} &= \frac{1}{2} \sum_q \left(v_{nq}^{\text{LDA,a}} \mathcal{C}_{qm}^\ell + \mathcal{C}_{nq}^\ell v_{qm}^{\text{LDA,a}} \right)_{;k^b} \\
&= \frac{1}{2} \sum_q \left((v_{nq}^{\text{LDA,a}})_{;k^b} \mathcal{C}_{qm}^\ell + v_{nq}^{\text{LDA,a}} (\mathcal{C}_{qm}^\ell)_{;k^b} + (\mathcal{C}_{nq}^\ell)_{;k^b} v_{qm}^{\text{LDA,a}} + \mathcal{C}_{nq}^\ell (v_{qm}^{\text{LDA,a}})_{;k^b} \right), \quad (\text{C2})
\end{aligned}$$

where we omitted \mathbf{k} in all quantities. From Eq. (B6) we know that $\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k})$ can be readily calculated, and from Appendix G, both v_{nm}^a and \mathcal{C}_{nm}^ℓ are also known quantities, and thus the $\mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k})$ are known, which in turns means that $\mathcal{V}_{nm}^{\text{LDA,a},\ell}$ are also known. For the generalized derivative $(\mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k}))_{;\mathbf{k}}$ we use Eq. (31) to write

$$\begin{aligned}
(v_{nm}^{\text{LDA,a}})_{;k^b} &= im_e (\omega_{nm}^{\text{LDA}} r_{nm}^a)_{;k^b} \\
&= im_e (\omega_{nm}^{\text{LDA}})_{;k^b} r_{nm}^a + im_e \omega_{nm}^{\text{LDA}} (r_{nm}^a)_{;k^b} \\
&= im_e \Delta_{nm}^b r_{nm}^a + im_e \omega_{nm}^{\text{LDA}} (r_{nm}^a)_{;k^b} \quad \text{for } n \neq m, \quad (\text{C3})
\end{aligned}$$

where we used Eq (79) and $(r_{nm}^a)_{;k^b}$ is given in Eq. (H12).

Likewise,

$$\begin{aligned}
\mathcal{V}_{nm}^{\mathcal{S},a,\ell} &= \frac{1}{2} \left(v_{nm}^{\mathcal{S},a} \mathcal{C}^\ell + \mathcal{C}^\ell v_{nm}^{\mathcal{S},a} \right)_{nm} \\
&= \frac{1}{2} \sum_q \left(v_{nq}^{\mathcal{S},a} \mathcal{C}_{qm}^\ell + \mathcal{C}_{nq}^\ell v_{qm}^{\mathcal{S},a} \right) \\
(\mathcal{V}_{nm}^{\mathcal{S},a})_{;k^b} &= \frac{1}{2} \sum_q \left(v_{nq}^{\mathcal{S},a} \mathcal{C}_{qm}^\ell + \mathcal{C}_{nq}^\ell v_{qm}^{\mathcal{S},a} \right)_{;k^b} \\
&= \frac{1}{2} \sum_q \left((v_{nq}^{\mathcal{S},a})_{;k^b} \mathcal{C}_{qm}^\ell + v_{nq}^{\mathcal{S},a} (\mathcal{C}_{qm}^\ell)_{;k^b} + (\mathcal{C}_{nq}^\ell)_{;k^b} v_{qm}^{\mathcal{S},a} + \mathcal{C}_{nq}^\ell (v_{qm}^{\mathcal{S},a})_{;k^b} \right), \quad (\text{C4})
\end{aligned}$$

where $v_{nm}^{\mathcal{S},a}(\mathbf{k})$ are given in Eq. (27) and $(v_{nm}^{\mathcal{S},a})_{;k^b}$ is given in Eq. A(6) of Ref. 36,

$$(v_{nm}^{\mathcal{S},a})_{;k^b} = i \Delta f_{mn} (r_{nm}^a)_{;k^b}. \quad (\text{C5})$$

To evaluate $(\mathcal{C}_{nm}^\ell)_{;k^a}$, we use the fact that as $\mathcal{C}^\ell(z)$ is only a function of the z coordinate, its commutator with \mathbf{r} is zero, then,

$$\langle n\mathbf{k} | [r^a, \mathcal{C}^\ell(z)] | m\mathbf{k}' \rangle = \langle n\mathbf{k} | [r_e^a, \mathcal{C}^\ell(z)] | m\mathbf{k}' \rangle + \langle n\mathbf{k} | [r_i^a, \mathcal{C}^\ell(z)] | m\mathbf{k}' \rangle = 0. \quad (\text{C6})$$

The interband part reduces to,

$$\begin{aligned}
[r_e^a, \mathcal{C}^\ell(z)]_{nm} &= \sum_{q\mathbf{k}''} \left(\langle n\mathbf{k} | r_e^a | q\mathbf{k}'' \rangle \langle q\mathbf{k}'' | \mathcal{C}^\ell(z) | m\mathbf{k}' \rangle - \langle n\mathbf{k} | \mathcal{C}^\ell(z) | q\mathbf{k}'' \rangle \langle q\mathbf{k}'' | r_e^a | m\mathbf{k}' \rangle \right) \\
&= \sum_{q\mathbf{k}''} \delta(\mathbf{k} - \mathbf{k}'') \delta(\mathbf{k}' - \mathbf{k}'') \left((1 - \delta_{qn}) \xi_{nq}^a \mathcal{C}_{qm}^\ell - (1 - \delta_{qm}) \mathcal{C}_{nq}^\ell \xi_{qm}^a \right) \\
&= \delta(\mathbf{k} - \mathbf{k}') \left(\sum_q \left(\xi_{nq}^a \mathcal{C}_{qm}^\ell - \mathcal{C}_{nq}^\ell \xi_{qm}^a \right) + \mathcal{C}_{nm}^\ell (\xi_{mm}^a - \xi_{nn}^a) \right), \tag{C7}
\end{aligned}$$

where we used Eq. (A15), and the \mathbf{k} and z dependence is implicitly understood. From Eq. (A18) the intraband part is,

$$\langle n\mathbf{k} | [\hat{\mathbf{r}}_i, \mathcal{C}^\ell(z)] | m\mathbf{k}' \rangle = i\delta(\mathbf{k} - \mathbf{k}') (\mathcal{C}_{nm}^\ell)_{;\mathbf{k}}, \tag{C8}$$

then from Eq. (C6)

$$\begin{aligned}
&\left((\mathcal{C}_{nm}^\ell)_{;\mathbf{k}} - i \sum_q \left(\xi_{nq}^a \mathcal{C}_{qm}^\ell - \mathcal{C}_{nq}^\ell \xi_{qm}^a \right) - i \mathcal{C}_{nm}^\ell (\xi_{mm}^a - \xi_{nn}^a) \right) i\delta(\mathbf{k} - \mathbf{k}') = 0 \\
\frac{1}{i} (\mathcal{C}_{nm}^\ell)_{;\mathbf{k}} &= \sum_q \left(\xi_{nq}^a \mathcal{C}_{qm}^\ell - \mathcal{C}_{nq}^\ell \xi_{qm}^a \right) + \mathcal{C}_{nm}^\ell (\xi_{mm}^a - \xi_{nn}^a) \\
&= \sum_{q \neq nm} \left(\xi_{nq}^a \mathcal{C}_{qm}^\ell - \mathcal{C}_{nq}^\ell \xi_{qm}^a \right) + \left(\xi_{nn}^a \mathcal{C}_{nm}^\ell - \mathcal{C}_{nn}^\ell \xi_{nm}^a \right)_{q=n} + \left(\xi_{nm}^a \mathcal{C}_{mm}^\ell - \mathcal{C}_{nm}^\ell \xi_{mm}^a \right)_{q=m} \\
&\quad + \mathcal{C}_{nm}^\ell (\xi_{mm}^a - \xi_{nn}^a) \\
(\mathcal{C}_{nm}^\ell)_{;\mathbf{k}} &= i \sum_{q \neq nm} \left(\xi_{nq}^a \mathcal{C}_{qm}^\ell - \mathcal{C}_{nq}^\ell \xi_{qm}^a \right) + i \xi_{nm}^a (\mathcal{C}_{mm}^\ell - \mathcal{C}_{nn}^\ell) \\
&= i \sum_{q \neq nm} \left(r_{nq}^a \mathcal{C}_{qm}^\ell - \mathcal{C}_{nq}^\ell r_{qm}^a \right) + i r_{nm}^a (\mathcal{C}_{mm}^\ell - \mathcal{C}_{nn}^\ell) \\
&= i \left(\sum_{q \neq n} r_{nq}^a \mathcal{C}_{qm}^\ell - \sum_{q \neq m} \mathcal{C}_{nq}^\ell r_{qm}^a \right) + i r_{nm}^a (\mathcal{C}_{mm}^\ell - \mathcal{C}_{nn}^\ell), \tag{C9}
\end{aligned}$$

since in every ξ_{nm}^a , $n \neq m$, thus we replace it by r_{nm}^a . The matrix elements $\mathcal{C}_{nm}^\ell(\mathbf{k})$ are calculated in Appendix G.

For the general case of

$$\langle n\mathbf{k} | [\hat{r}^a, \hat{\mathcal{G}}(\mathbf{r}, \mathbf{p})] | m\mathbf{k}' \rangle = \mathcal{U}_{nm}(\mathbf{k}), \tag{C10}$$

above result would lead to a more general expression,

$$(\mathcal{G}_{nm}(\mathbf{k}))_{;k^a} = \mathcal{U}_{nm}(\mathbf{k}) + i \sum_{q \neq (nm)} \left(r_{nq}^a(\mathbf{k}) \mathcal{G}_{qm}(\mathbf{k}) - \mathcal{G}_{nq}(\mathbf{k}) r_{qm}^a(\mathbf{k}) \right) + i r_{nm}^a(\mathbf{k}) (\mathcal{G}_{mm}(\mathbf{k}) - \mathcal{G}_{nn}(\mathbf{k})). \tag{C11}$$

Appendix D: Generalized derivative $(\omega_n(\mathbf{k}))_{;\mathbf{k}}$

We obtain the generalized derivative $(\omega_n(\mathbf{k}))_{;\mathbf{k}}$. We start from

$$\langle n\mathbf{k}|\hat{H}_0^\sigma|m\mathbf{k}'\rangle = \delta_{nm}\delta(\mathbf{k}-\mathbf{k}')\hbar\omega_m^\sigma(\mathbf{k}), \quad (\text{D1})$$

then Eq. (A19) gives for $n = m$

$$\begin{aligned} (H_{0,nn}^\sigma)_{;\mathbf{k}} &= \nabla_{\mathbf{k}}H_{0,nn}^\sigma(\mathbf{k}) - iH_{0,nn}^\sigma(\mathbf{k}) (\boldsymbol{\xi}_{nn}(\mathbf{k}) - \boldsymbol{\xi}_{nn}(\mathbf{k})) \\ &= \hbar\nabla_{\mathbf{k}}\omega_m^\sigma(\mathbf{k}), \end{aligned} \quad (\text{D2})$$

where from Eq. (A18),

$$\langle n\mathbf{k}|[\hat{\mathbf{r}}_i, \hat{H}_0]|m\mathbf{k}\rangle = i\delta_{nm}\hbar(\omega_m^\sigma(\mathbf{k}))_{;\mathbf{k}} = i\delta_{nm}\hbar\nabla_{\mathbf{k}}\omega_m^\sigma(\mathbf{k}), \quad (\text{D3})$$

then

$$(\omega_n^\sigma(\mathbf{k}))_{;\mathbf{k}} = \nabla_{\mathbf{k}}\omega_n^\sigma(\mathbf{k}). \quad (\text{D4})$$

From Eq. (20)

$$\langle n\mathbf{k}|[\hat{\mathbf{r}}, \hat{H}_0^\sigma]|m\mathbf{k}\rangle = i\hbar\mathbf{v}_{nm}^\sigma(\mathbf{k}), \quad (\text{D5})$$

therefore, substituting above into

$$\langle n\mathbf{k}|[\hat{\mathbf{r}}, \hat{H}_0^\sigma]|m\mathbf{k}\rangle = \langle n\mathbf{k}|[\hat{\mathbf{r}}_i, \hat{H}_0^\sigma]|m\mathbf{k}\rangle + \langle n\mathbf{k}|[\hat{\mathbf{r}}_e, \hat{H}_0^\sigma]|m\mathbf{k}\rangle, \quad (\text{D6})$$

we get

$$i\hbar\mathbf{v}_{nm}^\sigma(\mathbf{k}) = i\delta_{nm}\hbar\nabla_{\mathbf{k}}\omega_m^\sigma(\mathbf{k}) + \omega_{mn}^\sigma\mathbf{r}_{e,nm}(\mathbf{k}), \quad (\text{D7})$$

from where

$$\begin{aligned} \nabla_{\mathbf{k}}\omega_n^\sigma(\mathbf{k}) &= \mathbf{v}_{nn}^\sigma(\mathbf{k}) \\ \nabla_{\mathbf{k}}(\omega_n^{\text{LDA}}(\mathbf{k}) + \frac{\Sigma}{\hbar}(1-f_n)) &= \nabla_{\mathbf{k}}\omega_n^{\text{LDA}}(\mathbf{k}) \\ \nabla_{\mathbf{k}}\omega_n^{\text{LDA}}(\mathbf{k}) &= \mathbf{v}_{nn}^\sigma(\mathbf{k}), \end{aligned} \quad (\text{D8})$$

where we used Eq. (16), but from Eq. (27), $v_{nn}^S = 0$, and then $\mathbf{v}_{nn}^\sigma = v_{nn}^{\text{LDA}}$. Thus, from Eq. (D4)

$$(\omega_n^\sigma(\mathbf{k}))_{;k^a} = (\omega_n^{\text{LDA}}(\mathbf{k}))_{;k^a} = v_{nn}^{\text{LDA},a}(\mathbf{k}), \quad (\text{D9})$$

the same for the LDA and scissored Hamiltonians; $\mathbf{v}_{nn}^{\text{LDA}}(\mathbf{k})$ are the LDA velocities of the electron in state $|n\mathbf{k}\rangle$.

Appendix E: Expressions for χ_{abc}^S in terms of $\mathcal{V}_{mn}^{\sigma,a,\ell}$

As can be seen from the prefactor of Eqs. (76) and (77), they diverge as $\tilde{\omega} \rightarrow 0$. To remove this apparent divergence of χ^S , we perform a partial fraction expansion in $\tilde{\omega}$.

1. Intraband Contributions

For the intraband term of Eq. (76) we obtain

$$I = C \left[-\frac{1}{2(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} + \frac{2}{(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}} + \frac{1}{2(\omega_{nm}^\sigma)^2} \frac{1}{\tilde{\omega}} \right] \\ - D \left[-\frac{3}{2(\omega_{nm}^\sigma)^3} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} + \frac{4}{(\omega_{nm}^\sigma)^3} \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}} + \frac{1}{2(\omega_{nm}^\sigma)^3} \frac{1}{\tilde{\omega}} - \frac{1}{2(\omega_{nm}^\sigma)^2} \frac{1}{(\omega_{nm}^\sigma - \tilde{\omega})^2} \right], \quad (\text{E1})$$

where $C = f_{mn} \mathcal{V}_{mn}^{\sigma,a} (r_{nm}^{\text{LDA},b})_{;k^c}$, and $D = f_{mn} \mathcal{V}_{mn}^{\sigma,a} r_{nm}^b \Delta_{nm}^c$.

Time-reversal symmetry leads to the following relationships:

$$\begin{aligned} \mathbf{r}_{mn}(\mathbf{k})|_{-\mathbf{k}} &= \mathbf{r}_{nm}(\mathbf{k})|_{\mathbf{k}}, \\ (\mathbf{r}_{mn})_{;\mathbf{k}}(\mathbf{k})|_{-\mathbf{k}} &= (-\mathbf{r}_{nm})_{;\mathbf{k}}(\mathbf{k})|_{\mathbf{k}}, \\ \mathcal{V}_{mn}^{\sigma,a,\ell}(\mathbf{k})|_{-\mathbf{k}} &= -\mathcal{V}_{nm}^{\sigma,a,\ell}(\mathbf{k})|_{\mathbf{k}}, \\ (\mathcal{V}_{mn}^{\sigma,a,\ell})_{;\mathbf{k}}(\mathbf{k})|_{-\mathbf{k}} &= (\mathcal{V}_{nm}^{\sigma,a,\ell})_{;\mathbf{k}}(\mathbf{k})|_{\mathbf{k}}, \\ \omega_{mn}^\sigma(\mathbf{k})|_{-\mathbf{k}} &= \omega_{nm}^\sigma(\mathbf{k})|_{\mathbf{k}}, \\ \Delta_{nm}^a(\mathbf{k})|_{-\mathbf{k}} &= -\Delta_{nm}^a(\mathbf{k})|_{\mathbf{k}}. \end{aligned} \quad (\text{E2})$$

For a clean cold semiconductor, $f_n = 1$ for an occupied or valence ($n = v$) band, and $f_n = 0$ for an empty or conduction ($n = c$) band independent of \mathbf{k} , and $f_{nm} = -f_{mn}$. Using above relationships, we can show that the $1/\omega$ terms cancel each other out. Therefore, all the remaining non-zero terms in expressions (E1) are simple ω and 2ω resonant denominators well behaved at zero frequency.

To apply time-reversal invariance, we notice that the energy denominators are invariant under $\mathbf{k} \rightarrow -\mathbf{k}$, and then we only look at the numerators, then

$$\begin{aligned} C &\rightarrow f_{mn} \mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA},b} \right)_{;k^c} |_{\mathbf{k}} + f_{mn} \mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA},b} \right)_{;k^c} |_{-\mathbf{k}} \\ &= f_{mn} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA},b} \right)_{;k^c} |_{\mathbf{k}} + \left(-\mathcal{V}_{nm}^{\sigma,a,\ell} \right) \left(-r_{mn}^{\text{LDA},b} \right)_{;k^c} |_{\mathbf{k}} \right] \\ &= f_{mn} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA},b} \right)_{;k^c} + \mathcal{V}_{nm}^{\sigma,a,\ell} \left(r_{mn}^{\text{LDA},b} \right)_{;k^c} \right] \\ &= f_{mn} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA},b} \right)_{;k^c} + \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA},b} \right)_{;k^c} \right)^* \right] \end{aligned}$$

$$= 2f_{mn} \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right], \quad (\text{E3})$$

and likewise,

$$\begin{aligned} D &\rightarrow f_{mn} \mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \Delta_{nm}^c |_{\mathbf{k}} + f_{mn} \mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \Delta_{nm}^c |_{-\mathbf{k}} \\ &= f_{mn} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \Delta_{nm}^c |_{\mathbf{k}} + \left(-\mathcal{V}_{nm}^{\sigma,a,\ell} \right) r_{mn}^{\text{LDA,b}} \left(-\Delta_{nm}^c \right) |_{\mathbf{k}} \right] \\ &= f_{mn} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} + \mathcal{V}_{nm}^{\sigma,a,\ell} r_{mn}^{\text{LDA,b}} \right] \Delta_{nm}^c \\ &= f_{mn} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} + \left(\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \right)^* \right] \Delta_{nm}^c \\ &= 2f_{mn} \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \right] \Delta_{nm}^c. \end{aligned} \quad (\text{E4})$$

The last term in the second line of Eq. (E1) is dealt with as follows.

$$\begin{aligned} \frac{D}{2(\omega_{nm}^\sigma)^2} \frac{1}{(\omega_{nm}^\sigma - \tilde{\omega})^2} &= \frac{f_{mn}}{2} \frac{\mathcal{V}_{mn}^{\sigma,a} r_{nm}^b}{(\omega_{nm}^\sigma)^2} \frac{\Delta_{nm}^c}{(\omega_{nm}^\sigma - \tilde{\omega})^2} = -\frac{f_{mn}}{2} \frac{\mathcal{V}_{mn}^{\sigma,a} r_{nm}^b}{(\omega_{nm}^\sigma)^2} \left(\frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} \right)_{;k^c} \\ &= \frac{f_{mn}}{2} \left(\frac{\mathcal{V}_{mn}^{\sigma,a} r_{nm}^b}{(\omega_{nm}^\sigma)^2} \right)_{;k^c} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}}, \end{aligned} \quad (\text{E5})$$

where we used Eqs. (79) and for the last line, we performed an integration by parts over the Brillouin zone, where the contribution from the edges vanishes.³³ Now, we apply the chain rule, to get

$$\left(\frac{\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}}}{(\omega_{nm}^\sigma)^2} \right)_{;k^c} = \frac{r_{nm}^{\text{LDA,b}}}{(\omega_{nm}^\sigma)^2} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} + \frac{\mathcal{V}_{mn}^{\sigma,a,\ell}}{(\omega_{nm}^\sigma)^2} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} - \frac{2\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}}}{(\omega_{nm}^\sigma)^3} (\omega_{nm}^\sigma)_{;k^c}, \quad (\text{E6})$$

and work the time-reversal on each term. The first term is reduced to

$$\begin{aligned} \frac{r_{nm}^{\text{LDA,b}}}{(\omega_{nm}^\sigma)^2} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} |_{\mathbf{k}} + \frac{r_{nm}^{\text{LDA,b}}}{(\omega_{nm}^\sigma)^2} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} |_{-\mathbf{k}} &= \frac{r_{nm}^{\text{LDA,b}}}{(\omega_{nm}^\sigma)^2} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} |_{\mathbf{k}} + \frac{r_{nm}^{\text{LDA,b}}}{(\omega_{nm}^\sigma)^2} \left(\mathcal{V}_{nm}^{\sigma,a,\ell} \right)_{;k^c} |_{\mathbf{k}} \\ &= \frac{1}{(\omega_{nm}^\sigma)^2} \left[r_{nm}^{\text{LDA,b}} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} + \left(r_{nm}^{\text{LDA,b}} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} \right)^* \right] \\ &= \frac{2}{(\omega_{nm}^\sigma)^2} \operatorname{Re} \left[r_{nm}^{\text{LDA,b}} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} \right], \end{aligned} \quad (\text{E7})$$

the second term is reduced to

$$\begin{aligned} \frac{\mathcal{V}_{mn}^{\sigma,a,\ell}}{(\omega_{nm}^\sigma)^2} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} |_{\mathbf{k}} + \frac{\mathcal{V}_{mn}^{\sigma,a,\ell}}{(\omega_{nm}^\sigma)^2} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} |_{-\mathbf{k}} &= \frac{\mathcal{V}_{mn}^{\sigma,a,\ell}}{(\omega_{nm}^\sigma)^2} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} |_{\mathbf{k}} + \frac{\mathcal{V}_{nm}^{\sigma,a,\ell}}{(\omega_{nm}^\sigma)^2} \left(r_{mn}^{\text{LDA,b}} \right)_{;k^c} |_{\mathbf{k}} \\ &= \frac{1}{(\omega_{nm}^\sigma)^2} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} + \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right)^* \right] \\ &= \frac{2}{(\omega_{nm}^\sigma)^2} \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right], \end{aligned} \quad (\text{E8})$$

and by using (79), the third term is reduced to

$$\begin{aligned}
\frac{2\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm}}{(\omega_{nm}^\sigma)^3} (\omega_{nm}^\sigma)_{;k^c} | \mathbf{k} + \frac{2\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm}}{(\omega_{nm}^\sigma)^3} (\omega_{nm}^\sigma)_{;k^c} | -\mathbf{k} &= \frac{2\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm}}{(\omega_{nm}^\sigma)^3} \Delta_{nm}^c | \mathbf{k} + \frac{2\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm}}{(\omega_{nm}^\sigma)^3} \Delta_{nm}^c | -\mathbf{k} \\
&= \frac{2\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm}}{(\omega_{nm}^\sigma)^3} \Delta_{nm}^c | \mathbf{k} + \frac{2\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm}}{(\omega_{nm}^\sigma)^3} \Delta_{nm}^c | \mathbf{k} \\
&= \frac{2}{(\omega_{nm}^\sigma)^3} \left[\mathcal{V}_{nm}^{\sigma,a,\ell,LDA,b} r_{mn} + \left(\mathcal{V}_{nm}^{\sigma,a,\ell,LDA,b} r_{mn} \right)^* \right] \Delta_{nm}^c \\
&= \frac{4}{(\omega_{nm}^\sigma)^3} \text{Re} \left[\mathcal{V}_{nm}^{\sigma,a,\ell,LDA,b} r_{mn} \right] \Delta_{nm}^c. \tag{E9}
\end{aligned}$$

Combining the results from (E7), (E8), and (E9) into (E6),

$$\begin{aligned}
\frac{f_{mn}}{2} \left[\left(\frac{\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm}}{(\omega_{nm}^\sigma)^2} \right)_{;k^c} | \mathbf{k} + \left(\frac{\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm}}{(\omega_{nm}^\sigma)^2} \right)_{;k^c} | -\mathbf{k} \right] \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} = \\
\left(2 \text{Re} \left[r_{nm}^{\text{LDA,b}} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} \right] + 2 \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right] - \frac{4}{\omega_{nm}^\sigma} \text{Re} \left[\mathcal{V}_{nm}^{\sigma,a,\ell,LDA,b} r_{mn} \right] \Delta_{nm}^c \right) \frac{f_{mn}}{2(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}}. \tag{E10}
\end{aligned}$$

We substitute (E3), (E4), and (E10) in (E1),

$$\begin{aligned}
I = & \left[-\frac{2f_{mn} \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right]}{2(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} + \frac{4f_{mn} \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right]}{(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}} \right] \\
& + \left[\frac{6f_{mn} \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm} \right] \Delta_{nm}^c}{2(\omega_{nm}^\sigma)^3} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} - \frac{8f_{mn} \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm} \right] \Delta_{nm}^c}{(\omega_{nm}^\sigma)^3} \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}} \right. \\
& \left. + \frac{f_{mn} \left(2 \text{Re} \left[r_{nm}^{\text{LDA,b}} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} \right] + 2 \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right] - \frac{4}{\omega_{nm}^\sigma} \text{Re} \left[\mathcal{V}_{nm}^{\sigma,a,\ell,LDA,b} r_{mn} \right] \Delta_{nm}^c \right)}{2(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} \right].
\end{aligned}$$

If we simplify,

$$\begin{aligned}
I = & -\frac{2f_{mn} \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right]}{2(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} + \frac{4f_{mn} \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right]}{(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}} \\
& + \frac{6f_{mn} \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm} \right] \Delta_{nm}^c}{2(\omega_{nm}^\sigma)^3} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} - \frac{8f_{mn} \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell,LDA,b} r_{nm} \right] \Delta_{nm}^c}{(\omega_{nm}^\sigma)^3} \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}} \\
& + \frac{2f_{mn} \text{Re} \left[r_{nm}^{\text{LDA,b}} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} \right]}{2(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} \\
& + \frac{2f_{mn} \text{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right]}{2(\omega_{nm}^\sigma)^2} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}} \\
& - \frac{4f_{mn} \text{Re} \left[\mathcal{V}_{nm}^{\sigma,a,\ell,LDA,b} r_{mn} \right] \Delta_{nm}^c}{2(\omega_{nm}^\sigma)^3} \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}}, \tag{E11}
\end{aligned}$$

we conveniently collect the terms in columns of ω and 2ω . We can now express the susceptibility in terms of ω and 2ω . Separating the 2ω terms and substituting in above equation

$$\begin{aligned}
I_{2\omega} &= -\frac{e^3}{\hbar^2} \sum_{mn\mathbf{k}} \left[\frac{4f_{mn} \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right]}{(\omega_{nm}^\sigma)^2} - \frac{8f_{mn} \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \right] \Delta_{nm}^c}{(\omega_{nm}^\sigma)^3} \right] \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}} \\
&= -\frac{e^3}{\hbar^2} \sum_{mn\mathbf{k}} \frac{4f_{mn}}{(\omega_{nm}^\sigma)^2} \left[\operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right] - \frac{2 \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \right] \Delta_{nm}^c}{\omega_{nm}^\sigma} \right] \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}}. \quad (\text{E12})
\end{aligned}$$

We can express the energies in terms of transitions between bands. Therefore, $\omega_{nm}^\sigma = \omega_{cv}^\sigma$ for transitions between conduction and valence bands. To take the limit $\eta \rightarrow 0$, we use

$$\lim_{\eta \rightarrow 0} \frac{1}{x \pm i\eta} = P \frac{1}{x} \mp i\pi\delta(x), \quad (\text{E13})$$

and can finally rewrite (E12) in the desired form,

$$\operatorname{Im}[\chi_{i,a,\ell bc,2\omega}^{s,\ell}] = -\frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{c}\mathbf{k}} \frac{4}{(\omega_{cv}^\sigma)^2} \left(\operatorname{Re} \left[\mathcal{V}_{vc}^{\sigma,a,\ell} \left(r_{cv}^{\text{LDA,b}} \right)_{;k^c} \right] - \frac{2 \operatorname{Re} \left[\mathcal{V}_{vc}^{\sigma,a,\ell} r_{cv}^{\text{LDA,b}} \right] \Delta_{cv}^c}{\omega_{cv}^\sigma} \right) \delta(\omega_{cv}^\sigma - 2\omega). \quad (\text{E14})$$

where we added a 1/2 from the sum over $\mathbf{k} \rightarrow -\mathbf{k}$. We do the same for the $\tilde{\omega}$ terms in (E11) to obtain

$$\begin{aligned}
I_\omega &= -\frac{e^3}{2\hbar^2} \sum_{nm\mathbf{k}} \left[-\frac{2f_{mn} \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right]}{(\omega_{nm}^\sigma)^2} + \frac{6f_{mn} \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \right] \Delta_{nm}^c}{(\omega_{nm}^\sigma)^3} \right. \\
&\quad \left. + \frac{2f_{mn} \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} \left(r_{nm}^{\text{LDA,b}} \right)_{;k^c} \right]}{(\omega_{nm}^\sigma)^2} - \frac{4f_{mn} \operatorname{Re} \left[\mathcal{V}_{nm}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \right] \Delta_{nm}^c}{(\omega_{nm}^\sigma)^3} \right. \\
&\quad \left. + \frac{2f_{mn} \operatorname{Re} \left[r_{nm}^{\text{LDA,b}} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} \right]}{(\omega_{nm}^\sigma)^2} \right] \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}}. \quad (\text{E15})
\end{aligned}$$

We reduce in the same way as (E12),

$$I_\omega = -\frac{e^3}{2\hbar^2} \sum_{nm\mathbf{k}} \frac{f_{mn}}{(\omega_{nm}^\sigma)^2} \left[2 \operatorname{Re} \left[r_{nm}^{\text{LDA,b}} \left(\mathcal{V}_{mn}^{\sigma,a,\ell} \right)_{;k^c} \right] + \frac{2 \operatorname{Re} \left[\mathcal{V}_{mn}^{\sigma,a,\ell} r_{nm}^{\text{LDA,b}} \right] \Delta_{nm}^c}{\omega_{nm}^\sigma} \right] \frac{1}{\omega_{nm}^\sigma - \tilde{\omega}}, \quad (\text{E16})$$

and using (E13) we obtain our final form,

$$\operatorname{Im}[\chi_{i,a,\ell bc,\omega}^{s,\ell}] = -\frac{\pi|e|^3}{2\hbar^2} \sum_{c\mathbf{v}\mathbf{k}} \frac{1}{(\omega_{cv}^\sigma)^2} \left(\operatorname{Re} \left[r_{cv}^{\text{LDA,b}} \left(\mathcal{V}_{vc}^{\sigma,a,\ell} \right)_{;k^c} \right] + \frac{\operatorname{Re} \left[\mathcal{V}_{vc}^{\sigma,a,\ell} r_{cv}^{\text{LDA,b}} \right] \Delta_{cv}^c}{\omega_{cv}^\sigma} \right) \delta(\omega_{cv}^\sigma - \omega), \quad (\text{E17})$$

where again we added a 1/2 from the sum over $\mathbf{k} \rightarrow -\mathbf{k}$.

2. Interband Contributions

We follow the equivalent procedure for the interband contribution. From Eq. (77) we get

$$E = A \left[-\frac{1}{2\omega_{lm}^\sigma(2\omega_{lm}^\sigma - \omega_{nm}^\sigma)} \frac{1}{\omega_{lm}^\sigma - \tilde{\omega}} + \frac{2}{\omega_{nm}^\sigma(2\omega_{lm}^\sigma - \omega_{nm}^\sigma)} \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}} + \frac{1}{2\omega_{lm}^\sigma\omega_{nm}^\sigma} \frac{1}{\tilde{\omega}} \right] \\ - B \left[-\frac{1}{2\omega_{nl}^\sigma(2\omega_{nl}^\sigma - \omega_{nm}^\sigma)} \frac{1}{\omega_{nl}^\sigma - \tilde{\omega}} + \frac{2}{\omega_{nm}^\sigma(2\omega_{nl}^\sigma - \omega_{nm}^\sigma)} \frac{1}{\omega_{nm}^\sigma - 2\tilde{\omega}} + \frac{1}{2\omega_{nl}^\sigma\omega_{nm}^\sigma} \frac{1}{\tilde{\omega}} \right], \quad (\text{E18})$$

where $A = f_{ml}\mathcal{V}_{mn}^{\sigma,a}r_{nl}^c r_{lm}^b$ and $B = f_{ln}\mathcal{V}_{mn}^{\sigma,a}r_{nl}^b r_{lm}^c$.

Appendix F: Matrix elements of $\tau_{nm}^{ab}(\mathbf{k})$

To calculate τ_{nm}^{ab} , first we need to calculate

$$\mathcal{L}_{nm}^{ab}(\mathbf{k}) = \frac{1}{i\hbar} \langle n\mathbf{k} | [\hat{r}^a, \hat{v}^{nl,b}] | m\mathbf{k}' \rangle \delta(\mathbf{k} - \mathbf{k}') = \frac{1}{\hbar^2} \langle n\mathbf{k} | [\hat{r}^a, [\hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}'), \hat{r}^b]] | m\mathbf{k}' \rangle \delta(\mathbf{k} - \mathbf{k}'), \quad (\text{F1})$$

for which we need the following triple commutator

$$[\hat{r}^a, [\hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}'), \hat{r}^b]] = [\hat{r}^b, [\hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}'), \hat{r}^a]], \quad (\text{F2})$$

where the r.h.s follows from the Jacobi identity, since $[\hat{r}^a, \hat{r}^b] = 0$. We expand the triple commutator as,

$$[\hat{r}^a, [\hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}'), \hat{r}^b]] = [\hat{r}^a, \hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}') \hat{r}^b] - [\hat{r}^a, \hat{r}^b \hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}')] \\ = [\hat{r}^a, \hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}')] \hat{r}^b - \hat{r}^b [\hat{r}^a, \hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}')] \\ = \hat{r}^a \hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}') \hat{r}^b - \hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}') \hat{r}^a \hat{r}^b - \hat{r}^b \hat{r}^a \hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}') + \hat{r}^b \hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}') \hat{r}^a. \quad (\text{F3})$$

Then,

$$\frac{1}{\hbar^2} \langle n\mathbf{k} | [\hat{r}^a, [\hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}'), \hat{r}^b]] | m\mathbf{k}' \rangle = \frac{1}{\hbar^2} \int d\mathbf{r} d\mathbf{r}' \langle n\mathbf{k} | \mathbf{r} \rangle \langle \mathbf{r} | [\hat{r}^a, [\hat{V}^{nl}(\hat{\mathbf{r}}, \hat{\mathbf{r}}'), \hat{r}^b]] | \mathbf{r}' \rangle \langle \mathbf{r}' | m\mathbf{k}' \rangle \delta(\mathbf{k} - \mathbf{k}') \\ = \frac{1}{\hbar^2} \int d\mathbf{r} d\mathbf{r}' \psi_{n\mathbf{k}}^*(\mathbf{r}) \left(r^a V^{nl}(\mathbf{r}, \mathbf{r}') r'^b - V^{nl}(\mathbf{r}, \mathbf{r}') r'^a r'^b \right. \\ \left. - r^b r^a V^{nl}(\mathbf{r}, \mathbf{r}') + r^b V^{nl}(\mathbf{r}, \mathbf{r}') r'^a \right) \psi_{m\mathbf{k}}(\mathbf{r}') \delta(\mathbf{k} - \mathbf{k}') \\ = \frac{1}{\hbar^2 \Omega} \sum_{\mathbf{K}, \mathbf{K}'} C_{n\mathbf{k}}^*(\mathbf{K}) C_{m\mathbf{k}}(\mathbf{K}') \int d\mathbf{r} d\mathbf{r}' e^{-i\mathbf{K} \cdot \mathbf{r}} \left(r^a V^{nl}(\mathbf{r}, \mathbf{r}') r'^b - V^{nl}(\mathbf{r}, \mathbf{r}') r'^a r'^b \right. \\ \left. - r^b r^a V^{nl}(\mathbf{r}, \mathbf{r}') + r^b V^{nl}(\mathbf{r}, \mathbf{r}') r'^a \right) e^{i\mathbf{K}' \cdot \mathbf{r}'} \delta(\mathbf{k} - \mathbf{k}'). \quad (\text{F4})$$

We use the following identity

$$\begin{aligned}
& \left(\frac{\partial^2}{\partial K^a \partial K'^b} + \frac{\partial^2}{\partial K'^a \partial K^b} + \frac{\partial^2}{\partial K^a \partial K^b} + \frac{\partial^2}{\partial K^b \partial K'^a} \right) \int d\mathbf{r} d\mathbf{r}' e^{-i\mathbf{K} \cdot \mathbf{r}} V^{\text{nl}}(\mathbf{r}, \mathbf{r}') e^{i\mathbf{K}' \cdot \mathbf{r}'} \\
&= \int d\mathbf{r} d\mathbf{r}' e^{-i\mathbf{K} \cdot \mathbf{r}} \left(r^a V^{\text{nl}}(\mathbf{r}, \mathbf{r}') r'^b - V^{\text{nl}}(\mathbf{r}, \mathbf{r}') r'^a r'^b - r^b r^a V^{\text{nl}}(\mathbf{r}, \mathbf{r}') + r^b V^{\text{nl}}(\mathbf{r}, \mathbf{r}') r'^a \right) e^{i\mathbf{K}' \cdot \mathbf{r}'} \\
&= \left(\frac{\partial^2}{\partial K^a \partial K'^b} + \frac{\partial^2}{\partial K'^a \partial K^b} + \frac{\partial^2}{\partial K^a \partial K^b} + \frac{\partial^2}{\partial K^b \partial K'^a} \right) \langle \mathbf{K} | V^{\text{nl}} | \mathbf{K}' \rangle,
\end{aligned} \tag{F5}$$

to write

$$\mathcal{L}_{nm}^{\text{ab}}(\mathbf{k}) = \frac{1}{\hbar^2 \Omega} \sum_{\mathbf{K}, \mathbf{K}'} C_{n\mathbf{k}}^*(\mathbf{K}) C_{m\mathbf{k}}(\mathbf{K}') \left(\frac{\partial^2}{\partial K^a \partial K'^b} + \frac{\partial^2}{\partial K'^a \partial K^b} + \frac{\partial^2}{\partial K^a \partial K^b} + \frac{\partial^2}{\partial K^b \partial K'^a} \right) \langle \mathbf{K} | V^{\text{nl}} | \mathbf{K}' \rangle \tag{F6}$$

The double derivatives with respect to \mathbf{K} and \mathbf{K}' can be worked out as it is done in Appendix B to obtain the matrix elements of $[\hat{V}^{\text{nl}}(\hat{\mathbf{r}}, \hat{\mathbf{r}}'), \hat{r}^b]$,³⁷ and thus we could have the value of the matrix elements of the triple commutator.³²

With above results we can proceed to evaluate the matrix elements $\tau_{nm}(\mathbf{k})$. From Eq. (H1)

$$\begin{aligned}
\langle n\mathbf{k} | \tau^{\text{ab}} | m\mathbf{k}' \rangle &= \langle n\mathbf{k} | \frac{i\hbar}{m_e} \delta_{ab} | m\mathbf{k}' \rangle + \langle n\mathbf{k} | \frac{1}{i\hbar} [r^a, v^{\text{nl},b}] | m\mathbf{k}' \rangle \\
\mathcal{L}_{nm}^{\text{ab}}(\mathbf{k}) \delta(\mathbf{k} - \mathbf{k}') &= \delta(\mathbf{k} - \mathbf{k}') \left(\frac{i\hbar}{m_e} \delta_{ab} \delta_{nm} + \mathcal{L}_{nm}^{\text{ab}}(\mathbf{k}) \right) \\
\tau_{nm}^{\text{ab}}(\mathbf{k}) &= \tau_{nm}^{\text{ba}}(\mathbf{k}) = \frac{i\hbar}{m_e} \delta_{ab} \delta_{nm} + \mathcal{L}_{nm}^{\text{ab}}(\mathbf{k}),
\end{aligned} \tag{F7}$$

which is an explicit expression that can be numerically calculated.

Appendix G: Explicit expressions for $\mathcal{V}_{nm}^{a,\ell}(\mathbf{k})$ and $\mathcal{C}_{nm}^\ell(\mathbf{k})$

Expanding the wave function in plane waves we obtain

$$\psi_{n\mathbf{k}}(\mathbf{r}) = \sum_{\mathbf{G}} A_{n\mathbf{k}}(\mathbf{G}) e^{i(\mathbf{k}+\mathbf{G}) \cdot \mathbf{r}}, \tag{G1}$$

where $\{\mathbf{G}\}$ are the reciprocal basis vectors satisfying $e^{\mathbf{R} \cdot \mathbf{G}} = 1$, with $\{\mathbf{R}\}$ the translation vectors in real space, and $A_{n\mathbf{k}}(\mathbf{G})$ are the expansion coefficients. Using $m_e \mathbf{v} = -i\hbar \nabla$ into Eqs. (72) and (70) we obtain,²⁹

$$\mathcal{V}_{nm}^\ell(\mathbf{k}) = \frac{\hbar}{2m_e} \sum_{\mathbf{G}, \mathbf{G}'} A_{n\mathbf{k}}^*(\mathbf{G}') A_{m\mathbf{k}}(\mathbf{G}) (2\mathbf{k} + \mathbf{G} + \mathbf{G}') \delta_{\mathbf{G}_\parallel \mathbf{G}'_\parallel} f_\ell(G_\perp - G'_\perp), \tag{G2}$$

where

$$f_\ell(g) = \frac{1}{L} \int_{z_\ell - \Delta_\ell^b}^{z_\ell + \Delta_\ell^f} e^{igz} dz, \tag{G3}$$

where the reciprocal lattice vectors \mathbf{G} are decomposed into components parallel to the surface \mathbf{G}_{\parallel} , and perpendicular to the surface $G_{\perp}\hat{z}$, so that $\mathbf{G} = \mathbf{G}_{\parallel} + G_{\perp}\hat{z}$. Likewise we obtain that

$$\begin{aligned} \mathcal{C}_{nm}(\mathbf{k}) &= \int \psi_{n\mathbf{k}}^*(\mathbf{r}) f(z) \psi_{m\mathbf{k}}(\mathbf{r}) d\mathbf{r} \\ &= \sum_{\mathbf{G}, \mathbf{G}'} A_{n\mathbf{k}}^*(\mathbf{G}') A_{m\mathbf{k}}(\mathbf{G}) \int f(z) e^{-i(\mathbf{G}-\mathbf{G}')\cdot\mathbf{r}} \\ &= \sum_{\mathbf{G}, \mathbf{G}'} A_{n\mathbf{k}}^*(\mathbf{G}') A_{m\mathbf{k}}(\mathbf{G}) \underbrace{\int e^{-i(\mathbf{G}_{\parallel}-\mathbf{G}'_{\parallel})\cdot\mathbf{R}_{\parallel}} d\mathbf{R}_{\parallel}}_{\delta_{\mathbf{G}_{\parallel}\mathbf{G}'_{\parallel}}} \underbrace{\int e^{-i(g-g')z} f(z) dz}_{f_{\ell}(G_{\perp}-G'_{\perp})}, \end{aligned}$$

which we can express compactly as,

$$\mathcal{C}_{nm}^{\ell}(\mathbf{k}) = \sum_{\mathbf{G}, \mathbf{G}'} A_{n\mathbf{k}}^*(\mathbf{G}') A_{m\mathbf{k}}(\mathbf{G}) \delta_{\mathbf{G}_{\parallel}\mathbf{G}'_{\parallel}} f_{\ell}(G_{\perp} - G'_{\perp}). \quad (\text{G4})$$

The double summation over the \mathbf{G} vectors can be efficiently done by creating a pointer array to identify all the plane-wave coefficients associated with the same G_{\parallel} . We take z_{ℓ} at the center of an atom that belongs to layer ℓ , and thus above equations gives the ℓ -th atomic-layer contribution to the optical response.²⁹

If $\mathcal{C}^{\ell}(z) = 1$ from Eqs. (G2) and (G4) we recover the well known result

$$\begin{aligned} v_{nm}(\mathbf{k}) &= \frac{\hbar}{m_e} \sum_{\mathbf{G}} A_{n\mathbf{k}}^*(\mathbf{G}) A_{m\mathbf{k}}(\mathbf{G}) (\mathbf{k} + \mathbf{G}) \\ \mathcal{C}_{nm}^{\ell} &= \delta_{nm}, \end{aligned} \quad (\text{G5})$$

since for this case $f_{\ell}(g) = \delta_{g0}$.

We remark that $\mathbf{V}_{nm}^{\ell}(\mathbf{k})$ of Eq. (G2) does not contain the contribution coming from the scissors operator. As commented in the paragraph after Eq. (73) $\mathbf{V}_{nm}^{\sigma,\ell}(\mathbf{k}) \neq (\omega_{nm}^{\sigma}/\omega_{nm}) \mathbf{V}_{nm}^{\text{LDA},\ell}(\mathbf{k})$ and $\mathbf{V}_{nn}^{\sigma,\ell}(\mathbf{k}) \neq \mathbf{V}_{nn}^{\text{LDA},\ell}(\mathbf{k})$, relations that are correct whether or not the contribution of \mathbf{v}^{nl} is taken into account. Therefore, in order to take the scissors correction correctly, we must follow Appendix C.

1. Time-reversal relations

The following relations hold for time-reversal symmetry.

$$\begin{aligned} A_{n\mathbf{k}}^*(\mathbf{G}) &= A_{n-\mathbf{k}}(\mathbf{G}), \\ \mathbf{P}_{n\ell}(-\mathbf{k}) &= \hbar \sum_{\mathbf{G}} A_{n-\mathbf{k}}^*(\mathbf{G}) A_{\ell-\mathbf{k}}(\mathbf{G}) (-\mathbf{k} + \mathbf{G}), \end{aligned}$$

$$(\mathbf{G} \rightarrow -\mathbf{G}) = -\hbar \sum_{\mathbf{G}} A_{n\mathbf{k}}(\mathbf{G}) A_{\ell\mathbf{k}}^*(\mathbf{G})(\mathbf{k} + \mathbf{G}) = -\mathbf{P}_{\ell n}(\mathbf{k}),$$

$$\begin{aligned} \mathcal{C}_{nm}(L; -\mathbf{k}) &= \sum_{\mathbf{G}_{\parallel}, g, g'} A_{n-\mathbf{k}}^*(\mathbf{G}_{\parallel}, g) A_{m-\mathbf{k}}(\mathbf{G}_{\parallel}, g') f_{\ell}(g - g') \\ &= \sum_{\mathbf{G}_{\parallel}, g, g'} A_{n\mathbf{k}}(\mathbf{G}_{\parallel}, g) A_{m\mathbf{k}}^*(\mathbf{G}_{\parallel}, g') f_{\ell}(g - g') \\ &= \mathcal{C}_{mn}(L; \mathbf{k}). \end{aligned}$$

Appendix H: Generalized derivative $(\mathbf{r}_{nm}(\mathbf{k}))_{;\mathbf{k}}$ for non-local potentials

We obtain the generalized derivative $(\mathbf{r}_{nm}(\mathbf{k}))_{;\mathbf{k}}$ for the case of a non-local potential in the Hamiltonian. We start from (see Eq. (26))

$$[r^a, v^{\text{LDA},b}] = [r^a, v^b] + [r^a, v^{\text{nl},b}] = \frac{i\hbar}{m_e} \delta_{ab} + [r^a, v^{\text{nl},b}] \equiv \tau^{\text{ab}}, \quad (\text{H1})$$

where we used the fact that $[r^a, p^b] = i\hbar \delta_{ab}$. Then,

$$\langle n\mathbf{k} | [r^a, v^{\text{LDA},b}] | m\mathbf{k}' \rangle = \langle n\mathbf{k} | \tau^{\text{ab}} | m\mathbf{k}' \rangle = \tau_{nm}^{\text{ab}}(\mathbf{k}) \delta(\mathbf{k} - \mathbf{k}'), \quad (\text{H2})$$

so

$$\langle n\mathbf{k} | [r_i^a, v^{\text{LDA},b}] | m\mathbf{k}' \rangle + \langle n\mathbf{k} | [r_e^a, v^{\text{LDA},b}] | m\mathbf{k}' \rangle = \tau_{nm}^{\text{ab}}(\mathbf{k}) \delta(\mathbf{k} - \mathbf{k}'), \quad (\text{H3})$$

where the matrix elements of $\tau_{nm}^{\text{ab}}(\mathbf{k})$ are calculated in Appendix F. From Eq. (A18) and (A19)

$$\langle n\mathbf{k} | [r_i^a, v_{\text{LDA}}^b] | m\mathbf{k}' \rangle = i\delta(\mathbf{k} - \mathbf{k}') (v_{nm}^{\text{LDA},b})_{;k^a} \quad (\text{H4})$$

$$(v_{nm}^{\text{LDA},b})_{;k^a} = \nabla_{k^a} v_{nm}^{\text{LDA},b}(\mathbf{k}) - i v_{nm}^{\text{LDA},b}(\mathbf{k}) (\xi_{nn}^a(\mathbf{k}) - \xi_{mm}^a(\mathbf{k})), \quad (\text{H5})$$

and

$$\begin{aligned}
\langle n\mathbf{k} | [r_e^a, v^{\text{LDA,b}}] | m\mathbf{k}' \rangle &= \sum_{\ell\mathbf{k}''} \left(\langle n\mathbf{k} | r_e^a | \ell\mathbf{k}'' \rangle \langle \ell\mathbf{k}'' | v^{\text{LDA,b}} | m\mathbf{k}' \rangle \right. \\
&\quad \left. - \langle n\mathbf{k} | v^{\text{LDA,b}} | \ell\mathbf{k}'' \rangle \langle \ell\mathbf{k}'' | r_e^a | m\mathbf{k}' \rangle \right) \\
&= \sum_{\ell\mathbf{k}''} \left((1 - \delta_{n\ell}) \delta(\mathbf{k} - \mathbf{k}'') \xi_{n\ell}^a \delta(\mathbf{k}'' - \mathbf{k}') v_{\ell m}^{\text{LDA,b}} \right. \\
&\quad \left. - \delta(\mathbf{k} - \mathbf{k}'') v_{n\ell}^{\text{LDA,b}} (1 - \delta_{\ell m}) \delta(\mathbf{k}'' - \mathbf{k}') \xi_{\ell m}^a \right) \\
&= \delta(\mathbf{k} - \mathbf{k}') \sum_{\ell} \left((1 - \delta_{n\ell}) \xi_{n\ell}^a v_{\ell m}^{\text{LDA,b}} \right. \\
&\quad \left. - (1 - \delta_{\ell m}) v_{n\ell}^{\text{LDA,b}} \xi_{\ell m}^a \right) \\
&= \delta(\mathbf{k} - \mathbf{k}') \left(\sum_{\ell} \left(\xi_{n\ell}^a v_{\ell m}^{\text{LDA,b}} - v_{n\ell}^{\text{LDA,b}} \xi_{\ell m}^a \right) \right. \\
&\quad \left. + v_{nm}^{\text{LDA,b}} (\xi_{mm}^a - \xi_{nn}^a) \right). \tag{H6}
\end{aligned}$$

Using Eqs. (H4) and (H6) into Eq. (H3) gives

$$\begin{aligned}
i\delta(\mathbf{k} - \mathbf{k}') \left((v_{nm}^{\text{LDA,b}})_{;k^a} - i \sum_{\ell} \left(\xi_{n\ell}^a v_{\ell m}^{\text{LDA,b}} - v_{n\ell}^{\text{LDA,b}} \xi_{\ell m}^a \right) \right. \\
\left. - i v_{nm}^{\text{LDA,b}} (\xi_{mm}^a - \xi_{nn}^a) \right) = \tau_{nm}^{\text{ab}}(\mathbf{k}) \delta(\mathbf{k} - \mathbf{k}'), \tag{H7}
\end{aligned}$$

then

$$(v_{nm}^{\text{LDA,b}})_{;k^a} = -i\tau_{nm}^{\text{ab}} + i \sum_{\ell} \left(\xi_{n\ell}^a v_{\ell m}^{\text{LDA,b}} - v_{n\ell}^{\text{LDA,b}} \xi_{\ell m}^a \right) + i v_{nm}^{\text{LDA,b}} (\xi_{mm}^a - \xi_{nn}^a), \tag{H8}$$

and from Eq. (H5),

$$\nabla_{k^a} v_{nm}^{\text{LDA,b}} = -i\tau_{nm}^{\text{ab}} + i \sum_{\ell} \left(\xi_{n\ell}^a v_{\ell m}^{\text{LDA,b}} - v_{n\ell}^{\text{LDA,b}} \xi_{\ell m}^a \right). \tag{H9}$$

Now, there are two cases. We use Eq. (31).

Case $n = m$

$$\begin{aligned}
\nabla_{k^a} v_{nn}^{\text{LDA,b}} &= -i\tau_{nn}^{\text{ab}} + i \sum_{\ell} \left(\xi_{n\ell}^a v_{\ell n}^{\text{LDA,b}} - v_{n\ell}^{\text{LDA,b}} \xi_{\ell n}^a \right) \\
&= -i\tau_{nn}^{\text{ab}} - \sum_{\ell \neq n} \left(r_{n\ell}^a \omega_{\ell n}^{\text{LDA,b}} r_{\ell n}^b - \omega_{n\ell}^{\text{LDA,b}} r_{n\ell}^b r_{\ell n}^a \right) \\
&= -i\tau_{nn}^{\text{ab}} - \sum_{\ell \neq n} \omega_{\ell n}^{\text{LDA}} \left(r_{n\ell}^a r_{\ell n}^b - r_{n\ell}^b r_{\ell n}^a \right), \tag{H10}
\end{aligned}$$

since the $\ell = n$ cancels out. This would give the generalization for the inverse effective mass tensor $(m_n^{-1})_{ab}$ for nonlocal potentials. Indeed, if we neglect the commutator of \mathbf{v}^{nl} in Eq. (H1), we obtain $-i\tau_{nn}^{\text{ab}} = \hbar/m_e\delta_{ab}$ thus obtaining the familiar expression of $(m_n^{-1})_{ab}$.³³

Case $n \neq m$

$$\begin{aligned}
(v_{nm}^{\text{LDA,b}})_{;k^a} &= -i\tau_{nm}^{\text{ab}} + i \sum_{\ell \neq m \neq n} \left(\xi_{n\ell}^a v_{\ell m}^{\text{LDA,b}} - v_{n\ell}^{\text{LDA,b}} \xi_{\ell m}^a \right) \\
&\quad + i \left(\xi_{nm}^a v_{mm}^{\text{LDA,b}} - v_{nm}^{\text{LDA,b}} \xi_{mm}^a \right) \\
&\quad + i \left(\xi_{nn}^a v_{nm}^{\text{LDA,b}} - v_{nn}^{\text{LDA,b}} \xi_{nm}^a \right) + i v_{nm}^{\text{LDA,b}} (\xi_{mm}^a - \xi_{nn}^a) \\
&= -i\tau_{nm}^{\text{ab}} - \sum_{\ell} \left(\omega_{\ell m}^{\text{LDA}} r_{n\ell}^a r_{\ell m}^b - \omega_{n\ell}^{\text{LDA}} r_{n\ell}^b r_{\ell m}^a \right) + i \xi_{nm}^a (v_{mm}^{\text{LDA,b}} - v_{nn}^{\text{LDA,b}}) \\
&= -i\tau_{nm}^{\text{ab}} - \sum_{\ell} \left(\omega_{\ell m}^{\text{LDA}} r_{n\ell}^a r_{\ell m}^b - \omega_{n\ell}^{\text{LDA}} r_{n\ell}^b r_{\ell m}^a \right) + i r_{nm}^a \Delta_{mn}^b, \tag{H11}
\end{aligned}$$

where we use Δ_{mn}^a of Eq. (79). Now, for $n \neq m$, Eqs. (31), (D9) and (H11) and the chain rule, give

$$\begin{aligned}
(r_{nm}^b)_{;k^a} &= \left(\frac{v_{nm}^{\text{LDA,b}}}{i\omega_{nm}^{\text{LDA}}} \right)_{;k^a} = \frac{1}{i\omega_{nm}^{\text{LDA}}} (v_{nm}^{\text{LDA,b}})_{;k^a} - \frac{v_{nm}^{\text{LDA,b}}}{i(\omega_{nm}^{\text{LDA}})^2} (\omega_{nm}^{\text{LDA}})_{;k^a} \\
&= -i\tau_{nm}^{\text{ab}} + \frac{i}{\omega_{nm}^{\text{LDA}}} \sum_{\ell} \left(\omega_{\ell m}^{\text{LDA}} r_{n\ell}^a r_{\ell m}^b - \omega_{n\ell}^{\text{LDA}} r_{n\ell}^b r_{\ell m}^a \right) + \frac{r_{nm}^a \Delta_{mn}^b}{\omega_{nm}^{\text{LDA}}} \\
&\quad - \frac{r_{nm}^b}{\omega_{nm}^{\text{LDA}}} (\omega_{nm}^{\text{LDA}})_{;k^a} \\
&= -i\tau_{nm}^{\text{ab}} + \frac{i}{\omega_{nm}^{\text{LDA}}} \sum_{\ell} \left(\omega_{\ell m}^{\text{LDA}} r_{n\ell}^a r_{\ell m}^b - \omega_{n\ell}^{\text{LDA}} r_{n\ell}^b r_{\ell m}^a \right) + \frac{r_{nm}^a \Delta_{mn}^b}{\omega_{nm}^{\text{LDA}}} \\
&\quad - \frac{r_{nm}^b v_{nn}^{\text{LDA,a}} - v_{mm}^{\text{LDA,a}}}{\omega_{nm} m_e} \\
&= -i\tau_{nm}^{\text{ab}} + \frac{r_{nm}^a \Delta_{mn}^b + r_{nm}^b \Delta_{mn}^a}{\omega_{nm}^{\text{LDA}}} + \frac{i}{\omega_{nm}^{\text{LDA}}} \sum_{\ell} \left(\omega_{\ell m}^{\text{LDA}} r_{n\ell}^a r_{\ell m}^b - \omega_{n\ell}^{\text{LDA}} r_{n\ell}^b r_{\ell m}^a \right), \tag{H12}
\end{aligned}$$

where the $-i\tau_{nm}^{\text{ab}}$ term, generalizes the usual expression of $\mathbf{r}_{nm;\mathbf{k}}$ for local Hamiltonians,^{14,31,36,38} to the case of a nonlocal potential in the Hamiltonian.

1. Layer Case

To obtain the generalized derivative expressions for the case of the layered matrix elements ar required by Eq. (71), we could start form Eq. (H1) again, and replace $\hat{\mathbf{v}}^{\text{LDA}}$ by \mathbf{v}^{LDA} , to obtain the equivalent of Eqs. (H10) and (H11), for which we need to calculate the new τ_{nm}^{ab} , that is given

by

$$\begin{aligned}
\mathcal{T}_{nm}^{\text{ab}} &= [r^{\text{a}}, \mathcal{V}^{\text{LDA,b}}]_{nm} = [r^{\text{a}}, \mathcal{V}^{\text{b}}]_{nm} + [r^{\text{a}}, \mathcal{V}^{\text{nl,b}}]_{nm} \\
&= \frac{1}{2} [r^{\text{a}}, v^{\text{b}} C^\ell(z) + C^\ell(z) v^{\text{b}}]_{nm} + \frac{1}{2} [r^{\text{a}}, v^{\text{nl,b}} C^\ell(z) + C^\ell(z) v^{\text{nl,b}}]_{nm} \\
&= \left([r^{\text{a}}, v^{\text{b}}] C^\ell(z) \right)_{nm} + \left([r^{\text{a}}, v^{\text{nl,b}}] C^\ell(z) \right)_{nm} \\
&= \sum_p [r^{\text{a}}, v^{\text{b}}]_{np} C_{pm}^\ell + \sum_p [r^{\text{a}}, v^{\text{nl,b}}]_{np} C_{pm}^\ell \\
&= \frac{i\hbar}{m_e} \delta_{\text{ab}} C_{nm}^\ell + \sum_p [r^{\text{a}}, v^{\text{nl,b}}]_{np} C_{pm}^\ell.
\end{aligned} \tag{H13}$$

For a full-slab calculation, that would correspond to a bulk calculation as well, $C^\ell(z) = 1$ and then, $C_{nm}^\ell = \delta_{nm}$, and from above expression $\mathcal{T}_{nm}^{\text{ab}} \rightarrow \tau_{nm}^{\text{ab}}$. Thus, the layered expression for $\mathcal{V}_{nm}^{\text{LDA,a}}$ becomes

$$(\mathcal{V}_{nm}^{\text{LDA,a}})_{;k^{\text{b}}} = \frac{\hbar}{m_e} \delta_{\text{ab}} C_{nm}^\ell - i \sum_p [r^{\text{b}}, v^{\text{nl,a}}]_{np} C_{pm}^\ell + i \sum_\ell \left(r_{n\ell}^{\text{b}} \mathcal{V}_{\ell m}^{\text{LDA,a}} - \mathcal{V}_{n\ell}^{\text{LDA,a}} r_{\ell m}^{\text{b}} \right) + i r_{nm}^{\text{b}} \tilde{\Delta}_{mn}^{\text{a}}, \tag{H14}$$

where

$$\tilde{\Delta}_{mn}^{\text{a}} = \mathcal{V}_{nn}^{\text{LDA,a}} - \mathcal{V}_{mm}^{\text{LDA,a}}. \tag{H15}$$

As mentioned before, the term $[r^{\text{b}}, v^{\text{nl,a}}]_{nm}$ calculated in Appendix F, is small compared to the other terms, thus we neglect it throughout this work.³² The expression for C_{nm}^ℓ is calculated in Appendix G.

Appendix I: Coding

In this Appendix we reproduce all the quantities that should be coded.

Eqs. (II), (I3), (I2) and (I4)

$$\text{Im}[\chi_{e,\text{abc},\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{c}\mathbf{k}} \sum_{l \neq (v,c)} \frac{1}{\omega_{cv}^\sigma} \left[\frac{\text{Im}[\mathcal{V}_{lc}^{\sigma,\text{a},\ell} \{r_{cv}^{\text{b}} r_{vl}^{\text{c}}\}]}{(2\omega_{cv}^\sigma - \omega_{cl}^\sigma)} - \frac{\text{Im}[\mathcal{V}_{vl}^{\sigma,\text{a},\ell} \{r_{lc}^{\text{c}} r_{cv}^{\text{b}}\}]}{(2\omega_{cv}^\sigma - \omega_{lv}^\sigma)} \right] \delta(\omega_{cv}^\sigma - \omega), \tag{I1}$$

$$\text{Im}[\chi_{i,\text{abc},\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{cv\mathbf{k}} \frac{1}{(\omega_{cv}^\sigma)^2} \left[\text{Re} \left[\left\{ r_{cv}^{\text{b}} \left(\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \right)_{;k^{\text{c}}} \right\} \right] + \frac{\text{Re} \left[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \{r_{cv}^{\text{b}} \Delta_{cv}^{\text{c}}\} \right]}{\omega_{cv}^\sigma} \right] \delta(\omega_{cv}^\sigma - \omega), \tag{I2}$$

$$\text{Im}[\chi_{e,\text{abc},2\omega}^{s,\ell}] = -\frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{c}\mathbf{k}} \frac{4}{\omega_{cv}^\sigma} \left[\sum_{v' \neq v} \frac{\text{Im}[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \{r_{cv'}^{\text{b}} r_{v'v}^{\text{c}}\}]}{2\omega_{cv'}^\sigma - \omega_{cv}^\sigma} - \sum_{c' \neq c} \frac{\text{Im}[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \{r_{cc'}^{\text{c}} r_{c'v}^{\text{b}}\}]}{2\omega_{c'v}^\sigma - \omega_{cv}^\sigma} \right] \delta(\omega_{cv}^\sigma - 2\omega), \tag{I3}$$

and

$$\text{Im}[\chi_{i,\text{abc},2\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{k}} \frac{4}{(\omega_{cv}^\sigma)^2} \left[\text{Re} \left[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \left\{ \left(r_{cv}^{\text{b}} \right)_{;k^c} \right\} \right] - \frac{2\text{Re} \left[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \{ r_{cv}^{\text{b}} \Delta_{cv}^{\text{c}} \} \right]}{\omega_{cv}^\sigma} \right] \delta(\omega_{cv}^\sigma - 2\omega), \quad (\text{I4})$$

- Coding: $\mathcal{V}_{nm}^{\sigma,\text{a},\ell} \rightarrow \text{calVsig}$, $r_{nm}^{\text{a}} \rightarrow \text{posMatElem}$, $(\mathcal{V}_{nm}^{\sigma,\text{a},\ell})_{;k^{\text{b}}} \rightarrow \text{gdcalVsig}$,
 $(r_{nm}^{\text{a}})_{;k^{\text{b}}} \rightarrow \text{derMatElem}$ $\Delta_{nm}^{\text{a}} \rightarrow \text{Delta}$ and $\omega_n^\sigma \rightarrow \text{band}(\mathbf{n})$
- proof:

To evaluate above expressions we need the following ($m_e = 1$):

$$\mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k}) = (1/m_e)\mathbf{p}_{nm}(\mathbf{k}) + \mathbf{v}_{nm}^{\text{nl}}(\mathbf{k}) = \mathbf{p}_{nm}(\mathbf{k}) + \mathbf{v}_{nm}^{\text{nl}}(\mathbf{k}), \quad (\text{I5})$$

that includes the local and nonlocal parts of the pseudopotential. They correspond to the following files:

- $\mathbf{p}_{nm}(\mathbf{k}) \rightarrow \text{me_pmn_*}$
- $\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k}) \rightarrow \text{me_vnlnm_*}$

where the `nm` or `mn` order in the files is irrelevant, and ought to be fixed just for the *biuty* of it.

Option `-n` in `all_responses.sh` does

1. `> cp me_pmn_* me_pmn_*.o`
2. adds `me_pmn_*` and `me_vnlnm_*` into `me_pmn_*`
3. calculates the response
4. `> mv me_pmn_*.o me_pmn_*`

so $\mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k})$, stored in `vldaMatElem` is available for the calculation of the response, and with it we calculate (Eqs. (29) and (30)),

$$\begin{aligned} \mathbf{v}_{nm}^\sigma(\mathbf{k}) &= \left(1 + \frac{\Sigma}{\omega_c(\mathbf{k}) - \omega_v(\mathbf{k})} \right) \mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k}) \quad n \notin D_m \\ \mathbf{v}_{nn}^\sigma(\mathbf{k}) &= \mathbf{v}_{nn}^{\text{LDA}}(\mathbf{k}) \\ \mathbf{r}_{nm}(\mathbf{k}) &= \frac{\mathbf{v}_{nm}^\sigma(\mathbf{k})}{i\omega_{nm}^\sigma(\mathbf{k})} = \frac{\mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k})}{i\omega_{nm}^{\text{LDA}}(\mathbf{k})} \quad n \notin D_m. \end{aligned} \quad (\text{I6})$$

If option `-n` is not chosen, then the contribution of $\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k})$ is neglected in the calculation of any response. Obviously, in this case the code only uses `me_pmn_*` without adding `me_vnlnm_*`

We need Eq. (C1) and (C2)

$$\begin{aligned} \mathcal{V}_{nm}^{\sigma,a,\ell} &= \mathcal{V}_{nm}^{\text{LDA},a,\ell} + \mathcal{V}_{nm}^{\mathcal{S},a,\ell} \\ \left(\mathcal{V}_{nm}^{\sigma,a,\ell} \right)_{;k^b} &= \left(\mathcal{V}_{nm}^{\text{LDA},a,\ell} \right)_{;k^b} + \left(\mathcal{V}_{nm}^{\mathcal{S},a,\ell} \right)_{;k^b}. \end{aligned} \quad (\text{I7})$$

The first LDA term is

$$\mathcal{V}_{nm}^{\text{LDA},a,\ell} = \frac{1}{2} \sum_q \left(v_{nq}^{\text{LDA},a} \mathcal{C}_{qm}^\ell + \mathcal{C}_{nq}^\ell v_{qm}^{\text{LDA},a} \right). \quad (\text{I8})$$

If option `-n` is not chosen in `all_responses.sh` Eq. (I8) is not calculated and

- $\mathcal{V}_{nm}^{\text{LDA},a,\ell} \rightarrow \text{me_cpmn_}$ *

If option `-n` is chosen Eq. (I8) must be calculated as given in `set_input_ascii.f90`. We mention that $\mathcal{V}_{nm}^{\text{LDA},a,\ell}$ can be computed directly,³⁹ avoiding the sum over the full set of bands q , however we chose to compute Eq. (I8), which is done in `functions.f90` under the name `calVlda`. Then, we need Eq. (G4)

$$\begin{aligned} \mathcal{C}_{nm}^\ell(\mathbf{k}) &= \sum_{\mathbf{G}, \mathbf{G}'} A_{n\mathbf{k}}^*(\mathbf{G}') A_{m\mathbf{k}}(\mathbf{G}) \delta_{\mathbf{G} \parallel \mathbf{G}'} f_\ell(G_\perp - G'_\perp) \\ \mathcal{C}_{mn}^\ell(\mathbf{k}) &= (\mathcal{C}_{nm}^\ell(\mathbf{k}))^*, \end{aligned} \quad (\text{I9})$$

which is coded in `sub_pmn_ascii.f90` within the same subroutine of \mathcal{V}_{nm}^ℓ calculated with Eq. (G2). However, Sean out of the blue, call it `me_cfmn_*` in `run_tiniba.sh`, and Darwin won (what else? ID??), thus I call it `cfMatElem` in `SRC_1setinput`. ID would call it `ccMatElem` but long live CD!

The second LDA term is

$$\left(\mathcal{V}_{nm}^{\text{LDA},a,\ell} \right)_{;k^b} = \frac{1}{2} \sum_q \left((v_{nq}^{\text{LDA},a})_{;k^b} \mathcal{C}_{qm}^\ell + v_{nq}^{\text{LDA},a} (\mathcal{C}_{qm}^\ell)_{;k^b} + (\mathcal{C}_{nq}^\ell)_{;k^b} v_{qm}^{\text{LDA},a} + \mathcal{C}_{nq}^\ell (v_{qm}^{\text{LDA},a})_{;k^b} \right), \quad (\text{I10})$$

where

- for $n \neq m$

Eq. (C3)

$$\begin{aligned} (v_{nm}^{\text{LDA},a})_{;k^b} &= im_e \left(\Delta_{nm}^b r_{nm}^a + \omega_{nm}^{\text{LDA}} (r_{nm}^a)_{;k^b} \right) \\ (v_{mn}^{\text{LDA},a})_{;k^b} &= ((v_{nm}^{\text{LDA},a})_{;k^b})^* \quad \text{for } n \neq m, \end{aligned} \quad (\text{I11})$$

with Eq. (79)

$$\Delta_{nm}^a = v_{nn}^{\text{LDA},a} - v_{mm}^{\text{LDA},a}, \quad (\text{I12})$$

and (H12)

$$\begin{aligned}
(r_{nm}^b)_{;k^a} &= -i\mathcal{T}_{nm}^{ab} + \frac{r_{nm}^a \Delta_{mn}^b + r_{nm}^b \Delta_{mn}^a}{\omega_{nm}^{\text{LDA}}} + \frac{i}{\omega_{nm}^{\text{LDA}}} \sum_{\ell} \left(\omega_{\ell m}^{\text{LDA}} r_{n\ell}^a r_{\ell m}^b - \omega_{n\ell}^{\text{LDA}} r_{n\ell}^b r_{\ell m}^a \right) \\
&\approx \frac{r_{nm}^a \Delta_{mn}^b + r_{nm}^b \Delta_{mn}^a}{\omega_{nm}^{\text{LDA}}} + \frac{i}{\omega_{nm}^{\text{LDA}}} \sum_{\ell} \left(\omega_{\ell m}^{\text{LDA}} r_{n\ell}^a r_{\ell m}^b - \omega_{n\ell}^{\text{LDA}} r_{n\ell}^b r_{\ell m}^a \right) \\
(r_{mn}^b)_{;k^a} &= \left((r_{nm}^b)_{;k^a} \right)^*,
\end{aligned} \tag{I13}$$

where $\mathcal{T}_{nm}^{ab} \approx 0$.

- for $n = m$

Since $\mathcal{T}_{nn}^{ab} \approx (\hbar/m_e)\delta_{ab}$, Eq. (90) gives

$$\begin{aligned}
(v_{nn}^{\text{LDA},a})_{;k^b} &= -i\mathcal{T}_{nn}^{ab} - \sum_{\ell \neq n} \omega_{\ell n}^{\text{LDA}} \left(r_{n\ell}^a r_{\ell n}^b + r_{n\ell}^b r_{\ell n}^a \right) \\
&\approx \frac{\hbar}{m_e} \delta_{ab} - \sum_{\ell \neq n} \omega_{\ell n}^{\text{LDA}} \left(r_{n\ell}^a r_{\ell n}^b + r_{n\ell}^b r_{\ell n}^a \right).
\end{aligned} \tag{I14}$$

For Eq. (I10) we need (C9)

$$\begin{aligned}
(\mathcal{C}_{nm}^{\ell})_{;k^a} &= i \sum_{q \neq nm} \left(r_{nq}^a \mathcal{C}_{qm}^{\ell} - \mathcal{C}_{nq}^{\ell} r_{qm}^a \right) + i r_{nm}^a (\mathcal{C}_{mm}^{\ell} - \mathcal{C}_{nn}^{\ell}) \\
(\mathcal{C}_{mn}^{\ell})_{;\mathbf{k}} &= \left((\mathcal{C}_{nm}^{\ell})_{;\mathbf{k}} \right)^*.
\end{aligned} \tag{I15}$$

For the scissor related term we have: Eq. (C4), (C5) and (27)

$$\begin{aligned}
\nu_{nm}^{\mathcal{S},a,\ell} &= \frac{1}{2} \sum_q \left(v_{nq}^{\mathcal{S},a} \mathcal{C}_{qm}^{\ell} + \mathcal{C}_{nq}^{\ell} v_{qm}^{\mathcal{S},a} \right) \\
\left(\nu_{nm}^{\mathcal{S},a,\ell} \right)_{;k^b} &= \frac{1}{2} \sum_q \left((v_{nq}^{\mathcal{S},a})_{;k^b} \mathcal{C}_{qm}^{\ell} + v_{nq}^{\mathcal{S},a} (\mathcal{C}_{qm}^{\ell})_{;k^b} + (\mathcal{C}_{nq}^{\ell})_{;k^b} v_{qm}^{\mathcal{S},a} + \mathcal{C}_{nq}^{\ell} (v_{qm}^{\mathcal{S},a})_{;k^b} \right),
\end{aligned} \tag{I16}$$

with Eqs. (27) and (C5)

$$v_{nm}^{\mathcal{S},a} = i\Sigma f_{mn} r_{nm}^a, \tag{I17}$$

$$(v_{nm}^{\mathcal{S},a})_{;k^b} = i\Sigma f_{mn} (r_{nm}^a)_{;k^b}, \tag{I18}$$

where $\hbar\Sigma$ is the scissors correction. Notice that $v_{nn}^{\mathcal{S},a} = 0$ and $(v_{nn}^{\mathcal{S},a})_{;k^b} = 0$. Substituting Eq. (I17) into (I16), we obtain

$$\nu_{nm}^{\mathcal{S},a,\ell} = \frac{i\Sigma}{2} \sum_q \left(f_{qn} r_{nq}^a \mathcal{C}_{qm}^{\ell} + f_{mq} \mathcal{C}_{nq}^{\ell} r_{qm}^a \right), \tag{I19}$$

- Coding: `functions.f90` array `calVscissors` where f_n is coded in `set_input_ascii.f90`

Notice that $q = n$ and $q = m$ give zero contribution from the f_{nm} factors, but we set in the code $r_{nn}^a = 0$ so the program would not complain that such values of the array `posMatElem` do not exist, since actually, the diagonal elements do not exist. Explicitly (although, we don't code them),

$$\begin{aligned}\mathcal{V}_{vc}^{S,a,\ell} &= -\frac{i\Sigma}{2} \left[\sum_{v'} r_{vv'}^a C_{v'c}^\ell + \sum_{c'} C_{vc'}^\ell r_{c'c}^a \right], \\ \mathcal{V}_{cv}^{S,a,\ell} &= \frac{i\Sigma}{2} \left[\sum_{v'} r_{cv'}^a C_{v'v}^\ell + \sum_{c'} C_{cc'}^\ell r_{c'v}^a \right], \\ \mathcal{V}_{cv}^{S,a,\ell} &= (\mathcal{V}_{vc}^{S,a,\ell})^*\end{aligned}\tag{I20}$$

and

$$\mathcal{V}_{cc}^{S,a,\ell} = -\Sigma \sum_v \text{Im} \left[r_{cv}^a C_{vc}^\ell \right], \tag{I21}$$

$$\mathcal{V}_{vv}^{S,a,\ell} = \Sigma \sum_c \text{Im} \left[r_{vc}^a C_{cv}^\ell \right], \tag{I22}$$

where the last two are real functions as they must, since they are velocities.

Substituting Eqs. (I17) and (I18) into (I16), we obtain

$$\begin{aligned}\left(\mathcal{V}_{nm}^{S,a,\ell} \right)_{;k^b} &= \frac{i\Sigma}{2} \sum_q \left(f_{qn} \left[(r_{nq}^a)_{;k^b} C_{qm}^\ell + r_{nq}^a (C_{qm}^\ell)_{;k^b} \right] + f_{mq} \left[(C_{nq}^\ell)_{;k^b} r_{qm}^a + C_{nq}^\ell (r_{qm}^a)_{;k^b} \right] \right) \\ \left(\mathcal{V}_{mn}^{S,a,\ell} \right)_{;k^b} &= \left(\left(\mathcal{V}_{nm}^{S,a,\ell} \right)_{;k^b} \right)^*,\end{aligned}\tag{I23}$$

- Coding:

$(r_{nm}^a)_{;k^b} \rightarrow \text{derMatElem } C_{nm}^\ell \rightarrow \text{cfMatElem } r_{nm}^a \rightarrow \text{posMatElem } (C_{nm}^\ell)_{;k^b} \rightarrow \text{gdf}$, and
 $\left(\mathcal{V}_{nm}^{S,a,\ell} \right)_{;k^b} \rightarrow \text{gdcalVS}$

Also

$$\begin{aligned}\left(\mathcal{V}_{cv}^{S,a,\ell} \right)_{;k^b} &= \frac{i\Sigma}{2} \left(\sum_{v'} \left((r_{cv'}^a)_{;k^b} C_{v'v}^\ell + r_{cv'}^a (C_{v'v}^\ell)_{;k^b} \right) + \sum_{c'} \left((C_{cc'}^\ell)_{;k^b} r_{c'v}^a + C_{cc'}^\ell (r_{c'v}^a)_{;k^b} \right) \right) \\ \left(\mathcal{V}_{vc}^{S,a,\ell} \right)_{;k^b} &= \left(\left(\mathcal{V}_{cv}^{S,a,\ell} \right)_{;k^b} \right)^*,\end{aligned}\tag{I24}$$

$$\left(\mathcal{V}_{cc}^{S,a,\ell} \right)_{;k^b} = -\Sigma \sum_v \text{Im} \left[(r_{cv}^a)_{;k^b} C_{vc}^\ell + r_{cv}^a (C_{vc}^\ell)_{;k^b} \right], \tag{I25}$$

and

$$\left(\mathcal{V}_{vv}^{S,a,\ell} \right)_{;k^b} = \Sigma \sum_c \text{Im} \left[(r_{vc}^a)_{;k^b} C_{cv}^\ell + r_{vc}^a (C_{cv}^\ell)_{;k^b} \right]. \tag{I26}$$

1. Coding for $\mathcal{V}_{nm}^{\sigma,a,\ell}(\mathbf{k})$

Recall that $\mathcal{V}_{mn}^{\text{LDA},a,\ell} = (\mathcal{V}_{nm}^{\text{LDA},a,\ell})^*$ and $\mathcal{V}_{mn}^{\mathcal{S},a,\ell} = (\mathcal{V}_{nm}^{\mathcal{S},a,\ell})^*$

- If `-n` option is chosen in `all_responses.sh`

– $\mathcal{V}_{nm}^{\text{LDA},a,\ell}$, comes from Eq. (I8), coded in `functions.f90` as `calVlda`

- If `-n` option is NOT chosen in `all_responses.sh`

– $\mathcal{V}_{nm}^{\text{LDA},a,\ell}$ is used from `me_cpmn_*` which is Eq. (G2) and is coded in `sub_pmn_ascii.f90`

For either case

- $\mathcal{V}_{nm}^{\mathcal{S},a,\ell}$ is obtained from Eqs. (I20), (I21) or (I22), depending on nm . This is coded in `functions.f90` and used in `set_input_ascii.f90`

Thus,

- $\mathcal{V}_{nm}^{\sigma,a,\ell}(\mathbf{k}) = \mathcal{V}_{nm}^{\text{LDA},a,\ell}(\mathbf{k}) + \mathcal{V}_{nm}^{\mathcal{S},a,\ell}(\mathbf{k})$

is stored in `calMomMatElem` array, constructed in `set_input_ascii.f90`, and used in `SRC_2latm` for integrating the response function. A brave young soul, should change `calMomMatElem` to `calVelMatElem` in order to have a more appropriate name. But as good old DNA, we construct upon available ATGC; using the old structure, adding functionality and keeping all the useless non-codifying crap, thus making Darwin proud of us!

2. $\Delta_{nm}^{\sigma,a,\ell}(\mathbf{k})$

$\Delta_{nm}^{\sigma,a,\ell}(\mathbf{k})$ is given by

$$\Delta_{nm}^{\sigma,a,\ell}(\mathbf{k}) = \mathcal{V}_{nn}^{\sigma,a,\ell}(\mathbf{k}) - \mathcal{V}_{mm}^{\sigma,a,\ell}(\mathbf{k}) \quad (\text{I27})$$

$$\begin{aligned} \Delta_{nm}^{\sigma,a}(\mathbf{k}) &= v_{nn}^{\sigma,a,\ell}(\mathbf{k}) - v_{mm}^{\sigma,a,\ell}(\mathbf{k}) \\ &= v_{nn}^{\text{LDA},a,\ell}(\mathbf{k}) - v_{mm}^{\text{LDA},a,\ell}(\mathbf{k}), \end{aligned} \quad (\text{I28})$$

since $\mathbf{v}_{nn}^{\mathcal{S}} = 0$.

- Coding: $\Delta_{nm}^{\sigma,a,\ell}(\mathbf{k}) \rightarrow \text{calDelta}$ and $\Delta_{nm}^{\sigma,a}(\mathbf{k}) \rightarrow \text{Delta}$ both in `set_input_ascii.f90`

3. Coding for $(\mathcal{V}_{nm}^{\text{LDA},a,\ell}(\mathbf{k}))_{;k^b}$

- Δ_{nm}^a available in array `Delta`, calculated in `set_input_ascii.f90`, and contains the contribution from $\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k})$ if the `-n` option is chosen in `all_responses.sh`
- $(r_{nm}^a(\mathbf{k}))_{;k^b}$ available in array `derMatElem`, calculated in `set_input_ascii.f90` and `functions.f90`, and contains the contribution from $\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k})$ if the `-n` option is chosen in `all_responses.sh`
- With above two we compute $(v_{nm}^{\text{LDA},a}(\mathbf{k}))_{;k^b}$ in `set_input_ascii.f90` and store it in `gdVlda` for diagonal and off diagonal terms.
- $(\mathcal{C}_{nm}^\ell(\mathbf{k}))_{;k^a}$ is coded in `set_input_ascii.f90` and store it in `gdf` for diagonal and off diagonal terms. Darwin at work!
- $(v_{nq}^{\text{LDA},a})_{;k^b} \rightarrow \text{gdVlda}$, $\mathcal{C}_{qm}^\ell \rightarrow \text{cfMatElem}$, $v_{nq}^{\text{LDA},a} \rightarrow \text{vldaMatElem}$, $(\mathcal{C}_{qm}^\ell)_{;k^b} \rightarrow \text{gdf}$
 $v_{nq}^{\text{LDA},a} \rightarrow \text{vldaMatElem}$,

$$\begin{aligned} \left(\mathcal{V}_{nm}^{\text{LDA},a,\ell}\right)_{;k^b} &= \frac{1}{2} \sum_q \left((v_{nq}^{\text{LDA},a})_{;k^b} \mathcal{C}_{qm}^\ell + v_{nq}^{\text{LDA},a} (\mathcal{C}_{qm}^\ell)_{;k^b} + (\mathcal{C}_{nq}^\ell)_{;k^b} v_{qm}^{\text{LDA},a} + \mathcal{C}_{nq}^\ell (v_{qm}^{\text{LDA},a})_{;k^b} \right) \\ \left(\mathcal{V}_{mn}^{\text{LDA},a,\ell}\right)_{;k^b} &= \left(\left(\mathcal{V}_{nm}^{\text{LDA},a,\ell}\right)_{;k^b} \right)^*, \end{aligned} \quad (\text{I29})$$

$$\left(\mathcal{V}_{nm}^{\text{LDA},a,\ell}\right)_{;k^b} \rightarrow \text{gdcalVlda} \text{ and coded in } \text{set_input_ascii.f90}$$

4. Summary

- $\mathcal{V}_{nm}^{\sigma,a,\ell}(\mathbf{k}) = \mathcal{V}_{nm}^{\text{LDA},a,\ell}(\mathbf{k}) + \mathcal{V}_{nm}^{S,a,\ell}(\mathbf{k}) \rightarrow \text{calMomMatElem}$
- $\left(\mathcal{V}_{nm}^{\text{LDA},a,\ell}\right)_{;k^b} \rightarrow \text{gdcalVlda}$
- $\left(\mathcal{V}_{nm}^{S,a,\ell}\right)_{;k^b} \rightarrow \text{gdcalVS}$
- $\left(\mathcal{V}_{nm}^{\sigma,a,\ell}\right)_{;k^b} = \left(\mathcal{V}_{nm}^{\text{LDA},a,\ell}\right)_{;k^b} + \left(\mathcal{V}_{nm}^{S,a,\ell}\right)_{;k^b} \rightarrow \text{gdcalVsig}$

5. Bulk expressions

For a bulk $C_{nm}^\ell(\mathbf{k}) = \delta_{nm}$, then $(C_{nm}^\ell(\mathbf{k}))_{;\mathbf{k}} = 0$, and Eq. (I7) reduces to

$$\begin{aligned} v_{nm}^{\sigma,a} &= v_{nm}^{\text{LDA},a} + v_{nm}^{\mathcal{S},a} \\ \mathbf{v}_{nm}^\sigma(\mathbf{k}) &= \left(1 + \frac{\Sigma}{\omega_c(\mathbf{k}) - \omega_v(\mathbf{k})}\right) \mathbf{v}_{nm}^{\text{LDA}}(\mathbf{k}) \quad n \notin D_m \\ \mathbf{v}_{nn}^\sigma(\mathbf{k}) &= \mathbf{v}_{nn}^{\text{LDA}}(\mathbf{k}), \end{aligned} \quad (\text{I30})$$

where in \$TINIBA/latm the values are coded in the array called `momMatElem`. If option `-n` is given while running `all_resposnses.sh`, then $\mathbf{v}_{nm}^{\text{nl}}(\mathbf{k})$ are included in `momMatElem`. Also,

$$\begin{aligned} (v_{nm}^{\sigma,a})_{;k^b} &= (v_{nm}^{\text{LDA},a})_{;k^b} + (v_{nm}^{\mathcal{S},a})_{;k^b} \\ &= (v_{nm}^{\text{LDA},a})_{;k^b} + i\Sigma f_{mn}(r_{nm}^a)_{;k^b} \\ (v_{mn}^{\sigma,a})_{;k^b} &= \left((v_{nm}^{\sigma,a})_{;k^b}\right)^*, \end{aligned} \quad (\text{I31})$$

where with the r.h.s. expressions are given above.

• Coding: $\mathbf{v}_{nm}^\sigma(\mathbf{k}) \rightarrow \text{momMatElem}$, $(v_{nm}^{\text{LDA},a})_{;k^b} \rightarrow \text{gdVlda}$, $(r_{nm}^{\text{LDA},a})_{;k^b} \rightarrow \text{derMatElem}$, and $(v_{nm}^{\sigma,a})_{;k^b} \rightarrow \text{gdVsig}$

6. Layer or Bulk calculation

- Layer: The layer calculation is done by using Eqs. (I34), (I38), (I36) and (I40).
- Bulk: A bulk calculation can be performed by using the same Eqs. (I34), (I38), (I36) and (I40), and by simply replacing

1. $\mathcal{V}_{nm}^\sigma(\text{calMomMatElem}) \rightarrow \mathbf{v}_{nm}^\sigma(\text{momMatElem})$
2. $(\mathcal{V}_{nm}^\sigma)_{;\mathbf{k}}(\text{gdcalVsig}) \rightarrow (\mathbf{v}_{nm}^\sigma)_{;\mathbf{k}}(\text{gdVsig})$

- Therefore: For the code to run either possibility we use the same arrays as for the layered response, where, if bulk is chosen, it simply copies the bulk matrix elements into the layer arrays, i.e.

- Layer: $\mathcal{V}_{nm}^\sigma(\text{calMomMatElem})$ and $(\mathcal{V}_{nm}^\sigma)_{;\mathbf{k}}(\text{gdcalVsig})$
- Bulk: $\mathbf{v}_{nm}^\sigma(\text{momMatElem} \rightarrow \text{calVsig})$ and $(\mathbf{v}_{nm}^\sigma)_{;\mathbf{k}}(\text{gdVsig} \rightarrow \text{gdcalVsig})$

This change is done in `set_input_ascii.f90` (look for `layer-to-bulk` tag)

– ID: Notice that we have assigned

`calMomMatElem` \rightarrow `calVsig` (keeping `calMomMatElem`), so it is easier to code the responses. Therefore, we have

$\mathcal{V}_{nm}^\sigma \rightarrow \text{calVsig}$ and $(\mathcal{V}_{nm}^\sigma)_{;\mathbf{k}} \rightarrow \text{gdcalVsig}$

either for bulk or layered response.

If `calMomMatElem` is not used, we should get rid of it (ID at work).

7. \mathcal{V} vs \mathcal{R}

Using $\text{Re}[iz] = -\text{Im}[z]$, $\text{Im}[iz] = \text{Re}[z]$, and

$$\mathcal{R}_{nm}^a = \frac{\mathcal{P}_{nm}^a}{im_e \omega_{nm}} = \frac{\mathcal{V}_{nm}^a}{i\omega_{nm}} \quad n \neq m, \quad (\text{I32})$$

we can show the equivalence between the two formulations, i.e.

$$\text{Im}[\chi_{e,\text{abc},\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{ck}} \sum_{l \neq (v,c)} \left[\frac{\omega_{lc}^S \text{Re}[\mathcal{R}_{lc}^{a,\ell} \{r_{cv}^b r_{vl}^c\}]}{\omega_{cv}^S (2\omega_{cv}^S - \omega_{cl}^S)} - \frac{\omega_{vl}^S \text{Re}[\mathcal{R}_{vl}^{a,\ell} \{r_{lc}^c r_{cv}^b\}]}{\omega_{cv}^S (2\omega_{cv}^S - \omega_{lv}^S)} \right] \delta(\omega_{cv}^S - \omega), \quad (\text{I33})$$

$$\text{Im}[\chi_{e,\text{abc},\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{ck}} \sum_{l \neq (v,c)} \frac{1}{\omega_{cv}^S} \left[\frac{\text{Im}[\mathcal{V}_{lc}^{\sigma,a,\ell} \{r_{cv}^b r_{vl}^c\}]}{(2\omega_{cv}^\sigma - \omega_{cl}^S)} - \frac{\text{Im}[\mathcal{V}_{vl}^{\sigma,a,\ell} \{r_{lc}^c r_{cv}^b\}]}{(2\omega_{cv}^\sigma - \omega_{lv}^S)} \right] \delta(\omega_{cv}^\sigma - \omega), \quad (\text{I34})$$

$$\text{Im}[\chi_{i,\text{abc},\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{ck}} \frac{1}{\omega_{cv}^S} \left[\text{Im}[\{r_{cv}^b (\mathcal{R}_{vc}^{a,\ell})_{;k^c}\}] + \frac{2\text{Im}[\mathcal{R}_{vc}^{a,\ell} \{r_{cv}^b \Delta_{cv}^c\}]}{\omega_{cv}^S} \right] \delta(\omega_{cv}^S - \omega), \quad (\text{I35})$$

$$\text{Im}[\chi_{i,\text{abc},\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{ck}} \frac{1}{(\omega_{cv}^S)^2} \left[\text{Re} \left[\left\{ r_{cv}^b (\mathcal{V}_{vc}^{\sigma,a,\ell})_{;k^c} \right\} \right] + \frac{\text{Re} [\mathcal{V}_{vc}^{\sigma,a,\ell} \{r_{cv}^b \Delta_{cv}^c\}]}{\omega_{cv}^S} \right] \delta(\omega_{cv}^\sigma - \omega), \quad (\text{I36})$$

$$\text{Im}[\chi_{e,\text{abc},2\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{ck}} 4 \left[\sum_{v' \neq v} \frac{\text{Re}[\mathcal{R}_{vc}^{a,\ell} \{r_{cv'}^b r_{v'v}^c\}]}{2\omega_{cv'}^S - \omega_{cv}^S} - \sum_{c' \neq c} \frac{\text{Re}[\mathcal{R}_{vc}^{a,\ell} \{r_{cc'}^c r_{c'v}^b\}]}{2\omega_{c'v}^S - \omega_{cv}^S} \right] \delta(\omega_{cv}^S - 2\omega), \quad (\text{I37})$$

$$\text{Im}[\chi_{e,\text{abc},2\omega}^{s,\ell}] = -\frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{ck}} \frac{4}{\omega_{cv}^S} \left[\sum_{v' \neq v} \frac{\text{Im}[\mathcal{V}_{vc}^{\sigma,a,\ell} \{r_{cv'}^b r_{v'v}^c\}]}{2\omega_{cv'}^\sigma - \omega_{cv}^\sigma} - \sum_{c' \neq c} \frac{\text{Im}[\mathcal{V}_{vc}^{\sigma,a,\ell} \{r_{cc'}^c r_{c'v}^b\}]}{2\omega_{c'v}^\sigma - \omega_{cv}^\sigma} \right] \delta(\omega_{cv}^\sigma - 2\omega), \quad (\text{I38})$$

and

$$\text{Im}[\chi_{i,\text{abc},2\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{ck}} \frac{4}{\omega_{cv}^S} \left[\text{Im}[\mathcal{R}_{vc}^{a,\ell} \{ (r_{cv}^b)_{;k^c} \}] - \frac{2\text{Im}[\mathcal{R}_{vc}^{a,\ell} \{r_{cv}^b \Delta_{cv}^c\}]}{\omega_{cv}^S} \right] \delta(\omega_{cv}^S - 2\omega), \quad (\text{I39})$$

$$\text{Im}[\chi_{i,\text{abc},2\omega}^{s,\ell}] = \frac{\pi|e|^3}{2\hbar^2} \sum_{v\mathbf{k}} \frac{4}{(\omega_{cv}^S)^2} \left[\text{Re} \left[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \left\{ \left(r_{cv}^{\text{b}} \right)_{;k^c} \right\} \right] - \frac{2\text{Re} \left[\mathcal{V}_{vc}^{\sigma,\text{a},\ell} \{ r_{cv}^{\text{b}} \Delta_{cv}^c \} \right]}{\omega_{cv}^S} \right] \delta(\omega_{cv}^\sigma - 2\omega), \quad (\text{I40})$$

If we take $\mathcal{R}_{nm}^{\text{a},\ell} \rightarrow r_{nm}^{\text{a}}$, we would recover the expressions for a bulk response. We prefer to use the expressions in terms of \mathcal{V}^ℓ , since they are more physically appealing, as the velocity is what gives the current of a given layer, from which the polarization is computed and the χ^ℓ extracted.

Remark: We mention that above expressions with $\mathcal{R}_{nm}^{\text{a},\ell} \rightarrow r_{nm}^{\text{a}}$, are coded in `integrands.f90`, instead of Eq. 40 and 41 of Cabellos et al.³⁶, which were derived by using Eq. 19 of Aversa and Sipe.¹⁴ To obtain above equations, we started from Eq. 18 of Aversa and Sipe,¹⁴ which has the advantage that applying the layer-by-layer formalism is very transparent and straightforward. This coding is what constitutes the *Length*-gauge implementation in TINIBA[®], which is, within a very small numerical difference, equal to the *Velocity*-gauge implementation of Eq. 35 of Cabellos et al.³⁶, also in TINIBA[®].

8. Other responses

Warning: the layered responses **MUST** be looked at again, and modified according to the newly calculated \mathcal{V}_{nm}^σ and $(\mathcal{V}_{nm}^\sigma)_{;k}$. Linear response, current and spin injection, should be revisited again!!

• Injection Current

We need $\mathbf{v}_{nn}^\sigma(\mathbf{k})$ or $\mathcal{V}_{nn}^\sigma(\mathbf{k})$, but $\mathbf{v}_{nn}^S(\mathbf{k}) = 0$ and $\mathcal{V}_{nn}^S(\mathbf{k}) = 0$ (proven numerically, would be nice to try analytically), since the velocity of the electron in the conduction bands should not depend on the scissors rigid (\mathbf{k} -independent) correction thus

$$\begin{aligned} \mathcal{V}_{nn}^\sigma(\mathbf{k}) &= \mathcal{V}_{nn}^{\text{LDA}}(\mathbf{k}) \\ \mathbf{v}_{nn}^\sigma(\mathbf{k}) &= \mathbf{v}_{nn}^{\text{LDA}}(\mathbf{k}), \end{aligned} \quad (\text{I41})$$

contained in `CalMomMatElem` and `momMatElem`, respectively. Both would have the contribution from \mathbf{v}^{nl} if the options `(-v,-n)` are used. If \mathbf{v}^{nl} is neglected, the option `-1` for a layer calculation would be much faster as we only need to calculate the diagonal elements of Eq. (G2), but since the idea is to *always* include it, we are obliged to use Eq. (I8), where $\mathcal{C}_{nm}^\ell(\mathbf{k})$ is needed, and thus we ought to use option `-c`. Since `CalMomMatElem` is calculated for off-diagonal elements only, we have added a `do` loop in `set_input_ascii.f90` to compute the diagonal part, Eq. (I41), which is stored in `calVsig`. In accordance to I12, we

have checked that we obtain the same results by using Eq. (G2) or Eq. (I43), in a layered injection current calculation, which means that the results obtained thus far in our articles are correct, of course, neglecting \mathbf{v}^{nl} .

INCLUDE FIGURES.

9. Consistency check-up 1

To check that the layered expressions Eqs. (I1), (I3), (I2) and (I4), agree with a bulk calculation, we must take $\mathbf{V}_{nm}^\sigma \rightarrow \mathbf{v}_{nm}^\sigma$ and $\mathbf{V}_{nm;\mathbf{k}}^\sigma \rightarrow \mathbf{v}_{nm;\mathbf{k}}^\sigma$. To do this, proceed as follows

1. Run bulk GaAs using `rlayer.sh` and `chose_layers.sh` as if it were a surface, even though it make no sense.
2. In `$TINIBA/latm/SRC_1setinput/set_input_ascii.f90` look for

```
##### MIMIC A BULK RESPONSE #####d
```

and follow instructions given there.
3. Compile `set_input_*` in `$TINIBA/latm/SRC_1setinput`
4. run `all_responses.sh` using

```
-w layer -r 44 ...
```

```
-w total -r 21 ...
```

and

```
-w total -r 42 ...
```

thus obtaining a `layer` calculation using bulk matrix elements, a `total` calculation for the length and the velocity gauge, and plot the three χ 's, they ought to be identical, if not CRY!. Try out to reproduce Fig. 3

10. Consistency check-up 2

In Fig. 4 we show $\text{Im}[\chi_{xx}]$ for a surface, where the The full-slab result is twice the half-slab result, with or without \mathbf{v}^{nl} , as it must be. Also, the scissors correction rigidly shifts the spectrum by $\hbar\Sigma$ as it should be.

11. Consistency check-up 3

Check-of-Checks: A $(100) 2 \times 1$ surface has χ_{xxx} different from zero, whereas the ideally terminated (100) surface has $\chi_{xxx} = 0$. Clean Si(100) has the 2×1 surface as a possible reconstruction. Then, to calculate such a surface, one can use a slab such that its front surface is the reconstructed Si(100) 2×1 surface and its back surface is H-terminated. Therefore, for the layer-by-layer scheme one should expect that

$$\chi_{xxx}^{\text{half-slab}} \equiv \chi_{xxx}^{\text{full-slab}}, \quad (\text{I42})$$

since the contribution from the back surface (H-terminated), would have zero contribution, since this tensor component of χ is symmetry forbidden. Fancy at Fig. 5, and notice that $\chi^{\text{nl}} < \chi$. i.e. the susceptibility with the inclusion of the non-local part of the pseudopotential is smaller than that without it.

King-of-Kings: Rejoice at Fig. 6.

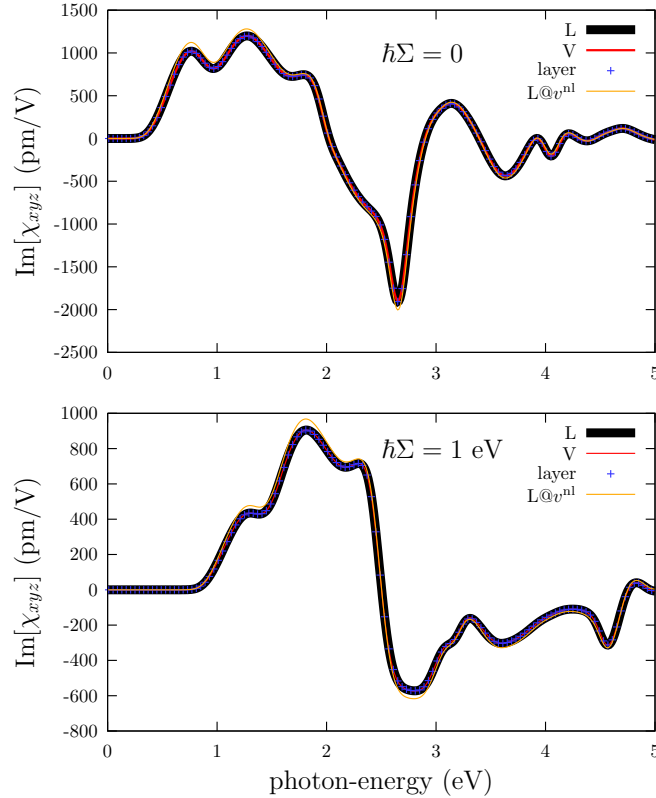


FIG. 3: $\text{Im}[\chi_{xyz}]$ for GaAs, 10 Ha and 47 \mathbf{k} -points, using the layered formulation and mimicking a bulk. The correction due to \mathbf{v}^{nl} , also agrees with the velocity and the layered approach (not shown in the figure for clarity).

12. Consistency check-up 4

To check that the coding of $\mathcal{C}_{nm}^\ell(\mathbf{k})$ is correct, we can calculate $\mathcal{V}_{nm}^{a,\ell}(\mathbf{k})$ using Eq. (72) as follows

$$\begin{aligned}\mathcal{V}_{nm}^{a,\ell}(\mathbf{k}) &= \frac{1}{2m_e} \left(\mathcal{C}^\ell(z) p^a + p^a \mathcal{C}^\ell(z) \right)_{nm} \\ &= \frac{1}{2m_e} \sum_q \left(\mathcal{C}_{nq}^\ell p_{qm}^a + p_{nq}^a \mathcal{C}_{qm}^\ell \right),\end{aligned}\tag{I43}$$

which must give the same results as those computed through Eq. (G2). Indeed, we have checked that this is the case. The `$TINIBA/util/consistency-of-cfmm.sh` is used to check this.

13. Consistency check-up 5

When the `-n` option is chosen, using `all_responses.sh` as coded above doesn't give consistent results, i.e. χ with \mathbf{v}^{nl} is not smaller than χ without \mathbf{v}^{nl} . Thus, we follow the bellow approach instead.

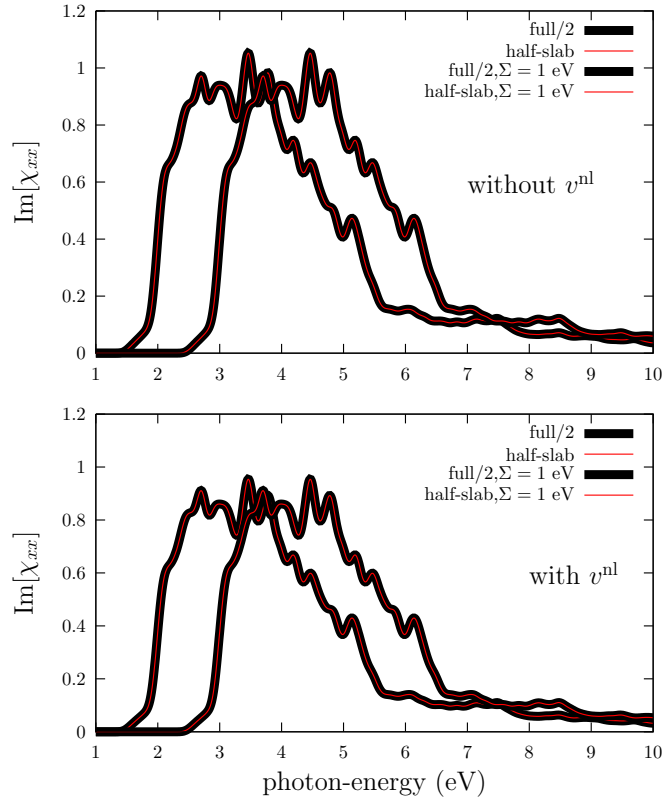


FIG. 4: $\text{Im}[\chi_{xx}]$ for a Si(111):As surface of 6-layers, 5 Ha and 14 \mathbf{k} -points using the layered formulation. The full-slab result is twice the half-slab result, as it must be.

We use Eq. (H14)

$$(\mathcal{V}_{nm}^{\text{LDA},a})_{;k^b} = \frac{\hbar}{m_e} \delta_{ab} C_{nm}^\ell - i \sum_p [r^b, v^{\text{nl},a}]_{np} C_{pm}^\ell + i \sum_\ell \left(r_{n\ell}^b \mathcal{V}_{\ell m}^{\text{LDA},a} - \mathcal{V}_{n\ell}^{\text{LDA},a} r_{\ell m}^b \right) + i r_{nm}^b \tilde{\Delta}_{mn}^a, \quad (\text{I44})$$

where

$$\tilde{\Delta}_{mn}^a = \mathcal{V}_{nn}^{\text{LDA},a} - \mathcal{V}_{mm}^{\text{LDA},a}, \quad (\text{I45})$$

which is coded instead of Eq. (I29). As mentioned before, the term $[r^b, v^{\text{nl},a}]_{nm}$ calculated in Appendix F, is small compared to the other terms, thus we neglect it throughout this work.³² The expression for C_{nm}^ℓ is calculated in Appendix G.

Likewise, with the help of Eq. (D9) into Eq. (I18), we obtain

$$\begin{aligned} (v_{nm}^{\mathcal{S},a})_{;k^b} &= i \Sigma f_{mn} (r_{nm}^a)_{;k^b} = i \Sigma f_{mn} \left(\frac{v_{nm}^{\text{LDA},a}}{i \omega_{nm}^{\text{LDA}}} \right)_{;k^b} \\ &= \Sigma \frac{f_{mn}}{\omega_{nm}^{\text{LDA}}} \left[(v_{nm}^{\text{LDA},a})_{;k^b} - \frac{v_{nm}^{\text{LDA},a}}{\omega_{nm}^{\text{LDA}}} (\omega_{nm}^{\text{LDA}})_{;k^b} \right] \\ &= \Sigma \frac{f_{mn}}{\omega_{nm}^{\text{LDA}}} \left[(v_{nm}^{\text{LDA},a})_{;k^b} - \frac{\Delta_{nm}^b}{\omega_{nm}^{\text{LDA}}} v_{nm}^{\text{LDA},a} \right], \end{aligned} \quad (\text{I46})$$

which is generalized as follows

$$(\mathcal{V}_{nm}^{\mathcal{S},a})_{;k^b} = \Sigma \frac{f_{mn}}{\omega_{nm}^{\text{LDA}}} \left[(\mathcal{V}_{nm}^{\text{LDA},a})_{;k^b} - \frac{\Delta_{nm}^b}{\omega_{nm}^{\text{LDA}}} \mathcal{V}_{nm}^{\text{LDA},a} \right], \quad (\text{I47})$$

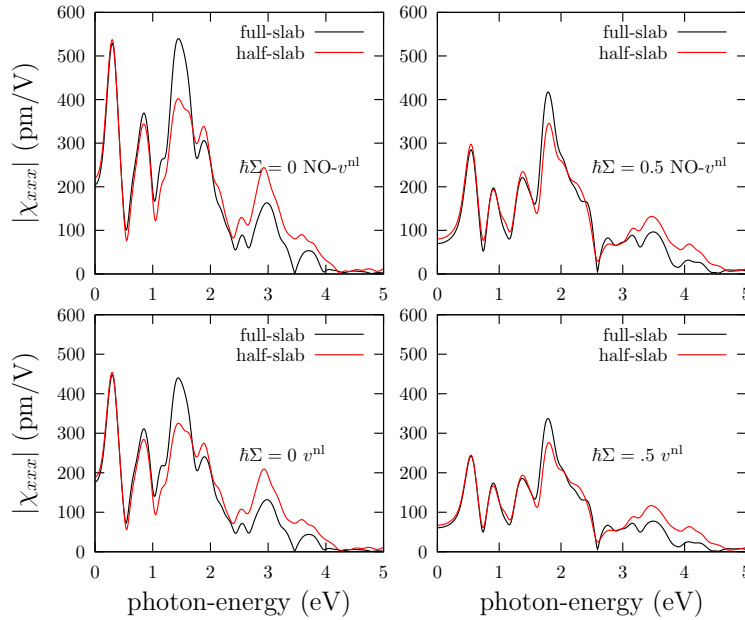


FIG. 5: $|\chi_{xxx}|$ for a Si(100) 2×1 surface of 16 Si-layers and one H layer, 10 Ha, 132 bands and 244 \mathbf{k} -points using the layered formulation. We see that $\chi_{xxx}^{\text{half-slab}} \sim \chi_{xxx}^{\text{full-slab}}$, validating the layer-by-layer approach.

although, I haven't found a way to prove this rigorously, it gives very similar results to those obtained by Eq. (I23), which is coded. The following is also tempting,

$$\begin{aligned} v_{nm}^{\mathcal{S},a} &= \Sigma \frac{f_{mn}}{\omega_{nm}^{\text{LDA}}} v_{nm}^{\text{LDA},a} \\ \mathcal{V}_{nm}^{\mathcal{S},a} &= \Sigma \frac{f_{mn}}{\omega_{nm}^{\text{LDA}}} \mathcal{V}_{nm}^{\text{LDA},a}. \end{aligned} \quad (\text{I48})$$

Again, I haven't found a way to prove this rigorously, but it gives very similar results to those obtained by Eq. (C4), which is coded. In Fig. 7 we show the comparison between the two alternatives, from where we see that they are basically equivalent.

14. Subroutines

The following subroutines/shells are involved in the coding, and are documented between

#BMSd

⋮

#BMSu

marks.

1. \$TINIBA/utills/all_responses.sh
2. \$TINIBA/latm/SRC_1setinput/inparams.f90

Warning: compile both

\$TINIBA/latm/SRC_1setinput/

and

\$TINIBA/latm/SRC_2latm/

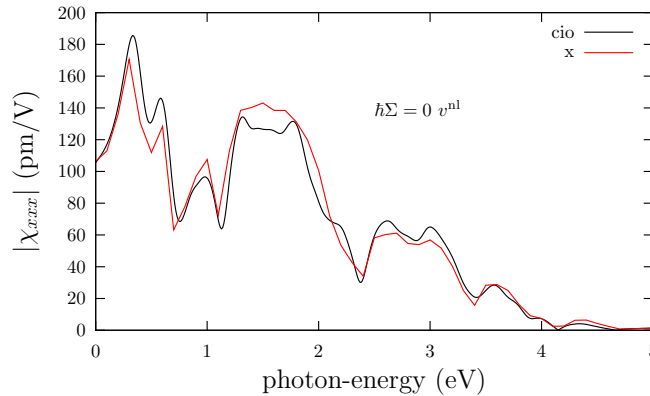


FIG. 6: $|\chi_{xx}|$ for a Si(100) 2×1 surface of 12 Si-layers and one H layer, 5 Ha, 100 bands and 244 \mathbf{k} -points for the CIO-TINIBA[®]-coding and 256 \mathbf{k} -point for the X-DP[©]-coding. Both broadened by 0.1 eV.

3. \$TINIBA/latm/SRC_1setinput/set_input_ascii.f90

prescindir

-
- ¹ M. C. Downer, B. S. Mendoza, and V. I. Gavrilenko, **31**, 966986 (2001), URL <http://onlinelibrary.wiley.com/doi/10.1002/sia.1133/abstract>. I, II
- ² G. Lpke, **35**, 75 (1999-11), ISSN 0167-5729, URL <http://www.sciencedirect.com/science/article/pii/S0167572999000072>. I
- ³ B. S. Mendoza, M. Palummo, G. Onida, and R. Del Sole, **63**, 205406 (2001-04-18), URL <http://link.aps.org/doi/10.1103/PhysRevB.63.205406>. I, V
- ⁴ D. Lim, M. C. Downer, J. G. Ekerdt, N. Arzate, B. S. Mendoza, V. I. Gavrilenko, and R. Q. Wu, **84**, 34063409 (2000), URL <http://link.aps.org/doi/10.1103/PhysRevLett.84.3406>.
- ⁵ V. I. Gavrilenko, R. Q. Wu, M. C. Downer, J. G. Ekerdt, D. Lim, and P. Parkinson, **364**, 1 (2000-03-27), ISSN 0040-6090, URL <http://www.sciencedirect.com/science/article/pii/S0040609099009001>.
- ⁶ B. S. Mendoza, W. L. Mochán, and J. A. Maytorena, **60**, 14334 (1999), URL http://prb.aps.org/abstract/PRB/v60/i20/p14334_1.
- ⁷ B. S. Mendoza, A. Gaggiotti, and R. Del Sole, **81**, 37813784 (1998), URL <http://link.aps.org/doi/10.1103/PhysRevLett.81.3781>. V
- ⁸ B. S. Mendoza and W. L. Mochán, **53**, 1047310476 (1996), URL <http://link.aps.org/doi/10.1103/PhysRevB.53.R10473>.

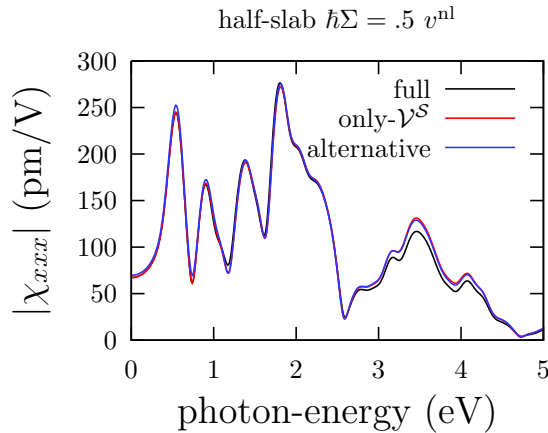


FIG. 7: $|\chi_{xxx}|$ for a Si(100) 2×1 surface of 16 Si-layers and one H layer, 10 Ha, 132 bands and 244 \mathbf{k} -points using the layered formulation. “Full” uses full coding of \mathcal{V}_{nm}^S and $\mathcal{V}_{nm:\mathbf{k}}^S$ through Eq. (C4); “only- \mathcal{V}^S ” uses \mathcal{V}_{nm}^S through Eq. (C4) and $\mathcal{V}_{nm:\mathbf{k}}^S$ through Eq. (I47); “alternative” uses \mathcal{V}_{nm}^S through Eq. (I48) and $\mathcal{V}_{nm:\mathbf{k}}^S$ through Eq. (I47). Notice that the three curves are almost identical.

- ⁹ B. S. Mendoza and W. L. Mochán, **55**, 2489 (1997), URL http://prb.aps.org/abstract/PRB/v55/i4/p2489_1.
- ¹⁰ P. Guyot-Sionnest, A. Tadjeddine, and A. Liebsch, **64**, 1678 (1990-04-02), URL <http://link.aps.org/doi/10.1103/PhysRevLett.64.1678>. I
- ¹¹ B. S. Mendoza, Epioptics 2000, Ed. A. Cricenti (World Scientific, 2001). I
- ¹² N. Arzate and B. S. Mendoza, **63**, 125303 (2001-03-06), URL <http://link.aps.org/doi/10.1103/PhysRevB.63.125303>. I
- ¹³ J. D. Jackson, Classical electrodynamics (1975), URL <http://scitation.aip.org/content/aip/magazine/physicstoday/article/30/7/10.1063/1.3037637?crawler=true>. II
- ¹⁴ C. Aversa and J. E. Sipe, **52**, 14636 (1995-11-15), URL <http://link.aps.org/doi/10.1103/PhysRevB.52.14636>. III, III, III, H, I7, I7
- ¹⁵ J. E. Sipe and A. I. Shkrebtii, **61**, 5337 (2000), URL http://prb.aps.org/abstract/PRB/v61/i8/p5337_1. III
- ¹⁶ W. Lambrecht and S. Rashkeev, **217**, 599 (2000), ISSN 1521-3951, URL [http://onlinelibrary.wiley.com/doi/10.1002/\(SICI\)1521-3951\(200001\)217:1<599::AID-PSSB599>3.0.CO;2-0/abstract](http://onlinelibrary.wiley.com/doi/10.1002/(SICI)1521-3951(200001)217:1<599::AID-PSSB599>3.0.CO;2-0/abstract). III
- ¹⁷ A. E. N., J. Chem. Phys. **21** (1953). III
- ¹⁸ E. I. Blount, F. Seitz, and D. Turnbull, **13**, 305 (1962). III, A
- ¹⁹ S. Ismail-Beigi, E. K. Chang, and S. G. Louie, Phys. Rev. Lett. **20**, 087402 (2001). III
- ²⁰ Reference. III, B, B
- ²¹ C. Motta, M. Giantomassi, M. Cazzaniga, K. Gaál-Nagy, and X. Gonze, **50**, 698 (2010-12), ISSN 0927-0256, URL <http://www.sciencedirect.com/science/article/pii/S0927025610005409>. III, B, B
- ²² L. Kleinman and D. M. Bylander, **48**, 1425 (1982-05-17), URL <http://link.aps.org/doi/10.1103/PhysRevLett.48.1425>.
- ²³ B. Adolph, V. I. Gavrilenko, K. Tenelsen, F. Bechstedt, and R. Del Sole, **53**, 9797 (1996-04-15), URL <http://link.aps.org/doi/10.1103/PhysRevB.53.9797>. III, B, B
- ²⁴ L. Reining, R. Del Sole, M. Cini, and J. G. Ping, **50**, 8411 (1994-09-15), URL <http://link.aps.org/doi/10.1103/PhysRevB.50.8411>. V, V
- ²⁵ H. Sano, G. Mizutani, W. Wolf, and R. Podloucky, Phys. Rev. B **66**, 195338 (2002). V
- ²⁶ J. E. Mejia, B. MENDOZA, and C. SALAZAR, **50**, 134 (2004), URL <http://ojs.unam.mx/index.php/rmf/article/view/13974>. V
- ²⁷ C. Hogan, R. Del Sole, and G. Onida, **68**, 035405 (2003-07-01), URL <http://link.aps.org/doi/10.1103/PhysRevB.68.035405>. V
- ²⁸ C. Castillo, B. S. Mendoza, W. G. Schmidt, P. H. Hahn, and F. Bechstedt, **68**, 041310 (2003-07-30), URL <http://link.aps.org/doi/10.1103/PhysRevB.68.041310>. V
- ²⁹ B. Mendoza, F. Nastos, N. Arzate, and J. Sipe, **74**, 075318 (2006-08), ISSN 1098-0121, 1550-235X, URL <http://link.aps.org/doi/10.1103/PhysRevB.74.075318>. V, G, G
- ³⁰ (????). VI

- ³¹ S. N. Rashkeev, W. R. L. Lambrecht, and B. Segall, **57**, 3905 (1998-02-15), URL <http://link.aps.org/doi/10.1103/PhysRevB.57.3905>. VI, H
- ³² V. Vénard, private communication. VI, F, H1, I13
- ³³ N. W. Ashcroft and N. D. Mermin, Solid State Physics (1976). VI, E1, H
- ³⁴ A. Gordienko and A. Poplavnoi, Russ. Phys. J. **47**, 687 (2004). B
- ³⁵ C. P. C. . . . M. Fuchs, M. Scheffler, Phys. Commun. **119**, 67 (1999). B, B
- ³⁶ C. J., B. Mendoza, M. Escobar, F. Nastos, and J. Sipe, **80**, 155205 (2009-10), ISSN 1098-0121, 1550-235X, URL <http://link.aps.org/doi/10.1103/PhysRevB.80.155205>. C, H, I7, I7
- ³⁷ V. Olevano, private communication. F
- ³⁸ F. Nastos, B. Olejnik, K. Schwarz, and J. E. Sipe, **72**, 045223 (2005-07-29), URL <http://link.aps.org/doi/10.1103/PhysRevB.72.045223>. H
- ³⁹ Nicolas Tancogne-Dejean private communication. Indeed, one can compute the layered contribution of the non-local contribution to \mathbf{v} with an analytic expression. However, one needs to compute this within the DP code. I