

The contribution of nitrogen Frenkel-pair formation to the high-temperature heat capacity of uranium mononitride

Mohamed AbdulHameed^{a,c}, Benjamin Beeler^{a,b,*}

^a*Department of Nuclear Engineering, North Carolina State University, Raleigh, NC 27695, USA*

^b*Idaho National Laboratory, Idaho Falls, ID 83415, USA*

^c*School of Mechanical and Manufacturing Engineering, UNSW Sydney, Sydney, NSW 2052, Australia*

Abstract

The high-temperature heat capacity of uranium mononitride (UN) remains uncertain due to conflicting measurements and models above ~ 1700 K. To assess whether intrinsic defect formation contributes to the observed superlinear behavior of $C_P(T)$, we perform large-scale molecular dynamics simulations using two interatomic potentials to quantify nitrogen diffusion and Frenkel-pair populations from 1800–2600 K. Both models show increasing anion mobility, but the Tseplyaev potential yields substantially larger Frenkel concentrations, producing a defect heat-capacity contribution of up to ~ 10 J/(mol-K). This defect-driven term **contributes to the nonlinear high-temperature response**, suggesting that nitrogen sublattice disorder provides a plausible intrinsic mechanism for **part of the heat-capacity increase in** UN.

Keywords: Uranium nitride, Molecular dynamics, Specific heat capacity, Frenkel defects


*Corresponding author

Email address: bwbeeler@ncsu.edu (Benjamin Beeler)

Highlights

- MD simulations reveal nitrogen Frenkel-pair formation in UN above 1800 K
- Defect heat capacity reaches ~ 10 J/(mol-K) at 2600 K for Tseplyaev potential
- Anion sublattice disorder is proposed as a mechanism for superlinear $C_P(T)$

Graphical Abstract

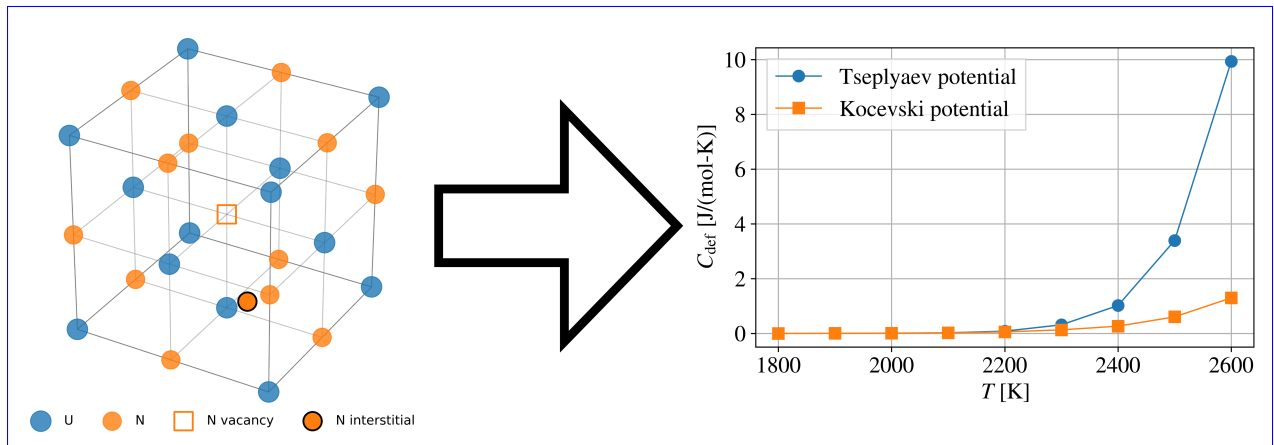

1. Introduction

The specific heat, C_P , of uranium mononitride (UN) is not yet conclusively established, with experimental datasets and theoretical predictions offering conflicting descriptions above roughly 1700 K. The most widely used correlation, developed by Hayes *et al.* [1], exhibits a strongly superlinear increase in $C_P(T)$ at elevated temperatures, approaching a nearly T^5 dependence [2]. This trend originates from the high-temperature enthalpy measurements of Conway and Flagella [3], which extend to approximately 2600 K and remain the only measurements reaching such elevated temperatures. The only other available high-temperature measurements, i.e., those by Affortit [4] that extend up to about 2300 K, report an almost linear temperature dependence. They also report higher $C_P(T)$ values than all other datasets in the temperature range of 1200–1900 K. Thus, Hayes *et al.* [1] decided to disregard Affortit’s dataset and rely only on the measurements of Conway and Flagella to extract $C_P(T)$ at high temperatures.

A central complication arises from the composition of the Conway-Flagella samples, which contained roughly 20 wt.% UO_2 . Because UO_2 exhibits a premelting (superionic) transition driven by oxygen Frenkel defects [5, 6], any attempt to extract a UN-specific enthalpy from mixed-material calorimetry requires subtracting a defect-rich UO_2 contribution whose behavior changes rapidly with temperature [1]. While the specific heat capacity extracted from Conway-Flagella enthalpy measurements agrees with other datasets at moderate temperature [1], it develops a strong upward curvature when extrapolated above ~ 1700 K. Given the known defect thermodynamics of UO_2 [5, 6], this trend could plausibly reflect the UO_2 component rather than the intrinsic response of UN [7].

Theoretical predictions also diverge. Early *ab initio* molecular dynamics (AIMD) simulations reported a nearly perfectly linear $C_P(T)$ [8]. Classical molecular dynamics (MD) using the angular-dependent potential (ADP) of Tseplyaev and Starikov [9, 10] produced a steep increase in $C_P(T)$ consistent with the Hayes correlation [2]. The embedded atom method (EAM) potential of Kocevski *et al.* [11] also predicts a nearly linear $C_P(T)$ at high temperatures [2]. Recent AIMD simulations combined with the disordered local moment (DLM) method predict a T^2 -like increase in $C_P(T)$ [12]. This result is significant because AIMD+DLM is a first-principles method that treats both lattice dynamics and magnetic disorder on equal footing. The fact that a high-accuracy *ab initio* calculation yields a moderate, T^2 -like increase suggests that while the anomaly is likely less dramatic than the historical correlation implies, there is independent evidence that a nonlinear increase in $C_P(T)$ is an intrinsic feature of UN at high temperatures.

The unresolved question is not only the magnitude of the heat capacity but the physical origin of its temperature dependence. Galvin *et al.* [7] argued that current data support two plausible interpretations: either the Kocevski potential correctly predicts an asymptotically linear high-temperature heat capacity and the Conway-Flagella curvature is extrinsic, likely influenced by UO_2 in the samples, or the stronger rise seen with the Tseplyaev potential reflects an intrinsic mechanism in UN that has not yet been experimentally confirmed. They also suggested that strong anharmonicity, phonon softening, or even partial UN decomposition could contribute to the observed rise in $C_P(T)$ if defect mechanisms alone are insufficient.

These considerations frame two useful reference behaviors for intrinsic UN:

the Hayes correlation, which reflects the strongest curvature inferred from the Conway-Flagella enthalpy dataset, and the more moderate nonlinear increase obtained from recent AIMD+DLM calculations. Agreement with the Hayes correlation trend can therefore be interpreted as evidence that anion disorder *can* generate heat-capacity contributions of the required scale, but it does not uniquely establish the intrinsic UN behavior because the Conway-Flagella samples contained substantial UO_2 .

A useful reference is the defect thermodynamics of UO_2 , where oxygen Frenkel pairs proliferate as the temperature approaches the superionic transition, producing large excess contributions to both enthalpy and heat capacity [5]. MD simulations by Cooper *et al.* [6] demonstrated that oxygen diffusion increases sharply and $C_P(T)$ exhibits a broad anomaly near 2700 K as the anion sublattice disorders. Because Conway-Flagella’s samples contained enough UO_2 to contribute significantly to the measured enthalpy, it is plausible that the reconstructed UN correlation inherited part of this defect-driven curvature. However, the nonlinear T^2 -like behavior obtained in recent AIMD+DLM simulations [12] suggests that a degree of intrinsic anion-sublattice softening may also occur in UN. This raises the question whether nitrogen Frenkel-pair formation in UN could contribute to UN’s $C_P(T)$ analogous to that observed in UO_2 .

2. Computational details

To address this question, we performed classical MD simulations of UN using two interatomic potentials: the Tseplyaev angular-dependent potential [10] and the Kocevski EAM potential. All calculations **utilize** the Large-scale Atomic/Molecular Massively Parallel Simulator (LAMMPS) software package [13, 14] using a 1 fs time step, with periodic boundary conditions (PBCs) applied in all directions. The OVITO software package [15] is used for supercell visualization and analysis. All simulations employ a $50 \times 50 \times 50$ supercell (10^6 atoms), allowing us to sample both transport and point-defect statistics over the temperature range of 1800–2600 K.

We note that melting temperatures obtained from direct-heating MD of perfect crystals generally overestimate the thermodynamic melting point due to superheating and the solid-liquid interface nucleation barrier [16, 17]. We therefore cite thermodynamic melting points from our prior void-induced melting simulations [2]: $T_m \approx 2700$ K for the Tseplyaev potential and $T_m \approx 3100$ K for the Kocevski potential. All simulations here remain within the solid-phase stability window of both potentials. Although the Tseplyaev results at 2600 K approach that model’s thermodynamic melting range, the Tseplyaev potential remains crystalline up to ~ 3000 K in perfect-supercell heating because of expected hysteresis.

For diffusivity calculations, the supercells are equilibrated in the NPT ensemble and then evolved for a total of 5 ns. The self-diffusion coefficients are obtained from the long-time limit of the mean-squared displacement, MSD,

$$D = \lim_{t \rightarrow \infty} \frac{\langle \Delta r^2(t) \rangle}{6t}, \quad (1)$$

using the slope over the final 3 ns of each trajectory. No defects were inserted in any of these simulations, and all contributions to the MSD originate from spontaneously produced Frenkel pairs. In all cases, uranium remained effectively immobile on these timescales, while nitrogen exhibited increasingly rapid motion with temperature. We note that these are transient, dynamically formed vacancy–interstitial pairs identified from instantaneous snapshots rather than **quenched or static** Frenkel defects in the classical thermodynamic sense. **The** term “Frenkel pair” is used throughout for convenience. The goal of this direct MD-based defect count is to estimate the defect contribution to $C_P(T)$ in UN without *a priori* assumptions about defect equilibrium or the functional form of defect concentration.

3. Results

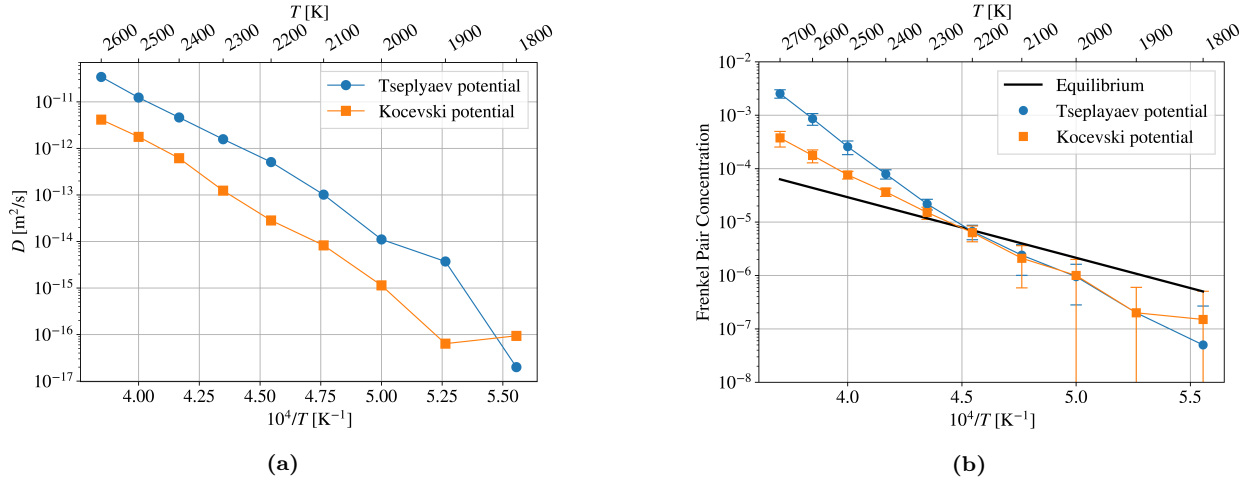


Figure 1: (Color online) **(a)** Nitrogen self-diffusion coefficients obtained from MSD analysis. **(b)** Nitrogen Frenkel-pair concentrations extracted using Wigner–Seitz defect analysis over 200 ps trajectories. Data points denote temporal averages over the post-equilibration sampling window, and error bars represent **one temporal standard deviation in linear concentration units and may appear asymmetric on the logarithmic scale**. The equilibrium concentration is based on Frenkel-pair formation energy of 4.5 eV calculated elsewhere using DFT and 0 K MD [2, 18, 19].

Fig. 1a summarizes the nitrogen self-diffusion coefficients for both potentials. For the Tseplyaev potential, the nitrogen diffusivity, D_N , is essentially zero at temperatures below 1800 K and then increases sharply, rising from $3.7 \times 10^{-15} \text{ m}^2/\text{s}$ at 1900 K to $3.4 \times 10^{-11} \text{ m}^2/\text{s}$ at 2600 K, spanning nearly four orders of magnitude. The Kocevski potential yields the same qualitative trend but with systematically smaller values, typically one order of magnitude lower across the entire range, with D_N approaching $4.1 \times 10^{-12} \text{ m}^2/\text{s}$ at 2600 K. The increasing nitrogen transport above 1800–1900 K, especially for the Tseplyaev potential, coincides with the temperature range where the Conway-Flagella enthalpy data start deviating from an approximately linear trend into a pronounced nonlinear increase. This suggests that the same microscopic process responsible for the rapid growth of nitrogen mobility—namely, the onset of significant anion-sublattice disorder and Frenkel-pair formation—may also underlie the excess enthalpy that produces the apparent high-temperature anomaly in the empirical heat capacity. **To confirm that the 2600 K state remains solid and that the**

observed anion mobility and concentration are not a pre-melting artifact, we examined radial distribution functions at 2600 K and found them consistent with a crystalline solid (no liquid-like collapse of higher-neighbor peaks) for either potential.

To more directly quantify point-defect formation, we analyzed nitrogen Frenkel-pair concentrations using the Wigner-Seitz (WS) defect analysis implemented in OVITO [15]. In this method, a defect-free reference lattice defines the positions of ideal sites, each associated with a Wigner-Seitz cell, i.e., the region of space closer to that site than to any other. For a given instantaneous configuration, each atom is assigned to the nearest reference site. Sites with occupancy zero correspond to vacancies, while sites with occupancy greater than one indicate interstitial defects. This nearest-site mapping provides a robust, topology-based identification of point defects. For each temperature, we simulated for 200 ps, recorded snapshots every 10 ps, and applied the WS analysis to all configurations after the first 10 ps to ensure equilibration. The reported Frenkel-pair concentrations correspond to the time-averaged mean over the sampled configurations, and the associated error bars represent the standard deviation over the temporal sampling window.

Here, $n_{\text{FP}}(T)$ is the total number of nitrogen Frenkel pairs in the MD supercell, obtained from the number of nitrogen WS vacancies. The plotted concentration is normalized by the total number of atoms,

$$c_{\text{FP}}(\mathbf{T}) = \frac{n_{\text{FP}}(\mathbf{T})}{N_{\text{atoms}}}. \quad (2)$$

This definition affects only the concentration normalization and the Arrhenius prefactor, but not C_{def} , which is evaluated from the absolute Frenkel-pair count $n_{\text{FP}}(T)$ in Eq. (4).

The resulting nitrogen Frenkel-pair concentrations, $c_{\text{FP}}(T)$, are shown in Fig. 1b. For the Tseplyaev potential, c_{FP} increases from 5×10^{-8} at 1800 K to 8.6×10^{-4} at 2600 K. Fitting an Arrhenius form [20],

$$c_{\text{FP}}(T) = A \exp \left[-\frac{Q}{k_{\text{B}}T} \right], \quad (3)$$

yields an effective activation energy $Q_{\text{ADP}} = 4.97$ eV, while the Kocevski potential produces a lower activation energy, $Q_{\text{EAM}} = 3.79$ eV, and lower defect populations at all temperatures. Thus, the Tseplyaev potential generates nitrogen Frenkel concentrations large enough to potentially alter the thermodynamics.

Frenkel-pair formation contributes an additional term to the heat capacity [5, 21]:

$$C_{\text{def}}(T) = \frac{1}{n_{\text{moles}}} \frac{\partial}{\partial T} [n_{\text{FP}}(T) Q_{\text{FP}}] \approx \frac{Q_{\text{FP}}}{n_{\text{moles}}} \frac{\partial n_{\text{FP}}}{\partial T}. \quad (4)$$

In practice, we evaluate $C_{\text{def}}(T)$ directly from the Frenkel-pair populations obtained by the WS analysis for both interatomic potentials. We assume a formation enthalpy $Q_{\text{FP}} = 4.5$ eV, consistent with both the DFT estimates [18, 19] and the $T \rightarrow 0$ K Frenkel pair formation energies of both the Tseplyaev and Kocevski potentials [2]. The temperature derivative in Eq. (4) is computed using centered finite differences applied to the simulated

defect populations. Here, n_{moles} is the number of moles of UN formula units in the simulation cell.

To connect the directly counted Frenkel-pair population with the heat-capacity response, we compare three quantities. First, the total constant-pressure heat capacity, C_P , is written as

$$C_P = C_{\text{lat}} + C_{\text{elec}}, \quad (5)$$

where C_{lat} is the MD lattice heat capacity and C_{elec} is the electronic heat-capacity contribution, following our previous assessment of these potentials [2]. Second, we define a residual lattice term, $C_{\text{anharm+def}}$, by subtracting the constant-volume heat capacity, C_V , and the thermal-expansion contribution, C_{exp} , from C_{lat} :

$$C_{\text{anharm+def}} = C_{\text{lat}} - C_V - C_{\text{exp}}. \quad (6)$$

Here, $C_{\text{anharm+def}}$ represents the part of the lattice heat capacity that remains after removing the constant-volume and expansion contributions. The C_{lat} , C_V , and C_{exp} terms were obtained from fits generated from the MD data reported in our previous assessment [2]. We label this residual $C_{\text{anharm+def}}$ because the high-temperature MD trajectories allow Frenkel pairs to form spontaneously. Therefore, the residual contains both non-expansive anharmonic lattice contributions and defect-generation contributions. Finally, we compare this residual with the independently estimated defect heat capacity, $C_{\text{def}}(T)$, obtained from the WS Frenkel-pair populations using Eq. (4).

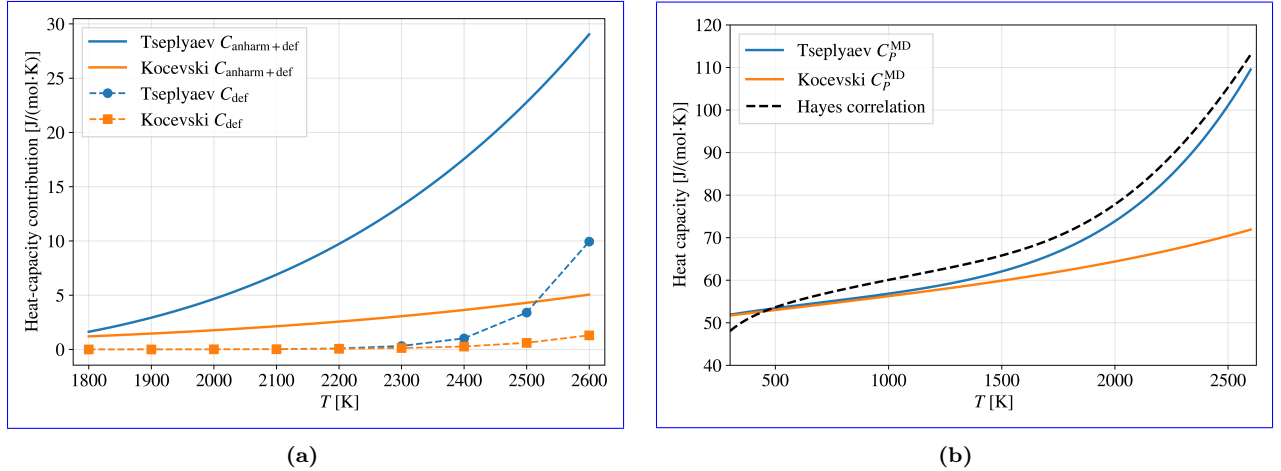


Figure 2: (Color online) (a) Comparison of $C_{\text{def}}(T)$ with the residual lattice term $C_{\text{anharm+def}}$. (b) Total $C_P(T)$ for both interatomic potentials and the Hayes correlation presented for reference.

The resulting $C_{\text{def}}(T)$ curves and their comparison with $C_{\text{anharm+def}}$ are shown in Fig. 2. For the Tseplyaev potential, C_{def} remains small below 2400 K but increases rapidly at the highest temperatures, reaching 3.39 J/(mol-K) at 2500 K and 9.94 J/(mol-K) at 2600 K. These values correspond to 3.4% and 9.1% of the total C_P , respectively. The corresponding $C_{\text{anharm+def}}$ values are 22.78 and 29.04 J/(mol-K), so the directly counted Frenkel-pair term accounts for approximately 15% of the residual at 2500 K and 34% at 2600 K.

For the Kocevski potential, C_{def} remains much smaller, increasing from 0.61 J/(mol-K) at 2500 K to 1.30 J/(mol-K) at 2600 K. These values correspond to 0.9% and 1.8% of the total C_P , respectively. The corresponding $C_{\text{anharm+def}}$ values are 4.30 and 5.05 J/(mol-K), so C_{def} accounts for approximately 14% of the residual at 2500 K and 26% at 2600 K. Thus, although the defect term is not the entire heat capacity or the entire residual, it becomes a substantial fraction of the high-temperature nonlinear contribution.

This comparison provides a possible explanation for why the Tseplyaev potential produces a stronger nonlinear heat-capacity response than the Kocevski potential. The Tseplyaev potential generates a rapidly increasing Frenkel-pair contribution at high temperature, whereas the Kocevski potential gives both a smaller residual lattice contribution and a smaller explicitly counted defect term.

The difference between the two potentials likely reflects their different functional forms and fitting targets. The Tseplyaev angular-dependent potential has previously been found to better describe energetic quantities such as heat capacity and point-defect formation energies, whereas the Kocevski EAM potential better reproduces structural and elastic properties but is less reliable for defect energetics [2]. These differences lead to different nitrogen vacancy-interstitial free-energy landscapes and therefore different Frenkel-pair populations at high temperature.

The onset of nitrogen mobility also coincides with the onset of nonlinear heat-capacity growth. As shown in Fig. 1a, D_N remains negligible below approximately 1800 K and then increases rapidly above 1800–1900 K. The Frenkel-pair concentration follows the same trend, indicating that nitrogen transport is coupled to spontaneous anion-disorder formation. This temperature range overlaps with the onset of nonlinear growth in the Hayes heat-capacity correlation and with the high-temperature departure from lower-temperature behavior in the AIMD+DLM results. This correspondence supports the interpretation that nitrogen Frenkel-pair formation and anion-sublattice disorder contribute to the intrinsic nonlinear component of $C_P(T)$ in UN.

Because UN is metallic, C_{elec} is not negligible. Using $C_{\text{elec}} = \gamma T$, with $\gamma = 3.7 \times 10^{-3} \text{ J mol}^{-1} \text{ K}^{-2}$ [22], gives $C_{\text{elec}} \approx 9.6 \text{ J/(mol-K)}$ at 2600 K. However, this contribution is linear in T , whereas the high-temperature increase in C_P is strongly nonlinear. Therefore, C_{elec} can shift the magnitude of C_P , but it cannot explain the curvature.

Our results therefore support a defect-driven interpretation of the high-temperature heat capacity of UN: nitrogen Frenkel-pair formation and associated sublattice disorder provide a plausible intrinsic mechanism for the observed superlinear $C_P(T)$. The calculated $C_{\text{def}}(T)$ should be regarded as qualitative, since the defect populations are sensitive to the choice of interatomic potential and Eq. (4) is a simplified estimate. Nevertheless, the order-of-magnitude difference in Frenkel-pair concentration between the two potentials produces a correspondingly large difference in the defect contribution to the heat capacity. Thus, while the Tseplyaev potential predicts defect populations large enough to reproduce the curvature in the Hayes correlation and the Kocevski potential yields a much weaker response, the true intrinsic behavior of UN potentially lies between these limits.

This hypothesis is experimentally testable. High-purity UN samples with carefully controlled oxygen content, combined with high-temperature calorimetry and tracer-diffusion measurements, are therefore essential to determine whether an anion-mobility crossover and correlated superlinear enhancement in $C_P(T)$ occur near the temperatures predicted here.

4. Conclusions

In this work, we used MD simulations with two interatomic potentials to investigate whether intrinsic nitrogen Frenkel-pair formation contributes to the high-temperature heat capacity of UN. Both potentials predict increasing nitrogen Frenkel-pair concentrations and diffusivities above 1800 K, but the Tseplyaev potential yields defect populations roughly an order of magnitude larger than the Kocevski potential across the entire temperature range. This difference translates directly into the thermodynamic response: C_{def} reaches ~ 10 J/(mol·K) for the Tseplyaev potential at 2600 K but remains near ~ 1 J/(mol·K) for the Kocevski potential.

These results offer an atomistic explanation for the divergent heat-capacity predictions of the two potentials. When Frenkel pairs form in appreciable concentrations, the associated defect enthalpy **contributes a nonlinear component** to $C_P(T)$; when defect populations remain small, the heat capacity is dominated by lattice, **electronic, expansion, and anharmonic contributions and remains closer to linear over the simulated temperature range**. This behavior resembles the defect-driven anomalies in UO_2 , suggesting that UN may undergo a similar anion-sublattice disordering crossover at high temperature. Resolving the quantitative magnitude of this effect will require high-temperature calorimetry and tracer-diffusion measurements on high-purity UN samples.

5. Discussion

The defect contribution to the heat capacity estimated here via Eq. (4) is simplified relative to the comprehensive statistical-thermodynamic treatment developed by Pavlov *et al.* for UO_2 [5]. Several approximations distinguish the present approach: (i) the Frenkel-pair formation enthalpy Q_{FP} is taken as temperature-independent, whereas Pavlov *et al.* allowed it to decrease with temperature through Debye–Hückel screening of charged defect interactions; (ii) no non-configurational formation entropy is included; (iii) defect populations are extracted directly from the MD trajectories rather than solved self-consistently from coupled mass-action equations; and (iv) only a single defect type—nitrogen Frenkel pairs—is considered, neglecting, e.g., Schottky defects. Two physical features of UN, however, make these simplifications considerably more defensible than they would be for UO_2 .

First, nitrogen Frenkel pairs in UN are electrically neutral because UN behaves as a metal [23], in contrast to the charged oxygen vacancy-interstitial pairs ($v_{\text{O}}^{\bullet\bullet}$ and O_i'') in UO_2 . In UO_2 , the net attractive force between oppositely charged defects reduces the effective formation enthalpy as their concentration increases, which in turn accelerates further defect production until the available interstitial sites begin to saturate, producing a maximum in $C_P(T)$ [5, 6]. No such self-reinforcing mechanism operates for neutral defects, so treating Q_{FP} as temperature-independent is appropriate for UN, and $C_{\text{def}}(T)$ is expected to increase

monotonically until melting rather than peak, consistent with the behavior predicted by both potentials in this work.

Second, the omission of the non-configurational formation entropy can be justified quantitatively. Following the thermodynamic framework of Varotsos [24], the formation entropy of a Frenkel defect can be written as:

$$S_{\text{FP}} = -\frac{Q_{\text{FP}}}{B_0} \frac{\partial B}{\partial T}. \quad (7)$$

For a bulk modulus of the linear form $B(T) = B_0(1 - \alpha T)$, this simplifies to:

$$S_{\text{FP}} = Q_{\text{FP}} \alpha, \quad (8)$$

independent of B_0 . Using the temperature coefficient $\alpha = 2.375 \times 10^{-5} \text{ K}^{-1}$ for UN [25] and $Q_{\text{FP}} = 4.5 \text{ eV}$ gives $S_{\text{FP}} \approx 1.07 \times 10^{-4} \text{ eV/K} \approx 1.24 k_B$. The corresponding Boltzmann prefactor is $\exp(S_{\text{FP}}/(2k_B)) \approx 1.86$, meaning that including entropy would uniformly scale the equilibrium Frenkel-pair concentration by a factor of approximately 1.86 at all temperatures, which is negligible relative to the order-of-magnitude difference in c_{FP} between the two interatomic potentials. By comparison, Pavlov *et al.* [5] used a formation entropy of $S_{\text{FP}} \approx 8.5 k_B$ for oxygen Frenkel pairs in UO_2 , yielding $\exp(S_{\text{FP}}/(2k_B)) \approx 69.11$, roughly two orders of magnitude larger than the UN value.

Another limitation is that the present simulations consider only stoichiometric UN. Real samples may deviate slightly from ideal stoichiometry, which could shift the onset of anion-sublattice disorder. Nitrogen-deficient UN contains pre-existing nitrogen vacancies that may enhance vacancy-mediated transport, while nitrogen-rich UN may favor interstitial-type disorder. Quantifying these effects requires dedicated off-stoichiometric simulations and is left for future work.

Finally, the agreement between the Tseplyaev potential and the Hayes correlation should be interpreted as mechanistic consistency rather than a unique validation of the intrinsic UN heat-capacity curve. The Conway–Flagella enthalpy data underlying the Hayes correlation were obtained from samples containing substantial UO_2 , which could influence the reconstructed high-temperature $C_P(T)$. The recent AIMD+DLM result, which predicts a more moderate non-linear increase, remains an important first-principles reference for high-purity UN.

Acknowledgments

The authors thank Jacob Eapen for the fruitful discussions and useful suggestions. This research made use of the resources of the High-Performance Computing Center at Idaho National Laboratory, which is supported by the Office of Nuclear Energy of the U.S. Department of Energy and the Nuclear Science User Facilities under Contract No. DE-AC07-05ID14517.

References

- [1] S. L. Hayes, J. K. Thomas, K. L. Peddicord, Material property correlations for uranium mononitride IV. thermodynamic properties, *Journal of Nuclear Materials* 171 (1990) 300–318.

- [2] M. AbdulHameed, B. Beeler, C. O. Galvin, M. W. Cooper, Assessment of uranium nitride interatomic potentials, *Journal of Nuclear Materials* 600 (2024) 155247. doi:<https://doi.org/10.1016/j.jnucmat.2024.155247>.
- [3] J. B. Conway, P. N. Flagella, Physical and mechanical properties of reactor materials, Tech. Rep. GEMP-1004, General Electric Company (10 1969). doi:[10.2172/4815902](https://doi.org/10.2172/4815902).
- [4] C. Affortit, Chaleur spécifique de UC et UN, *Journal of Nuclear Materials* 34 (1) (1970) 105–107. doi:[https://doi.org/10.1016/0022-3115\(70\)90014-0](https://doi.org/10.1016/0022-3115(70)90014-0).
- [5] T. R. Pavlov, M. R. Wenman, L. Vlahovic, D. Robba, R. J. Konings, P. V. Uffelen, R. W. Grimes, Measurement and interpretation of the thermo-physical properties of UO_2 at high temperatures: The viral effect of oxygen defects, *Acta Materialia* 139 (2017) 138–154. doi:[10.1016/j.actamat.2017.07.060](https://doi.org/10.1016/j.actamat.2017.07.060).
- [6] M. W. Cooper, S. T. Murphy, P. C. Fossati, M. J. Rushton, R. W. Grimes, Thermophysical and anion diffusion properties of $(\text{U}_x\text{Th}_{1-x})\text{O}_2$, *Proceedings of the Royal Society A: Mathematical, Physical and Engineering Sciences* 470 (2014). doi:[10.1098/rspa.2014.0427](https://doi.org/10.1098/rspa.2014.0427).
- [7] C. Galvin, N. Kuganathana, N. Barron, R. Grimes, Predicted thermophysical properties of UN, PuN, and (U, Pu)N, *Journal of Applied Physics* 135 (2024). doi:[10.1063/5.0177315](https://doi.org/10.1063/5.0177315).
- [8] V. Kocevski, D. A. Rehn, A. J. Terricabras, A. van Veelen, M. W. Cooper, S. W. Paisner, S. C. Vogel, J. T. White, D. A. Andersson, Finite temperature properties of uranium mononitride, *Journal of Nuclear Materials* 576 (2023) 154241. doi:[10.1016/j.jnucmat.2023.154241](https://doi.org/10.1016/j.jnucmat.2023.154241).
- [9] A. Y. Kuksin, S. V. Starikov, D. E. Smirnova, V. I. Tseplyaev, The diffusion of point defects in uranium mononitride: Combination of DFT and atomistic simulation with novel potential, *Journal of Alloys and Compounds* 658 (2016) 385–394. doi:[10.1016/j.jallcom.2015.10.223](https://doi.org/10.1016/j.jallcom.2015.10.223).
- [10] V. I. Tseplyaev, S. V. Starikov, The atomistic simulation of pressure-induced phase transition in uranium mononitride, *Journal of Nuclear Materials* 480 (2016) 7–14. doi:[10.1016/j.jnucmat.2016.07.048](https://doi.org/10.1016/j.jnucmat.2016.07.048).
- [11] V. Kocevski, M. W. Cooper, A. J. Claisse, D. A. Andersson, Development and application of a uranium mononitride (UN) potential: Thermomechanical properties and Xe diffusion, *Journal of Nuclear Materials* 562 (2022). doi:[10.1016/j.jnucmat.2022.153553](https://doi.org/10.1016/j.jnucmat.2022.153553).
- [12] M. AbdulHameed, B. Beeler, A. Claisse, Ab initio molecular dynamics of paramagnetic uranium mononitride (UN) using disordered local moments, *Computational Materials Science* 260 (2025) 114115. doi:<https://doi.org/10.1016/j.commatsci.2025.114115>.

- [13] S. Plimpton, Fast parallel algorithms for short-range molecular dynamics, *Journal of Computational Physics* 117 (1995) 1–19. [doi:10.1006/JCPH.1995.1039](https://doi.org/10.1006/JCPH.1995.1039).
- [14] A. P. Thompson, H. M. Aktulga, R. Berger, D. S. Bolintineanu, W. M. Brown, P. S. Crozier, P. J. in 't Veld, A. Kohlmeyer, S. G. Moore, T. D. Nguyen, R. Shan, M. J. Stevens, J. Tranchida, C. Trott, S. J. Plimpton, LAMMPS - a flexible simulation tool for particle-based materials modeling at the atomic, meso, and continuum scales, *Computer Physics Communications* 271 (2022). [doi:10.1016/j.cpc.2021.108171](https://doi.org/10.1016/j.cpc.2021.108171).
- [15] A. Stukowski, Visualization and analysis of atomistic simulation data with OVITO—the open visualization tool, *Modelling and Simulation in Materials Science and Engineering* 18 (2010). [doi:10.1088/0965-0393/18/1/015012](https://doi.org/10.1088/0965-0393/18/1/015012).
- [16] S. Alavi, D. L. Thompson, Simulations of melting of polyatomic solids and nanoparticles, *Molecular Simulation* 32 (2006). [doi:10.1080/08927020600823158](https://doi.org/10.1080/08927020600823158).
- [17] Y. Zhang, E. J. Maginn, A comparison of methods for melting point calculation using molecular dynamics simulations, *Journal of Chemical Physics* 136 (2012). [doi:10.1063/1.3702587](https://doi.org/10.1063/1.3702587).
- [18] L. Yang, N. Kaltsoyannis, Incorporation of Kr and Xe in uranium mononitride: A density functional theory study, *Journal of Physical Chemistry C* 125 (2021) 26999–27008. [doi:10.1021/acs.jpcc.1c08523](https://doi.org/10.1021/acs.jpcc.1c08523).
- [19] V. Kocovski, D. A. Rehn, M. W. D. Cooper, D. A. Andersson, First-principles investigation of uranium mononitride (UN): Effect of magnetic ordering, spin-orbit interactions and exchange correlation functional, *Journal of Nuclear Materials* 559 (2022). [doi:10.1016/j.jnucmat.2021.153401](https://doi.org/10.1016/j.jnucmat.2021.153401).
- [20] D. R. Olander, A. T. Motta, *Light Water Reactor Materials Volume I: Fundamentals*, American Nuclear Society, 2017.
- [21] R. Szwarc, The defect contribution to the excess enthalpy of uranium dioxide: Calculation of the Frenkel energy, *Journal of Physics and Chemistry of Solids* 30 (1969). [doi:10.1016/0022-3697\(69\)90024-9](https://doi.org/10.1016/0022-3697(69)90024-9).
- [22] M. Samsel-Czekala, E. Talik, P. De, R. Troć, H. Misiorek, C. Sułkowski, Electronic structure and magnetic and transport properties of single-crystalline UN, *Physical Review B* 76 (2007) 144426. [doi:10.1103/PhysRevB.76.144426](https://doi.org/10.1103/PhysRevB.76.144426).
- [23] M. AbdulHameed, B. Beeler, A. Claisse, Atomistic investigation of plastic deformation and dislocation motion in uranium mononitride, *Applied Sciences* 15 (2024) 2666. [doi:https://doi.org/10.3390/app15052666](https://doi.org/10.3390/app15052666).
- [24] P. Varotsos, Comments on the formation entropy of a Frenkel defect in BaF₂ and CaF₂, *Phys. Rev. B* 13 (2) (1976) 938. [doi:10.1103/PhysRevB.13.938](https://doi.org/10.1103/PhysRevB.13.938).
- [25] S. L. Hayes, J. K. Thomas, K. L. Peddicord, Material property correlations for uranium mononitride II. mechanical properties, *Journal of Nuclear Materials* 171 (1990) 271–288.