



BRAINSPARK

DFM / DFA Analysis

Rear subframe bracket — «hostile» “fixture” × ½ (revision diff)

CHASSIS · ALUMINIUM A356 (CAST) · DIE CASTING (ALUMINIUM)

GENERATED 2026-08-10 · 3/8 RULES EVALUATED

EXECUTIVE SUMMARY

2 rule families run speculatively

No single process was settled, so some findings below are for a route this part will never take.

not scored

MANUFACTURABILITY

4

FINDINGS


3

HIGH SEVERITY

€76,800

PRICED / YEAR

THE PART

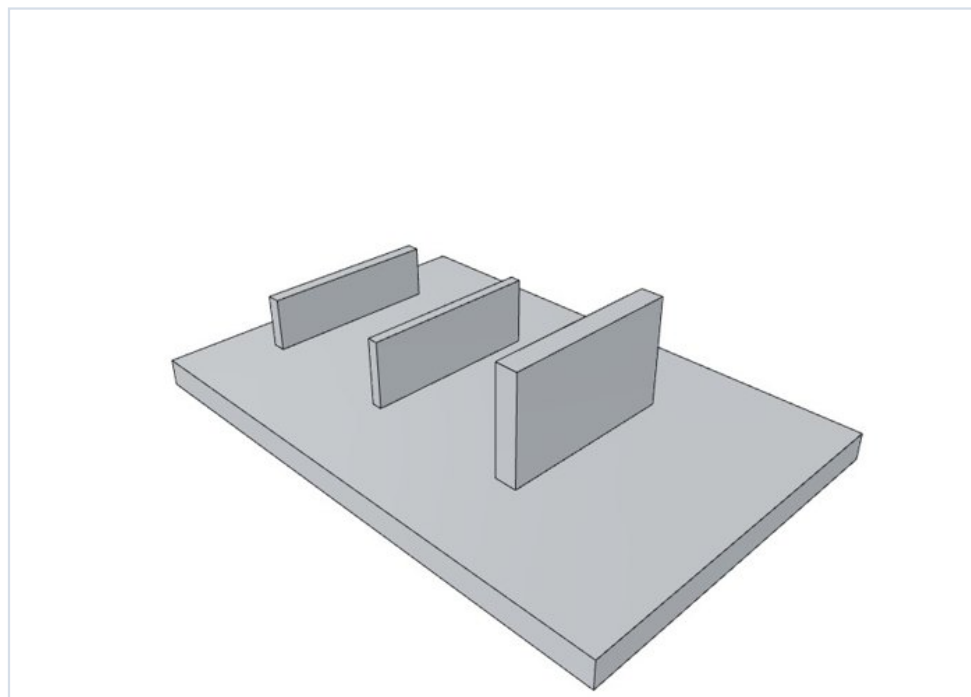

ENVELOPE

248.5 x 162.3 x 88.1 mm

VOLUME

412.7 cm3

SURFACE

1863.2 cm2

FACES

214

VIEW


Isometric, part axes

WHAT IS WRONG, WORST FIRST

	FINDING	MEASURED	GUIDELINE	IMPACT / YR
HIGH	Wall thickness outside the die-casting range	30 mm	1–3.5 mm	€76,800
HIGH	Wall area below the minimum die-casting draft	41.2 %	<= 5 %	not priced
HIGH	Undercuts require slides or lifters in the die	3 reg	<= 0 reg	not priced
MEDIUM	Cored hole beyond the core-pin slenderness limit	14.2 L/D	<= 10 L/D	not priced



How this report was produced, and from what

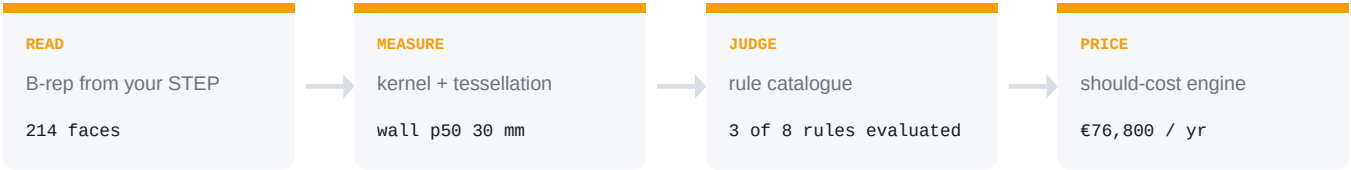


MEASURED GEOMETRY

BOUNDING BOX	VOLUME
248.5 x 162.3 x 88.1 mm	412.7 cm3
WALL p5 / p50 / p95	WALL UNIFORMITY
2.1 / 30 / 61.4 mm	non-uniform
DRAW DIRECTION	UNDERCUT REGIONS
[0, 0, 1]	3
WALL AREA BELOW MIN DRAFT	UNCLASSIFIED AREA
41.2 %	22.8 %
HOLES & CUT-OUTS	INTERNAL CUT LENGTH
none	—


RECOGNISED RIBS

Thickness is measured at the base, where the 40-60%-of-wall guideline applies; a drafted rib is opened out by the draft term rather than reported at its thinner mid-height. Ratios are against the measured 30 mm nominal wall.

#	THICKNESS	HEIGHT	LENGTH	DRAFT/SIDE	T / WALL	H / WALL
1	4.85 mm	28.4 mm	112.75 mm	1.5 deg	0.16	0.95
2	3.2 mm	19.6 mm	88.4 mm	0 deg	0.11	0.65
3	2.05 mm	14.2 mm	—	2.25 deg	0.07	0.47
4	1.9 mm	33.8 mm	64.1 mm	0 deg	0.06	1.13

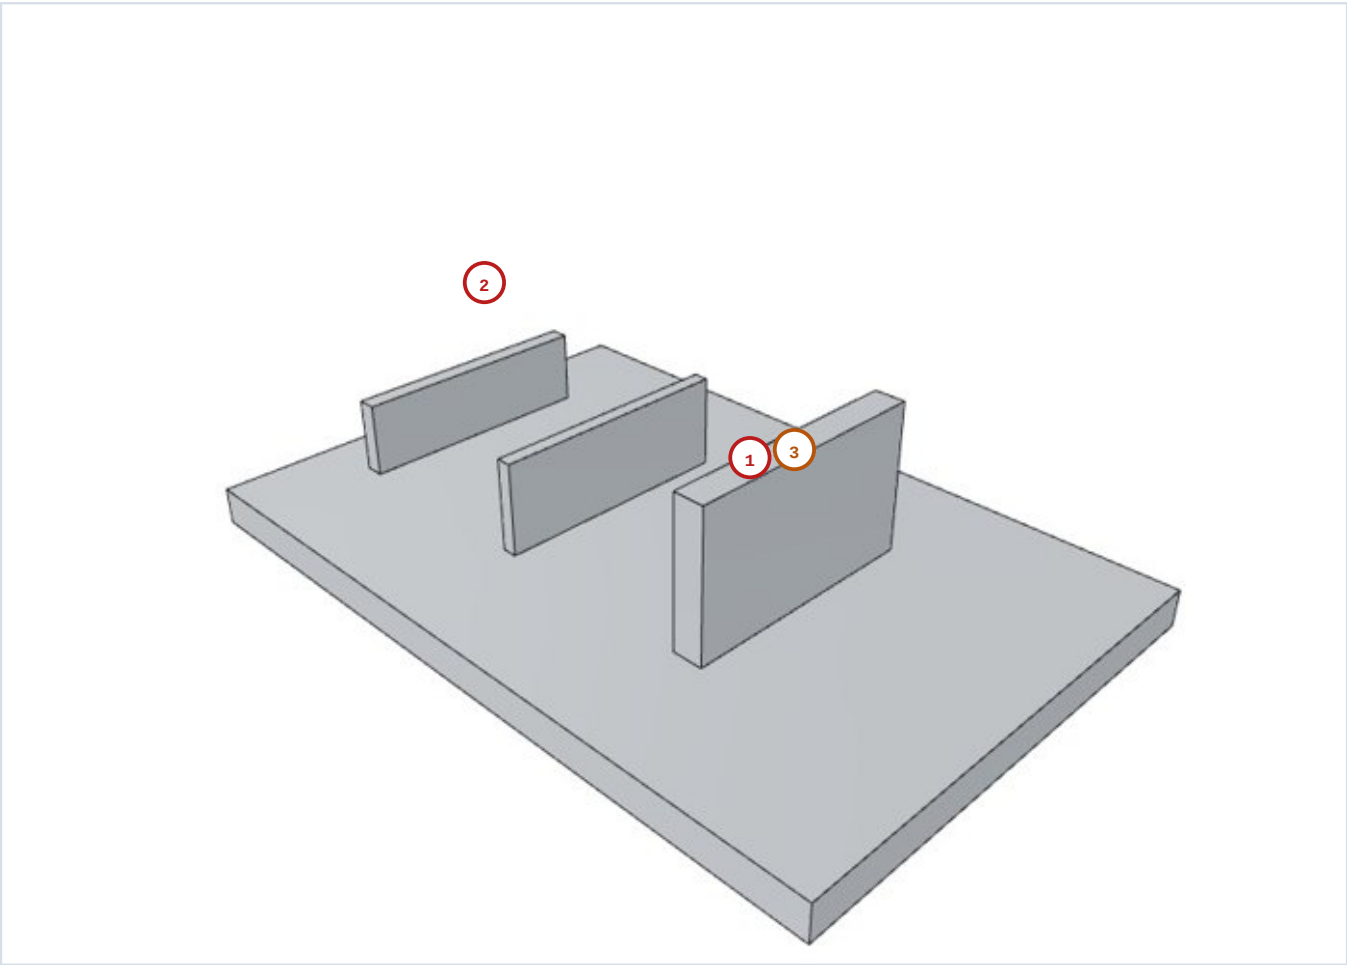

WHAT IS MARKED	MEASURED AGAINST ITS LIMIT	WHICH INSTANCE
1 Wall area below the minimum die-casting draft	41.2 % of wall area · limit <= 5	flattest of 2 under-drafted walls
2 Undercuts require slides or lifters in the die	3 regions · limit <= 0	largest of 3 undercut regions
3 Cored hole beyond the core-pin slenderness limit	14.2 core L/D · limit <= 10	worst of 9

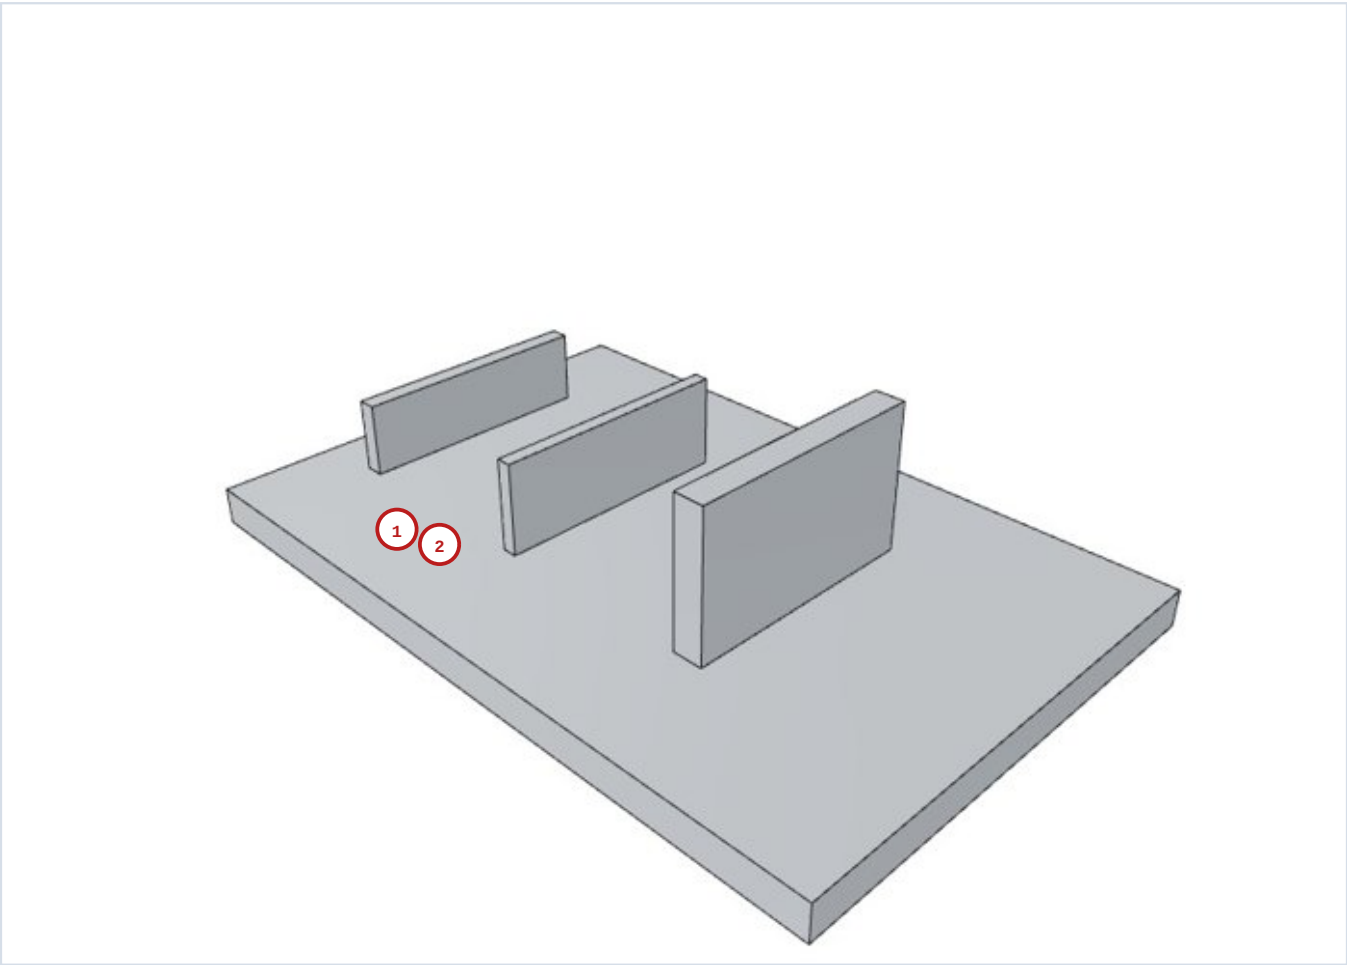

WHAT IS MARKED	MEASURED AGAINST ITS LIMIT	WHICH INSTANCE
1 Wall area below the minimum die-casting draft	41.2 % of wall area · limit <= 5	flattest of 2 under-drafted walls
2 Undercuts require slides or lifters in the die	3 regions · limit <= 0	largest of 3 undercut regions

WHAT CHANGED

This revision against Rev A - 2026-07-02

0 findings closed, 1 new, 1 newly visible, 2 still open

The two revisions were judged by DIFFERENT rule families, so a rule missing from one side has not been fixed — it was never asked. Findings are matched by rule id and the unmatched ones are listed as such.

0	1	2	18 -> 25
FIXED	NEW	STILL OPEN	SCORE

NO LONGER FAILING		
● Thin web below the fill limit	0.8 mm -> -	NOT FIXED — rule not run on this revision
● Slide count beyond the die budget	6 reg -> -	NOT FIXED — rule not run on this revision
NEW		
● Undercuts require slides or lifters in the die	3 reg vs <= 0 regions	was passing on the previous revision
STILL OPEN		
● Wall thickness outside the die-casting range	44 mm -> 30 mm	-14 mm
● Wall area below the minimum die-casting draft	82.5 % -> 41.2 %	-41.3 %
NEWLY VISIBLE		
● Cored hole beyond the core-pin slenderness limit	not a regression	no cored hole was recognised on the earlier revis...

ACTIONS

4 decisions, worst first

FINDING, AND THE CHANGE THAT CLEARS IT		OWNER (ROLE) / DECISION NEEDED
1	Wall thickness outside the die-casting range Hold a uniform nominal wall in the 2.0-3.5 mm band and core out heavy sections rather than leaving solid mass. wall 30 mm -> 3.5 mm	Design engineering Approve the change, or state why the geometry has to stay DUE
2	Wall area below the minimum die-casting draft Add at least 1.5 deg of draft to every wall parallel to the draw. 41.2 % of wall area -> <= 5 % of wall area	Design + Tooling Decide without a price — Insufficient draft shortens die life through galling; die life is a tooling-amortisation input, not a geometric one DUE
3	Undercuts require slides or lifters in the die Redesign the three occluded faces so they release along the draw, or budget a slide for each. 3 regions -> <= 0 regions	Tooling / diemaker Get a quote: the engines do not price this, only cited literature does DUE
4	Cored hole beyond the core-pin slenderness limit Shorten the cored hole to 10 diameters or open it up. 14.2 core L/D -> <= 10 core L/D	Design engineering Decide without a price — Core-pin replacement frequency is a tooling-maintenance input, not a geometric one the engine derives DUE

BY OWNER

Design engineering	2 actions, 1 high severity	EUR 76,800/yr
Design + Tooling	1 action, 1 high severity	not priced
Tooling / diemaker	1 action, 1 high severity	not priced

FINDINGS NOT MARKED ON THE MODEL

- Wall thickness outside the die-casting range
- measured across the whole part, so there is no single face to mark

TOLERANCES

Read from the model

12 dimensions, 3 geometric tolerances and 2 datums were read from the model's semantic PMI. The tightest total band called out is 0.02 mm, and that is what the process-capability rules below are measured against.

flatness 0.05 mm
true position 0.1 mm
perpendicularity 0.08 mm

4 findings · 3/4 rules evaluated

MANUFACTURABILITY SCORE	RULE COVERAGE	PRICED IMPACT / YEAR
25 / 100	75%	EUR 76,800

Wall thickness outside the die-casting range

HIGH

MEASURED 30 mm · GUIDELINE 1–3.5 mm

Below about 1 mm the die will not fill reliably before the melt freezes off, and cold shuts appear along the last-to-fill boundary; above about 3.5 mm the section traps porosity as it solidifies from the outside in, holds the cycle open while the centre gives up its heat, and leaves a shrinkage void exactly where the casting is thickest and a machinist is most likely to break into it. Neither failure is recoverable by process tuning once the wall is drawn, which is why wall thickness is the first thing a die caster looks at and the last thing a designer wants to change.

WHAT TO DO

Hold a uniform nominal wall in the 2.0-3.5 mm band and core out heavy sections rather than leaving solid mass. Where local stiffness is needed, add ribs at 40-60% of the nominal wall rather than thickening the wall itself; where a boss must be thick, core it from the back so the section stays even. WARNING_TOKEN_THAT_IS_EXTREMELY_LONG_AND_UNBREAKABLE_ABCDEFGHIJKLMNOPQRSTUVWXYZ0123456789

COST IMPACT

wall 30 mm -> 3.5 mm: EUR 12.84 to EUR 12.2 per part, a saving of EUR 0.64 per part (EUR 76,800 per year). Basis: computeShouldCost — cooling-limited cycle (base + k-wall²) and the mass change that comes with it.

SOURCE [INDUSTRY CONSENSUS, no primary source audited]: Aluminium HPDC design guidance (1.0 mm minimum, 2.0–3.5 mm recommended).

Wall area below the minimum die-casting draft

HIGH

MEASURED 41.2 % of wall area · GUIDELINE <= 5 % of wall area

Below about 1 mm the die will not fill reliably before the melt freezes off, and cold shuts appear along the last-to-fill boundary; above about 3.5 mm the section traps porosity as it solidifies from the outside in, holds the cycle open while the centre gives up its heat, and leaves a shrinkage void exactly where the casting is thickest and a machinist is most likely to break into it. Neither failure is recoverable by process tuning once the wall is drawn, which is why wall thickness is the first thing a die caster looks at and the last thing a designer wants to change.

WHAT TO DO

Add at least 1.5 deg of draft to every wall parallel to the draw. Inside walls need roughly twice the outside figure because the casting shrinks onto them.

COST IMPACT

Not priced. Insufficient draft shortens die life through galling; die life is a tooling-amortisation input, not a geometric one the engine derives.

SOURCE [INDUSTRY CONSENSUS, no primary source audited]: Aluminium HPDC design guidance (1.0 mm minimum, 2.0–3.5 mm recommended).

Cored hole beyond the core-pin slenderness limit

MEDIUM

MEASURED 14.2 core L/D · GUIDELINE <= 10 core L/D

Below about 1 mm the die will not fill reliably before the melt freezes off, and cold shuts appear along the last-to-fill boundary; above about 3.5 mm the section traps porosity as it solidifies from the outside in, holds the cycle open while the centre gives up its heat, and leaves a shrinkage void exactly where the casting is thickest and a machinist is most likely to break into it. Neither failure is recoverable by process tuning once the wall is drawn, which is why wall thickness is the first thing a die caster looks at and the last thing a designer wants to change.

WHAT TO DO

Shorten the cored hole to 10 diameters or open it up. A drilled secondary operation is the alternative and it carries its own cost.

COST IMPACT

Not priced. Core-pin replacement frequency is a tooling-maintenance input, not a geometric one the engine derives.

3 of 9 checked features break this:

- 2x Ø5 x71 14.2 core L/D at (43, -18, 6)
- Ø6.5 x83.2 12.8 core L/D at (-105, 63, 33)
- 4x Ø10 x104 10.4 core L/D at (0, 0, -12)

SOURCE [YOUR COMPANY STANDARD, set in this workspace]: Company standard: our tool room will not run a core pin...
THRESHOLD: resolved for company standard

Undercuts require slides or lifters in the die

HIGH

MEASURED 3 regions · GUIDELINE <= 0 regions

Below about 1 mm the die will not fill reliably before the melt freezes off, and cold shuts appear along the last-to-fill boundary; above about 3.5 mm the section traps porosity as it solidifies from the outside in, holds the cycle open while the centre gives up its heat, and leaves a shrinkage void exactly where the casting is thickest and a machinist is most likely to break into it. Neither failure is recoverable by process tuning once the wall is drawn, which is why wall thickness is the first thing a die caster looks at and the last thing a designer wants to change.

WHAT TO DO

Redesign the three occluded faces so they release along the draw, or budget a slide for each. A lifter is cheaper than a slide where the feature is shallow.

COST IMPACT

Not priced. Slide and loose-core tooling is quoted by the diemaker; the piece-price engines do not model it.

Industry guidance puts a side action, lifter or collapsible core at roughly \$500–\$5,000 of tooling per feature. Cited literature, NOT an engine result — confirm with your toolmaker.

SOURCE [INDUSTRY CONSENSUS, no primary source audited]: Aluminium HPDC design guidance (1.0 mm minimum, 2.0–3.5 mm recommended).

PASSED (1)

- Sharp internal corners concentrate stress and restrict flow — measured 2.4 mm against >= 1.6 mm

0 findings · 0/4 rules evaluated

MANUFACTURABILITY SCORE	RULE COVERAGE	PRICED IMPACT / YEAR
not scored	0%	none priced

No rule in this family could be evaluated on this geometry, so no score is given. A score of 100 over zero checks would be meaningless.

- NOT EVALUATED (4) — these were NOT checked and are NOT passes
- Inside bend radius below one material thickness — no measurement available for "minBendRadiusToThickness" on this geom...
 - Punched hole smaller than the material thickness — no measurement available for "minHoleDiaToThickness" on this geometry
 - Hole too close to a bend line — threshold is a formula
 - Flange too short to form — no measurement available for "minFlangeToThickness" on this geometry

DESIGN FOR ASSEMBLY

6 parts · 3 distinct types

6

PARTS

41.8 s

ASSEMBLY TIME

withheld

THEORETICAL MIN

withheld

DFA INDEX

5 of 5 parts have unanswered DFA questions, so the theoretical minimum and design efficiency are withheld. Handling and insertion times below are geometric and stand on their own.

Handling and insertion times come from the brainspark-dfa-v1 model. MTM-structured; BrainSpark coefficients; calibratable. NOT Boothroyd & Dewhurst tables.

#	PART	OFF	a+b	HANDLE s	INSERT s	TOTAL s
0	bracket casting	1	720	3.24	1.5	4.74
1	reinforcement plate — very long...	1	360	1.63	1.5	3.13
2	M10 bolt	4	180	1.13	6.5	7.63
3	washer	4	180	1.83	1.5	3.33
4	bush	2	180	1.13	2.5	3.63

Suspected fasteners (geometric signature only, confirm against the BOM): solid-3 (medium), solid-4 (medium).

Where every number came from

GEOMETRY	Measured by an OpenCascade kernel. Draft angles, undercut classification and wall thickness on the tessellation — which works on freeform surfaces, where a plane-and-cylinder analysis measures almost nothing on a real cast or moulded part. Holes, apertures and features from the B-rep topology. The AI wrote none of the numbers in this report.
DRAW DIRECTION	Chosen by sweeping candidate axes and scoring undercut area, not assumed. Undercuts are separated from zero-draft drag faces: a zero-draft wall is fixable with a degree of taper, an undercut buys a slide or a lifter, and reporting them as one number would overstate the tooling problem.
COST	Re-run through the same deterministic engines used elsewhere in BrainSpark, once with the geometry as drawn and once with the rule satisfied. Findings the engines cannot price say so, with the reason.
THRESHOLDS	Every DIMENSION here was measured from your file and is reproducible. The GUIDELINES they are compared against are not of the same standing. The catalogue-wide counts were not sent with this analysis, so they are not stated here — each finding still carries its own grade beside its source, which is where the claim that matters for that finding lives. Every finding carries its grade. Treat a finding as a screening result that opens a conversation with your supplier — not as a specification.
THREE OUTCOMES, NOT TWO	Failed, passed, and NOT EVALUATED. A rule whose measurement this part does not provide is listed as unevaluated with the reason, never as a pass — so the coverage figure beside the score tells you how much of the catalogue actually ran.
DFA	Handling times follow the published Boothroyd-Dewhurst METHOD. Their tables are copyrighted and are not reproduced; the coefficients here are ours and should be calibrated against your own line data before a labour commitment. Part symmetry is MEASURED by rotating each solid and intersecting it with itself, not inferred from inertia. The three DFA questions concern function and intent, which a static solid cannot answer — until every part is answered, the theoretical minimum and the index are withheld.
WHAT THIS DOES NOT COVER	Threads are not recognised. GD&T is read only where the file carries semantic AP242 PMI. Ribs are found from opposed planar side faces on a planar base, so a rib with curved sides is not checked. Surface finish and material come from your input, not from the model. The tool-reach sweep does not model the holder, the spindle nose or the machine envelope, so a face it calls reachable may still not be.