

检测报告

编号: SDFS2303001583FF_CN 日期: 2023-04-06 页码: 第 1 页共 10 页

湖北回天新材料股份有限公司

湖北省襄阳市高新区关羽路 1 号

样品描述: 7931/7937MS 胶

产品规格: 600mL/支

生产商: 湖北回天新材料股份有限公司

以上数据和信息为客户提供并确认, SGS 不对这些数据和信息的真实性、完整性以及由此引发的结果和/或结论的有效性负责。

SGS 参考编号: WHIN2303000153PL01

试样收到日期: 2023-03-29

测试执行时间: 2023-03-29 至 2023-04-06

测试要求:

TB/T 3237-2010 《动车组用内装材料阻燃技术条件》

1. GB/T 2406.2-2009 《塑料—用氧指数法测定燃烧行为 第 2 部分: 室温试验》
2. UIC 564-2:1991 附录 4: 测定刚性非热塑性材料防火性能的测试方法
3. GB/T 8323.2-2008 《塑料—烟生成—第 2 部分: 单室法测量烟密度试验方法》
4. TB/T 3237-2010 《动车组用内装材料阻燃技术条件》条款 4.4 毒性气体分析

测试结果: -- 参见数据附表 --

通标标准技术服务有限公司
顺德分公司
授权代表签署

刘楠

扫码查看在线报告



SDFS2303001583FF

刘楠
批准签署人

此报告结果仅对测试样品负责。



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1/F, 1 Building, European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde Foshan, Guangdong, China 528333 t (86-757) 22805888 f (86-757) 22805858 www.sgs.com.cn
中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757) 22805888 f (86-757) 22805858 sgs.china@sgs.com

检测报告

编号: SDFS2303001583FF_CN 日期: 2023-04-06 页码: 第 2 页共 10 页

I. 样品信息

样品描述	涂层+铝板
颜色	黑色
基材信息	铝板
暴露(测试)面	涂层面
样品尺寸	GB/T 2406.2: 80mm×10mm×4mm
	UIC 564-2: 400mm×160mm×7mm
	GB/T 8323.2 & TB/T 3237 条款 4.4: 75mm×75mm×7mm

II. 结果概要

No.	测试项目	测试方法	测试结果*	
1	氧指数测试	GB/T 2406.2-2009	42.8%	
2	燃烧性试验	UIC 564-2:1991	A 级	
3	烟密度测试	GB/T 8323.2-2008	无引燃模式	D _{s1.5} 0.00
				D _{s4.0} 118.60
			引燃模式	D _{s1.5} 0.12
				D _{s4.0} 175.23
4	毒性气体分析	TB/T 3237-2010 条款 4.4	气体种类	实测值(ppm)
			CO	164
			CO ₂	7957
			HF	ND
			HBr	ND
			HCl	ND
			NO _x (以 NO ₂ 计)	ND
			SO ₂	ND
			HCN	ND

其中 ND 表示未发现。

* 测试详细信息, 参见本报告的附录。



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1/F, 1 Building, European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde Foshan, Guangdong, China 528333 t (86-757) 22805888 f (86-757) 22805858 www.sgs.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757) 22805888 f (86-757) 22805858 sgs.china@sgs.com

检测报告

编号: SDFS2303001583FF_CN 日期: 2023-04-06 页码: 第 3 页共 10 页

III. 技术要求

内装材料燃烧后毒性气体指标

气体种类	浓度 mg/m ³ (ppm)
CO	<4000 (3500)
CO ₂	<90000 (50000)
HF	<82 (100)
HBr	<330 (100)
HCl	<150 (100)
NO _x (以NO ₂ 计)	<190 (100)
SO ₂	<260 (100)
HCN	<110 (100)



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1/F, 1st Building, European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde Foshan, Guangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgs.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 sgs.china@sgs.com

检测报告

编号: SDFS2303001583FF_CN

日期: 2023-04-06

页码: 第 4 页共 10 页

内装材料氧指数及燃烧性能指标

材料		氧指数 %	燃烧性 级
顶板板材、饰面材料及其密封连接材料	板材、饰面材料	≥35	A
	密封连接材料	≥30	A、B
侧板、墙壁板、饰面材料及其密封连接材料	侧板、墙壁板、饰面材料	≥32	A
	密封连接材料	≥30	A、B
构成门的材料		≥32	A、B
窗帘、遮光帘		≥30	A、B
灯罩		≥32	A、B
座椅、卧铺	非金属构架	≥35	A
	蒙面布	≥32	A
	弹性垫材	≥28	A、B
地板、地板布以及连接材料	地板、地板布	≥30	A、B
	连接材料	≥28	
构成行李架的非金属材料		≥32	A
卫生间（盥洗室）板材、饰面材料及其密封材料	板材、饰面材料	≥35	A
	密封材料	≥30	A、B
防腐密封降噪材料	车内用阻尼涂料	≥32	A
	门窗密封材料	≥28	A、B
防寒材料	高分子材料类	≥32	A、B
	无机材料类	≥45	A
空调风道与内壁及其连接密封用材料		≥32	A
其他附件 ^a		与其所使用部位要求一致	

^a在材料选择上，应优先选用燃烧性等级为A的材料，如采购方与生产方同意，也可选用燃烧性等级为B级的材料。

内装材料烟密度指标

燃烧方式	D _{s1.5}	D _{s4.0}
无引燃模式	≤100	≤200
引燃模式	≤100	≤200



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

11/F, Building European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde Foshan, Guangdong, China 528333 t (86-757) 22805888 f (86-757) 22805858 www.sgs.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757) 22805888 f (86-757) 22805858 sgs.china@sgs.com

检测报告

编号: SDFS2303001583FF_CN 日期: 2023-04-06 页码: 第 5 页共 10 页

测试数据:

附录 1. 氧指数测试

1.1 测试方法

本试验按照 GB/T 2406.2-2009 塑料 用氧指数法测定燃烧行为 第 2 部分 室温试验进行。

1.2. 预处理

T: (23±2) °C, R.H: (50±5)% 至少调节 88h。

1.3. 测试结果

试样类型: III 点燃方法: 顶面点燃法

氧指数 [浓度, % (V/V)]: 42.8 [圆整到 0.1 % (V/V)]氧气浓度步长(d): 0.2 % (V/V)标准偏差 $\hat{\sigma}$: 0.195燃烧现象: 烧焦

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1/F, 1st Building, European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde Foshan, Guangdong, China 528333 t (86-757) 22805888 f (86-757) 22805858 www.sgs.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757) 22805888 f (86-757) 22805858 sgs.china@sgs.com

检测报告

编号: SDFS2303001583FF_CN 日期: 2023-04-06 页码: 第 6 页共 10 页

附录 2. 燃烧性能

2.1. 测试方法

该测试按照 UIC 564-2:1991 附录 4: 测定钢性非热塑性材料防火性能的测试方法进行。

2.2. 预处理

T: (20~24)°C, R.H: (50~65)%, 至少 48h。

2.3. 测试结果

项目	1	2	3	4	均值
在酒精火焰熄灭后续燃时间(s)	0	0	0	0	0
在酒精火焰熄灭后阴燃时间 (s)	0	0	0	0	0
火焰破坏的表面积(cm ²)	36	42	42	42	40
燃烧颗粒和落下物的释放 (是/否)	否	否	否	否	-
是否样品燃烧至上部边缘 (是/否)	否	否	否	否	-

评级: A 级

材料测试按照下述方针进行分类

持续燃烧时间 (s) (1) 表面区域 (cm ²) (2)	P≤2	2<P≤10	P>10
S≤100			
100<S≤150			
S>150			

(1)P=酒精火焰熄灭后的火焰续燃时间, 以秒计。

(2)S=测试后样品表面的损毁面积, 以 cm² 计。



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

11/F, Building European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde Foshan, Guangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgs.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 sgs.china@sgs.com

检测报告

编号: SDFS2303001583FF_CN 日期: 2023-04-06 页码: 第 7 页共 10 页

等级 A:

所有样品的单个结果都落入白框内且满足下列条件且没有 1 个样品具有:

- 达到样品上边缘
- 观察到燃烧的碎片或滴落
- 观察酒精火焰熄灭后的阴燃时间超过 10 秒

等级 B:

所有样品的续燃时间平均值和损毁区域面积落入灰色或白色区域内

此外, 满足没有 1 个样品:

- 达到上部边缘
- 观察释放燃烧的碎片或滴落
- 观察酒精火焰熄灭后的阴燃时间超过 10 秒钟

等级 C:

所有样品测试结果不满足 A 级和 B 级的情况下归类为 C 级



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1/F, 1st Building, European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde Foshan, Guangdong, China 528333 t (86-757) 22805888 f (86-757) 22805858 www.sgs.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757) 22805888 f (86-757) 22805858 sgs.china@sgs.com

检测报告

编号: SDFS2303001583FF_CN 日期: 2023-04-06 页码: 第 8 页共 10 页

附录 3. 烟密度测试

3.1. 测试方法

GB/T 8323.2-2008 《塑料—烟生成—第 2 部分:单室法测量烟密度试验方法》

3.2. 预处理

T:(23±2)℃, R.H:(50±10)%, 直到样品的重量按标准要求达到质量恒定状态。

3.3. 测试结果

1) 测试模式: 辐射强度 25 kW/m², 无引燃火焰

测试样品	1 st	2 nd	3 rd	均值
质量 (g)	69.0	71.8	69.6	70.1
$D_{s,max}$	408.92	413.14	405.95	409.34
$T(D_{s,max})$ [min:s]	13:08	14:46	15:00	---
$D_{s1.5}$	0.00	0.00	0.00	0.00
$D_{s4.0}$	107.76	131.79	116.25	118.60
D_{s10}	393.77	399.17	395.00	395.98
D_c	3.40	0.00	0.00	---
观察	无焰燃烧			

2) 测试模式: 辐射强度 25 kW/m², 引燃火焰

测试样品	1 st	2 nd	3 rd	均值
质量 (g)	73.5	70.8	69.5	71.3
$D_{s,max}$	334.39	298.39	391.42	341.40
$T(D_{s,max})$ [min:s]	14:01	14:40	15:00	---
$D_{s1.5}$	0.00	0.00	0.37	0.12
$D_{s4.0}$	183.80	161.19	180.70	175.23
D_{s10}	306.55	281.90	316.17	301.54
D_c	30.41	14.55	17.19	---
观察	有焰燃烧			

备注:

 $D_{s1.5}$ —测试开始 1.5min 时的比光密度; $D_{s4.0}$ —测试开始 4.0min 时的比光密度; $D_{s,max}$ —整个测试期间 (20min) 内最大比光密度; $T(D_{s,max})$ —发生最大比光密度 $D_{s,max}$ 时的时间, 单位 min:s; D_c —清晰光束校正因子; D_{s10} —测试开始 10min 时的比光密度。

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1/F, 1st Building, European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde Foshan, Guangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgs.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 sgs.china@sgs.com

检测报告

编号: SDFS2303001583FF_CN 日期: 2023-04-06 页码: 第 9 页共 10 页

附录 4. 毒性气体分析

4.1. 测试方法

TB/T 3237-2010 《动车组用内装材料阻燃技术条件》条款 4.4 毒性气体分析

4.2. 样品处理

T:(23±2)°C,R.H:(50±10)%,直到样品的重量按标准要求达到质量恒定状态。

4.3. 测试结果

测试模式: 辐射照度为25 kW/m²,有引燃火焰

表3

气体种类	要求浓度 mg/m ³ (ppm)	实测值(ppm)	是否符合
CO	<4000 (3500)	164	符合
CO ₂	<90000 (50000)	7957	符合
HF	<82(100)	ND	符合
HBr	<330 (100)	ND	符合
HCl	<150 (100)	ND	符合
NO _x (以NO ₂ 计)	<190 (100)	ND	符合
SO ₂	<260 (100)	ND	符合
HCN	<110 (100)	ND	符合

其中 ND 表示未发现。

声明:

本试验结果得出的产品性能是在特殊条件下的检验结果。在实际应用中, 它们不能单独作为评价该产品潜在火灾、烟气和毒性危险性的依据

本测试结果仅代表被测试试样, 成分、厚度等试样的任何微小的变化可能会导致测试结果的巨大变化, 因此此测试结果对此无效。实际应用时, 在材料的提供和使用上需要格外小心以保证使用的材料充分代表测试试样。

测试试样由申请者提供, SGS-CSTC顺德分公司没有涉及任何的选样和取样计划和程序。

注: 未获得本公司书面批准, 本文件不得进行复制, 全文除外。



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

11/F, Building European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde Foshan, Guangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgs.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 sgs.china@sgs.com


检测报告

编号: SDFS2303001583FF_CN

日期: 2023-04-06

页码: 第 10 页共 10 页

附录照片

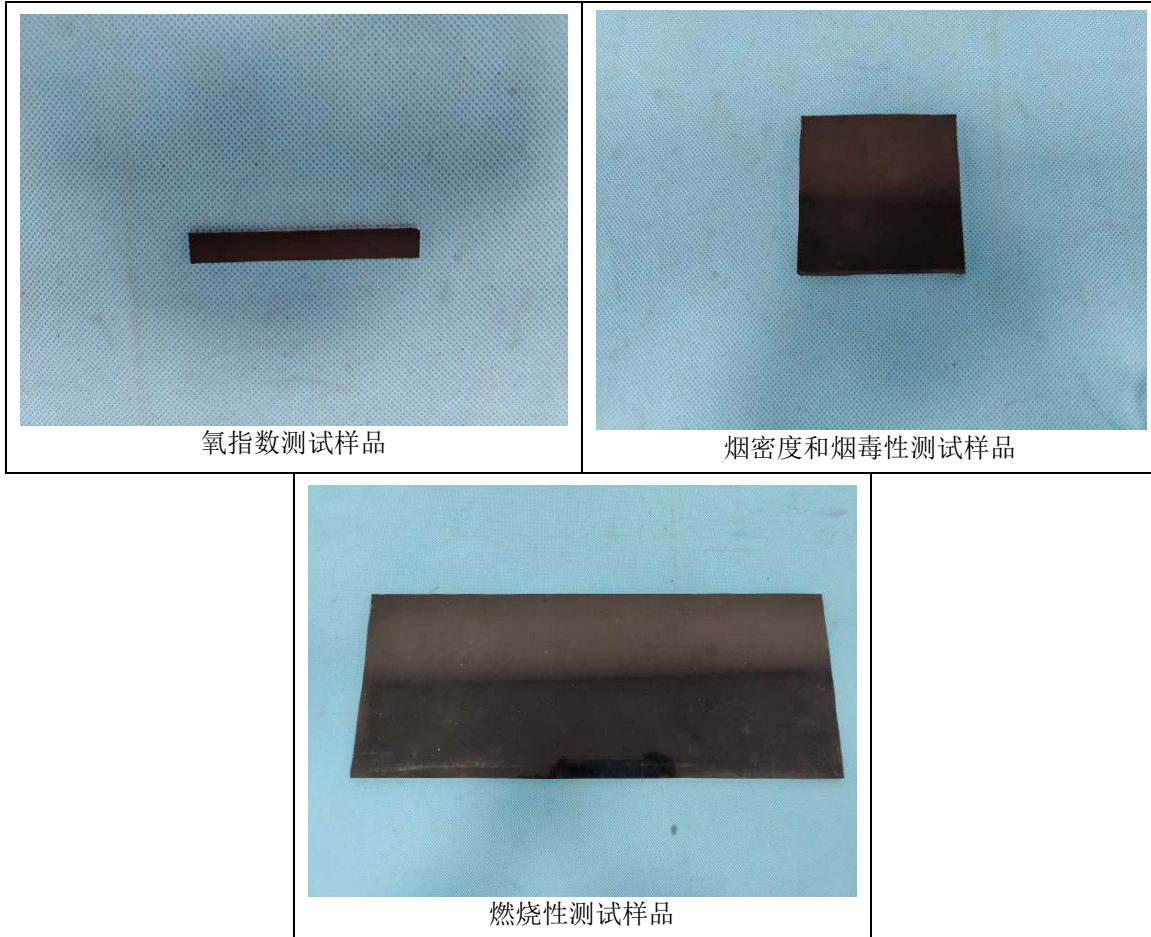

报告结束



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1/F, 1 Building, European Industrial Park, No.1 Shunhe South Road, Wusha Section, Daliang Town, Shunde, Foshan, Guangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgs.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 sgs.china@sgs.com