

Flammable materials list and results  
易燃材料清单及结果

System:/系统: Window for Shenzhen additionalpurchase/深圳增购项目      Compiled by:/编制的: HANDONG/韩东  
Contract:/合同: Shenzhen additionalpurchase/深圳增购项目      Revision:/修订: A01

| REV# | Item#/项目 | Item Description<br>项目描述 | Part and Product<br>Number/产品编号 | Supplier/供应商                             | Material/材料 | Surface Area<br>(cm <sup>2</sup> )<br>表面区域 | Weight<br>(kg)<br>重量 | Report number 报告编号                    |
|------|----------|--------------------------|---------------------------------|------------------------------------------|-------------|--------------------------------------------|----------------------|---------------------------------------|
| 1    | Window   | Windshield               | CV3039220H01                    | Shenyang Liaohe special glass<br>factory | 回天 8955     | 0                                          | 0.064                | Document No. :<br>AJFS2104003183FF-01 |
|      |          |                          |                                 |                                          |             |                                            |                      |                                       |
|      |          |                          |                                 |                                          |             |                                            |                      |                                       |



中国认可  
国际互认  
检测  
TESTING  
CNAS L4743

## Test Report

No. AJFS2104003183FF

Date: APR.28, 2021

Page 1 of 11

HUBEI HUITIAN NEW MATERIALS STOCK CO., LTD

NO.7 HANGTAI ROAD NATIONAL HIGH AND NEW TECHNOLOGY DEVELOPMENT ZONE XIANGYANG  
CITY HUBEI PROVINCE CHINA

**Sample Name:** 8955 PU

**SGS Ref No.:** WHIN2104001500SC

**Style/Item No.:** /

The above sample(s) was / were submitted and identified on behalf of the client. SGS is not responsible for the authenticity, integrity and results of the data and information and / or the validity of the conclusion arising therefrom. Results apply to the sample as received.

\*\*\*\*\*

### Test Requested:

EN 45545-2:2013+A1:2015 Railway applications—Fire protection on railway vehicles Part 2: Requirements for fire behaviour of materials and components, and testing according to Table 5 — Material requirement sets (R1)

**Test Results:** -- See attached sheet --

### Test Period:

Sample Receiving Date : APR.19, 2021

Test Performing Date : APR.19, 2021 TO APR.26, 2021

Signed for and on behalf of  
SGS-CSTC Co., Ltd. Anji Branch

Allen Zou  
Lab Manager

scan to see the report



AJFS2104003183FF



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgsgroup.com.cn  
中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e sgs.china@sgs.com

Member of the SGS Group (SGS SA)

# Test Report

No. AJFS2104003183FF

Date: APR.28, 2021

Page 2 of 11

## I. Description of Test specimens

|                        |                                               |
|------------------------|-----------------------------------------------|
| Sample description     | Glue + Aluminum plate                         |
| Color                  | Black / Silver                                |
| Exposed (test) surface | The black surface                             |
| Size of specimens      | T02 ISO 5658-2: About 800mm×155mm×2.8mm       |
|                        | T03.01 ISO 5660-1: About 100mm×100mm×2.8mm    |
|                        | T10.01/ T10.02/ T11.01: About 75mm×75mm×2.8mm |
| Substrate              | Aluminium plate / 2.0mm / Silver              |

## II. Summary of test results

| Requirement set<br>(used for)                                                                                 | Test method reference                            | Parameter Unit                           | Test results * |
|---------------------------------------------------------------------------------------------------------------|--------------------------------------------------|------------------------------------------|----------------|
| R1<br>(IN1A; IN1B; IN1D;<br>IN1E; IN4;<br>IN5; IN6A;<br>IN7; IN8;<br>IN9B;<br>IN11; IN12A; IN12B;<br>IN14;F5) | T02<br>ISO 5658-2                                | <i>CFE</i><br>kW/m <sup>2</sup>          | 50.0           |
|                                                                                                               | T03.01<br>ISO 5660-1: 50 kW/m <sup>2</sup>       | <i>MARHE</i><br>kW/m <sup>2</sup>        | 0.9            |
|                                                                                                               | T10.01<br>EN ISO 5659-2:<br>50 kW/m <sup>2</sup> | <i>Ds</i> (4)<br>dimensionless           | 0.7            |
|                                                                                                               | T10.02<br>EN ISO 5659-2:<br>50 kW/m <sup>2</sup> | <i>VOF</i> <sub>4</sub><br>min           | 1.7            |
|                                                                                                               | T11.01<br>EN ISO 5659-2:<br>50 kW/m <sup>2</sup> | <i>CIT</i> <sub>G</sub><br>dimensionless | 0.022          |

\* For the test details, please see the appendix of this test report.

## III. Conclusion

According to the test results, the submitted sample **meets** the requirements of R1 (detailed in Table 5 of EN 45545-2:2013+A1:2015) for **HL3** Hazard Level Classification.

To be continued...



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e sgs.china@sgs.com

# Test Report

No. AJFS2104003183FF

Date: APR.28, 2021

Page 3 of 11

## Test Criteria for EN 45545-2:2013+A1:2015 Table 5 Material requirement sets (R1)

| Requirement set (used for)                                                                                              | Test method reference                            | Parameter Unit                    | Requirement Definition | HL1     | HL2     | HL3     |
|-------------------------------------------------------------------------------------------------------------------------|--------------------------------------------------|-----------------------------------|------------------------|---------|---------|---------|
| R1<br>(IN1A; IN1B;<br>IN1D; IN1E;<br>IN4;<br>IN5; IN6A;<br>IN7; IN8;<br>IN9B;<br>IN11; IN12A;<br>IN12B;<br>IN14;<br>F5) | T02<br>ISO 5658-2                                | CFE<br>kW/m <sup>2</sup>          | Minimum                | 20<br>a | 20<br>a | 20<br>a |
|                                                                                                                         | T03.01<br>ISO 5660-1:<br>50 kW/m <sup>2</sup>    | MARHE<br>kW/m <sup>2</sup>        | Maximum                | a<br>-  | 90      | 60      |
|                                                                                                                         | T10.01<br>EN ISO 5659-2:<br>50 kW/m <sup>2</sup> | Ds(4)<br>dimensionless            | Maximum                | 600     | 300     | 150     |
|                                                                                                                         | T10.02<br>EN ISO 5659-2:<br>50 kW/m <sup>2</sup> | VOF <sub>4</sub><br>min           | Maximum                | 1200    | 600     | 300     |
|                                                                                                                         | T11.01<br>EN ISO 5659-2:<br>50 kW/m <sup>2</sup> | CIT <sub>G</sub><br>dimensionless | Maximum                | 1.2     | 0.9     | 0.75    |

<sup>a</sup> If flaming droplets/particles are reported according to 5.3.7 EN 45545-2:2013+A1:2015, during the test ISO 5658-2, or for the special case of materials which do not ignite in ISO 5658-2 and are additionally reported as unclassifiable, the following requirements shall be added:

Test to the requirements of EN ISO 11925-2 with 30s flame application.

The acceptance requirements are:

--- flame spread < 150 mm within 60s;

--- no burning droplets/particles.

### Statements:

This declaration of conformity is only based on the result of this laboratory activity, the impact of the uncertainty of the results was not included.

The test results relate to the behaviour of the test specimens of a product under the particular conditions of the test; they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use.

The test results relate only to the specimens of the product in the form in which were tested.

To be continued...



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e sgs.china@sgs.com

# Test Report

No. AJFS2104003183FF

Date: APR.28, 2021

Page 4 of 11

## APPENDIX 1: T02 ISO 5658-2:2006 Lateral flame spread

### 1. Conditioning

T: 23±2°C, R.H: 50±5%, until the test sample was conditioned to constant mass.

### 2. Test results

| Specimen No.:                | 1     |     | Heat for Sustained Burning (MJ/m <sup>2</sup> ) | 2     |       | Heat for Sustained Burning (MJ/m <sup>2</sup> ) | 3     |     | Heat for Sustained Burning (MJ/m <sup>2</sup> ) |
|------------------------------|-------|-----|-------------------------------------------------|-------|-------|-------------------------------------------------|-------|-----|-------------------------------------------------|
| Weight (g)                   | 854.3 |     |                                                 | 858.4 |       |                                                 | 849.9 |     |                                                 |
| Time to Ignition: (min: sec) | 0:33  |     |                                                 | 0:28  |       |                                                 | 0:30  |     |                                                 |
| Time to Travel               | min   | sec |                                                 | min   | sec   |                                                 | min   | sec |                                                 |
| 50 mm                        | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 100 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 150 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 200 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 250 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 300 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 350 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 400 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 450 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 500 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 550 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 600 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 650 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 700 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| 750 mm                       | -     | -   | -                                               | -     | -     | -                                               | -     | -   |                                                 |
| Duration of Test (min: sec)  | 10:33 |     | 10:28                                           |       | 10:30 |                                                 |       |     |                                                 |
| Final Travel (mm)            | 30    |     | 30                                              |       | 40    |                                                 |       |     |                                                 |
| CFE (kW/m <sup>2</sup> )     | 50.0  |     | 50.0                                            |       | 50.0  |                                                 |       |     |                                                 |

**Observations during test:** None

Calculated from the data in above table for each specimen for each of the parameters

| PARAMETER                                                       | Specimen No. |      |      |      | Avg  |
|-----------------------------------------------------------------|--------------|------|------|------|------|
|                                                                 | 1            | 2    | 3    | 4    |      |
| Average Heat for Sustained Burning (Qsb) (MJ/m <sup>2</sup> )   | -            | -    | -    | -    | -    |
| Critical Heat Flux at Extinguishment (CFE) (kW/m <sup>2</sup> ) | 50.0         | 50.0 | 50.0 | 50.0 | 50.0 |

Remark:

“-” indicates the flame did not spread to 150mm.

To be continued...



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
 中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e sgs.china@sgs.com



## APPENDIX 2: T03.01 ISO 5660-1:2015/Amd.1:2019 Reaction-to-fire tests -- Heat release, smoke production and mass loss rate – Part 1: Heat release rate (cone calorimeter method) and smoke production rate (dynamic measurement), Heat flux 50 kW/m<sup>2</sup>

### 1. Conditioning

T: 23 ± 2°C, R.H: 50 ± 5%, until the test sample was conditioned to constant mass.

### 2. Test result

|                                                                                                              |            |        |        |         |
|--------------------------------------------------------------------------------------------------------------|------------|--------|--------|---------|
| Test orientation                                                                                             | Horizontal |        |        |         |
| The exposed surface area of the test specimen / m <sup>2</sup>                                               | 0.0088     |        |        |         |
| Irradiance / (kW/m <sup>2</sup> )                                                                            | 50         |        |        |         |
| Distance between the cone base plate and the upper specimen surface / (mm)                                   | 25         |        |        |         |
| Specimen No.                                                                                                 | 1          | 2      | 3      | Average |
| Initial mass / g                                                                                             | 64.0       | 60.1   | 68.8   | 64.3    |
| Mass at sustained flaming / g                                                                                | —          | —      | —      | —       |
| Remained mass / g                                                                                            | 62.1       | 58.2   | 67.1   | 62.5    |
| Sample Mass Loss / g/m <sup>2</sup>                                                                          | 210.0      | 220    | 190.0  | 206.7   |
| Average Mass Loss Rate $\dot{m}$ / (g·m <sup>-2</sup> ·s <sup>-1</sup> )                                     | 0.2        | 0.2    | 0.2    | 0.2     |
| Average rate of specimen mass loss per unit area $\dot{m}_{A,10-90}$ / (g·m <sup>-2</sup> ·s <sup>-1</sup> ) | 0.2        | 0.2    | 0.3    | 0.2     |
| Flashing or transitory flaming time at/s                                                                     | —          | —      | —      | —       |
| Time to sustained flaming / s                                                                                | —          | —      | —      | —       |
| Whether re-insert the spark igniter <sup>1)</sup>                                                            | NO         | NO     | NO     | —       |
| Maximum heat release rate per unit area / (kW/m <sup>2</sup> )                                               | 1.1        | 1.9    | 2.2    | 1.8     |
| Average heat release rate per unit area for 180s after ignition / (kW/m <sup>2</sup> ) <sup>2)</sup>         | —          | —      | —      | —       |
| Average heat release rate per unit area for 300s after ignition / (kW/m <sup>2</sup> )                       | —          | —      | —      | —       |
| Total heat release / (MJ/m <sup>2</sup> )                                                                    | 0.7        | 0.8    | 0.9    | 0.8     |
| Average effective heat of combustion / (MJ/kg)                                                               | —          | —      | —      | —       |
| Total smoke production per unit area over the non-flaming phase / m <sup>2</sup> m <sup>-2</sup>             | 33.7       | 35.6   | 54.3   | 41.2    |
| Total smoke production per unit area over the flaming phase / m <sup>2</sup> m <sup>-2</sup>                 | —          | —      | —      | —       |
| Test duration / s <sup>3)</sup>                                                                              | 1200.0     | 1200.0 | 1200.0 | 1200.0  |
| Maximum value of average rate of heat emission (MARHE) / KW/m <sup>2</sup>                                   | 0.6        | 0.8    | 1.2    | 0.9     |
| Additional observations <sup>4)</sup>                                                                        | ---        |        |        |         |
| Special mounting procedures <sup>5)</sup>                                                                    | f          |        |        |         |
| Whether the specimen is suitable for the testing <sup>8)</sup>                                               | Suitable   |        |        |         |

\* The samples did not ignite.

To be continued...



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
 中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e sgs.china@sgs.com

## Test Report

No. AJFS2104003183FF

Date: APR.28, 2021

Page 6 of 11

### Remark:

- 1) If the flame extinguishes in less than 60 s after turning off the spark, re-insert the spark igniter and turn on the spark within 5 s, do not remove the spark until the entire test is completed.
- 2) The 180 s mean heat release readings shall be compared for the three specimens. If any of these mean readings differ by more than 10 % from the arithmetic mean of the three readings, then a further set of three specimens shall be tested unless the mean value is less than 10 kW m<sup>-2</sup>.
- 3) Collect all data until:  
The data collection interval shall be 2 s and data collection shall be terminated at 20 min.
- 4) Observe and record physical changes to the sample such as melting, swelling, and cracking.
- 5) Special mounting procedures that were used:
  - ☐ a. Samples that intumesce or deform so that they contact the spark plug prior to ignition, or the underside of the cone heater after ignition, shall be tested with the separation of 60 mm between the base plate of the cone heater and the upper surface of the specimen.
  - ☐ b. Other dimensionally unstable products, for example products that warp or shrink during testing, shall be restrained against excessive movement. This shall be accomplished with 4 tie wires. A tie wire is then looped around the sample holder and retainer frame assembly, so that it is parallel to and approximately 20 mm away from one of the 4 sides of the assembly. The ends of the wire are twisted together such that the wire is pulled firmly against the retainer frame. Excess wire is trimmed from the twisted section before testing. The 3 remaining wires shall be fitted around the specimen holder and retainer frame assembly in a similar manner, parallel to the three remaining sides.
  - ☐ c. Materials that distort so extensively that they cannot be held by 4 wires should be tested using the fine wire grid made of (0,8 ± 0,1) mm with wire spacing of (20 ± 2) mm.
  - ☐ d. Materials that intumesce in a fluid phase such that molten materials overflow the edge frame or seep between the edge frame and the specimen holder invalidate the test. Therefore, such materials should be tested without the edge frame and should be housed in 0,1 mm thick aluminum tray wrappings which extends 10mm above the top edge of the test specimen.
  - ☐ e. Materials, such as fibres, which need to be both physically restrained or compressed to be tested at installed densities should be tested in a wire cage structure made of (1,0 ± 0,1) mm steel wire with (9 ± 1) mm spacing which provides appropriate artificial boundaries to enable the materials to be tested.
  - ☒ f. No special mounting procedures that were used.
- 6) Heat release rate (per unit area), expressed in kilowatts per square metre curve of specimens is given in figure 1.
- 7) The orifice constant is 0.043; the exhaust flow rate is 0.024±0.002 m<sup>3</sup>/s.
- 8) If, when tested with a separation of 60 mm between the cone heater base plate and the upper surface of the specimen, the specimen still intumesces or deforms such that it contacts the spark plug prior to ignition, or the upper specimen surface reaches the level of the cone heater baseplate, the specimen is not suitable for the testing to this document.

To be continued...



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e sgs.china@sgs.com

Curve:

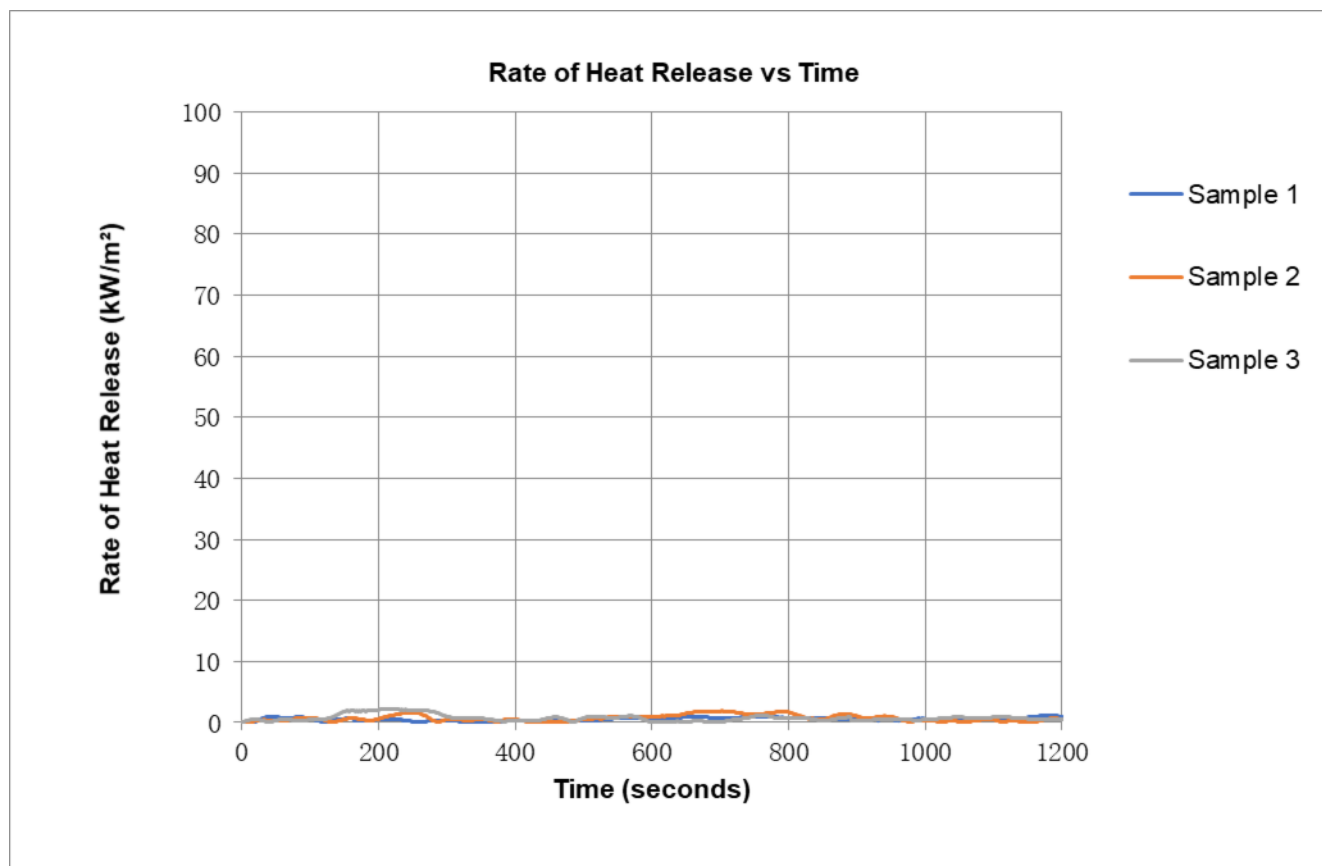


Figure 1 --- Rate of Heat Release vs Time

To be continued...



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: [CN.Doccheck@sgs.com](mailto:CN.Doccheck@sgs.com)

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e [sgs.china@sgs.com](mailto:sgs.china@sgs.com)



# Test Report

No. AJFS2104003183FF

Date: APR.28, 2021

Page 8 of 11

## **APPENDIX 3: T10.01&T10.02 EN ISO 5659-2:2017 Plastics—Smoke generation — Part 2: Determination of optical density by a single- chamber test. Heat flux 50kW/m<sup>2</sup> without pilot flame, test duration is 10min.**

### **1. Conditioning**

T: 23±2 °C, R.H: 50±5%, until the test sample was conditioned to constant mass.

### **2. Test Results**

| Parameters               | 1    | 2    | 3    | Avg  |
|--------------------------|------|------|------|------|
| Weight (g)               | 35.6 | 36.8 | 39.0 | 37.1 |
| D <sub>s</sub> (1.5)     | 0.7  | 0.4  | 0.1  | 0.4  |
| D <sub>s</sub> (4)       | 1.2  | 0.6  | 0.2  | 0.7  |
| D <sub>s</sub> (10)      | 1.6  | 1.5  | 1.6  | 1.6  |
| VOF <sub>4</sub> min     | 2.9  | 1.7  | 0.6  | 1.7  |
| D <sub>s</sub> max       | 1.6  | 1.5  | 1.6  | 1.6  |
| T (D <sub>s</sub> max) s | 600  | 597  | 595  | /    |

### **NOTE:**

D<sub>s</sub> (n) is the specific optical density at n<sup>th</sup> min.

VOF<sub>4</sub> is the cumulative value of specific optical densities in the first 4 min of the test.

D<sub>s</sub> max is the maximum optical density in the test chamber.

To be continued...



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e sgs.china@sgs.com

Member of the SGS Group (SGS SA)

# Test Report

No. AJFS2104003183FF

Date: APR.28, 2021

Page 9 of 11

## **APPENDIX 4: T11.01 EN 45545-2:2013+A1:2015, Annex C Gas analysis in the smoke chamber EN ISO 5659-2, using FTIR technique. Heat flux 50kW/m<sup>2</sup> without pilot flame, test duration is 10min.**

### **1. Conditioning**

T: 23±2°C and R.H 50±5%, until the test sample was conditioned to constant mass.

### **2. Test results**

#### **1) 4 min after the test start**

| Gas                                | 1    | 2    | 3    | Avg  |
|------------------------------------|------|------|------|------|
| Carbon Dioxide (CO <sub>2</sub> )  | 46.0 | 57.8 | 59.2 | 54.3 |
| Carbon Monoxide (CO)               | 4.7  | 4.6  | 2.1  | 3.8  |
| Hydrogen Fluoride (HF)             | ND   | ND   | ND   | ---  |
| Hydrogen Chloride (HCl)            | 4.6  | 3.9  | 3.5  | 4.0  |
| Hydrogen Bromide (HBr)             | ND   | ND   | ND   | ---  |
| Hydrogen Cyanide (HCN)             | 1.2  | 1.1  | 1.1  | 1.1  |
| Nitrogen Oxides (NO <sub>x</sub> ) | 2.4  | 4.1  | 2.6  | 3.0  |
| Sulphur Dioxide (SO <sub>2</sub> ) | ND   | ND   | ND   | ---  |

#### **2) 8 min after the test start**

| Gas                                | 1     | 2     | 3     | Avg   |
|------------------------------------|-------|-------|-------|-------|
| Carbon Dioxide (CO <sub>2</sub> )  | 467.1 | 371.5 | 373.6 | 404.1 |
| Carbon Monoxide (CO)               | 143.1 | 35.6  | 28.5  | 69.1  |
| Hydrogen Fluoride (HF)             | 1.3   | 0.8   | 0.8   | 1.0   |
| Hydrogen Chloride (HCl)            | 7.6   | 5.9   | 2.9   | 5.5   |
| Hydrogen Bromide (HBr)             | ND    | ND    | ND    | ---   |
| Hydrogen Cyanide (HCN)             | 1.5   | 1.1   | 1.1   | 1.2   |
| Nitrogen Oxides (NO <sub>x</sub> ) | 2.6   | 3.9   | 3.7   | 3.4   |
| Sulphur Dioxide (SO <sub>2</sub> ) | ND    | ND    | ND    | ---   |

Where, ND indicates Non-detected.

Note: All values given are in mg/m<sup>3</sup>.

To be continued...



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: [CN.Doccheck@sgs.com](mailto:CN.Doccheck@sgs.com)

SGS-CSIC Inspection & Testing Services Co., Ltd.  
Anji Branch Fire Technology Service

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e [sgs.china@sgs.com](mailto:sgs.china@sgs.com)

Member of the SGS Group (SGS SA)

### 3) Calculation of $CIT_G$

| Gas component                      | Reference concentration;<br>mg/m <sup>3</sup> |
|------------------------------------|-----------------------------------------------|
| Carbon Dioxide (CO <sub>2</sub> )  | 72 000                                        |
| Carbon Monoxide (CO)               | 1 380                                         |
| Hydrogen Fluoride (HF)             | 25                                            |
| Hydrogen Chloride (HCl)            | 75                                            |
| Hydrogen Bromide (HBr)             | 99                                            |
| Hydrogen Cyanide (HCN)             | 55                                            |
| Nitrogen Oxides (NO <sub>x</sub> ) | 38                                            |
| Sulphur Dioxide (SO <sub>2</sub> ) | 262                                           |

$$CIT_G = 0.0805 \cdot \sum_{i=1}^{i=8} \frac{C_i}{C_i}$$

Where,

$CIT_G$  — Conventional Index of Toxicity;

$C_i$  — Concentration of the  $i^{th}$  gas;

$C_i$  — Reference concentration of the  $i^{th}$  gas.

| PARAMETER       | 1     | 2     | 3     | Avg   |
|-----------------|-------|-------|-------|-------|
| $CIT_G$ (4 min) | 0.012 | 0.015 | 0.011 | 0.013 |
| $CIT_G$ (8 min) | 0.029 | 0.021 | 0.017 | 0.022 |

To be continued...



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CSI Technology Service Co., Ltd.  
Anji Branch Fire Technology Service

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e sgs.china@sgs.com


## Test Report

No. AJFS2104003183FF

Date: APR.28, 2021

Page 11 of 11

### Photo Appendix:

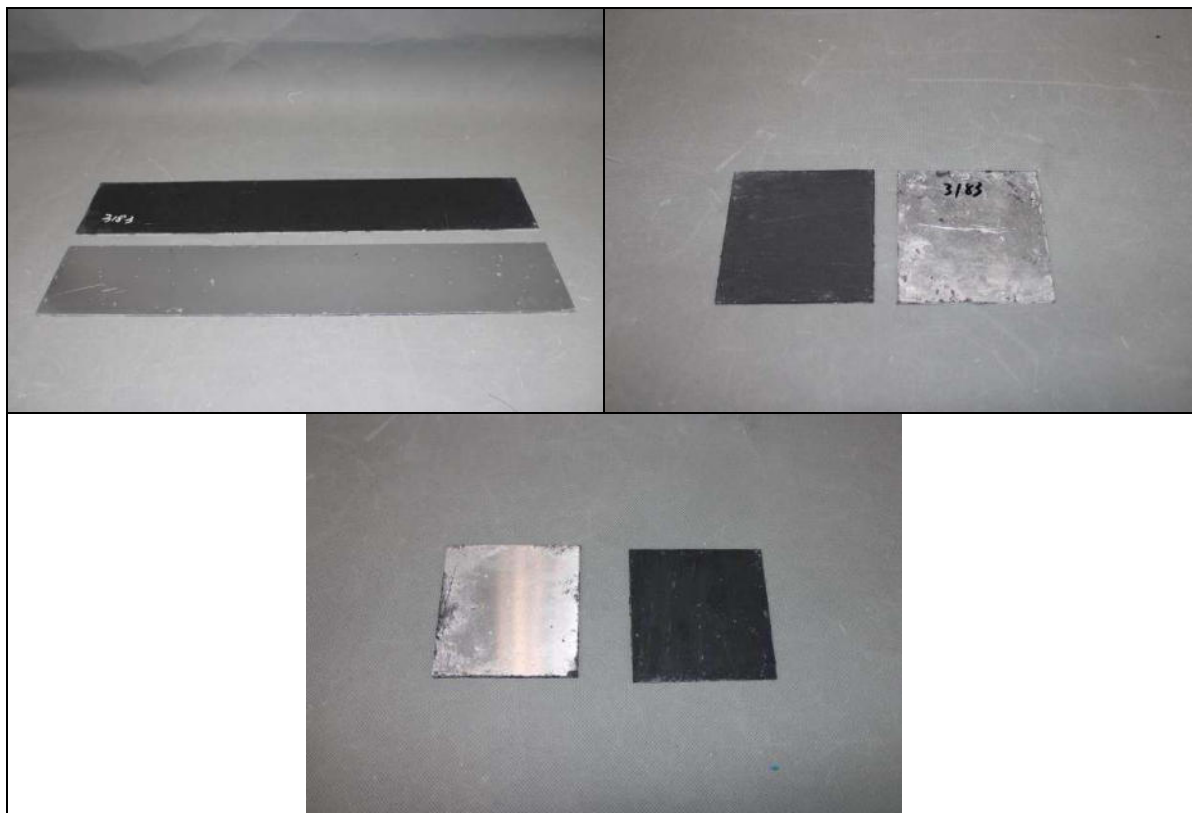

SGS authenticate the photo on original report only

\*\*\*End of Report\*\*\*



SGS (Shanghai) Inspection & Testing Services Co., Ltd.  
Anji Branch Fire Technology Service

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: [CN.Doccheck@sgs.com](mailto:CN.Doccheck@sgs.com)

No. 301, Sunlight Road, 2 Block, Sunlight Industry Zone, Anji County, Zhejiang Province, China 313300 t (86-572) 5018825 f (86-572) 5018829 www.sgs.com.cn  
中国·浙江·安吉县阳光工业园二区阳光大道301号 邮编: 313300 t (86-572) 5018825 f (86-572) 5018829 e [sgs.china@sgs.com](mailto:sgs.china@sgs.com)

Member of the SGS Group (SGS SA)