

Automated Construction of Multi-Element MEAM Interatomic Potentials

A DFT-Informed Neural-Network Optimization Framework

Can Durmaz

METU, Department of Physics

PHYS 400 Final Presentation





Outline

1

Motivation

2

Method: the five-stage pipeline

3

Results

4

Discussion & summary



- The cubic stiffness constants C_{11} , C_{12} , and the derived Young's modulus E and Poisson's ratio ν , are the main design criteria for structural alloys.
- Measuring them is slow and expensive. Classical molecular dynamics recovers the same properties at negligible cost, but only if an accurate interatomic potential is available.
- For metals that potential is usually the Modified Embedded Atom Method (MEAM) [1, 2], the standard semi-empirical form.


Objective

Build MEAM potentials automatically for a chosen set of elements, with no manual parameter fitting and no experimental input.



A material's elastic response is captured by two numbers. For a cubic crystal both follow from the stiffness constants C_{11} and C_{12} , the quantities this work predicts: C_{11} is the stress needed to stretch the crystal along one axis; C_{12} is the sideways stress that builds up while it stretches.


E : resistance to stretching

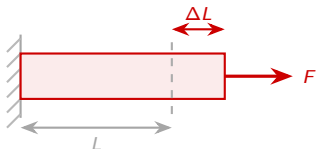

$$E = \frac{\sigma}{\epsilon} = \frac{F/A}{\Delta L/L}$$

Large E means stiff: steel ≈ 200 , Al ≈ 70 GPa.

ν : sideways thinning when pulled

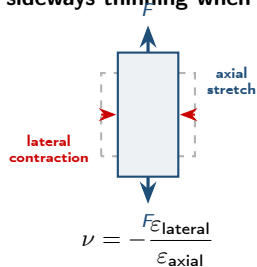

Stretch it and it thins: most metals $\nu \approx 0.3$.

$$E = \frac{(C_{11} - C_{12})(C_{11} + 2C_{12})}{C_{11} + C_{12}}, \quad \nu = \frac{C_{12}}{C_{11} + C_{12}}; \quad \text{stability requires } C_{11} > C_{12} \text{ (Born-Cauchy).}$$



Interatomic potential. Closed-form approximation of the many-body potential energy $U(\{\mathbf{r}_i\})$; forces obtained as $\mathbf{F}_i = -\nabla_i U$.

Historical development:

- Pairwise (Lennard-Jones, Morse): too crude for metals.
- Embedded Atom Method (1984): good for FCC metals.
- **Modified EAM (MEAM)** [1]: adds angular terms and covers BCC, HCP and mixed bonding.

Density-functional theory (DFT).

First-principles electronic-structure method (Kohn–Sham equations [3]); plane-wave + pseudopotential basis in Quantum Espresso [4].

Quantities computed:

- Cohesive energy E_{coh}
- Equilibrium lattice a_0 , bulk modulus B
- Binary formation energies $E_{\text{form}}(i, j)$
- Single-crystal elastic constants C_{11} , C_{12}

DFT: high accuracy, limited scale ($\leq 10^3$ atoms).

MEAM/MD: empirical, large scale ($\geq 10^6$ atoms).

DFT provides the reference dataset against which the MEAM potential is calibrated.



Published MEAM libraries cover disjoint subsets of elements; no single file spans the 12 elements treated in this work.

Library	Al	Co	Cr	Cu	Fe	Mg	Mn	Mo	Ni	Si	Ti	Zn
AlMgZn [5]	✓					✓						✓
AlSiCuMgFe [6]	✓			✓	✓	✓				✓		
CuMo [7]				✓				✓				
FeMnNiTiCuCrCoAl [8]	✓	✓	✓	✓	✓		✓		✓		✓	
Merged (this work)	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓

Limitation of direct merging: cross-interaction parameters between elements drawn from distinct libraries are not defined; manual refitting does not scale to $\binom{12}{2} = 66$ binary pairs.

Pure machine-learning potentials [9–11]: require $10^4 - 10^5$ DFT configurations and forfeit the physical interpretability of MEAM.

02

Method: the five-stage
pipeline



1

Motivation

2


Method: the five-stage pipeline

3

Results

4

Discussion & summary

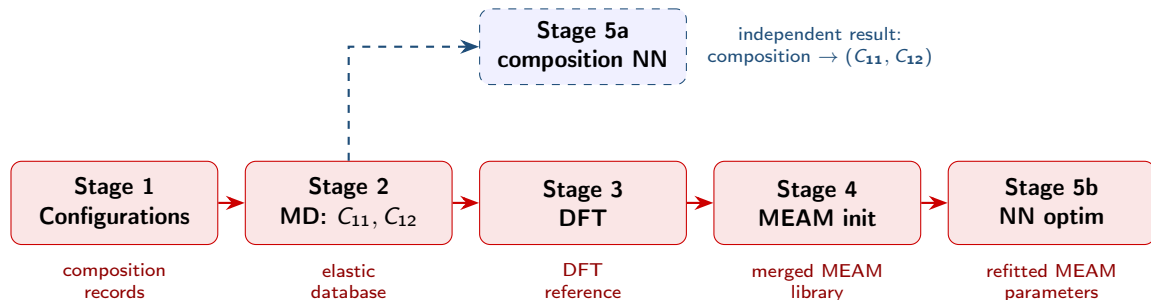

The four published libraries are merged into a single 12-element file; cross-terms are refitted by inverting an NN surrogate of the MEAM $\rightarrow (C_{11}, C_{12})$ map by gradient descent, with single-element parameters anchored to DFT references.



Sampling.

Uniform draws on the 12-element composition space


(Al, Co, Cr, Cu, Fe, Mg, Mn, Mo, Ni, Si, Ti, Zn);

Al-weighted to oversample the aluminium-alloy region.

Dataset statistics.

7879 configurations generated;

7815 retained after the physicality filter
($0 < E < 400$ GPa, $0 < \nu < 0.5$).

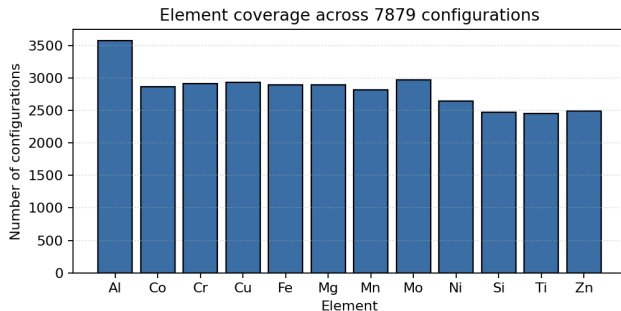

Element-occurrence distribution over the full generated dataset.



Implementation. [12]


LAMMPS molecular dynamics with the 4 published MEAM potentials.

Per-configuration protocol:


- ~ 4 nm cubic supercell
- Anisotropic energy minimisation
- Axial strain $\delta = 10^{-3}$ applied along $\pm x, \pm y, \pm z$
- Central-difference $\rightarrow C_{11}, C_{12}$

	Median	Std.	Range
E (GPa)	103.6	69.1	3 – 398
ν	0.326	0.063	0.01 – 0.50

$N = 7815$ retained configurations.

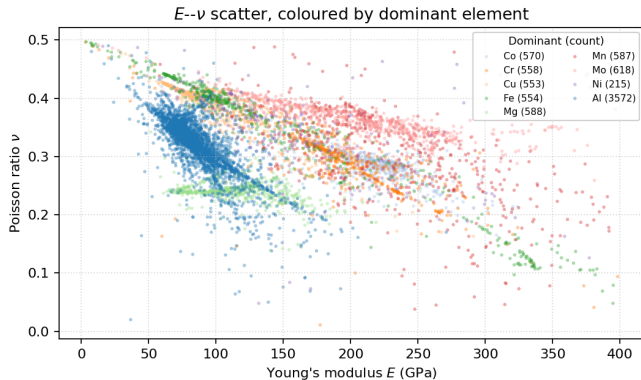

E - ν distribution, coloured by dominant element.




Single-element terms

Each element's (a_0, E_{coh}, B) pins the universal binding curve (spacing, well depth, curvature) and fixes the MEAM decay exponent

$$\alpha = \sqrt{9B\Omega/E_{\text{coh}}} \quad (\Omega : \text{atomic volume}).$$

Scope. 12 elements (FCC/BCC/HCP/diamond); $\alpha \approx 4.5$ (Al, Si) to 10.9 (Zn). PBE–GGA plane waves (Quantum Espresso); a_0, B from an equation-of-state fit.

Cross-terms

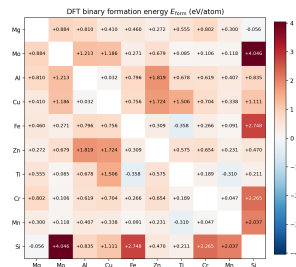

Binary formation energies $E_{\text{form}}(i, j)$ (eV/atom): negative = exothermic mixing, positive = limited solubility; the sign seeds each cross-term.

03

Results



1

Motivation

2

Method: the five-stage pipeline

3

Results

4

Discussion & summary




Architecture. $12 \rightarrow 32 \rightarrow 20 \rightarrow 2$
fully-connected MLP
with ReLU activation; Huber loss on $\hat{C}_{11}, \hat{C}_{12}$;
deep ensemble of five seeds [13] for
epistemic uncertainty.

Result

Validation Set (30 % of the dataset):
 $R_E^2 = 0.77$, $R_\nu^2 = 0.52$.

Al 7075 Example: $\hat{E} = 75.5$ GPa, $\hat{\nu} = 0.334$
(published: 71–72 GPa, $\nu \approx 0.33$; within $\sim 5\%$).

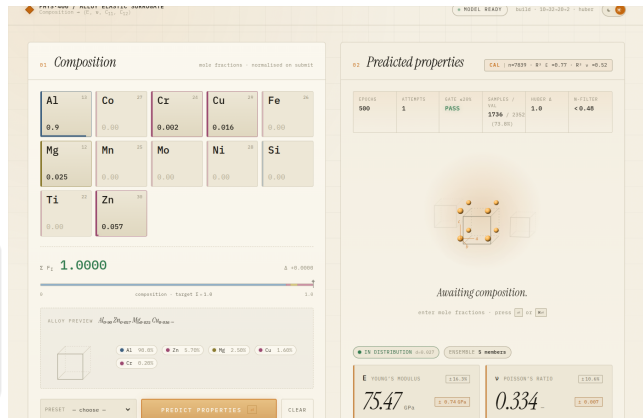

Interactive composition predictor.



Closed-loop procedure

- 1 **Surrogate.** A small MLP learns (MEAM params) $\rightarrow (C_{11}, C_{12})$.
- 2 **Fit.** Train it with Adam [14] on a Huber loss.
- 3 **Invert.** Descend through the *frozen* surrogate to the parameters that hit the target (C_{11}, C_{12}) .
- 4 **Loop.** Re-evaluate in LAMMPS, append samples, retrain.

Adam adapts the step size per parameter; the Huber loss keeps outlier (Mg/Zn) configurations from dominating the fit.



Surrogate Huber loss decays 0.30 $\rightarrow$ 0.16 over training.

Result: a working proof of concept

Tested on **30 unseen alloys**: **11** were physically stable, and **4** matched the MD reference within $\sim 20\%$. Accuracy grows with more data and longer training.



By material family ($N = 42$)

Family	N	E MAPE (%)		ν MAPE (%)	
		ML	MEAM	ML	MEAM
Aluminium	33	2.3	7.4	4.0	4.5
Titanium	6	11.6	140.0	13.2	14.6
Stainless	3	69.6	324.1	75.5	47.3
Overall	42	8.5	42.2	7.2	7.1

Aluminium by AA series ($N = 33$)

Al series	N	$\langle E_{lit} \rangle$ (GPa)	E MAPE (%)	
			ML	MEAM
2xxx (Al-Cu)	11	72.7	1.3	8.0
5xxx (Al-Mg)	9	70.5	2.1	7.9
6xxx (Al-Mg-Si)	7	68.9	3.8	4.2
7xxx (Al-Zn-Mg)	6	71.8	2.8	9.3
All aluminium	33	71.1	2.3	7.4

Both surrogates reproduce aluminium Young's modulus to within a few percent (ML 2.3 %, MEAM 7.4 %) across all four alloy series; error grows only *off* the Al-rich design domain, steeply for MEAM and gently for the composition NN.

42 basis-covered alloys; MAPE vs experimental data from ASM/MatWeb [15]. Unphysical MEAM runs excluded.

04

Discussion & summary



1

Motivation

2

Method: the five-stage pipeline

3

Results

4

Discussion & summary



Achieved

- ✓ **Automated 12-element MEAM pipeline.** An end-to-end workflow that assembles a multi-element potential.
- ✓ **Aluminium-alloy elastic prediction.** E , ν and C_{11} , C_{12} obtained from composition.
- ✓ **DFT-seeded, NN-trained MEAM.** First-principles references refit through a neural surrogate.

What comes next

- 1 **More data coverage.** Wider sampling across the composition space and crystal structures.
- 2 **More NN training epochs.** Deeper surrogate convergence before each refit.
- 3 **Denser atomic-cell DFT.** Finer cells and supercell sampling for sharper references.
- 4 **Inverse design.** Specify a target (E, ν) and invert the composition surrogate to propose candidate alloys.

The pipeline already runs end to end; what is left is more data, longer training, denser DFT references, and running the predictor in reverse.



- [1] M. I. Baskes. Modified embedded-atom potentials for cubic materials and impurities. *Physical Review B*, 46(5):2727–2742, 1992. doi: 10.1103/PhysRevB.46.2727.
- [2] Byeong-Joo Lee and M. I. Baskes. Second nearest-neighbor modified embedded-atom-method potential. *Physical Review B*, 64(18):184102, 2001. doi: 10.1103/PhysRevB.64.184102.
- [3] W. Kohn and L. J. Sham. Self-consistent equations including exchange and correlation effects. *Physical Review*, 140(4A):A1133–A1138, 1965. doi: 10.1103/PhysRev.140.A1133.
- [4] Paolo Giannozzi, Stefano Baroni, Nicola Bonini, Matteo Calandra, Roberto Car, Carlo Cavazzoni, Davide Ceresoli, Guido L. Chiarotti, Matteo Cococcioni, Ismaila Dabo, et al. QUANTUM ESPRESSO: a modular and open-source software project for quantum simulations of materials. *Journal of Physics: Condensed Matter*, 21(39):395502, 2009. doi: 10.1088/0953-8984/21/39/395502.
- [5] D E Dickel, M I Baskes, I Aslam, and C D Barrett. New interatomic potential for Mg-Al-Zn alloys with specific application to dilute mg-based alloys. *Modelling and Simulation in Materials Science and Engineering*, 26(4):045010, apr 2018. doi: 10.1088/1361-651x/aabaad.
- [6] B. Jelinek, S. Groh, M. F. Horstemeyer, J. Houze, S. G. Kim, G. J. Wagner, A. Moitra, and M. I. Baskes. Modified embedded-atom method potential for Al, Si, Mg, Cu, and Fe alloys. *Physical Review B*, 85(24):245102, 2012. doi: 10.1103/PhysRevB.85.245102.
- [7] Jiwon Wang, Sang-Ho Oh, and Byeong-Joo Lee. Second-nearest-neighbor modified embedded-atom method interatomic potential for Cu-M (M = Co, Mo) binary systems. *Computational Materials Science*, 178:109627, 2020. doi: 10.1016/j.commatsci.2020.109627.
- [8] Hamed Sharifi and Collin D. Wick. Developing interatomic potentials for complex concentrated alloys of Cu, Ti, Ni, Cr, Co, Al, Fe, and Mn. *Computational Materials Science*, 248:113595, 2025. doi: 10.1016/j.commatsci.2024.113595.



- [9] Jörg Behler and Michele Parrinello. Generalized neural-network representation of high-dimensional potential-energy surfaces. *Physical Review Letters*, 98(14):146401, 2007. doi: 10.1103/PhysRevLett.98.146401.
- [10] Alexander V. Shapeev. Moment tensor potentials: A class of systematically improvable interatomic potentials. *Multiscale Modeling & Simulation*, 14(3):1153–1173, 2016. doi: 10.1137/15M1054183.
- [11] Yuri Mishin. Machine-learning interatomic potentials for materials science. *Acta Materialia*, 214:116980, 2021. doi: 10.1016/j.actamat.2021.116980.
- [12] Aidan P. Thompson, H. Metin Aktulga, Richard Berger, Dan S. Bolintineanu, W. Michael Brown, Paul S. Crozier, Pieter J. in 't Veld, Axel Kohlmeyer, Stan G. Moore, Trung Dac Nguyen, Ray Shan, Mark J. Stevens, Julien Tranchida, Christian Trott, and Steven J. Plimpton. LAMMPS – a flexible simulation tool for particle-based materials modeling at the atomic, meso, and continuum scales. *Computer Physics Communications*, 271:108171, 2022. doi: 10.1016/j.cpc.2021.108171.
- [13] Balaji Lakshminarayanan, Alexander Pritzel, and Charles Blundell. Simple and scalable predictive uncertainty estimation using deep ensembles. In *Advances in Neural Information Processing Systems (NeurIPS)*, volume 30, 2017.
- [14] Diederik P. Kingma and Jimmy Ba. Adam: A method for stochastic optimization. In *International Conference on Learning Representations (ICLR)*, 2015.
- [15] ASM Aerospace Specification Metals, Inc. ASM material data sheets, MatWeb materials database. <https://asm.matweb.com>, 2026. Accessed June 2026.