

Technical Information

Mazda Rhodium White Met, Color 51K for Basecoat



Blend in repair process on the adjacent panel

Demonstrated on a primed fender faded out into the front vehicle door.

Preparation	 Filler patch: P500/P600 with interface soft sanding pad	 Surrounding old paintwork: P1000/ P2000	70-45 Cleaner	 1x	 wipe dry	 Mask the adjacent blending in panel if necessary.	
--------------------	---	---	----------------------	--------	--------------	---	--

Basecoat Step 1 Spray coat 1	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 2.0 bar	 1 normal coat	 Flash off until mat*	
---	-------------------------	-----------------------	------------	----------------------	-------------------	--------------------------	--

*The flash off process can be forced with a suitable Venturi system.

Basecoat Step 1 Spray coat 2	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 2.0 bar	 1 full coat	 Flash off until mat	
---	-------------------------	-----------------------	------------	----------------------	-----------------	-------------------------	--

Note: Demask the adjacent blending in panel after the last spray coat has been flashed off and clean the panel with a tack cloth.

Optional application of Blending Clear:

Blending Clear	45-W10 3 Stage Additive and Blending Clear	45-R45 Reducer	 100:70	 HVLP 1.4 2.0 bar	 1-2 full coats	 No flash off, apply basecoat step 1 directly.	
-----------------------	---	-----------------------	------------	----------------------	--------------------	---	--

Basecoat Step 1 Spray coat 1	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 0.8-1.5 bar	 1-2 coats	 Flash off until mat*	
---	-------------------------	-----------------------	------------	--------------------------	---------------	--------------------------	--

*The flash off process can be forced with a suitable Venturi system.

Blending Clear	45-W10 3 Stage Additive and Blending Clear	45-R45 Reducer	 100:70	 HVLP 1.4 2.0 bar	 1 full coat	 No flash off, apply basecoat step 2 directly.	
-----------------------	---	-----------------------	------------	----------------------	-----------------	---	--

The data contained in this publication are based on our current knowledge and experience. In view of the many factors that may affect processing and application of our products, these data do not relieve processors from carrying out their own investigations and tests; neither do these data imply any guarantee of certain properties, nor the suitability of the products for a specific purpose. Any descriptions, drawings, photographs, data, proportions, weights etc. given herein are for general information purpose only; they may change without prior information and do not constitute the agreed contractual quality of the products (product specification). It is the responsibility of the recipient of our products to ensure that any proprietary rights and existing laws and legislation are observed.

BASF Coatings GmbH, Automotive Refinish Coatings Solutions, Europe, Glasuritstraße 1, 48165 Münster, Germany

03/2025

Technical Information

Mazda Rhodium White Met, Color 51K for Basecoat



Blend in repair process on the adjacent panel

Demonstrated on a primed fender faded out into the front vehicle door.

Basecoat Step 2 Spray coat 1	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 1.5-2.0 bar	 1 coat	 Flash off until mat	
---	-----------------------------	---------------------------	------------	--------------------------------	---------------	----------------------------	--

Basecoat Step 2 Spray coat 2	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 1.5-2.0 bar	 1 full coat	 No flash off	
---	-----------------------------	---------------------------	------------	--------------------------------	--------------------	------------------	--

Basecoat Step 2 Spray coat 2 Transition area	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 0.8-1.5 bar	 1	 Flash off until mat	
---	-----------------------------	---------------------------	------------	--------------------------------	-------	----------------------------	--

Repeat this step until a uniform transition zone has been achieved.

Basecoat Step 2 Effect coat 1 Transition area	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 1.5-2.0 bar	 1 effect coat	 No flash off	
--	-----------------------------	---------------------------	------------	--------------------------------	----------------------	------------------	--

Basecoat Step 2 Effect coat 1 Fender	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 1.5-2.0 bar	 1 effect coat	 Flash off until mat	
---	-----------------------------	---------------------------	------------	--------------------------------	----------------------	----------------------------	--

Basecoat Step 2 Effect coat 2 Transition area	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 1.5-2.0 bar	 1 effect coat	 No flash off	
--	-----------------------------	---------------------------	------------	--------------------------------	----------------------	------------------	--

Basecoat Step 2 Effect coat 2 Fender	45 Line Basecoat	45-R45 Reducer	 100:70	 HVLP 1.4 1.5-2.0 bar	 1 effect coat	 10-15 Flash off before clear coat application*	
---	-----------------------------	---------------------------	------------	--------------------------------	----------------------	--	--

Note: Repeat the application of Basecoat Step 2 of mixing formula (effect coat 2 transition area and fender incl. flash off) until the number of spray coats of the initially selected spray out card is reached. This is likely to be at least 2 to 4 coats.

The data contained in this publication are based on our current knowledge and experience. In view of the many factors that may affect processing and application of our products, these data do not relieve processors from carrying out their own investigations and tests; neither do these data imply any guarantee of certain properties, nor the suitability of the products for a specific purpose. Any descriptions, drawings, photographs, data, proportions, weights etc. given herein are for general information purpose only; they may change without prior information and do not constitute the agreed contractual quality of the products (product specification). It is the responsibility of the recipient of our products to ensure that any proprietary rights and existing laws and legislation are observed.


Technical Information

Mazda Rhodium White Met, Color 51K for Basecoat



Safety instructions:

**The products are suitable for professional use only.
It cannot be ruled out that this product contains particles < 0.1 µm.**

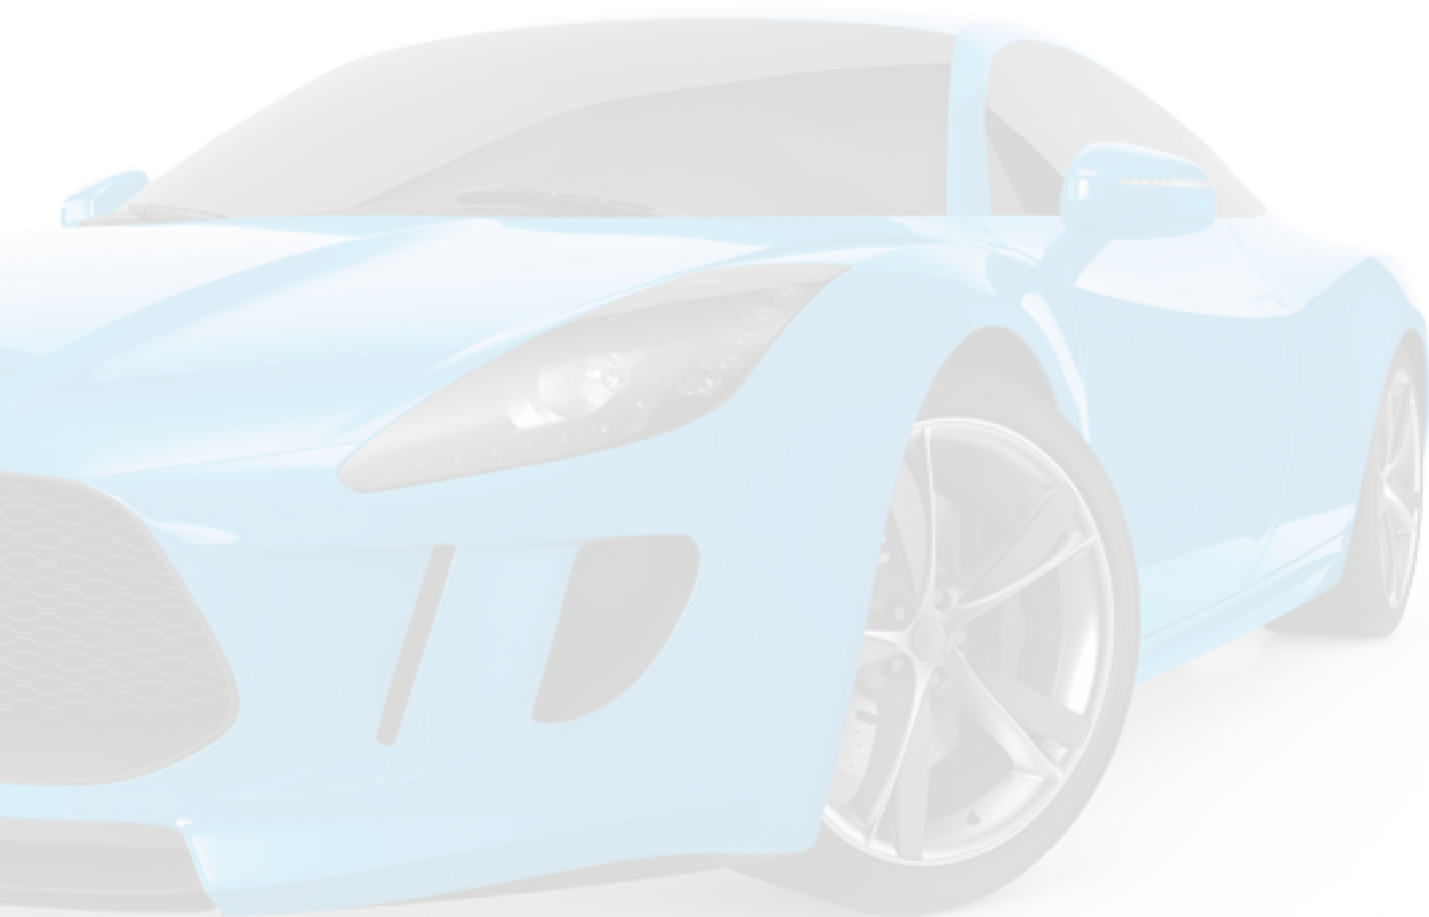

The data contained in this publication are based on our current knowledge and experience. In view of the many factors that may affect processing and application of our products, these data do not relieve processors from carrying out their own investigations and tests; neither do these data imply any guarantee of certain properties, nor the suitability of the products for a specific purpose. Any descriptions, drawings, photographs, data, proportions, weights etc. given herein are for general information purpose only; they may change without prior information and do not constitute the agreed contractual quality of the products (product specification). It is the responsibility of the recipient of our products to ensure that any proprietary rights and existing laws and legislation are observed.

BASF Coatings GmbH, Automotive Refinish Coatings Solutions, Europe, Glasuritstraße 1, 48165 Münster, Germany

03/2025