

Vedlegg 1: Strekkdata grafvedlegg



Uke 0

USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE0 20C- PLA (A-0)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1460	110	13,7	385	48,1	16,0
2	PLA	50,0	4,00	2,00	1310	118	14,8	390	48,7	15,8
3	PLA	50,0	4,00	2,00	1780	99,8	12,5	380	47,5	12,4
4	PLA	50,0	4,00	2,00	1350	139	17,4	423	52,9	8,06
5	PLA	50,0	4,00	2,00	1390	131	16,4	400	50,0	9,44
Average					1460	120	15,0	396	49,5	12,3
SD					188	15,8	1,98	17,2	2,15	3,62

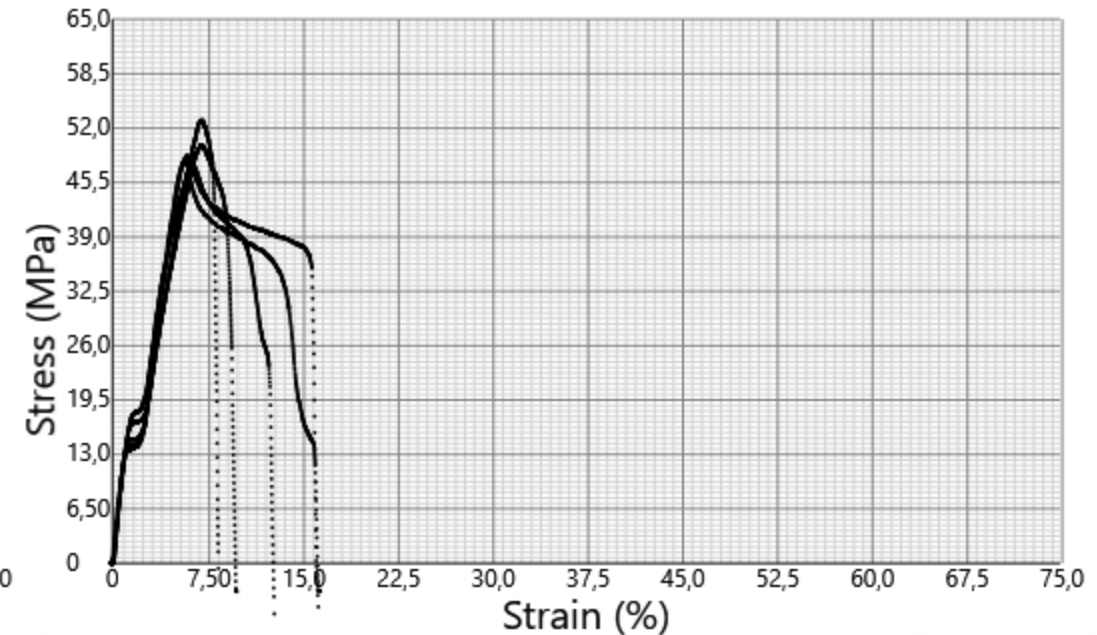
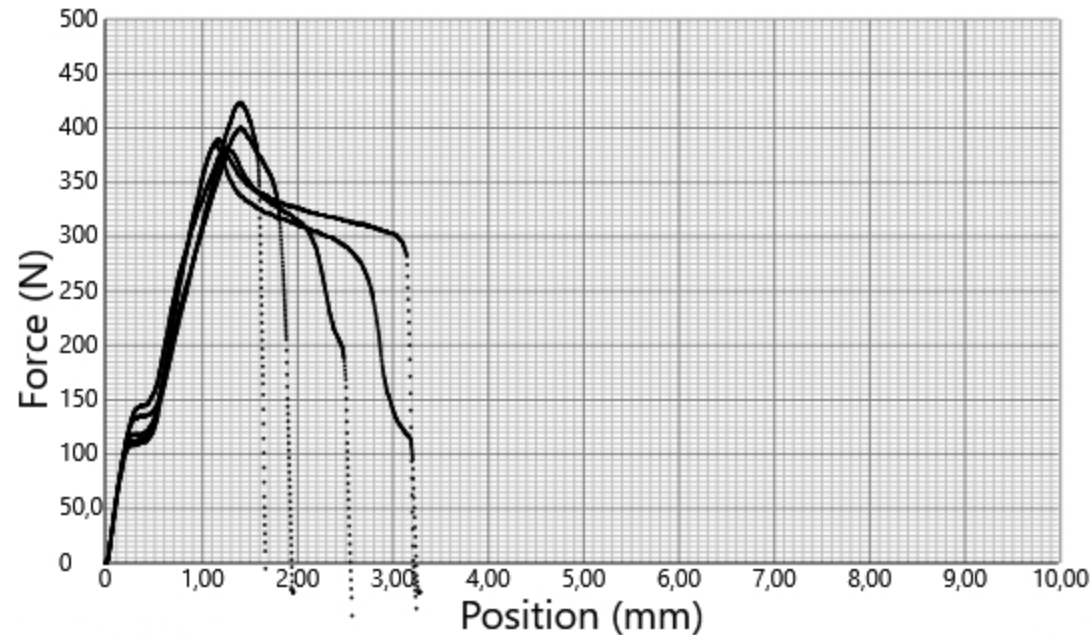


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE0 20C- PETG (B-0)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	879	130	16,2	348	43,5	11,3
2	PETG	50,0	4,00	2,00	851	143	17,8	348	43,5	11,1
3	PETG	50,0	4,00	2,00	875	133	16,6	347	43,3	11,0
4	PETG	50,0	4,00	2,00	863	126	15,7	342	42,7	11,4
5	PETG	50,0	4,00	2,00	844	121	15,1	337	42,1	11,0
Average					862	130	16,3	344	43,0	11,2
SD					14,9	8,27	1,03	5,08	0,635	0,172

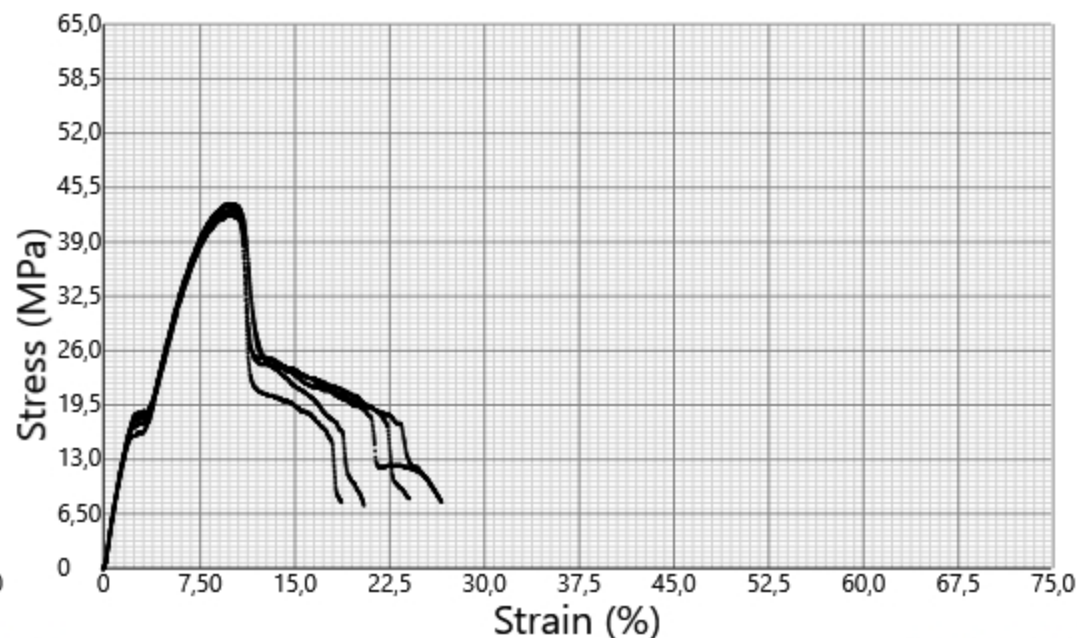
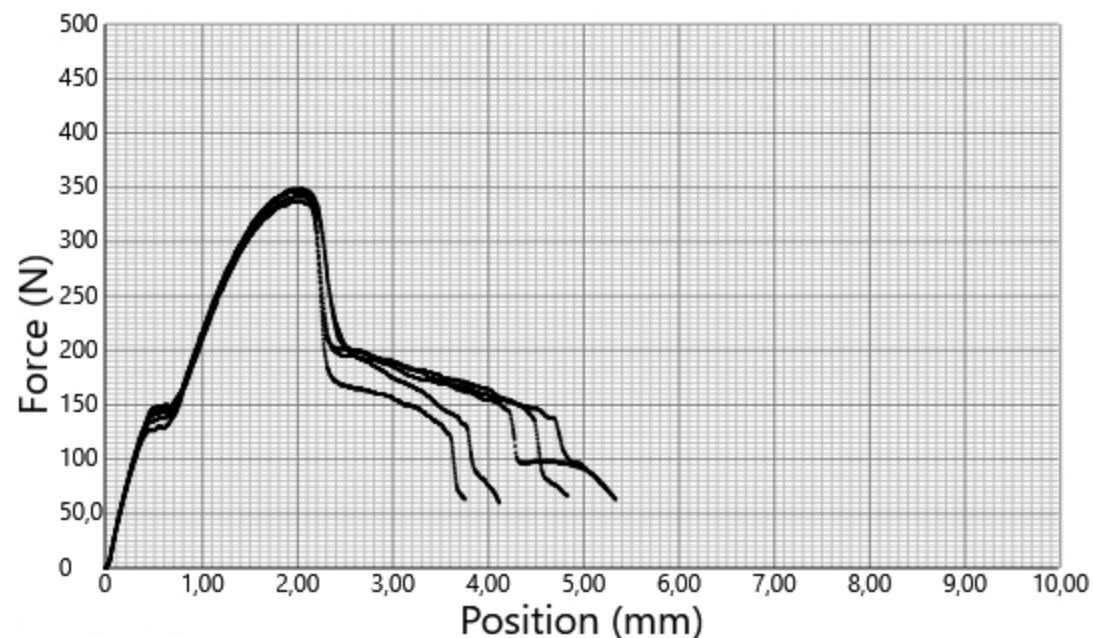


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE0 20C- ASA (A-0)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	1040	105	13,2	303	37,9	11,4
2	ASA	50,0	4,00	2,00	1150	108	13,2	305	38,1	12,4
3	ASA	50,0	4,00	2,00	941	99,1	12,4	297	37,1	11,3
4	ASA	50,0	4,00	2,00	1020	116	14,5	310	38,7	11,8
5	ASA	50,0	4,00	2,00	990	122	15,3	318	39,8	10,9
Average					1030	110	13,7	307	38,3	11,6
SD					78,6	9,32	1,17	8,07	1,01	0,553

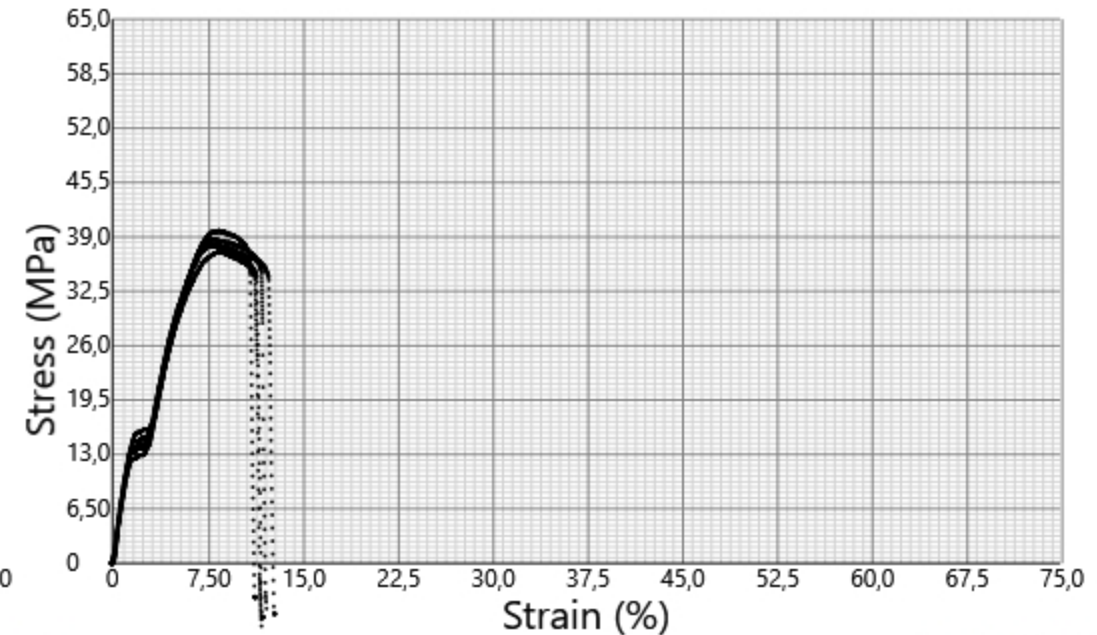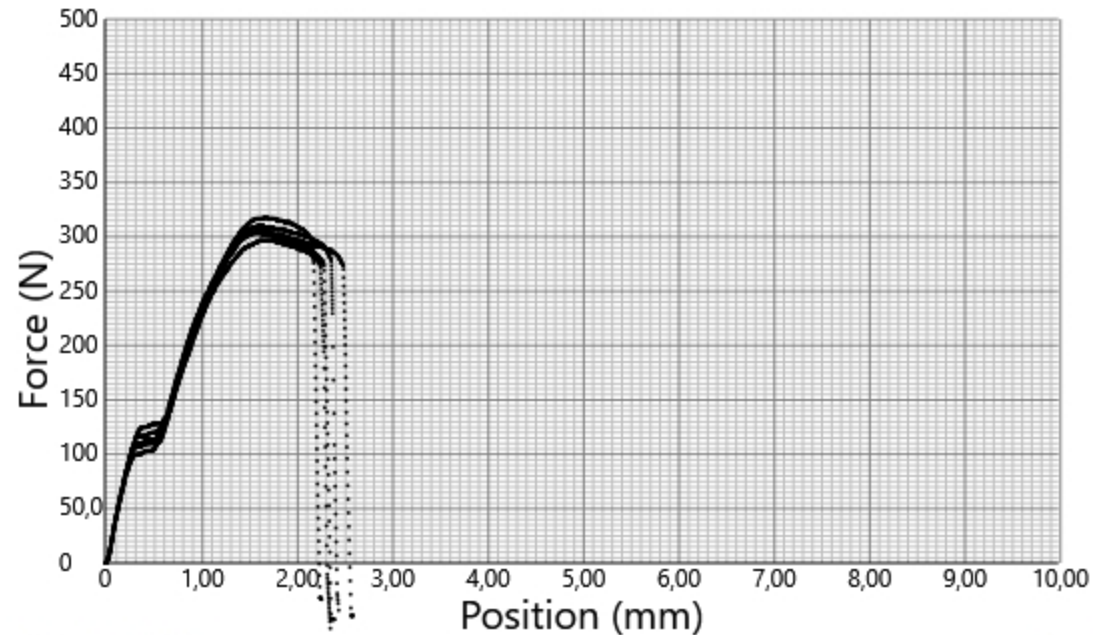



Uke 3

USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 20C TØRR - PLA (A-1-1)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	902	140	17,5	305	38,1	9,43
2	ASA	50,0	4,00	2,00	855	126	15,7	263	32,9	8,63
3	ASA	50,0	4,00	2,00	876	121	15,1	335	41,9	9,83
4	ASA	50,0	4,00	2,00	866	118	14,7	267	33,3	8,60
5	ASA	50,0	4,00	2,00	914	190	23,8	392	49,0	11,4
1	PLA	50,0	4,00	2,00	473	163	20,4	440	55,0	11,7
2	PLA	50,0	4,00	2,00	871	148	18,5	413	51,7	10,4
3	PLA	50,0	4,00	2,00	784	130	16,2	403	50,4	12,3
4	PLA	50,0	4,00	2,00	649	125	15,6	393	49,2	11,2
5	PLA	50,0	4,00	2,00	566	120	15,0	385	48,1	29,4
Average					775	138	17,3	360	45,0	12,3
SD					156	23,3	2,91	62,9	7,86	6,13

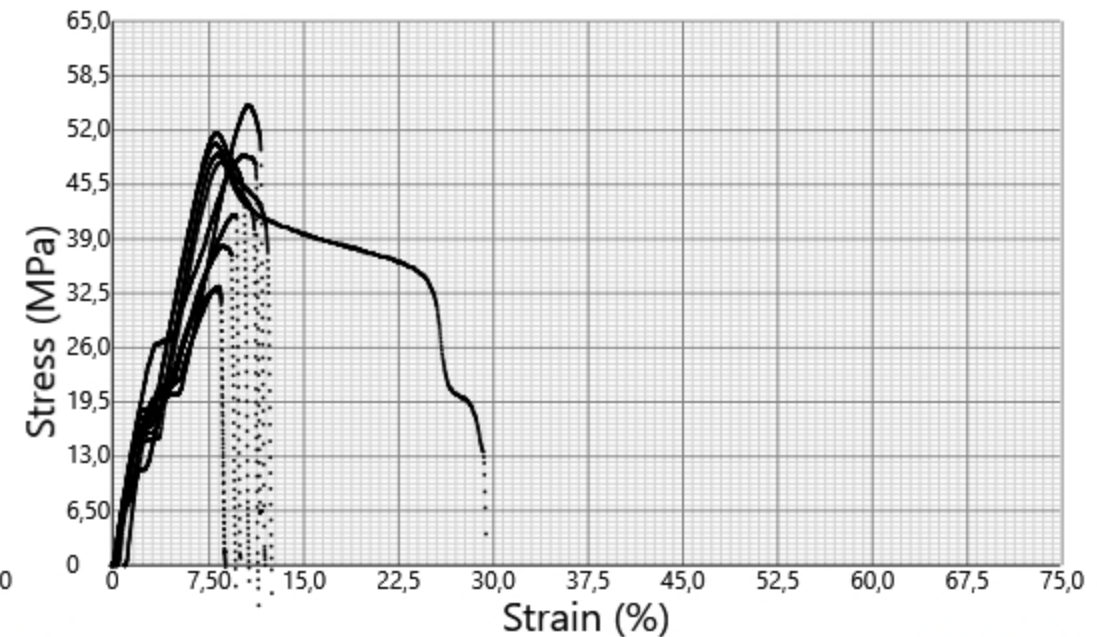
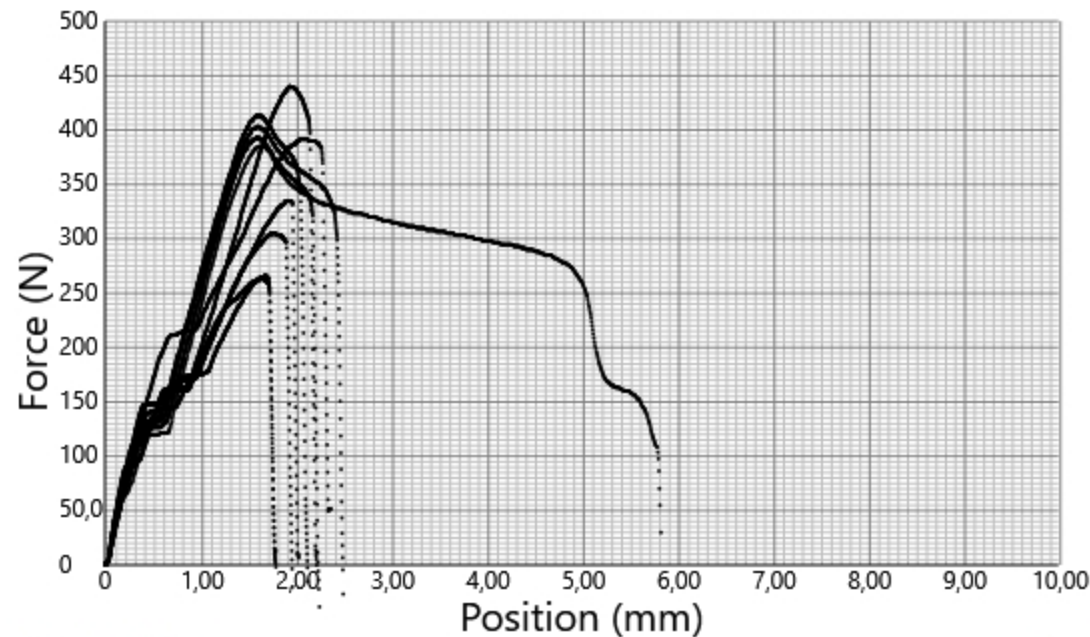


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 20C VÅT - PLA (A-1-2)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1250	124	15,5	383	47,9	15,5
2	PLA	50,0	4,00	2,00	1150	122	15,3	380	47,5	25,6
3	PLA	50,0	4,00	2,00	1220	128	16,0	377	47,1	30,2
4	PLA	50,0	4,00	2,00	645	153	19,2	382	47,7	24,8
5	PLA	50,0	4,00	2,00	1370	130	16,2	353	44,2	24,3
Average					1130	131	16,4	375	46,9	24,1
SD					281	12,7	1,58	12,4	1,55	5,31

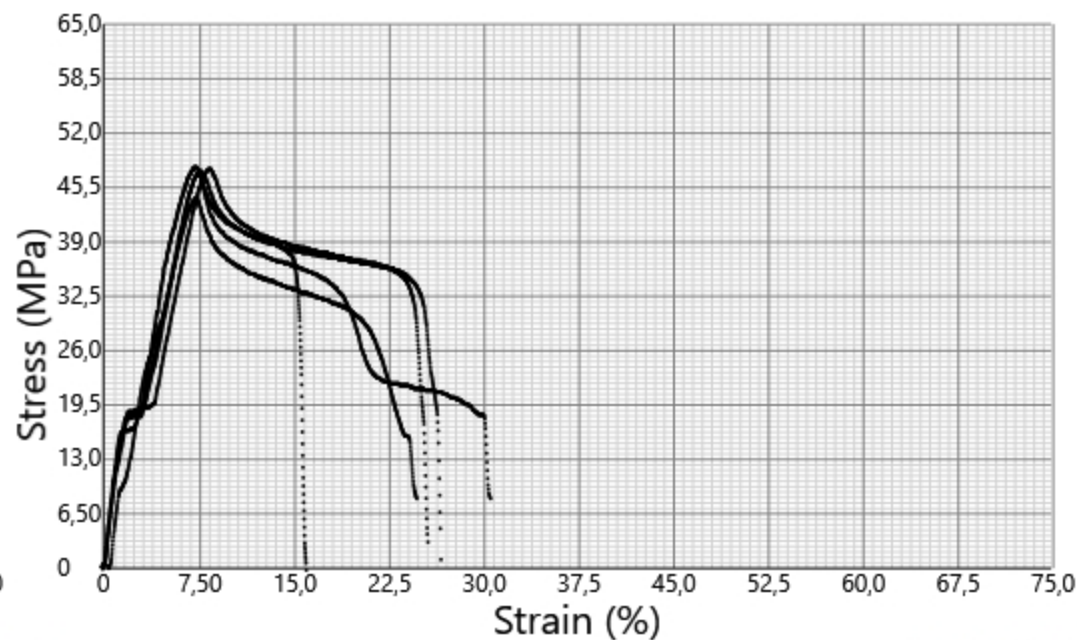
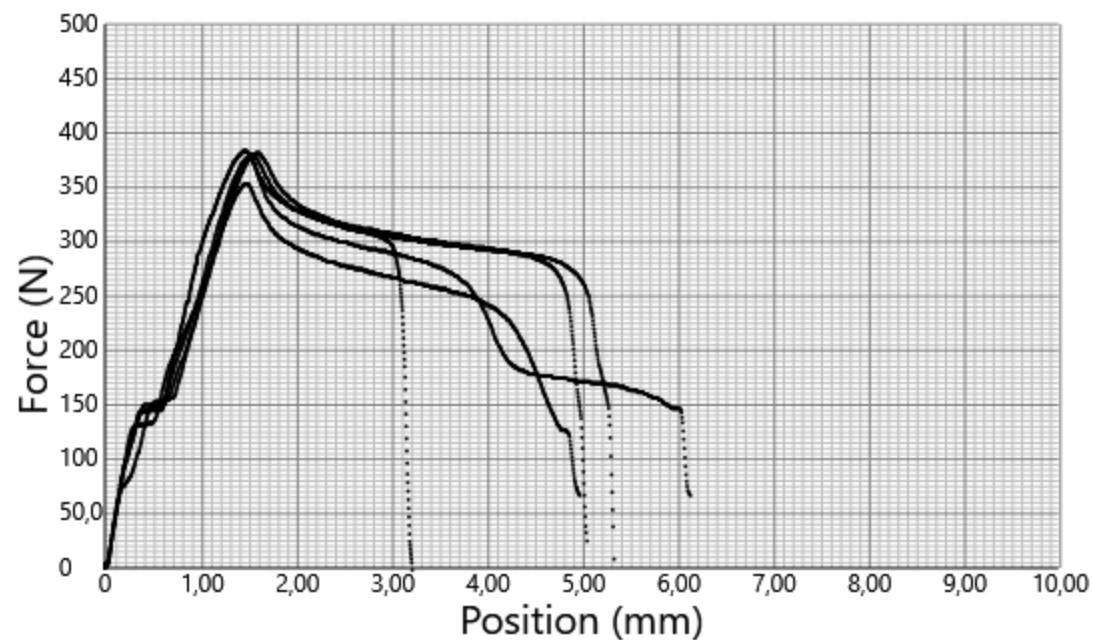


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 40C TØRR - PLA (A-2-1)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	734	120	15,0	393	49,2	9,65
2	PLA	50,0	4,00	2,00	729	133	16,7	395	49,4	38,9
3	PLA	50,0	4,00	2,00	758	140	17,4	402	50,2	26,1
4	PLA	50,0	4,00	2,00	656	128	16,1	400	50,0	37,4
5	PLA	50,0	4,00	2,00	1270	117	14,6	403	50,4	40,1
Average					830	128	16,0	399	49,8	30,4
SD					250	9,38	1,17	4,24	0,531	12,9

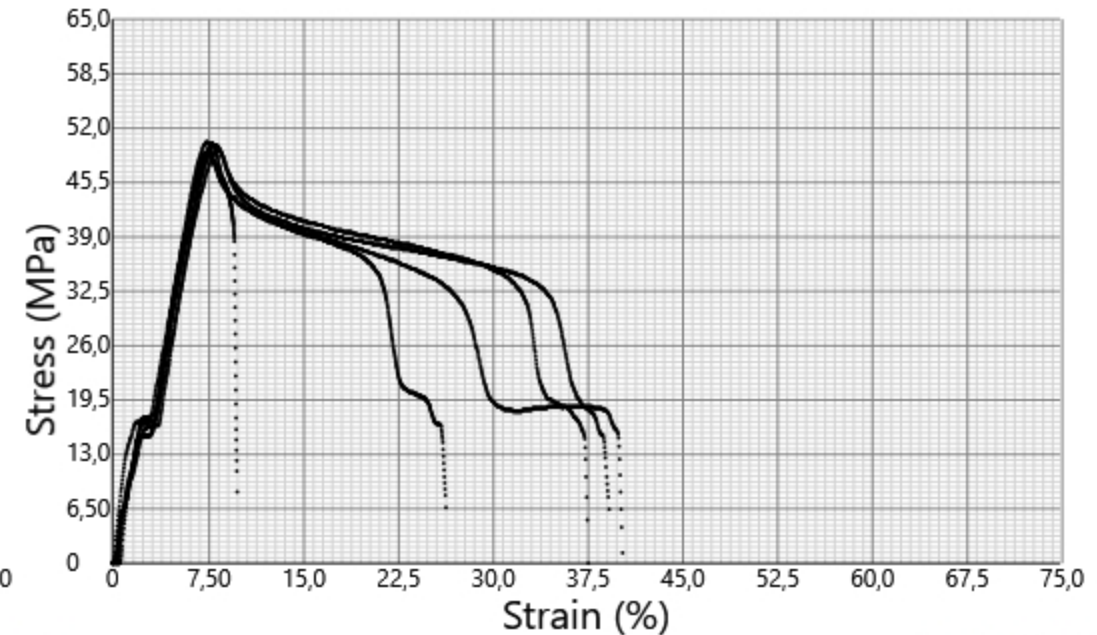
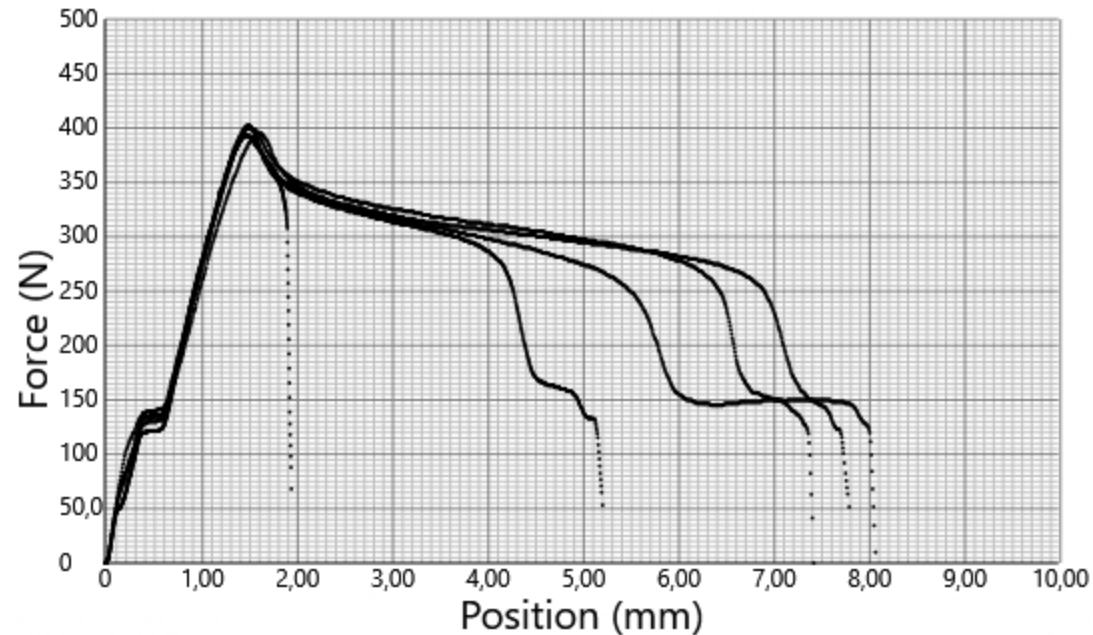


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 40C VÅT - PLA (A-2-2)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1200	113	14,1	380	47,5	45,2
2	PLA	50,0	4,00	2,00	549	125	15,6	348	43,5	37,2
3	PLA	50,0	4,00	2,00	672	142	17,7	383	47,9	19,3
4	PLA	50,0	4,00	2,00	587	140	17,5	358	44,8	45,7
5	PLA	50,0	4,00	2,00	541	146	18,2	380	47,5	63,3
Average					710	133	16,6	370	46,2	42,1
SD					280	13,7	1,72	15,6	1,96	15,9

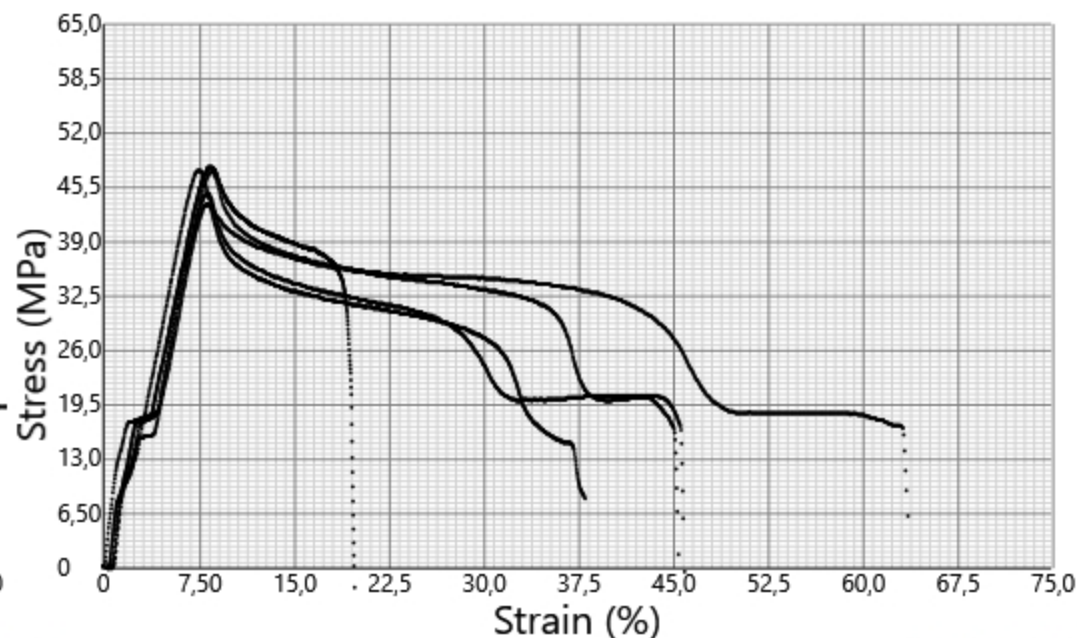
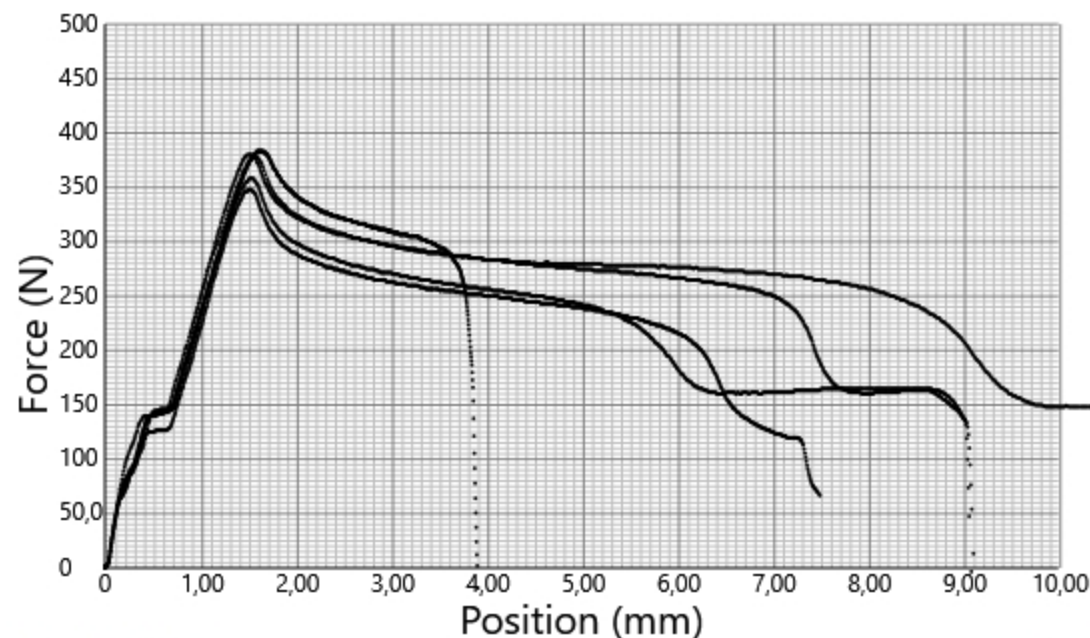


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 60C TØRR - PLA (A-3-1)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1410	123	15,4	300	37,5	5,99
2	PLA	50,0	4,00	2,00	1400	83,3	10,4	275	34,3	5,29
3	PLA	50,0	4,00	2,00	326	88,3	11,0	298	37,3	7,47
4	PLA	50,0	4,00	2,00	464	127	15,8	343	42,9	8,14
5	PLA	50,0	4,00	2,00	474	93,3	11,7	368	46,0	10,3
Average					815	103	12,9	317	39,6	7,43
SD					542	20,4	2,55	37,9	4,74	1,95

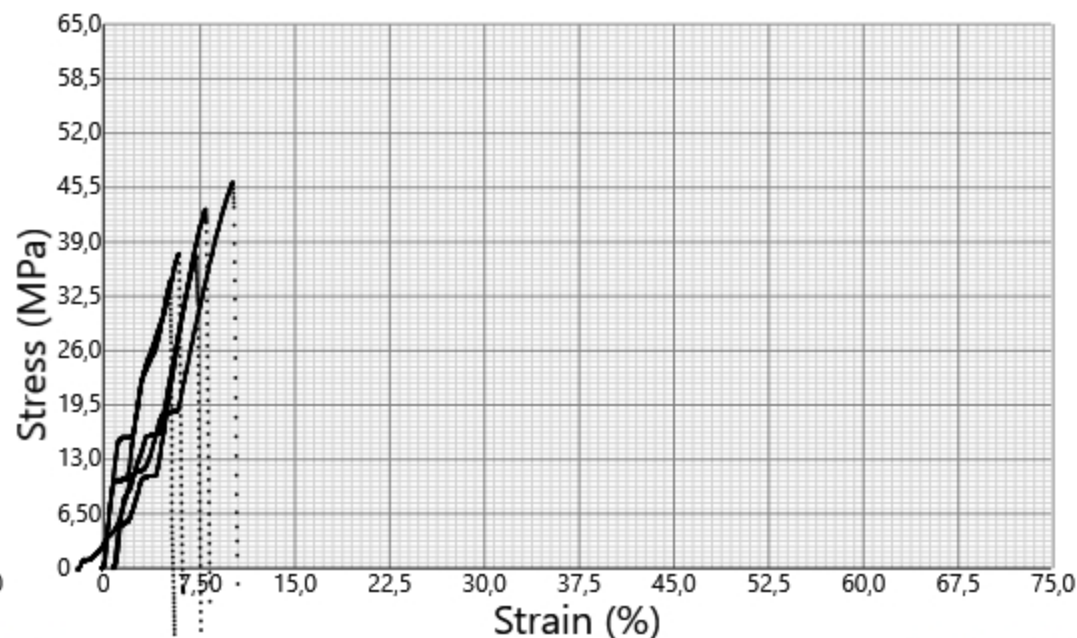
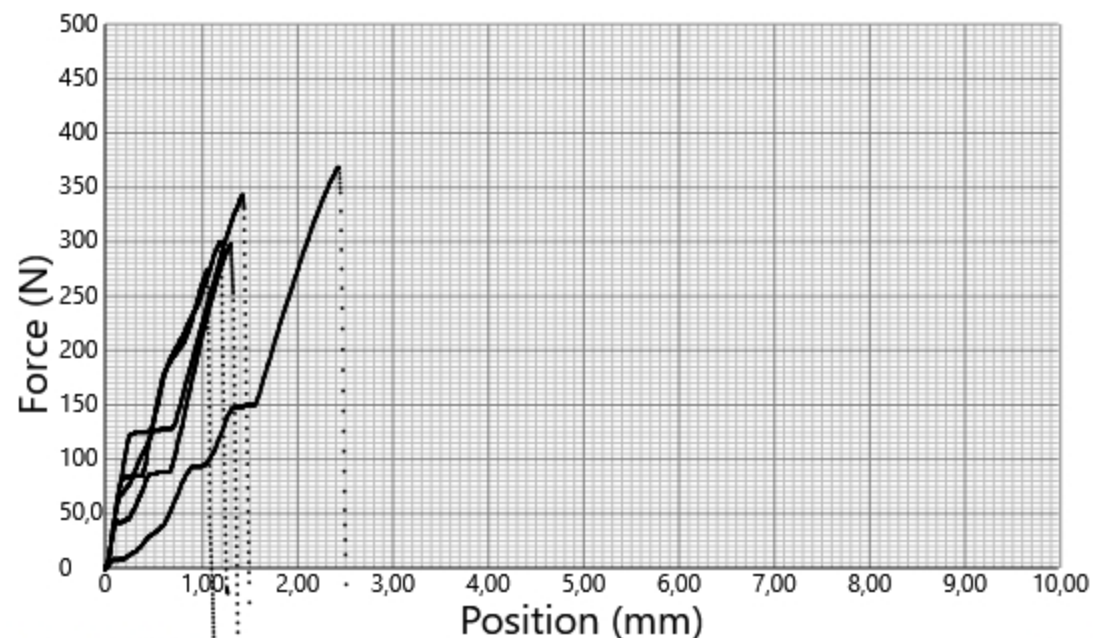


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 60C VÅT - PLA (A-3-2)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1170	110	13,7	408	50,8	10,4
2	PLA	50,0	4,00	2,00	1400	160	20,0	392	48,9	9,67
3	PLA	50,0	4,00	2,00	1250	172	21,5	385	48,1	9,19
4	PLA	50,0	4,00	2,00	1200	95,9	12,0	352	44,0	8,30
5	PLA	50,0	4,00	2,00	1500	95,1	11,9	345	43,1	7,96
Average					1310	126	15,8	376	47,0	9,10
SD					141	36,5	4,57	26,5	3,31	0,990

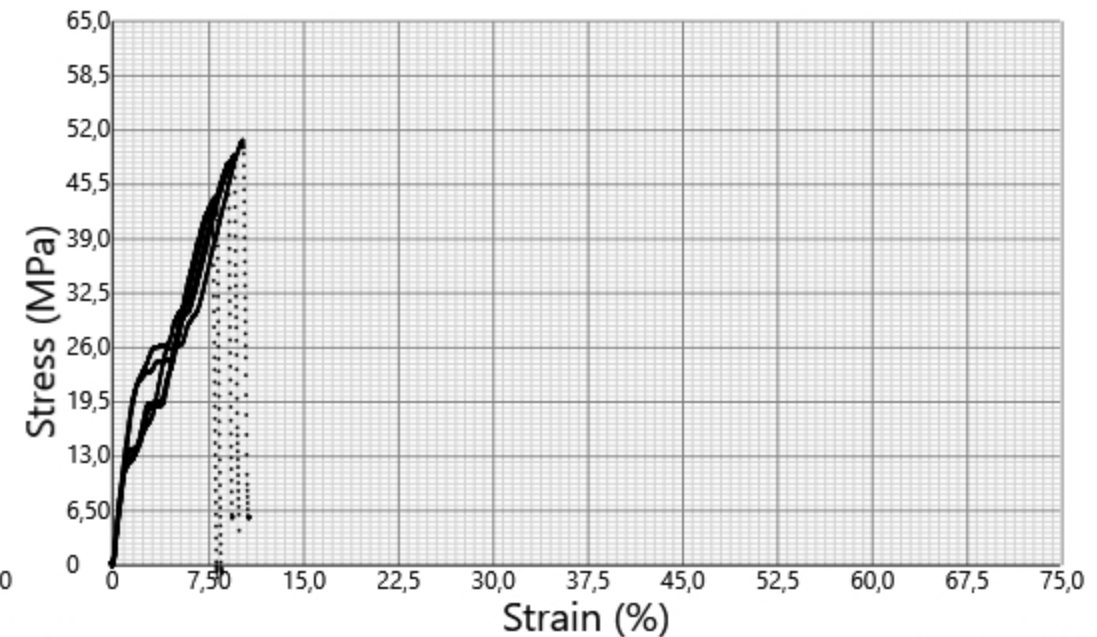
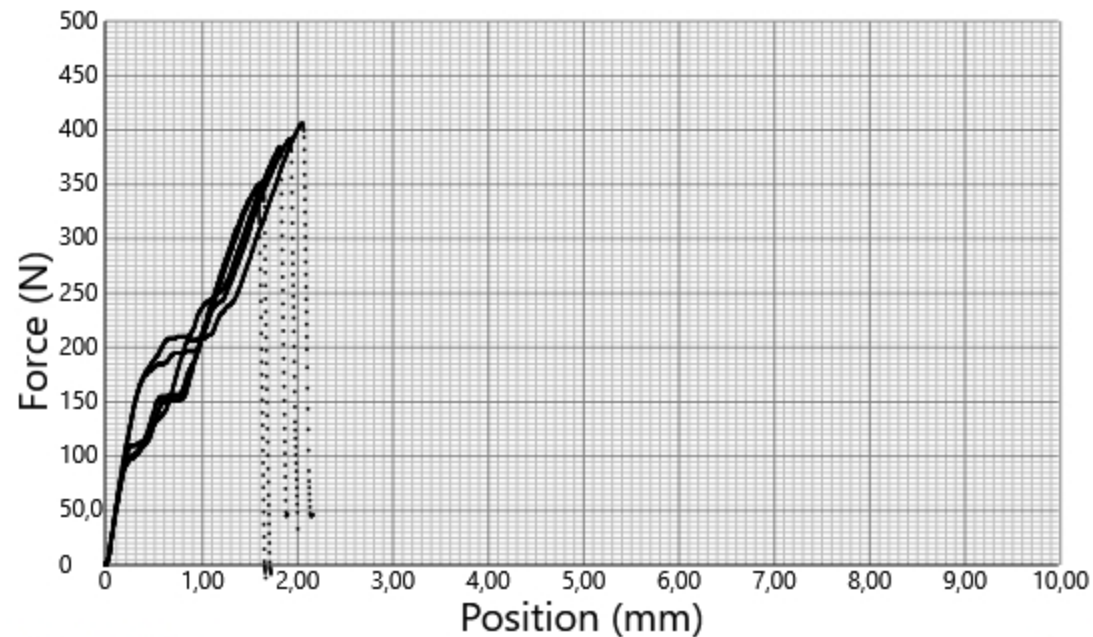


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 20C TØRR - PETG (B-1-1)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	462	157	19,6	393	49,2	13,9
2	PETG	50,0	4,00	2,00	747	105	13,2	388	48,5	13,0
3	PETG	50,0	4,00	2,00	611	96,7	12,1	375	46,9	13,3
4	PETG	50,0	4,00	2,00	625	99,0	12,4	375	46,9	13,8
4	PETG	50,0	4,00	2,00	779	118	14,8	390	48,7	12,5
Average					645	115	14,4	384	48,0	13,3
SD					126	24,6	3,08	8,71	1,09	0,590

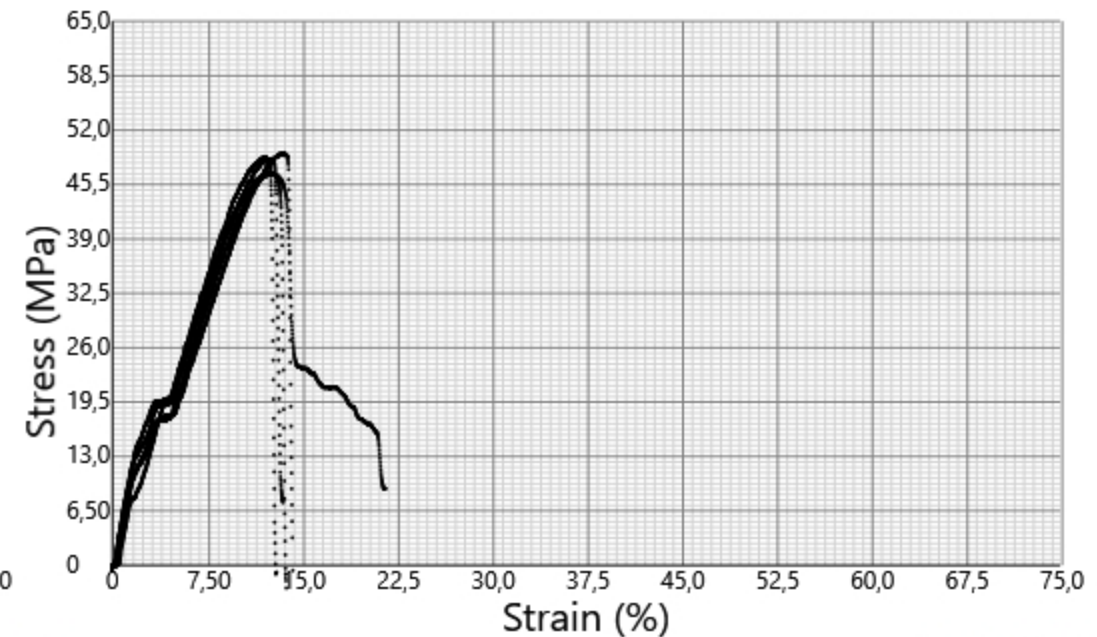
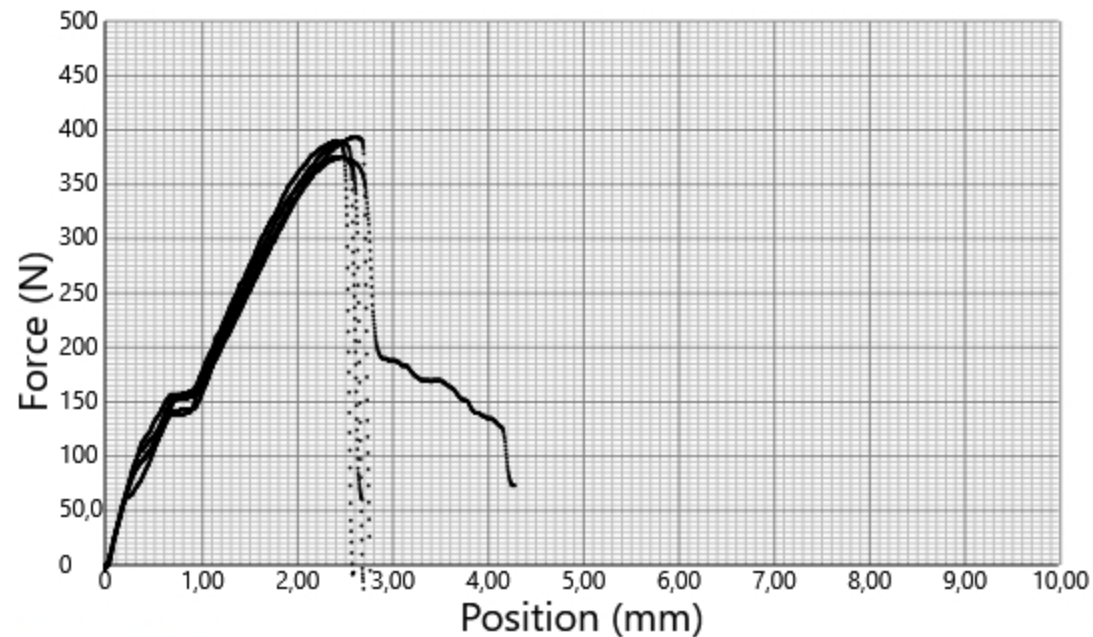


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 20C VÅT - PETG (B-1-2)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	779	116	14,5	350	43,7	11,3
2	PETG	50,0	4,00	2,00	760	158	19,8	383	47,9	12,3
3	PETG	50,0	4,00	2,00	786	132	16,6	368	46,0	11,6
4	PETG	50,0	4,00	2,00	766	132	16,5	363	45,4	12,5
5	PETG	50,0	4,00	2,00	762	121	15,1	378	47,3	36,1
Average					771	132	16,5	369	46,1	16,8
SD					11,5	16,3	2,03	13,1	1,64	10,8

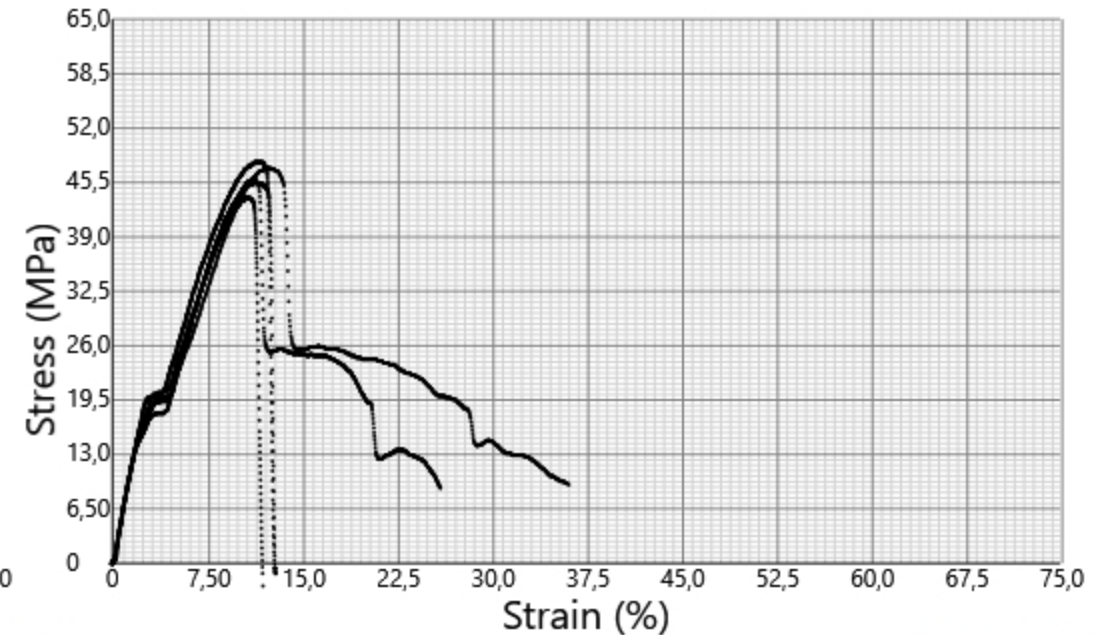
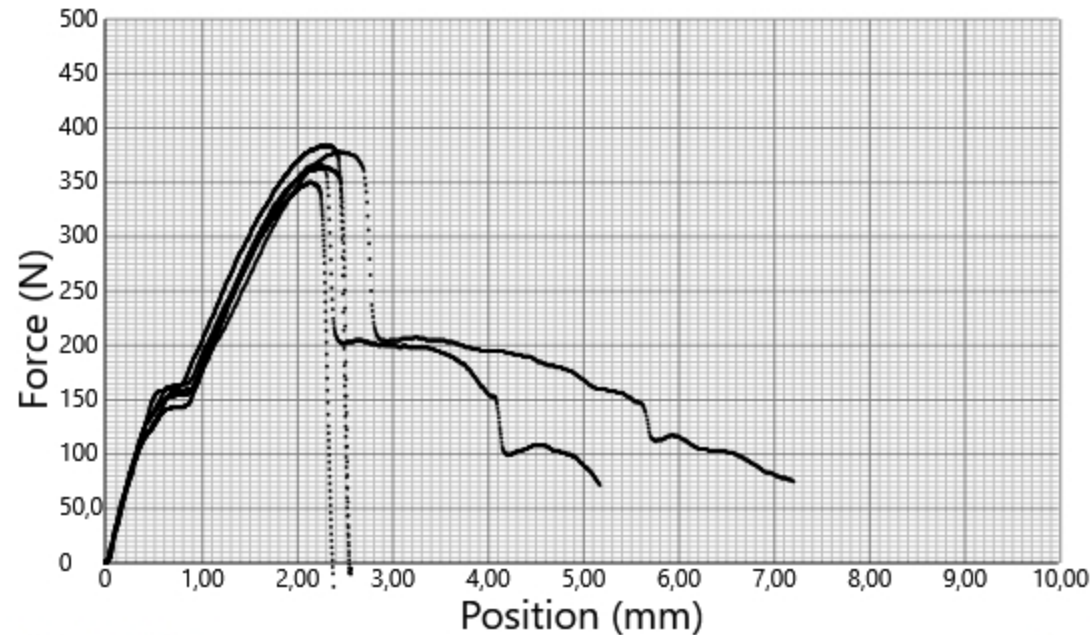


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 40C TØRR - PETG (B-2-1)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	485	148	18,5	413	51,7	12,9
2	PETG	50,0	4,00	2,00	722	115	14,4	435	54,4	12,8
3	PETG	50,0	4,00	2,00	416	147	18,3	423	52,9	14,2
4	PETG	50,0	4,00	2,00	730	147	18,4	435	54,4	13,2
5	PETG	50,0	4,00	2,00	471	163	20,4	442	55,2	13,3
Average					565	144	18,0	430	53,7	13,3
SD					150	17,6	2,20	11,3	1,41	0,535

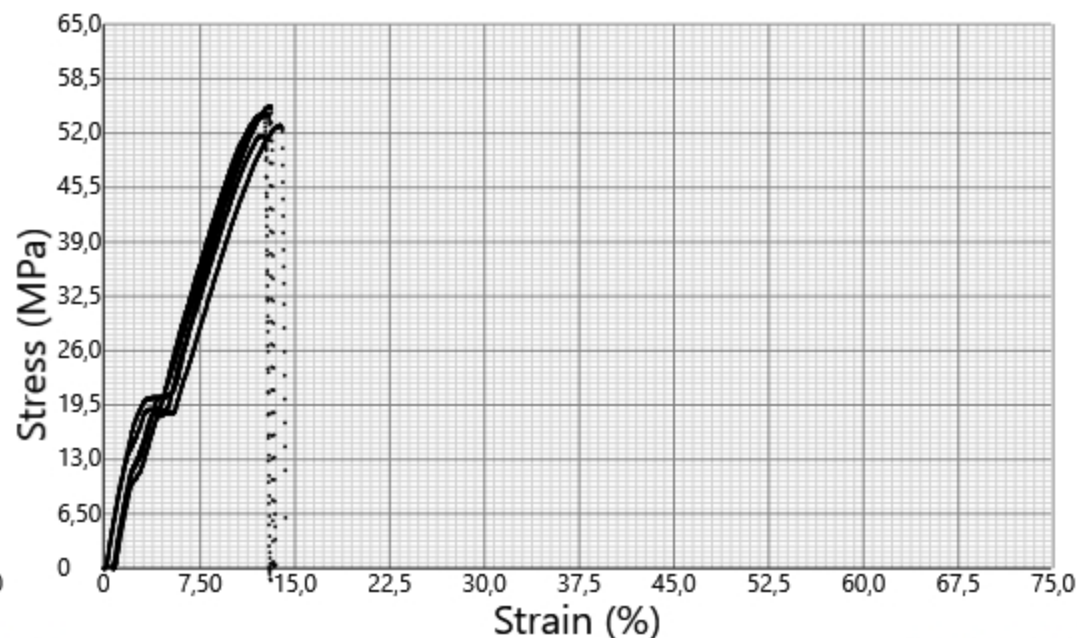
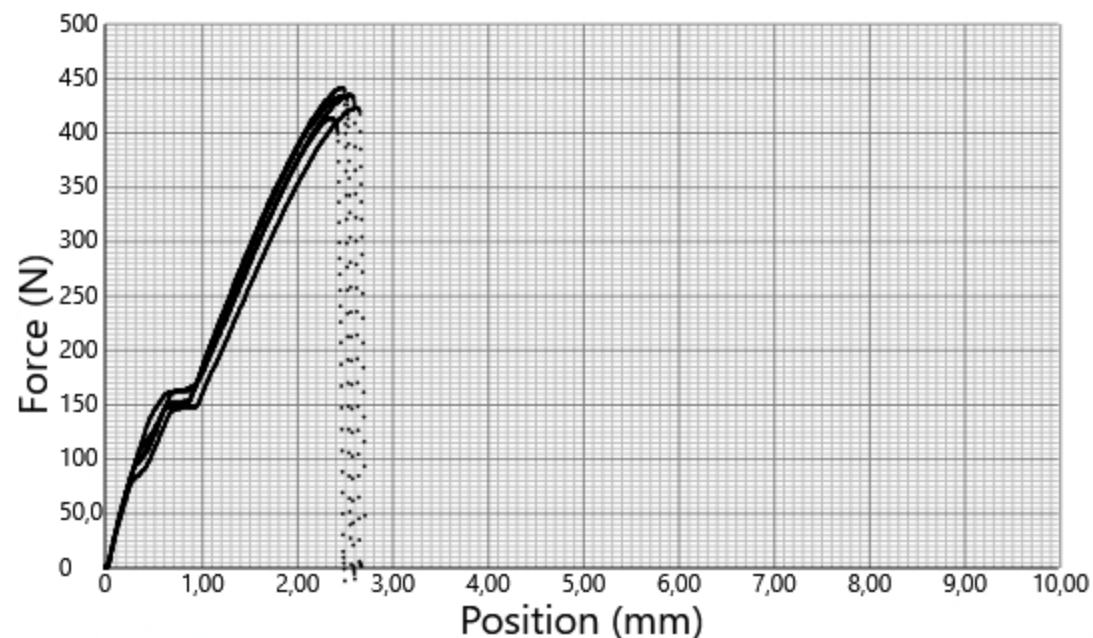


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 40C VÅT - PETG (B-2-2)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	768	118	14,7	405	50,6	11,8
2	PETG	50,0	4,00	2,00	737	112	14,0	423	52,9	13,2
3	PETG	50,0	4,00	2,00	811	147	18,4	415	51,9	11,9
4	PETG	50,0	4,00	2,00	794	136	16,9	430	53,7	13,0
5	PETG	50,0	4,00	2,00	770	128	16,0	422	52,7	12,4
Average					776	128	16,0	419	52,4	12,5
SD					28,5	14,0	1,75	9,52	1,19	0,656

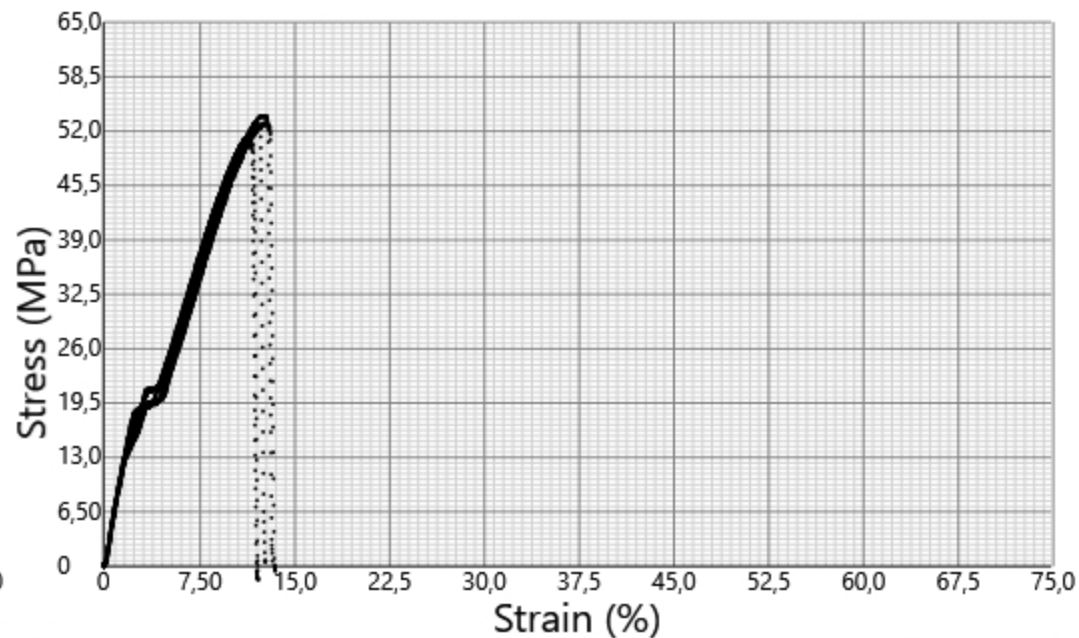
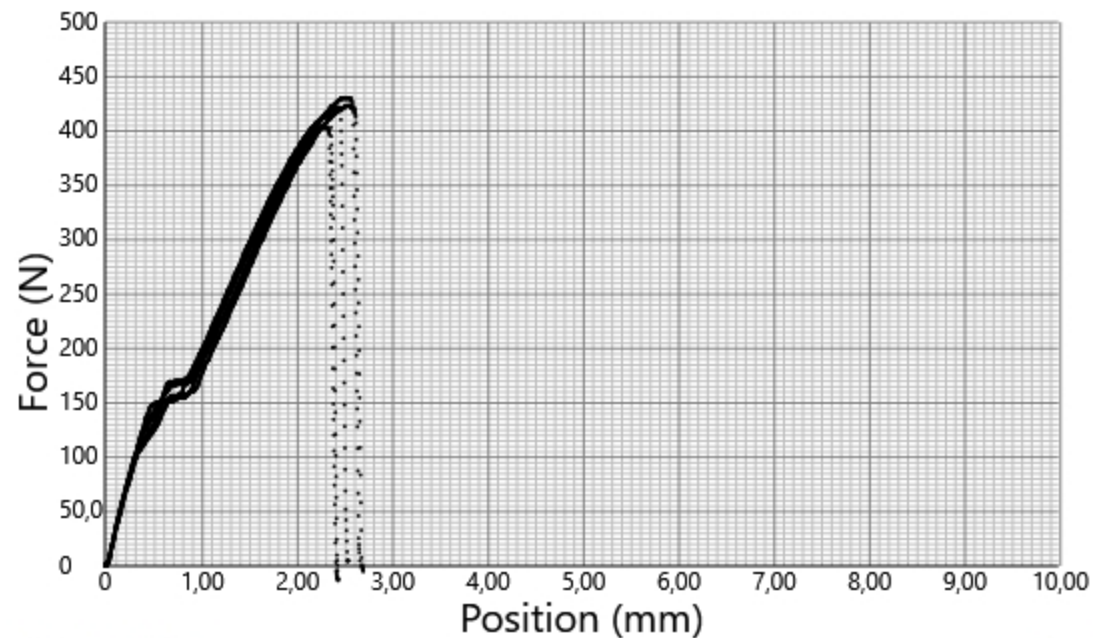


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 60C TØRR - PETG (B-3-1)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	749	124	15,5	403	50,4	48,8
2	PETG	50,0	4,00	2,00	338	93,8	11,7	375	46,9	14,8
3	PETG	50,0	4,00	2,00	759	124	15,5	395	49,4	13,8
4	PETG	50,0	4,00	2,00	773	136	17,1	397	49,6	37,4
5	PETG	50,0	4,00	2,00	707	102	12,7	372	46,5	13,4
Average					665	116	14,5	388	48,5	25,7
SD					185	17,7	2,22	14,1	1,76	16,4

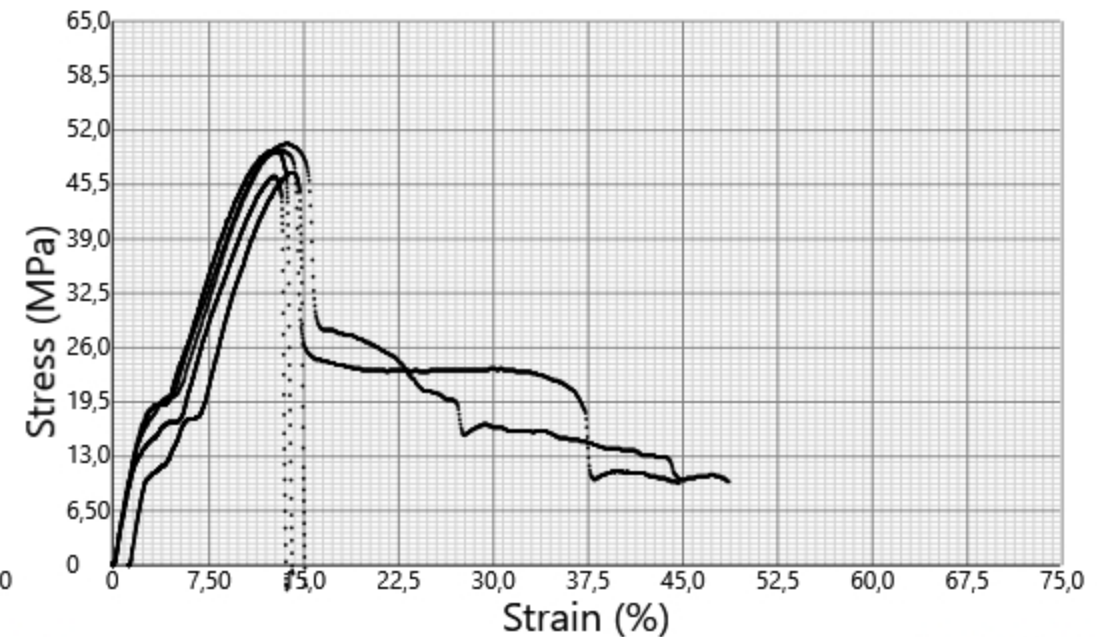
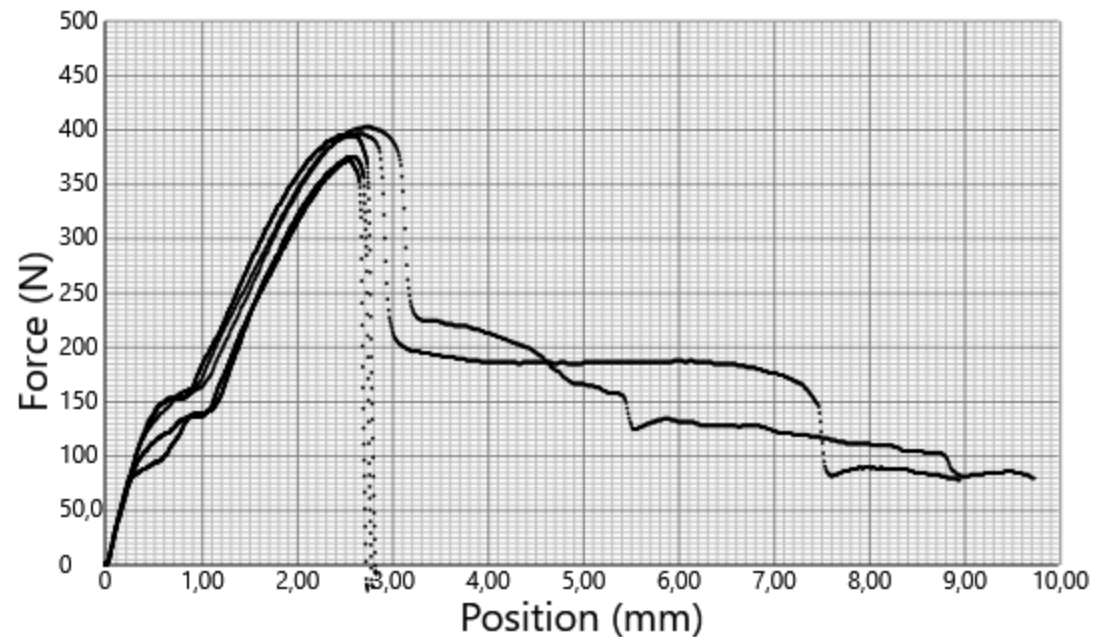


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 60C VÅT - PETG (B-3-2)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	683	105	13,2	357	44,6	237
2	PETG	50,0	4,00	2,00	321	153	19,2	363	45,4	15,2
3	PETG	50,0	4,00	2,00	703	98,1	12,3	363	45,4	15,3
4	PETG	50,0	4,00	2,00	364	158	19,8	375	46,9	59,4
5	PETG	50,0	4,00	2,00	505	93,2	11,7	365	45,6	14,1
Average					515	122	15,2	365	45,6	68,1
SD					176	31,5	3,94	6,60	0,825	96,2

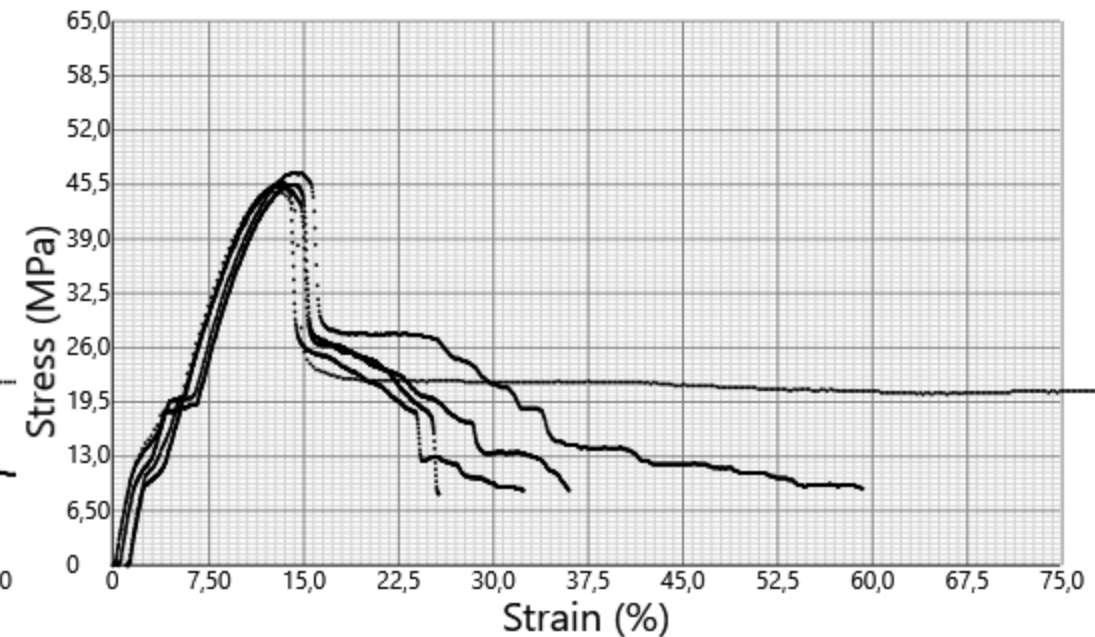
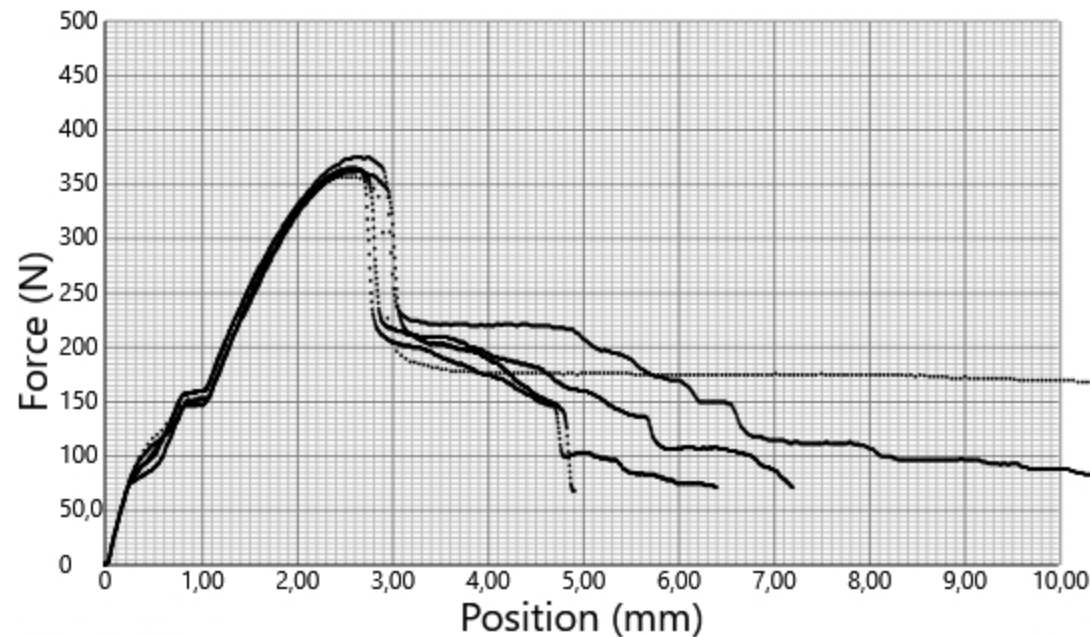


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 20C TØRR - ASA (C-1-1)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	846	132	16,5	332	41,5	11,1
2	ASA	50,0	4,00	2,00	874	112	14,0	258	32,3	8,60
3	ASA	50,0	4,00	2,00	833	112	14,0	317	39,6	11,3
4	ASA	50,0	4,00	2,00	850	111	13,9	328	41,0	11,8
5	ASA	50,0	4,00	2,00	857	140	17,5	352	44,0	12,8
Average					852	122	15,2	317	39,7	11,1
SD					15,3	13,7	1,71	35,3	4,41	1,57

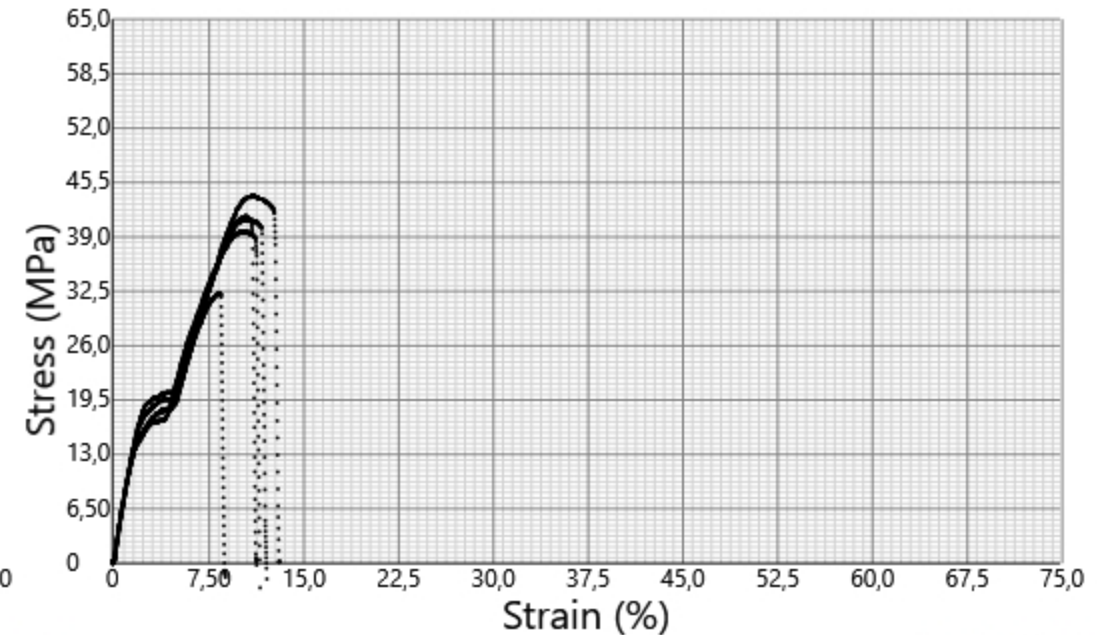
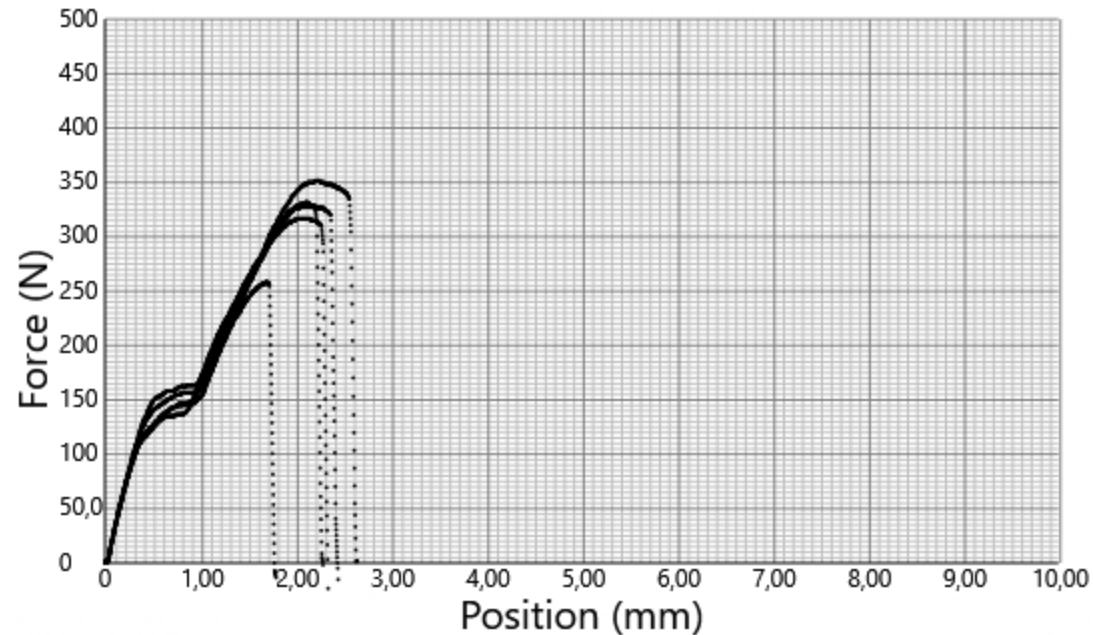


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 20C VÅT - ASA (C-1-2)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	805	145	18,1	295	36,9	10,0
2	ASA	50,0	4,00	2,00	818	111	13,9	325	40,6	10,8
3	ASA	50,0	4,00	2,00	850	131	16,4	303	37,9	9,69
4	ASA	50,0	4,00	2,00	888	128	16,0	287	35,8	10,4
5	ASA	50,0	4,00	2,00	870	122	15,3	317	39,6	10,1
Average					846	127	15,9	305	38,2	10,2
SD					34,4	12,4	1,56	15,6	1,95	0,418

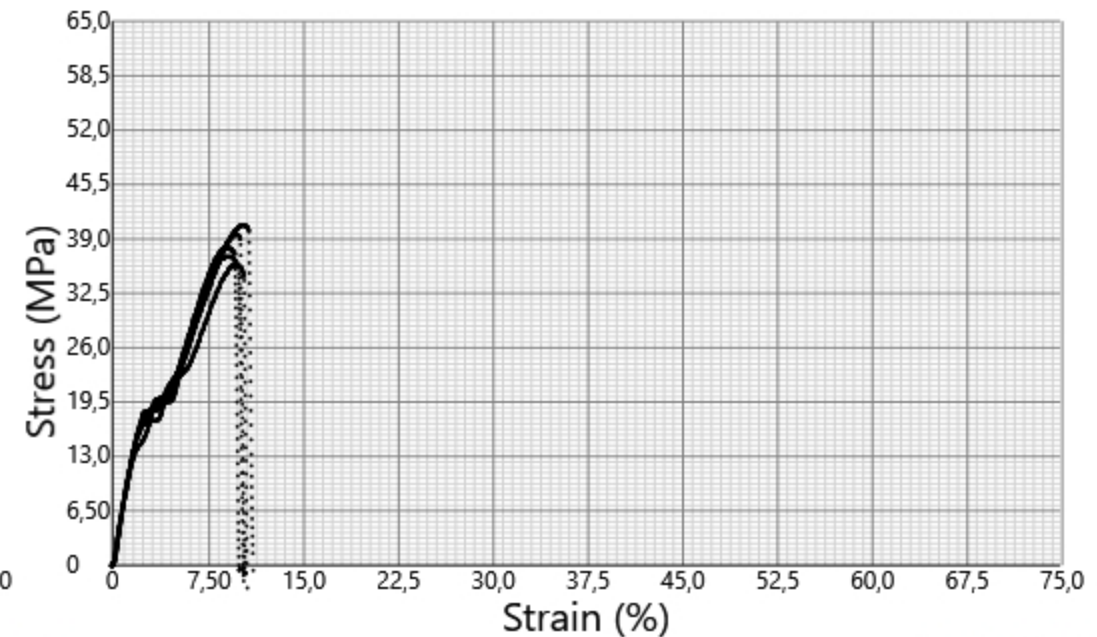
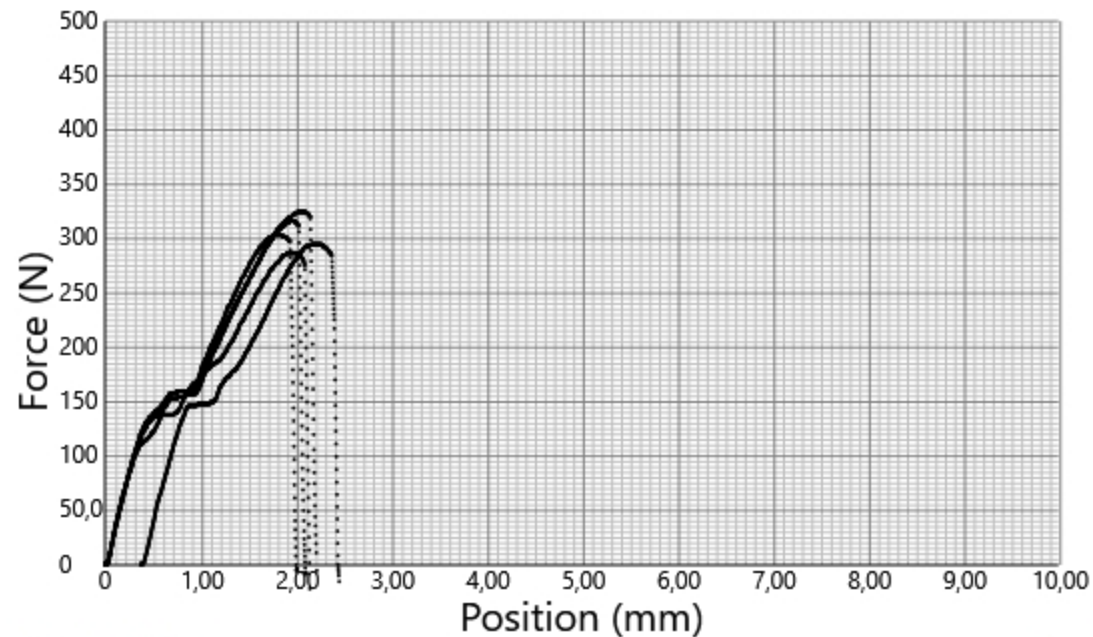


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 40C TØRR - ASA (C-2-1)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	927	154	19,2	333	41,7	9,27
2	ASA	50,0	4,00	2,00	844	131	16,4	310	38,7	10,8
3	ASA	50,0	4,00	2,00	798	110	13,8	327	40,8	11,5
4	ASA	50,0	4,00	2,00	818	138	17,2	245	30,6	8,27
5	ASA	50,0	4,00	2,00	855	132	16,5	255	31,9	8,15
Average					849	133	16,6	294	36,7	9,61
SD					49,4	15,7	1,97	41,2	5,15	1,52

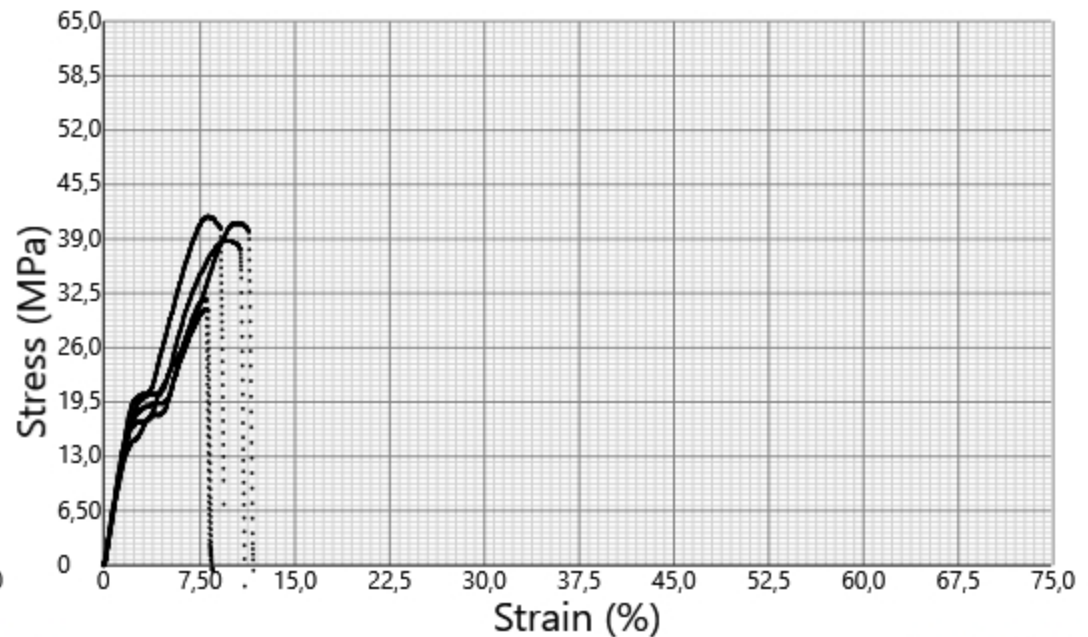
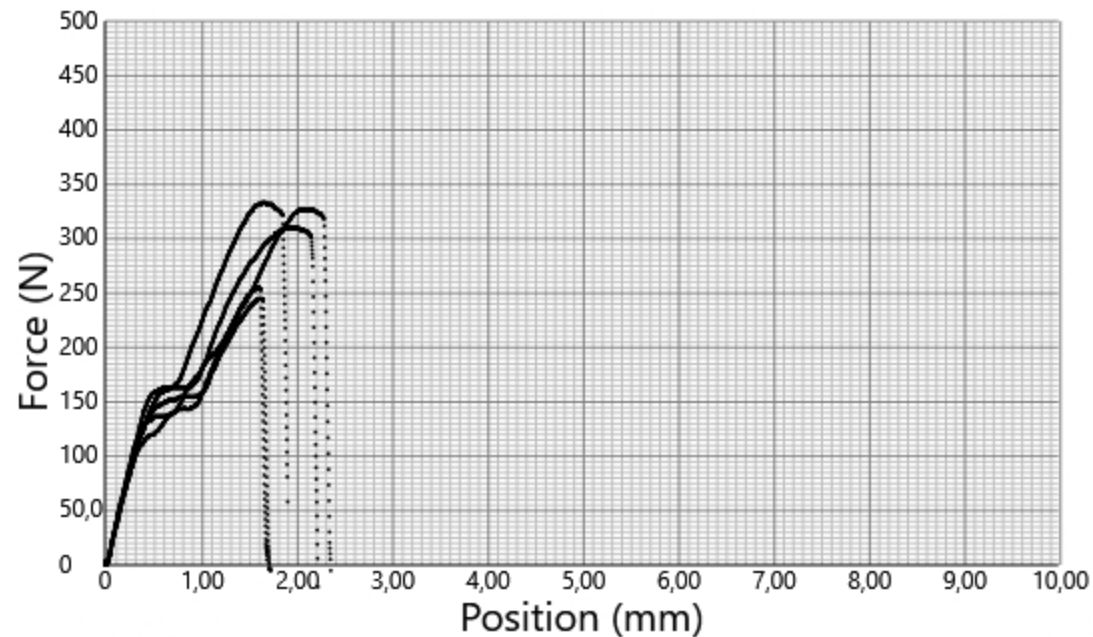


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 40C VÅT - ASA (C-2-2)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	959	113	14,1	258	32,3	7,82
2	ASA	50,0	4,00	2,00	735	78,5	9,82	297	37,1	10,7
3	ASA	50,0	4,00	2,00	859	130	16,3	318	39,8	10,9
4	ASA	50,0	4,00	2,00	888	129	16,2	305	38,1	10,3
5	ASA	50,0	4,00	2,00	874	124	15,5	348	43,5	10,6
Average					863	115	14,4	305	38,2	10,1
SD					81,3	21,5	2,69	32,8	4,10	1,27

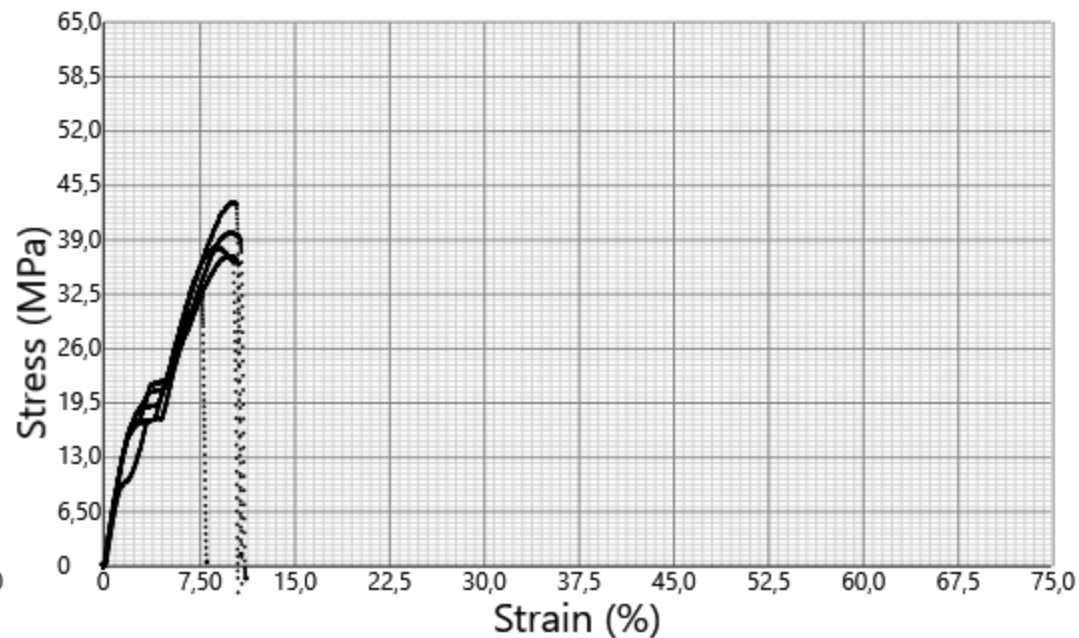
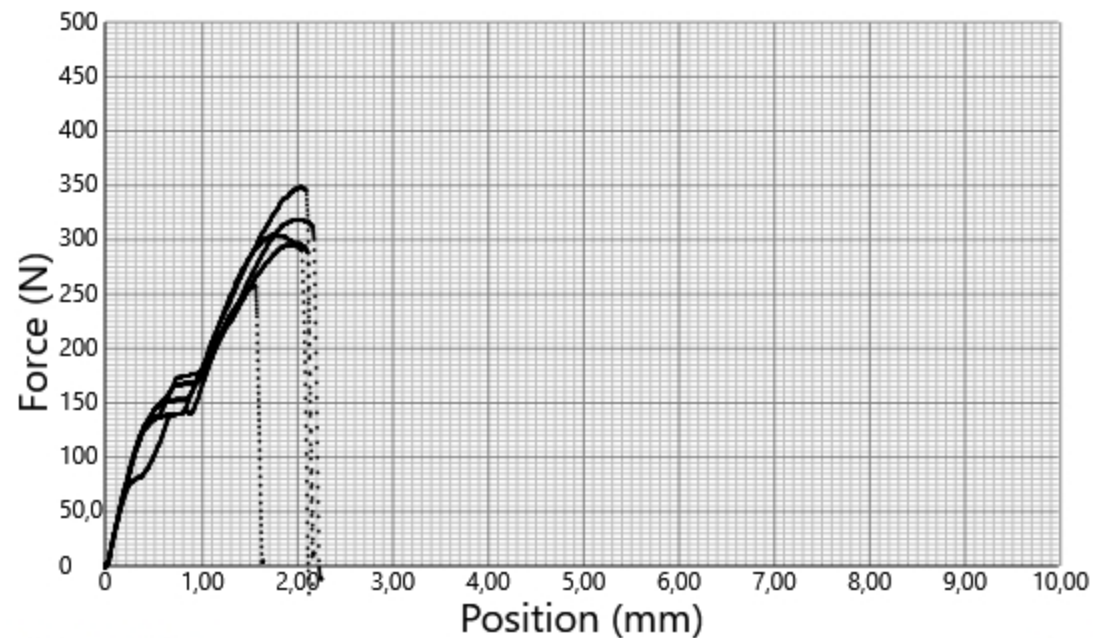


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 60C TØRR - ASA (C-3-1)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	849	132	16,5	322	40,2	10,0
2	ASA	50,0	4,00	2,00	1200	75,4	9,43	308	38,5	9,45
3	ASA	50,0	4,00	2,00	909	134	16,7	335	41,9	11,0
4	ASA	50,0	4,00	2,00	931	138	17,2	338	42,3	9,86
5	ASA	50,0	4,00	2,00	888	126	15,7	342	42,7	11,0
Average					955	121	15,1	329	41,1	10,3
SD					140	25,8	3,22	13,8	1,73	0,721

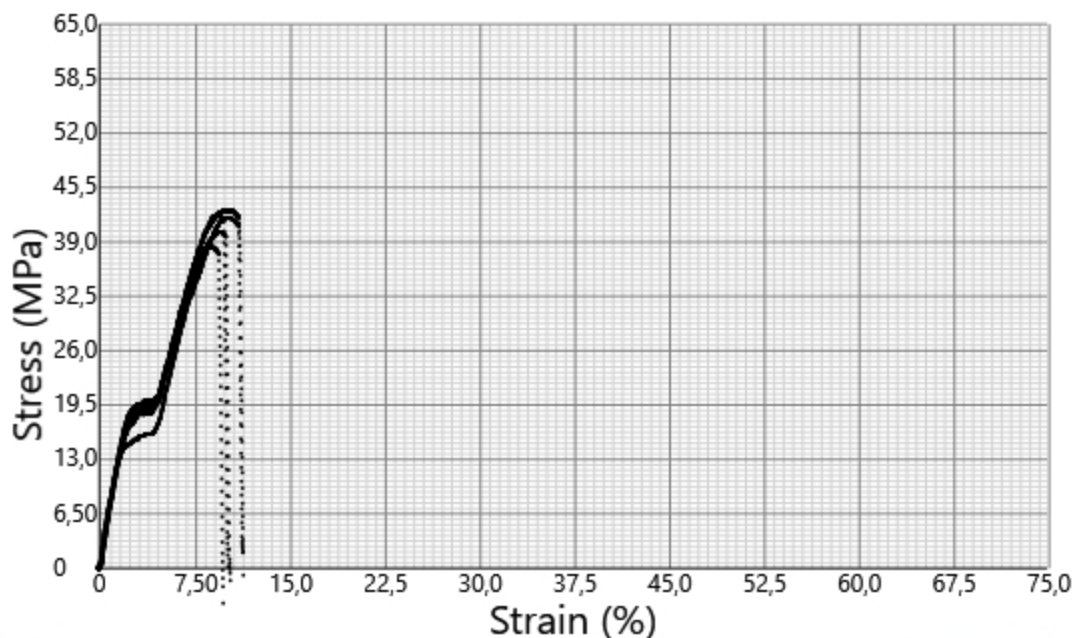
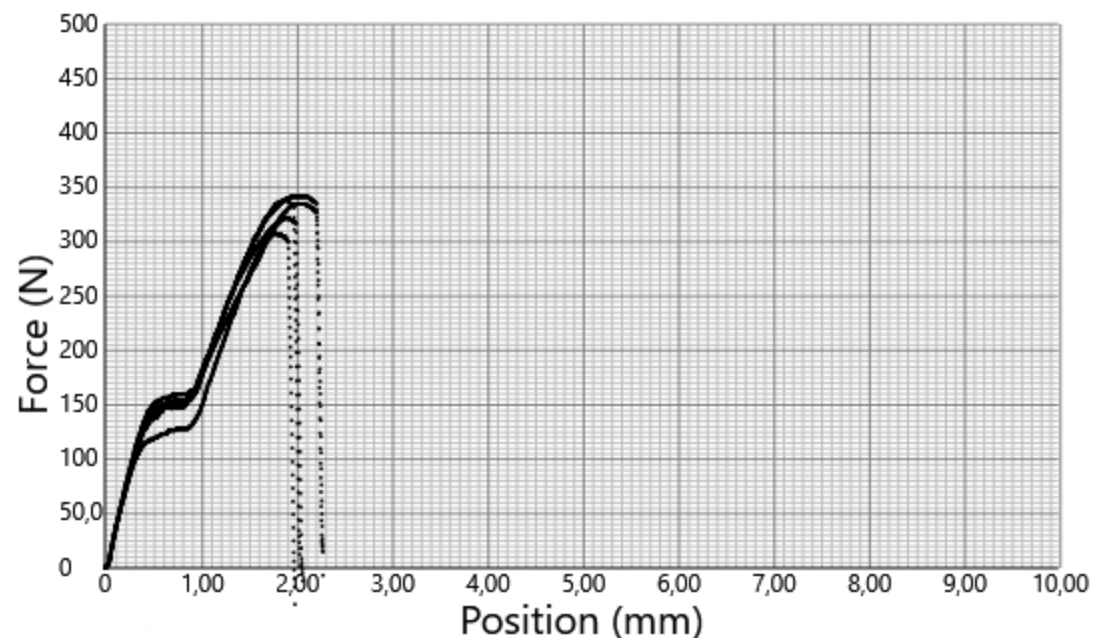


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE3 60C VÅT - ASA (C-3-2)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	902	140	17,5	305	38,1	9,43
2	ASA	50,0	4,00	2,00	855	126	15,7	263	32,9	8,63
3	ASA	50,0	4,00	2,00	876	121	15,1	335	41,9	9,83
4	ASA	50,0	4,00	2,00	866	118	14,7	267	33,3	8,60
5	ASA	50,0	4,00	2,00	914	190	23,8	392	49,0	11,4
Average					882	139	17,4	312	39,0	9,57
SD					24,6	30,0	3,75	53,3	6,66	1,14

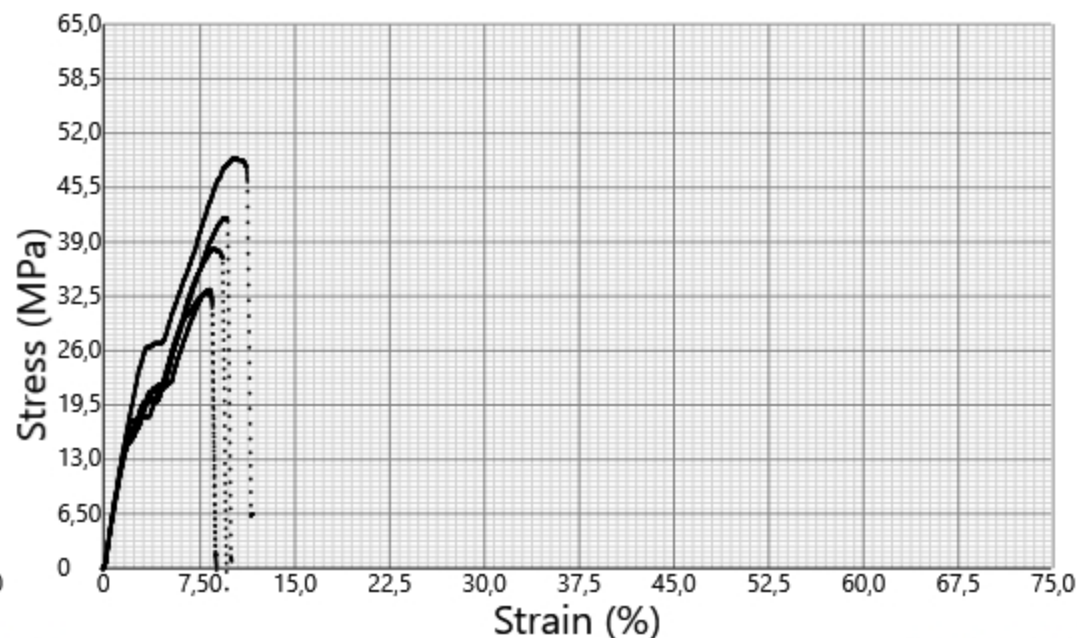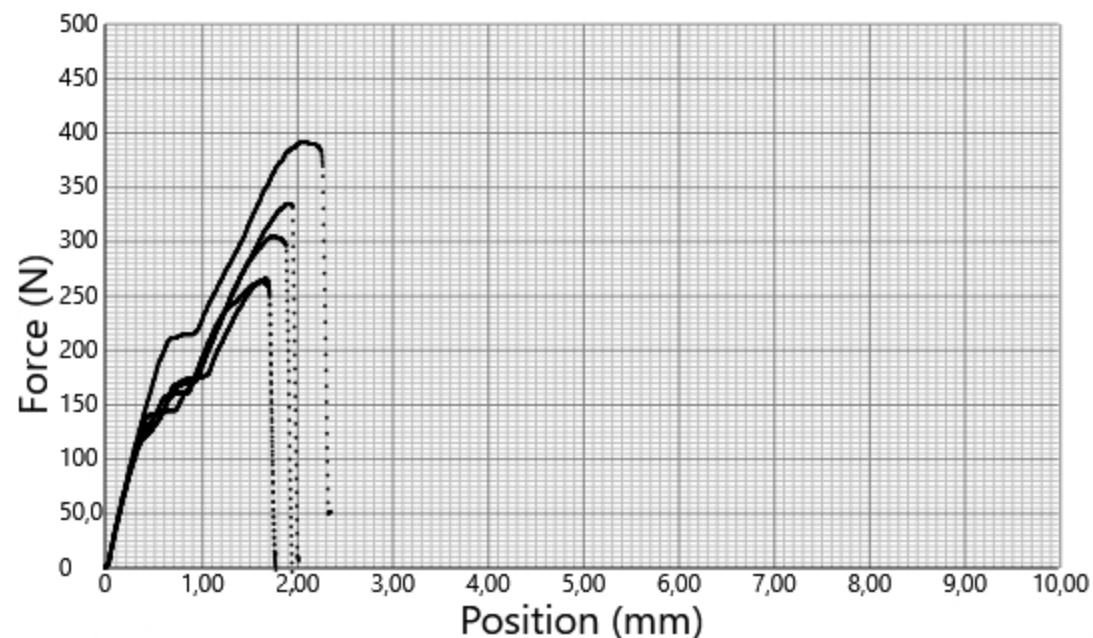



Uke 6

USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 20C TØRR - PLA (A-1-3)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1350	193	24,2	482	60,2	12,8
2	PLA	50,0	4,00	2,00	1140	95,8	12,0	377	47,1	23,4
3	PLA	50,0	4,00	2,00	409	88,3	11,0	353	44,2	13,7
4	PLA	50,0	4,00	2,00	1330	110	13,7	387	48,3	11,6
5	PLA	50,0	4,00	2,00	1270	93,3	11,7	365	45,6	13,1
Average					1100	116	14,5	393	49,1	14,9
SD					394	43,8	5,48	51,3	6,41	4,79

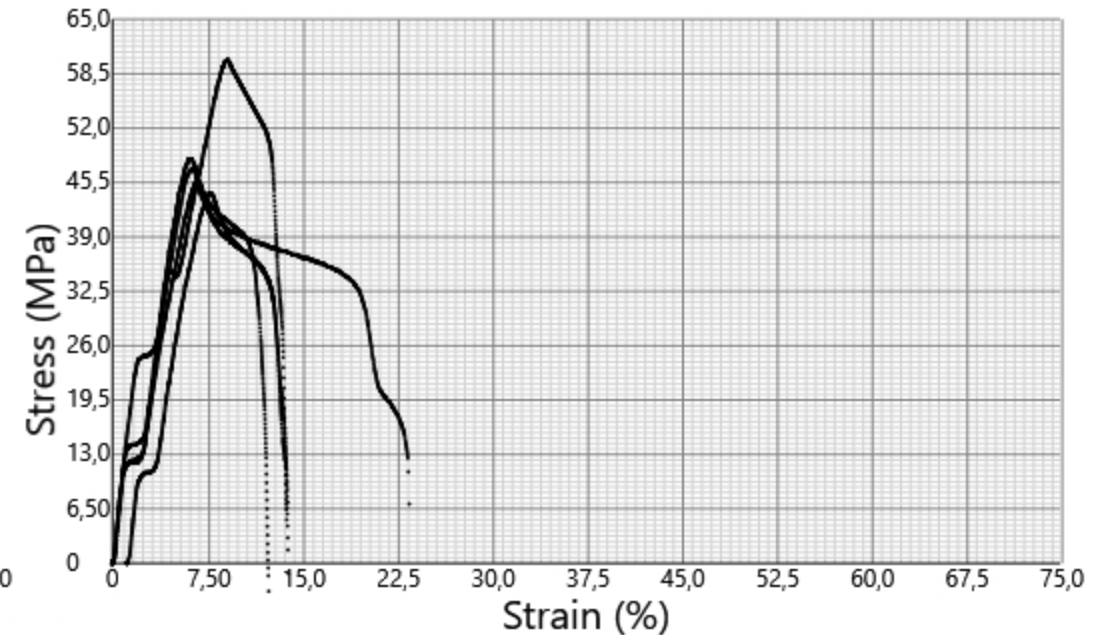
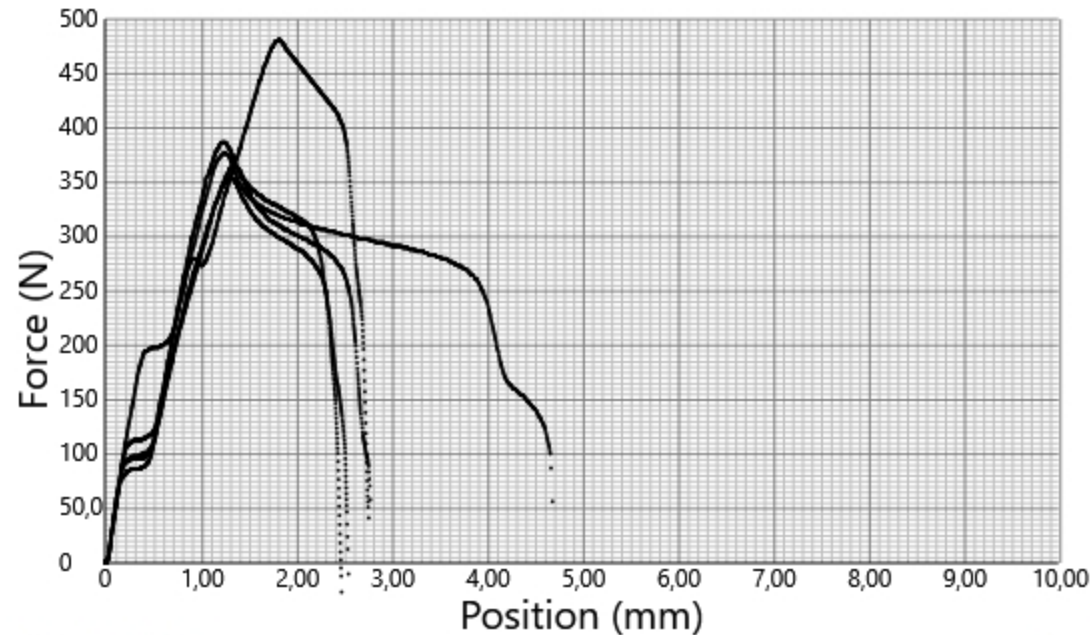


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 20C VÅT - PLA (A-1-4)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1280	107	13,3	355	44,4	57,5
2	PLA	50,0	4,00	2,00	1230	105	13,1	348	43,5	60,3
3	PLA	50,0	4,00	2,00	1100	85,5	10,7	333	41,7	19,2
4	PLA	50,0	4,00	2,00	1570	82,9	10,4	327	40,8	31,4
5	PLA	50,0	4,00	2,00	604	85,5	10,7	342	42,7	17,6
Average					1150	93,1	11,6	341	42,6	37,2
SD					352	11,7	1,46	11,3	1,42	20,5

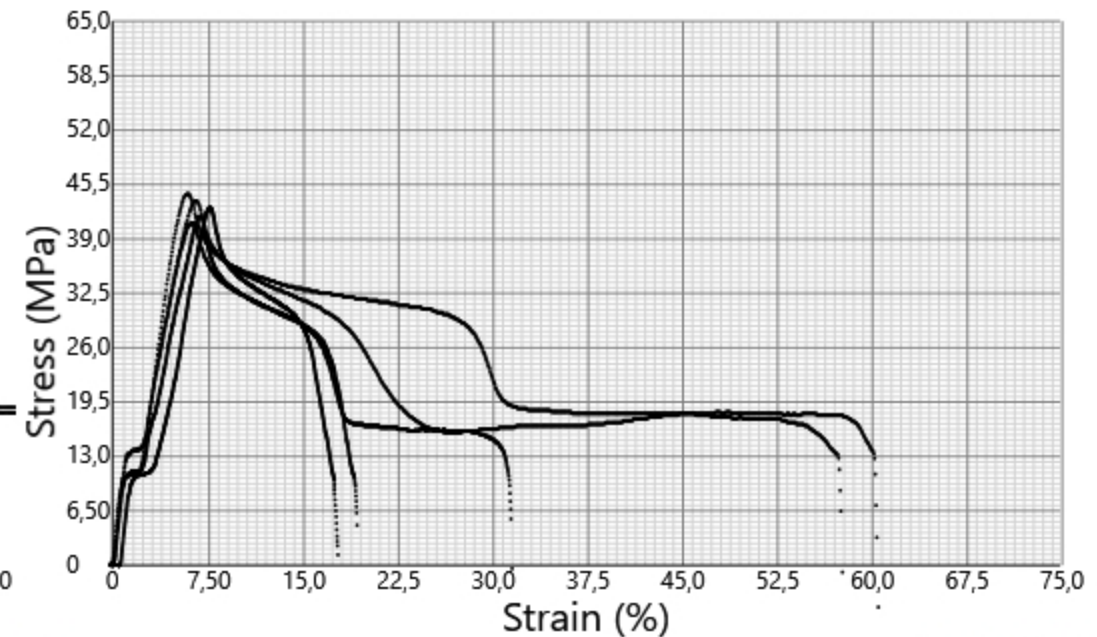
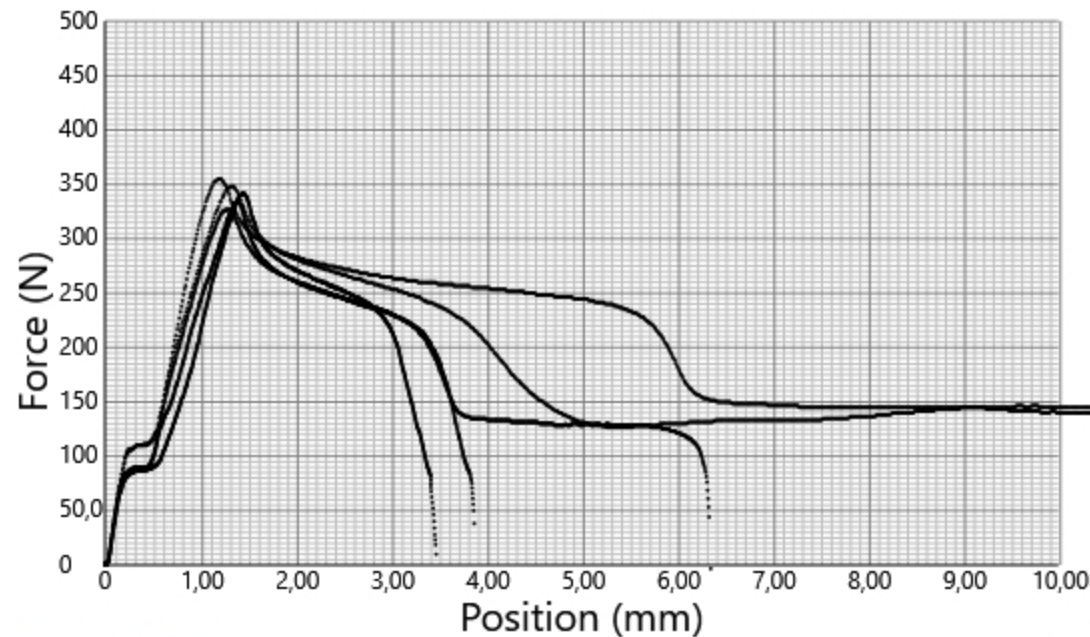


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 40C TØRR - PLA (A-2-3)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	714	332	41,5	338	42,3	25,4
2	PLA	50,0	4,00	2,00	651	331	41,3	335	41,9	28,4
3	PLA	50,0	4,00	2,00	1330	137	17,1	410	51,2	31,6
4	PLA	50,0	4,00	2,00	1290	142	17,7	413	51,7	20,7
5	PLA	50,0	4,00	2,00	1350	111	13,8	382	47,7	24,1
Average					1070	210	26,3	376	47,0	26,0
SD					353	111	13,9	37,7	4,71	4,17

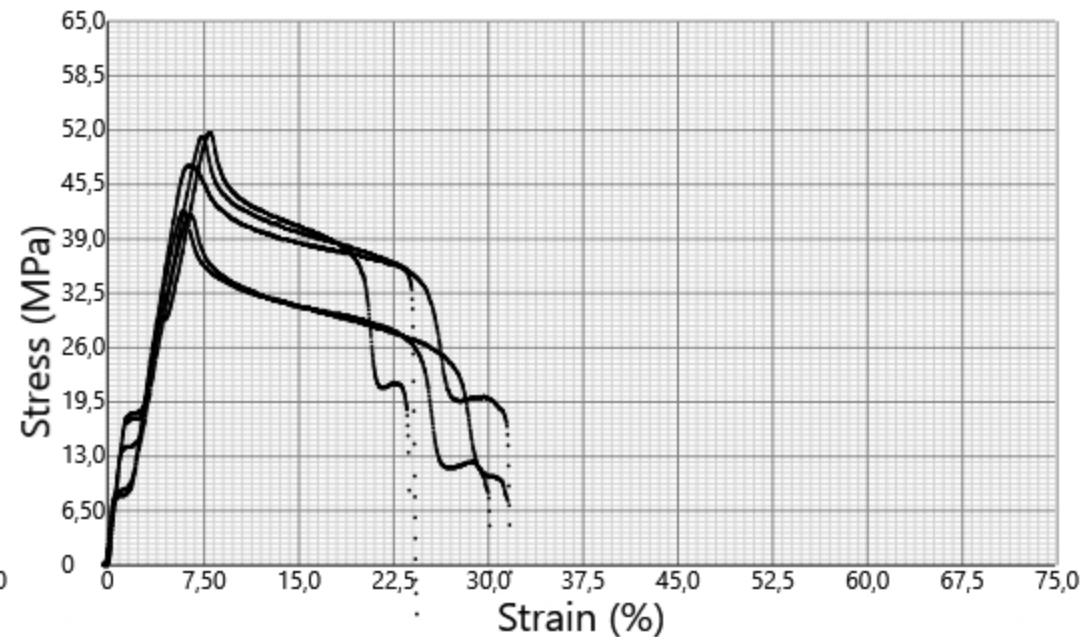
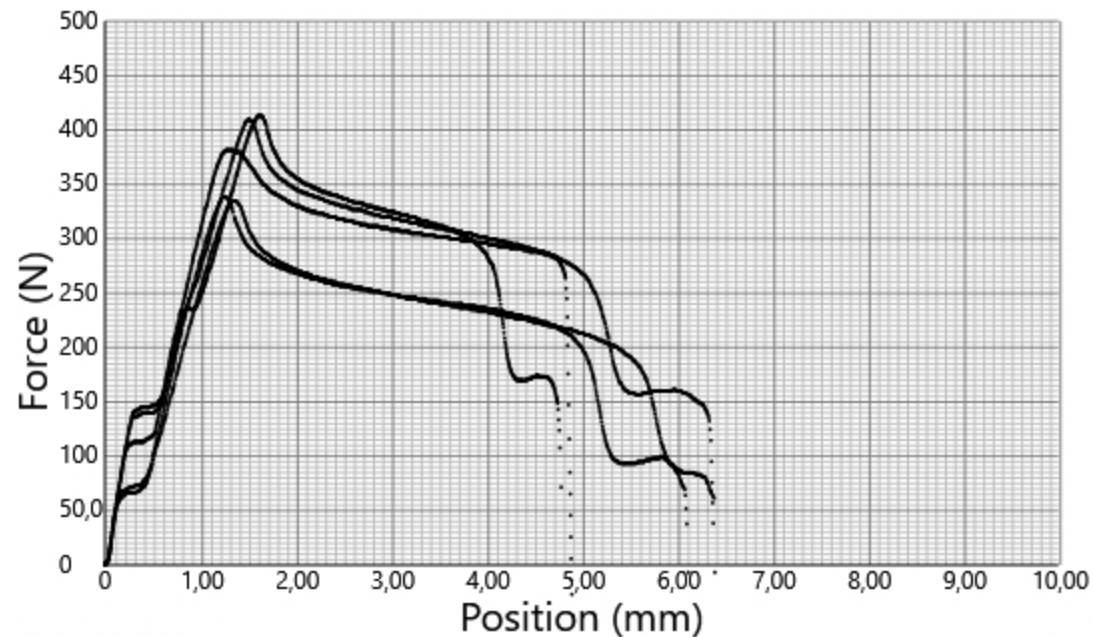


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 40C VÅT - PLA (A-2-4)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1220	88,3	11,0	327	40,8	37,6
2	PLA	50,0	4,00	2,00	1090	88,3	11,0	333	41,7	31,1
3	PLA	50,0	4,00	2,00	641	313	39,1	320	40,0	47,9
4	PLA	50,0	4,00	2,00	1300	110	13,7	353	44,2	30,2
5	PLA	50,0	4,00	2,00	1270	110	13,7	345	43,1	25,2
Average					1100	142	17,7	336	42,0	34,4
SD					272	96,0	12,0	13,6	1,70	8,76

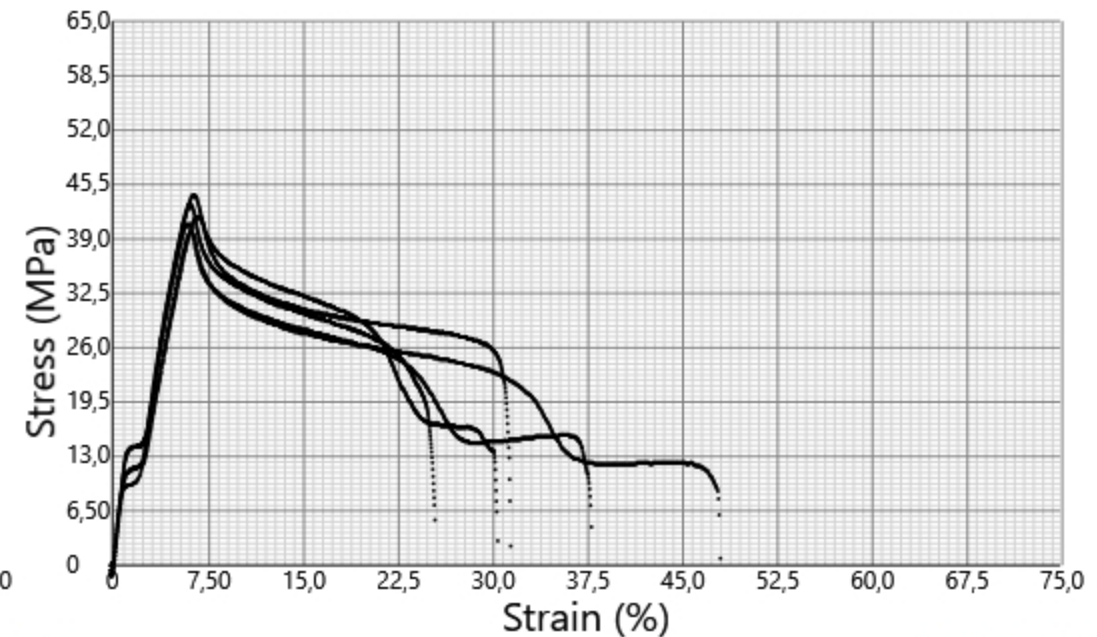
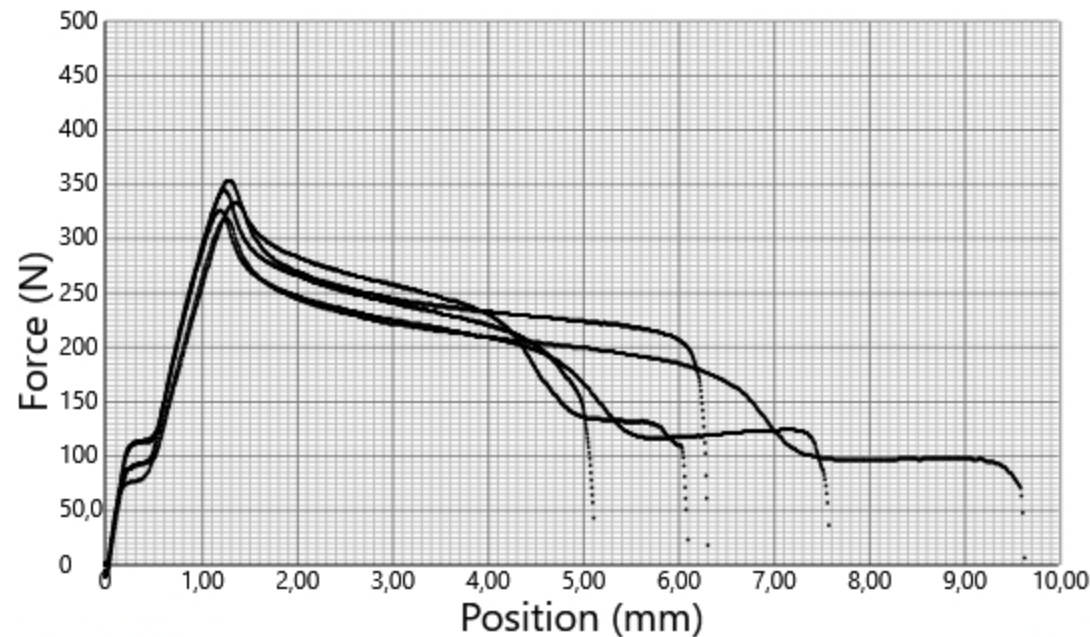


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 60C VÅT - PLA (A-3-4)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	N/F	N/F	N/F	N/F	N/F	N/F
2	PLA	50,0	4,00	2,00	N/F	N/F	N/F	N/F	N/F	N/F
3	PLA	50,0	4,00	2,00	N/F	N/F	N/F	N/F	N/F	N/F
4	PLA	50,0	4,00	2,00	N/F	N/F	N/F	N/F	N/F	N/F
5	PLA	50,0	4,00	2,00	N/F	N/F	N/F	N/F	N/F	N/F
Average					N/A	N/A	N/A	N/A	N/A	N/A
SD					N/A	N/A	N/A	N/A	N/A	N/A

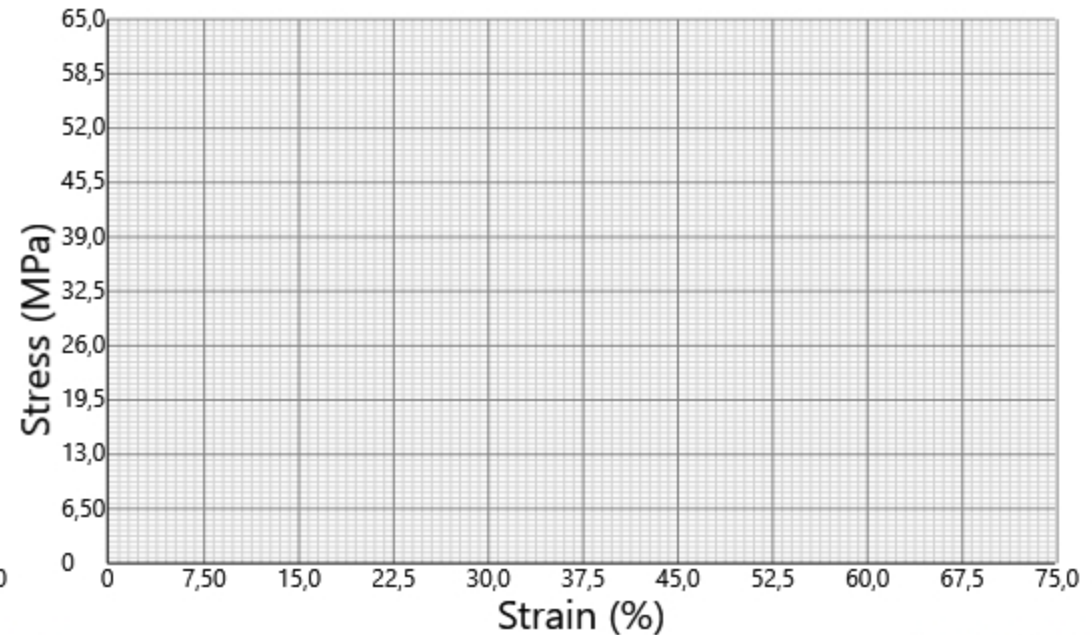
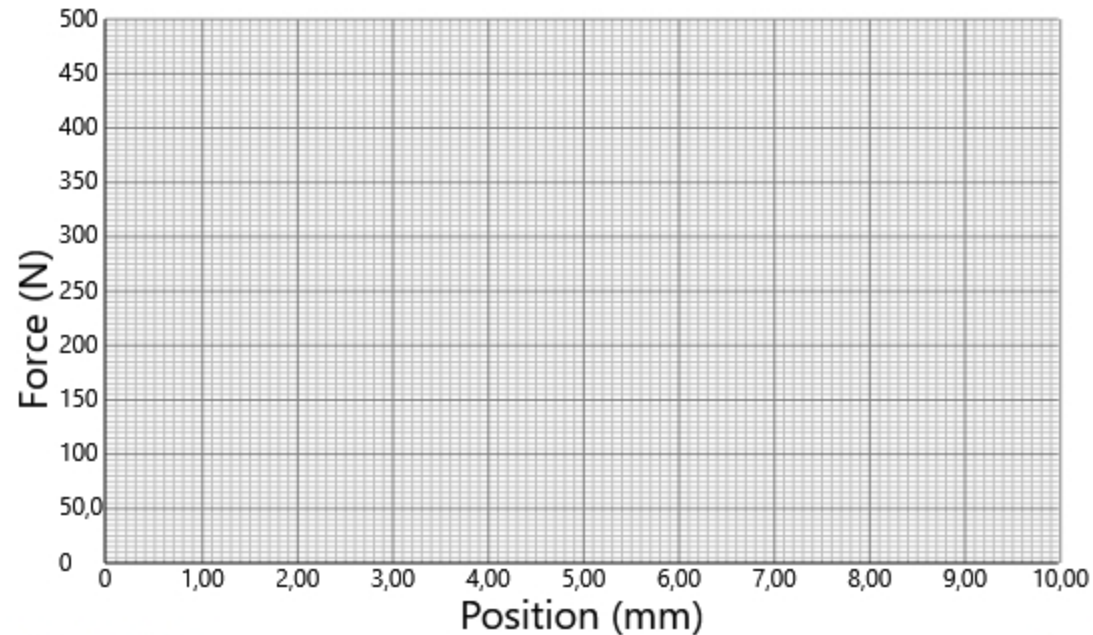


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 20C TØRR - PETG (B-1-3)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	808	115	14,4	363	45,4	11,7
2	PETG	50,0	4,00	2,00	823	113	14,1	360	45,0	11,7
3	PETG	50,0	4,00	2,00	815	125	15,6	372	46,5	11,0
4	PETG	50,0	4,00	2,00	823	110	13,7	365	45,6	11,9
5	PETG	50,0	4,00	2,00	829	151	18,8	405	50,6	13,3
Average					820	123	15,3	373	46,6	11,9
SD					7,92	16,6	2,07	18,4	2,30	0,843

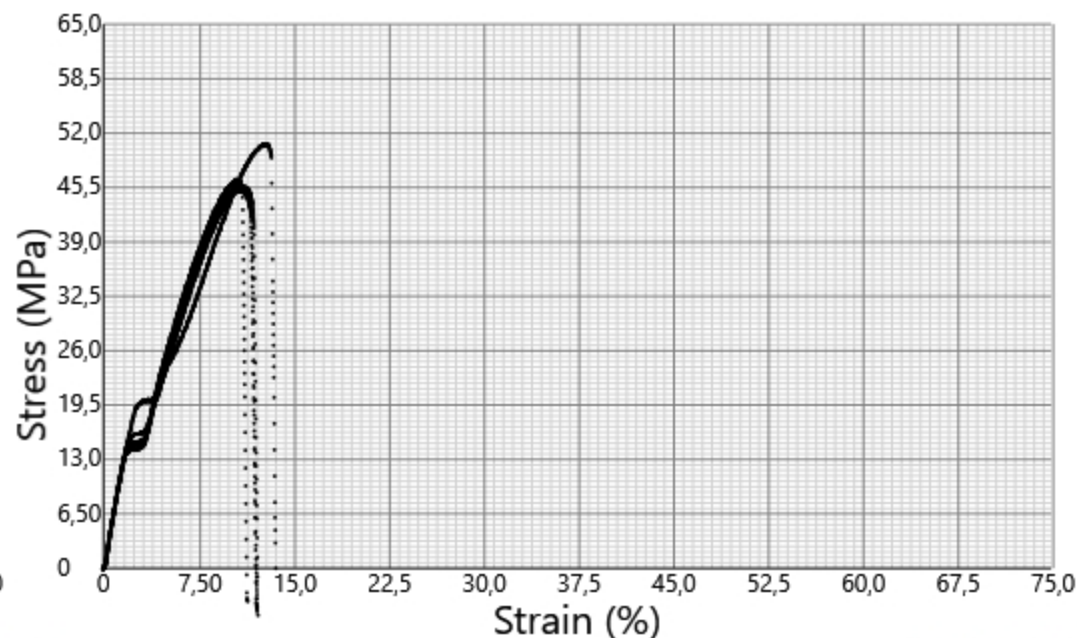
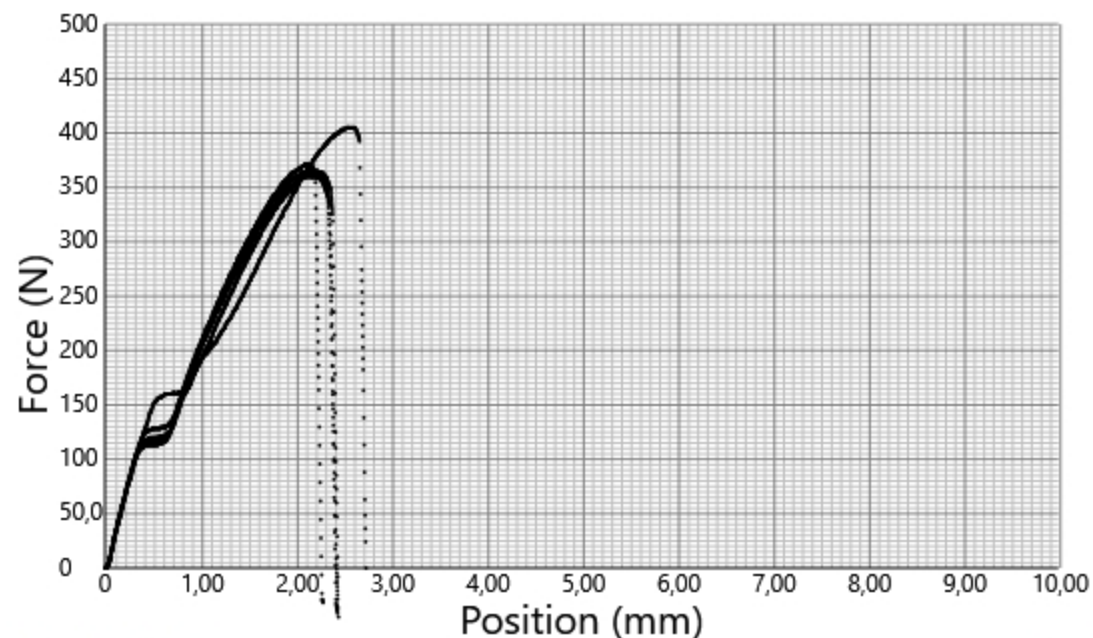


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 20C - PETG (B-1-4)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	837	109	13,6	345	43,1	9,68
2	PETG	50,0	4,00	2,00	919	126	15,8	372	46,5	11,6
3	PETG	50,0	4,00	2,00	1100	88,3	11,0	368	46,0	124
4	PETG	50,0	4,00	2,00	782	78,5	9,82	302	37,7	30,6
5	PETG	50,0	4,00	2,00	839	147	18,4	383	47,9	39,3
Average					895	110	13,7	354	44,2	43,1
SD					123	27,8	3,47	32,4	4,05	47,1

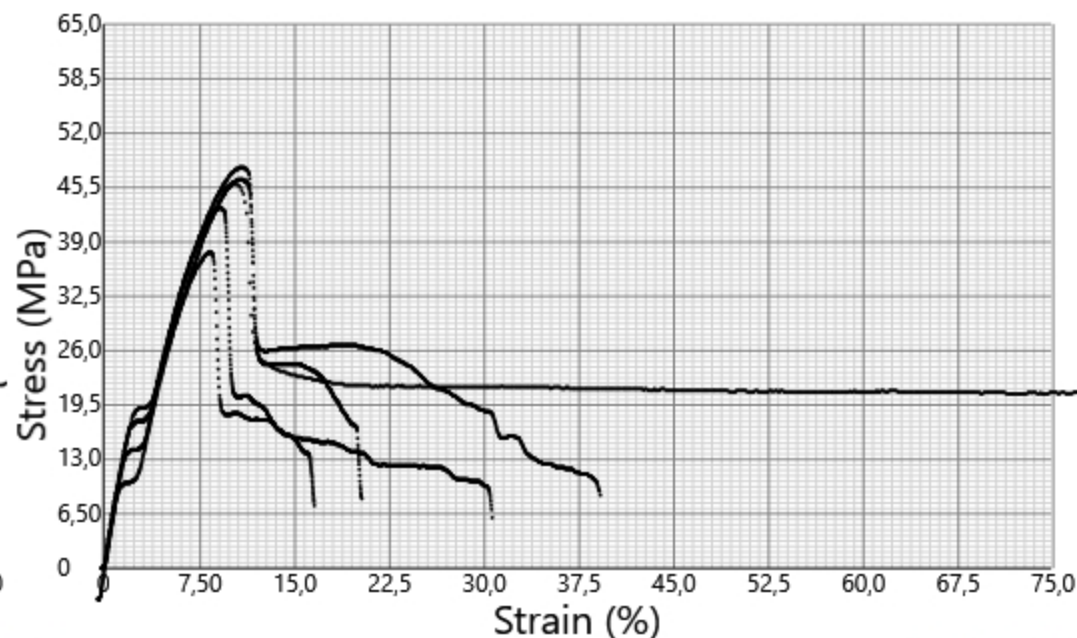
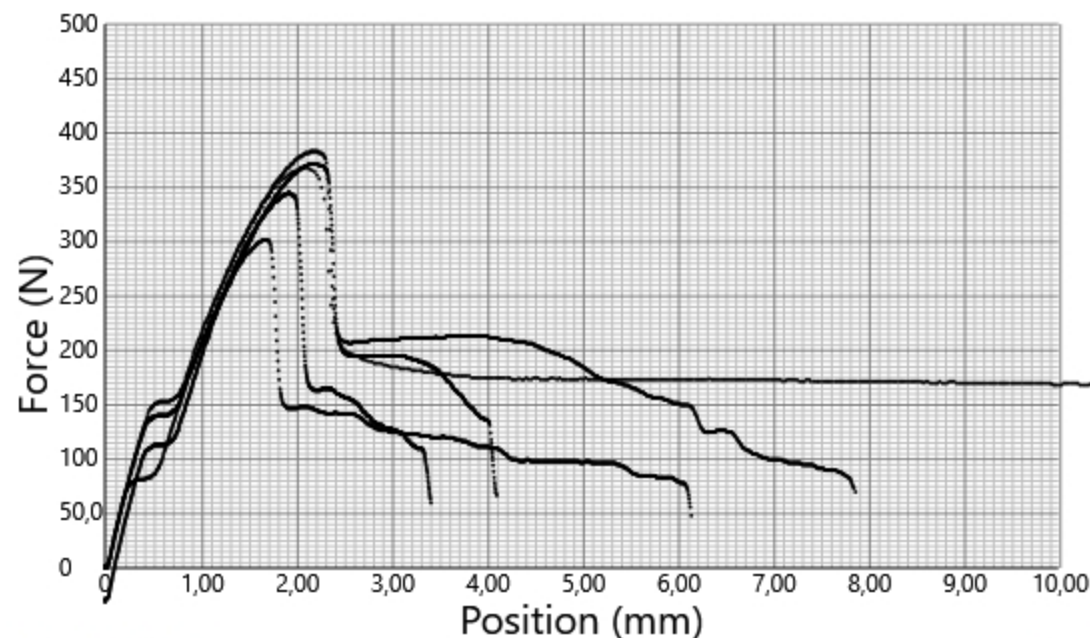


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 40C TØRR - PETG (B-2-3)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	708	115	14,4	447	55,8	13,4
2	PETG	50,0	4,00	2,00	816	158	19,8	460	57,5	13,1
3	PETG	50,0	4,00	2,00	795	125	15,6	430	53,7	12,4
4	PETG	50,0	4,00	2,00	853	163	20,4	463	57,9	12,9
5	PETG	50,0	4,00	2,00	776	137	17,1	447	55,8	13,6
Average					790	140	17,4	449	56,2	13,1
SD					53,7	20,9	2,61	13,2	1,65	0,463

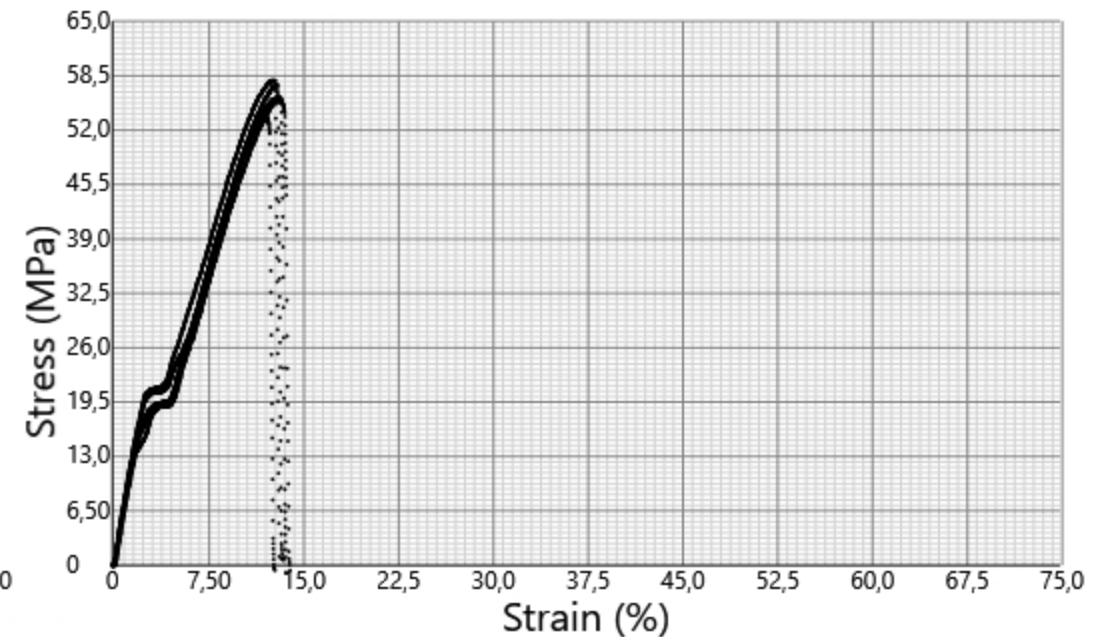
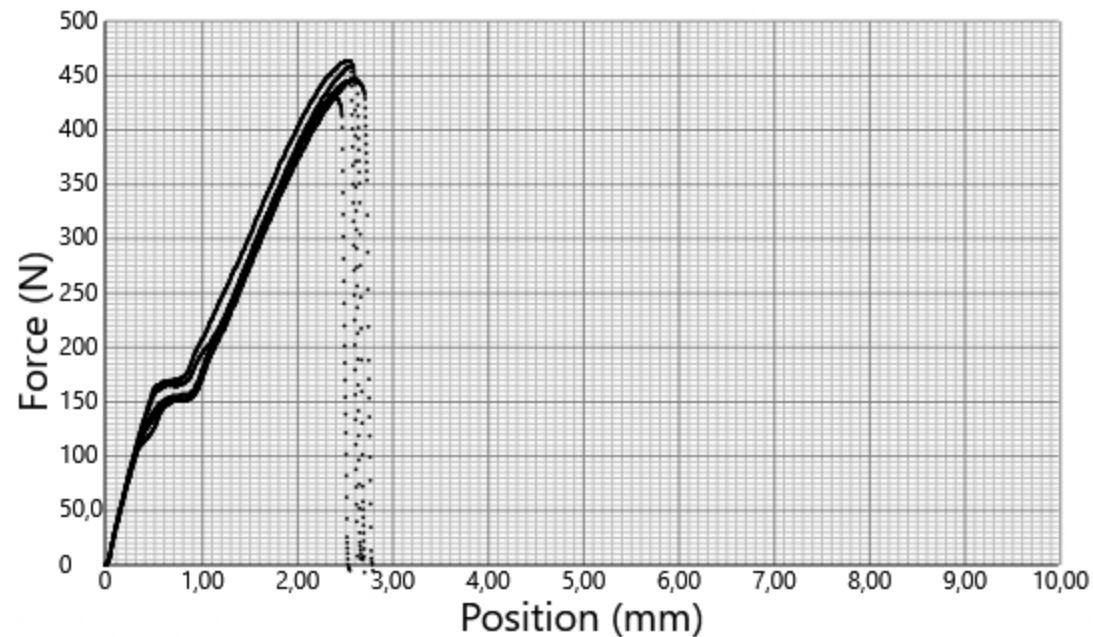


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 40C - PETG (B-2-4)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	849	140	17,4	415	51,9	11,8
2	PETG	50,0	4,00	2,00	830	137	17,1	412	51,5	11,2
3	PETG	50,0	4,00	2,00	798	135	16,9	408	51,0	11,4
4	PETG	50,0	4,00	2,00	827	134	16,8	395	49,4	10,8
5	PETG	50,0	4,00	2,00	822	147	18,3	413	51,7	11,3
Average					825	138	17,3	409	51,1	11,3
SD					18,9	5,01	0,628	8,03	1,00	0,294

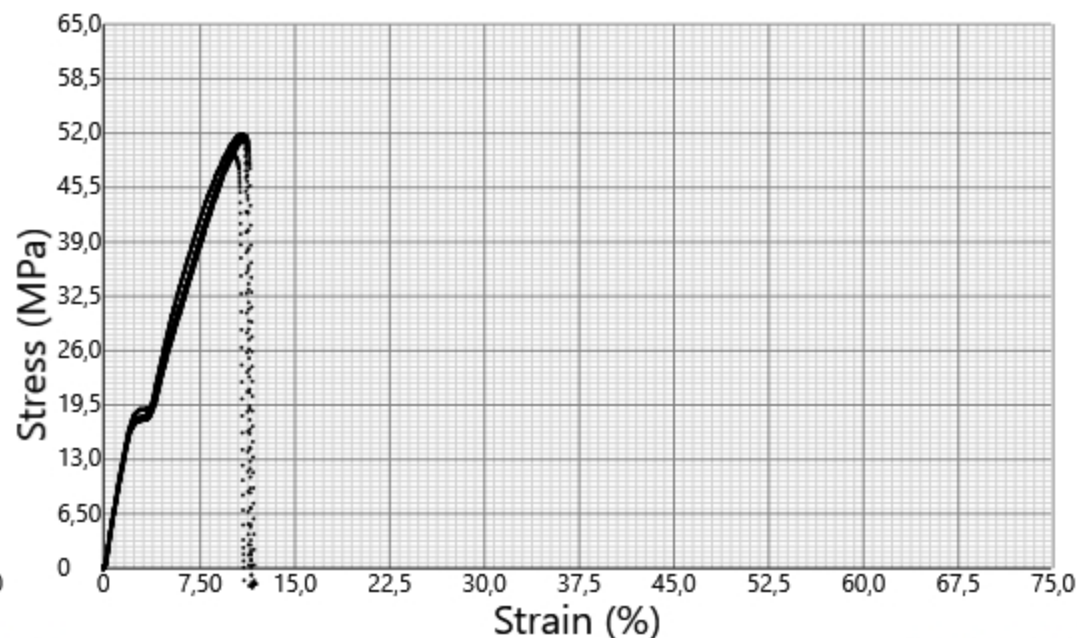
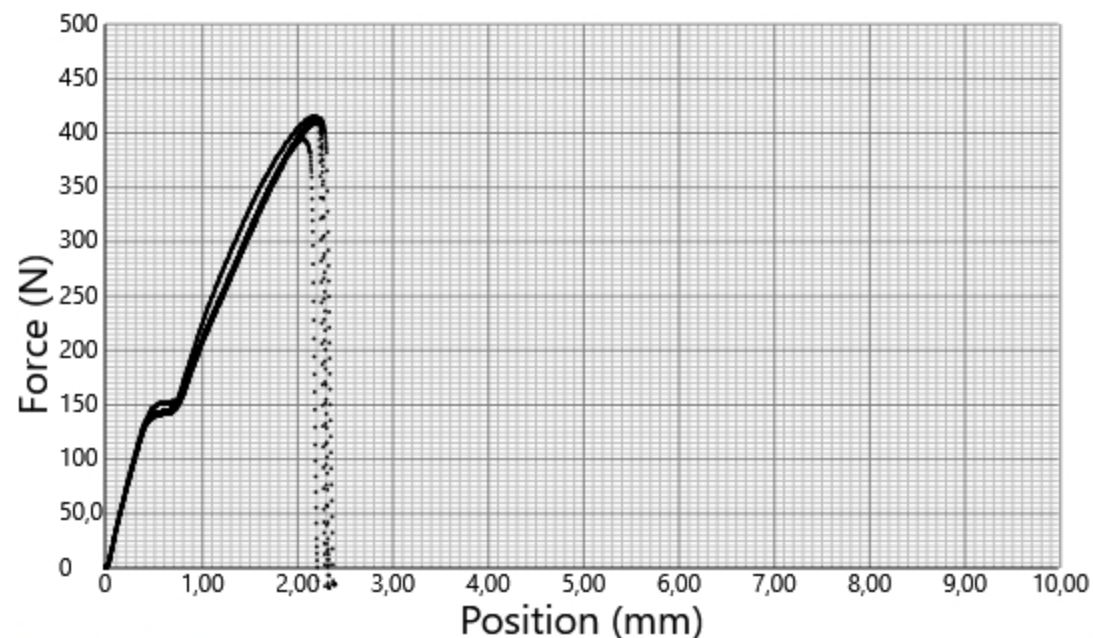


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 60C TØRR - PETG (B-3-3)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	836	144	18,0	383	47,9	11,7
2	PETG	50,0	4,00	2,00	819	159	19,9	413	51,7	13,4
3	PETG	50,0	4,00	2,00	823	156	19,5	405	50,6	12,9
4	PETG	50,0	4,00	2,00	849	155	19,4	420	52,5	14,1
5	PETG	50,0	4,00	2,00	795	112	14,0	370	46,2	12,8
Average					824	145	18,1	398	49,8	13,0
SD					20,2	19,4	2,43	21,0	2,63	0,906

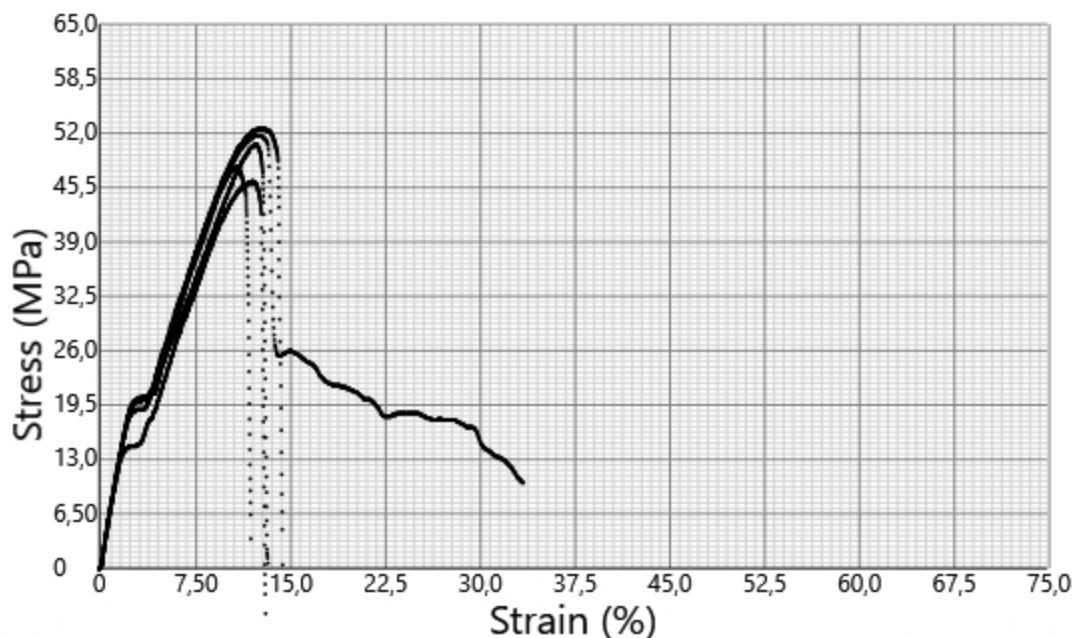
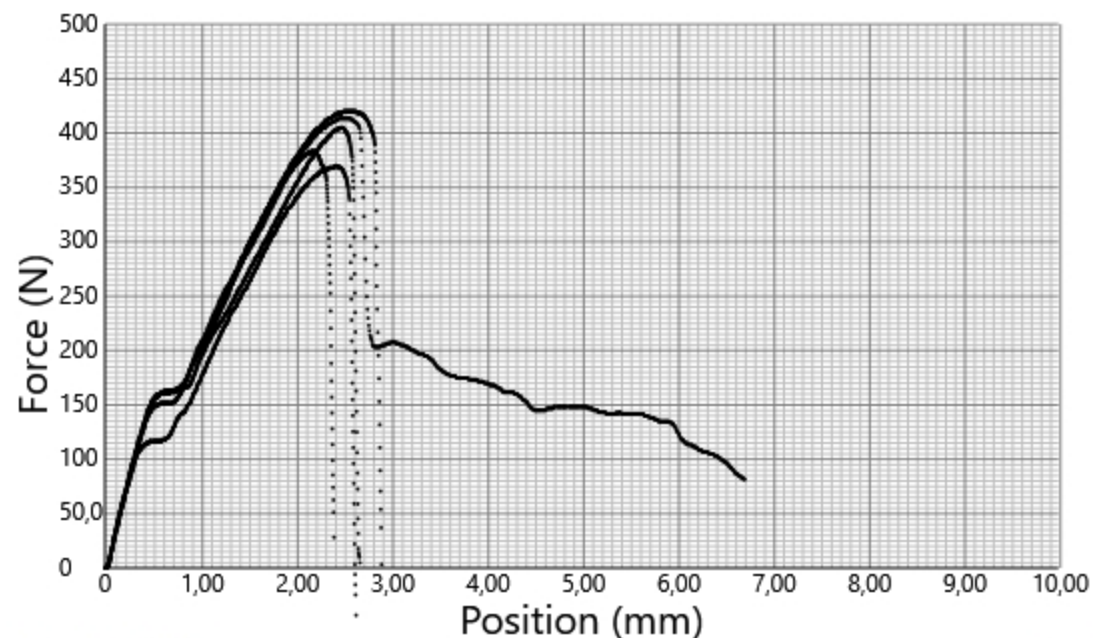


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 60C - PETG (B-3-4)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	773	123	15,4	348	43,5	12,1
2	PETG	50,0	4,00	2,00	759	117	14,7	345	43,1	12,5
3	PETG	50,0	4,00	2,00	790	113	14,2	338	42,3	11,8
4	PETG	50,0	4,00	2,00	744	111	13,9	355	44,4	13,7
5	PETG	50,0	4,00	2,00	773	119	14,8	350	43,7	12,3
Average					768	117	14,6	347	43,4	34,6
SD					17,1	4,67	0,583	6,19	0,774	49,5

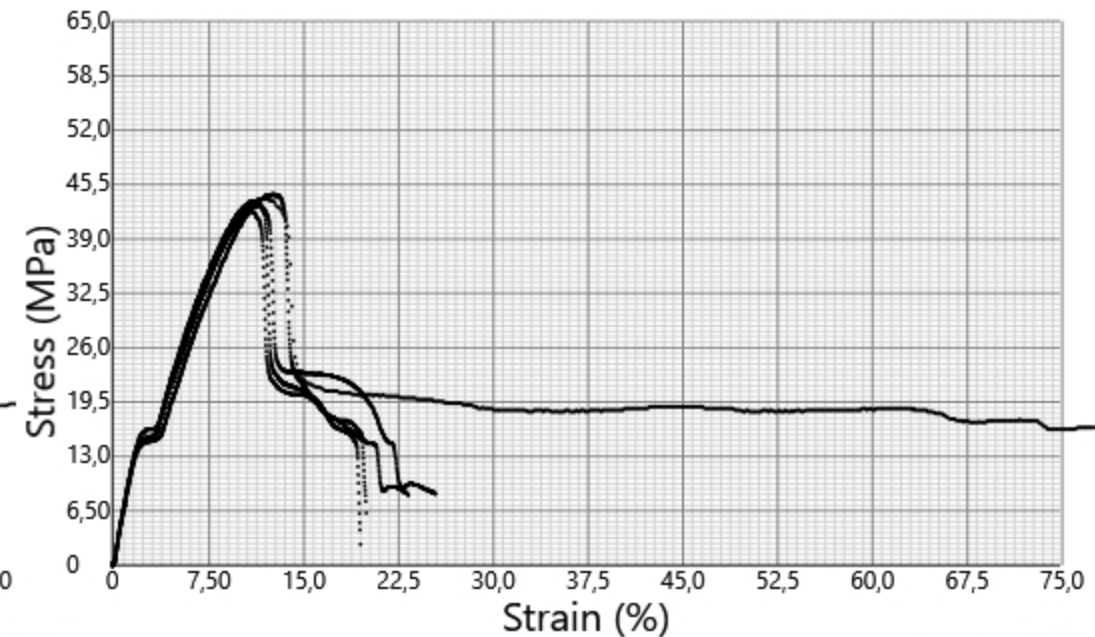
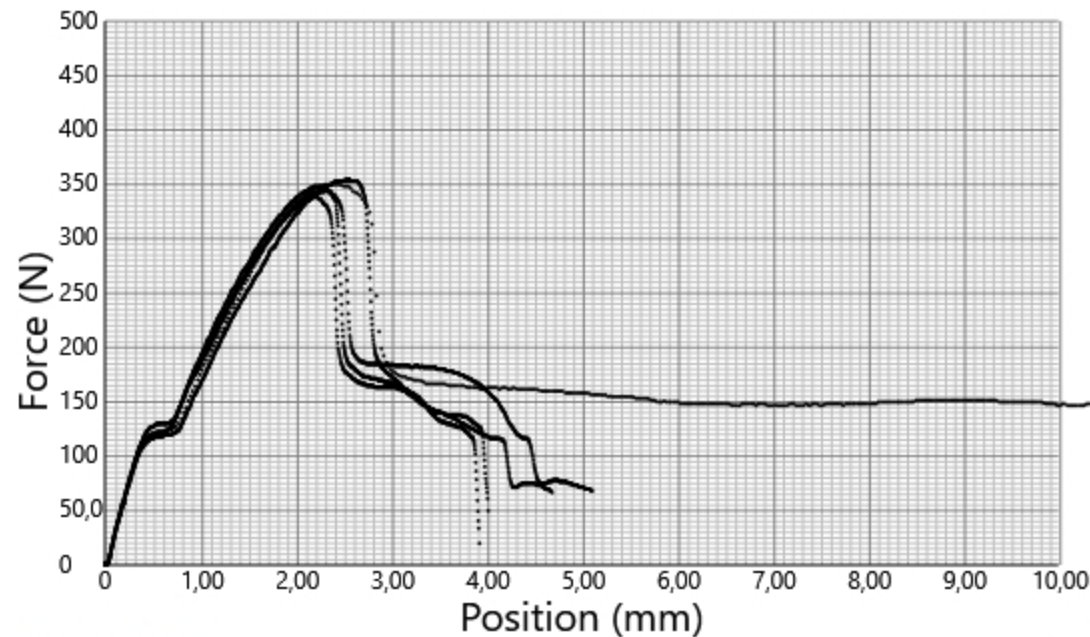


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 20C TØRR - ASA (C-1-3)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	879	112	14,0	277	34,6	8,58
2	ASA	50,0	4,00	2,00	1000	143	17,9	332	41,5	10,0
3	ASA	50,0	4,00	2,00	938	112	14,0	288	36,0	10,2
4	ASA	50,0	4,00	2,00	878	109	13,7	215	26,9	6,24
5	ASA	50,0	4,00	2,00	977	108	13,5	218	27,3	6,57
Average					935	117	14,6	266	33,2	8,33
SD					56,0	14,7	1,84	49,5	6,19	1,87

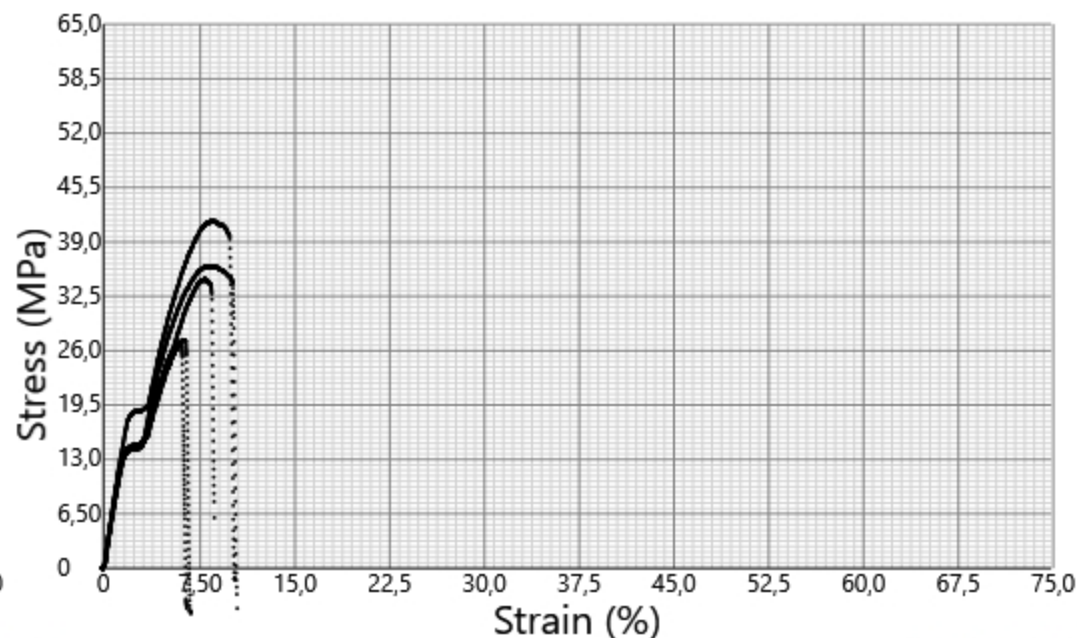
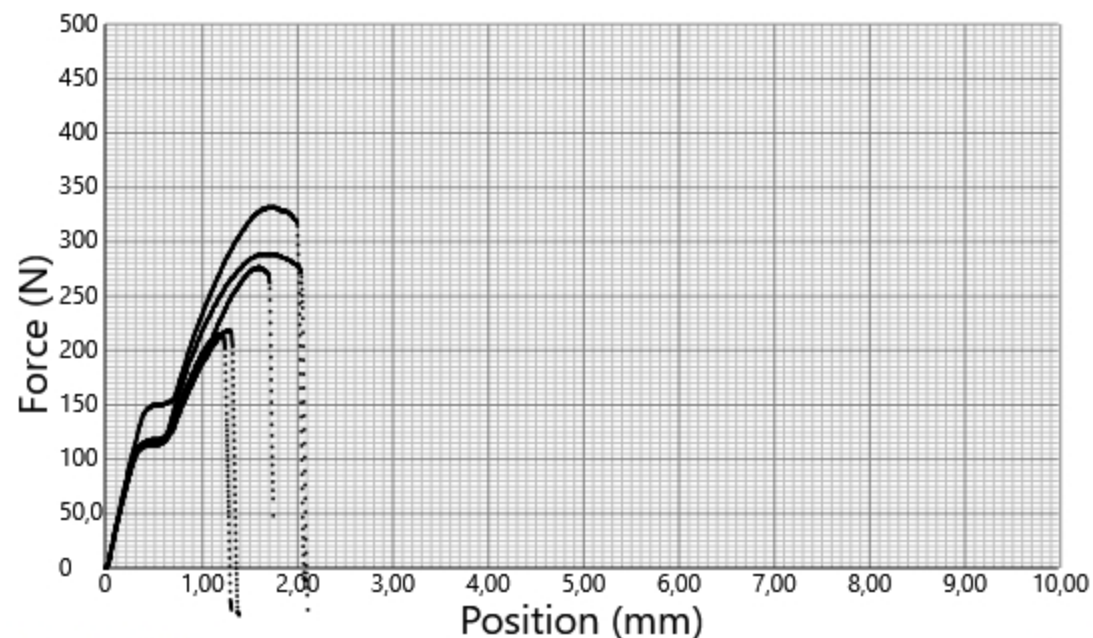


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 20C - ASA (C-1-4)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	869	121	15,2	242	30,2	7,44
2	ASA	50,0	4,00	2,00	846	126	15,8	302	37,7	9,61
3	ASA	50,0	4,00	2,00	826	120	15,0	295	36,9	9,90
4	ASA	50,0	4,00	2,00	793	83,3	10,4	235	29,4	7,25
5	ASA	50,0	4,00	2,00	887	103	12,9	208	26,0	6,82
Average					844	111	13,8	256	32,0	8,21
SD					36,8	17,7	2,22	40,4	5,05	1,44

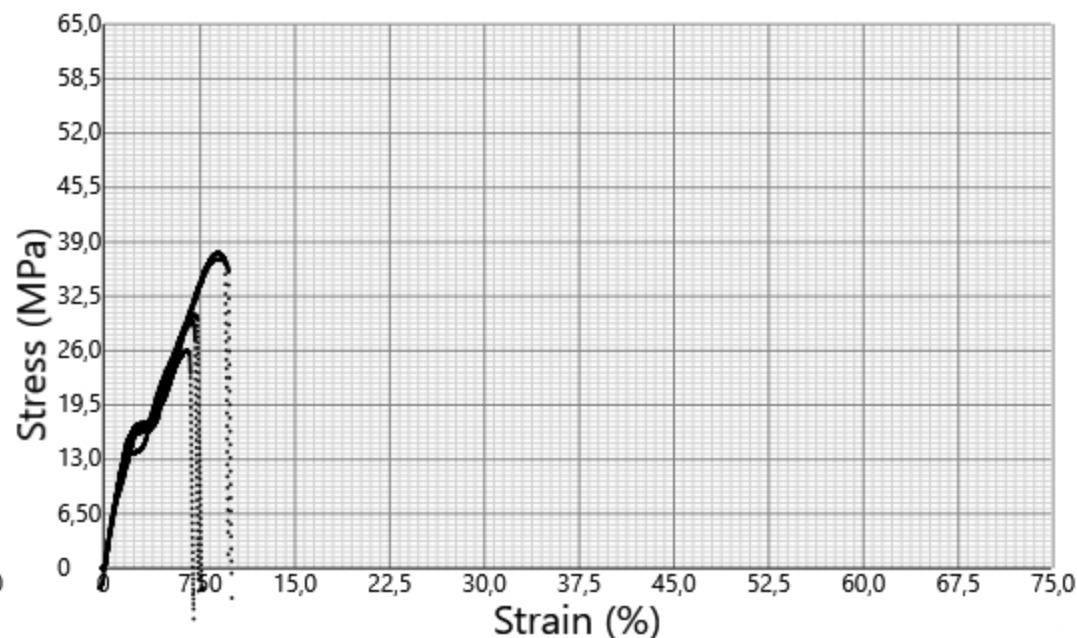
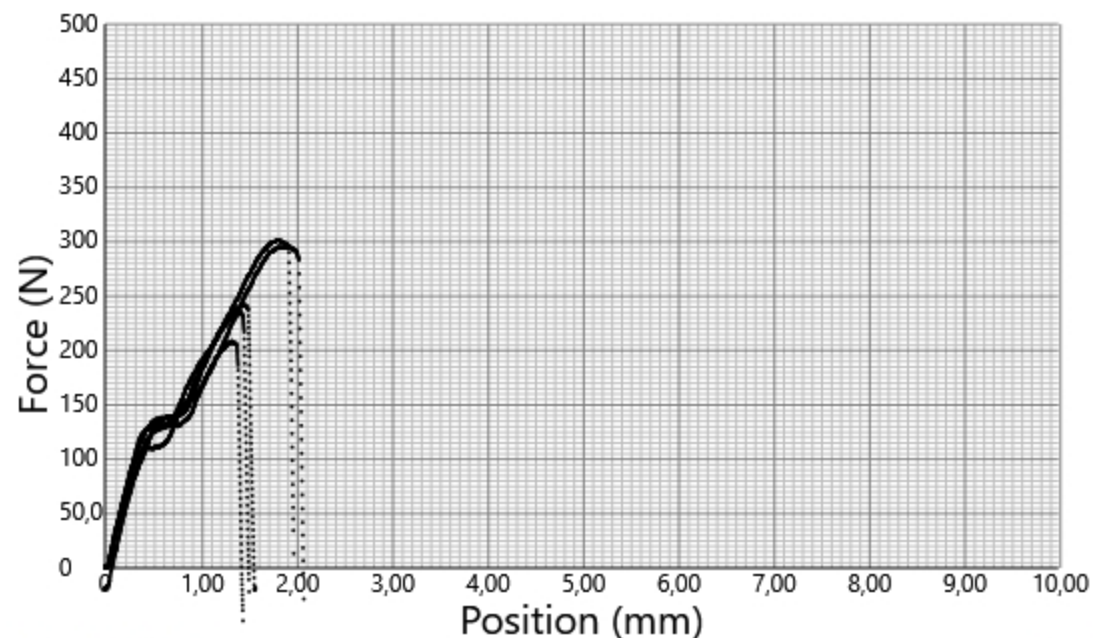


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 40C TØRR - ASA (C-2-3)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	874	110	13,8	302	37,7	9,71
2	ASA	50,0	4,00	2,00	893	107	13,4	285	35,6	9,86
3	ASA	50,0	4,00	2,00	927	117	14,6	298	37,3	9,46
4	ASA	50,0	4,00	2,00	887	113	14,2	292	36,5	9,52
5	ASA	50,0	4,00	2,00	894	113	14,2	308	38,5	12,1
Average					895	112	14,0	297	37,1	10,1
SD					19,5	3,66	0,458	9,01	1,13	1,10

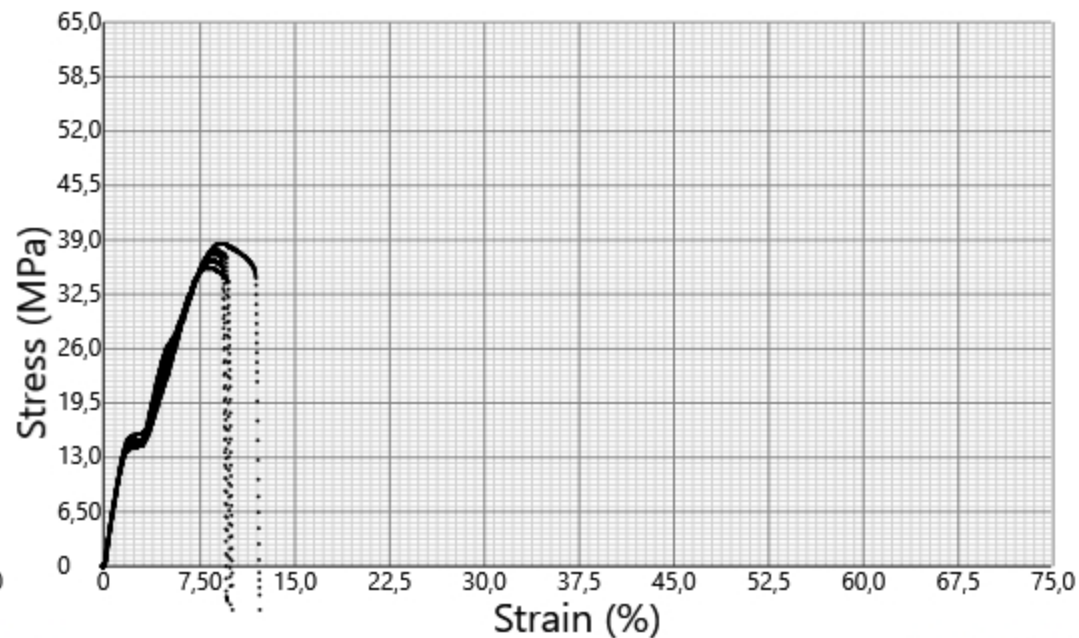
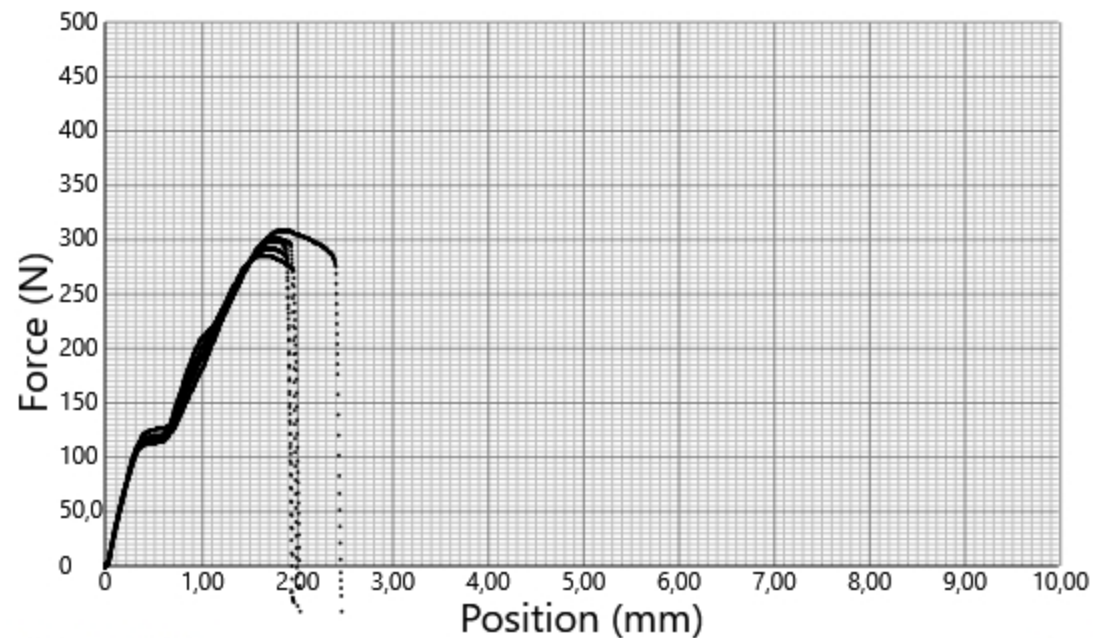


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 40C - ASA (C-2-4)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	884	147	18,3	328	41,0	9,34
2	ASA	50,0	4,00	2,00	906	115	14,4	285	35,6	8,69
3	ASA	50,0	4,00	2,00	880	113	14,1	275	34,4	8,24
4	ASA	50,0	4,00	2,00	939	112	13,9	307	38,3	10,2
5	ASA	50,0	4,00	2,00	954	116	14,5	225	28,1	6,00
Average					912	120	15,0	284	35,5	8,48
SD					32,9	14,8	1,85	38,9	4,86	1,56

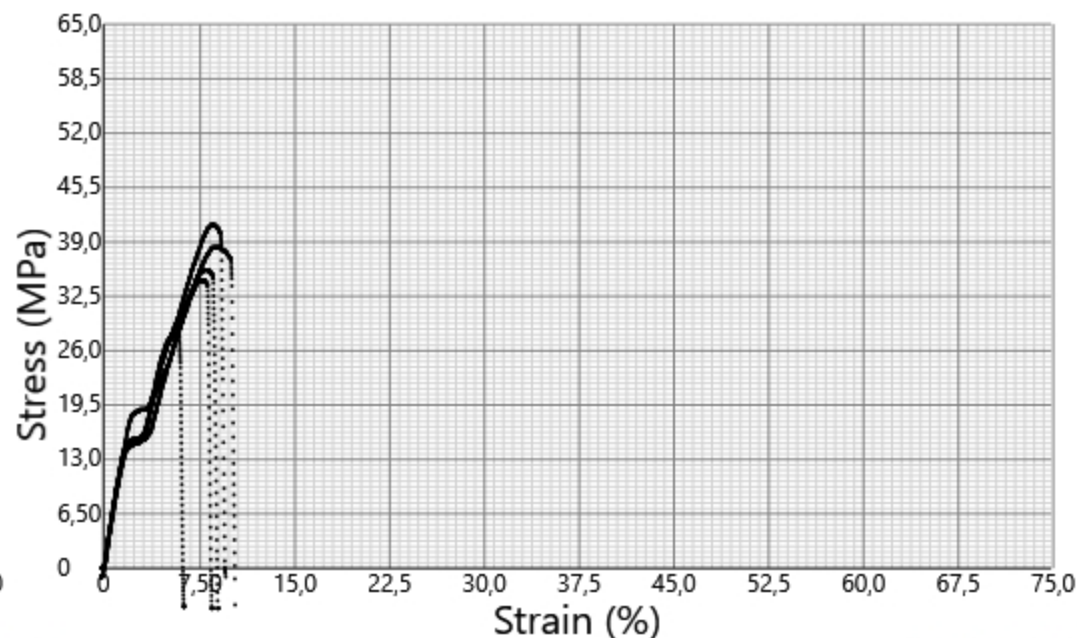
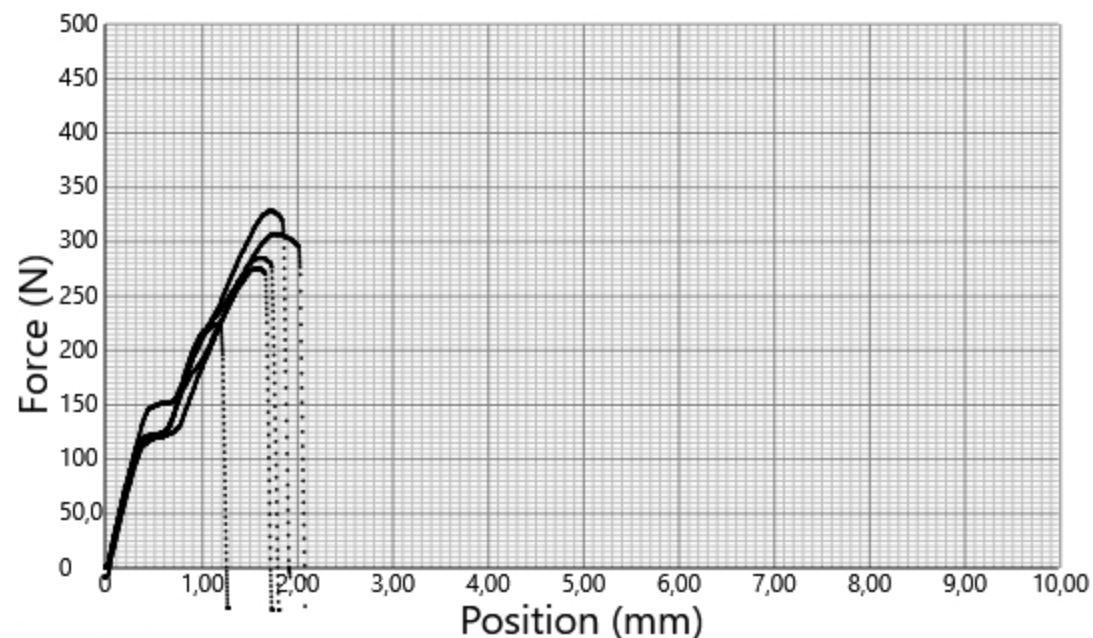


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 60C TØRR - ASA (C-3-3)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	916	140	17,5	318	39,8	8,80
2	ASA	50,0	4,00	2,00	883	113	14,2	232	29,0	6,96
3	ASA	50,0	4,00	2,00	878	125	15,6	305	38,1	10,1
4	ASA	50,0	4,00	2,00	929	107	13,3	302	37,7	10,4
5	ASA	50,0	4,00	2,00	941	107	13,3	277	34,6	8,45
Average					910	118	14,8	287	35,8	8,93
SD					27,8	14,2	1,77	34,2	4,28	1,37

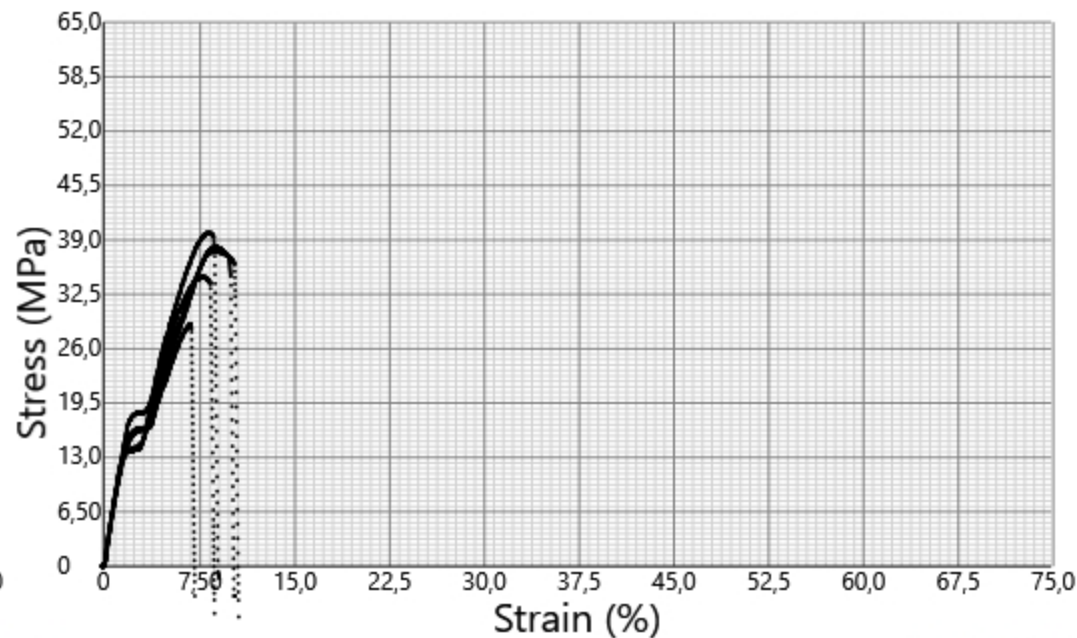
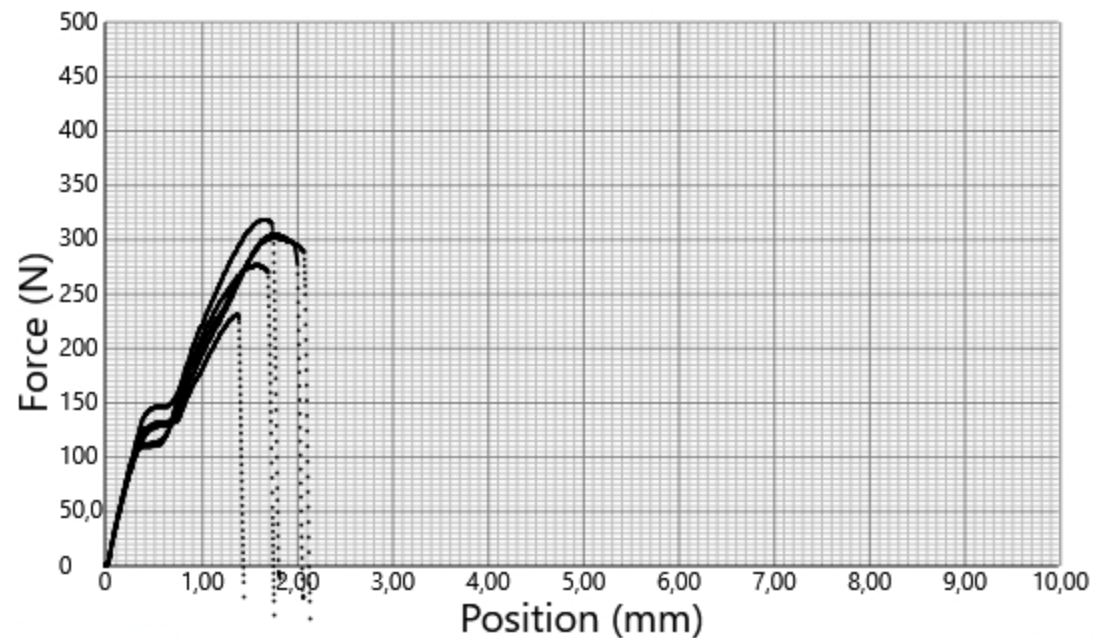


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE6 60C - ASA (C-3-4)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	882	119	14,9	228	28,5	6,14
2	ASA	50,0	4,00	2,00	932	157	19,6	335	41,9	9,24
3	ASA	50,0	4,00	2,00	915	137	17,1	330	41,2	9,50
4	ASA	50,0	4,00	2,00	885	129	16,2	310	38,7	9,38
5	ASA	50,0	4,00	2,00	899	123	15,4	305	38,1	9,07
Average					902	133	16,6	302	37,7	8,66
SD					21,0	14,9	1,86	42,9	5,37	1,42

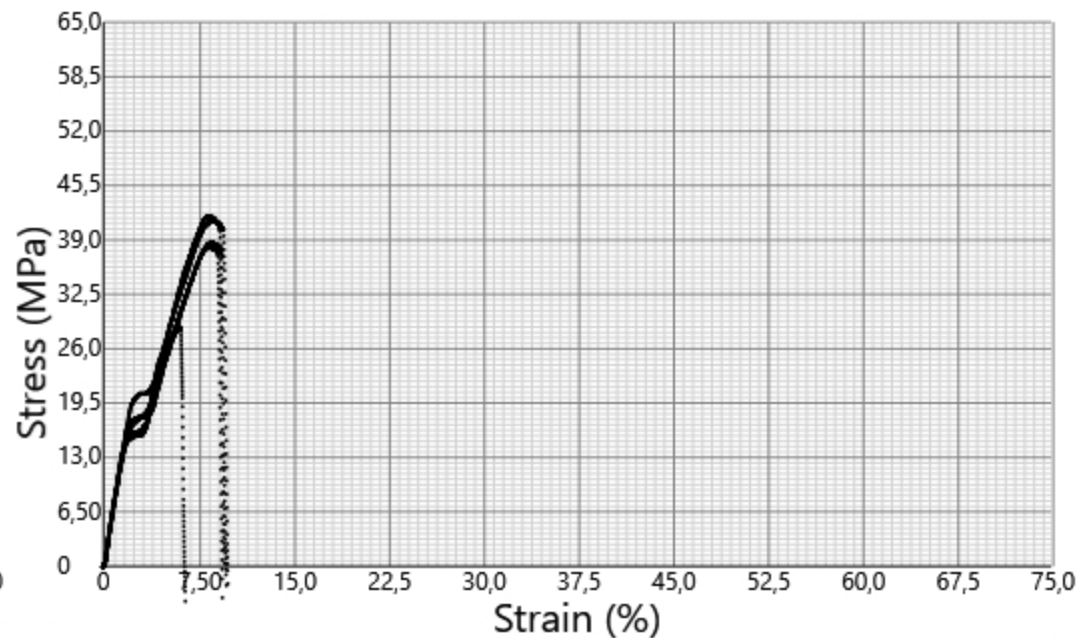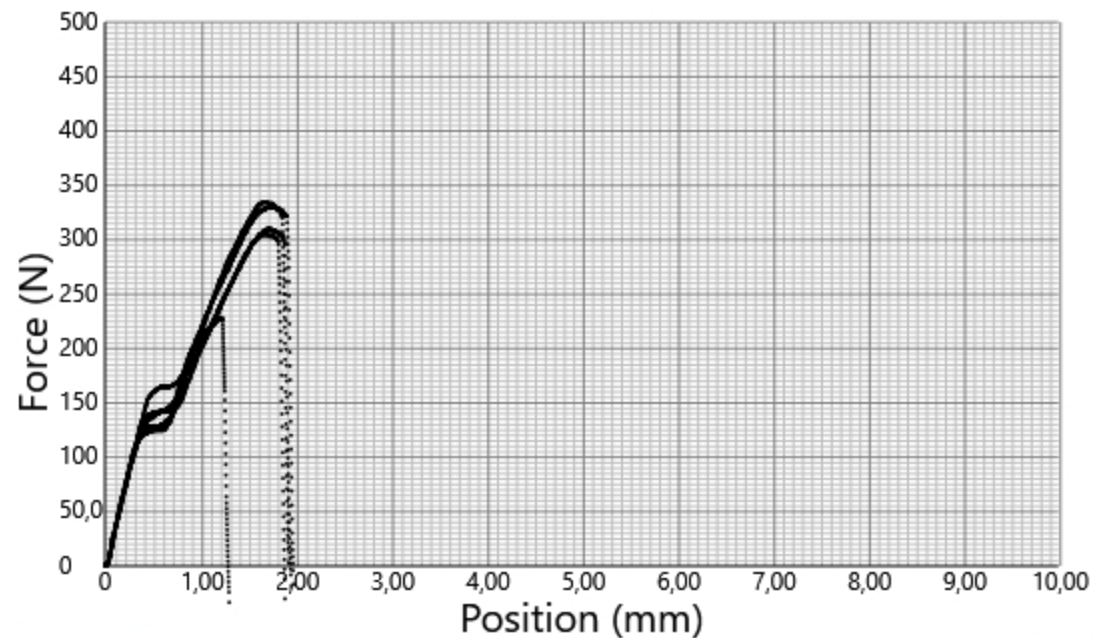



Uke 9

USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 20C TØRR - PLA (A-1-5)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1410	125	15,6	373	46,7	35,9
2	PLA	50,0	4,00	2,00	1330	143	17,8	396	49,6	36,4
3	PLA	50,0	4,00	2,00	1420	138	17,2	391	48,9	35,5
4	PLA	50,0	4,00	2,00	1330	152	19,0	413	51,7	19,3
5	PLA	50,0	4,00	2,00	1280	147	18,3	397	49,6	38,6
Average					1350	141	17,6	394	49,3	33,1
SD					58,7	10,5	1,32	14,3	1,79	7,84

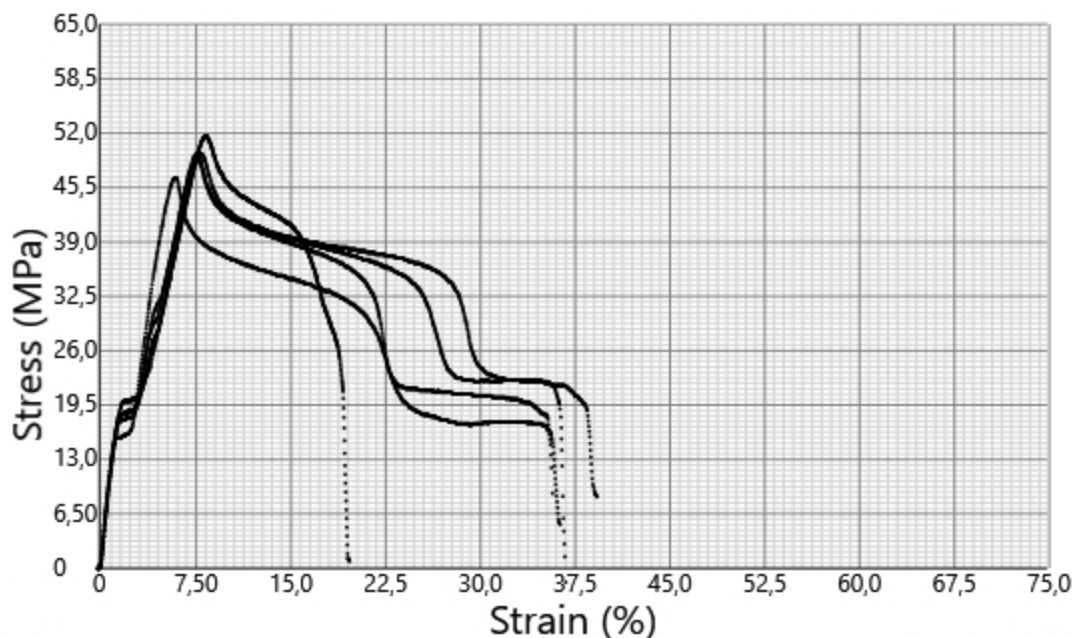
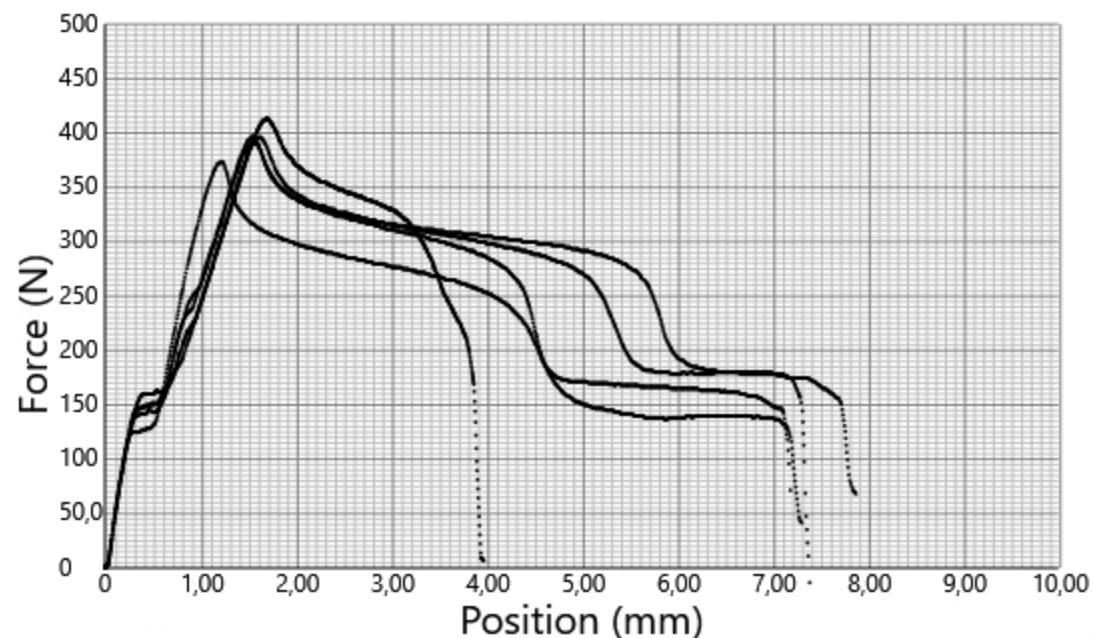


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 20C VÅT - PLA (A-1-6)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1340	152	19,0	398	49,8	23,6
2	PLA	50,0	4,00	2,00	1080	113	14,1	407	50,8	30,2
3	PLA	50,0	4,00	2,00	621	158	19,7	397	49,6	16,4
4	PLA	50,0	4,00	2,00	1290	138	17,3	395	49,4	45,1
5	PLA	50,0	4,00	2,00	1320	138	17,2	392	49,0	26,6
Average					1130	140	17,5	398	49,7	28,4
SD					302	17,4	2,18	5,60	0,700	10,6

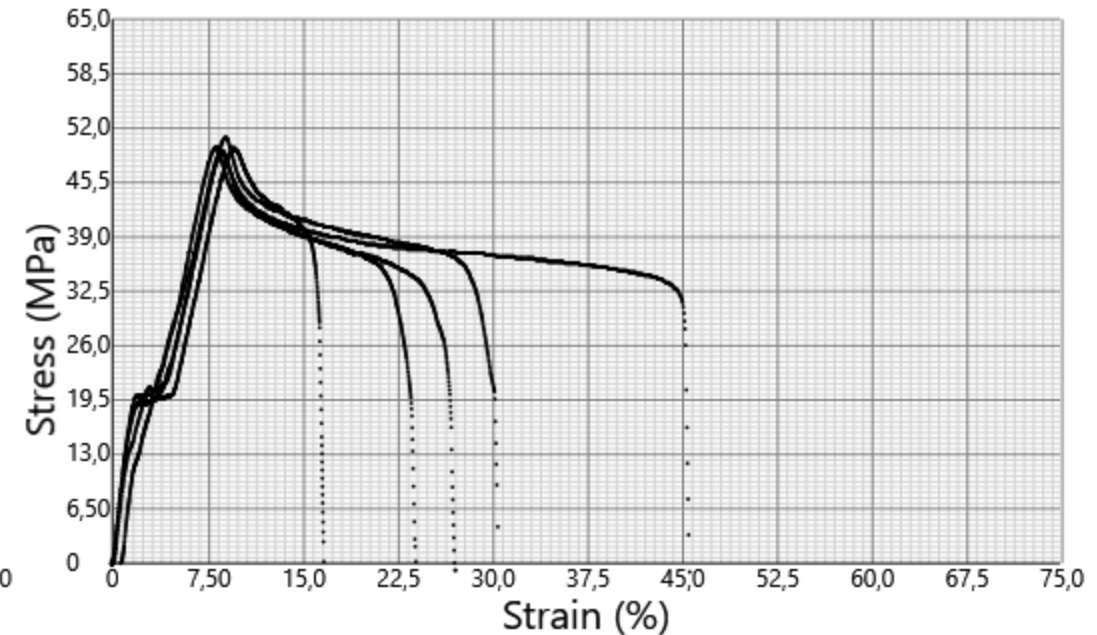
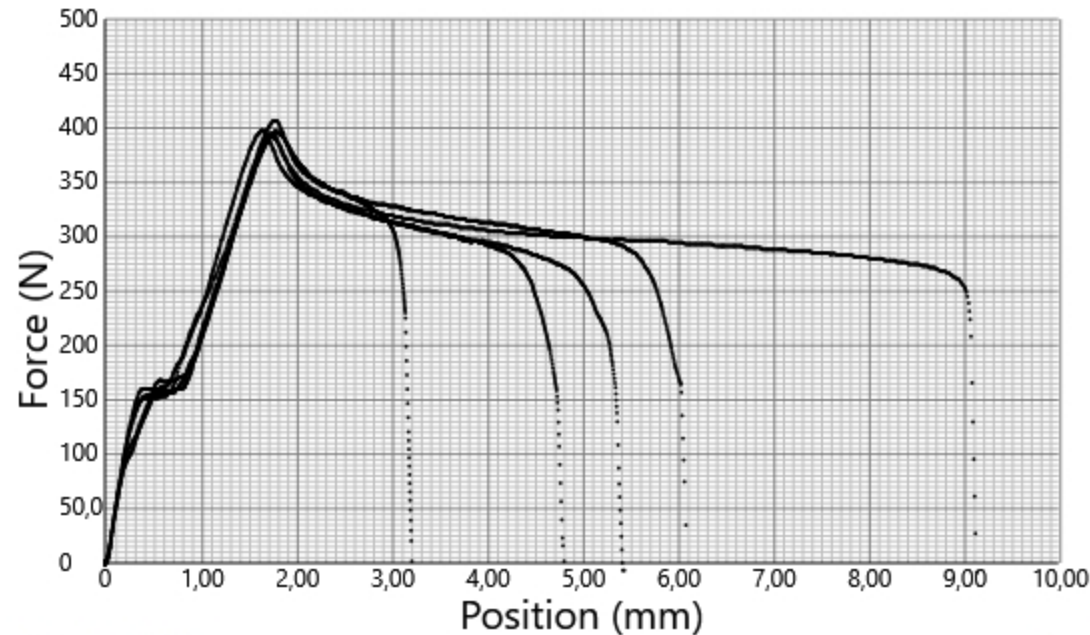


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 40C TØRR - PLA (A-2-5)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1450	152	19,0	408	51,0	15,1
2	PLA	50,0	4,00	2,00	1290	110	13,8	348	43,5	51,3
3	PLA	50,0	4,00	2,00	1360	122	15,2	372	46,4	19,2
4	PLA	50,0	4,00	2,00	1290	120	15,1	368	46,0	36,1
5	PLA	50,0	4,00	2,00	1190	115	14,3	360	45,0	57,3
Average					1320	124	15,5	371	46,4	35,8
SD					94,6	16,4	2,05	22,6	2,82	18,8

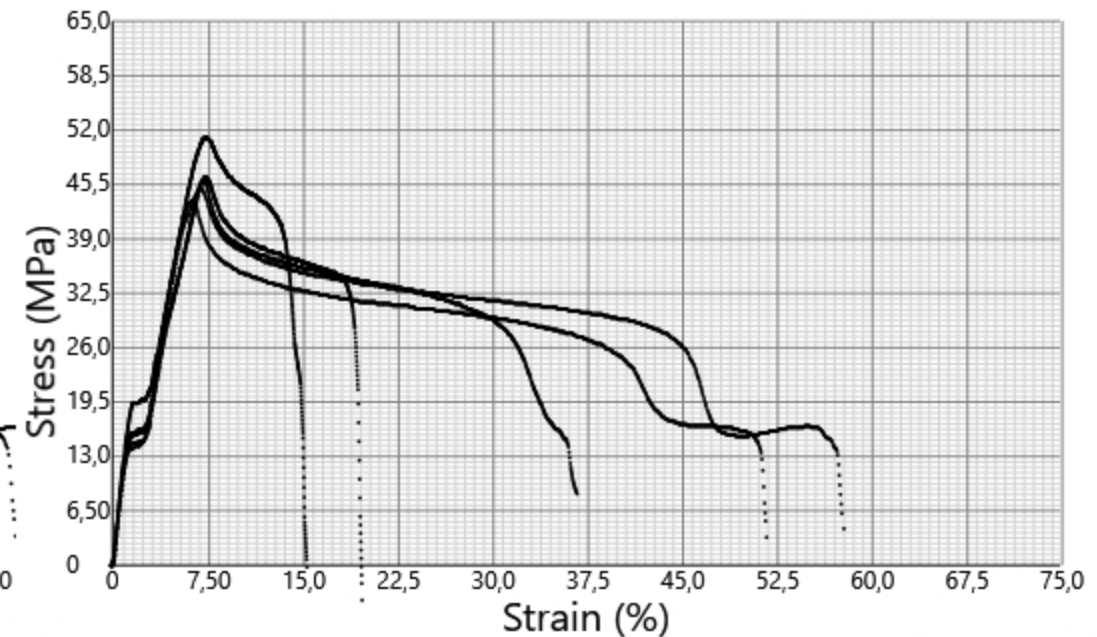
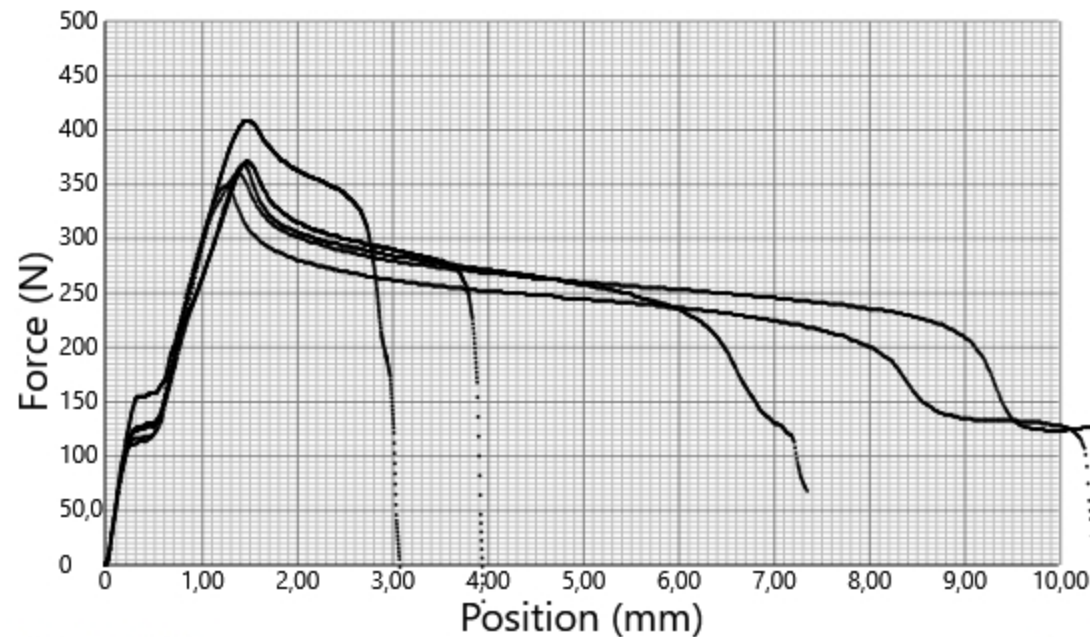


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 40C VÅT - PLA (A-2-6)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1190	118	14,7	400	50,0	11,9
2	PLA	50,0	4,00	2,00	1270	152	19,0	428	53,5	30,7
3	PLA	50,0	4,00	2,00	1270	165	20,7	432	54,0	18,2
4	PLA	50,0	4,00	2,00	1290	174	21,8	428	53,5	14,3
5	PLA	50,0	4,00	2,00	1400	162	20,3	415	51,8	45,4
Average					1280	154	19,3	421	52,6	24,1
SD					74,8	21,9	2,74	13,2	1,65	14,0

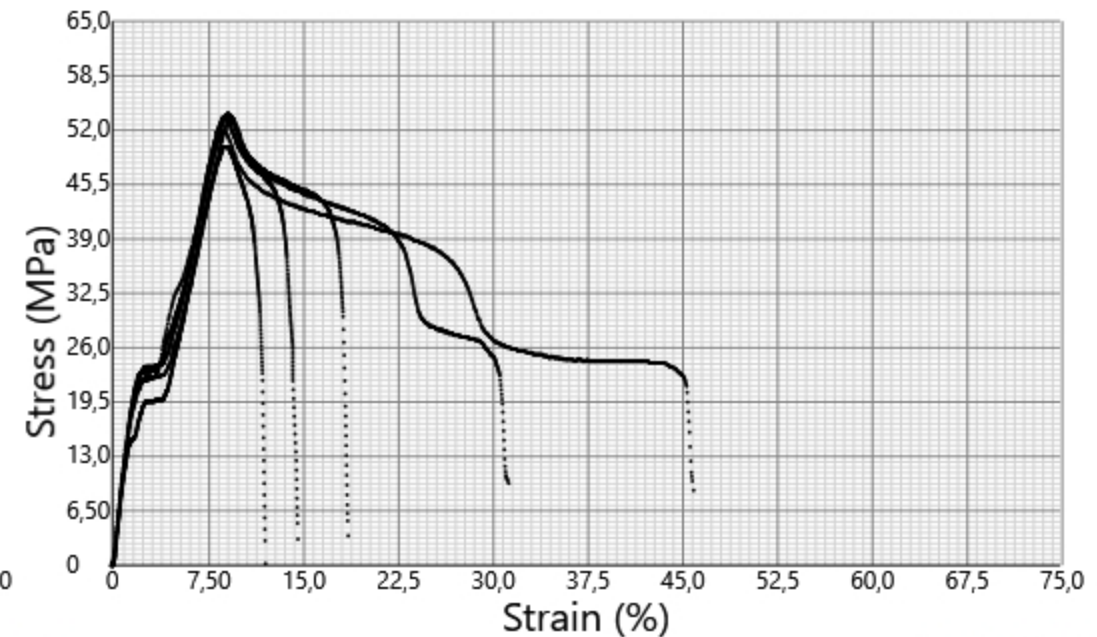
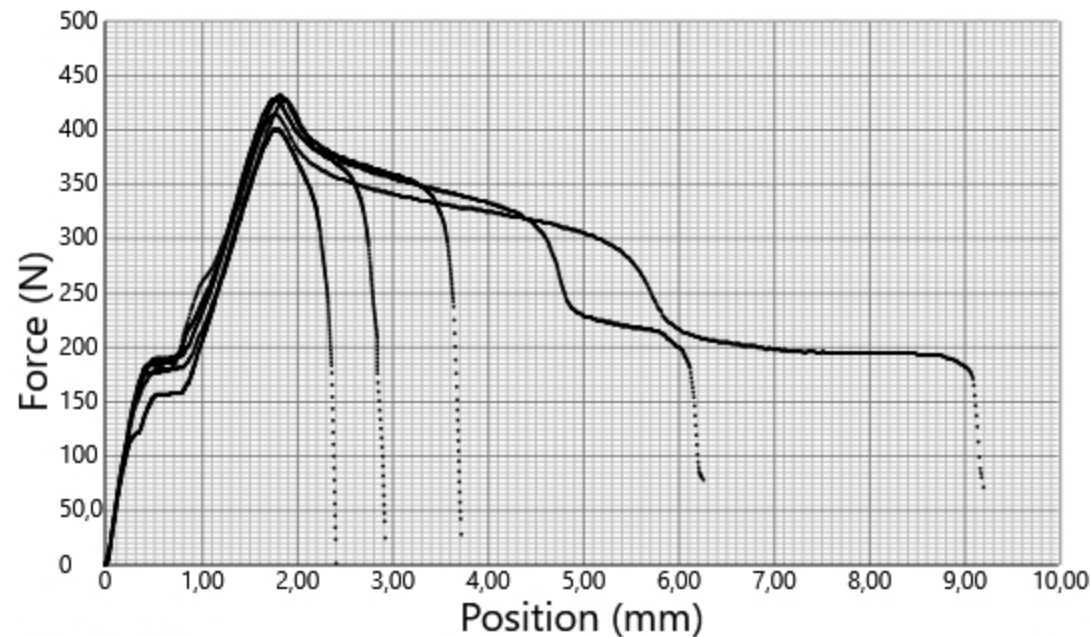


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 20C TØRR - PETG (B-1-5)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	878	129	16,2	393	49,2	12,0
2	PETG	50,0	4,00	2,00	829	130	16,3	360	45,0	11,8
3	PETG	50,0	4,00	2,00	884	140	17,5	378	47,3	13,2
4	PETG	50,0	4,00	2,00	856	133	16,6	388	48,5	13,1
5	PETG	50,0	4,00	2,00	865	135	16,8	378	47,3	12,1
Average					863	133	16,7	380	47,5	12,4
SD					21,7	4,22	0,527	12,8	1,60	0,638

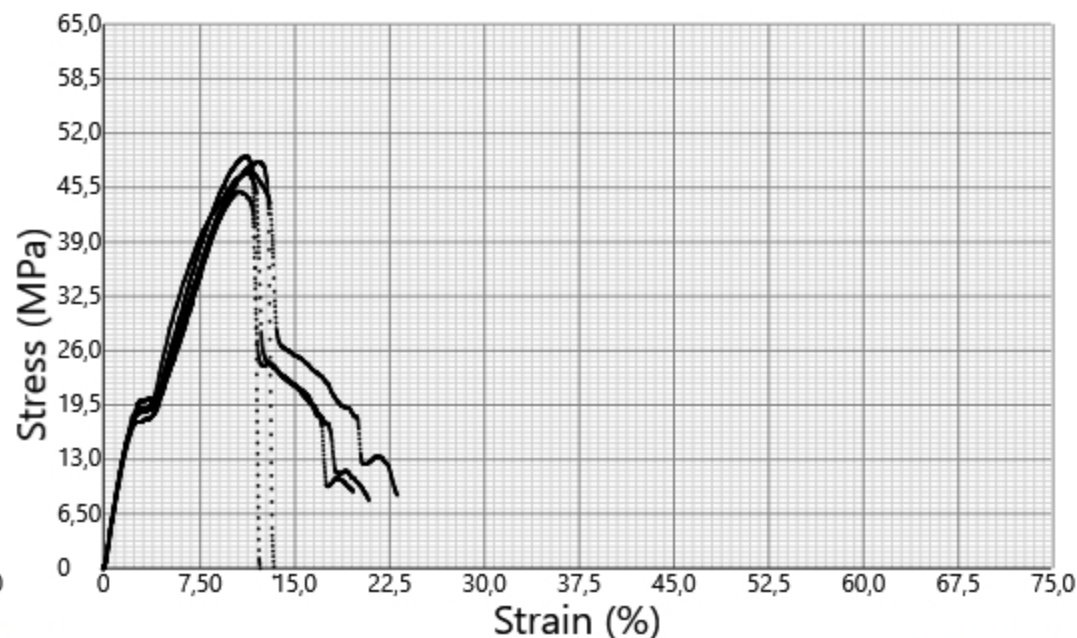
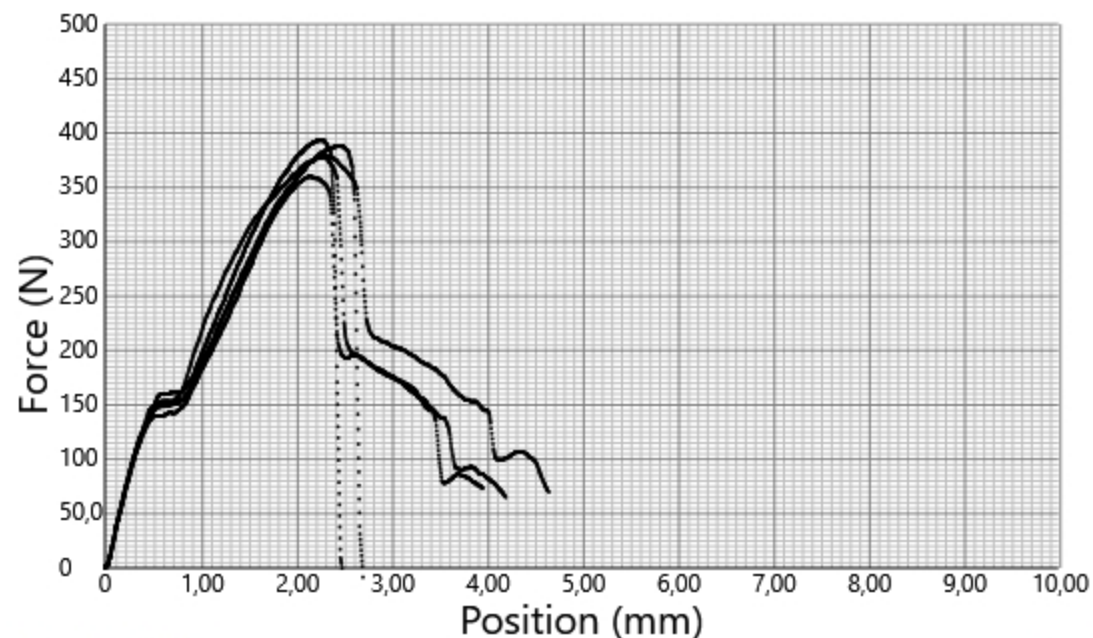


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 20C VÅT - PETG (B-1-6)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	831	129	16,1	390	48,7	13,3
2	PETG	50,0	4,00	2,00	852	134	16,7	367	45,8	12,0
3	PETG	50,0	4,00	2,00	836	127	15,9	372	46,5	12,4
4	PETG	50,0	4,00	2,00	786	134	16,7	412	51,5	14,0
5	PETG	50,0	4,00	2,00	831	138	17,3	362	45,2	11,9
Average					827	132	16,6	380	47,5	12,7
SD					24,7	4,35	0,543	20,5	2,57	0,893

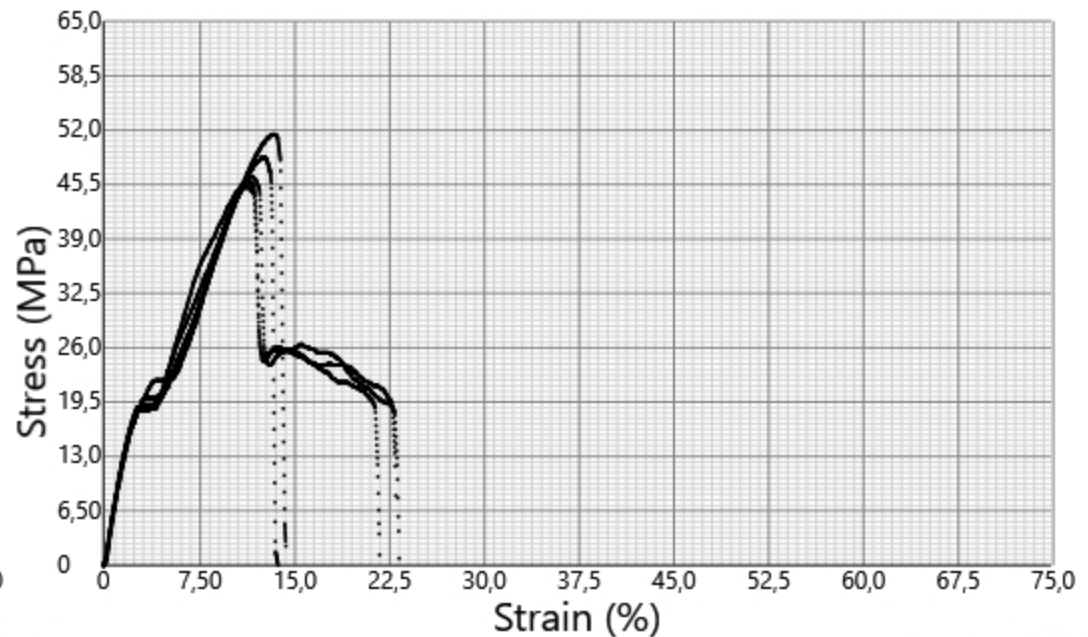
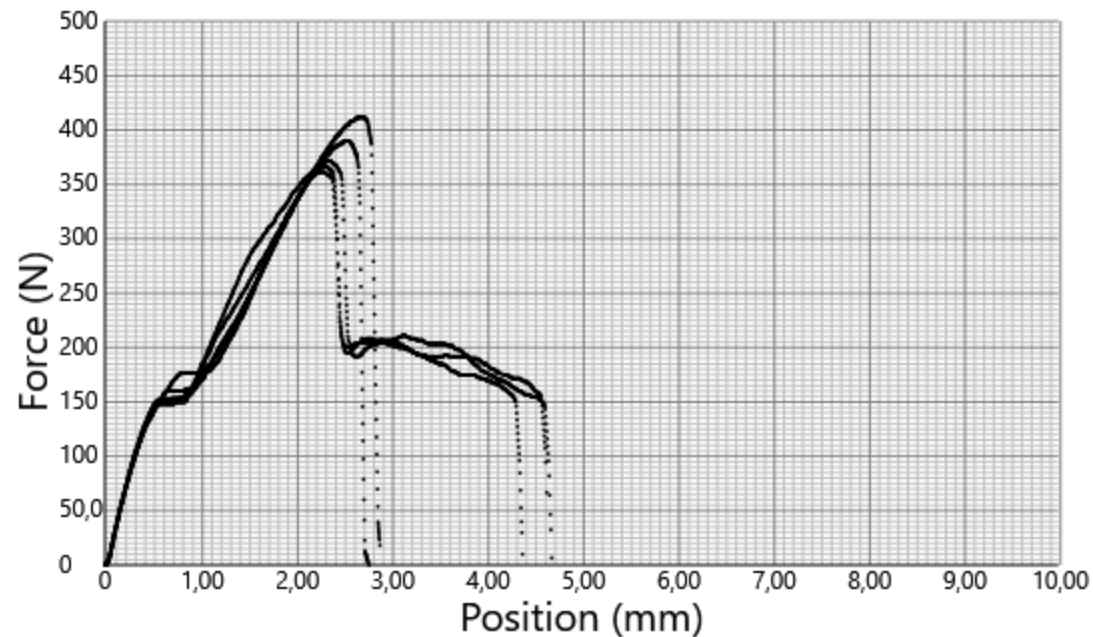


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 40C TØRR - PETG (B-2-5)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	858	126	15,7	412	51,5	11,7
2	PETG	50,0	4,00	2,00	866	140	17,5	415	51,9	11,9
3	PETG	50,0	4,00	2,00	841	143	17,9	440	55,0	12,8
4	PETG	50,0	4,00	2,00	829	129	16,2	425	53,1	13,1
5	PETG	50,0	4,00	2,00	1170	97,2	12,1	433	54,2	12,0
Average					913	127	15,9	425	53,1	12,3
SD					146	18,2	2,27	12,0	1,50	0,597

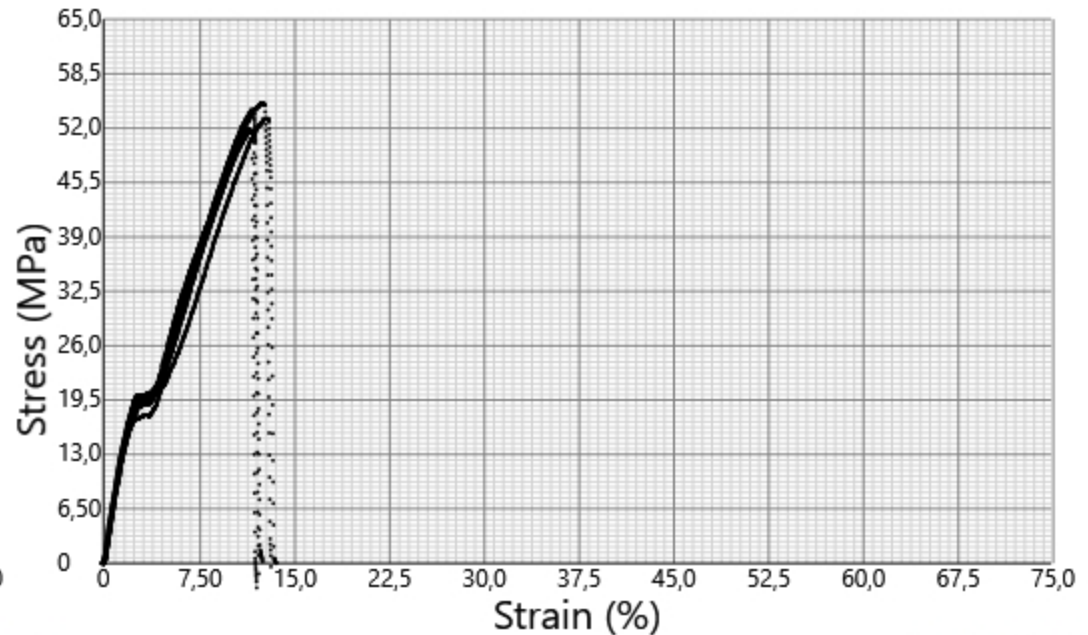
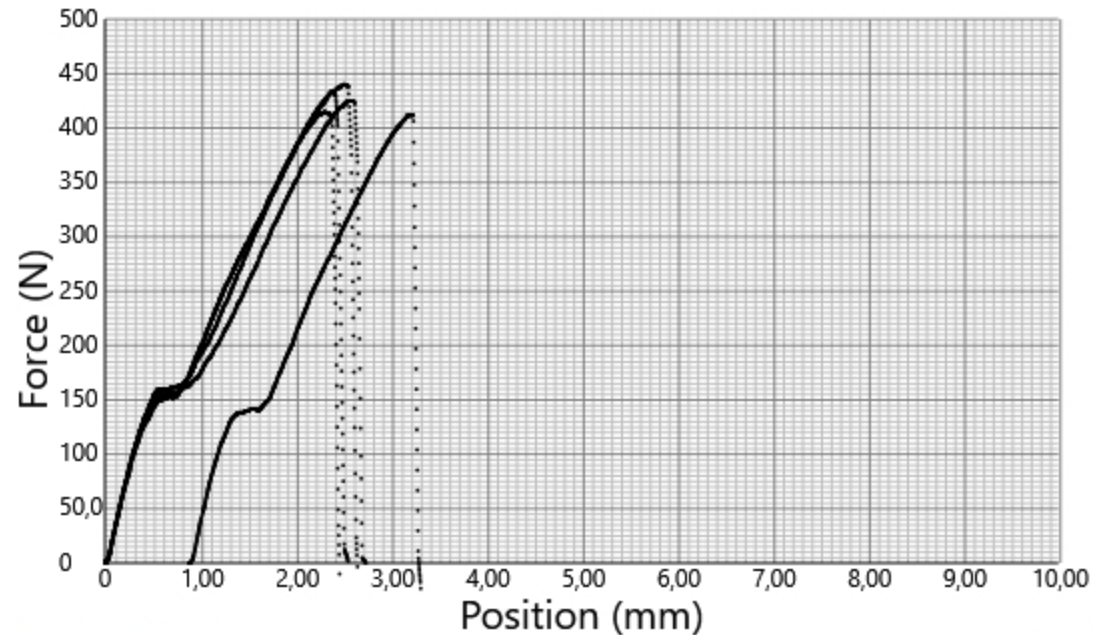


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 40C VÅT - PETG (B-2-6)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	830	133	16,6	423	52,9	13,1
2	PETG	50,0	4,00	2,00	839	153	19,1	437	54,6	13,1
3	PETG	50,0	4,00	2,00	804	156	19,5	443	55,4	13,4
4	PETG	50,0	4,00	2,00	789	155	19,4	442	55,2	13,8
5	PETG	50,0	4,00	2,00	760	128	16,0	425	53,1	13,3
Average					804	145	18,1	434	54,2	13,3
SD					32,1	13,5	1,69	9,32	1,17	0,290

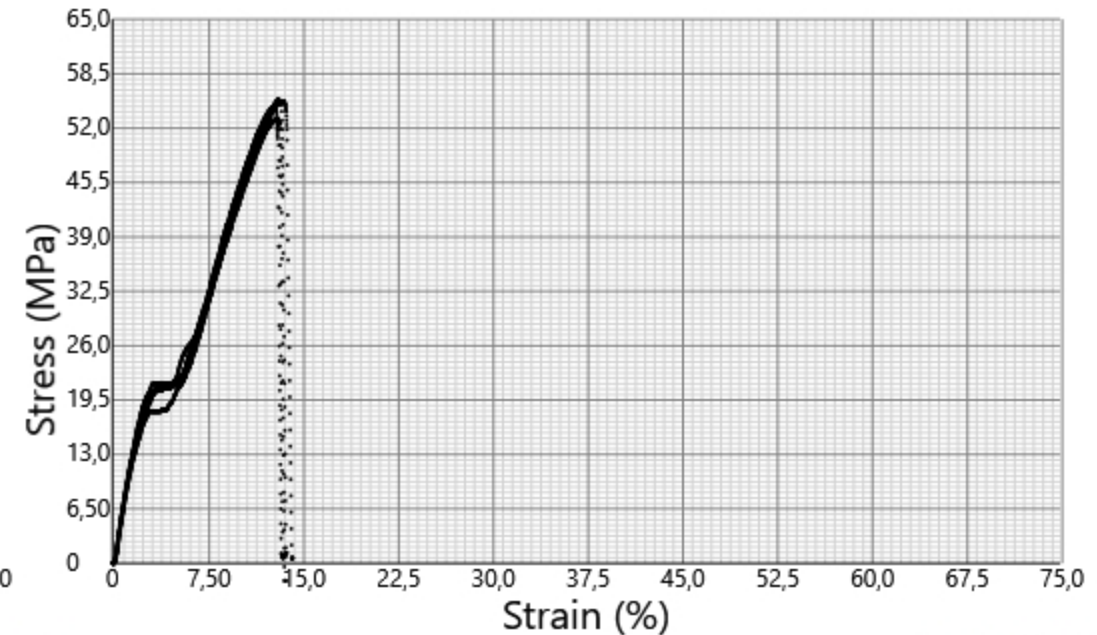
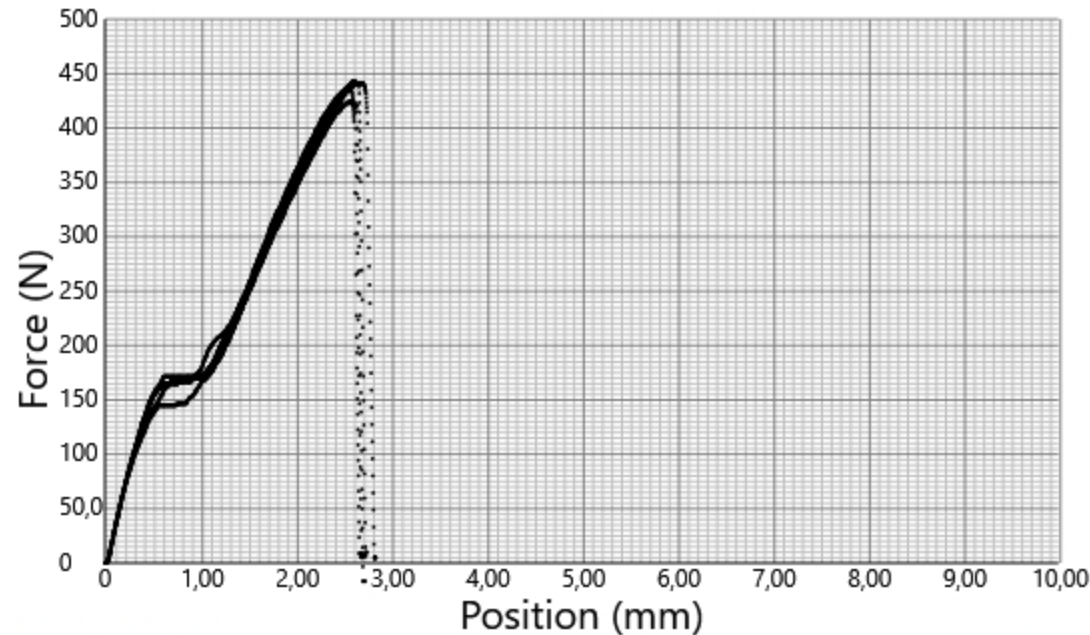


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 60C TØRR - PETG (B-3-5)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	820	135	16,8	360	45,0	11,9
2	PETG	50,0	4,00	2,00	797	126	15,8	393	49,2	33,6
3	PETG	50,0	4,00	2,00	848	141	17,6	370	46,2	11,8
4	PETG	50,0	4,00	2,00	833	134	16,8	377	47,1	11,9
5	PETG	50,0	4,00	2,00	853	130	16,2	377	47,1	12,2
Average					830	133	16,6	375	46,9	16,3
SD					22,8	5,53	0,692	12,2	1,52	9,66

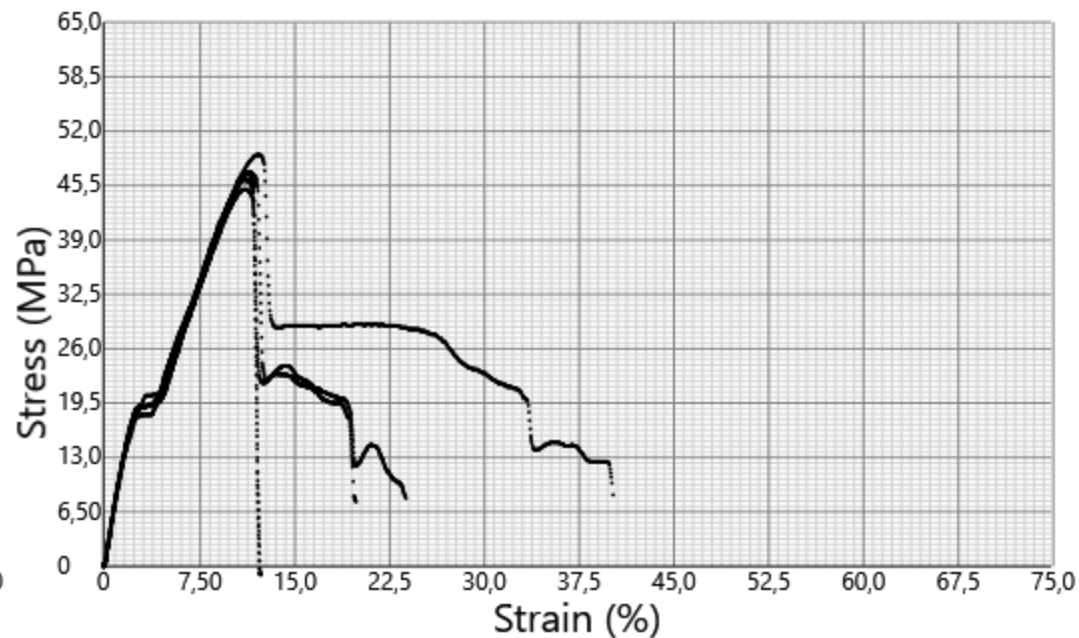
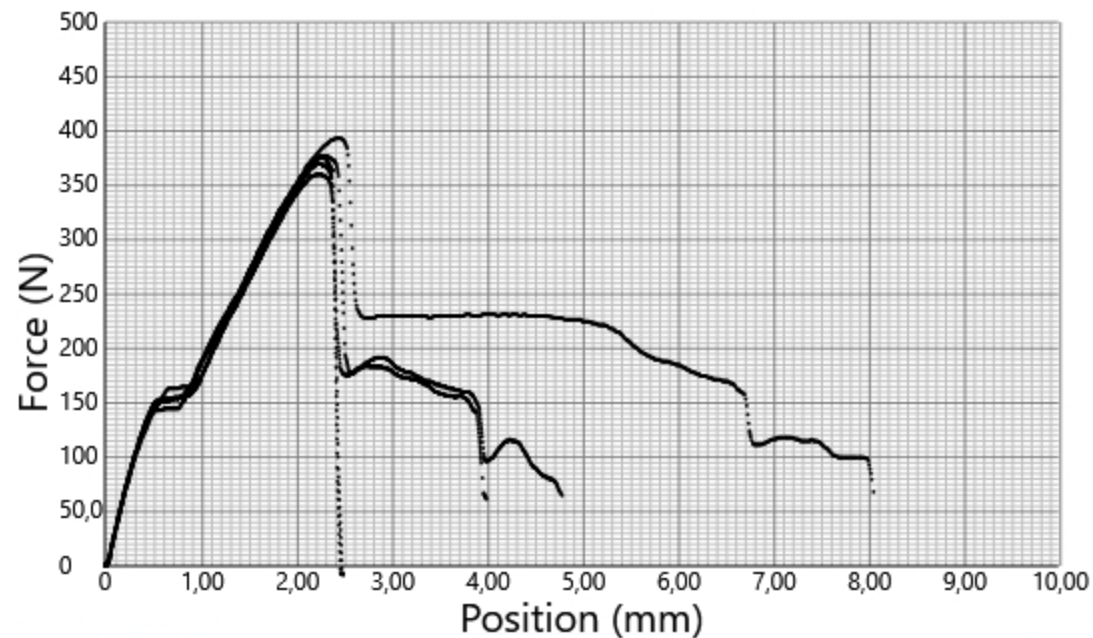


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 60C VÅT - PETG (B-3-6)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	871	145	18,1	390	48,7	38,7
2	PETG	50,0	4,00	2,00	796	129	16,1	373	46,7	12,7
3	PETG	50,0	4,00	2,00	772	117	14,6	398	49,8	13,7
4	PETG	50,0	4,00	2,00	859	137	17,1	402	50,2	15,0
5	PETG	50,0	4,00	2,00	377	170	21,2	400	50,0	16,3
Average					735	139	17,4	393	49,1	19,3
SD					205	20,0	2,50	11,7	1,46	11,0

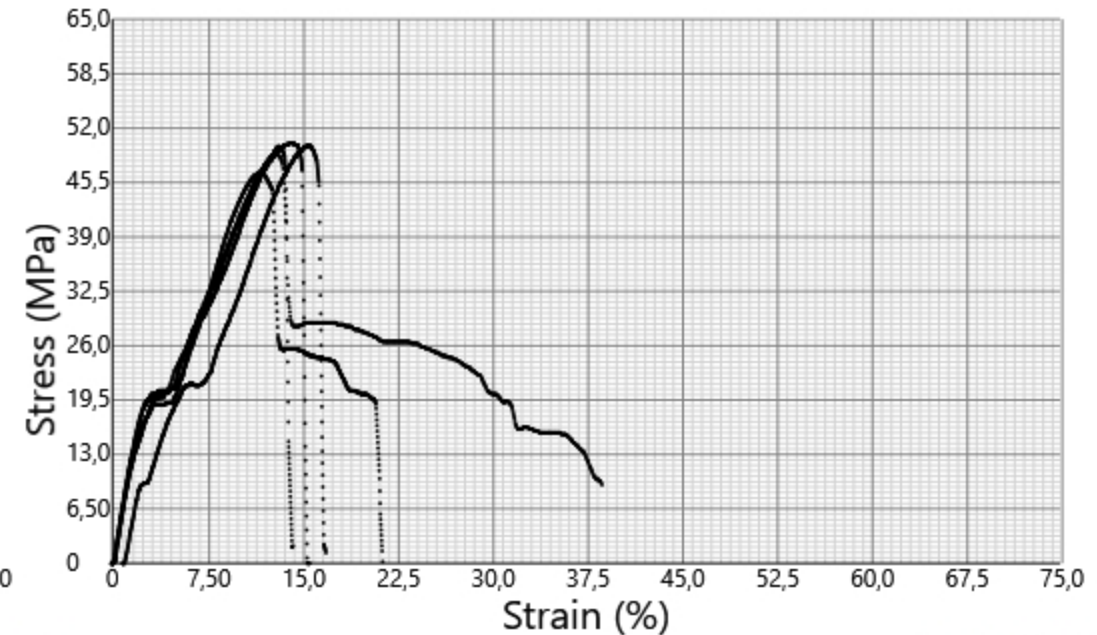
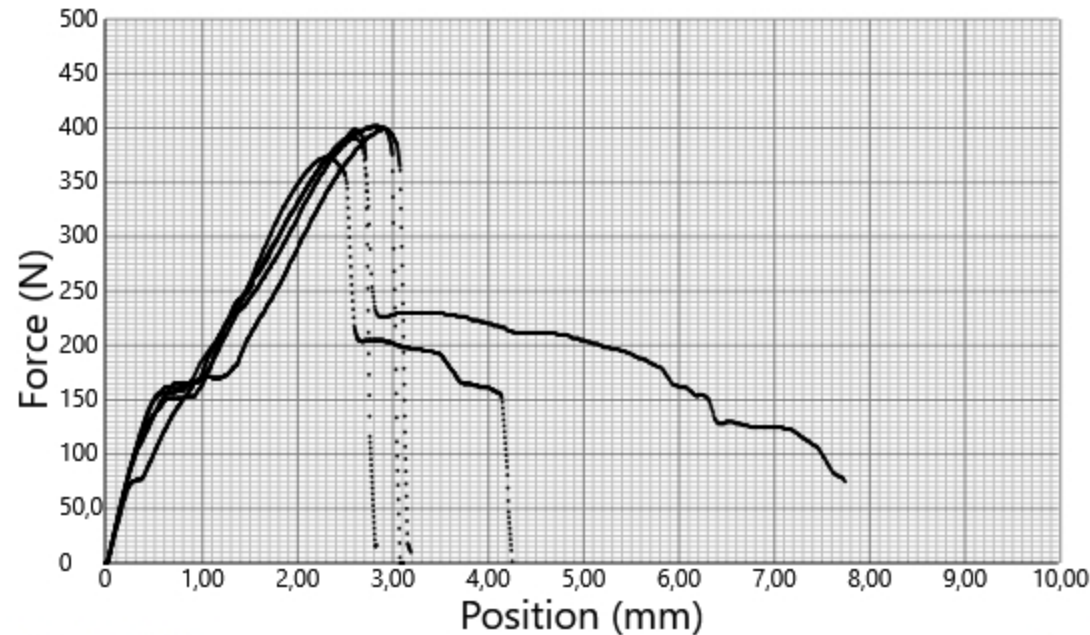


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 20C TØRR - ASA (C-1-5)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	1000	95,2	11,9	273	34,2	8,16
2	ASA	50,0	4,00	2,00	1040	89,6	11,2	268	33,5	8,93
3	ASA	50,0	4,00	2,00	880	104	13,0	278	34,8	9,02
4	ASA	50,0	4,00	2,00	1230	73,7	9,21	273	34,2	9,00
5	ASA	50,0	4,00	2,00	955	78,0	9,75	282	35,2	9,77
Average					1020	88,1	11,0	275	34,4	8,98
SD					133	12,3	1,54	5,14	0,642	0,570

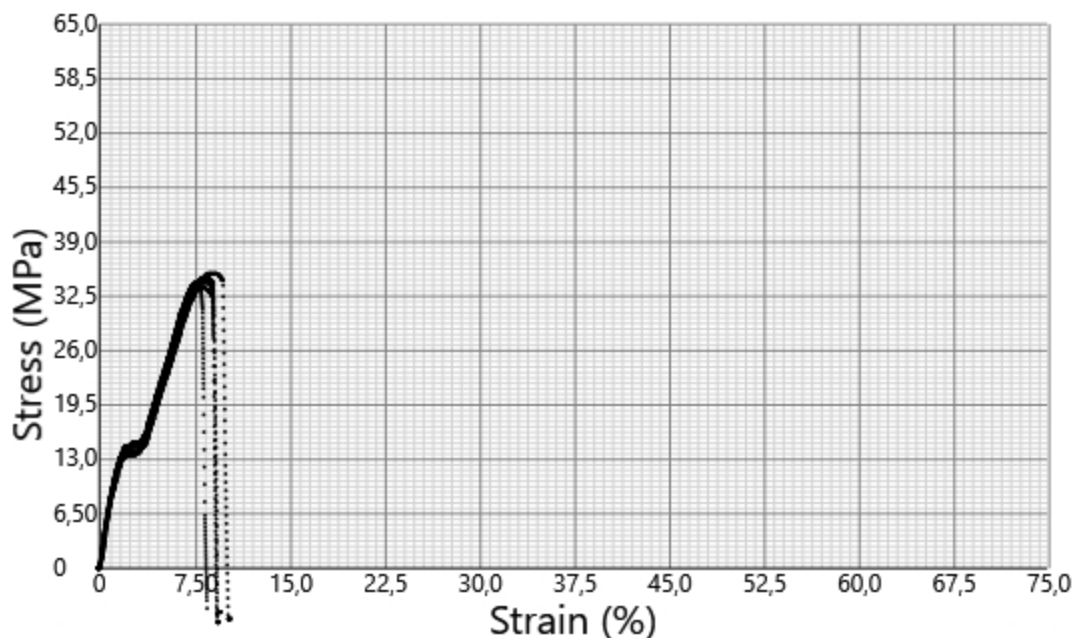
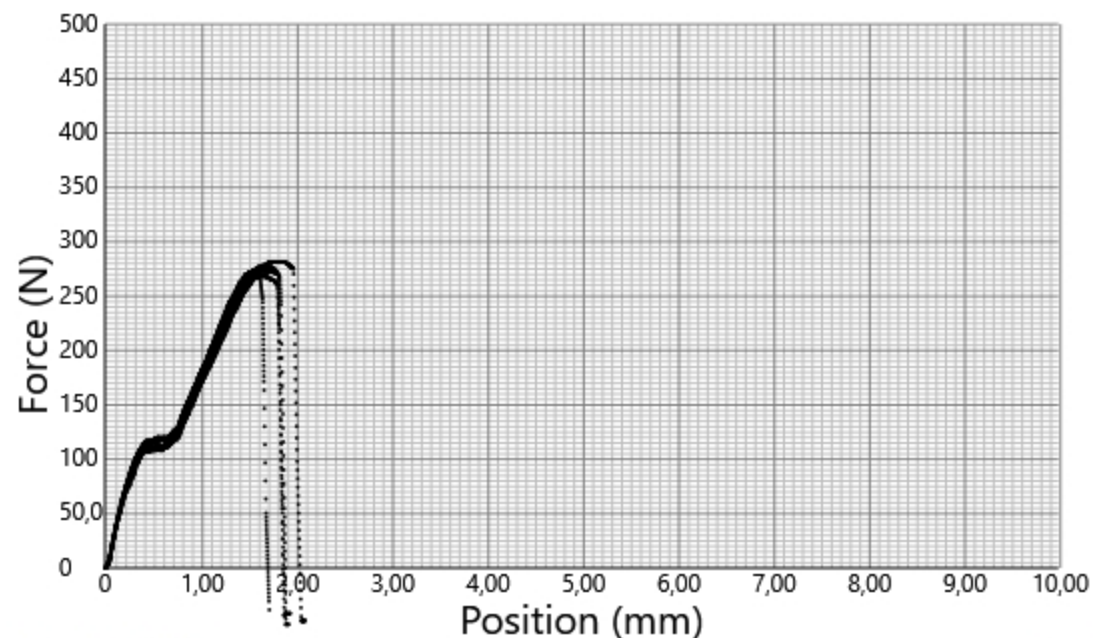


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 20C VÅT - ASA (C-1-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	995	117	14,7	232	29,0	6,79
2	ASA	50,0	4,00	2,00	913	106	13,3	235	29,4	7,28
3	ASA	50,0	4,00	2,00	916	107	13,4	245	30,6	7,91
4	ASA	50,0	4,00	2,00	855	120	15,0	320	40,0	12,6
5	ASA	50,0	4,00	2,00	977	116	14,5	312	39,0	10,8
Average					931	113	14,2	269	33,6	9,08
SD					55,9	6,29	0,786	43,4	5,43	2,52

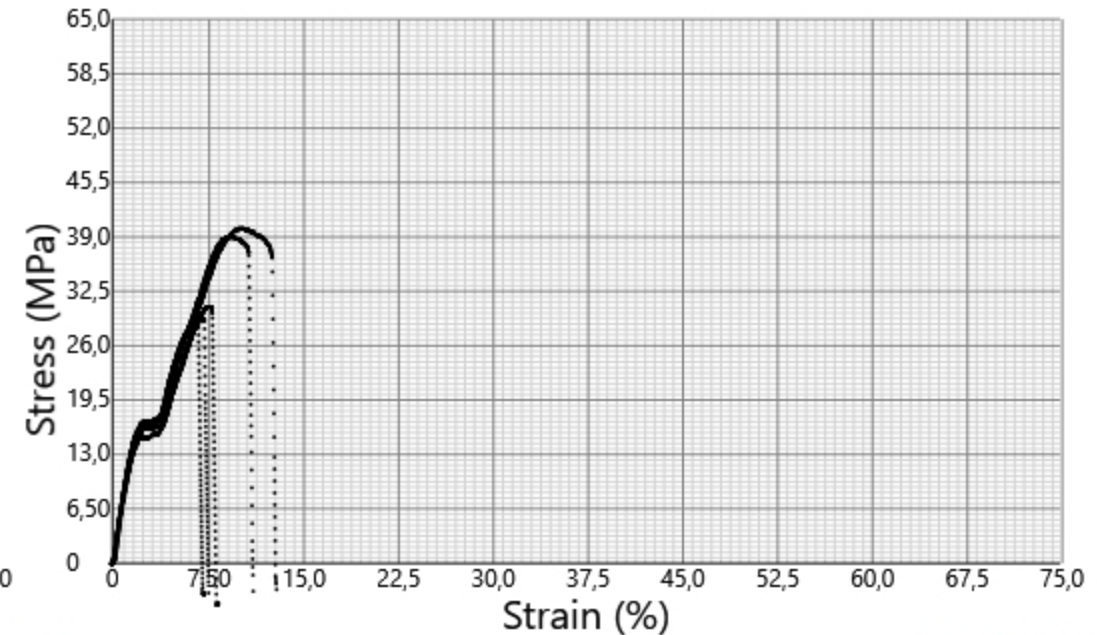
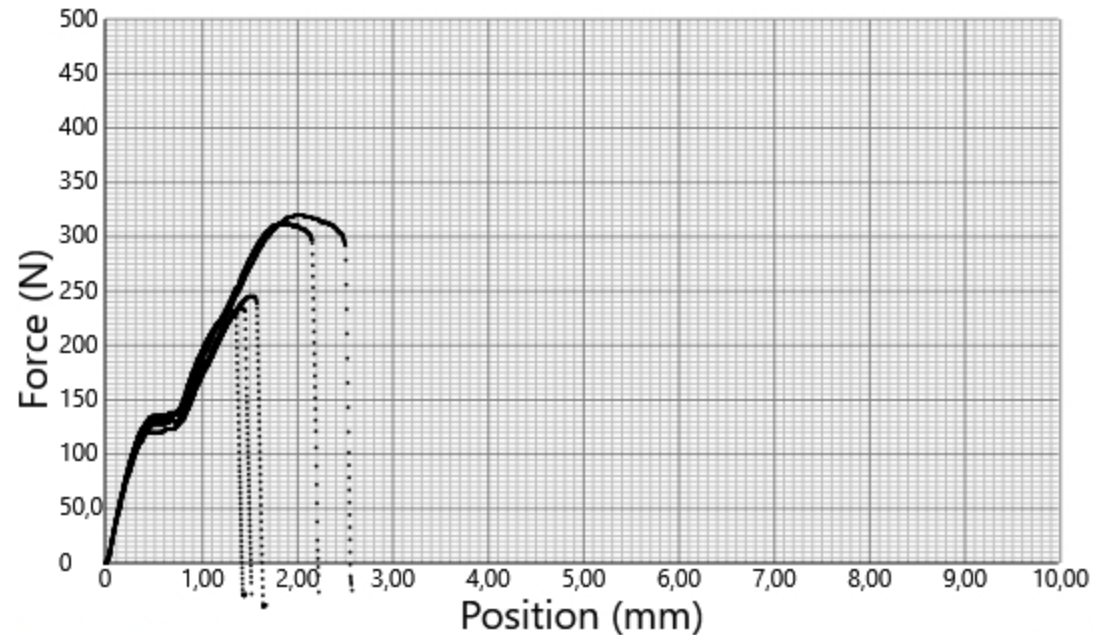


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 40C TØRR - ASA (C-2-5)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	971	85,4	10,7	218	27,3	7,44
2	ASA	50,0	4,00	2,00	737	77,7	9,72	275	34,4	9,85
3	ASA	50,0	4,00	2,00	989	121	15,2	310	38,7	11,4
4	ASA	50,0	4,00	2,00	935	101	12,7	267	33,3	8,46
5	ASA	50,0	4,00	2,00	1020	111	13,9	230	28,7	6,46
Average					929	99,4	12,4	260	32,5	8,71
SD					112	17,9	2,24	36,8	4,60	1,94

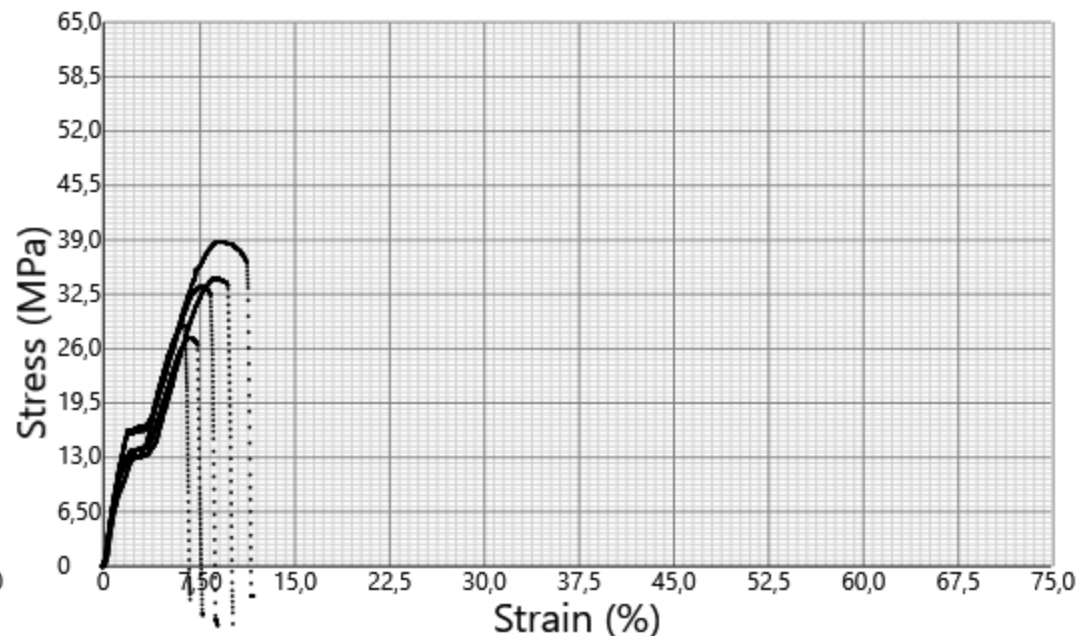
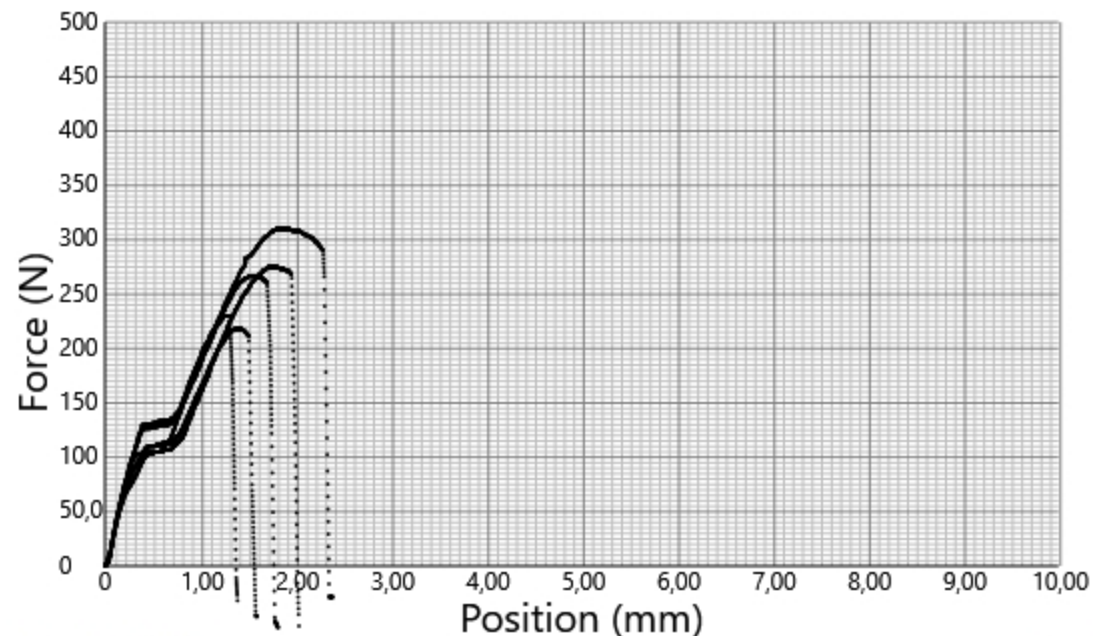


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 40C VÅT - ASA (C-2-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	967	120	15,0	255	31,9	7,76
2	ASA	50,0	4,00	2,00	922	114	14,3	310	38,7	11,6
3	ASA	50,0	4,00	2,00	988	115	14,4	297	37,1	9,26
4	ASA	50,0	4,00	2,00	922	112	14,0	292	36,5	10,3
5	ASA	50,0	4,00	2,00	815	107	13,3	308	38,5	11,1
Average					923	114	14,2	292	36,5	10,0
SD					66,7	4,91	0,614	22,3	2,78	1,53

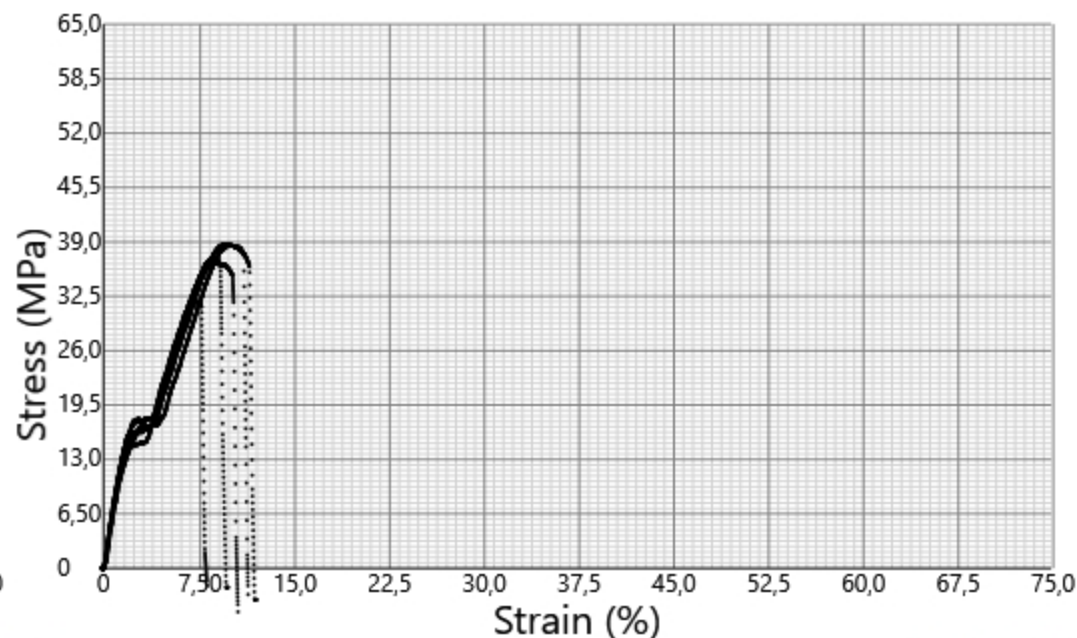
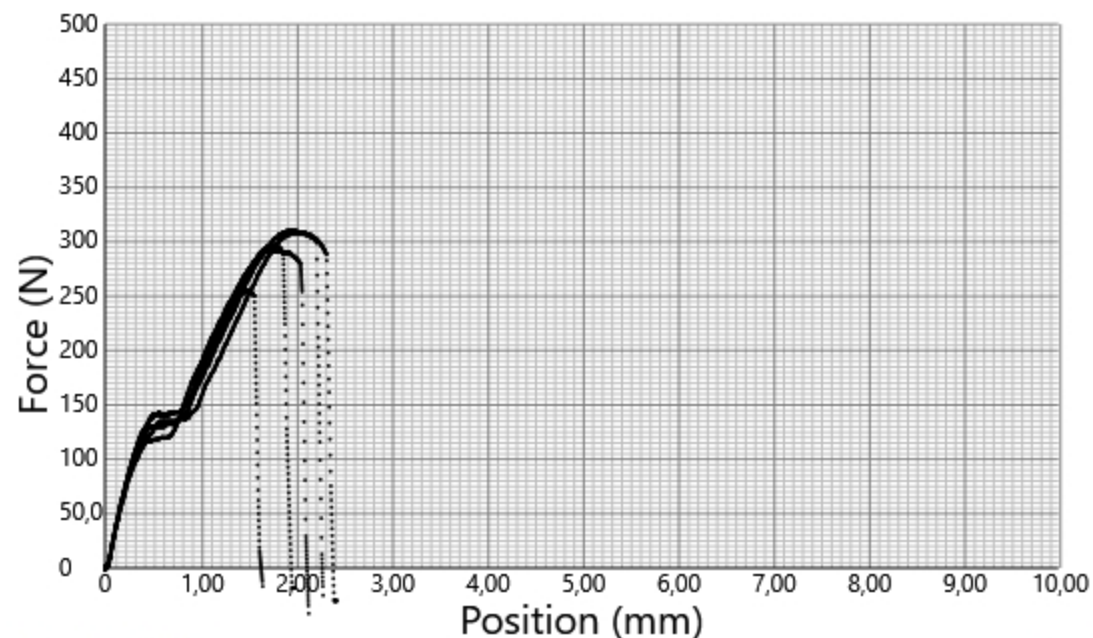


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 60C TØRR - ASA (C-3-5)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	887	106	13,3	272	34,0	9,14
2	ASA	50,0	4,00	2,00	846	104	13,0	298	37,3	11,5
3	ASA	50,0	4,00	2,00	891	100	12,5	232	29,0	8,02
4	ASA	50,0	4,00	2,00	898	103	12,9	297	37,1	11,1
5	ASA	50,0	4,00	2,00	903	125	15,6	307	38,3	12,3
Average					885	108	13,5	281	35,1	10,4
SD					22,5	9,66	1,21	30,5	3,81	1,76

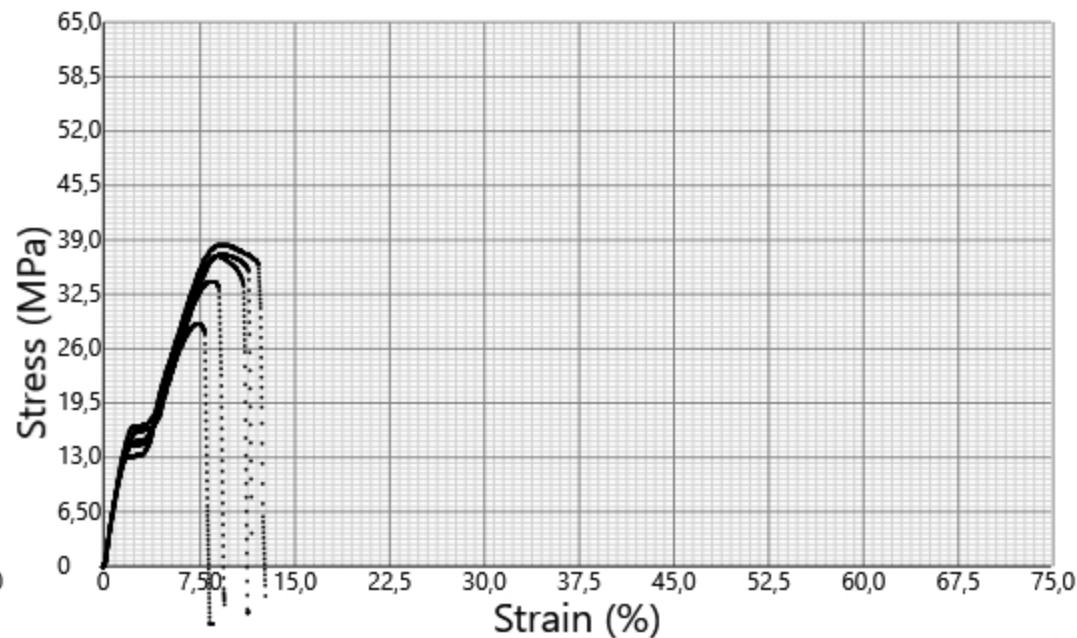
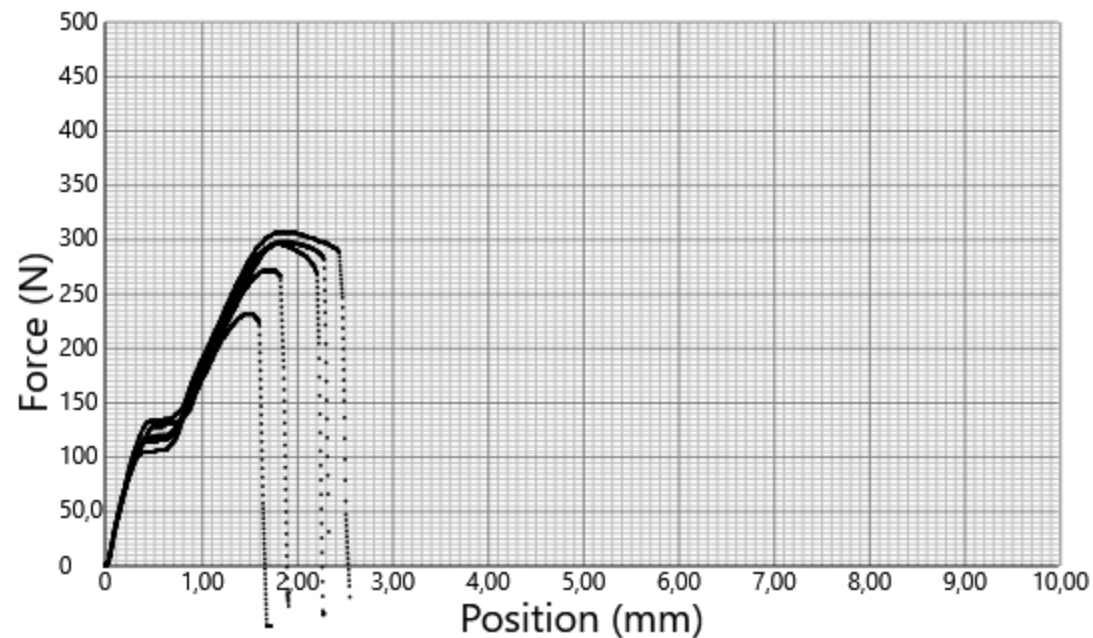


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE9 60C VÅT - ASA (C-3-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	939	125	15,7	313	39,2	9,65
2	ASA	50,0	4,00	2,00	909	110	13,8	317	39,6	10,4
3	ASA	50,0	4,00	2,00	972	114	14,3	300	37,5	9,35
4	ASA	50,0	4,00	2,00	1040	116	14,5	320	40,0	10,6
5	ASA	50,0	4,00	2,00	936	107	13,4	317	39,6	10,7
Average					959	114	14,3	313	39,2	10,2
SD					49,3	7,06	0,883	7,82	0,977	0,615

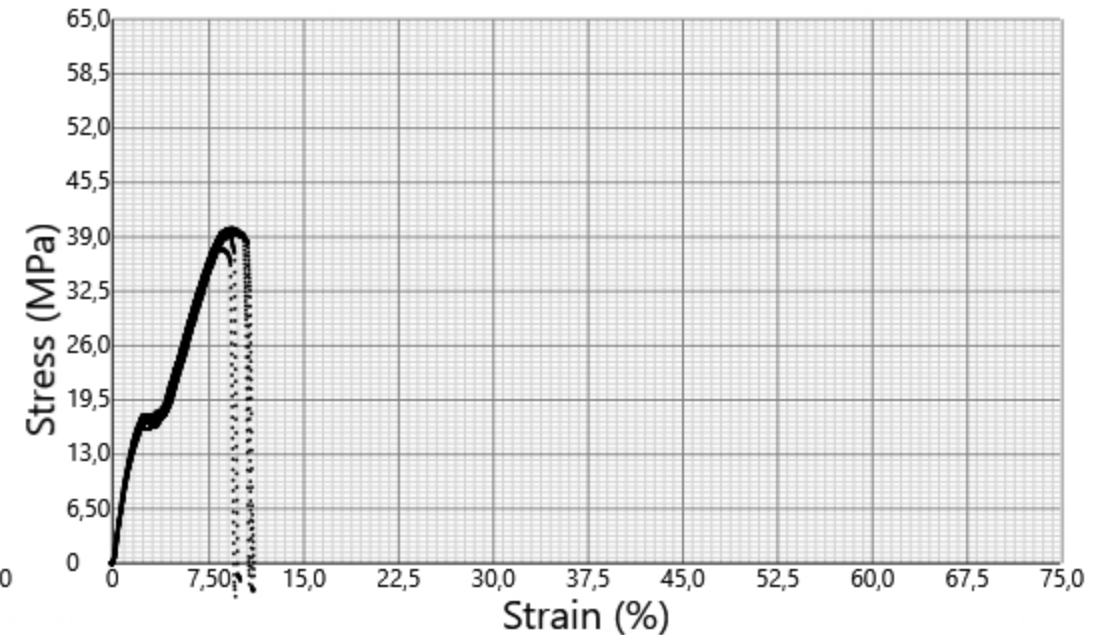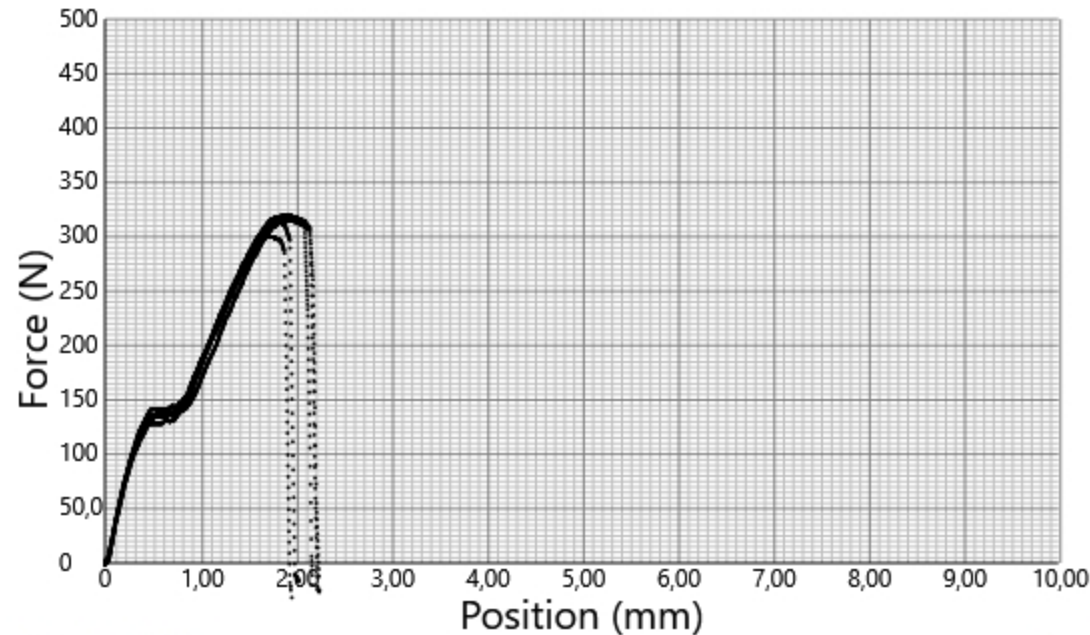



Uke 12

USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 20C - PLA (A-1-7)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1190	224	28,0	263	32,9	20,2
2	PLA	50,0	4,00	2,00	1400	109	13,6	367	45,8	18,7
3	PLA	50,0	4,00	2,00	707	343	42,9	345	43,1	12,5
4	PLA	50,0	4,00	2,00	1280	88,3	11,0	343	42,9	13,0
5	PLA	50,0	4,00	2,00	744	338	42,3	340	42,5	25,6
Average					1080	221	27,6	332	41,5	18,0
SD					319	121	15,2	39,6	4,95	5,42

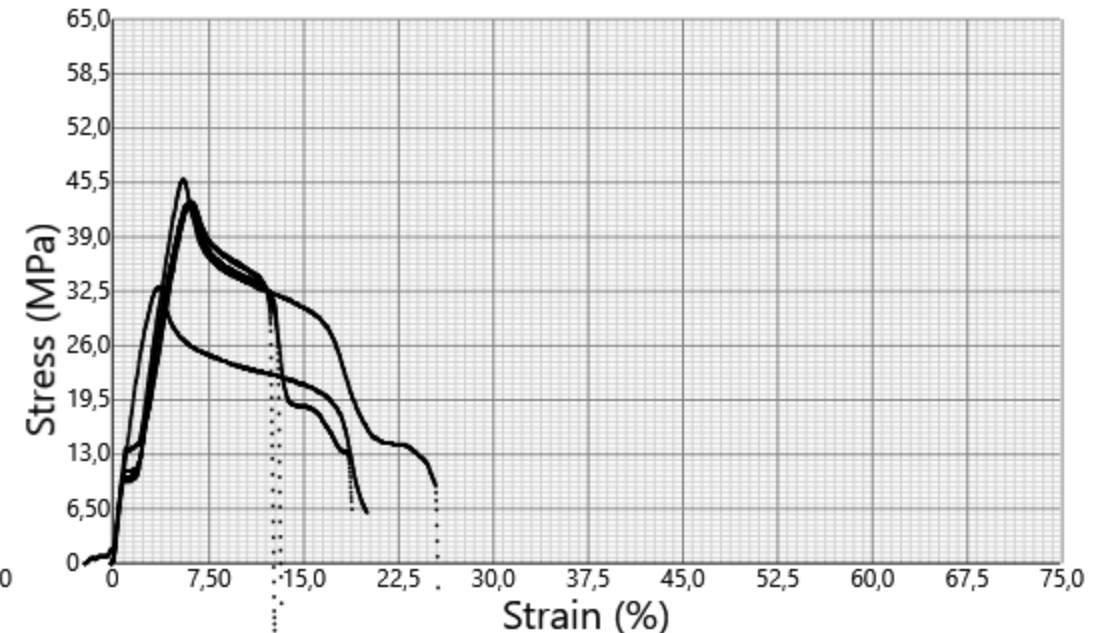
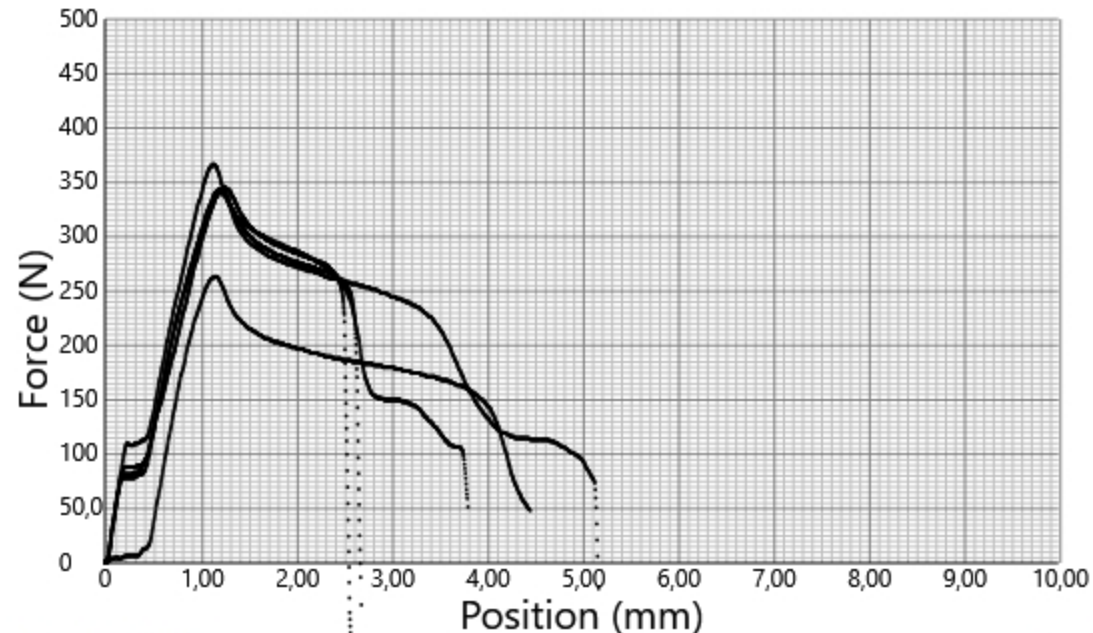


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 20C - PLA (A-1-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1390	217	27,1	245	30,6	29,2
2	PLA	50,0	4,00	2,00	1380	180	22,5	240	30,0	19,4
3	PLA	50,0	4,00	2,00	752	270	33,7	270	33,7	55,6
4	PLA	50,0	4,00	2,00	814	271	33,9	273	34,2	25,3
5	PLA	50,0	4,00	2,00	730	276	34,5	278	34,8	23,1
Average					1010	243	30,3	261	32,7	30,5
SD					342	42,4	5,31	17,5	2,19	14,5

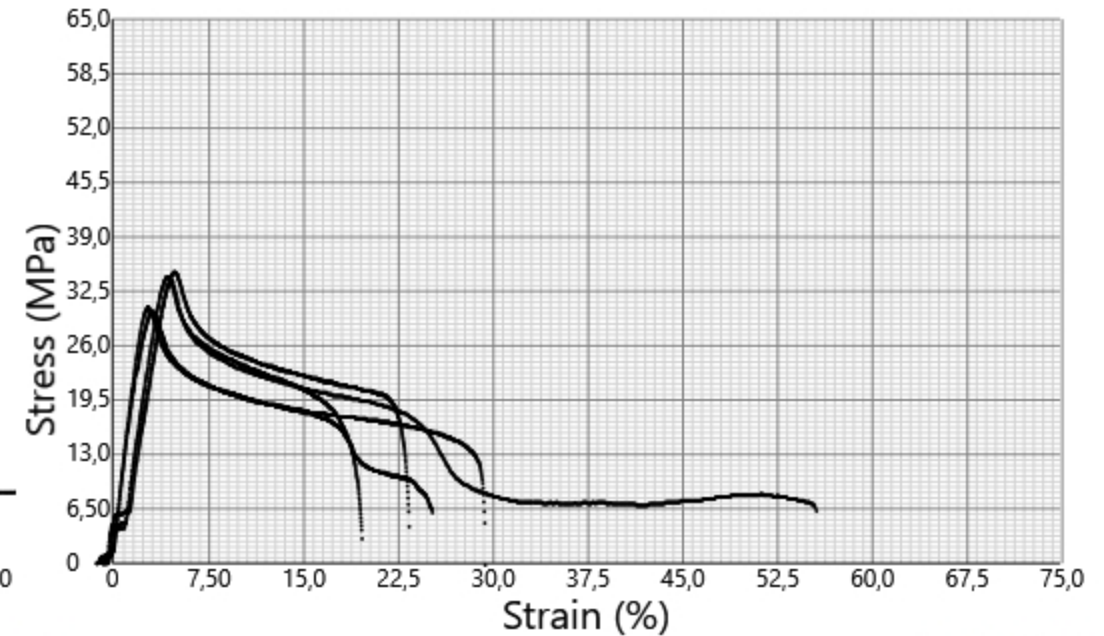
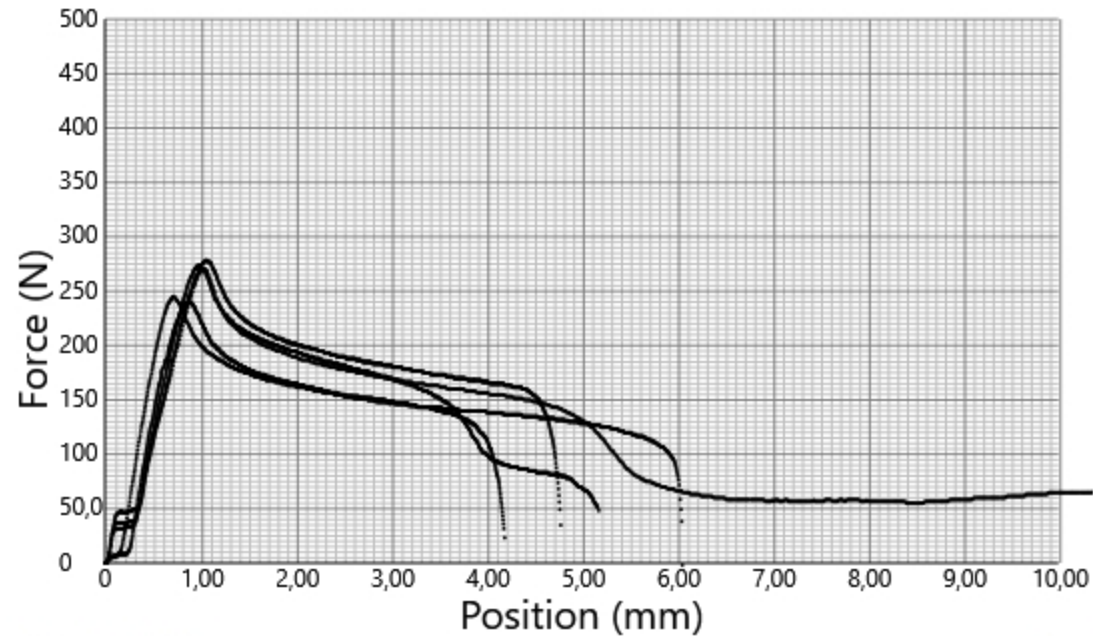


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 40C - PLA (A-2-7)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	426	85,1	10,6	340	42,5	27,0
2	PLA	50,0	4,00	2,00	822	317	39,6	317	39,6	7,82
3	PLA	50,0	4,00	2,00	729	307	38,3	308	38,5	9,66
4	PLA	50,0	4,00	2,00	772	294	36,7	295	36,9	24,4
5	PLA	50,0	4,00	2,00	853	307	38,4	311	38,9	23,5
Average					720	262	32,7	314	39,3	18,5
SD					171	99,1	12,4	16,4	2,06	9,03

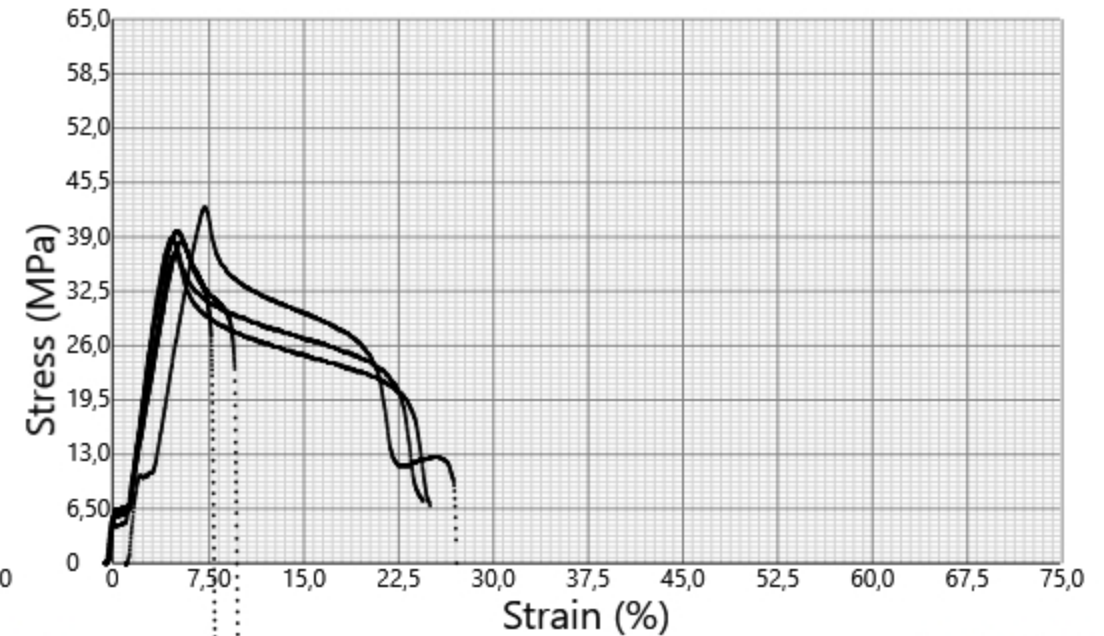
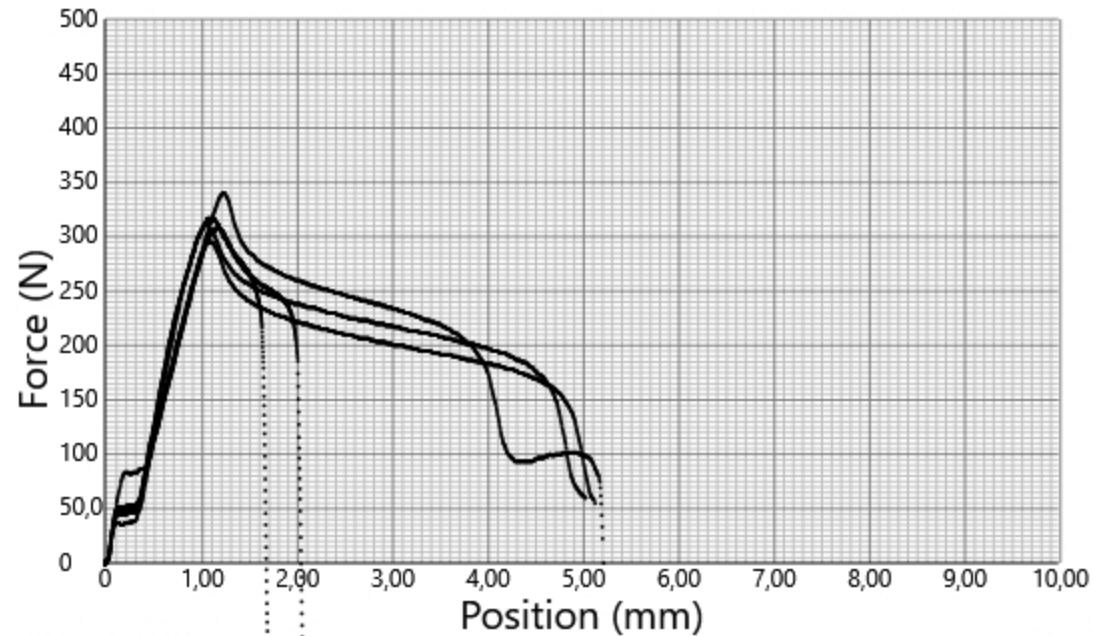


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 40C - PLA (A-2-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PLA	50,0	4,00	2,00	1140	164	20,5	260	32,5	4,89
2	PLA	50,0	4,00	2,00	751	292	36,5	297	37,1	26,4
3	PLA	50,0	4,00	2,00	800	250	31,2	250	31,2	30,2
4	PLA	50,0	4,00	2,00	760	270	33,7	270	33,7	13,3
5	PLA	50,0	4,00	2,00	853	265	33,1	265	33,1	13,5
Average					862	248	31,0	268	33,5	17,7
SD					163	49,3	6,16	17,5	2,19	10,4

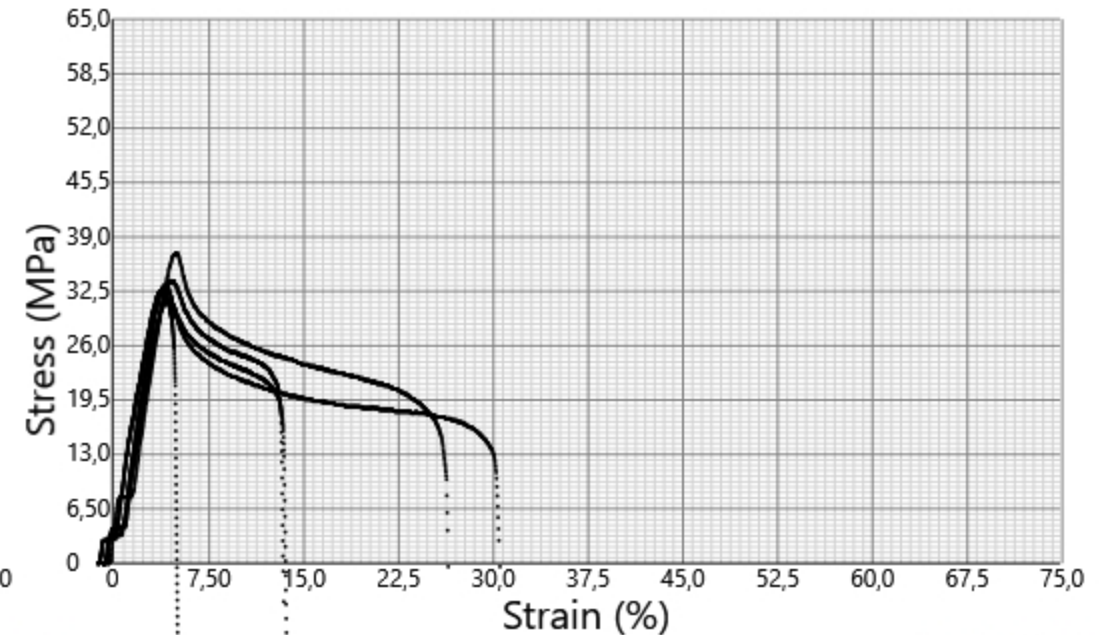
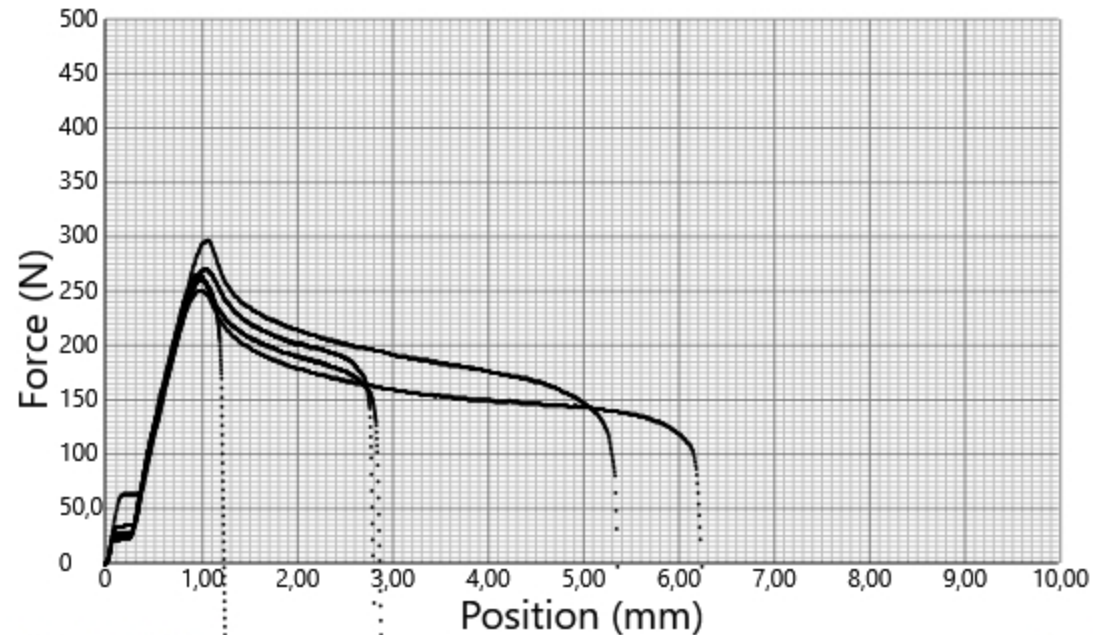


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 20C - PETG (B-1-7)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	489	308	38,5	315	39,4	9,76
2	PETG	50,0	4,00	2,00	570	290	36,2	290	36,2	7,19
3	PETG	50,0	4,00	2,00	503	313	39,2	318	39,8	9,47
4	PETG	50,0	4,00	2,00	493	302	37,8	303	37,9	8,49
5	PETG	50,0	4,00	2,00	500	302	37,7	302	37,7	8,54
Average					511	303	37,9	306	38,2	8,69
SD					33,5	8,75	1,09	11,3	1,42	1,01

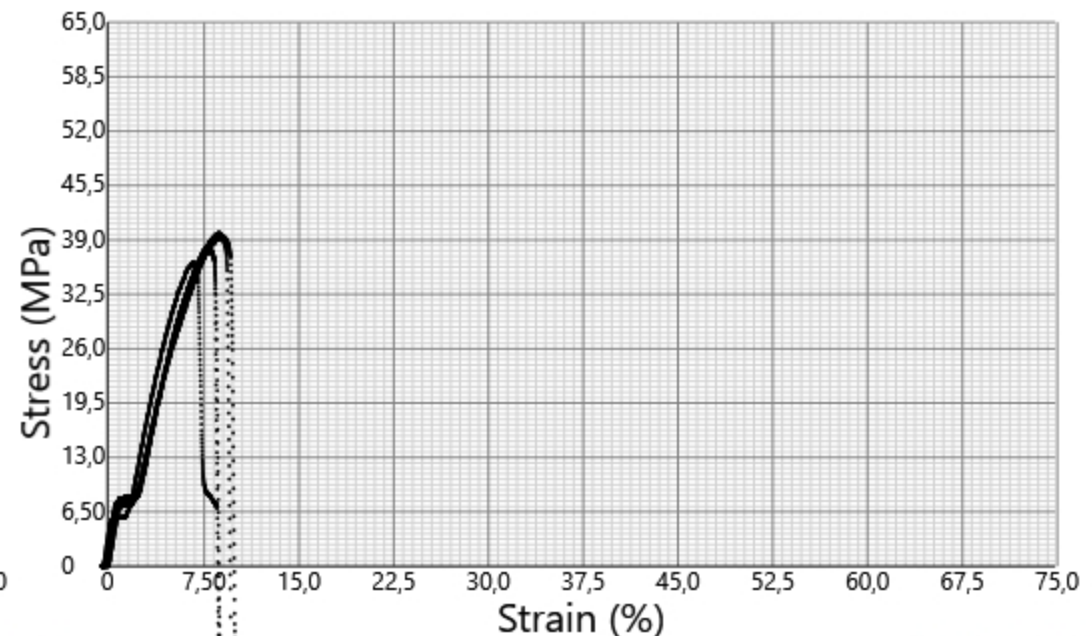
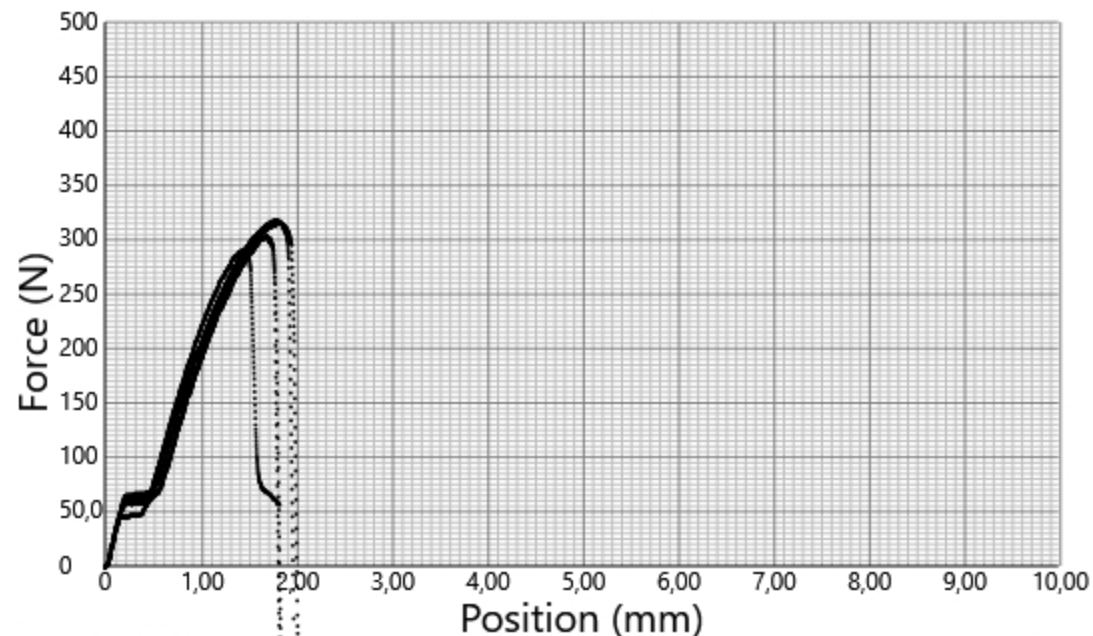


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 20C - PETG (B-1-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	528	296	37,0	298	37,3	7,98
2	PETG	50,0	4,00	2,00	478	295	36,9	303	37,9	9,81
3	PETG	50,0	4,00	2,00	437	295	36,9	298	37,3	9,91
4	PETG	50,0	4,00	2,00	472	293	36,7	302	37,7	73,7
5	PETG	50,0	4,00	2,00	510	290	36,2	292	36,5	7,95
Average					485	294	36,7	299	37,3	21,9
SD					35,5	2,35	0,294	4,47	0,559	29,0

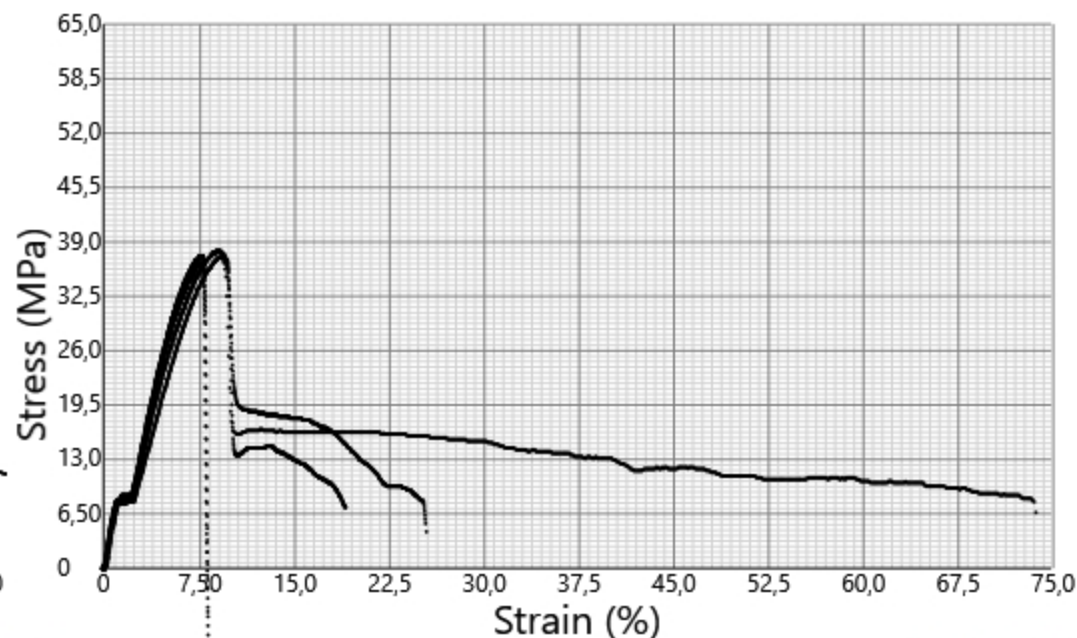
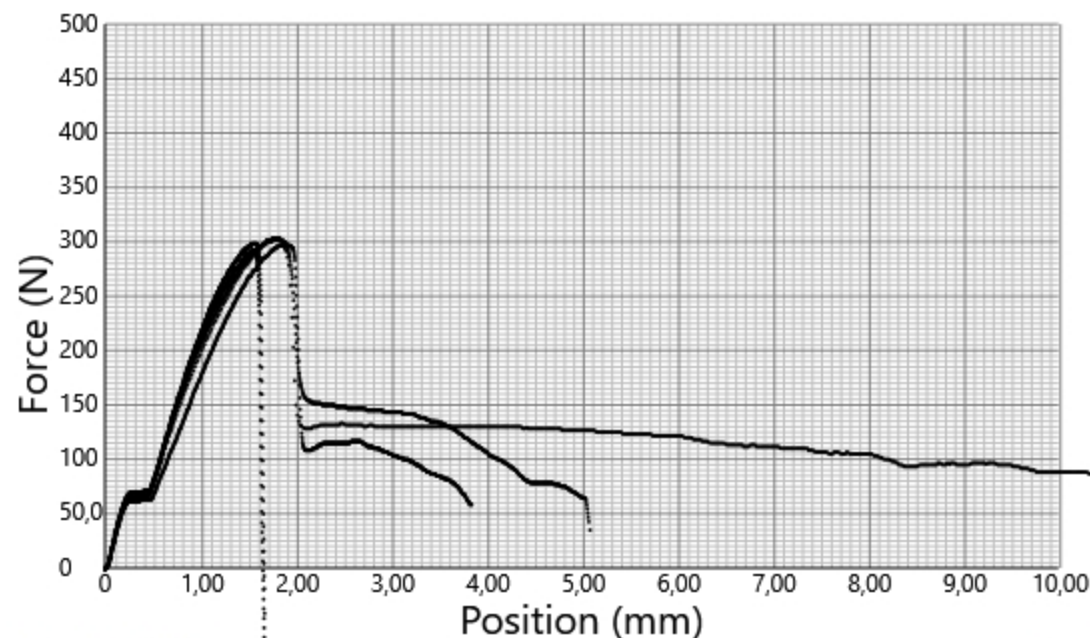


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 40C - PETG (B-2-7)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	521	342	42,7	345	43,1	8,75
2	PETG	50,0	4,00	2,00	697	242	30,2	325	40,6	7,59
3	PETG	50,0	4,00	2,00	515	294	36,8	295	36,9	7,91
4	PETG	50,0	4,00	2,00	560	335	41,9	337	42,1	8,26
5	PETG	50,0	4,00	2,00	503	314	39,3	317	39,6	8,60
Average					559	305	38,2	324	40,5	8,22
SD					79,9	40,1	5,01	19,3	2,42	0,481

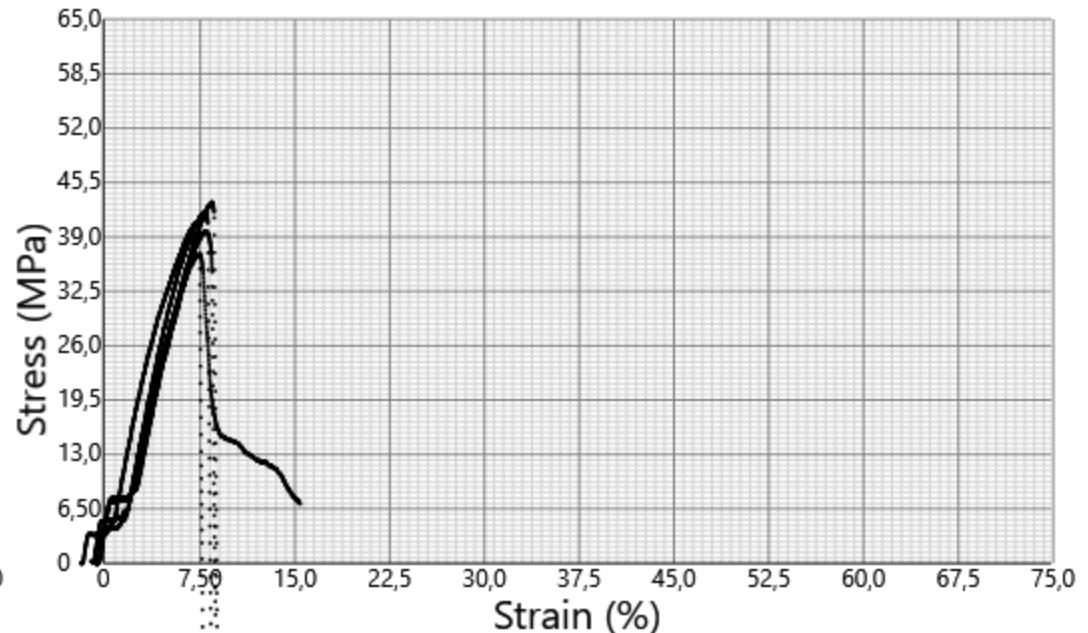
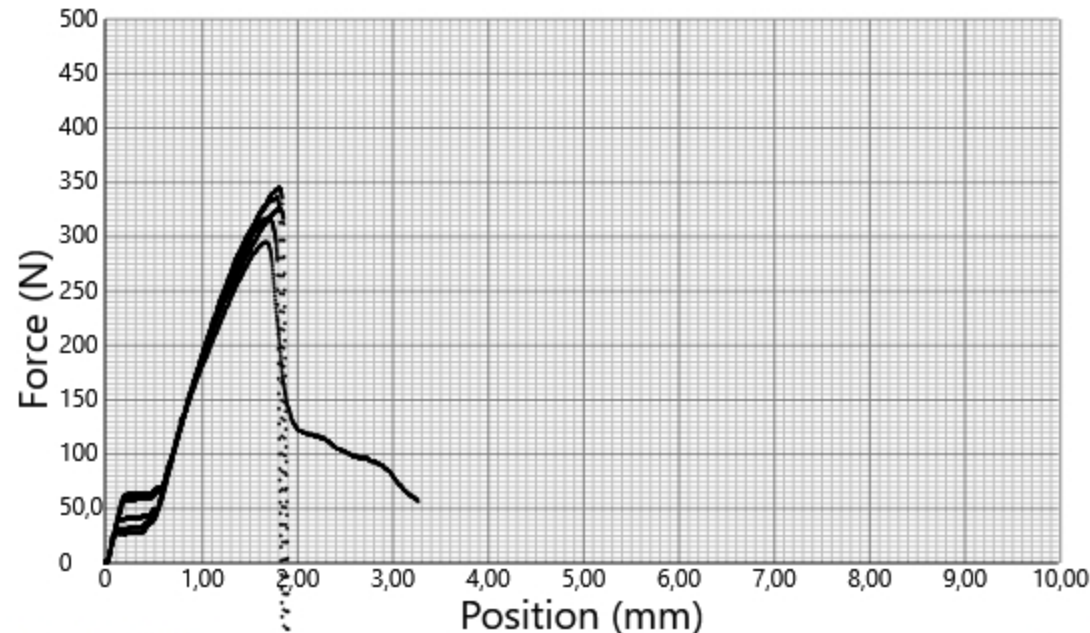


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 40C - PETG (B-2-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	547	333	41,7	340	42,5	9,11
2	PETG	50,0	4,00	2,00	528	317	39,6	322	40,2	8,49
3	PETG	50,0	4,00	2,00	517	320	40,0	320	40,0	8,47
4	PETG	50,0	4,00	2,00	501	358	44,8	360	45,0	10,0
5	PETG	50,0	4,00	2,00	536	333	41,7	335	41,9	8,69
Average					526	332	41,5	335	41,9	8,96
SD					18,0	16,4	2,05	16,2	2,03	0,648

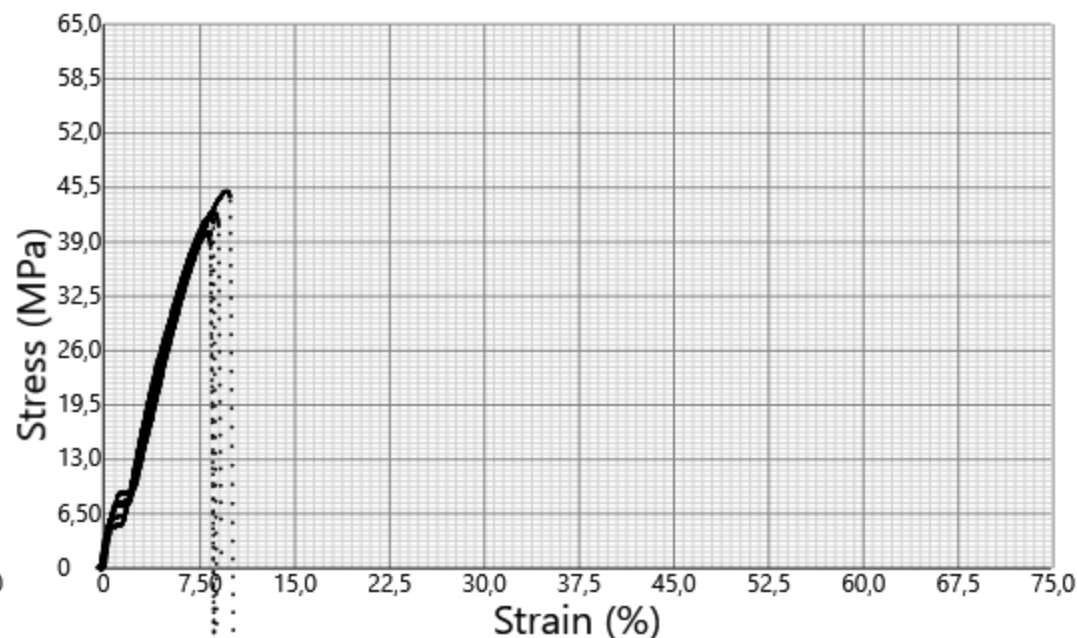
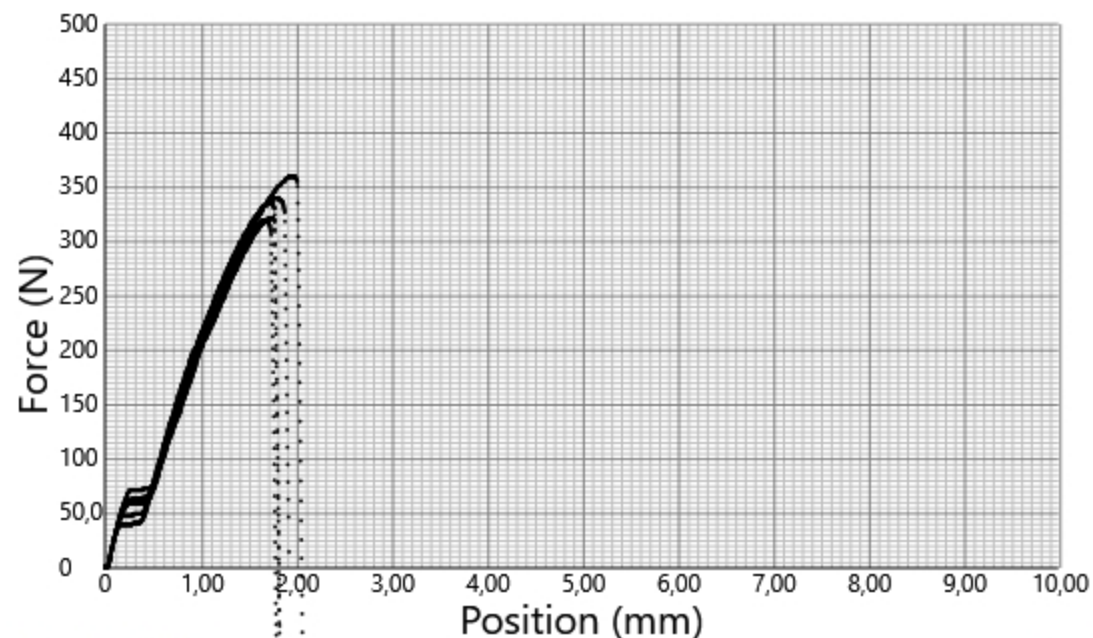


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 60C - PETG (B-3-7)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	486	335	41,9	337	42,1	9,85
2	PETG	50,0	4,00	2,00	425	300	37,5	305	38,1	10,7
3	PETG	50,0	4,00	2,00	821	95,0	11,9	363	45,4	11,5
4	PETG	50,0	4,00	2,00	467	292	36,5	295	36,9	9,18
5	PETG	50,0	4,00	2,00	496	322	40,2	323	40,4	9,23
Average					539	269	33,6	325	40,6	10,1
SD					160	98,6	12,3	27,0	3,37	1,02

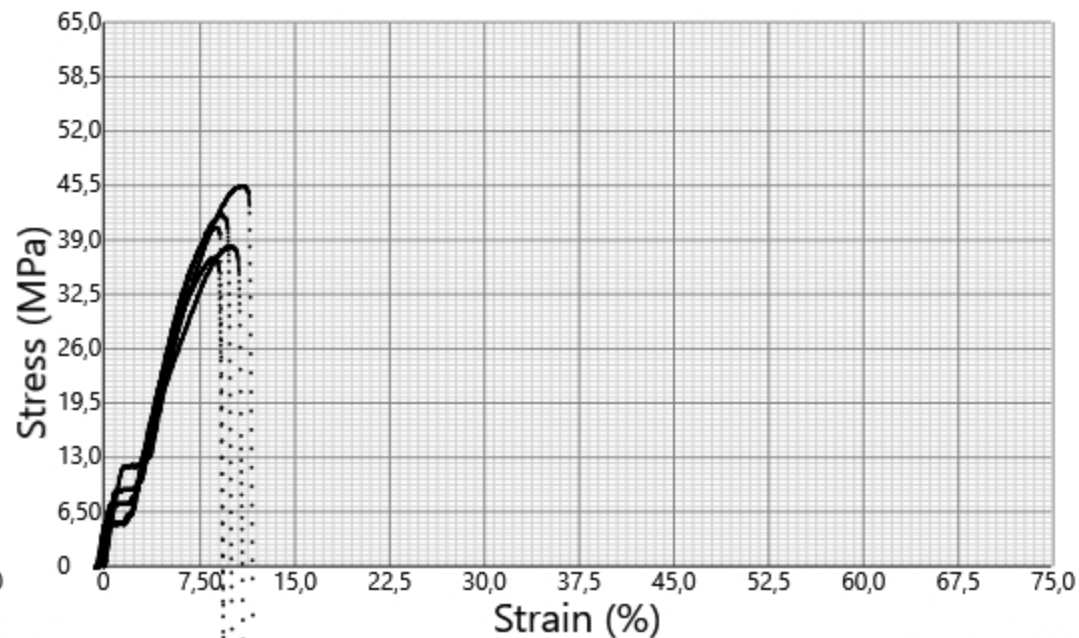
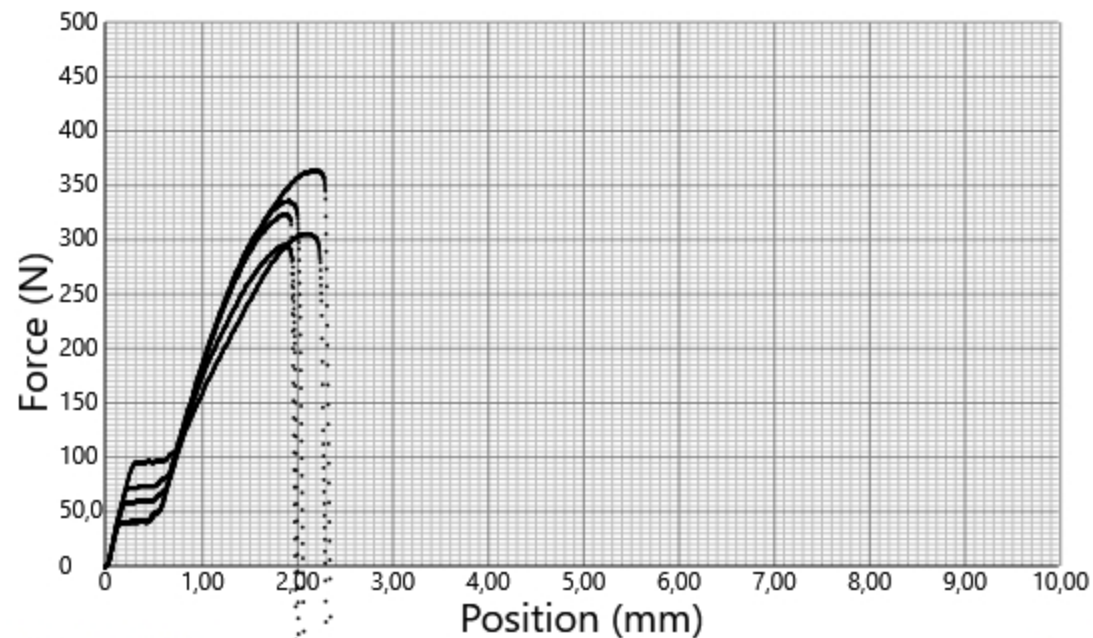


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 60C - PETG (B-3-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	PETG	50,0	4,00	2,00	822	139	17,4	393	49,2	12,2
2	PETG	50,0	4,00	2,00	829	129	16,1	380	47,5	10,8
3	PETG	50,0	4,00	2,00	761	110	13,8	368	46,0	12,4
4	PETG	50,0	4,00	2,00	839	135	16,9	398	49,8	12,5
5	PETG	50,0	4,00	2,00	833	133	16,7	393	49,2	41,5
Average					817	129	16,2	387	48,3	17,9
SD					31,7	11,2	1,40	12,3	1,54	13,2

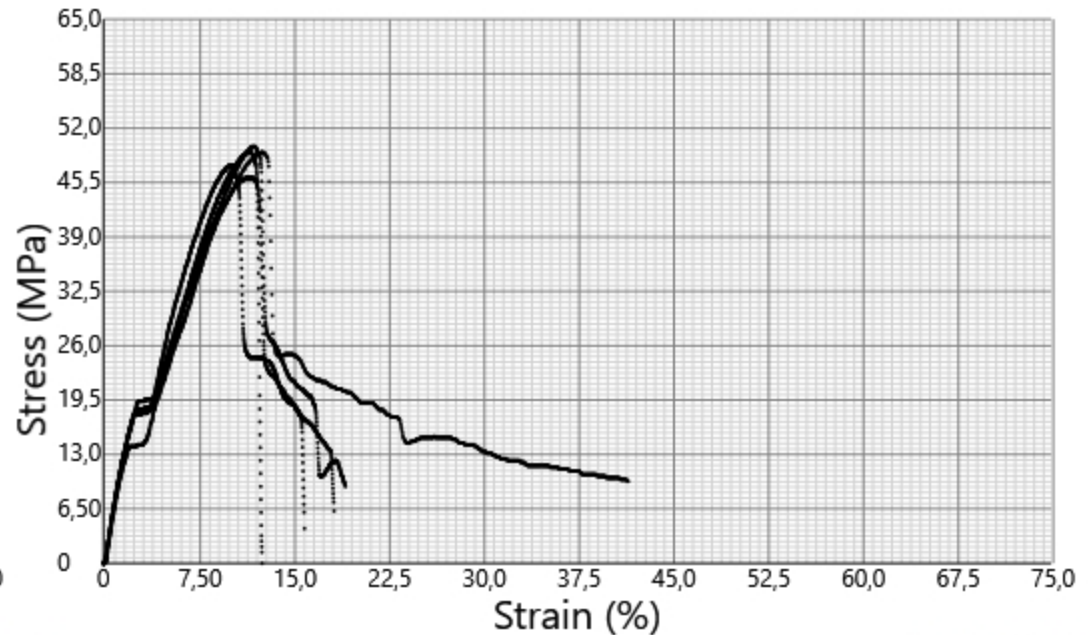
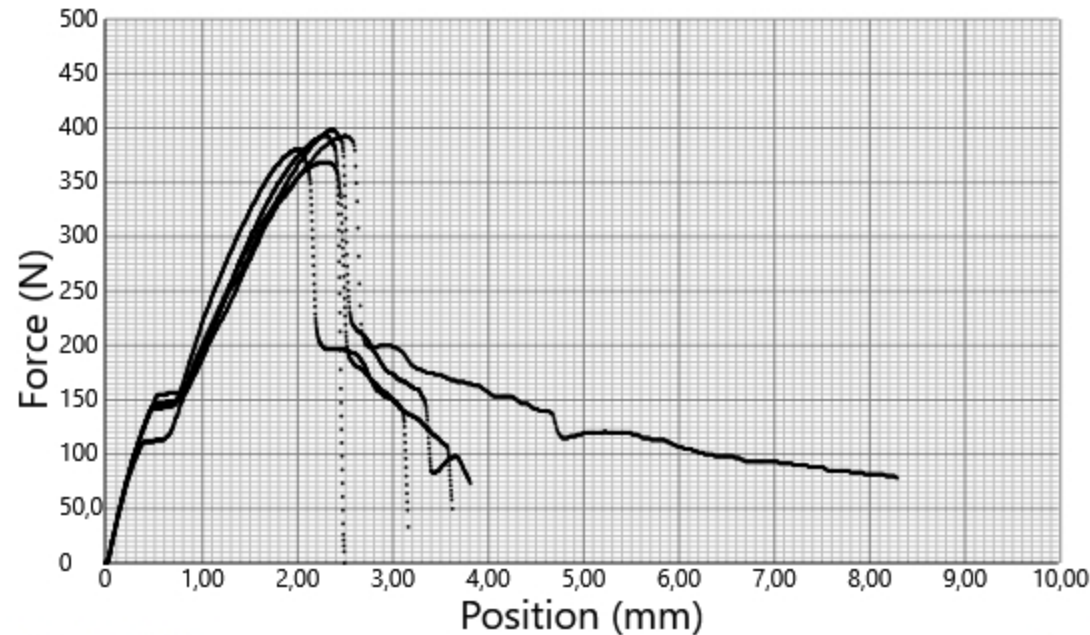


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 20C - ASA (C-1-7)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	1070	152	19,0	312	39,0	8,11
2	ASA	50,0	4,00	2,00	1030	138	17,2	315	39,4	8,92
3	ASA	50,0	4,00	2,00	1030	115	14,4	297	37,1	9,33
4	ASA	50,0	4,00	2,00	1030	130	16,3	293	36,7	8,83
5	ASA	50,0	4,00	2,00	1150	114	14,3	213	26,7	5,72
Average					1080	130	16,2	286	35,7	8,18
SD					52,6	15,8	1,98	41,7	5,21	1,45

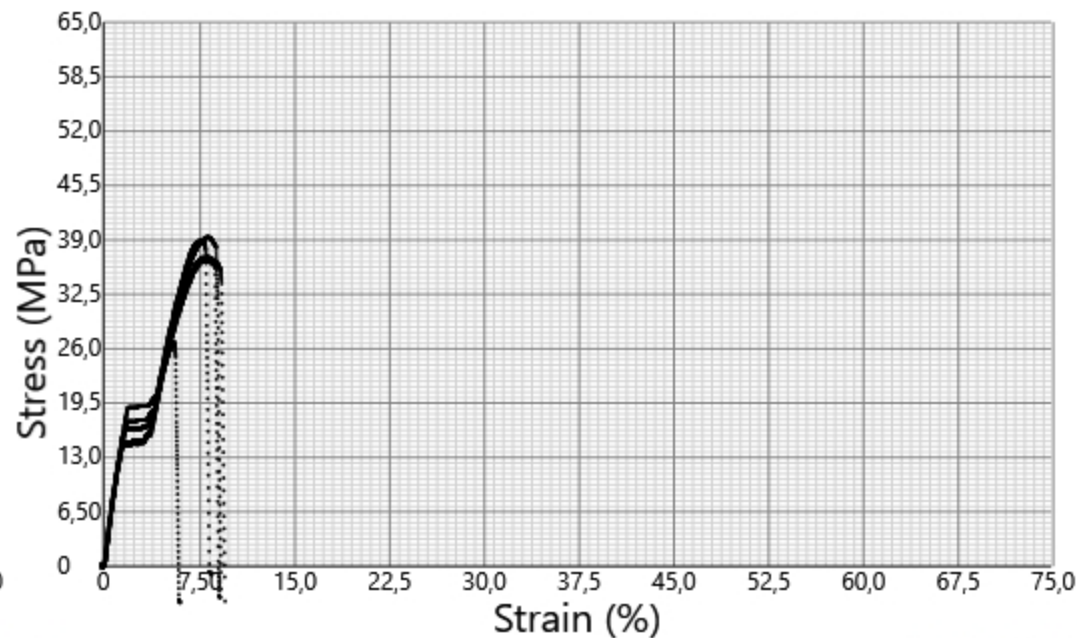
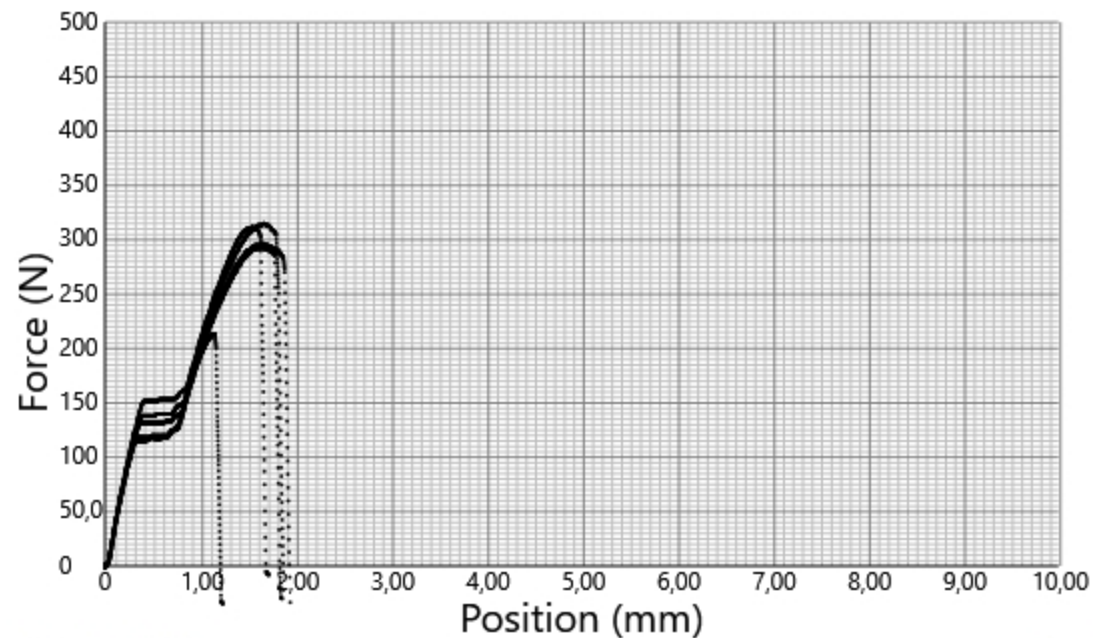


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 20C - ASA (C-1-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	345	58,3	7,29	233	29,2	8,48
2	ASA	50,0	4,00	2,00	447	187	23,3	190	23,7	5,78
3	ASA	50,0	4,00	2,00	462	200	25,0	200	25,0	6,46
4	ASA	50,0	4,00	2,00	473	208	25,9	210	26,2	6,55
5	ASA	50,0	4,00	2,00	791	35,0	4,37	133	16,7	5,16
Average					504	137	17,2	193	24,2	6,49
SD					169	83,6	10,5	37,2	4,65	1,25

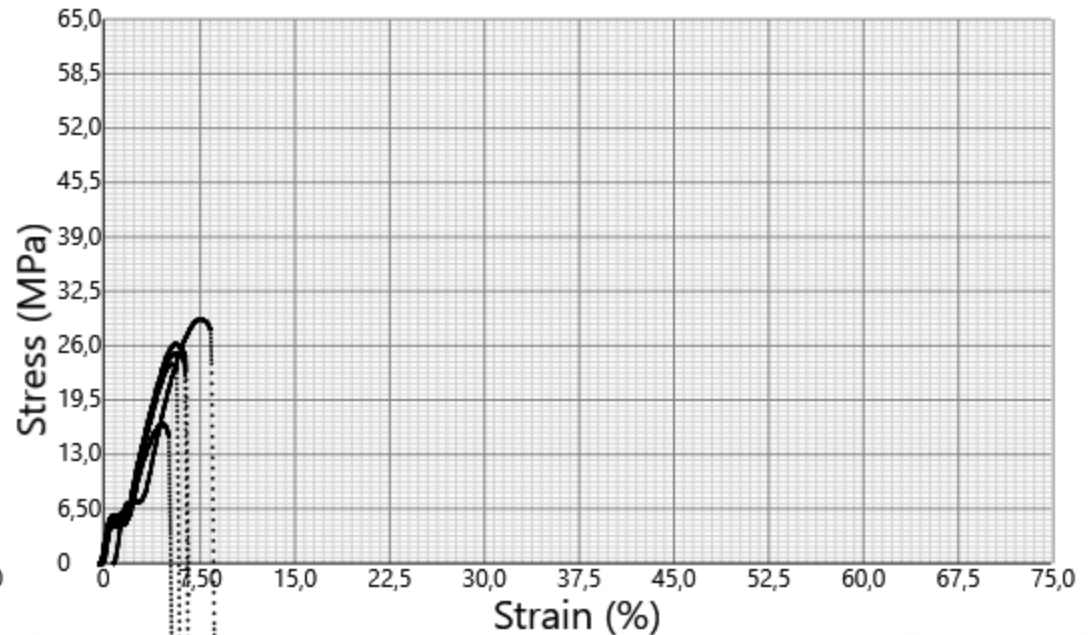
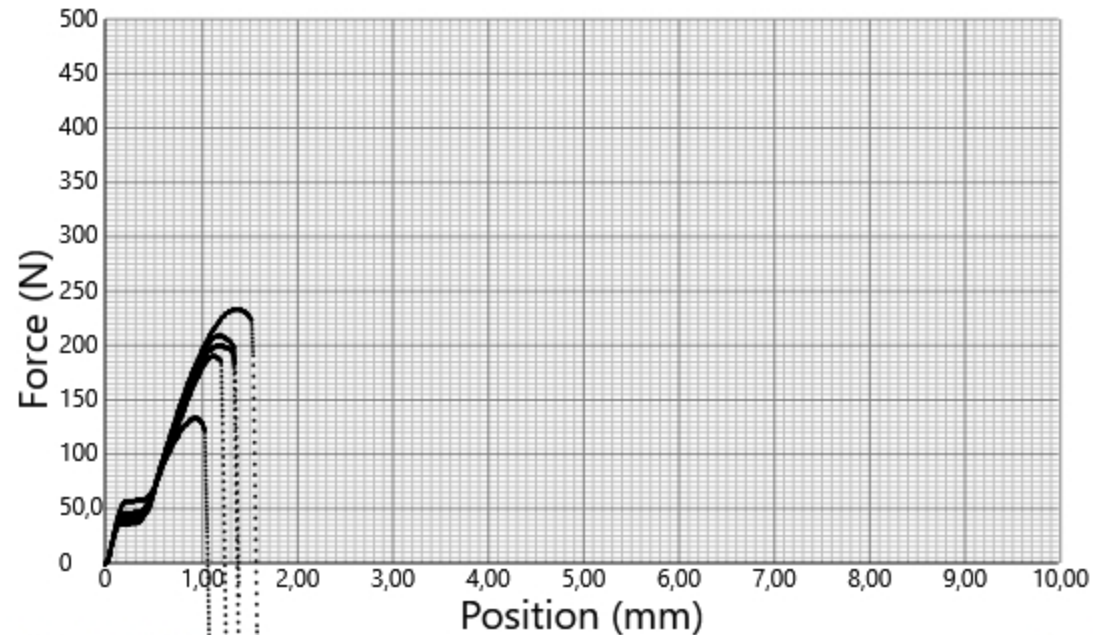


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 40C - ASA (C-2-7)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	1030	98,3	12,3	273	34,2	8,44
2	ASA	50,0	4,00	2,00	952	65,0	8,12	237	29,6	7,51
3	ASA	50,0	4,00	2,00	994	68,3	8,54	252	31,5	7,93
4	ASA	50,0	4,00	2,00	461	246	30,8	247	30,8	11,1
5	ASA	50,0	4,00	2,00	362	60,5	7,56	242	30,2	8,85
Average					760	108	13,5	250	31,2	8,76
SD					321	78,9	9,86	14,2	1,77	1,40

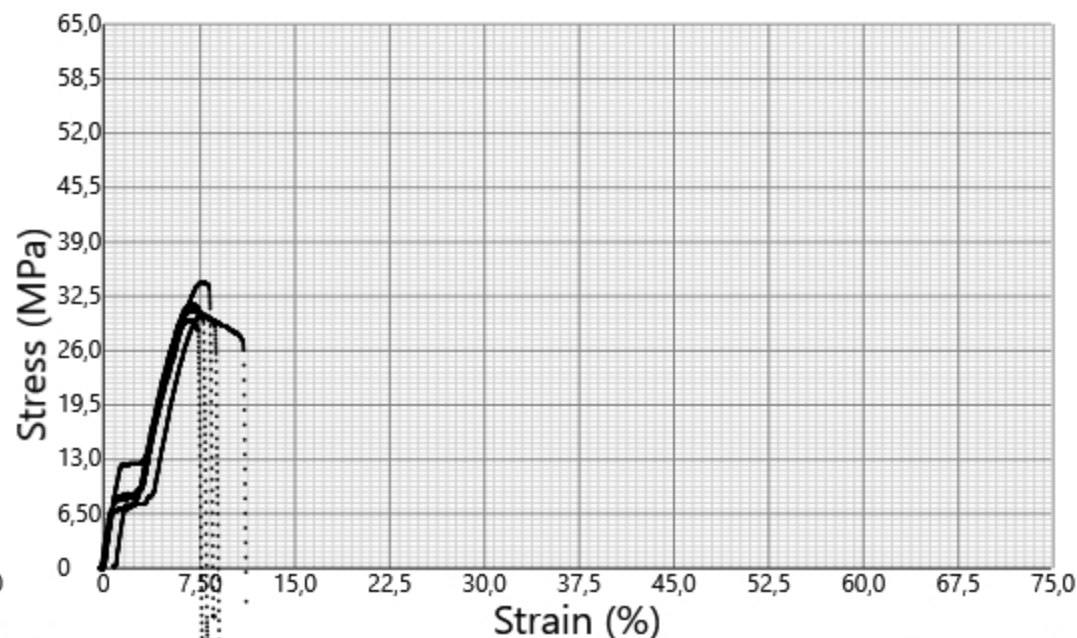
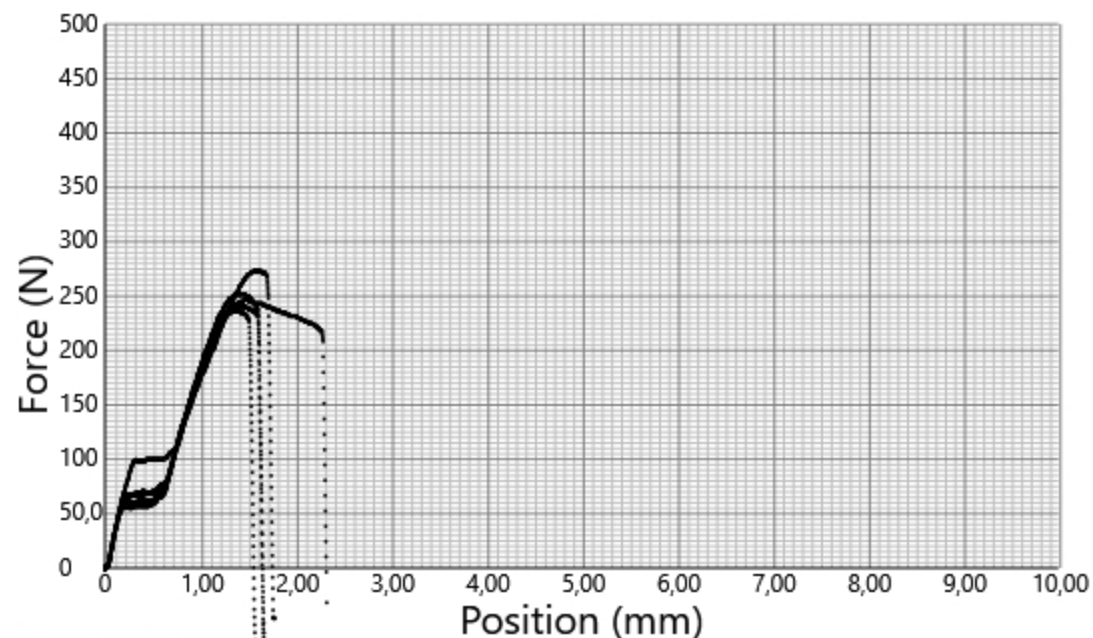


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 40C - ASA (C-2-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	530	213	26,7	215	26,9	5,87
2	ASA	50,0	4,00	2,00	463	190	23,8	193	24,2	6,01
3	ASA	50,0	4,00	2,00	459	225	28,1	225	28,1	7,81
4	ASA	50,0	4,00	2,00	728	31,7	3,96	123	15,4	4,71
5	ASA	50,0	4,00	2,00	907	103	12,9	275	34,4	7,91
Average					618	153	19,1	206	25,8	6,46
SD					196	82,8	10,4	55,2	6,90	1,37

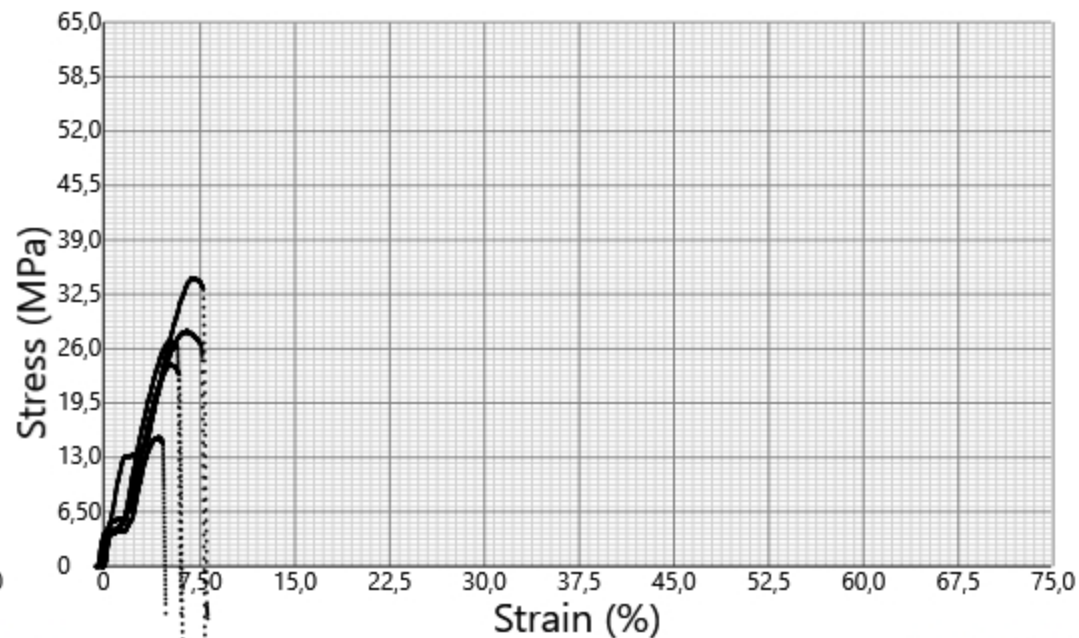
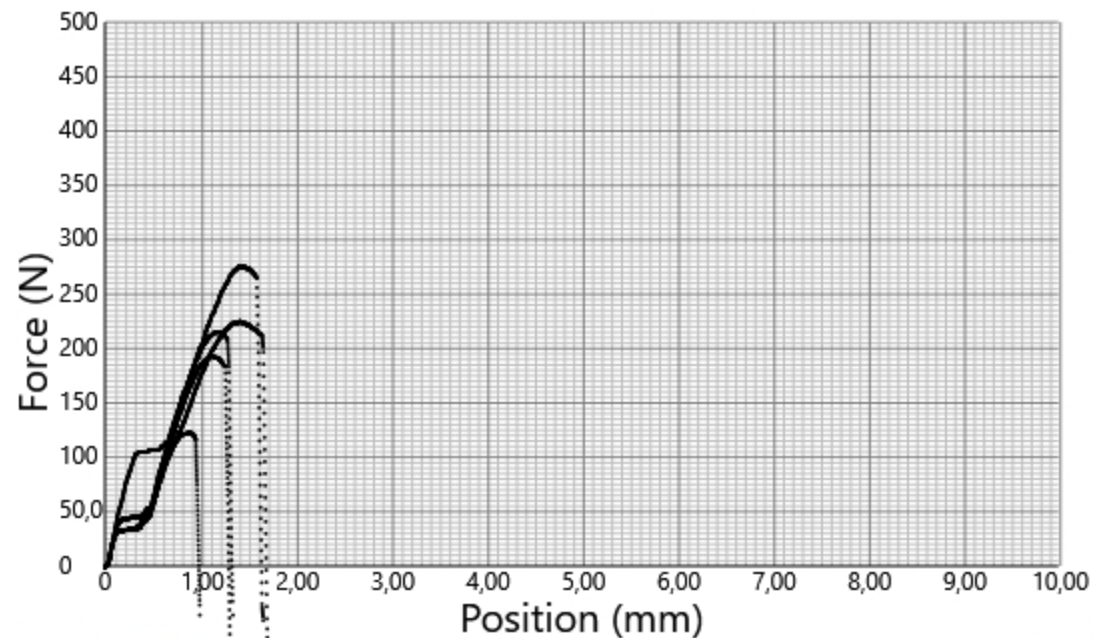


USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 60C - ASA (C-3-7)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	881	107	13,3	278	34,8	8,53
2	ASA	50,0	4,00	2,00	206	62,6	7,83	250	31,2	11,0
3	ASA	50,0	4,00	2,00	883	86,7	10,8	265	33,1	7,53
4	ASA	50,0	4,00	2,00	978	81,7	10,2	250	31,2	7,47
5	ASA	50,0	4,00	2,00	886	88,3	11,0	278	34,8	9,39
Average					766	85,2	10,6	264	33,0	8,78
SD					316	15,7	1,97	14,2	1,77	1,47

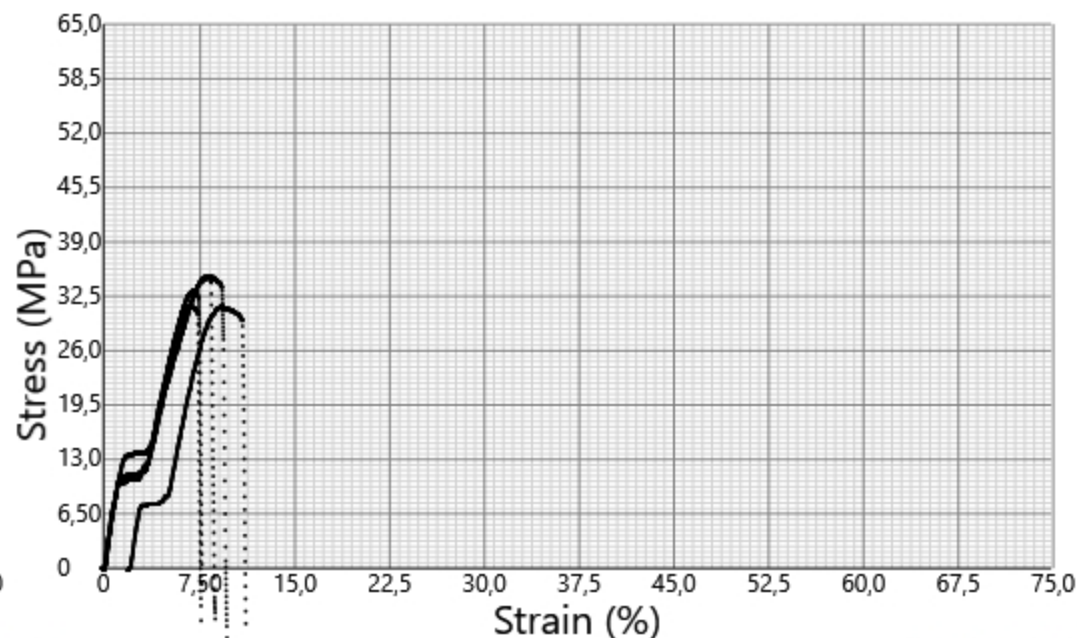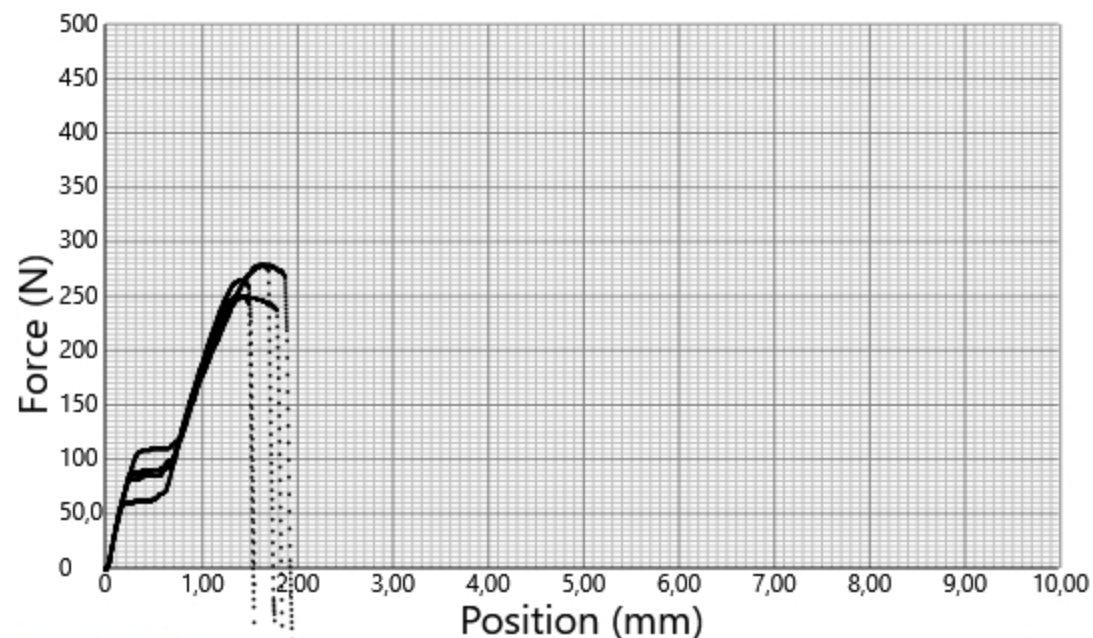

USN TEST REPORT

ISO 527 Tensile

Student Name: CMJ
Batch Name: UKE12 60C - ASA (C-3-8)

Specimen Number	Material	speed_stretch Speed mm/min	Width mm	Thickness mm	EModulus MPa	Offset Yield @ 0.2% N	Offset Yield @ 0.2% MPa	Ultimate Force N	Ultimate Strength MPa	Total Elongation (Auto) %
1	ASA	50,0	4,00	2,00	985	111	13,8	297	37,1	8,05
2	ASA	50,0	4,00	2,00	977	90,0	11,2	265	33,1	7,43
3	ASA	50,0	4,00	2,00	989	121	15,1	312	39,0	9,07
4	ASA	50,0	4,00	2,00	1020	104	12,9	283	35,4	8,41
5	ASA	50,0	4,00	2,00	924	99,2	12,4	282	35,2	8,43
Average					979	105	13,1	288	36,0	8,28
SD					34,5	11,8	1,47	17,5	2,19	0,600

