The Wyart–Cates strain clock depends on the protocol: shear reversal gives order one

[AUTHOR — to be confirmed][1]
[1] *[AFFILIATION — to be confirmed]*
(Dated: September 28, 2026)

Continuum models of shear-thickening suspensions let the frictional contact fraction f relax toward its steady value over a strain γ_0. The values in use span an order of magnitude, from 0.023 in particle simulations of a stress step to ≈ 0.2 in start-up experiments on corn starch, and nobody has measured γ_0 from a flow reversal, although reversal is the protocol through which γ_0 has been defined. We read γ_0 from the published shear-reversal transients of Lin *et al.* [1] on two colloidal suspensions. We first show that the inversion of the Wyart–Cates viscosity for f is affine in ϕ_J/ϕ. Consequently a relaxation constant fitted with free amplitudes is independent of ϕ, ϕ_0 and ϕ_m, even though a flow curve cannot determine ϕ_m, and it depends only on the divergence exponent. The fitted clock is 0.54–1.09 on 2 μm silica and 0.88–1.09 on 1.4 μm PMMA. It is controlled by strain rather than time over a decade in rate, and on silica it *falls* with rate, which a relaxation law with an added time term cannot produce. The minimum just after reversal lies at 0.56–0.74 of the model's own frictionless floor, which is itself within 3% of the lowest steady-state viscosity of each sample. On the one record where contact stress is known directly, a simulation, the directly evaluated contact-stress fraction recovers 41% faster than the inverted f. On a second silica, constant-stress start-up shows no exponential clock at all: the viscosity rises abruptly after a strain of 0.07–0.13, partly coupled to the instrument. We argue that γ_0 is not a material constant of scalar Wyart–Cates models: it depends on the protocol and on the definition of f.

I. INTRODUCTION

The Wyart–Cates (WC) model [2] describes discontinuous shear thickening (DST) through a fraction f of frictional contacts that interpolates the jamming volume fraction $\phi_J = (1-f)\phi_0 + f\phi_m$ between its frictionless and frictional values. Unsteady flows need a law for how f evolves. The common choice is a first-order relaxation in strain, sometimes with an additional time term [3–5]:

$$\frac{df}{dt} = -\left(\frac{\dot\gamma}{\gamma_0} + \frac{1}{t_r}\right)(f - f_{ss})\,. \tag{1}$$

At steady state $f = f_{ss}$ whatever γ_0 is, so a flow curve carries no information about the clock. The values in use differ by an order of magnitude. Particle simulations of a stress step gave an exponential strain scale of 0.023 [3], which Chacko *et al.* adopt [4]. The same paper defines γ_0 as "of order the strain required to evolve from one steady-state to another (for instance on flow reversal)". Richards *et al.* [5] report $\gamma_0 = O(10^{-1})$ from imposed-rate experiments. Corn-starch shear fronts give $\gamma^* \approx 0.197$ [6], a start-up scale in a different, multiplicative closure $g = 1 - e^{-\gamma/\gamma^*}$ rather than the constant of Eq. (1), and linear-stability work sweeps 0.05–0.5 [7]. Reversal recovery is known to take a strain "of order unity" [1, 8]. Gillissen *et al.* fitted the structural strain scale of a tensorial model to simulated reversal [9]. No value of the scalar clock in Eq. (1) has been measured from an experimental reversal.

Reversal has a subtlety that should be stated first. In scalar WC, f_{ss} depends on $|\sigma|$ alone, so reversing the flow at constant rate leaves $f = f_{ss}$ and Eq. (1) predicts *no* transient. Reading γ_0 off a reversal therefore assumes that reversal resets f, and it tests only the *recovery* half of the law. That is the physical reason a fabric is needed [9]. It is also what the clock in every reversal-based estimate means, ours included.

II. DATA AND INVERSION

We use the deposited data of Lin *et al.* [1] (Edinburgh DataShare 10283/886): the relative viscosity η_r against accumulated strain after a reversal, at four shear rates each for 2 μm silica (their Fig. 2b) and 1.4 μm PMMA (Fig. 2d), and the steady rate sweep of the same samples (Figs. 2a,c). The records are uniformly sampled in strain up to $\gamma = 10$ (10^4–2.5×10^4 points each).

Steady fit. We fit $\eta_r = (1-\phi/\phi_J)^{-n}$ with $f_{ss} = \exp(-\sigma^*/\sigma)$ to the thickening branch of each sweep, with $n = 2$ and ϕ_0 fixed at 0.64. A single flow curve determines only the ratios ϕ/ϕ_0 and ϕ_m/ϕ (the model is homogeneous of degree zero in (ϕ, ϕ_0, ϕ_m)), so ϕ_0 is a gauge choice and nothing below depends on it. The fits give $\phi = 0.391$, $\phi_m = 0.508$ (silica) and $\phi = 0.496$, $\phi_m = 0.587$ (PMMA) in that gauge.

The inversion is affine. Write $u = \phi_J/\phi = 1/(1-\eta_r^{-1/n})$. Solving $\phi_J = (1-f)\phi_0 + f\phi_m$ for f gives

$$f = A + Bu, \qquad A = \frac{\phi_0/\phi}{\phi_0/\phi - \phi_m/\phi}, \quad B = \frac{-1}{\phi_0/\phi - \phi_m/\phi}. \tag{2}$$

For any packing triple, $f(\gamma)$ is an affine image of $u(\gamma)$, and u depends only on the data and n. A relaxation $f = f_{ss} + (f_0 - f_{ss})e^{-\gamma/\gamma_0}$ fitted with both amplitudes free is exactly invariant under affine maps of the ordinate, so γ_0 is independent of ϕ, ϕ_0 and ϕ_m jointly. We checked this at four triples far off the covariance ray, with

ϕ/ϕ_0 from 0.32 to 0.87: the fitted clocks are bit-identical. Across $n = 1.8$–2.5 they move by at most 1.8%. The clock therefore escapes the degeneracy that makes ϕ_m unidentifiable from one flow curve.

Fit. Each record is reduced to log-spaced bins, each holding the median and the within-bin scatter. We start at the binned reversal minimum, eliminate the two amplitudes exactly by weighted linear least squares, and scan γ_0 on a logarithmic grid (variable projection [10]). A general-purpose nonlinear optimiser on the same records returned values differing by more than an order of magnitude depending only on its convergence tolerance (extttsrc/dst_fit/transient.py, extttfit_recovery docstring). We also report a fit-free landmark, γ_{50}: the strain from the minimum to half the plateau in f. Its definition does not depend on any fit window.

Where the fit starts. The minimum is a broad, noisy trough, so its position is uncertain by $\sim$ 0.1–0.2 in strain. A delay measured from it is ill-posed; our attempt to measure one failed its own synthetic controls (`scripts/probe_rebuild_lag.py`). Moving the start anywhere up to 0.20 strain *after* the minimum changes the fitted clock by at most 1.20× on every record. Starting *before* the minimum brings in the still-falling viscosity, which Eq. (1) does not describe. There the fit is ill-posed: on silica at $5\,\mathrm{s}^{-1}$ it has no interior optimum (`scripts/probe_start_sensitivity.py`).

III. RESULTS

The reversal minimum lies below the model's frictionless floor. With $f \geq 0$, WC bounds the viscosity from below by $(1-\phi/\phi_0)^{-n}$: 6.62 for silica and 19.66 for PMMA. Figure 1(a,b) shows the smoothed post-reversal minima at 0.65–0.74 (silica, 4 rates) and 0.56–0.64 (PMMA, 3 rates) of this floor. The fourth PMMA record ($\dot\gamma = 0.05\,\mathrm{s}^{-1}$) stays below the floor throughout. The floor is not an artefact of the fit. It lies within 3% of the lowest viscosity on each sample's own steady sweep (6.44 and 19.47), so the model-free statement is this: after reversal the viscosity falls 24–44% below anything the steady flow curve reaches. A scalar f cannot represent that state at any value: reversal removes more stress than the frictional contacts carry, consistent with the microstructural (fabric) contribution identified in Refs. [8, 9, 11].

Recovery is strain-controlled. Over a 10× span in rate, a pure strain clock leaves γ_{50} unchanged and a pure time clock leaves t_{50} unchanged. Measured spreads are γ_{50}: 2.14× and t_{50}: 21.4× for silica, and 1.16× and 11.6× for PMMA [Fig. 1(c)].

The clock is of order one. Figure 2(a) collects the estimates. The fitted constant is 0.54–1.09 (silica, 4 rates) and 0.88–1.09 (PMMA, 3 rates). Truncating the fit at $\gamma = 3$ moves it by at most 1.37×. The landmark γ_{50} is 0.74–1.59 and 1.41–1.64. Every estimate on both materials exceeds 0.2 by at least 2.7×, and exceeds the step-stress value 0.023 by more than an order of magnitude. One PMMA record ($0.05\,\mathrm{s}^{-1}$) is excluded: its fitted plateau in f lies outside $[0, 1]$. The model has no state for it, so it cannot test the model. Its clock is still shown, in grey.

On silica the clock falls with rate. The fitted constant falls monotonically by 2.00× across the four silica rates. In Eq. (1) the effective constant is $1/\gamma_{\mathrm{eff}} = 1/\gamma_0 + 1/(\dot\gamma t_r)$, which can only *rise* toward γ_0 with rate. No positive t_r produces the silica trend; the straight-line fit returns $t_r < 0$. The trend survives the start ambiguity only in part. Over after-minimum starts the fall is at least 1.81×, and the clocks at 0.5, 1 and $2\,\mathrm{s}^{-1}$ stay strictly ordered, but the 2 and $5\,\mathrm{s}^{-1}$ ranges overlap. On PMMA the clocks are not monotone in rate, so there the test cannot decide either way.

The recovery is not a single exponential. A two-component description beats one component decisively on the silica. Correcting for it reduces the rate trend from 1.90× to 1.70× but does not remove it. These come from a joint fit on a finer binning, so its single-exponential value, 1.90×, differs slightly from the 2.00× above (`scripts/probe_two_clock.py`). The decomposition itself is not robust to the fit window: the two fitted clocks moved severalfold between windows (probe docstring), so we do not interpret them as two processes. Figure 2(b) shows the underlying shape. The rise is slow, then fast, where Eq. (1) is steepest at its start.

The clock depends on the definition of f. Lin *et al.*'s simulations report the contact and hydrodynamic stresses separately. On that record the contact-stress fraction $s = \sigma_c/\sigma$ can be fitted by the same code as the inverted f. The results are $\gamma_0 = 0.289$ (s) and 0.488 (inverted f), a 41% difference with non-overlapping intervals. The difference is identical at two packing triples chosen so far apart that the inverted f leaves $[0, 1]$ in opposite directions. So it is the inversion, not the gauge. WC's f counts contacts, while s is a fraction of stress, and nothing requires them to be affinely related. They are not ($R^2 = 0.88$ between them).

A second protocol on silica: start-up is abrupt, not a relaxation. The deposit of Richards *et al.* [5] contains constant-stress start-ups on a comparable material: 4 μm silica in glycerol–water at $\phi = 0.574$, with 17 steps of 20 s, each preceded by $\sim$14 s at zero stress, and the same sample's steady curve. We take the solvent viscosity from the deposit's own ratio of absolute to relative viscosity (141 mPa s, identical on every steady row; the paper quotes 151 mPa s, so the deposit was presumably measured at a slightly different temperature; the clock depends on it only through $\eta_r^{-1/n}$). We pre-registered the same fit (`PREREG_startup_clock_2026-09-27.md`) and it *failed*. Above the onset ($\sigma \geq 3.2$ Pa) the fitted constants span more than an order of magnitude across the steps, with χ^2_r up to 10^4 A single exponential in strain does not describe these records, and the end-of-step viscosity also missed the steady curve by more than the registered 30% at two stresses, so even the plateau being relaxed towards is not the steady one on this protocol. Figure 3(a) shows

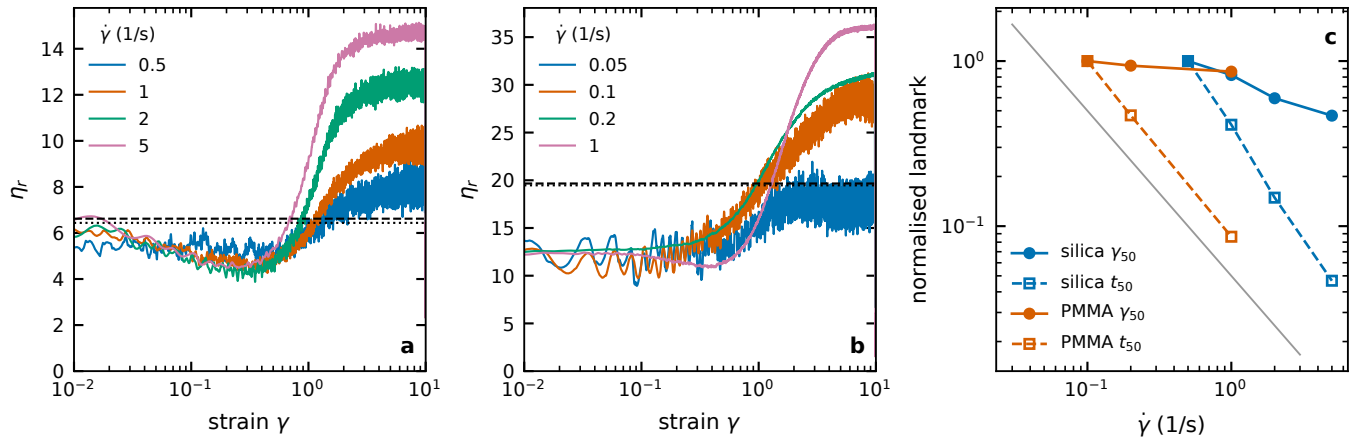


FIG. 1. (a,b) Post-reversal relative viscosity against strain, from Ref. [1]: (a) 2 μm silica, (b) 1.4 μm PMMA. One curve per shear rate. Dashed: the WC frictionless floor $(1-\phi/\phi_0)^{-n}$ from the steady fit. Dotted: the lowest viscosity on the same sample's steady sweep. (c) The fit-free half-recovery landmark read as a strain (γ_{50}, filled) and as a time ($t_{50}=\gamma_{50}/\dot\gamma$, open), each normalised by its value at the lowest admitted rate. The grey line has slope -1.

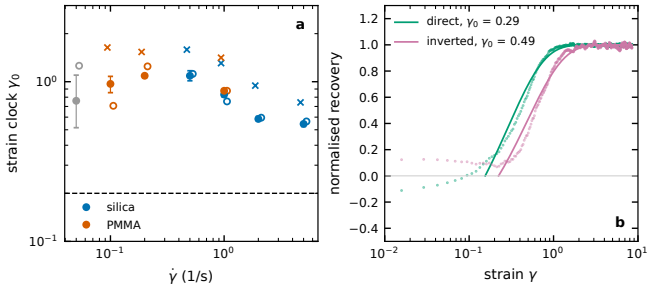


FIG. 2. (a) The strain clock per shear rate: full-record fit in f (filled, with its profile interval), the same fit truncated at $\gamma = 3$ (open), and the fit-free γ_{50} (crosses). Silica blue, PMMA orange; grey is the excluded PMMA record. The dashed line is $\gamma_0 = 0.2$. (b) One simulated reversal from Ref. [1] ($\dot\gamma = 0.74\dot\gamma_0$) read two ways, each normalised to its own fitted start and plateau: the directly evaluated contact-stress fraction $s = \sigma_c/\sigma$, and the WC inversion of the total viscosity. Lines are the fitted exponentials.

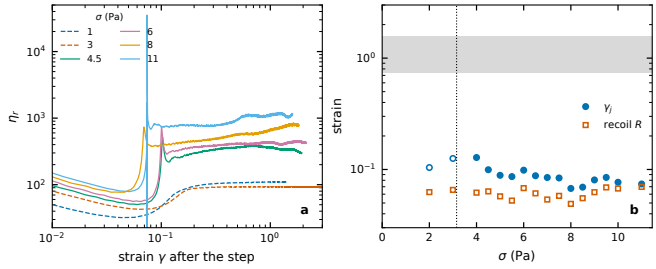


FIG. 3. Constant-stress start-up on 4 μm silica in glycerol–water, $\phi = 0.574$, from the deposit of Ref. [5]. (a) Relative viscosity against strain after the step, below (dashed) and above (solid) the steady thickening onset. The first ~ 0.05 in strain includes rotor spin-up. (b) The jam strain γ_j (steepest fall of the shear rate; filled above onset, open below) and the strain R recovered during the preceding rest, against stress. The dotted line marks the onset. The grey band is the reversal half-recovery strain γ_{50} on Lin's silica (Fig. 1), for scale.

why. The viscosity does not relax. It stays near its low-stress value and then jumps abruptly at $\gamma_j = 0.07$–0.13 on all 14 steps above onset. On 4/14 of them the shear rate briefly reverses sign at γ_j. Richards et al. class this sample as showing no large shear-rate oscillations, and reserve their oscillations for other samples [5]. A brief rate reversal is still consistent with the coupling of rheometer inertia and contact formation that they identify, so those jumps are not certainly a one-way material event. The fit-free reversal landmark γ_{50} on Lin's silica is at least 5.8× larger [Fig. 3(b)]. The two records are different samples, and we cannot tell whether γ_j is a material strain scale: over a 2.75× range of stress it spreads 1.90× in strain and 2.07× in time, so rotor spin-up is not excluded. A registered test that γ_j tracks the strain the sample recoils during the preceding rest also failed: the recoil varies too little between steps to test it, although γ_j exceeds it on 14/14 above-onset steps (post hoc). What survives is qualitative. On silica, start-up produces an abrupt rise in viscosity after a strain of order 0.1, possibly coupled to the instrument. That is the scale reported for start-up elsewhere [5, 6], and it is not the order-one, gradual recovery that reversal produces.

IV. DISCUSSION

Three statements survive every estimator we tried. (i) Measured from reversal, the strain clock of scalar WC relaxation is of order one: tens of times the step-stress value used in simulations, and several times the start-up value from corn starch. (ii) It is controlled by strain rather than time. On silica its rate dependence has the

TABLE I. The Wyart–Cates strain clock by protocol. Literature values as stated in the cited works (verified in `PRIOR_ART_STRAIN_CLOCK_2026-09-27.md`); "this work" values from `make_numbers.py`.

protocol	system	strain scale
step in stress	simulation	0.023 [3] (used in [4])
imposed rate	corn starch	$O(10^{-1})$ [5]
start-up (fronts)	corn starch	$\gamma^* \approx 0.197$, other closure [6]
start-up, constant σ	4 μm silica	abrupt at $\gamma_j = 0.07$–0.13 (this work; data of [5])
reversal	2 μm silica	$\gamma_0 = 0.54$–1.09 (this work)
reversal	1.4 μm PMMA	$\gamma_0 = 0.88$–1.09 (this work)

sign that Eq. (1) with a time term forbids. (iii) Reversal drives these suspensions below the model's frictionless floor. A scalar f can describe the recovery only after that state has been left.

Together with Table I, these say that γ_0 is a property of a *protocol and a definition*, not a material constant. Step, start-up and reversal probe different parts of the microstructure's response. A scalar f cannot distinguish them. The same record gives clocks differing by 41% depending on whether "frictional fraction" means a contact count or a stress fraction. For solvers that run Eq. (1) in flows containing reversal, such as drop impact, where the flow reverses at the rim, the consequence is concrete. A clock taken from a step or a start-up is likely several times too short for the recovery, and the softening immediately after reversal lies outside the model's reach at any γ_0.

Limitations. Two materials from one laboratory for reversal, and a different sample for start-up, where instrument inertia is not excluded. The exponent n is assumed; it matters at the 2% level. The single-exponential clock blends at least two processes. The definition-dependence is measured on a simulation, not on the experiments. What is needed next is reversal and step data on the same sample, with the contact contribution measured directly (for example, by the method of Ref. [1]).

Data and code. All numbers regenerate from `paper_strain_clock/make_numbers.py` and the figure scripts in the `dst_fit` repository [URL to be added].

[1] N. Y. C. Lin, B. M. Guy, M. Hermes, C. Ness, J. Sun, W. C. K. Poon, and I. Cohen, Hydrodynamic and contact contributions to continuous shear thickening in colloidal suspensions, Phys. Rev. Lett. **115**, 228304 (2015), 1509.02750.

[2] M. Wyart and M. E. Cates, Discontinuous shear thickening without inertia in dense non-Brownian suspensions, Phys. Rev. Lett. **112**, 098302 (2014).

[3] R. Mari, R. Seto, J. F. Morris, and M. M. Denn, Nonmonotonic flow curves of shear thickening suspensions, Phys. Rev. E **91**, 052302 (2015), 1412.4661.

[4] R. N. Chacko, R. Mari, M. E. Cates, and S. M. Fielding, Dynamic vorticity banding in discontinuously shear thickening suspensions, Phys. Rev. Lett. **121**, 108003 (2018), 1802.10586.

[5] J. A. Richards, J. R. Royer, B. Liebchen, B. M. Guy, and W. C. K. Poon, Competing timescales lead to oscillations in shear-thickening suspensions, Phys. Rev. Lett. **123**, 038004 (2019), 1902.07655.

[6] E. Han, M. Wyart, I. R. Peters, and H. M. Jaeger, Shear fronts in shear-thickening suspensions, Phys. Rev. Fluids **3**, 073301 (2018).

[7] B. Darbois Texier, H. Lhuissier, B. Metzger, and Y. Forterre, Shear-thickening suspensions down inclines: from Kapitza to Oobleck waves, J. Fluid Mech. **959**, A27 (2023).

[8] C. Ness and J. Sun, Two-scale evolution during shear reversal in dense suspensions, Phys. Rev. E **93**, 012604 (2016), 1509.01530.

[9] J. J. J. Gillissen, C. Ness, J. D. Peterson, H. J. Wilson, and M. E. Cates, Constitutive model for time-dependent flows of shear-thickening suspensions, Phys. Rev. Lett. **123**, 214504 (2019), 1911.00280.

[10] G. H. Golub and V. Pereyra, The differentiation of pseudo-inverses and nonlinear least squares problems whose variables separate, SIAM J. Numer. Anal. **10**, 413 (1973).

[11] F. Blanc, F. Peters, and E. Lemaire, Local transient rheological behavior of concentrated suspensions, J. Rheol. **55**, 835 (2011), 1111.6795.