Hydrogel Delamination During Solvent Evaporation

Haley Shamah

April 2026

1 Abstract

Poly(ethylene glycol)-based hydrogels are widely used in biomedical and soft robotic systems such as drug delivery and tissue engineering due to their ability to absorb solvents while maintaining their structural integrity and then revert back to their size. Here, we study drying, the dynamic process which occurs when solvent evaporates from a fully swollen gel. The drying process induces internal stress gradients that can lead to cracking, peeling, or fracturing, which limits practical applications for these materials. Here, I investigate drying-induced fracturing and peeling of PEG-based hydrogels, focusing on how solvent volatility, crosslinking density, and gel thickness influences these behaviors. We find that cracking and peeling behavior does not vary significantly across changes in gel thickness or crosslinker density, but it does depend on the volatility of the solvent. More volatile solvents lead to faster drying, as well as a greater extent of material fracturing. By quantifying the behaviors of drying-induced fractures, our research provides insights into these mechanics and offers strategies to design more durable PEG-based hydrogels. These insights also advance our understanding of solvent-gel interactions in various drying conditions and can be used to help inform the design of systems that rely on structural integrity and minimal instabilities.

2 Introduction

Hydrogels are water/ liquid soluble cross linked-polymers with a variety of different applications such as drug delivery and tissue engineering. They are most commonly found in bioengineering, but are an important area of soft matter physics as well. Hydrogels are a solid material that have the ability to expand and contract based on the introduction of an absorbed solvent, while maintaining the integrity of the polymer network[13]. Hydrogels make up many familiar products, for example Jello or Orbeez.

While there are several uses for hydrogels, I personally am most interested in the biomedical implications, such as drug delivery and tissue engineering. Drug delivery is the ability to transport a drug to a specific area of the body during a specific time and with a specific amount. There are many barriers to doing so with specific pill carriers, so polymers are used to bypass these [4]. It is useful to note that hydrogels are biocompatible (can interact with biological systems without producing toxins) and can break open at certain times or under certain stimulus [12]. As mentioned, hydrogels have a unique ability to expand and shrink back to their natural state, making them easily manipulatible and useful to drug delivery [8, 9].

Another biomedical hydrogel application is tissue engineering. Due to their ability to absorb water and soft structure, hydrogels have nearly identical elastic properties to human tissue [6]. This allows hydrogels to be used as scaffolding or support when regenerating tissue. The same physical structure, however, makes utilizing hydrogels for non-surface applications more difficult. As a result, researchers have been trying to figure out the best way to inject hydrogels into the human body in order to facilitate tissue regeneration.[2, 10].

Now, researchers are looking into a few biomedical hydrogel applications including corneal stromal defect, wound healing through skin adhesion, and an injectable self healing hydrogel [13]. Additionally, there has also been exploration into hydrogels' responsiveness to various stimulus signals, and how behavior can be manipulated to align with specific designer sensors [13]. These sensors with hydrogels could even be used in soft and wearable electronic devices [13]. Hydrogels have many applications in a variety of different fields and can be a useful tool in future medicines, healthcare, and technology. My research focuses on the drying behaviors of hydrogels in different solvents, with the goal of identifying broad patterns and trends.

I will start by identifying key characteristics of hydrogels and discussing what is known about their behavior. Then, I will summarize the current state of hydrogel research. Section 3 details my experimental methods and sections 4-6 will discuss the results of my experimentation and their significance.

2.1 PEG based hydrogels

During my research I have worked with PEG-based hydrogels due to their ease of fabrication and their ubiquity within hydrogel applications [7]. There are a few notable disadvantages of PEG-based hydrogels, however, such as injectability difficulty, uncontrollable degradation, and relatively weak structure [1].

The PEG-hydrogel system I used are made up of two monomers, PEGDA and PEGMEA (Figure 1). PEGDA is the crosslinker of the gel, while PEGMEA helps facilitate the crosslinking and is the backbone

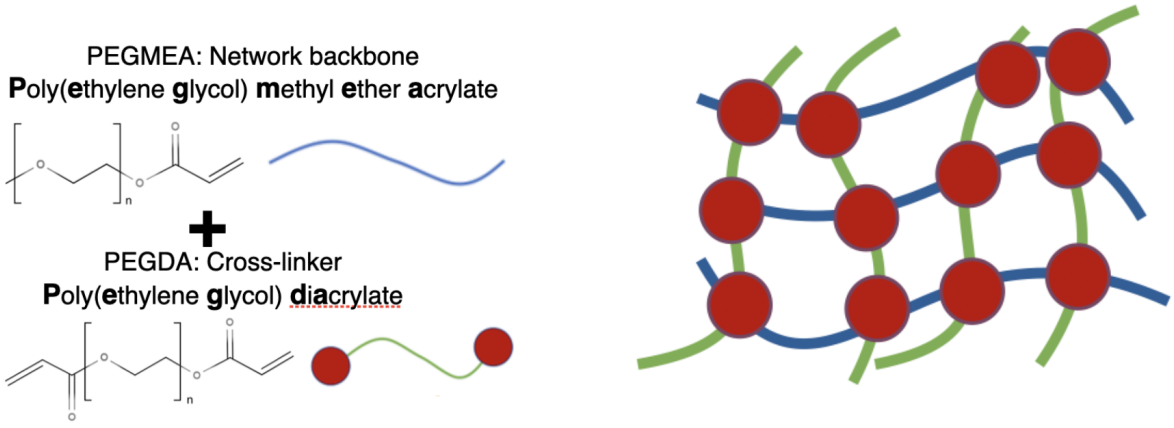


Figure 1: A graphic demonstrating the internal network of PEGDA and PEGMEA. PEGDA is the cross-linker of the gel while PEGMEA is the backbone.

polymer [3]. Since PEGDA is the crosslinker and controls the rigidity of the gel, a higher concentration of PEGDA will yield a stiffer and less malleable gel. There are other types of hydrogels/ hydrogel modifiers such as Coumarin, PDMS, and more [5, 10, 14] with different advantages and disadvantages, but for this work I will only be discussing PEG-based hydrogels.

2.2 Swelling Hydrogels

When submerged in a solvent, hydrogels are able to expand much larger than their dry size. This can range from $\approx 150\%$ mass increase to $\approx 700\%$ mass increase depending on the solvent and crosslinker density [11]. A gel placed in solvent will absorb solvent until it reaches an equilibrium point where they will no longer enlarge despite still being surrounded by solvent. The time frame to reach equilibrium depends on both the structure of the gel (amount of crosslinking) and the solvent; in my work this time frame was on the order of hours.

To calculate the rate at which gels swell, as well as how much they swell, we use the unswollen initial mass (m_0), mass of the gel (m(t)), and the equilibrium mass (m_eq). Taking the equilibrium swelling ratio to be

$$Q_{eq} = \frac{m_{eq}}{m_0} \tag{1}$$

and the normalized swelling ratio to be

$$\bar{Q(t)} = \frac{m(t) - m_0}{m_{eq} - m_0} \tag{2}$$

the swelling ratio of the gels is set by polymer network properties, as shown in Figure 2. Gels are labeled by their molar ratios, so a 20:80 gel will have a ratio of 20% PEGDA to 80% PEGMEA. We can see that gels with a lower PEGDA ratio will swell more than those with a higher PEGDA ratio (Figure 2a). Gels with a higher PEGDA ratio, however, will reach equilibrium faster (Figure 2b). Also, gels swollen in ethanol will reach equilibrium slower than those swollen in water (Figure 2c) [11]. From my observation, acetone swollen gels will reach equilibrium much faster than both water and ethanol.

Imbibing solvent creates larges stresses in the polymer network, and under certain conditions these can lead to material fracture. These fractures may take a few minutes after initial submersion to occur, but once they are initiated the fractures happen in a matter of milliseconds. Fracture behavior was only observed for gels with a PEGDA mol percentage of 3-20 [7]. At lower mol percentages there is the polymer network

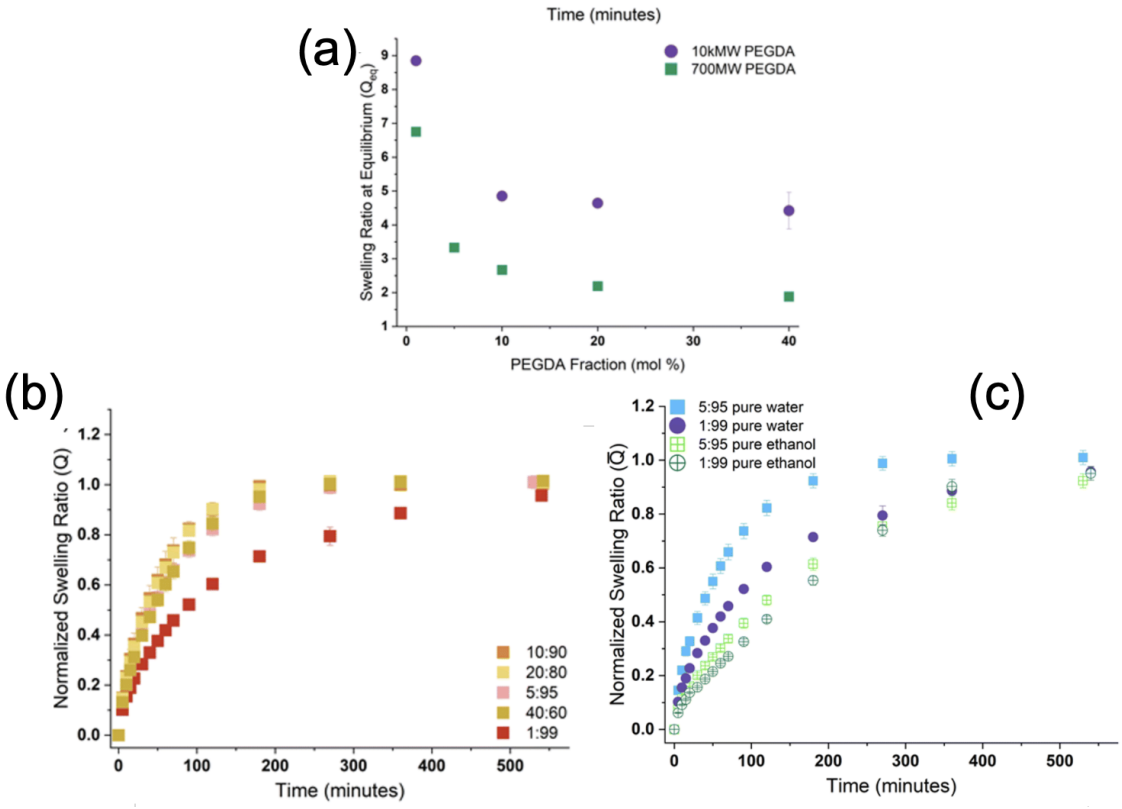


Figure 2: Hydrogel swelling ratios [11] comparing (a) the swelling ratio for different PEGDA fractions, (b) the normalized swelling ratio as a function of time for different PEGDA fractions to get a timescale, and (c) the normalized swelling ratio as a function of time to compare the timescale for different solvents.



Figure 3: Hydrogel delamination after removal from a solvent. Peels will form from the sides (a) and cracks will form on the surface (b). These images could be the top and side view of the same gel as both behaviors will occur at the same time.

is more flexible so it can accommodate the extra system stress, while at higher mol percentages there is minimal swelling possible due to the highly cross-linked network [7].

2.3 Hydrogel Delamination

As with swelling, evaporation of solvent also leads to large stresses which can cause material failure. As the solvent evaporates, the top layers of the gel will split up into separate peels and visible cracks will also appear on the surface (Figure 3). This delamination has been the focus of my research.

Delamination has been studied in a few other types of hydrogels, most notably PDMS and DN [5, 14]. Chung et al studying PDMS gels found that cracking and peeling behavior is the same regardless of curvature. Even if the gel is flat, a hemisphere, or a cylinder peeling will occur [5]. The PDMS gel is different from the PEG-based system I work with as the latter gels are very rigid. Yet, the peeling patterns that Chung finds are consistent with the patterns that I will discuss here in my research.

Another paper by Zhang et al discusses DN hydrogels. In this case, the top layer of the gel completely came off from the bulk [14]. While the top peels of PEG-based hydrogels remain connected to the remainder of the gel, the delamination was spontaneous in both cases. Even with slightly different materials and characteristics between Zhang's work, Chung's work, and my own, the core behaviors of hydrogels are comparable and delamination will occur. While similar behaviors have been observed in a few cases, here I wanted to explore how delamination is controlled by network properties, geometry, and solvent properties.

3 Methods of Experimentation

3.1 Sample Preparations

3.1.1 Solution Preparation

Hydrogel solution is prepared by combining PEGDA, PEGMEA, and DMPA (2,2-Dimethoxy-2-phenyl-acetophenone). The desired mol ratio (ex 10% PEGDA and 90% PEGMEA for a 10:90 gel) is multiplied by the molecular weight (480 g/mol PEGDA and 700 g/mol PEGMEA) to get the physical weight of each

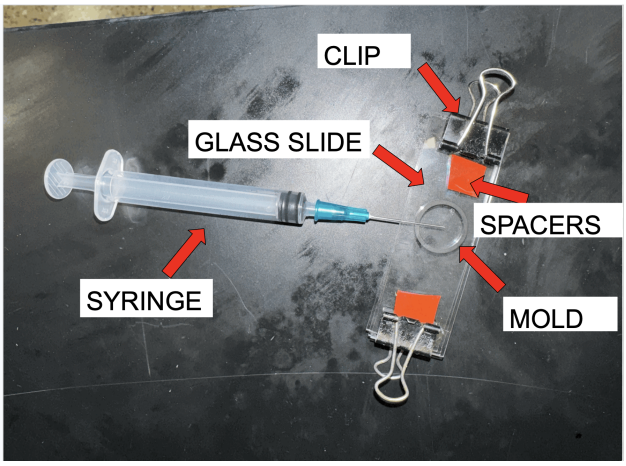


Figure 4: Setup to make cured hydrogels

chemical. The physical weight can then be divided by the desired solution weight to get the individual chemical masses needed. DMPA is the photo-initiator, or curing agent, needed to cure the PEG based gels. The needed amount of DMPA is .5% of the total weight. To ensure exact results I used a scale with measuring capabilities of the ten thousandth place. I then vortexted the vial with solution for 15-30 minutes until there were no solid DMPA particles remaining. The vial was kept inside tinfoil during this process to block any UV light which could initiate curing.

3.1.2 Gel Preparation

The completed solution is injected into a syringe with a .6mm diameter. A silicone mold in the outline of the desired shape with a slit is placed inside two glass microscope slides (Figure 4). Binder clips are placed on the ends of the slide to clamp the slides shut. Extra pieces of silicone with the exact thickness of the mold are placed as spacers on either side of the mold to prevent the clips from bending the glass. I then used the syringe to put the gel inside of the mold and create the desired shape. Silicone molds ranged in thickness from .5mm to 3mm. For this work, I used exclusively cylindrical shapes with a diameter of 14.4mm to keep everything uniform.

The glass slide is placed under a 3UV Series handheld UV lamp with a light intensity of approximately 100 mW/cm^2 for 7 minutes until the gel is cured, as indicated by it becoming solid. Gels with a higher concentration of PEGDA will be less malleable than gels with a lower concentration, but all gels will become solid for the formulations I used. Once the curing process was complete I removed the binder clips, separated the slides, and used a sharp edge to remove the gel from the glass if necessary. If the gel was not being used for experimentation within the same day, I placed it in a petri dish with dessicant to prevent moisture entering the gel prematurely.

3.1.3 Gel Swelling

Hardened gels were completely submerged in the desired solvent in order to swell. I used acetone, ethanol and Milli-q water in 200mL glass containers filled to around 75mL to prevent solvents having adverse reactions to the material. Glass beakers were covered with parafilm. In order to ensure that gels were completely swollen to equilibrium, I left them in the solvent for several hours until the gels reaching equilibrium swelling. For acetone I used at least 2-3 hours and for ethanol and water I waited at least another day [11]. I also kept in mind that gels with a higher concentration of PEGDA (greater than 20:80) take longer to swell so I made sure to keep them in the solvent for at least an hour or so longer.

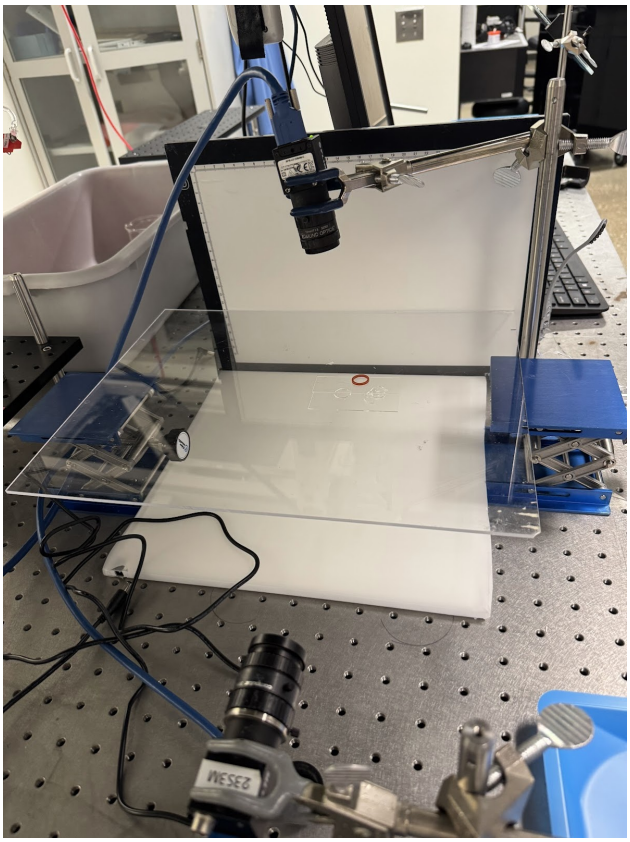


Figure 5: Room temperature evaporation camera setup

3.2 Experimental Setup

3.2.1 Room Temperature Evaporation

To take pictures and videos of the gels I placed them on top of a glass slide, with the slide resting on a piece of clear acrylic elevated above the tabletop (Figure 5). LED panels were placed behind and underneath the gels to prevent shadows and create high quality images. One camera was placed looking down upon the gel, and another camera was placed looking sideways at the gel. Both cameras were facing their respective light sources. To take the videos, I relied on the program SpinView to manipulate the exact frame rate I wanted, exposure rate, and to ensure the images were orientated correctly. On many samples, I placed silicone rings in between the glass and the gel to prevent adhesion and allow the solvent to escape from the bottom. This, however, caused visible dark rings on the images that made analyzing more inconvenient. After realizing that there was no behavior difference between having the rings present and removing them, I started placing the gels directly on the glass slide to allow for better imaging.

3.2.2 High Speed Camera

To capture one specific crack I utilized a high speed camera, which allowed me to record many more frames per second. In this case, I was interested in the behavior of one singular crack formed on the surface of the gel, and how quickly it moved across the surface. I used a high-speed Phantom camera and the Phantom Camera Control Application program.

I placed the high speed camera on an elevated surface, making sure it was properly secure (Figure 6). On a separate and lower elevated surface right in front of the camera I placed a piece of glass with the gel. The outer ring visible in many images is a silicone mold, which I just used as a marker of where to put the gel to ensure it was in frame and focused right away. I placed an angled mirror above the gel, which is what

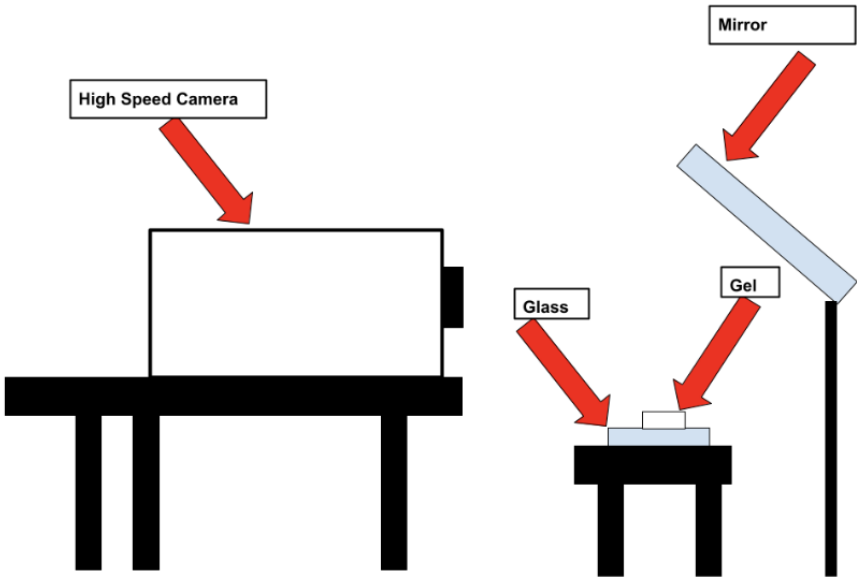


Figure 6: High speed camera setup

the camera actually filmed.

3.3 Experimental Methods

For image analysis I used the platform ImageJ. This allowed me to take measurements, track speed, and identify exact frames that certain behaviors occurred.

3.3.1 Distance Measurements

Much of the data I took required measurements of specific distances or lengths on the gels. This included finding specific peel thicknesses and how tall the peels reached. For these I used the "measure" feature on ImageJ and manually dragged a line over the desired area. In each video I included a silicone mold with a known height so I could set the scale and get an accurate conversion length between pixels and millimeters.

3.3.2 Speed Analysis

For cracking analysis I tracked displacement of the crack and then calculated its velocity. I again used ImageJ for this task, and utilized the "manual tracking" feature. For each frame of the video I placed a point for the edge of the line at that moment. The computer then calculated the x and y position at each frame. Using Python, I then calculated the total distance traveled at each frame by subtracting the x and y positions by the position of the point at the first frame. The total distance traveled was was plotted as a function of time by dividing the frame number by the frame per second rate of the video. To calculate velocities I found the total distance traveled in the last frame measured and divided it by the time elapsed.

4 Methods of Data Analysis

4.1 Acetone and Ethanol Swollen Gels

Videos of acetone and ethanol swollen gels were taken over the course of an hour, and captured 1 frame per second. Top and side view videos were started at the exact same time, so the frame numbers match up between them. Four samples were created for each gel thickness/ concentration. Gels that cracked during swelling were discarded

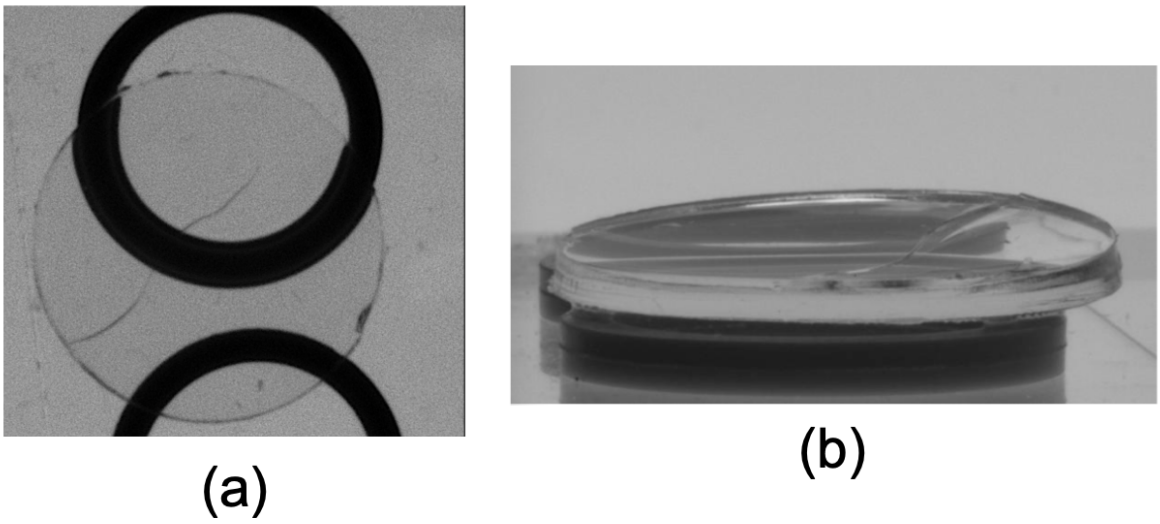


Figure 7: Initial Gel Behaviors (a) Initial Crack (b) Initial Peel. These behaviors do not necessarily happen at the same time.

4.1.1 Crack and Peel Initiation Times

The frame number in which the gel is placed on the glass is subtracted from the frame number in which the first crack is visible on the top view video (Figure 7a). This number corresponds to the crack initiation time, or the number of seconds it takes for the first crack to appear.

Similarly, the placement frame number is subtracted from the frame number in which the first peel is visible on the side view video (Figure 7b). This number corresponds to the peel initiation time.

I took the mean of the times for each gel group and used the standard error of the mean (SEM) to represent deviations. These points were plotted on a scatter plot with a log log basis, with an additional dashed horizontal line representing the average value for a given solvent.

4.1.2 Relaxation Times

For each gel there came a point where the peels began to lower and the gel regressed back into its original shape (T_{relax}). The placement frame number was subtracted from the frame number in which this behavior started to occur, which was the relaxation time value. Again, relaxation times were plotted in a log log scatter plot using the mean, SEM, and horizontal line for total mean.

4.2 Thicknesses

Physical measurements were taken using the side view videos. First, to set the scale I measured the thickness of the silicone mold in each video and set the scale so that the distance was 1.68mm. I then was able to convert height measurements in pixels to mm.

4.2.1 Peel Thickness

Peel thickness corresponds to how thick each individual peel was. I measured the first visible peel at the first frame it separated from the bulk of the gel. Sometimes the first peel happened facing away from the camera. When this happened, I used the first peel that I was capable of measuring. When varying initial heights, I chose to measure the "swollen height", or the thickness of the gel immediately after it was removed

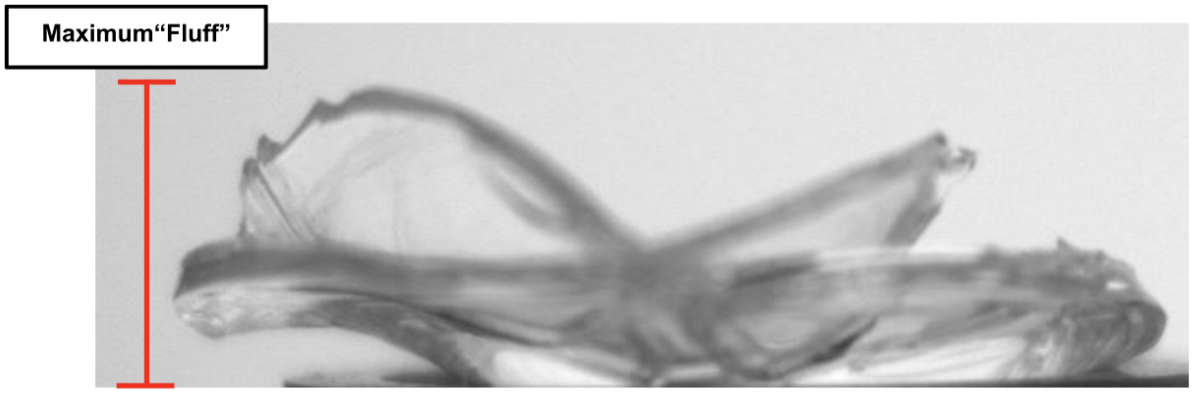


Figure 8: Maximum Fluff Visualization

from the solvent. The gel naturally got a little bit thicker after swelling, and I felt this was a more accurate measurement than the unswollen initial height.

4.2.2 Maximum "Fluff"

Fluff is a term I use to denote the total distance between the top of a peel and the bottom of the gel (Figure 8). Maximum fluff is then the largest total distance, or the highest the peels will travel upwards. Usually, this point is right before the gel starts to relax.

Just as I did with the peel thickness, I again measured the swollen height when varying initial heights of the gel. I also normalized the height of the maximum fluff, rather than use the strict amount. To do this I used the formula

$$NormalizedHeight = \frac{MaximumFluff}{SwollenHeight}. \tag{3}$$

4.2.3 Light Intensity

In lieu of counting the number of cracks that occurred on the surface of a gel, I instead calculated the light intensity. Cracks make the top of the gel darker, so a higher light intensity corresponds to a smaller number of cracks and vice versa. I again used imageJ to calculate the normalized light intensity, based on the initial gel placement. I used the top view videos and found the light intensity value of the placement. I then found the frame where the most amount of cracks were visible (Figure 9), and used Python to divide this intensity by the initial one. An intensity value of 1 means that the gel did not crack while the solvent was evaporating. I plotted these points as an ordinary scatter plot with a linear basis. Since there were many overlaps, I set the opacity of the points to be lower, so a thicker point means that multiple samples had the same value.

4.2.4 Speed of Cracks

Using the Phantom Control Camera Application I carefully cropped the high speed camera videos to start at the precise moment a crack occurs and stop at the precise moment the crack finishes formulating. Acetone swollen gels were captured at a rate of 10,000 frames per second, while ethanol swollen gels were captured at a rate of 3,000 frames per second. For this experiment I only used 20:80 gels with an initial thickness of 1mm. All velocities of each solvent were averaged together and an SEM was calculated for the deviation. I analyzed roughly one crack per gel, but not each crack was necessarily the first crack visible. I also disregarded any crack that happened through the part of the gel that solvent was adhering to the glass.

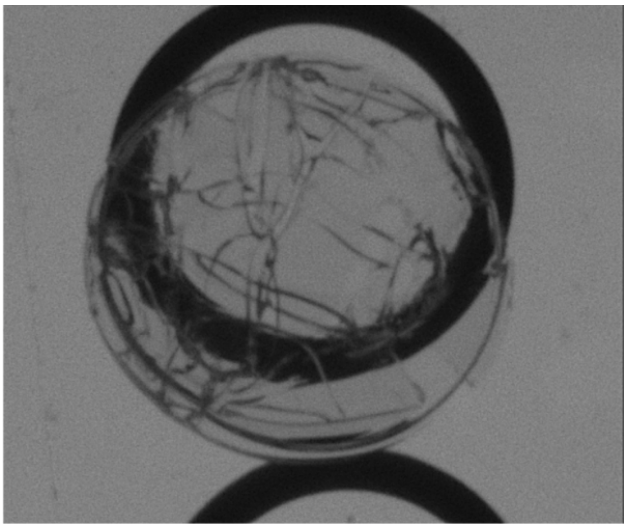


Figure 9: Point of max cracking. This is the maximum amount of cracks visible on a gel during the solvent evaporation process.

Concentration	Percentage Cracked
1:99	0%
2:98	25%
3:97	0%
4:96	0%
5:95	50%
10:90	100%
20:80	100%
30:70	100%

Table 1: Percentage of gels that cracked while swelling in room temperature milli-q water. For each molar concentration I created 4 samples.

4.3 Water Evaporation

Since water evaporation is a relatively new area of exploration, I have not yet figured out the best way to quantify the information I have gathered. Currently, I am relying on qualitative observations. Collecting water evaporation data also comes with some limitations as many gels break into pieces during the swelling process, and are therefore unusable. Based on sets of 4 gels swollen in water (Table 1), the cutoff point for making water swollen gels is determined to be 5:95. This is consistent with previous work, as Leslie found that gels were more likely to crack in water with a molar ratio of 3-20 [7].

4.3.1 Room Temperature

In a similar process to acetone and ethanol evaporation, I used the same camera set up and program to video water evaporation at room temperature. Instead of 1 frame per second, however, I employed a significantly slower process. For 1:99 and 2:98 gels I used 1 frame per 10 minutes for 24 total hours. For 3:97 and 4:96 gels I used 1 frame per 5 minutes for 24 total hours. In these videos I primarily looked for if the gel broke apart or stayed intact while the solvent was evaporating.

4.3.2 Oven

Based on experimental data by my graduate student mentor, Samira Khan, the vapor pressure of water at different temperatures is known (Figure 10). At 20 C ($\approx$ room temperature) the vapor pressure of acetone

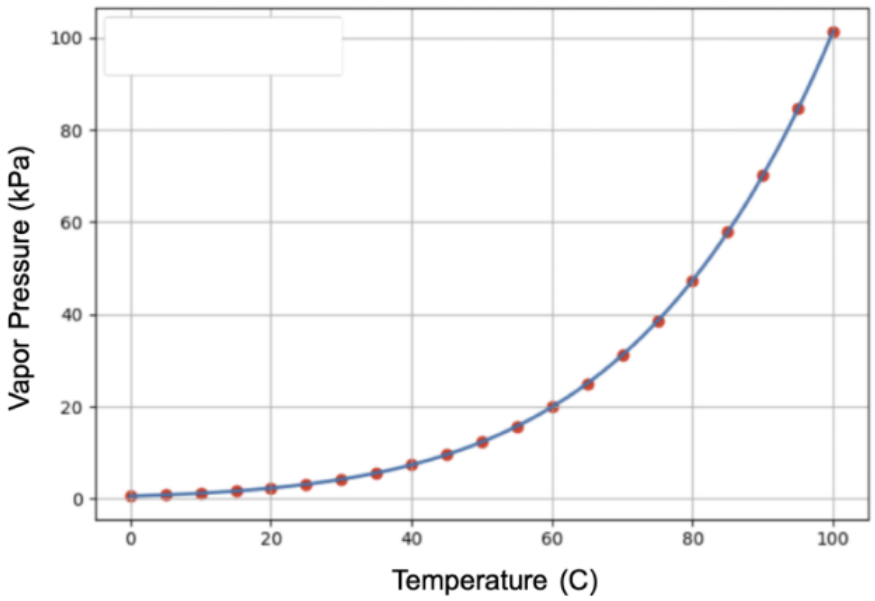


Figure 10: The vapor pressure of water at given ambient temperatures

.

is 24.5 kPA and the vapor pressure of ethanol is 5.95 kPA. Then, the vapor pressure of acetone at room temperature should be the same as water at 60 C. In an effort to make the water evaporation rate match the acetone evaporation rate at room temperature, I placed a swollen 2:98 gel in an oven at 60 C. I used my iPhone camera to take pictures of the gel every two minutes for a total of an hour. I did need to open the oven every two minutes to take these pictures, so the temperature did not stay constant for the entire process.

5 Results

5.1 Initiation Times

5.1.1 Varying Thickness

Graphing crack and peel initiation times for different gel thicknesses showed that time was independent of thickness and set only by solvent. Crack (Figure 11a) and peel (Figure 11b) initiation times for acetone were much quicker than ethanol for all thicknesses. The average time difference between ethanol and acetone cracking was ≈ 200 seconds. Crack and Peel initiation times are consistent with a constant, but large error bars do not rule out a weak dependence. What is abundantly clear is that acetone causes cracking and peeling to occur faster than ethanol.

This trend follows for relaxation times (Figure 11c). Again, gels swollen in acetone will start relaxing back into their original state much faster than gels swollen in ethanol, no matter what their initial thickness was. On average, the time difference between ethanol and acetone is ≈ 1000 seconds, which is larger than the crack and peel initation time differences. This lines up with what I was observing qualitatively. While all videos were taken for an hour, gels swollen in acetone had often completely finished drying out within half of that time, while gels swollen in ethanol needed the full video duration. There may be a weak dependence of relaxation initiation time on gel thickness but more trials are needed to confirm.

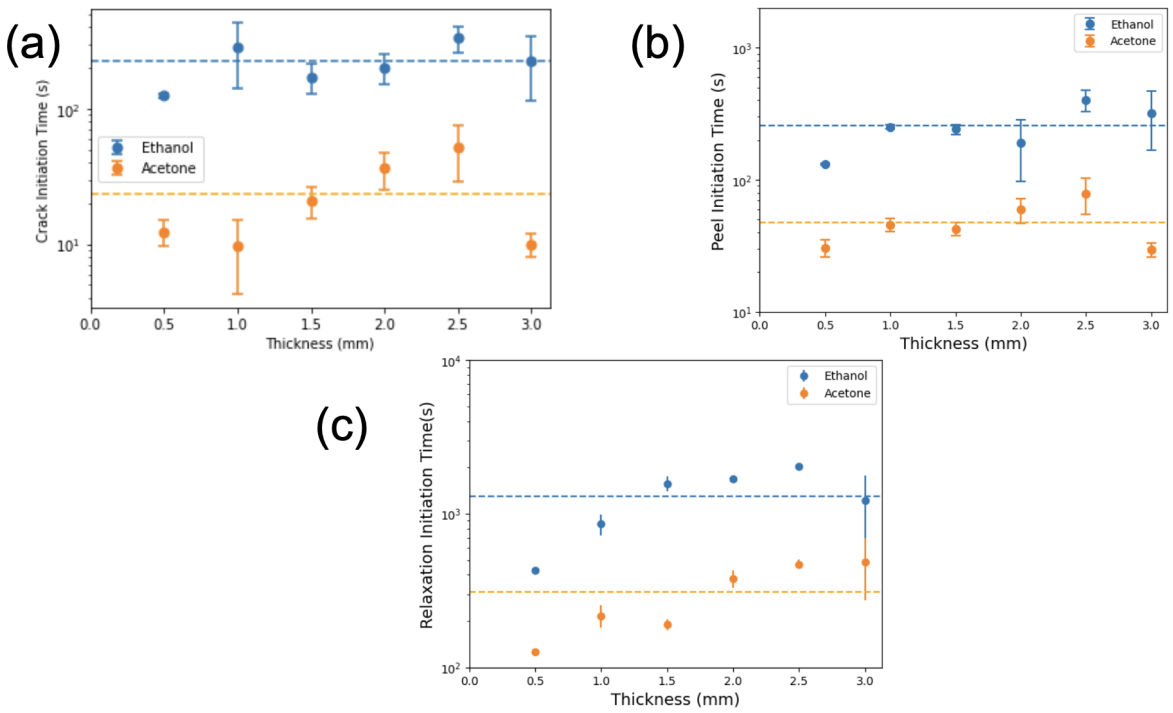


Figure 11: Initiation times for (a) cracking, (b) peeling, and (c) relaxation when varying the thickness of the gel from .5mm to 3mm.

5.1.2 Varying Concentrations

For the most part, the same results are visible across varying PEGDA concentrations as varying thicknesses. Gels swollen in Acetone are faster to crack, peel, and relax than their ethanol swollen counterparts (Figure 12). While there is a little bit more variation among gels with a smaller concentration of PEGDA, the trends still hold.

There is also not a clear enough trend to show that initiation times vary with respect to PEGDA concentration. This is a little bit surprising, as the hypothesis before conducting this experiment was that varying concentrations would have a tangible effect on behavior since the internal network makes an impact on the gels ability to handle the stress of solvent evaporation and absorption. While it is by no means constant, there is no clear pattern between times and PEGDA percentage. Excluding some early inconsistencies, the graphs for varying concentrations and varying thicknesses effectively show the same exact thing. The average difference between solvents for the crack initiation time is ≈ 300 seconds and the average relaxation initiation time difference is ≈ 850 seconds.

5.1.3 Varying Initial Thickness

5.2 Peel Thickness

Unlike the timescales of different processes, the solvent does not seem to have any impact on peel thickness (Figure 13a) for the top layer of the gel. When varying the heights of the gels the peel thickness appears very scattered across swollen heights and solvents. I believe that this large scattering is due, at least in part, to the difficulty in taking measurements. Video imperfections result and shadows from lights may have resulted in unclear distinctions of the peel boundaries. There are no clear patterns, and the range of thicknesses is extremely large in comparison to the heights of the gels. Peel thickness does not correlate with height of the gel, nor does it vary with the solvent.

A similar concept emerges when varying concentrations (Figure 13 b). No matter the percent of PEGDA in a gel, the peel thickness does not seem to change. Again, it also does not appear to rely on the solvent.

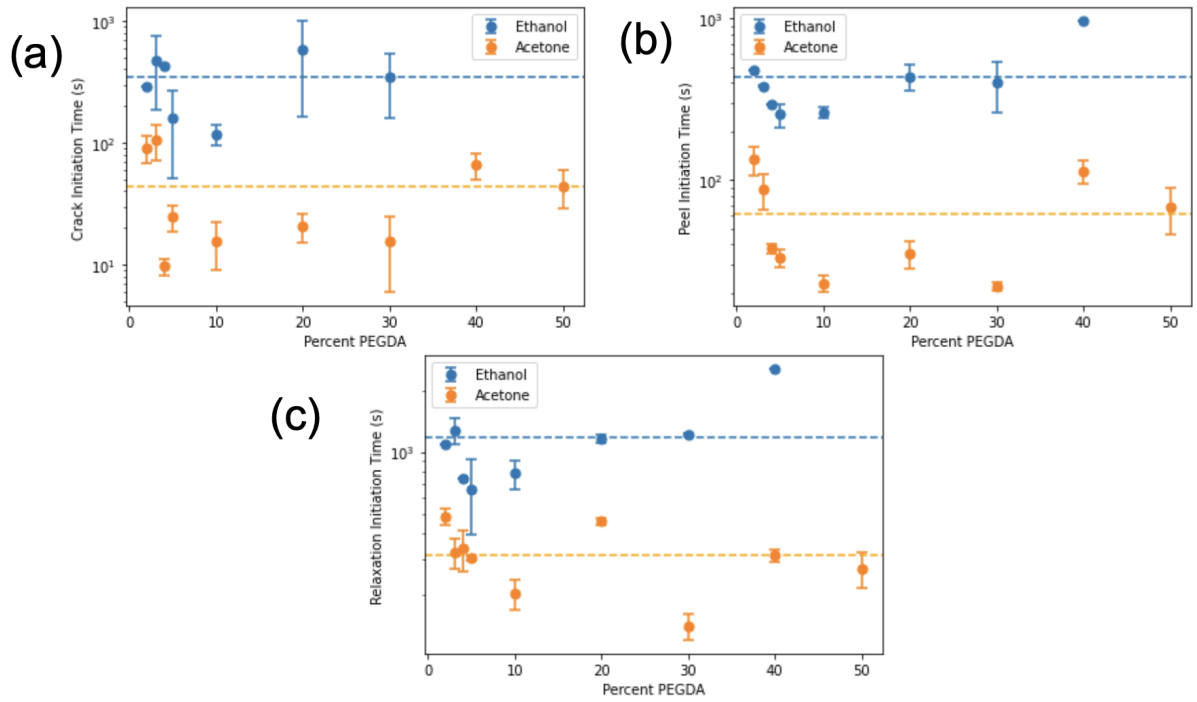


Figure 12: Initiation times for (a) cracking, (b) peeling, and (c) relaxation when varying the the molar concentration from 1% to 50% PEGDA.

Although there is an extremely large range of peel thicknesses (especially considering all these gels started at a height of 1mm), there are no clear patterns in the graph. The solvent may impact how fast things happen, but it may not impact the visible behavior of cracks and peels. Additionally, the average peel thicknesses across all thicknesses, concentrations, and solvents are pretty similar at about .5mm.

5.3 Maximum "Fluff"

Contrary to peel thickness, maximum "fluff" does seem to vary with respect to the swollen height (Figure 14a). The normalized "fluff" appears to be inversely related to swollen height. The thinner a gel, the higher the peels will reach in comparison to its starting height. Again, the solvent does not seem to have any impact on behavior except for a few outliers at a low height.

When varying only the concentration and keeping the initial height constant, the behavior does seem to align with the previously discussed peel thickness (Figure 14b). While the data is quite scattered, there does not appear to be any correlations in regards to concentration or solvent. The solvent does not impact the peeling or relaxation process except to set the timescale.

5.4 Light Intensity

The intensity graph shows the crack density when varying gel thickness (Figure 15a). A smaller intensity means that the gel cracked more since the surface of the gel is darker. Therefore a larger light intensity means a smaller crack density. As shown, gels with a higher thickness cracked more than those with a lower one. This is also shown qualitatively (Figure 15c). That being said, not all of these cracks occur on the surface of the gel. It is likely that the top layers of the gel all crack the same amount, but thicker gels have more layers so they may have a larger number of total cracks. While there may be some correlation between solvent and crack density, the data is not conclusive enough to make that judgment.

Figure 15b shows the relationship between intensity and concentration. As shown, there is not a clear correlation between concentration and amount of cracks. Yet, contrary to every other behavior discussed,

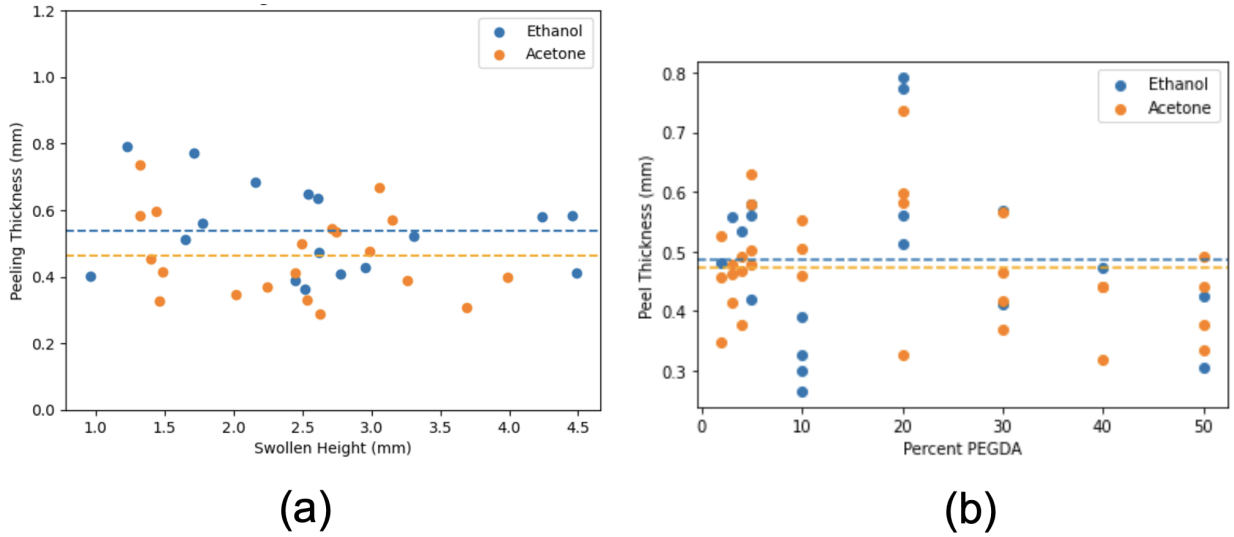


Figure 13: Thicknesses of the top layer of peels that emerge from the evaporation process for (a) varying thicknesses and (b) varying concentrations. Measurements are taken at the first moment the peel is visible.

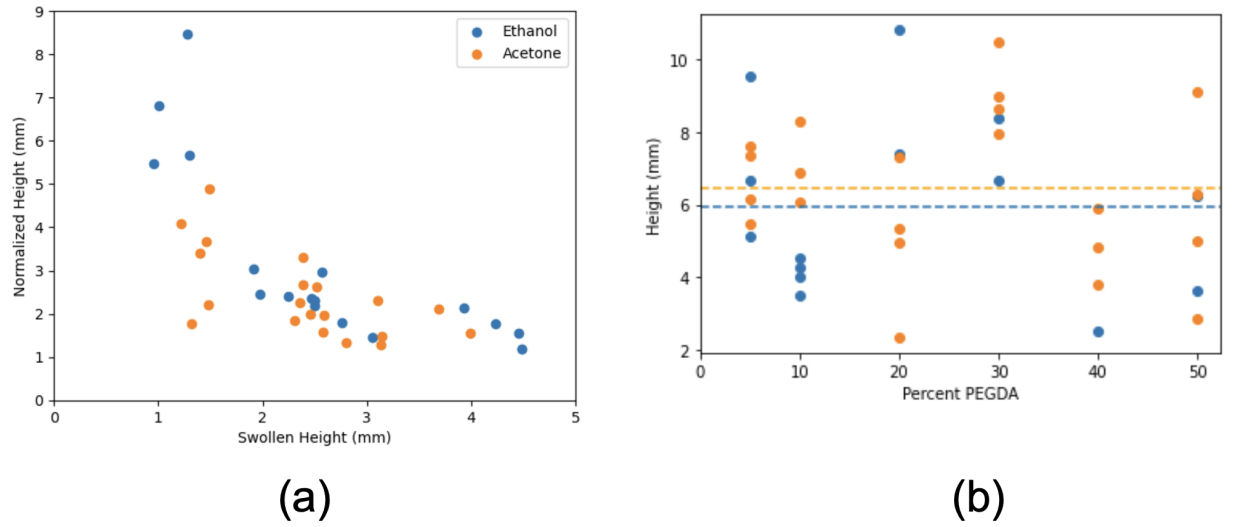


Figure 14: Maximum "Fluff" for varying thicknesses (a) and concentrations (b). Measurements are taken at the largest possible height. The fluff is graphed in relation to the thickness when the gel is fully swollen (a) and normalized. (b) is not normalized since all gels started at the same initial thickness of 1mm.

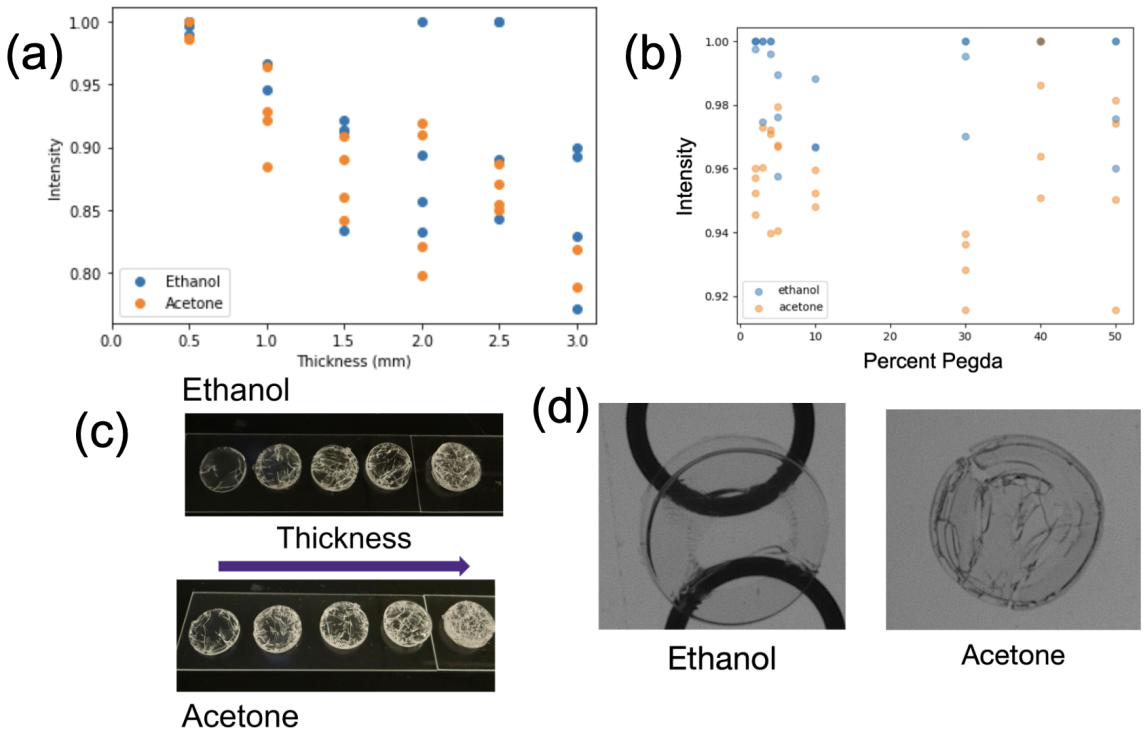


Figure 15: Light Intensity when the most amount of cracks are visible when varying thickness (a) and concentration (b). Since cracks are darker, a lower light intensity corresponds to a larger amount of cracks on the gel. In (b), a darker circle means that multiple gels had the same intensity value. An intensity of 1 corresponds to a gel that did not crack. The same trends are shown qualitatively- (c) shows an increasing amount of cracks as the thickness increases and (b) shows an increasing amount of cracks using acetone as a solvent. All gels in this image are 20:80 concentration, with (a) ranging in thickness from 1mm to 3mm and (b) is 1mm thick.

there is a correlation between the amount of cracks and the solvent. Gels swollen in acetone cracks more- and more often- than those swollen in ethanol. Qualitatively, the graph aligns with the samples for 1mm gels at 20:80(Figure 15d).

5.5 Speed of Cracks

I completed preliminary measurements exploring crack velocity as a function of solvent under one sample composition (20:80). I found that in an ethanol swollen gel, cracks moved at 434.1 mm/sec +/- 511.3 mm/sec, and in an acetone swollen gel at 5950.4 mm/sec =/- 2122.3 mm/sec. Crack velocities for gels swollen in acetone are, on average, much faster than those for ethanol. Additionally, the cracks themselves look fundamentally the same across solvents. Even with a large standard deviation, there is an order of magnitude difference between these two values. This agrees with the results from peel thickness and maximum fluff, where solvents change timescale of all behaviors but may not change the actual behaviors themselves.

5.6 Water Evaporation

5.6.1 Room Temperature

Water evaporation at room temperature yielded an entirely new behavior than its acetone and ethanol counterparts, as the gel started completely breaking (Figure 16). I call this behavior the “cinnamon roll”



Figure 16: A 2:98 water swollen gel evaporating at room temperature. The gel broke off into curved pieces (like a cinnamon roll) instead of cracking or peeling as seen with ethanol or acetone.

because the curvature of the broken pieces resembles the swirl of a cinnamon role. Not all gels broke in this specific pattern, but the ones that did break did have a similar concept of an outer piece breaking off. Breaks did not completely penetrate the gels. Gels at a higher concentration took a shorter time to finish drying, but all room temperature evaporation ≈ 24 hours.

5.6.2 Oven

I completed preliminary measurements for water swollen gels drying out at different temperatures under one sample composition (2:98). As mentioned previously, the evaporation rate of acetone in room temperature is about the same as water in 60 $\deg C$. By adjusting evaporation rates to make them equal, gels swollen in acetone and water will behave similarly (Figure 17). While tests were only done for a single composition and thickness, these results point to the fact that evaporation rate is likely the control parameter for the mechanical response of the gel to drying stresses.

6 Discussion

6.1 Concentration and thickness have minimal impact on behavior

The physical geometry of a gel has minimal impact on the cracking and peeling patterns displayed. With the exception of maximum fluff (Figure 14a), there are no identifiable patterns for gels of differing concentrations and thicknesses. This includes peel thickness, cracking on the top surface of the gel, and the speed of behaviors initiating. I originally hypothesized that increasing the concentration of PEGDA would increase maximum fluff or peel thickness because the gels would not be able to accommodate the stress through deformations, which would therefore cause more of it to break off. This has shown to not be the case (Figures 13b and 14b).

The two behavior differences were maximum fluff and amount of cracks in relation to gel thickness (Figures 14a and 15a). As mentioned previously, it is believed that the increased number of cracks per increased thickness relates to the higher number of layers capable of cracking, and the amount of cracks on the surface is the same across all gels. That leaves the normalized maximum fluff as the only substantive

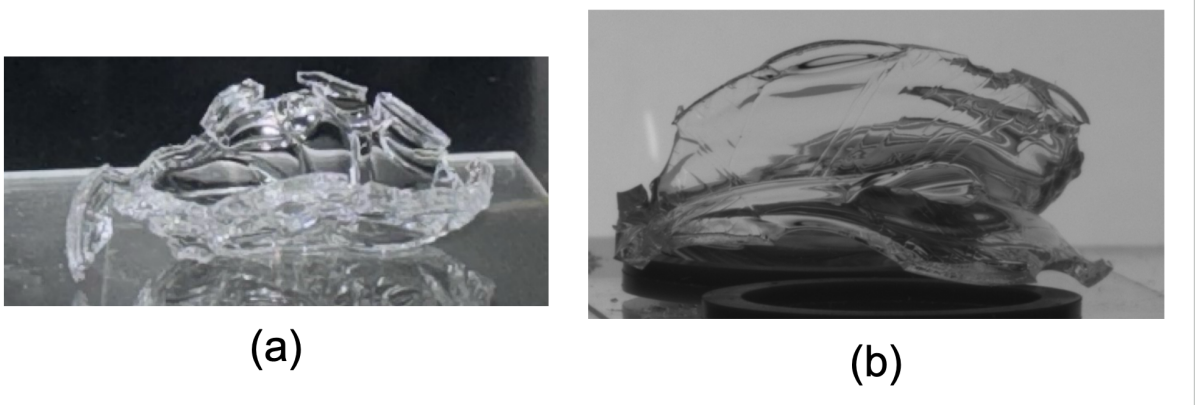


Figure 17: 2:98 gels swollen in (a) water and (b) acetone. (a) is placed in a 60 deg C oven while (a) is at room temperature. Due to the differing vapor pressures of water and acetone, the evaporation rates of both processes are the same. This is demonstrating by similar behaviors occurring between the two images.

difference across all samples, meaning that behavior cannot be effectively determined by gel geometry.

6.2 Acetone and Ethanol as solvents behave mostly the same

There are two main behavior differences between acetone and ethanol, which includes the speed at which behaviors occur and the extent to which behaviors occur. The behaviors themselves, however, appear to be similar across solvents. The solvent sets the timescale, but does not determine much else of the evaporation process behaviors. An ethanol swollen gel and an acetone swollen gel delaminating look effectively the same.

Acetone is a much more volatile solvent, so the increased speeds of behavior were not surprising to me. The increased probability of behaviors occurring and an increased number of cracks (Figure 15b) did disagree with my earlier conclusions. It did, however, lead me to believe that solvents must be the cause of gel behaviors since geometry appeared to make little impact.

6.3 Evaporation Rate is the key difference in determining behavior

The main takeaway from my experiments is that evaporation rate must be the reason for behavior differences such as the amount of cracks. Acetone and ethanol have several differences between them, such as the slight difference in size, interactions with different molecules, and a different chemical composition. That being said, the largest difference is the fact that acetone has a vapor pressure four times as high as ethanol's.

To test my hypothesis, I wanted to try only changing the vapor pressure by conducting water experiments. At an extremely low vapor pressure (more than two times less than ethanol at room temperature), gels swollen in water will not crack or peel at all. When placed in an oven to increase vapor pressure, their behavior drastically changes. Additionally, this does not vary with concentration. At all concentrations tested, the gel did not crack or peel when evaporating at room temperature and only cracked or peeled when the evaporative flux increased.

Interestingly, Chung et al found that the cutoff point for peeling occuring is 40 deg C when swelling a PDMS gel in hexane [5]. In that case, the vapor pressure would be 37 kPA, which is higher than the 24.5 kPA for acetone at room temperature. The difference in gel composition may explain the difference in exact cutoff points, but the idea of a specific evaporation rate determining gel behavior lines up with previous work.

This is an ongoing project, and more information is needed to definitively state that evaporation rate is the reason for behavior differences. Water evaporation at room temperature needs to be quantified to fully understand what patterns (if any) are taking place and if behavior could be predicted. Additionally, I am curious to see what would happen if water evaporation were to take place at different temperatures and evaporation rates beyond room temperature and 60 C. This last question is actively being discussed

and worked on, and I hope to see some progress before my time with the lab is complete. That being said, with what we know now, it seems increasingly likely that evaporative flux is the most important factor in gel drying behavior.

7 Conclusion

In this study I utilized hydrogels in the shape of a disk and swelled them in various solvents to measure behavior of solvent evaporation. By varying disk thickness, crosslinker concentrations, and evaporation rates of various solvents I concluded that evaporative flux is the reason for differing behavior of hydrogel delamination. This result is semi-surprising since I initinally thought that crosslinker concentrations would have a greater impact. Nevertheless, it presents a clear motive and reasoning for unusual behavior.

Before the work presented here is published, there needs to be more careful experimentation of water evaporation of hydrogels. Currently, I am assisting with building an oven that will allow us to take clear videos that are easily quantifiable, as well as manipulate temperature. Properly analyzing delamination at other temperatures will provide more evidence that evaporation rate is indeed the main factor in determining behavior. Additionally, I need to figure out the additional ways to quantify gel behavior that is not cracking or peeling, such as measuring curvature or breakage.

8 Acknowledgments

This work was made possible by the Northwestern Office of Undergraduate Research, NSF/DMR (Award 2311698), and the Baker Program in Undergraduate Research.

This thesis was a labor of love, and I am so thankful to everyone who helped me get to this point. Big or small, there are so many people who provided invaluable support that I would not be here without. To my mentor Samira Khan, thank you so much for introducing me to hydrogels and helping me every step of the way. Your patience, guidance, and encouragement ensured that I would be able to make this project my own. To everyone I overlapped with in Driscoll Lab, thank you so much for your feedback, advice and support. Specifically, I would like to thank Audra, Isabella, Abby, Carly, Charlie, and Shih-Yuan. To Professor Driscoll, I could not ask for a better undergraduate PI. Thank you for your understanding, continued presence, and guidance in this project. Finally, I am so grateful for my friends, family, and everyone in the Physics & Astronomy Department for the past four years. I have been able to travel to conferences, give talks, present posters, and conduct research. None of these opportunities would have been possible without everyone's support.

References

[1] Todd Hoare Ali Affar Fei Xu. "Poly(ethylene glycol) (PEG) and Synthetic PEG Derivatives for Tissue Engineering and Cell Delivery". In: *Material Matters* 13.3 (2018).

[2] Emilia Bakaic, Niels MB Smeets, and Todd Hoare. "Injectable hydrogels based on poly (ethylene glycol) and derivatives as functional biomaterials". In: *RSC advances* 5.45 (2015), pp. 35469–35486.

[3] Jeffrey A Beamish et al. "The effects of monoacrylated poly (ethylene glycol) on the properties of poly (ethylene glycol) diacrylate hydrogels used for tissue engineering". In: *Journal of Biomedical Materials Research Part A: An Official Journal of The Society for Biomaterials, The Japanese Society for Biomaterials, and The Australian Society for Biomaterials and the Korean Society for Biomaterials* 92.2 (2010), pp. 441–450.

[4] Roberta Cassano, Silvia Mellace, and Sonia Trombino. "Responsive polymer-biomacromolecule conjugates for drug delivery". In: *Stimuli Responsive Polymeric Nanocarriers for Drug Delivery Applications, Volume 1*. Elsevier, 2018, pp. 433–452.

[5] Jun Young Chung, Ido Regev, and L Mahadevan. "Spontaneous exfoliation of a drying gel". In: *Soft matter* 12.37 (2016), pp. 7855–7862.

[6] Tzu-Chuan Ho et al. "Hydrogels: properties and applications in biomedicine". In: *Molecules* 27.9 (2022), p. 2902.

[7] Kelsey-Ann Leslie et al. "Gel rupture during dynamic swelling". In: *Soft Matter* 17.6 (2021), pp. 1513–1520.

[8] Nikolaos A Peppas et al. "Poly (ethylene glycol)-containing hydrogels in drug delivery". In: *Journal of controlled release* 62.1-2 (1999), pp. 81–87.

[9] Shouye Sun et al. "Drug delivery systems based on polyethylene glycol hydrogels for enhanced bone regeneration". In: *Frontiers in bioengineering and biotechnology* 11 (2023), p. 1117647.

[10] Huaping Tan et al. "Novel multiarm PEG-based hydrogels for tissue engineering". In: *Journal of Biomedical Materials Research Part A: An Official Journal of The Society for Biomaterials, The Japanese Society for Biomaterials, and The Australian Society for Biomaterials and the Korean Society for Biomaterials* 92.3 (2010), pp. 979–987.

[11] Alyssa VanZanten et al. "Unconstrained dynamic gel swelling generates transient surface deformations". In: *Soft Matter* 20.34 (2024), pp. 6742–6753.

[12] Xu Xue et al. "Recent advances in design of functional biocompatible hydrogels for bone tissue engineering". In: *Advanced Functional Materials* 31.19 (2021), p. 2009432.

[13] Dayong Yang. *Recent advances in hydrogels*. 2022.

[14] Kaihuan Zhang et al. "Creating an interface: rendering a double-network hydrogel lubricious via spontaneous delamination". In: *ACS applied materials & interfaces* 11.28 (2019), pp. 25427–25435.