Chemical Engineering Science, autumn 2023, https://doi.org/10.1016/j.ces.2023.119282

Pipe rheology of wet aqueous application foams

Antti I. Koponen[1*], Janika Viitala[1], Atsushi Tanaka[2],

Baranivignesh Prakash[1], Olli-Ville Laukkanen[1], and Ari Jäsberg[1],

[1]VTT Technical Research Centre of Finland Ltd, Koivurannantie 1, 40400 Jyväskylä, Finland
[2]VTT Technical Research Centre of Finland Ltd, Biologinkuja 7, 02044 Espoo, Finland

* Corresponding author: Antti.Koponen@vtt.fi

Abstract

Foam application of chemicals to the wet web is currently being developed for the paper and board industry. An important part of this work is to understand the rheology of the used application foams. Polyvinyl alcohol (PVOH) is widely used as a strength additive in paper and board, and it was the main surfactant in this study. The PVOH foam density varied between 100 kg/m^3 and 300 kg/m^3 and the dosage of PVOH varied between 0.5% to 6%. The foam viscosity and slip flow were determined with a pipe rheometer using three pipe diameters. The slip velocity was quantified by recording the foam motion in the vicinity of the wall of an acrylic pipe with a high-speed video camera. A measurement setup was also built for measuring the slip flow indirectly in opaque pipes. General formulas for the foam viscosity and slip flow, based on several physical quantities describing both the foam and the base liquid, were obtained using dimensional analysis. Specifically, dimensionless shear stress and dimensionless wall shear stress were found to be proportional to certain powers of the capillary number and slip capillary number, respectively. The contribution of the slip flow to the total flow rate was significant, especially with lower flow rates when most of the volumetric flow was due to the slip. In the literature, many papers have suggested that there is no slip flow in steel pipes. Our results suggest that this is due to the high pipe roughness used in those works. In our measurements, the slip velocity of a smooth-walled steel pipe was equal to the slip in an acrylic pipe. The obtained viscosity and slip models form a solid basis for developing and running various industrial processes including foam application processes. For new foam recipes, quite a small number of rheological measurements are needed to determine the model parameters.

1. Introduction

Liquid foams are two-phase systems composed of gas bubbles surrounded by a continuous liquid-surfactant solution, where the role of the surfactant is to stabilize the foam by lowering the surface tension between the gas and liquid phases (Weaire and Hutzler, 1999). When the (volumetric) gas content φ is below the jamming transition point φ_J the gas bubbles are spherical and relatively free to move. In this case, the foam is called bubbly liquid. For monodisperse bubbles φ_J = 0.64 (Saint-Jalmes and Durian, 1999), but in practice, the foams are usually polydisperse and the jamming transition point is higher - slightly below 0.7 (Farr and Groot, 2009)(Lexis and Willenbacher, 2014). The distinction between wet and dry foams is not uniquely defined but foams with φ < 0.95 are usually considered wet foams (Furuta et al., 2016). Above the jamming transition point, in wet foams, the bubbles are still approximately spherical whereas in dry foams they are polyhedral.

Foams have several unique and useful properties (Schramm, 2005). The density of the foam can be controlled by the air content - with high air content foams can be made very lightweight. Above the jamming transition point, foams have yield stress, which immobilizes the foam under low-stress

forces. Foams have also a high liquid-gas surface area, which can be utilized in transport processes. The foams can also be stabilized by using polymers or small particles.

Foams have applications in many industrial systems. In many cases, the foam itself is the final industrial product, such as a fire-fighting foam, a food foam, or a pharmacy/personal care product. However, foams are also used as a temporary medium in many industrial processes – e.g., as a carrier medium of chemicals and solids. In flotation processes, bubbly liquids are used for separating solids from the fluid phase (Nguyen and Schulze, 2003). In the oil and gas industry, drilling foams are used to remove and clean the drill cuttings from the downhole (Lyons et al., 2020). In the nonwoven and paper and board industry the traditional carrier fluid, water, can be replaced with aqueous foams as the carrier medium of fibers (Hjelt et al., 2021). This leads to improved sheet uniformity and decreases the energy needed in the drying of the sheet due to the decreased usage of water. In the textile industry, the foam-assisted application is used for spreading chemical solutions or particle dispersions on fabric surfaces (Sen, 2007)(Kentta et al., 2022).

Foams possess not only significant practical relevance but are also academically interesting as a subject of study. A highly relevant area of research for the process industry is the study of the rheology and flow behaviour of foams (Barigou and Deshpande, 2000) (Herzhaft, 1999) (Gardiner et al., 1999) (Heller and Kuntamukkula, 1987)(Dollet and Raufaste, 2014)(Cohen-Addad and Höhler, 2014). Foams have complex rheological behaviour that can change significantly with foam structure and processing conditions. On the other hand, different foams can also exhibit universal properties. Foams are e.g., generally shear-thinning fluids, and their viscous behaviour can be described with good accuracy with the Herschel–Bulkley model (Princen and Kiss 1986)(Höhler and Cohen-Addad, 2005)

$$\tau = \tau_y + K\dot{\gamma}^n \tag{1}$$

Above, τ is the shear stress, τ_y is the yield stress, $\dot{\gamma}$ is the shear rate, K is the consistency index, and n is the flow index. In many cases, the used shear stress is clearly higher than the yield stress, and the viscous behaviour is described well by the simple power law

$$\mu = K\dot{\gamma}^{n-1} \tag{2}$$

Notice that in Eqs. (1) and (2), parameters K and n can be functions of many quantities including air content, surfactant solution viscosity and surface tension, as well as bubble size.

The no-slip boundary condition, which holds for most one-phase continuum fluids, does not always hold for foam flow (Denkov et al., 2005) (Briceño and Joseph, 2003)(Marze et al., 2008). This is due to a narrow lubricating pure-liquid layer that develops at the solid walls. A possible explanation for the development of the slip layer is the shear forces dragging out liquid to the wall from the regions between the bubbles (Thondavadi and Lemlich, 1985)(Gardiner et al., 1999). The ensuing slip flow needs to be taken into account when measuring the shear rheology of foams. Slip flow has also practical relevance, as it can increase the flow rate *e.g.* in pipes significantly. The magnitude of the slip flow depends on the wall shear stress and the foam properties. The slip flow depends also on the roughness of the solid walls (Marze et al., 2008). Strong slip flow has been reported both for glass and acrylic pipes (Jäsberg, Selenius, and Koponen 2015a)(Thondavadi and Lemlich 1985). On the other hand, several papers have reported that slip flow was not seen for steel pipes (Thondavadi and Lemlich, 1985)(Harris and Reidenbach, 1987) (Larmignat et al., 2008). Finally, notice that wall slip depends also on the surface chemistry. Wall slip is higher on hydrophilic surfaces and lower on hydrophobic surfaces (Omirbekov et al., 2022).

In the paper and board industry, chemicals are conventionally dosed to the fiber stock before forming. However, foam application of chemicals to the wet web would offer several advantages (Kinnunen-Raudaskoski et al., 2014) (Kenttä et al., 2014)(Kinnunen-Raudaskoski et al., 2017) (Bliss et al., 2021). Strength-additive induced fiber flocculation would be eliminated, and the retention of chemicals on the fiber surfaces would be close to 100% with high dosages and low adsorbing tendencies. Foam application also allows dealing with high-viscosity solutions, and the penetration depth of the applied material to the porous substance can be controlled. Notice that a problem with a close relative of foam-assisted application, spray application, are the creation of mist, limited dosage levels of chemicals due to the difficulty of dealing with highly viscous fluid, the high clogging tendency of the spray nozzles, and problems in obtaining uniform coverage of the base with the sprayed chemical.

The current work was part of a public multi-company project where foam application was developed for the paper and board industry (Hjelt et al., 2023)(Oksanen et al., 2023). An important part of this project was the study of the shear rheology, slip flow and pumping of application foams in laboratory and pilot environments. The rheological studies focused on wet foams and the foam density varied between 100 kg/m^3 and 300 kg/m^3. Polyvinyl alcohol (PVOH) was used as the main surfactant, as it is widely used by the paper and board industry as a strength additive (Gottberg et al., 2019). The dosage of PVOH varied between 0.5% to 6%. Due to the ageing of foam and slip flow, rheological analysis of the application foams was not feasible with traditional rheometer geometries, and a pipe rheometer was used for this purpose (Larmignat et al., 2008) (Enzendorfer et al., 1995) (Ari Jäsberg et al., 2015a). Notice that preliminary results for the PVOH foams, based on a subset of data that constituted one-third of the total dataset, were published in (Jäsberg et al., 2023).

The manuscript has been organized in the following way: First, we will introduce the reader to the pipe rheometer, used surfactants and a setup for studying slip flow in opaque pipes. Then we present examples of pressure loss, slip flow and viscosity data in different process conditions and look at the entire dataset. Next, we will perform dimensional analysis for foam viscosity and slip flow to obtain generic formulas that are then used in the analysis of the measurement data. The obtained rheological models are then tested with an experimental surfactant developed for foam application. Then we will present the results of the slip behavior of foam in a smooth steel pipe. Next, we will test the obtained rheological models using a 30 m long pipe with a foam made of a mixture of an experimental surfactant and a widely used dry strength additive. Finally, we will discuss our results, and finish the manuscript in our concluding remarks.

2. Experimental

Due to their high interfacial free energy, foams are thermodynamically unstable, and the gas and liquid phases tend to gradually separate (Weaire and Hutzler, 1999). This ageing process of the foam is slowed down by the surfactant, but for many foams, it is too rapid for the use of traditional rheometer geometries. Moreover, even with a stable foam, slip flow can be high at the solid walls of the flow geometry and the interpretation of the rheometer results may be challenging (Kroezen et al., 1988) (Marze et al., 2008). For these reasons, foam rheology was studied in this work by using pipe flow. In this case, the foam behaviour can be studied shortly after the foam generation, and the slip flow can be reliably measured. In the literature, several pipe diameters have often been used, and the slip velocity has been estimated by using either the Mooney or Oldrey and Jastrzebski analysis (Enzendorfer et al., 1995)(Gardiner et al., 1998). However, if the pipes are transparent, slip velocity can also be measured explicitly by high-speed imaging (Ari Jäsberg et al., 2015a). In this study, we employed this method. The problem with this approach is that it can be applied directly only to

transparent pipes. For this reason, we developed also a setup for measuring the slip flow indirectly in opaque pipes. Notice that the measurement of yield stress is in principle possible with a pipe rheometer (Ari Jäsberg et al., 2015a), but it was left out of the scope of this study. To test the obtained rheological models we performed pressure loss measurements in a 30 m-long pipe.

Pipe rheometer

The laboratory-scale pipe flow test environment (pipe rheometer) is shown in Figure 1. The foam was generated and pumped to the test pipes with a foam mixer manufactured by Hansa Industrie-Mixer GmbH & Co. KG (see Supplementary material). The mixer consists of a pumping unit that enforces a constant volumetric flow rate Q_L of the liquid-surfactant solution and a foaming unit. In the foaming unit, a well-controlled amount of compressed air is first added to the liquid and then a rotor-stator mixer (see Supplementary material) disperses the air into bubbles, thus generating the foam. The bubble size can be adjusted by controlling the rotation speed of the rotor in the rotor-stator element. The user sets the mass flow rate and the foam density. Based on these values and the absolute pressure measured at the point of air addition, the device adjusts the airflow so that the density of foam discharging at the end of the flow line to 1 atm pressure stays constant.

The volumetric flow rate Q_F, absolute back pressure P_F, and bubble size distribution of the foam were measured at the outlet of the foam generator with a magnetic flow meter Siemens SITRANS FM MAG 1100 DN6, differential pressure transmitter Endress+Hauser Deltabar PMD235, and Pixact online foam monitoring device (Koponen et al., 2019), respectively. Next, the foam flowed into one of the three acrylic horizontal pipes chosen by operating manual valves at the pipe inlets. The length of the pipes was 1.5 m and their inner radii were R = 4.0, 6.0, and 9.5 mm. The viscous pressure drop was measured over a fixed span of pipe, after which the flow discharged to ambient room air pressure. The span was 0.3 m for the smallest R = 4.0 mm pipe, and 1.0 m for the other two pipes.

The entrance length of laminar non-Newtonian flow is obtained from the formula (Poole and Ridley 2007)(Lambride et al. 2023)

$$L_e/2R = [(0.246n^2 - 0.675n + 1.03)^{1.6} + (0.0567\,\mathrm{Re})^{1.6}]^{1/1.6} \quad (3)$$


where Re is the Metzner-Reed Reynolds number (Metzner and Reed, 1955)(Barigou and Deshpande, 2000)

$$\mathrm{Re} = \frac{8\rho v^{(2-n)} R^n}{K\left(3+1/n\right)^n} \quad (4)$$

Above R is the pipe radius, and K and n are the consistency index and flow index, respectively (see Eq. (2)). The highest Re was 500 (see Figure 19 and Figure 20), and the entrance length was smaller than 50 cm. Thus, the flow was always laminar and fully developed in the measurement pipe.


The slip velocity was quantified by recording, through the transparent acrylic pipe, the motion of foam bubbles in the vicinity of the pipe's inner wall with a high-speed video camera (Ari Jäsberg et al., 2015a). The slip velocity was calculated as the average speed of the bubbles in the mean flow direction. No-slip condition is indicated by the bubbles being stationary. Based on the variation in the calculated slip velocity during each trial point, the error in the slip velocity was estimated to be less than 3%. The flow rate varied in the pipes between 0.4 l/min and 11 l/min. The Weissenberg-

168 Rabinowitsch correction was applied to the measured flow rate–pressure loss data for calculating the
169 real viscosity vs. shear rate behaviour of the foam (see below).

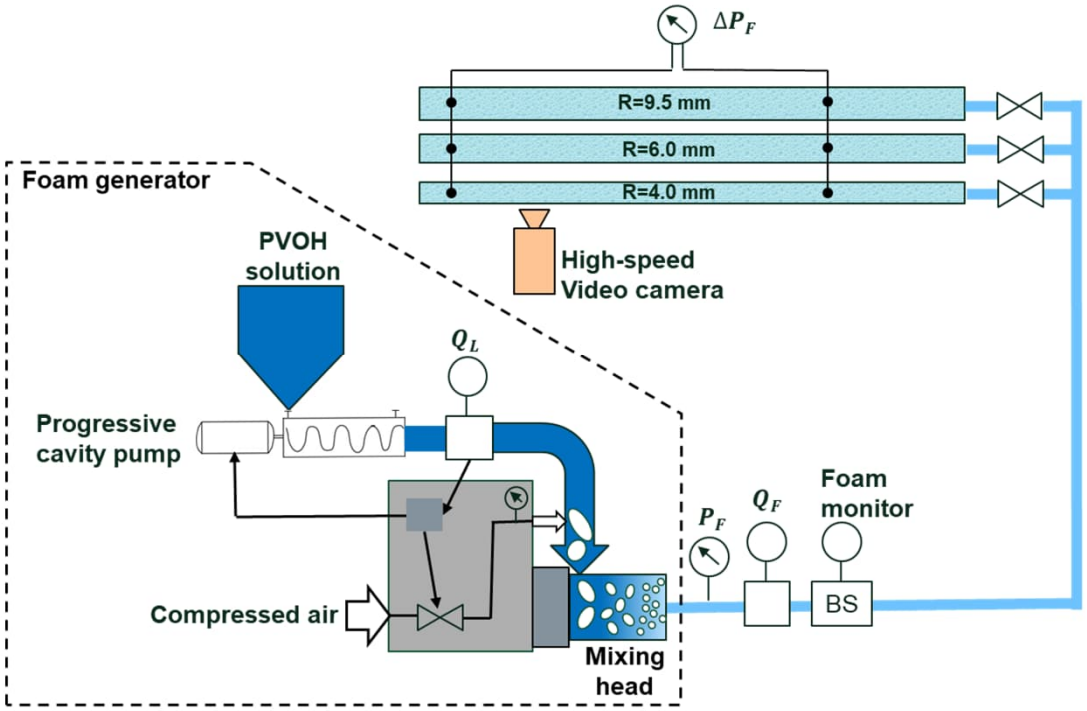

170

171 Figure 1 Schematic drawing of the components in the experimental setup. The foam generator is
172 shown inside the dashed polygon. The components outside the polygon are the flow line and the
173 measurements used for quantifying the flow rheology of foam. The setup contains the measurements
174 for the volumetric flow rate Q_L of the liquid surfactant, absolute back pressure P_F at the foam
175 generator outlet, the volumetric flow rate Q_F of the foam, the bubble size distribution (BS) of the
176 foam, and the pressure drop ΔP_F in the foam flow over a fixed span of the test pipe section (0.3 m
177 span for the $R = 4.0$ mm pipe, and 1.0 m span for the other two pipes). Figure from (Jäsberg et al.,
178 2023).

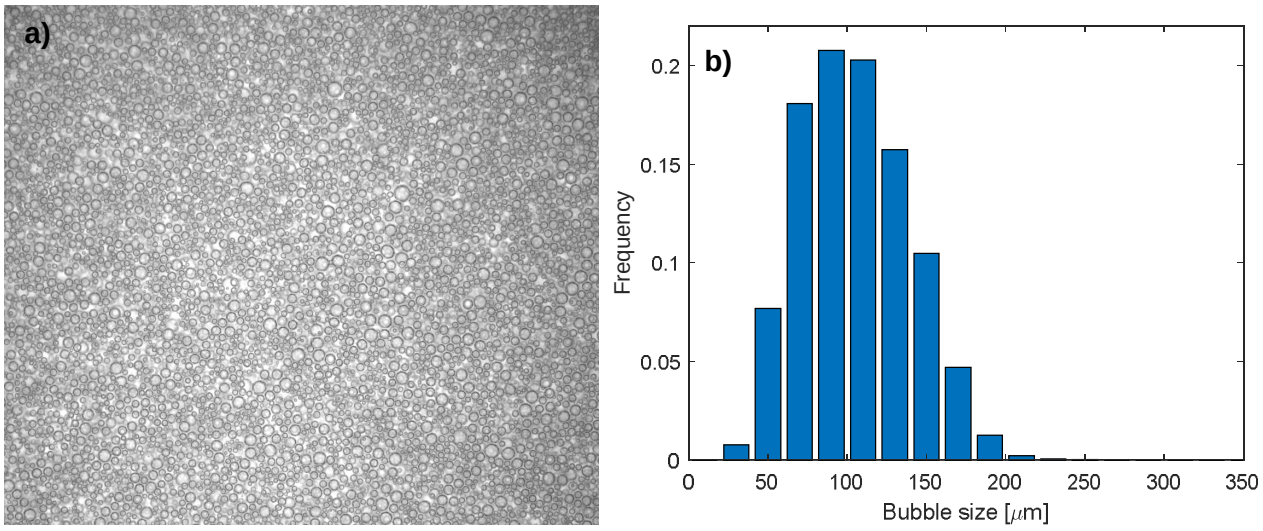

179

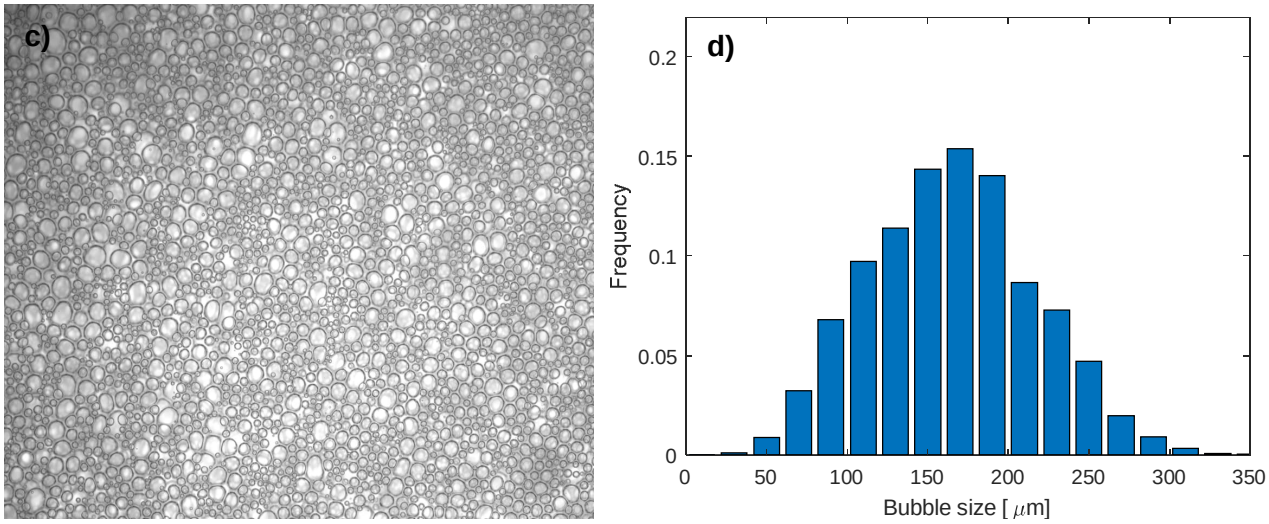


Figure 2 Images of PVOH foam, taken with the Pixact online foam monitoring device at an elevated pressure, and the corresponding bubble size distributions. PVOH concentration is 3%, the pipe radius is 6 mm and the mass flow rate in the pipe is 100 kg/h. a) and b) Bubble size (Sauter mean diameter) is 104 µm. At atmospheric pressure, foam density is 300 kg/m^3. c) and d) Bubble size is 165 µm. At atmospheric pressure, foam density is 100 kg/m^3. Image dimensions are 7.5 mm × 6.7 mm and pixel resolution is 3.5 µm.

We used as the mean bubble diameter the surface area-weighted average, i.e. Sauter mean diameter, which is inversely related to the total interfacial area per unit volume (Kowalczuk and Drzymala, 2016):

$$D = \frac{\sum_{i=1}^{n} n_i d_i^3}{\sum_{i=1}^{n} n_i d_i^2} \tag{5}$$

Analogous to emulsions, Sauter mean diameter should be used for wet foams (Herzhaft et al., 2005). For bubbly liquids, the volume-weighted average is preferred. Figure 2 shows two images of PVOH foams, taken with the Pixact online foam monitoring device, and the corresponding surface area weighted bubble size distributions.

As we use dimensional analysis for developing models for the foam viscosity and slip flow, we use below the air content instead of the foam density. As the air density is much smaller than the density of the liquid surfactant solution, air content is obtained with good accuracy from the formula (Larmignat et al., 2008)

$$\varphi \approx \frac{\rho_l - \rho_f}{\rho_l} \tag{6}$$

Here ρ_l is the liquid solution density and ρ_f the foam density.

Weissenberg-Rabinowitsch correction

The Weissenberg-Rabinowitsch correction was applied to the measured flow rate–pressure loss data for calculating the real viscosity vs. shear rate behaviour of the foam.

For stationary flow in a circular pipe, the wall shear stress is independent of the detailed flow profile and can be calculated from the measured pressure gradient as follows

$$\tau_w = \frac{R}{2}\nabla P \tag{7}$$

Above R is the inner radius of the pipe. Usually, the slip layer is very thin (a few microns) as compared with the mean bubble diameter or the pipe diameter. Thus, in the analysis, one can consider the foam filling the pipe fully, and the slip velocity is considered as a non-zero velocity boundary condition at the pipe wall. To extract material parameters one has to examine the foam flow in the frame of reference moving at the speed of the slip velocity. The measured slip velocity v_s is thus subtracted from the measured mean flow velocity v_{avg}:

$$v_{\mathrm{bulk}} = v_{\mathrm{avg}} - v_{\mathrm{s}} \tag{8}$$

The apparent shear rate of the foam $\dot{\gamma}_a$ at the immediate vicinity of the pure fluid slip layer is

$$\dot{\gamma}_a = \frac{4v_{\mathrm{bulk}}}{R} \tag{9}$$

The real shear rate $\dot{\gamma}$ at the pipe wall can be obtained by applying the Weissenberg-Rabinowitsch correction that takes into account the non-Newtonian features of the velocity profile (Mooney, 1931)(Morrison, 2001)

$$\dot{\gamma} = \dot{\gamma}_a \times \frac{1}{4}\left(3 + \frac{\mathrm{d}\ln\dot{\gamma}_a}{\mathrm{d}\ln\tau_w}\right) \tag{10}$$

Viscosity at a given shear rate is now obtained as the ratio of the wall shear stress to the real wall shear rate:

$$\mu = \tau_w / \dot{\gamma} \tag{11}$$

Materials

The main surfactant in this study was polyvinyl alcohol (PVOH) Kuraray Poval™ 6-88 (Gottberg et al., 2019). This PVOH grade has a low molecular weight and a degree of hydrolysis in the range of 86.7–88.7. The aqueous component was normal tap water, with salinity between 0.2–0.5 mmol/l. The PVOH solutions were prepared by cooking PVOH with tap water at a 10% concentration and diluting the cooled solution to concentrations of 0.5%, 1.0%, 3.0%, or 6.0% by weight. Before measurements, the concentration of each diluted batch was verified in the laboratory. The cooking was started by heating 100 liters of water to the temperature of 50 ºC and adding solid PVOH resin gradually into the water. Next, the temperature was raised to 85 ºC and cooking was continued until the turbidity of the solution disappeared (a few hours). All PVOH solutions were prepared from the same delivered batch of solid resin, and they were stored at room temperature for no more than a few days before being used in the experiment. The pipe rheometer measurements were carried out with an initial PVOH solution in thermal equilibrium with a room temperature of ca. 22°C, and foam density was varied between 100 g/l and 300 g/l with 50 g/l increments. The number of PVOH trial points was 966.

An experimental non-ionic polymeric surfactant (ES) by Solenis developed for foam application processes was used test to the rheological models obtained for viscosity and slip flow with the PVOH foams. ES foam was also used to measure the slip flow in a steel pipe. The ES foams were prepared similarly to the PVOH foams. These measurements were performed with the R = 6 mm pipe. ES dosages were 0.3%, 0.4%, 0.5% and 0.6% by weight. The density of the ES foams was either 200 or 100 kg/m^3. The number of ES trial points was 149. The measurements in a long hose were performed with a mixture of 0.4% ES and 3.0% Solenis HercoBond™ 7700-EU (HB), which is a commonly used dry strength additive.

Base solution viscosity measurements

The viscosities of the surfactant solutions were mainly measured using a stress-controlled DHR-2 rheometer (TA Instruments) equipped with a concentric cylinder geometry (cup radius = 15 mm, bob radius = 14 mm). The temperature of the sample was controlled by a Peltier concentric cylinder jacket that was connected to a circulating water bath (Julabo AWC100). Steady-state viscosities were measured over a shear rate range of 1-100 1/s at the temperature of 22°C. For the final analysis, viscosities measured at the shear rate of 56 1/s were used to minimize experimental artefacts due to the low-torque limit of the instrument at low shear rates and instrument inertia effects at high shear rates (Ewoldt et al. 2015). Table 1 shows the viscosity of PVOH and ES solutions as a function of solution concentration (w/w). The viscosity of the ES-HB mixture was measured with Brookfield DV-II+ Pro viscometer at the shear rate of 55 1/s at the temperature of 22°C. The relative error of the viscosity measurement was estimated to be not more than 2 % based on the variation of the viscosity measured at different shear rates.

Dynamic surface tension and dilatational complex modulus measurements

We used in this work dynamic surface tension instead of static surface tension as we are dealing with a dynamic process, where the foam is experiencing continuous shearing. The dynamic surface tension of the surfactant solutions was measured by the rising bubble method using a DSA100 drop-shape analyzer (KRÜSS Scientific). A small air bubble (10 µl) was created at the tip of a J-shaped capillary needle inside a temperature-controlled SC30 glass cuvette (KRÜSS Scientific) that was filled with the sample solution. The shape of the air bubble was recorded every 0.1 seconds for 10 minutes, and the surface tension was calculated based on the Young-Laplace equation using the ADVANCE software (v1.12, KRÜSS Scientific). The surface tension measurements were performed at the temperature of 22°C. For the final analysis, surface tension measured at t = 0.5 s was used. The choice of the reference time was not critical - the surface tension at e.g. t = 0.1 s and at t = 1.0 s were less than 2% higher and 1% smaller, respectively, than at t = 0.5 s. According to the instrument manufacturer, the accuracy of the surface tension measurement is 0.3 mN/m. Table 1 shows the surface tension of PVOH, ES and ES-HB solutions as a function of solution concentration.

Following the surface tension measurements, the dilatational complex moduli of the air/solution interfaces were measured by sinusoidally oscillating the volume of the air bubble with a computer-controlled oscillating drop module (DS3270, KRÜSS Scientific). The area oscillation amplitude was set to 4-5 % to ensure a linear viscoelastic response, and the oscillation frequency was set to 0.125 Hz following the work of (Denkov et al., 2005). The oscillating bubble experiments were conducted at the temperature of 22°C, and the dilatational moduli were computed with the ADVANCE software (v1.12, KRÜSS Scientific). Table 1 shows the dilatational complex modulus of PVOH, ES and ES-HB solutions as a function of solution concentration. The accuracy of the dilatational modulus

measurement has been reported to be 0.02 mN/m for a similar measurement setup (Atanase et al. 2015).

Surfactant	Concentration	Viscosity	Surface tension	Dilatational complex modulus
	% (w/w)	mPas	mN/m	mN/m
PVOH	0.5	1.32	52.7	6.16
	1.0	1.59	50.5	4.07
	3.0	3.45	47.8	2.34
	6.0	9.70	46.2	2.35
ES	0.3	1.45	59.3	7.56
	0.4	1.66	58.7	9.20
	0.5	1.79	58.3	8.84
	0.6	1.98	57.8	6.85
ES+HB	0.4 + 3.0	2.70	57.2	6.76

Table 1 PVOH, ES and ES+HB solution viscosity, dynamic surface tension and dilatational complex modulus at different concentrations. The temperature is 22°C.

Measurement of slip flow in an opaque pipe

In this study, we measured the slip velocity in acrylic pipes with a high-speed video camera. For opaque pipes, such as steel pipes, this is not possible, and the slip velocity must be measured indirectly. Figure 3 shows the experimental setup used for this purpose. There were two pipes with the same length of 2.0 m and an inner radius of 6 mm. The transparent pipe was acrylic, and the opaque pipe was a steel pipe. Flow was divided equally to the two pipes with a 3D-printed flow splitter (see Figure 4). The symmetry of the foam splitter was tested by repeating a selected set of measurements after flipping the splitter around. On average, there was no shift between the results measured before and after the flipping, thus the flow splitter can be considered close to symmetric. The flow discharged from the pipes into atmospheric pressure. The pressure loss in the pipes was the same, but if there were a difference in the slip flow, the mass flow rates in the pipes would be different. The pipe mass flow rates were measured by collecting the foam discharging from the pipes simultaneously into separate 2-litre buckets. The maximum error in the measured flow rate was estimated to be 5%. The foam samples were also used to measure the foam density. The slip velocity in the transparent pipe was measured with a high-speed video camera (Ari Jäsberg et al., 2015a). The slip velocity in the steel pipe was obtained from the formula

$$v_{\mathrm{slip},2} = v_{\mathrm{slip},1} + \frac{Q_2 - Q_1}{\pi R^2} \tag{12}$$

where Q_1 and Q_2 are the volumetric flow rates in the acrylic pipe and steel pipe, respectively, and $v_{\mathrm{slip},1}$ is the slip velocity in the acrylic pipe. The difference in the sampled foam densities and flow rates between the two opposite orientations of the splitter was minimal.

The measurements were performed for a DIN EN10216-5 (16X2,0 D4/T3 EN1.4404) stainless steel pipe. The surface roughness of the pipes was measured with the Mitutoyo SJ-210 traversing tester. The roughness of the steel and acrylic pipe was $1.5 \pm 0.1\ \mu m$ and $0.27 \pm 0.03\ \mu m$, respectively.

Foam density was 100 kg/m^3 and it was made from the experimental non-ionic polymeric surfactant (ES) with a dosage of 0.4%.

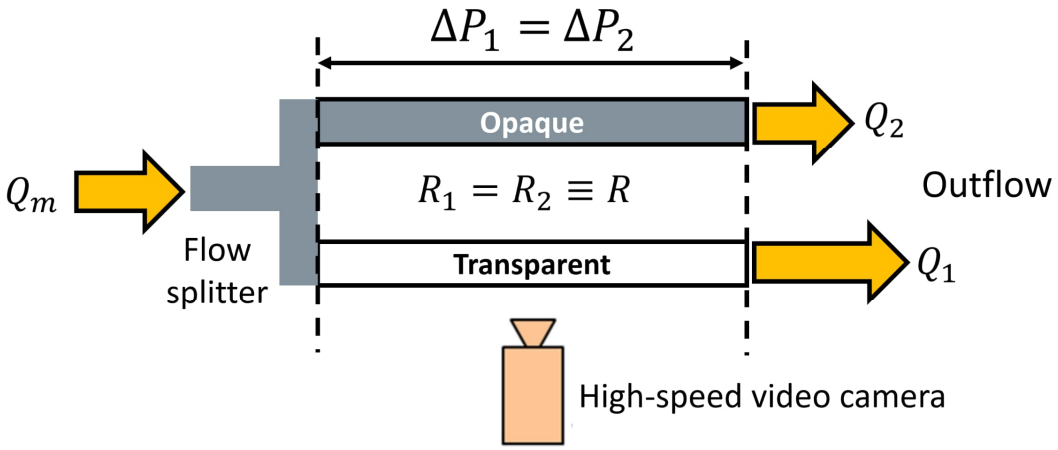


Figure 3 The principle of measuring slip flow in opaque pipes.

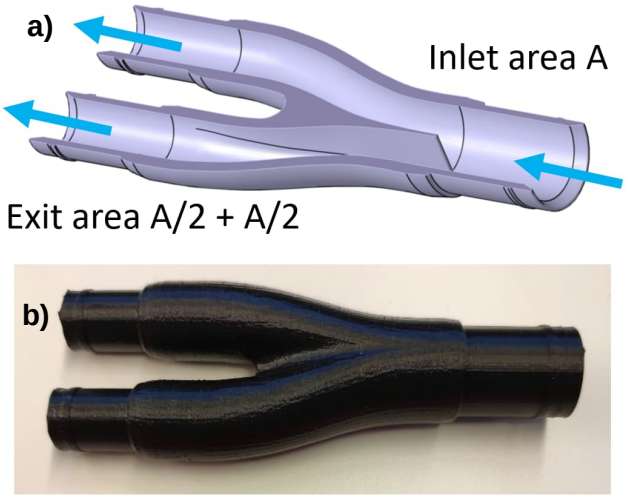


Figure 4 a) Schematic of a flow splitter. b) 3D printed flow splitter.

Pressure loss measurements in a long pipe

The setup for testing the obtained rheological models is shown in Figure 5. Here a 30-meter-long flow line was made of R = 8 mm reinforced transparent PVC hose, which was twisted into a coil with a diameter of ca. 1 m. At the outlet from the foam generator, volumetric flow rate, absolute pressure, and bubble size distribution were measured. Bubble size distribution at the end of the test line was measured with a second Pixact foam analyzer unit. Due to the pressure drop over the latter foam analyzer, the pressure level at the end of the test hose was elevated, and this value was measured. The flow was discharged from the test line into ambient pressure through a manual ball valve.

The measurements were done with ES foam (surfactant concentration 0.4 %) with 3%-wt of dry-strength additive HercoBond™ 7700-EU. Foam density was 100 g/l and the temperature of the surfactant solution was 22 ºC. The mass flow rate values 100, 125, and 150 kg/h were used in this test. First, the measurement was done for the full-length PVC hose with the discharge valve fully open. Then, six meters of the hose were cut off, and the measurements were repeated for the remaining 24 meters of the hose by adjusting the discharge valve so that the back pressure at the beginning of

the hose remained unchanged. Again, six meters of the hose were removed and the measurements were repeated. At this point, the hose was 18 meters long, and the outflow pressure sensor started to hit its high limit (in Figure 21, data points at a distance of 18 meters are a bit low from the trend set by the remaining data points) and no further measurements with a shorter line were possible.

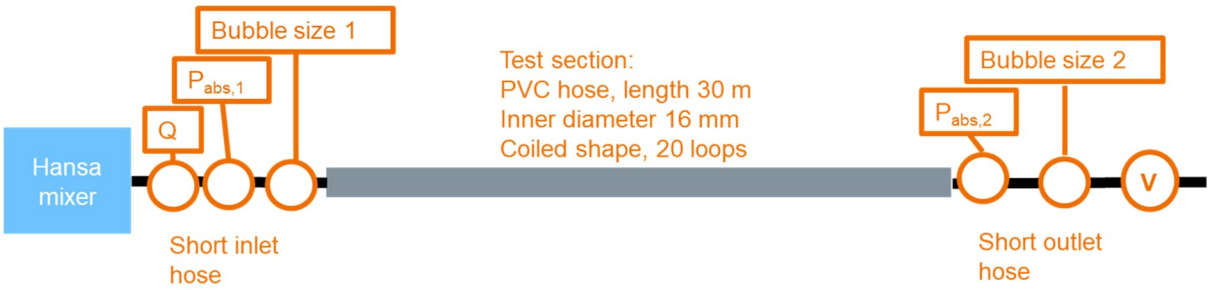


Figure 5 A schematic drawing of the setup used for foam transport tests in a long PVC hose.

A 1D model was used to simulate stationary flow through the hose. The model assumes power-law viscosity behaviour (Eq. (2)) and it takes into account slippage at the hose wall and the compressibility of foam. Due to viscose losses, the pressure level varies considerably along the long hose (while in the short pipes used for measuring the rheology, the pressure level was close to the atmospheric one). Here, the largest absolute pressure measured at the inlet to the hose was ca. 430 kPa (see Figure 21). In the model, local foam density is calculated from the local pressure by considering the compressibility of air inside foam bubbles. In a stationary case, any flow variable is constant in time. In addition, the mass flow rate through any cross-section of the hose is independent of the position in the flow direction. The mass flow rate Q_m can be calculated from the condition measured at the exit from the foam generator: $Q_m = \rho_2 Q$. The foam density ρ_2 at the generator outlet can be calculated from the measured pressure level $P_{\mathrm{abs},1}$ and from the nominal foam density $\rho_0 = 100$ g/l.

For a power-law fluid, the local pressure gradient dP_{abs}/dL in an unidirectional flow in a straight can be calculated from the local volumetric flow rate Q:

$$\frac{dP_{\mathrm{abs}}}{dL} = \frac{2K}{R}\left[\frac{3+1/n}{\pi R^3} Q\right]^n \tag{13}$$

where K and n are the power-law parameters in Eq. (2). These were obtained from the viscosity model, Eq. (19), developed in this work. The effect of the curvature of the hose on the viscous losses (pressure drop) was estimated with the result derived by Dean (Zhou and Shah, 2004):

$$\frac{f_{\mathrm{CL}}}{f_{\mathrm{SL}}} = \left[1 - 0.03058\left(\frac{K_{\mathrm{De}}}{576}\right)^2 + 0.01195\left(\frac{K_{\mathrm{De}}}{576}\right)^4\right]^{-1} \tag{14}$$

Here f_{CL} and f_{SL} are the friction factor for the hose in a coiled and a straight shape, respectively, and the Dean number K_{De} can be calculated from the formula

$$K_{\mathrm{De}} = 2\mathrm{Re}^2 \frac{R}{R_c} \tag{15}$$

Here, Re is the Metzner-Reed Reynolds number (see Eq. (4)) and R_c is the radius of curvature of the coiled shape. In the current case, the maximum value of the Dean number is ca. 500, and inserting it

into Eq. (14) gives less than 2% correction in the viscous losses. Thus we can neglect the curvature effect in our study and consider the flow unidirectional.

The equation (13) was solved by integrating numerically upstream starting from measurement point 2 at the end of the hose. At each step, the local absolute pressure P_{abs} was used to calculate the local foam density ρ by scaling the known nominal density. The local flow rate was calculated from the constant mass flow rate: $Q = Q_m/\rho$. The contribution of the slip was obtained from the slip model, Eq. (24), developed in this work.


3. Results and discussion

Examples of the measured PVOH foam process data

We look at some examples of the measured process data in the R = 6.0 mm pipe with a 0.5% PVOH concentration. Foam density varied between 100 kg/m^3 and 300 kg/m^3. Figure 6 presents loss curves, i.e., pressure drop per unit length of the pipe vs. volumetric flow rate of foam. We see that the viscous pressure loss increases with decreasing foam density (increasing air content). The shape of the loss curves is typical for a shear-thinning fluid: the slope of the curves decreases with an increasing flow rate.

Figure 7a shows the slip velocity as a function of wall shear stress. We see that slip increases with increasing wall shear stress. The slip velocity is higher with higher foam density, as it is then easier to drag liquid from the foam to the wall. However, the slope of the curves is similar for the different foam densities. Figure 7b shows that the contribution of the slip flow to the total flow rate can be significant. The contribution is highest at low flow rates and decreases with increasing flow rates. With the smallest flow rates, as much as 70% of the measured flow rate is caused by slip velocity.

By applying the Weissenberg-Rabinowitsch correction to the measurement data shown in Figure 6 and Figure 7 we got the viscosity-shear rate curves shown in Figure 8. The plotted values are real material parameters without any reference to the used measurements setup (e.g., pipe size or slip flow). We see from Figure 8 that the foam viscosity strongly increases with decreasing foam density. We also see that the relation between the foam viscosity and shear rate is with all the foam densities with a high accuracy a power law, Eq. (2). Moreover, the shear thinning behaviour increases (flow index n decreases) with decreasing foam density.

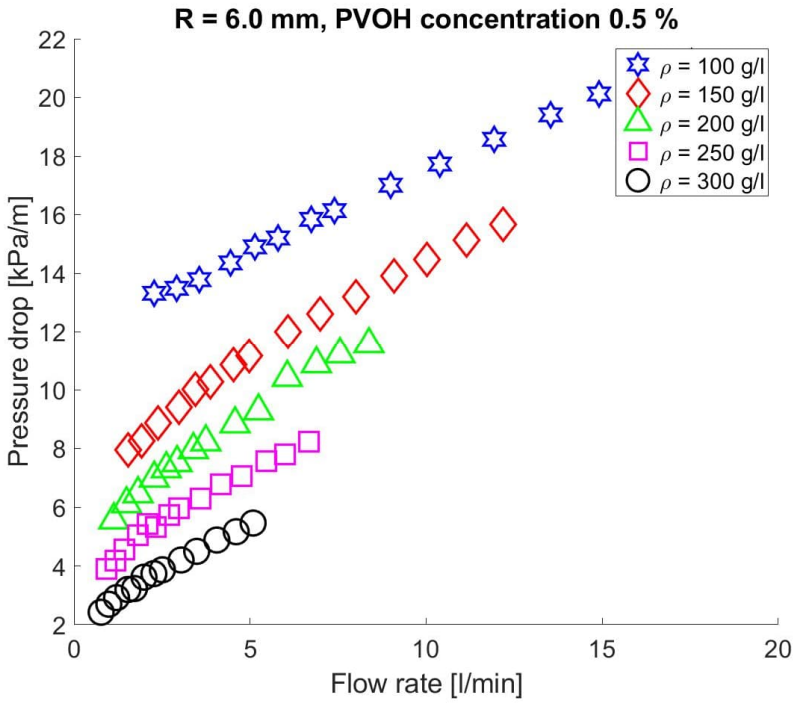


391

392 Figure 6 Pressure loss curves for different foam densities in R = 6.0 mm pipe at 0.5% PVOH
393 concentration. Data adapted from (Jäsberg et al., 2023).

394

395

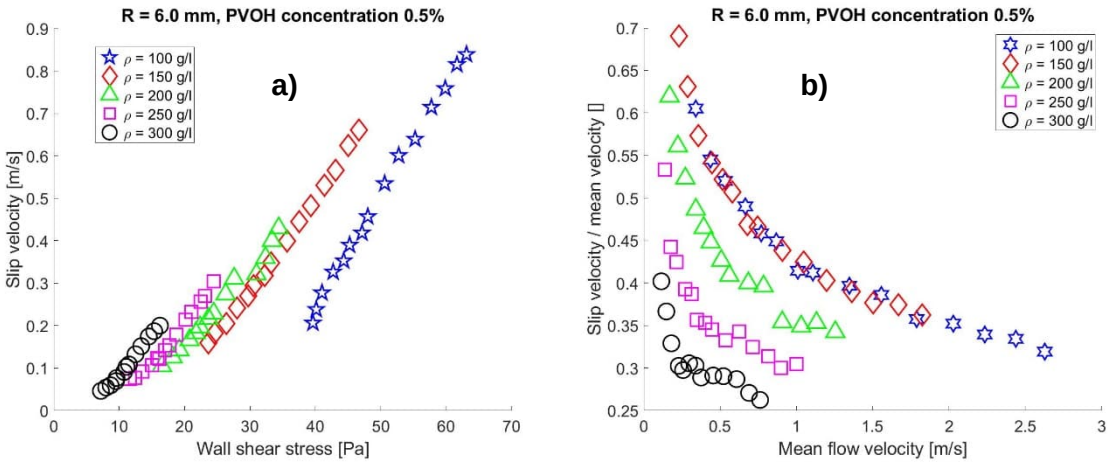

396

397

398 Figure 7. Slip velocity data for different foam densities in R = 6.0 mm pipe at 0.5% PVOH
399 concentration. a) Slip velocity vs. wall shear stress. b) Relative slip velocity vs. mean flow velocity.
400 Data adapted from (Jäsberg et al., 2023).

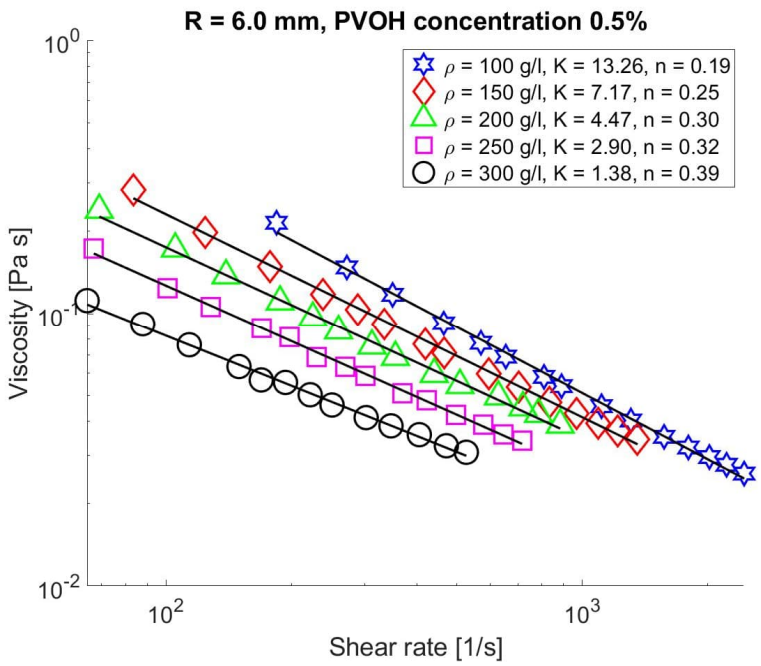


Figure 8. Analyzed viscosity for different foam densities in $R = 6.0$ mm pipe at 0.5% PVOH concentration. Straight lines are fits of the power law Eq. (2). The fitting parameters K and n are shown in the legend. Data adapted from (Jäsberg et al., 2023).

Inspection of the full PVOH dataset

Figure 9 shows the bubble size as the function of air content for all the trial points. We see that bubble size tends to decrease both with increasing PVOH solution concentration and with decreasing air content. With higher surfactant dosage the foam is more stable and the higher solution viscosity leads to higher shear forces in the foam generation unit and the bubble size becomes smaller. With higher air content longer processing times and/or higher mixing speed are probably needed for obtaining as small bubbles as with the lower air contents. This is supported by the fact that bubble size generally increased with the increasing flow rate of the foam.

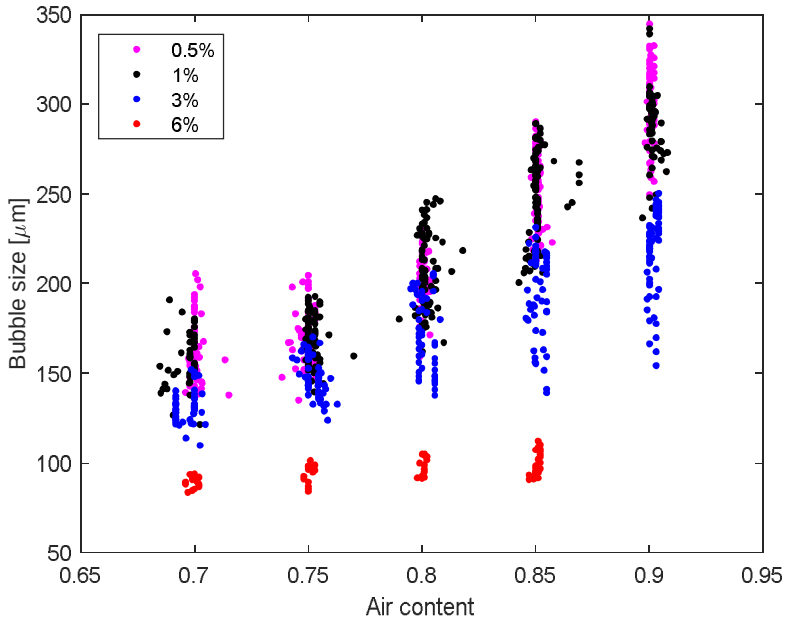


Figure 9 Bubble size as a function of air content. PVOH solution concentration is shown with different marker colours. There is some variation in the air contents, but the average air contents were 0.70, 0.75, 0.80, 0.85 and 0.90.

Foam viscosity is shown as a function of the shear rate for all data points in Figure 10. Air content is shown in this figure with colour coding. We see from Figure 10 that viscosity generally increased with an increasing air content and follows the power law Eq. (2). With a 6% PVOH concentration the highest air content was 0.85 (see Figure 9). For this reason, the highest viscosities were not obtained with the highest air content of 0.9.

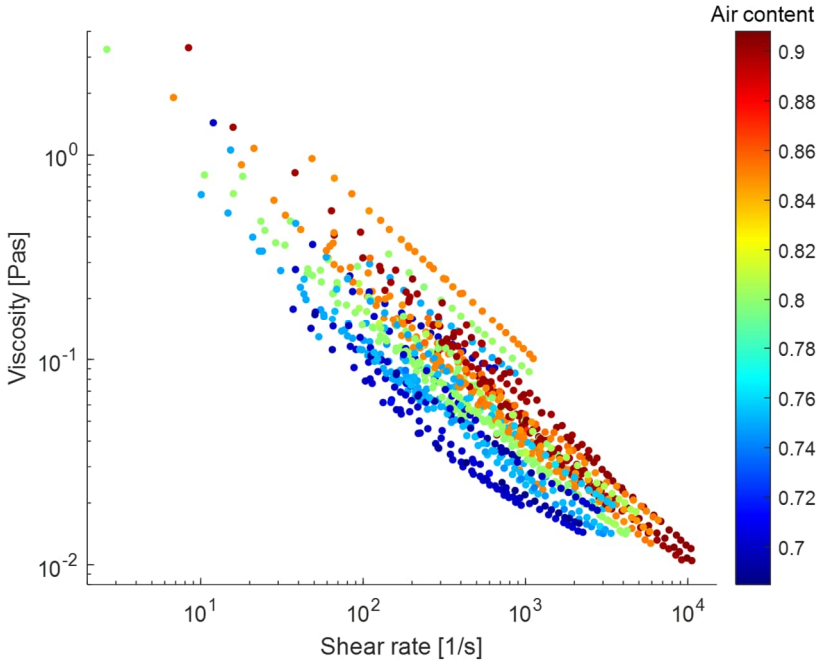


Figure 10 Viscosity as a function of shear rate for all data points. Air content is shown with colour coding.

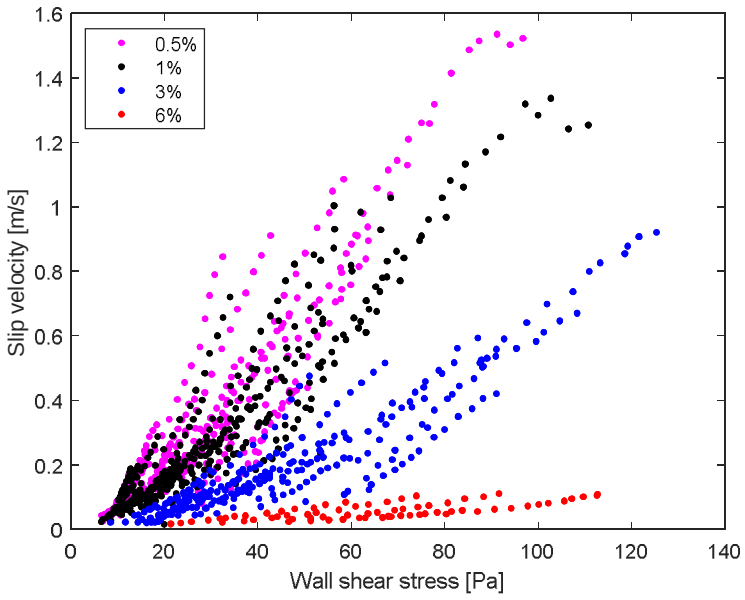


Figure 11 Slip velocity as a function of wall shear stress for all data points. PVOH concentration is shown with different marker colours.

Figure 11 shows slip velocity as a function of wall shear stress for all data points. PVOH concentration is shown in this figure with different marker colours. We see from Figure 11 that the PVOH concentration has a strong effect on the slip velocity. We also see that slip velocity increases with increasing wall shear stress and the relation between the two quantities is nonlinear.

Models for foam viscosity and slip velocity

Dimensional analysis is a widely used tool in fluid dynamics for simplifying complex problems and making predictions about fluid behaviour based on the underlying dimensionless parameters (White, 1998). In this work, we used dimensional analysis to obtain models for the foam viscosity and slip velocity. The parameters of these models were then obtained from the measurement data by regression analysis on the PVOH data.

The foam viscosity μ depends at least on the following quantities: liquid viscosity, μ_l, liquid surface tension, σ_l, liquid density, ϱ_l, air density, ϱ_a, air content, φ, average bubble size, D, and shear rate $\dot{\gamma}$. When choosing μ_l, σ_l and ϱ_l as the scaling parameters, the dimensional analysis gives the following dimensionless Π-parameters:

$$\Pi_1 = \frac{\mu}{\mu_l}, \Pi_2 = \varphi, \Pi_3 = \frac{\varrho_l \sigma_l D}{\mu_l^2}, \Pi_4 = \frac{\mu_l^3 \dot{\gamma}}{\varrho_l \sigma_l^2}, \Pi_5 = \frac{\varrho_a}{\varrho_l} \quad (16)$$

Π_1 is the relative viscosity of the foam and Π_3 is the Laplace number, which is used to characterize free surface fluid dynamics. Π_4 has no established name. Generally, Π_1 is a function of the other Π-parameters, i.e.,

$$\Pi_1 = f(\Pi_2, \Pi_3, \Pi_4, \Pi_5) \quad (17)$$

In our setup, the pressure level is close to the atmospheric pressure in the measurement pipe and the air density should have a negligible effect on the foam viscosity. We thus dropped Π_5 from the subsequent analysis.

An important step of dimensional analysis is the selection of the function f in Eq. (17). We chose a power law type model, which is often a natural choice:

$$\frac{\mu}{\mu_l} = A(\varphi) \left(\frac{\varrho_l \sigma_l D}{\mu_l^2} \right)^{a(\varphi)} \left(\frac{\mu_l^3 \dot{\gamma}}{\varrho_l \sigma_l^2} \right)^{b(\varphi)} \quad (18)$$

We performed a regression analysis for Eq. (18) for each air content φ separately. The values of the fitting functions $A(\varphi)$, $a(\varphi)$ and $b(\varphi)$ are shown in Supplementary material. As $a(\varphi)$ and $b(\varphi)$ were close to each other with all the air contents (the average difference was below 4%), Eq. (18) can be simplified into the form

$$\frac{\mu}{\mu_l} = B(\varphi) \left(\frac{\dot{\gamma} D \mu_l}{\sigma_l} \right)^{m(\varphi)} \quad (19)$$

Above

$$\mathrm{Ca} = \frac{\dot{\gamma} D \mu_l}{\sigma_l} \quad (20)$$

is the capillary number of the shear flow. In this work, Ca varied between 5×10^{-5} and 0.2 and the average was 0.02. Capillary forces thus dominated the viscous forces in the whole dataset, and the deformation of bubbles due to shear forces was in most cases rather small (Rust and Manga, 2002).

Table 2 The fitted values of functions $B(\varphi)$ and $m(\varphi)$ of Eq. (19) for each air content φ.

φ	$B(\varphi)$	$m(\varphi)$	R^2
0.70	0.466 ± 0.039	-0.639 ± 0.014	0.94
0.75	0.636 ± 0.023	-0.637 ± 0.006	0.98
0.80	0.659 ± 0.016	-0.691 ± 0.004	0.99
0.85	0.718 ± 0.021	-0.735 ± 0.005	0.99
0.90	0.883 ± 0.022	-0.762 ± 0.006	0.99

Table 2 shows the values of functions $B(\varphi)$ and $m(\varphi)$ given by a regression analysis that was performed for Eq. (19) at each air content separately. We see from Figure 12 that Eq. (19) gives the viscous behaviour of the PVOH foam with very good accuracy. There are only a few outliers with lower air contents. This may be due to these foams being more unstable; this was in some cases seen in partial phase separation (some liquid had drained to the bottom of the pipe). Notice that by comparing Eqs. (2) and (19) we see that $n = 1+m$ where n is the flow index. Flow index n thus generally slightly decreases with increasing air content; an example of this was shown already in Figure 8.

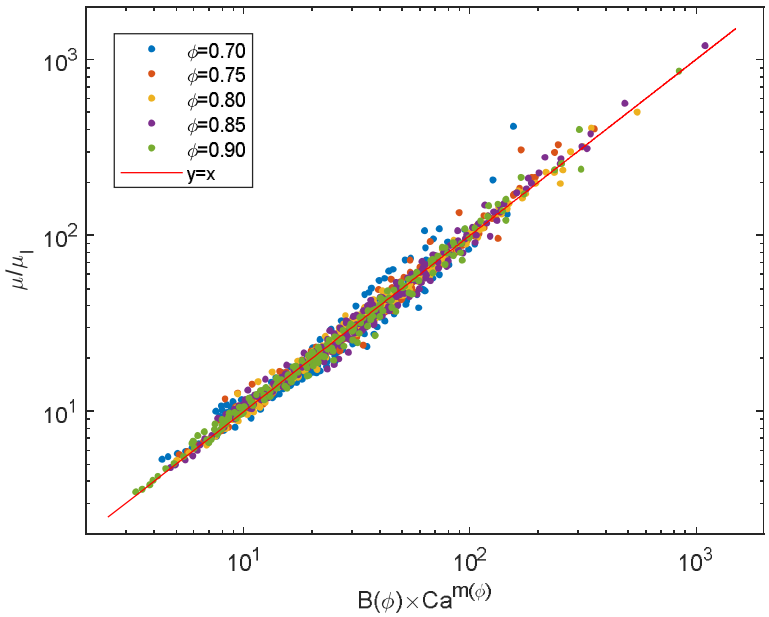


Figure 12 Dimensionless viscosity $\frac{\mu}{\mu_l}$, of PVOH foam, as a function of $B(\varphi)\times \mathrm{Ca}^{m(\varphi)}$ (see Eq. (19) and Table 2). The coefficient of determination of the whole dataset is 0.99.

The slip velocity v_s depends at least on the following quantities: liquid viscosity, μ_l, liquid surface tension, σ_l, liquid density, ϱ_l, air content, φ, average bubble size, D, and wall shear stress τ_w. The dimensional analysis gives the Π-parameters:

$$\Pi_1 = \frac{\mu_l v_s}{\sigma_l}, \Pi_2 = \varphi, \Pi_3 = \frac{\varrho_l \sigma_l D}{\mu_l^2}, \Pi_4 = \frac{\mu_l^2 \tau_w}{\varrho_l \sigma_l^2}, \Pi_5 = \frac{\varrho_a}{\varrho_l} \quad (21)$$

where

$$\Pi_1 = f(\Pi_2, \Pi_3, \Pi_4, \Pi_5). \quad (22)$$

We dropped Π_5 from the analysis as the density of air is expected to have a marginal effect on the slip flow. We once again chose a power law–type model, without fixing the formula for the air content:

$$\frac{\mu_l v_s}{\sigma_l} = A'(\varphi) \left(\frac{\varrho_l \sigma_l D}{\mu_l^2} \right)^{a'(\varphi)} \left(\frac{\mu_l^2 \tau_w}{\varrho_l \sigma_l^2} \right)^{b'(\varphi)}. \quad (23)$$

We performed a regression analysis for Eq. (23) for each air content separately. The average difference between $a'(\varphi)$ and $b'(\varphi)$ was 3% (see Supplementary material). This suggests that Eq. (23) can be simplified into the form

$$\frac{\mu_l v_s}{\sigma_l} = G(\varphi) \left(\frac{D\tau_w}{\sigma_l} \right)^{w(\varphi)}. \quad (24)$$

Above

$$\mathrm{Ca}^* = \frac{\mu_l v_s}{\sigma_l} \quad (25)$$

is the slip capillary number, which varied between 0.002 and 0.07, and

$$\tau_w^* = \frac{D\tau_w}{\sigma_l} \quad (26)$$

is the dimensionless wall shear stress of the slip flow. Notice that τ_w^* can be interpreted as the ratio of the wall shear stress and the bubble capillary pressure. The physical interpretation of this is that wall shear stress is higher when capillary pressure is higher, as then the slip film thickness remains thinner. (The capillary pressure resists expanding the slip film by the dynamic pressure.) A detailed explanation can be found in (Denkov et al. 2005).

Table 3 shows the values of functions $G(\varphi)$ and $w(\varphi)$ given by a regression analysis that was performed for Eq. (24) at each air content separately. We see from Figure 13 that Eq. (24) works generally well. There are, however, some outliers obtained mainly with the pipe radius of 9.5 mm (see Supplementary material). The flow rates in the R = 9.5 mm pipe were usually lower than in the other two pipes, and occasionally phase separation took place already during the pipe flow (some liquid was collected on the pipe bottom). The deviations from the slip model, however, did not correlate with the average velocity of the flow, nor with any other measured quantity. It is unlikely that the outliers are due to measurement errors in the measured slip velocities, as this would lead to outliers also in the obtained foam viscosities. The measurements took several months, and it is possible that the variations in the quality of the tap water, such as salinity, explain this discrepancy.

Table 3 The fitted values of functions $G(\varphi)$ and $w(\varphi)$ of Eq. (24) for each air content φ.

φ	$G(\varphi)$	w(φ)	R^2
0.7	0.610 ± 0.086	1.60 ± 0.05	0.88
0.75	0.434 ± 0.043	1.62 ± 0.04	0.90

0.8	0.351 ± 0.017	1.74 ± 0.02	0.97
0.85	0.244 ± 0.016	1.82 ± 0.04	0.92
0.9	0.168 ± 0.009	2.01 ± 0.04	0.93

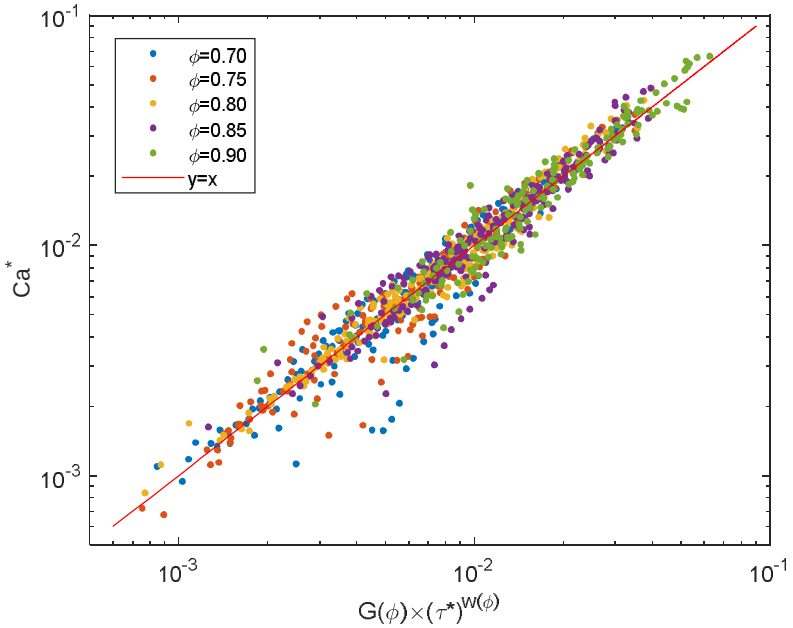


Figure 13 Dimensionless slip, Ca*, of PVOH foam as a function of $G(\varphi)\times(\tau^*)^{w(\varphi)}$ (See Eq. (24) and Table 3). The coefficient of determination is 0.97.

For practical purposes, when the air content can be anything between 0.7 and 0.9, we fitted the 2nd-order polynomial

$$f(\varphi) = a_0 + a_1\varphi + a_2\varphi^2 \tag{27}$$

to the values of functions $B(\varphi)$, $m(\varphi)$, $G(\varphi)$ and $w(\varphi)$ shown in Table 2 and Table 3. The obtained fitting parameters a_0, a_1 and a_2 are shown in Table 4. (The fits are shown in Supplementary material.)

Table 4 The fitting parameters a_0, a_1 and a_2 of the 2nd order polynomial Eq. (27) for functions $B(\varphi)$, $m(\varphi)$, $G(\varphi)$ and $w(\varphi)$.

	a_0	a_1	a_2	R^2
$B(\varphi)$	-0.3124	0.6171	0.7614	0.93
$m(\varphi)$	-1.024	1.534	-1.389	0.96
$G(\varphi)$	5.275	-10.19	5.024	0.99
$w(\varphi)$	6.020	-12.82	9.294	0.99

Testing the rheological models with ES foams

Figure 14 shows the bubble size as the function of air content for all the trial points of ES foams. ES foam viscosity is shown as a function of the shear rate for all data points in Figure 15. Figure 16 shows the ES foam slip velocity as a function of wall shear stress for all data points.

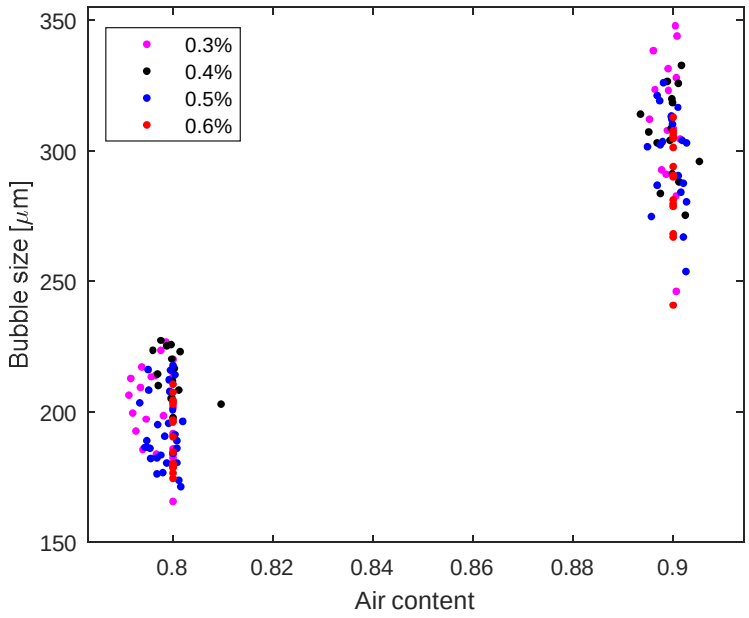


Figure 14 Bubble size as a function of air content for the ES foam. The ES solution concentration is shown with different marker colours.

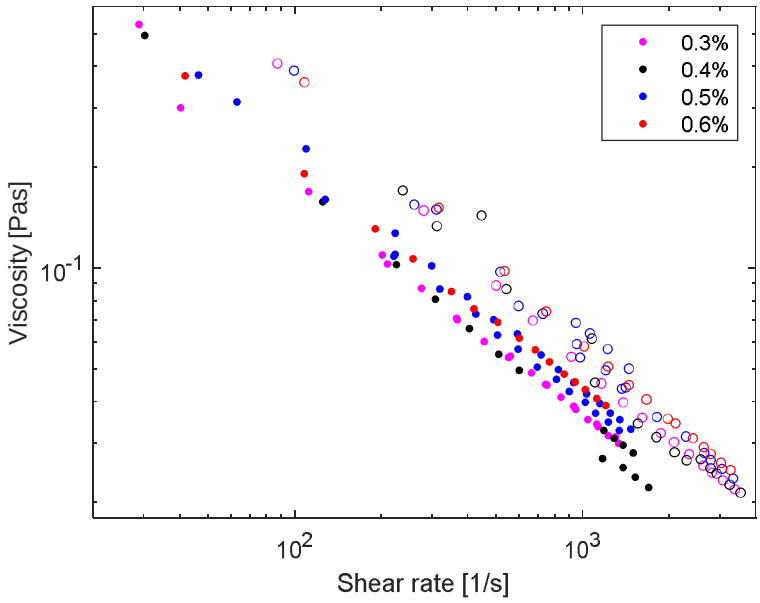


Figure 15 Viscosity as a function of shear rate for the ES foam. The ES solution concentration is shown with different marker colours. Air content is 0.8 for filled markers and 0.9 for open markers.


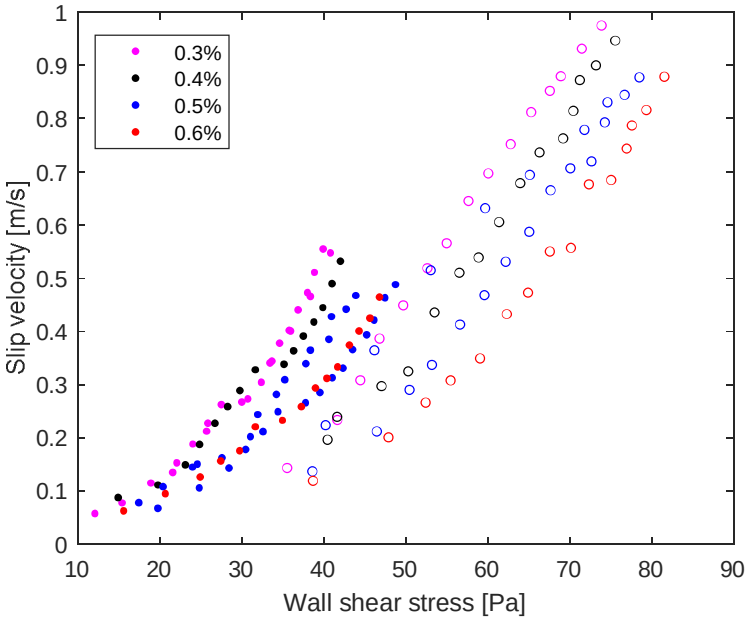



Figure 16 Slip velocity as a function of wall shear stress for the ES foam. The ES solution concentration is shown with different marker colours. Air content is 0.8 for filled markers and 0.9 for open markers.

The models for viscosity and slip, with the parameters of Table 4, were tested with ES foams. Figure 17 shows the dimensionless viscosity $\frac{\mu}{\mu_l}$, of ES foam, as a function of $B(\varphi)\times \mathrm{Ca}^{m(\varphi)}$ (see Eq. (19)). We see that the viscosity model predicted the viscosity of the ES foam with very good accuracy. The coefficient of determination was 0.99 and the modelled viscosity was on average 1.9% smaller than the measured viscosity. Figure 18 shows the dimensionless slip, Ca*, of ES foam, as a function of $G(\varphi)\times(\tau^*)^{w(\varphi)}$ (See Eq. (24)). The prediction based on the PVOH foam is also here quite good although the slip is very sensitive to process conditions. The coefficient of determination was 0.96 and the modelled slip was on average 5.8% bigger than the measured slip. Notice that the viscosity and slip models and their parameters were used directly without fitting the models to the ES foam data. This suggests that the rheological models derived from PVOH data are more general and will be useful in developing application foams and processes.

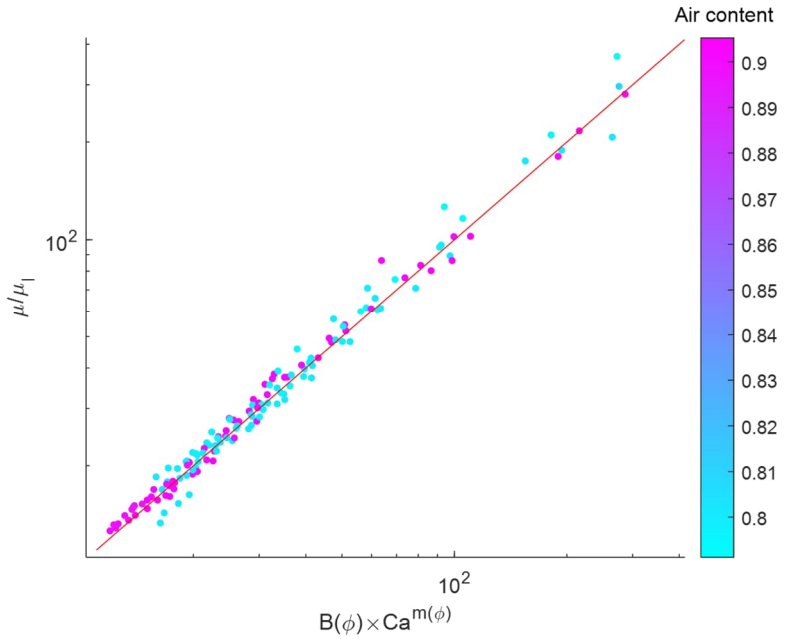

549

550 Figure 17 Dimensionless viscosity $\frac{\mu}{\mu_l}$, of ES foam, as a function of $B(\varphi)\times \mathrm{Ca}^{m(\varphi)}$ (see Eq. (19) and
551 Table 4). The coefficient of determination is 0.99. The modelled viscosity was on average 1.9%
552 smaller than the measured viscosity. The red line shows the curve $y = x$.

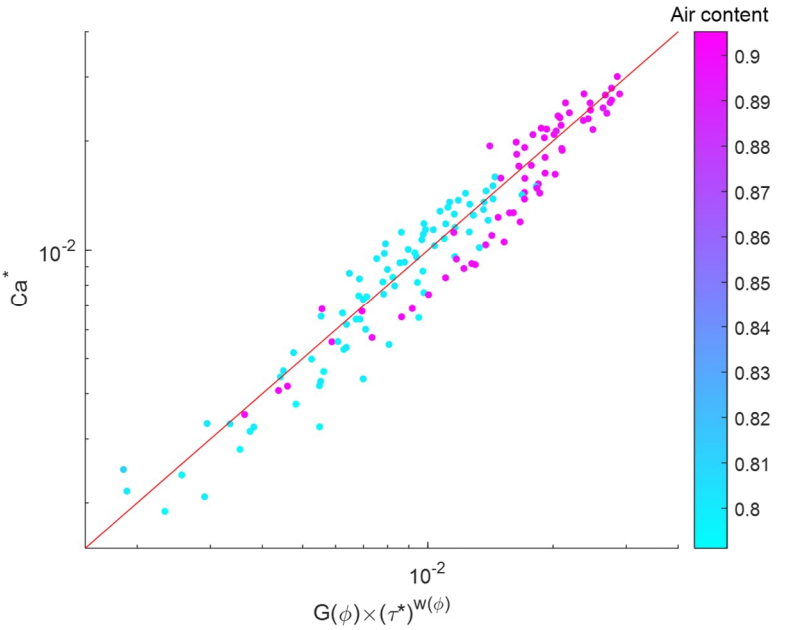

553

554 Figure 18 Dimensionless slip, Ca*, of ES foam, as a function of $G(\varphi)\times(\tau^*)^{w(\varphi)}$ (See Eq. (24) and
555 Table 4). The coefficient of determination is 0.96. The modelled slip was on average 5.8% bigger
556 than the measured slip. The variation around the (red) $y = x$ curve is similar to the PVOH foams (see
557 Figure 13).

558 *Fanning friction factor*

559 The Fanning friction factor f is widely used for both Newtonian and non-Newtonian flows for
560 calculating the pressure drop in pipes. It is defined as

$$f = \frac{\tau_w}{\frac{1}{2}\rho v^2} \tag{28}$$

where τ_w is the wall shear stress, ρ is the fluid (foam) density and v is the average flow velocity. For Newtonian and power-law fluids (Barigou and Deshpande, 2000)

$$f = \frac{16}{\mathrm{Re}} \tag{29}$$


where Re is the Metzner-Reed Reynolds number (see Eq. (4)). Figure 19 shows the Fanning friction factor as a function of the Reynolds number for PVOH foams. We see that the data lie very well on a unique line and follow the expression (R^2=0.993)

$$f = \frac{13.7}{\mathrm{Re}^{0.98}} \tag{30}$$


(If the power of Re is fixed to 1, one gets f = 14.4/Re.) The friction factor f is for PVOH foams slightly smaller than for ideal power-law fluids. The reason is the slip flow that increases the flow rate with a given wall shear stress thus effectively decreasing the friction factor. Notice that if the friction factor and the Reynolds number are calculated with the slip-corrected flow velocity (see Figure 20), the relation between them is (R^2=0.994)

$$f = \frac{16.7}{\mathrm{Re}^{1.01}} \tag{31}$$

(If the power of Re is fixed to 1, one gets f = 16.2/Re.) This formula is very close to the theoretical expression Eq. (29).

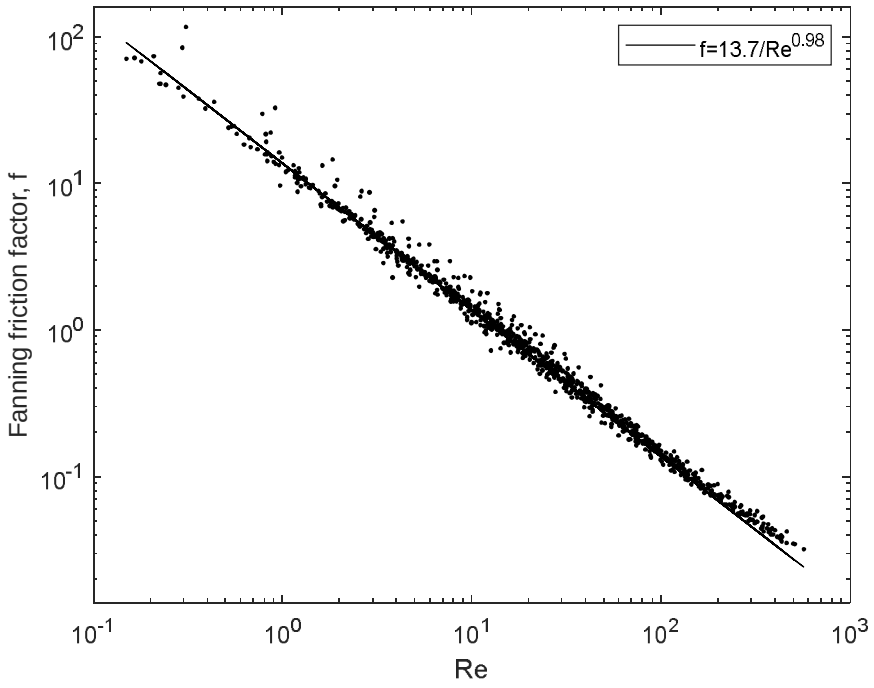

579 Figure 19 The Fanning friction factor as a function of the Metzner-Reed Reynolds number for PVOH
580 foams. The coefficient of determination is 0.993.

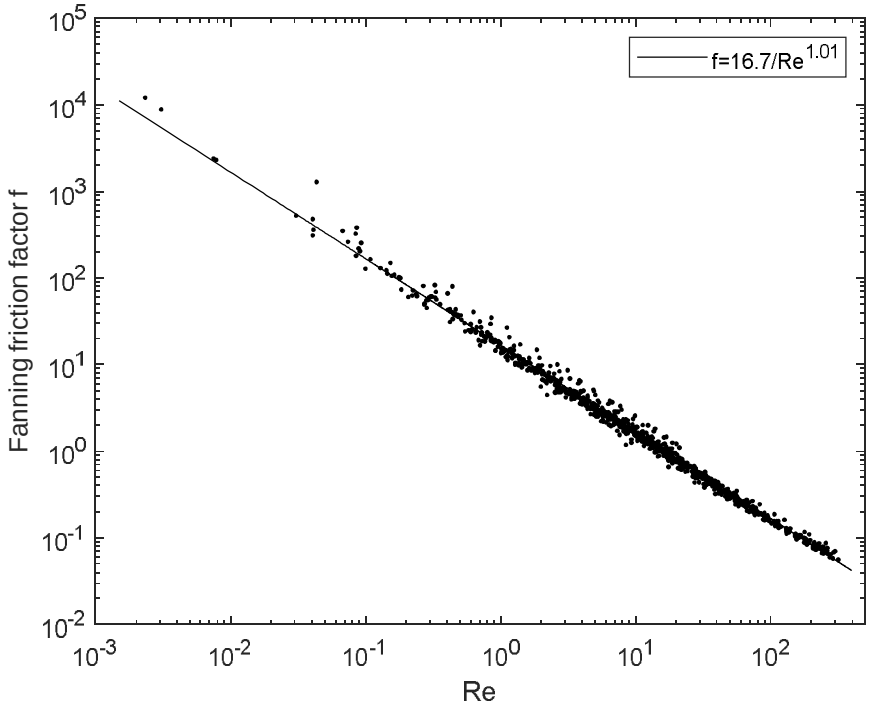

581

582 Figure 20 The Fanning friction factor as a function of the Metzner-Reed Reynolds number for PVOH
583 foams. The slip-corrected flow velocity has been used in the calculation of *f* and Re. The coefficient
584 of determination is 0.994.

585 *Slip flow in a steel pipe*

586 Table 5 summarizes the slip flow measurements in the EN 1.4404 steel pipe with the setup shown in
587 Figure 3. Both acrylic-acrylic and acrylic-steel pipe pairs were used in the measurements. The foam
588 density was 100 kg/m^3 and the mass flow rate varied between 20 kg/h and 140 kg/h. In this flow
589 range, the relative slip in the acrylic pipe was always significant. The relative flow speed difference
590 between the two pipes varied slightly between the trial points, but there was no systematic difference
591 between the acrylic and steel pipes. The calculated flow speed difference between the acrylic and
592 steel pipes was always very low compared to the measured slip velocity in the acrylic pipe. These
593 results suggest that slip flow (in steel pipes) depends strongly on the wall roughness. With smooth
594 walls, slip behaves similarly for the materials that are used in real-life processes.

595 Table 5 Slip flow measurements with the setup shown in Figure 3. From left to right: The material of
596 pipe 1 and pipe 2, the total mass flow rate Q_m in the two pipes, the volumetric flow rates Q_1 and Q_2
597 in the pipes, the flow speeds v_1 and v_2 in the pipes, the relative difference of the flow speeds $(v_2\text{-}v_1)/v_1$
598 in the pipes, slip velocity $v_{s,1}$ in the pipe 1, and relative slip in the pipe 1.

Pipe 1 material	Pipe 2 material	Q_m kg/h	Q_1 l/min	Q_2 l/min	v_1 m/s	v_2 m/s	$(v_2\text{-}v_1)/v_1$ %	$v_{s,1}$ m/s	$v_{s,1}/v_1$ %
acrylic	acrylic	20	1.518	1.495	0.224	0.220	1.5	0.174	78
acrylic	acrylic	40	3.210	3.031	0.473	0.447	5.6	0.287	61
acrylic	acrylic	60	4.862	4.753	0.716	0.700	2.2	0.388	54
acrylic	acrylic	100	7.962	7.809	1.173	1.151	1.9	0.513	44

acrylic	acrylic	140	10.80	11.14	1.591	1.642	-3.2	0.586	37
acrylic	steel	20	1.633	1.477	0.241	0.218	9.5	0.172	72
acrylic	steel	40	3.125	3.083	0.460	0.454	1.3	0.269	58
acrylic	steel	60	4.805	4.815	0.708	0.710	-0.2	0.377	53
acrylic	steel	100	7.812	8.193	1.151	1.207	-4.9	0.539	47
acrylic	steel	140	10.98	11.52	1.617	1.697	-4.9	0.643	40

Pressure loss in a long pipe

Figure 21 shows the measured pressure profiles along the flow line. Solid lines are the numerical solutions of Eq. (11). Considering the simplifications that were made in the simulation (there is no validated method to take into account the effect of foam compressibility, i.e. the varying density of the gas, in rheology), the agreement is surprisingly good. Table 6 lists the main experimental quantities at different locations of the PVC hose.

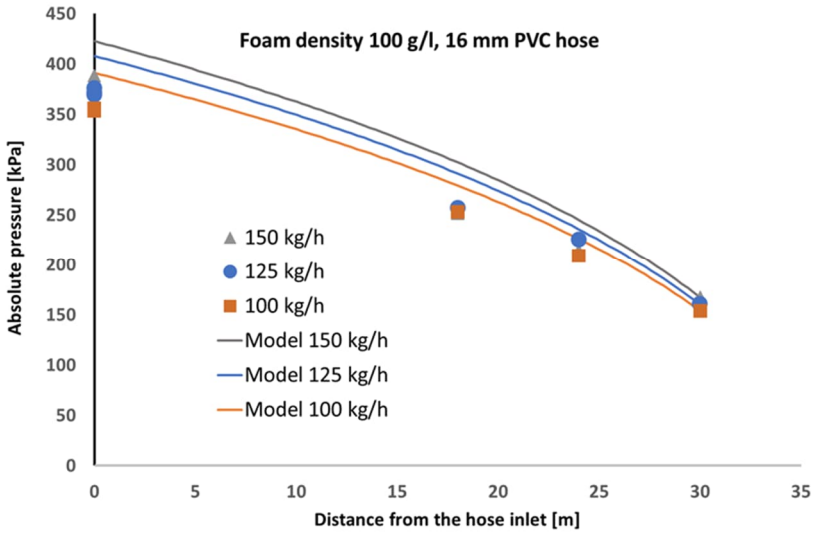


Figure 21 Measured pressure profiles and the values calculated based on the measured foam rheology for different mass flow rates. (For the 18-meter-long hose, the outflow pressure sensor was close to its high limit. For this reason, the data points at a distance of 18 meters are a bit low from the trend set by the remaining data points.)

Table 6 Flow quantities at the inlet, exit and standard pressure 1 atm for the PVC hose at varying lengths L: mass flow rate, Q_m, foam density at the inlet, ρ_1, flow speed at the inlet, v_1, foam density at the exit, ρ_2, flow speed at the exit, v_2, flow speed at 1 atm, v_{atm}, and the bubble diameter at 1 atm, D_{atm}.

L	Q_m	ρ_1 (inlet)	v_1 (inlet)	ρ_2 (exit)	v_2 (exit)	v_{atm}	D_{atm}
m	kg/h	g/l	m/s	g/l	m/s	m/s	µm
30	100	283	0.49	146	0.94	1.38	435
30	125	292	0.59	152	1.14	1.73	407
30	150	302	0.69	157	1.32	2.07	330

24	100	282	0.49	188	0.73	1.38	444
24	125	295	0.59	200	0.86	1.73	450
24	150	298	0.69	193	1.07	2.07	389
18	100	283	0.49	220	0.63	1.38	457
18	125	291	0.59	222	0.78	1.73	421
18	150	295	0.70	218	0.95	2.07	365

4. Discussion

In the literature, foam rheology has often been measured by using several pipe diameters, and the slip velocity has been estimated by using either the Mooney or Oldroyd -Jastrzebski analysis (Enzendorfer et al., 1995)(Gardiner et al., 1998). In the Mooney analysis, it is assumed that $v_s = \beta_c \tau_w$ where coefficient β_c depends on the wall shear stress τ_w. On the other hand, in many papers, the Mooney analysis has failed and the Oldroyd-Jastrzebski analysis has been used. Here the assumption is $v_s = \beta_c \tau_w / R$, where R is the pipe radius. The assumed effect of pipe radius on the slip velocity is thus quite strong. We did not find any evidence of such a dependence of slip velocity on the pipe radius; adding the pipe radius to the dimensional analysis did not improve the accuracy of the obtained formula for slip velocity. Indeed, (Martin and Wilson, 2005) argue that the Oldrey-Jastrzebski analysis has no physical justification and its attraction has been only that when the Mooney analysis has failed, it has yielded seemingly reasonable results. They suggest that one should avoid the Oldrey-Jastrzebski analysis and use instead a modified Mooney analysis described in their paper. An obvious advantage of the slip measurement setups used in this work is that slip is measured directly, and no a priori assumptions of the slip behaviour are needed.

If we define the bubble Reynolds number as

$$\mathrm{Re}_D = \frac{\rho_l \dot{\gamma} D^2}{\mu_l} \tag{32}$$

we can write the Π-parameters 3 and 4 of the viscosity analysis (see Eq. (16)) with the capillary number Ca (see Eq. (20)) and the Reynolds number Re_D as follows:

$$\Pi_3 = \frac{\mathrm{Re}_D}{\mathrm{Ca}}$$

and

$$\Pi_4 = \frac{\mathrm{Ca}^2}{\mathrm{Re}_D}$$

Therefore, an alternative choice for the dimensionless groups 3 and 4 would be Ca and Re_D. As we see in Eq. (19), of the two, the dimensionless viscosity is here dependent only on the capillary number. This reveals that the dropped dimensionless group is Re_D, and the inertial force does not play a role in the foam viscosity. Notice that a corresponding analysis with a similar result can be performed also for the slip flow.

By substituting $\mu = \tau / \dot{\gamma}$ to Eq. (19) one gets an alternate formula for the foam rheology:

$$\frac{D\tau}{\sigma_l} = B(\varphi)\left(\frac{\dot{\gamma} D \mu_l}{\sigma_l}\right)^{m(\varphi)+1} \tag{33}$$

where

$$\tau^* = \frac{D\tau}{\sigma_l} \tag{34}$$

is the dimensionless shear stress. The dimensionless shear stress is thus proportional to the capillary number:

$$\tau^* \propto \mathrm{Ca}^n \tag{35}$$

In (Denkov et al., 2005) and (Denkov et al., 2009) Eq. (35) was obtained for the air content of 0.9 experimentally. Eq. (24) for slip flow can be written in the form

$$\tau_w^* = H(\varphi)\left(\mathrm{Ca}^*\right)^{k(\varphi)} \tag{36}$$

where $H(\varphi) = G(\varphi)^{-1/w(\varphi)}$ and $k(\varphi) = 1/w(\varphi)$. The dimensionless wall shear stress is thus proportional to the slip capillary number:

$$\tau_w^* \propto \mathrm{Ca}^{*k} \tag{37}$$

(Denkov et al., 2005) derived Eq. (37) theoretically with k depending only on the bubble surface mobility. (Denkov et al., 2005) suggested that for the air content of 0.9, in Eq. (35) n = 0.4 if the bubble surface was tangentially mobile (surface dilatational modulus < 100 mN/m) and n = 0.25 if the surface was immobile (surface dilatational modulus > 100 mN/m). (Denkov et al., 2005) found one exception, where n was 0.25 for a mobile surface. For Eq. (37) (Denkov et al., 2005) obtained theoretically k = 2/3 for a tangentially mobile surface and k = 1/2 for an immobile surface. Although the dilatational moduli of the air / PVOH solution interfaces are small and the surface is thus mobile (see Table 1), we got n = 0.25 and k = 0.5 for the 0.9 air content. Our dilatation moduli measurement is similar to (Denkov et al., 2005), so we might have found new exceptions for the above-mentioned classification of surfactants developed by (Denkov et al., 2005).

In the literature, it has often been stated that steel pipes have no slip flow. In our measurements, the slip flow of a smooth-walled steel pipe did not differ from the slip of an acrylic pipe. In the earlier studies (Thondavadi and Lemlich, 1985)(Harris and Reidenbach, 1987) (Larmignat et al., 2008) the absence of wall slip in steel pipes was likely caused by the steel pipes having a high surface roughness. In (Thondavadi and Lemlich, 1985), *e.g.*, galvanized steel pipes were used which typically have a roughness of a few hundred micrometres. Notice that for modelling and dimensioning practical processes and for process control the slip flow presents a challenge, as it can be very sensitive to small changes in the process parameters. This problem could be eliminated by using pipes with a high wall roughness at the cost of increasing the pressure loss and potential fouling of the pipe surfaces.

In foam application, the applied chemical can be used as the surfactant, as is the case with PVOH. However, usually, the application foam is used as the carrier for applying other chemicals and

materials, such as starch or microfibrillated cellulose. We presented one example in our long-pipe experiment where the foam was used to carry a commercial strength additive. In this case, the rheological model worked rather well, but the rheological behaviour of these mixtures can also differ from the carrier foam and should be measured before using them in real-life applications. In (Ari Jäsberg et al., 2015a)(A. Jäsberg et al., 2015b)(Prakash et al., 2021) the addition of cellulosic fibrous materials of various types and sizes up to 5 wt % changed the foam consistency index significantly, but the flow index remained practically unchanged. On the other hand, in (Thondavadi and Lemlich, 1985) the addition of small coal and sand particles up to 35 wt % did not change the foam rheology.

These measurements were performed at atmospheric pressure. In the future, the effect of elevated pressure level on the application foam rheology should be studied to find out when the elevated density of air starts to affect the foam rheology. Another future topic is the effect of temperature on application foam rheology. However, most temperature effects should already be implicitly included in Eqs. (19) and (24) in the solution viscosity, solution surface tension and the foam bubble size.

5. Conclusions

Foam application of chemicals to the wet web is currently being developed for the paper and board industry. An important part of this work is to understand the rheology of the used application foams. PVOH is widely used as a strength additive in paper and board, and it was chosen as the main surfactant for the foams of this study. The PVOH foam density varied between 100 kg/m^3 and 300 kg/m^3 and the dosage of PVOH varied between 0.5% to 6%.

The foam viscosity and slip flow were determined with a pipe rheometer using three pipe diameters. The slip velocity was quantified by recording the foam motion in the vicinity of the wall of an acrylic pipe with a high-speed video camera. A measurement setup was also built for measuring the slip flow directly in opaque pipes.

Dimensional analysis was used to obtain general formulas for the foam viscosity and slip flow that were based on several physical quantities describing both the foam and the base liquid. Here the dimensionless shear stress and dimensionless wall shear stress were proportional to certain powers of the capillary number and slip capillary number, respectively. Similar formulas had earlier been obtained by (Denkov et al., 2005) for the air content of 0.9. Our study widens the scope of the models to a much wider air-content region. The obtained rheological models were applied successfully for another surfactant for flow in a short pipe and flow in a long PVC hose using an industrially relevant mixture of carrier foam and a dry strength additive.

The contribution of the slip flow to the total flow rate was significant, especially with lower flow rates when most of the volumetric flow was due to the slip. In the literature, many papers have suggested that there is no slip flow in steel pipes. Our results suggest that this is due to the high pipe roughness used in these works. In our measurements, the slip velocity of a smooth-walled steel pipe was identical to an acrylic pipe. This should be taken into account when real-life processes are developed.

The obtained viscosity and slip models form a solid basis for developing and running various industrial processes including foam application processes. For new foam recipes, quite a small number of rheological measurements are needed for determining the model parameters for a fixed air content.

Acknowledgement

This research was done in the ChemFunc project funded mainly by Business Finland. The authors want to thank ChemFunc project parties Anpap, Metsä Board, Pixact, Solenis, Sulzer and Valmet for valuable discussion on this work and its results. We acknowledge Prof. Nikolai Denkov for valuable discussions with him. His expertise in foam rheology was particularly helpful in understanding the link between the surface dilatational modulus and the model exponents. Our gratitude also to Titta Kiiskinen and Joona Hast for their contribution to the measurement of foam rheology.

Open data

The rheological measurements of the PVOH foams can be downloaded from Zenodo. DOI: 10.5281/zenodo.8334762.

References

Atanase, L., Bistaca, S., Riessa, G., 2015, Effect of poly(vinyl alcohol-co-vinyl acetate) copolymer blockiness on the dynamic interfacial tension and dilational viscoelasticity of polymer–anionic surfactant complex at the water–1-chlorobutane interface. Soft Matter 11, 2665-2672. https://doi.org/10.1039/C4SM02766C

Barigou, M., Deshpande, N.S., 2000. The flow of gas-liquid foams in vertical pipes, Chemical Engineering Science 55(19), 4297–4309. https://doi.org/10.1016/S0009-2509(00)00057-9

Bliss, T., Luo, M., Nicholas, M., 2021. Application of foamed additives to the surface of wet handsheets, Tappi Journal 20, 9–19. https://doi.org/10.32964/tj20.1.9

Briceño, M.I., Joseph, D.D., 2003. Self-lubricated transport of aqueous foams in horizontal conduits, International Journal of Multiphase Flow 29(12), 1817–1831. https://doi.org/10.1016/j.ijmultiphaseflow.2003.10.001

Cohen-Addad, S., Höhler, R., 2014. Rheology of foams and highly concentrated emulsions, Current Opinion in Colloid & Interface Science 19(6), 536–548. https://doi.org/10.1016/j.cocis.2014.11.003

Denkov, N.D., Subramanian, V., Gurovich, D., Lips, A., 2005. Wall slip and viscous dissipation in sheared foams: Effect of surface mobility, Colloids and Surfaces A: Physicochemical and Engineering Aspects 263, 129–145. https://doi.org/10.1016/j.colsurfa.2005.02.038

Denkov, N.D., Tcholakova, S., Golemanov, K., Ananthpadmanabhan, K.P., Lips, A., 2009. The role of surfactant type and bubble surface mobility in foam rheology, Soft Matter 5, 3389-3408. https://doi.org/10.1039/b903586a

Dollet, B., Raufaste, C., 2014. Rheology of aqueous foams, Physical Reports 15, 731-747. https://doi.org/10.1016/j.crhy.2014.09.008

Enzendorfer, C., Harris, R.A., Valkó, P., Economides, M.J., Fokker, P.A., Davies, D.D., 1995. Pipe viscometry of foams, Journal of Rheology 39, 345–358. https://doi.org/10.1122/1.550701

Ewoldt, R.H., Johnston, M.T., Caretta, L.M., 2015. Experimental challenges of shear rheology: How to avoid bad data. In: Spagnolie, S. (Ed.), Complex Fluids in Biological Systems. Biological and Medical Physics, Biomedical Engineering. Springer, New York, NY. https://doi.org/10.1007/978-1-4939-2065-5_6

Farr, R.S., Groot, R.D., 2009. Close packing density of polydisperse hard spheres, Journal of Chemical Physics 131, 244104. https://doi.org/10.1063/1.3276799

Furuta, Y., Oikawa, N., Kurita, R., 2016. Close relationship between a dry-wet transition and a bubble rearrangement in two-dimensional foam, Scientific Reports 6, 37506. https://doi.org/10.1038/srep37506

Gardiner, B.S., Dlugogorski, B.Z., Jameson, G.J., 1999. Prediction of pressure losses in pipe flow of aqueous foams, Industrial & Engineering Chemistry Research 38(3), 1099–1106. https://doi.org/10.1021/ie980385i

Gardiner, B.S., Dlugogorski, B.Z., Jameson, G.J., 1998. Rheology of fire-fighting foams, Fire Safety Journal 31(1), 61-755. https://doi.org/10.1016/S0379-7112(97)00049-0

Gottberg, J.-M., Lappalainen, T., Salminen, K., 2019. Polyvinyl alcohol as foaming agent in foam formed paper. Tappi Journal 18(8), 475-485.

Harris, P.C., Reidenbach, V.G., 1987. High-temperature rheological study of foam fracturing fluids, Journal of Petroleum Technology 39, 613–619. https://doi.org/10.2118/13177-PA

Heller, J.P., Kuntamukkula, M.S., 1987. Critical review of the foam rheology literature, Industrial & Engineering Chemistry Research 26, 318–325. https://doi.org/10.1021/ie00062a023

Herzhaft, B., 1999. Rheology of aqueous foams: a literature review of some experimental works, Oil and Gas Science and Technology 54(5), 587–596. https://doi.org/10.2516/ogst:1999050

Herzhaft, B., Kakadjian, S., Moan, M., 2005. Measurement and modeling of the flow behavior of aqueous foams using a recirculating pipe rheometer, Colloids and Surfaces A: Physicochemical and Engineering Aspects 263, 153–164. https://doi.org/10.1016/j.colsurfa.2005.01.012

Hjelt, T., Henriksson, E., Jaiswal, A., Oksanen, A., 2023. Chemical addition to wet webs using foam application, Tappi Journal 22(1), 33–39.

Hjelt, T., Ketoja, J., Kiiskinen, H., Koponen, A., Pääkkönen, E., 2021. Foam forming of fiber products: a review, Journal of dispersion science and technology 43(10), 1462-1497. https://doi.org/10.1080/01932691.2020.1869035

Höhler, R., Cohen-Addad, S., 2005. Rheology of liquid foam, Journal of physics: condensed matter 17, R1041 https://doi.org/10.1088/0953-8984/17/41/R01

Jäsberg, Ari, Selenius, P., Koponen, A., 2015a. Experimental results on the flow rheology of fiber-laden aqueous foams, Colloids and Surfaces A: Physicochemical and Engineering Aspects 473, 147–155. https://doi.org/10.1016/j.colsurfa.2014.11.041

Jäsberg, A., Selenius, P., Koponen, A., 2015b. Flow rheology of fiber-laden aqueous foams, proceedings of PaperCon 2015, TAPPI Press, Vol. 2 (2015), 872-889.

Jäsberg, A., Viitala, J., Tanaka, A., Prakash, B., Koponen, A., 2023. Flow rheology of light foams generated from aqueous solutions of polyvinyl alcohol, Tappi Journal 22(1), 51–60.

Kenttä, E., Kinnunen-Raudaskoski, K., Hjelt, T., 2014. Characterization of thin pigment coating layers produced by foam coating, Tappi Journal 13(7), 21–27.

Kentta, E., Kumar, V., Andersson, P., Forsstrom, U., 2022. A novel foam coating approach to produce abrasive structures on textiles, Autex Research Journal 22(3), 335–342. https://doi.org/10.2478/aut-2021-0031

Kinnunen-Raudaskoski, K., Hjelt, T., Forsström, U., Sadocco, P., Paltakari, J., 2017. Novel thin functional coatings for paper by foam coating. Tappi Journal 16(4), 179–186. https://doi.org/10.32964/tj16.4.179

Kinnunen-Raudaskoski, K., Hjelt, T., Kentta, E., Forsstrom, U., 2014. Thin coatings for paper by foam coating. Tappi Journal 13(7), 9–19.

Koponen, A., Eloranta, H., Jäsberg, A., Honkanen, M., Kiiskinen, H., 2019. Real-time monitoring of bubble size distribution in a foam forming process. Tappi Journal 18(8), 487–494.

Kowalczuk, P.B., Drzymala, J., 2016. Physical meaning of the Sauter mean diameter of spherical particulate matter, Particulate Science and Technology 34(6), 645–647. https://doi.org/10.1080/02726351.2015.1099582

Kroezen, A.., Groot Wassink, J., Schipper, C., 1988. The flow properties of foam, Journal of the Society of Dyers and Colourists 104, 393–400. https://doi.org/10.1111/j.1478-4408.1988.tb01138.x

Lambride, C., Syrakos, A., Georgiou, G., 2023. Entrance length estimates for flows of power-law fluids in pipes and channels, Journal of Non-Newtonian Fluid Mechanics 317,105056. https://doi.org/10.1016/j.jnnfm.2023.105056

Larmignat, S., Vanderpool, D., Lai, H.K., Pilon, L., 2008. Rheology of colloidal gas aphrons (microfoams), Colloids and Surfaces A: Physicochemical and Engineering Aspects 322, 199–210. https://doi.org/10.1016/j.colsurfa.2008.03.010

Lexis, M., Willenbacher, N., 2014. Yield stress and elasticity of aqueous foams from protein and surfactant solutions – The role of continuous phase viscosity and interfacial properties Colloids and Surfaces A: Physicochemical and Engineering Aspects 459, 177–185. https://doi.org/10.1016/j.colsurfa.2014.06.030

Lyons, W.C., Stanley, J.H., Sinisterra, F.J., Weller, T., 2020. Air and Gas Drilling Manual. Elsevier, Oxford.

Martin, P.J., Wilson, D.I., 2005. A critical assessment of the Jastrzebski interface condition for the capillary flow of pastes, foams and polymers. Chem Eng Sci 60(2), 493–502. https://doi.org/10.1016/j.ces.2004.08.011

Marze, S., Langevin, D., Saint-Jalmes, A., 2008. Aqueous foam slip and shear regimes determined by rheometry and multiple light scattering. Journal of Rheology 52, 1091–1111. https://doi.org/10.1122/1.2952510

Metzner, A., Reed, J., 1955. Flow of non-Newtonian fluids - correlation of the laminar, transition and turbulent-flow regions. AIChE Journal 1, 434–440.

Mooney, M., 1931. Explicit formulas for slip and fluidity. Journal of Rheology 2, 210-222. https://doi.org/10.1122/1.3642116

Morrison, F.A., 2001. Understanding rheology. Oxford University Press, New York.

Nguyen, A.V., Schulze, H.J., 2003. Colloidal Science of Flotation. Marcel Dekker, New York.

Oksanen, A., Hjelt, T., Lehmonen, J., Rantanen, T., Asikainen, J., 2023. New opportunities in the paper and nonwovens industries with foam-assisted web forming and chemical application. Tappi Journal 22(1), 61–66.

Omirbekov, S., Davarzani, H., Sabyrbay, B., Colombano, S., Ahmadi-Senichault, A., 2022. Experimental study of rheological behavior of foam flow in capillary tubes. Journal of Non-Newtonian Fluid Mechanics 302, 104774. https://doi.org/10.1016/j.jnnfm.2022.104774

Poole, R., Ridley B., 2007. Journal of Fluids Engineering 129(10), 1281-1287, https://doi.org/10.1115/1.2776969

Prakash, B., Jäsberg, A., Koponen, A., 2021. Experimental investigation on the effect of fibre consistency on rheology of aqueous foams in pipe flow. Annual Transactions of the Nordic Society of Rheology 29, 27–34.

Princen, H.M., Kiss, A.D., 1986. Rheology of foams and highly concentrated emulsions: III.. Static shear modulus, Journal of Colloid and Interface Science 112(2), 427–437. https://doi.org/10.1016/0021-9797(86)90111-6

Rust, A.C., Manga, M., 2002. Bubble shapes and orientations in low Re simple shear flow, Journal of Colloid and Interface Science 249(2), 476–480. https://doi.org/10.1006/jcis.2002.8292

Saint-Jalmes, A., Durian, D.J., 1999. Vanishing elasticity for wet foams: Equivalence with emulsions and role of polydispersity, Journal of Rheology 43, 1411–1422. https://doi.org/10.1122/1.551052

Schramm, L.L., 2005. Emulsions, Foams, and Suspensions: Fundamentals and Applications. WILEY-VCH Verlag, Weinheim.

Sen, A.K., 2007. Coated Textiles - Principles and Applications, second edition. CRC Press, Boca Raton.

Thondavadi, N., Lemlich, R., 1985. Flow properties of foam with and without solid particles, Industrial and Engineering Chemistry Process Design and Development 24(3), 748–753. https://doi.org/10.1021/i200030a038

Weaire, D., Hutzler, S., 1999. The Physics of Foams. Oxford University Press, Oxford.

White, F.M., 1998. Fluid Mechanics, fourth edition. McGraw-Hill College.

Zhou, Y., Shah, S., 2004. Fluid flow in coiled tubing: A literature review and experimental investigation. Journal of Canadian Petroleum Technology 43, 52-61. https://doi.org/10.2118/04-06-03

Supplementary material

Foam generation

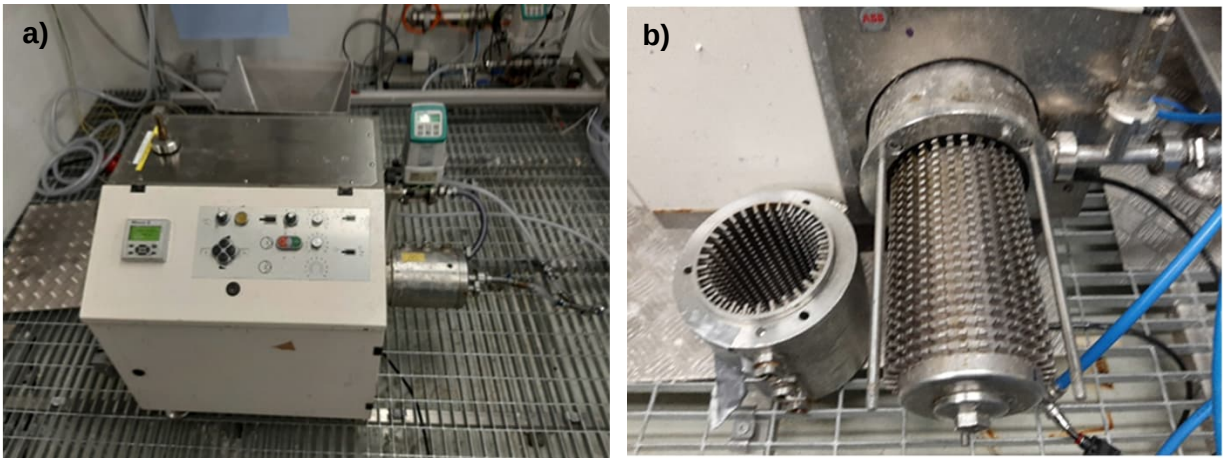


Figure 22 a) The foam generator (Hansa Industrie-Mixer GmbH & Co. KG). b) The mixing head unit (rotor-stator) opened. Figures from (Jäsberg et al., 2023).


Deriving the viscosity and slip models

Table 7 Viscosity analysis. The values of functions $A(\varphi)$, $a(\varphi)$ and $b(\varphi)$ of Eq. (18) with different air contents are given by a regression analysis. Functions $a(\varphi)$ and $b(\varphi)$ are close to each other.

φ	$A(\varphi)$	$a(\varphi)$	$b(\varphi)$	R^2
0.70	0.492 ± 0.050	-0.656 ± 0.022	-0.644 ± 0.015	0.94
0.75	0.671 ± 0.033	-0.652 ± 0.011	-0.641 ± 0.006	0.98
0.80	0.607 ± 0.021	-0.670 ± 0.007	-0.685 ± 0.004	0.99
0.85	0.581 ± 0.019	-0.691 ± 0.006	-0.725 ± 0.005	0.99
0.90	0.598 ± 0.032	-0.698 ± 0.009	-0.752 ± 0.005	0.99


Table 8 Slip analysis. The values of functions $A'(\varphi)$, $a'(\varphi)$ and $b'(\varphi)$ of Eq. (23) with different air contents are given by a regression analysis. Functions $a'(\varphi)$ and $b'(\varphi)$ are close to each other.

φ	$A'(\varphi)$	$a'(\varphi)$	$b'(\varphi)$	R^2
0.7	0.482 ± 0.072	1.73 ± 0.06	1.67 ± 0.05	0.89
0.75	0.327 ± 0.039	1.74 ± 0.05	1.68 ± 0.04	0.91
0.8	0.3198 ± 0.020	1.77 ± 0.03	1.75 ± 0.02	0.97
0.85	0.353 ± 0.028	1.76 ± 0.04	1.81 ± 0.03	0.93
0.9	0.346 ± 0.037	1.89 ± 0.04	1.99 ± 0.04	0.95

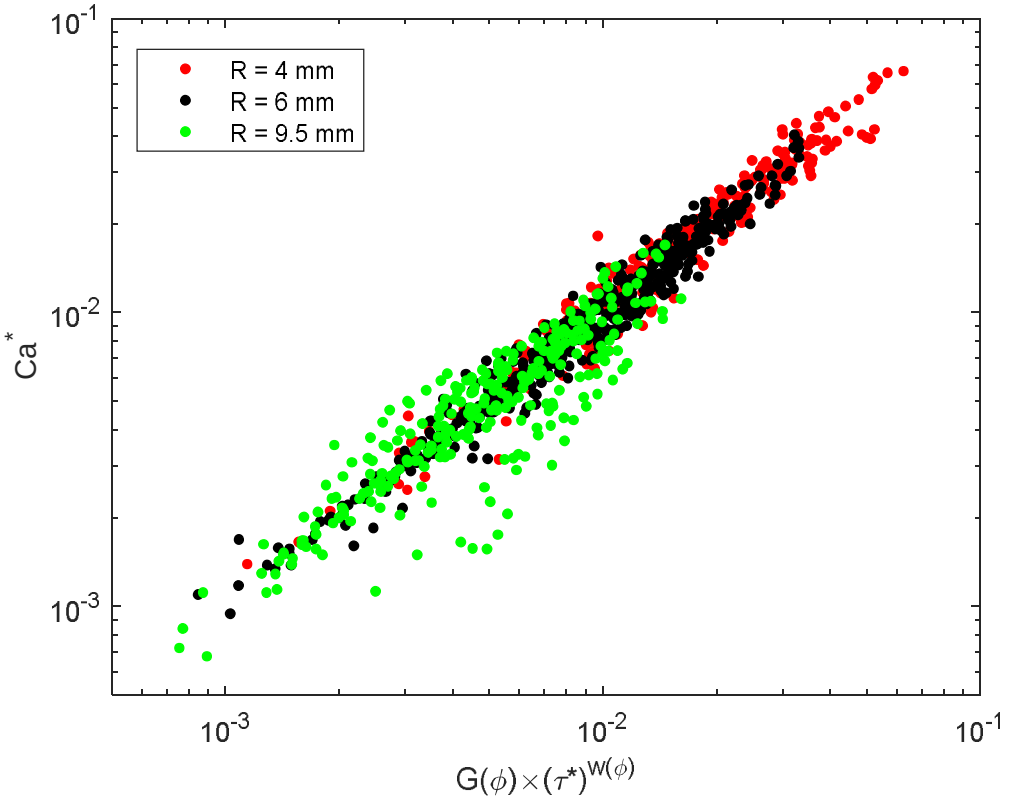


885

886 Figure 23 Dimensionless slip, Ca*, of PVOH foam, as a function of $G(\varphi)\times(\tau^*)^{w(\varphi)}$ (See Eq. (24) and
887 Table 3). The marker colours show the pipe radii. Outliers are mainly seen with the R = 9.5 mm pipe.

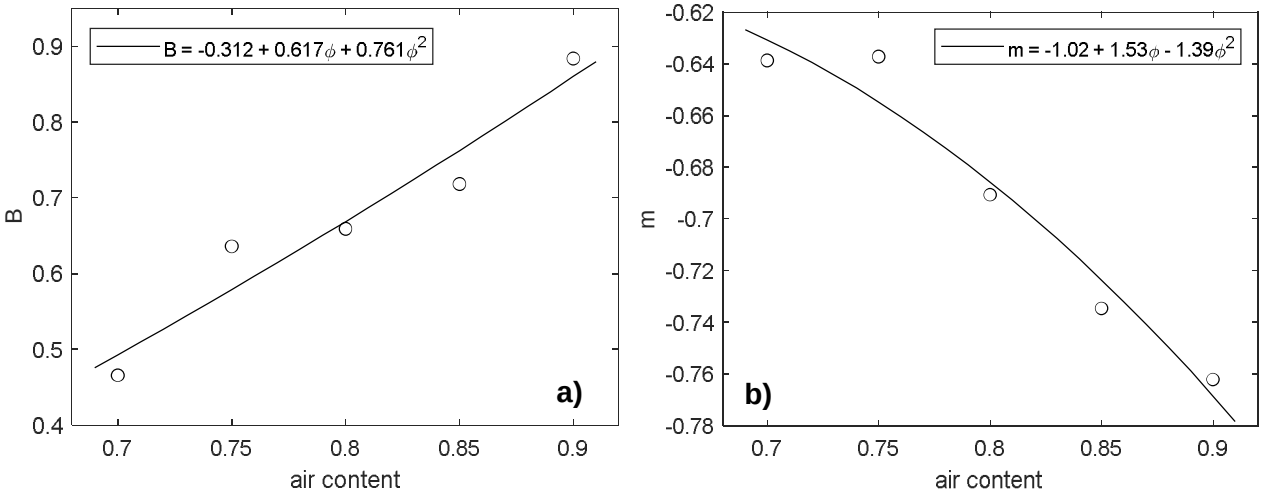

888

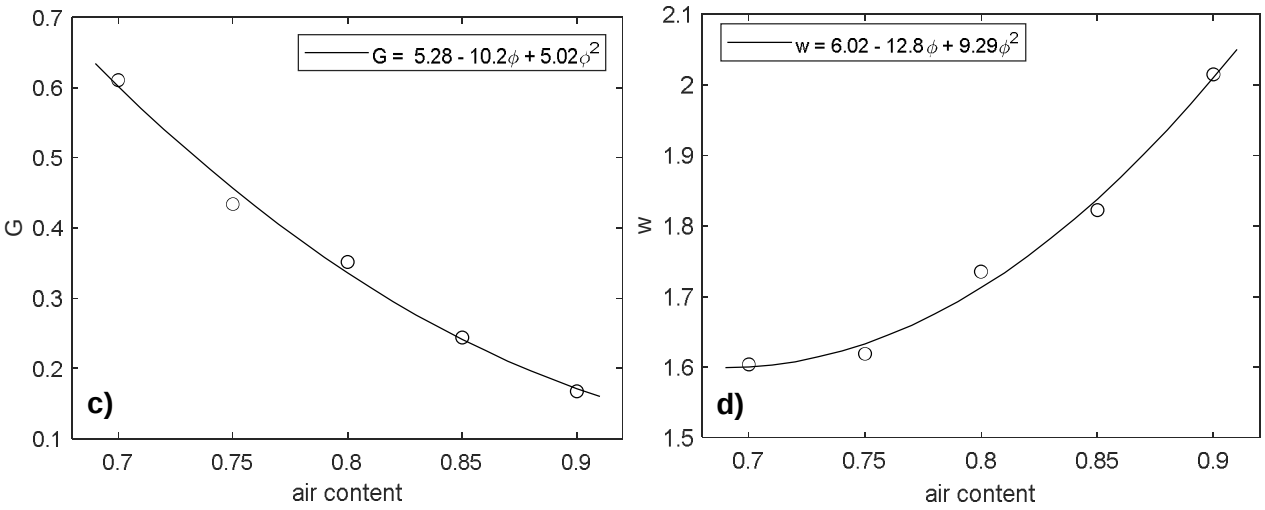

889

890 Figure 24 Fits of second-order polynomials to the values of functions $B(\varphi)$, $m(\varphi)$, $G(\varphi)$ and w(φ)
891 shown in Table 2 and Table 3.

892