

Cerium-doped Fused-silica Fibers as Wavelength Shifters

VERSION 0

**N. Akchurin,^{a,1} J. Damgov^a F. De Guio,^a G. Dissertori,^c E. Kendir,^b S. Kunori,^a T. Mengke,^a
F. Nessi-Tedaldi,^c S. Pigazzini,^d Ş. Yaltkaya^b**

^a*Texas Tech University, Department of Physics and Astronomy, Lubbock, TX, 79409, USA*

^b*Akdeniz University, Department of Physics, Antalya, 07070, Turkey*

^c*ETH, Zürich, Switzerland*

^d ???

E-mail: nural.akchurin@ttu.edu

ABSTRACT: As part of our continued R&D in radiation-hard scintillating and wavelength shifting fibers by doping fused-silica with cerium, we evaluated the performance of a Ce-doped fiber as wavelength shifter coupled to a CeF₃ crystal using electron beams at CERN. The pulse shape and collection efficiency were measured using irradiated (10 MRad) and un-irradiated fibers. In addition, we evaluated the light yield of additional Ce-doped fibers and explored the possibility of using these types of "hybrid" fibers for future precision timing applications in high-luminosity environment.

KEYWORDS: Cerium, optical fibers, fused silica

¹Corresponding author.

Contents

1	Introduction	1
2	Description of Fibers	1
3	Scintillation Light Yield Measurements	4
4	Ce-doped Fibers Coupled to CeF₃ Crystal	5
5	Timing Measurements	7
6	Conclusions	7
7	Acknowledgements	7

1 Introduction

Light emission by plastic scintillators typically degrades by half after a few MRads (a few 10 kGy). Our objective is to explore possible gains in radiation-hardness by doping fused-silica with inorganic “dyes” or rare-earth elements to produce scintillating and/or wavelength shifting fibers. Our experience [1–5] shows that clear (un-doped) fused-silica fibers survive large doses (O[10] MGy), and our preliminary results reported here, and those of others (for example, [6–15]), on doped fused-silica suggest that this approach is likely to result in meaningful progress because there has been accumulation of data complemented by improved understanding of radiation damage and light emission and absorption processes in these types of structures [16–18]. We described our results from the first two prototype fibers (so-called $S^{(1)}$ and $S^{(2)}$ fibers correspond to the Phase-I and -II fibers in this paper) in an earlier publication [19]. In this paper, we report on the performance of additional fibers, Phase-III, Phase-IV, and T14, and especially on their behavior under gamma irradiation. Clear fused-silica fiber containing no dopants was also included as benchmark. This fiber is the same fiber as in the active medium of CMS’s forward calorimeter, and its radiation-hardness properties were well-studied and reported in scientific literature. All fibers reported here are produced by Polymicro Technologies¹.

2 Description of Fibers

The first large-scale (> 1 km) cerium-doped fiber production in this study was that of Phase-I fiber. The cerium-doped core was $60\text{ }\mu\text{m}$ in diameter and enveloped by a $200\text{ }\mu\text{m}$ diameter coaxial glass layer. The core preform was doped with cerium by a proprietary dissolving method, and the Ce:Si

¹Polymicro Technologies is a subsidiary of Molex located in Phoenix, AZ, USA.

molar ratio was $\sim 10^{-3}$. Phase-II fiber was essentially the same as Phase-I except for a larger central core ($150\text{ }\mu\text{m}$ dia.). This fiber was also produced at a large scale ($\sim 2\text{ km}$) using standard industrial techniques.

The core of the Phase-III fiber was Ce-doped ($370\text{ }\mu\text{m}$ dia.) but without a glass layer around it. This fiber was produced to evaluate the efficacy of the clear glass layers in Phase-I and -II fibers in terms of light transport. Phase-IV fiber was produced with a $15\text{-}\mu\text{m}$ thick Ce-doped ring around a $200\text{-}\mu\text{m}$ diameter clear fused-silica core. In addition, a $600\text{-}\mu\text{m}$ diameter glass outer layer was introduced to further improve light transmission. The T14 fiber's Ce-doped core ($150\text{ }\mu\text{m}$ dia.) was surrounded by a high OH^- fused-silica layer ($400\text{ }\mu\text{m}$ dia). In contrast, the outer layers in Phase-I and -II fibers were composed of low OH^- glass.

Table 1 summarizes the dimensions of core, glass, cladding, and buffer while Figure 4 shows the fiber cross-sectional images. Some performance characteristics of Phase-I and -II fibers that were measured with the high energy beams at Fermilab were reported in our first paper [19]: For example, the Phase-I optical attenuation length measured about $5.8 \pm 0.7\text{ m}$ using 16 GeV electrons. The speed of light propagation was $19.50 \pm 0.38\text{ cm/ns}$ and was found to be consistent with the previously reported values [20, 21]. When the tail of the pulse was modeled by a sum of two exponential functions, two decay constants were $\tau_1 = 20.8 \pm 5.4$, and $\tau_2 = 93.0 \pm 12.6\text{ ns}$. The contributions of these components to the total light emission (radioluminescence) turned out to be $23.9 \pm 5.3\%$ and $76.1 \pm 5.3\%$, respectively.

Table 1. All fibers were clad with fluorinated acrylate and UV-cured acrylate buffer.

Fiber Name	Core OD [μm]	Glass OD [μm]	Clad OD [μm]	Buffer OD [μm]
Phase-I	60 ± 7	200 ± 6	230^{+5}_{-10}	350 ± 15
Phase-II	150 ± 20	400 ± 10	430 ± 10	550 ± 30
Phase-III	370 ± 8	-	400 ± 8	550 ± 15
Phase-IV	$200(\text{clear})$ $215(\text{doped})$	600 ± 6	630 ± 10	800 ± 30
Clear fused-silica	600 ± 10	-	630^{+5}_{-10}	800 ± 30
T14	150 ± 5	400 ± 5	450 ± 5	500 ± 15

Experimental setup in the beam figure here...

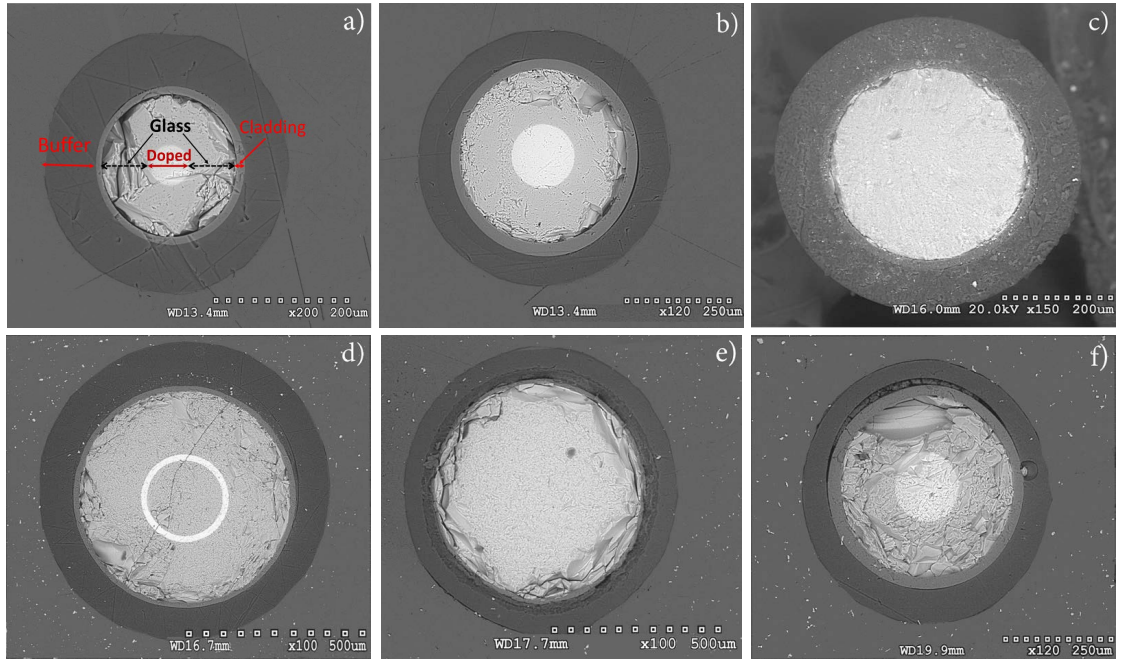


Figure 1. The cross-section of fibers *a)* Phase-I, *b)* -II, *c)* -III, *d)* -IV, *e)* clear fused-silica, and *f)* T14 are shown. The terminology used throughout the paper for different parts of the fiber is indicated on *a)*.

3 Scintillation Light Yield Measurements

R11864, phase4 unirradiated in front SPE 525.213 +/- 10.6236 Q [p.e] = 0.0924285 S [p.e] = 0.14725 S/Q = 1.59313

R11863, phase4 irradiate in front SPE 389.125 +/- 7.04617 Q [p.e] = 0.0578348 S [p.e] = 0.616969 S/Q = 10.6678

Geant4 prediction OD-ID=15um: Cerenkov : 0.131 p.e./evt Scintillation: 0.061 p.e./evt S/Q = 0.47 NB: G4 simulation has OD-ID = 15um for the ce-doped ring . In reality the OR-IR = 15um. Thus the S in this G4 setup is twice smaller and S/Q is twice lower than it should be - to be corrected if this G4 prediction is used. (JD - 18 Oct 2018)

4 Ce-doped Fibers Coupled to CeF₃ Crystal

A short paragraph on the CeF₃ crystal [22]

A figure on the absorption and emission lines of the CeF₃ crystal

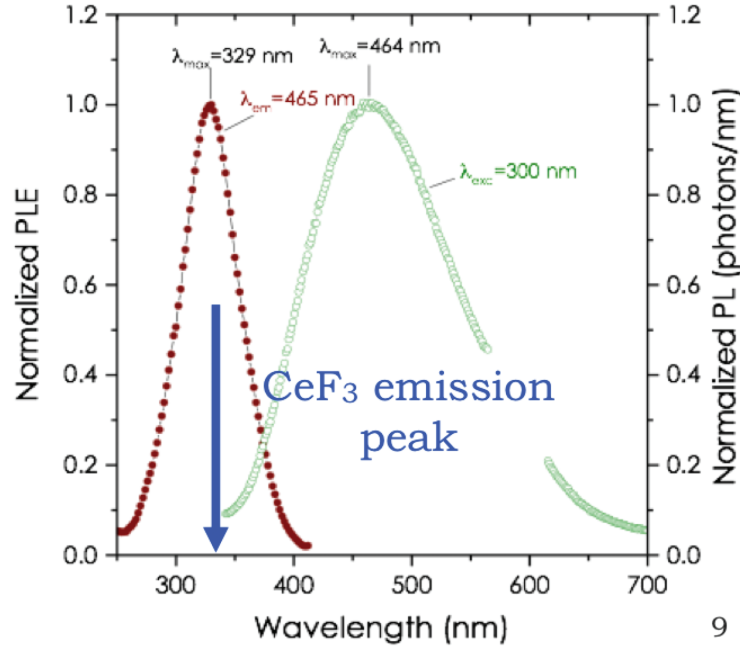


Figure 2. Spectrum.....

A figure on the fibers coupled to the CeF₃ crystal

Two sets of six fibers were air coupled to the larger of the crystal surfaces without optical grease and held in place by a tightly wrapped tyvek sheet as shown in Figure XXXX. One set of six consisted of un-irradiated and the other consisted of irradiated Phase-IV fibers that were viewed independently by photomultiplier tubes (Hamamatsu R6427). Irradiated fibers were subjected to 10 MRad of gamma irradiation three months prior to these measurements and some optical recovery had occurred. For cross calibration purposes between the two channels, the PMTs and the orientation of fibers on the crystal surfaces with respect to the beam direction were swapped in all possible (4) combinations. The PMT signals were read-out by a fast digitizer (CAEN V1742) at 5 GHz and a common trigger was generated by a fast multichannel photomultiplier (MCP). Figure 3 shows the measured spectra where the fast part (0-50 ns) of the spectra is clearly different and the irradiated fibers have lost sensitivity to this temporal region of light emission from the crystal. In the longer time scales (>50 ns), the tail of the signal is essentially the same (XX ns).

The following phenomena are responsible for this effect:

1. In the un-irradiated case (Figure XXX.a), the time structure of the CeF₃ emission is evident. The pulse ...
2. In the irradiated case (Figure XXX.b), the fiber has lost its efficacy due to radiation damage and it is inefficient ...

3. Although the wavelength shifting by the irradiated fiber has been compromised, the total light level has seemingly increased as displayed in Figure XXX.c. The sensitivity of the irradiated fibers to the charged particles has actually gotten larger by a factor of four (?) (Section 3), accidentally compensating for the total signal but not the temporal features of the CeF3 light.

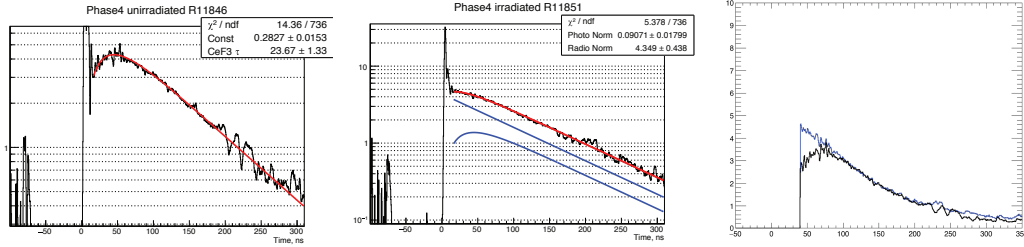


Figure 3. The averaged signals from the CeF₃ crystal coupled to either un-irradiated (left) or irradiated (middle) fibers display a significant difference at the short time scale (0-50 ns). The right plot shows the overlaid spectra when the two channels are calibrated for the same PMT gain. The red curve ... the blue curve...

5 Timing Measurements

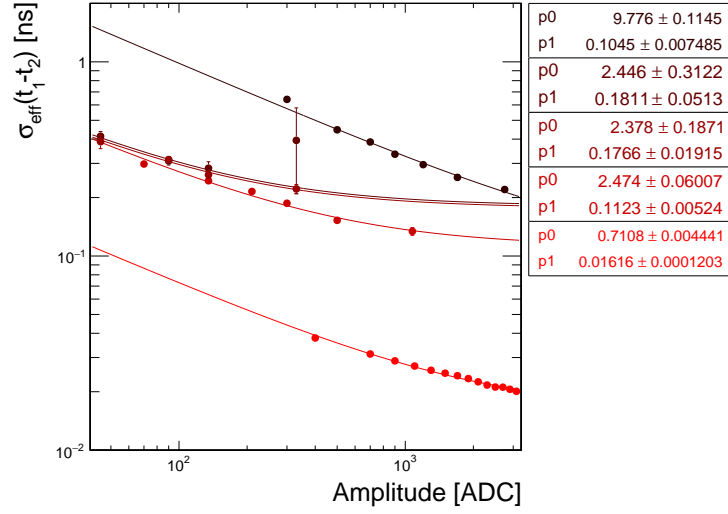


Figure 4. The timing resolution for ...

6 Conclusions

7 Acknowledgements

This work has been supported by the US Department of Energy, Office of Science (DE-SC001592), the Akdeniz University Scientific Research Projects Coordination Department (FDK-2017-2461), and the Scientific and Technological Research Council of Turkey, TÜBİTAK, (No. 1059B141601412). We express our thanks to the AIDA2020 program and to Etienne Auffray-Hillemanns for generously sharing the beam time at CERN. Jim Clarkin and Teo Tichindelean from Polymicro Technologies are thanked for their expertise, continued interest, and commitment to this R&D project.

References

- [1] N. Akchurin, A. Ayan, G. Bencze, I. Dumanoglu, E. Eskut, A. Fenyvesi et al., *Effects of radiation and their consequences for the performance of the forward calorimeters in the CMS experiment*, *Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms* **187** (2002) 66 – 78.
- [2] I. Dumanoglu, N. Akchurin, U. Akgun, S. Ayan, P. Bruecken, E. Eskut et al., *Radiation-hardness studies of high OH^- content quartz fibres irradiated with 500 MeV electrons*, *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment* **490** (2002) 444 – 455.
- [3] N. Akchurin and R. Wigmans, *Quartz fibers as active elements in detectors for particle physics*, *Review of Scientific Instruments* **74** (2003) 2955–2972.
- [4] R. D. Thomas, *Study of Radiation Hardness of Optical Fibers*. Thesis, Texas Tech University, 2004.
- [5] K. Cankocak, M. Bakirci, S. Cerçi, E. Gülmez, J. Merlo, Y. Onel et al., *Radiation-hardness measurements of high OH^- content quartz fibres irradiated with 24 GeV protons up to 1.25 Grad*, *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment* **585** (2008) 20 – 27.
- [6] M. Neff, V. Romano and W. Lüthy, *Metal-doped fibres for broadband emission: Fabrication with granulated oxides*, *Optical Materials* **31** (2008) 247 – 251.
- [7] S. Braccini, A. Ereditato, F. Giacoppo, I. Kreslo, K. P. Nesteruk, M. Nirkko et al., *A beam monitor detector based on doped silica and optical fibres*, *Journal of Instrumentation* **7** (2012) T02001.
- [8] E. Anoikin, A. Guryanov, D. Gusovsky, E. Dianov, V. Mashinsky, S. Miroshnichenko et al., *UV and gamma radiation damage in silica glass and fibres doped with germanium and cerium*, *Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms* **65** (1992) 392 – 396.
- [9] E. R. Rand, M. B. Smuckler, E. Go, M. S. Bradley and J. W. Bruno, *Luminescence studies of Cerium(III) incorporated in silica gels prepared using sol-gel methods*, *Inorganica Chimica Acta* **233** (1995) 71 – 77.
- [10] G. Malashkevich, E. Poddenezhny, I. Melnichenko and A. Boiko, *Optical centers of cerium in silica glasses obtained by the sol-gel process*, *Journal of Non-Crystalline Solids* **188** (1995) 107 – 117.
- [11] G. Q. Xu, Z. X. Zheng, W. M. Tang and Y. C. Wu, *Spectroscopic properties of Ce^{3+} doped silica annealed at different temperatures*, *Journal of Luminescence* **124** (2007) 151–156.
- [12] N. Chiodini, M. Fasoli, M. Martini, E. Rosetta, G. Spinolo, A. Vedda et al., *High-efficiency $SiO_2 : Ce^{3+}$ glass scintillators*, *Applied Physics Letters* **81** (2002) 4374–4376, [<https://doi.org/10.1063/1.1524294>].
- [13] A. Vedda, N. Chiodini, D. Di Martino, M. Fasoli, S. Keffer, A. Lauria et al., *Ce^{3+} -doped fibers for remote radiation dosimetry*, *Applied Physics Letters* **85** (2004) 6356–6358, [<https://doi.org/10.1063/1.1840127>].
- [14] M. Carrara, C. Cavatorta, M. Borroni, C. Tenconi, A. Cerrotta, C. Fallai et al., *Characterization of a Ce^{3+} doped SiO_2 optical dosimeter for dose measurements in HDR brachytherapy*, *Radiation Measurements* **56** (2013) 312 – 315.
- [15] N. Caretto, N. Chiodini, F. Moretti, D. Origgi, G. Tosi and A. Vedda, *Feasibility of dose assessment in radiological diagnostic equipments using Ce-doped radio-luminescent optical fibers*, *Nuclear*

Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment **612** (2010) 407 – 411.

- [16] D. L. Griscom, M. E. Gingerich and E. J. Friebele, *Radiation-induced defects in glasses: Origin of power-law dependence of concentration on dose*, *Phys. Rev. Lett.* **71** (Aug, 1993) 1019–1022.
- [17] V. A. Mashkov, W. R. Austin, L. Zhang and R. G. Leisure, *Fundamental Role of Creation and Activation in Radiation-Induced Defect Production in High-Purity Amorphous SiO₂*, *Physical Review Letters* **76** (Apr, 1996) 2926–2929.
- [18] C. D. Marshall, J. A. Speth and S. A. Payne, *Induced optical absorption in gamma, neutron and ultraviolet irradiated fused quartz and silica*, *Journal of Non-Crystalline Solids* **212** (1997) 59 – 73.
- [19] N. Akchurin, C. Cowden, J. Damgov, C. Dragoiu, P. Duderø, J. Faulkner et al., *Cerium-doped scintillating fused-silica fibers*, *Journal of Instrumentation* **13** (2018) P04010.
- [20] P. Gorodetzky, D. Lazic, G. Anzivino, E. Chiavassa, A. Contin, G. Dellacasa et al., *Quartz fiber calorimetry*, *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment* **361** (1995) 161 – 179.
- [21] N. Akchurin, K. Carrell, J. Hauptman, H. Kim, H. Paar, A. Penzo et al., *Electron detection with a dual-readout calorimeter*, *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment* **536** (2005) 29 – 51.
- [22] R. Becker, G. Dissertori, A. Gendotti, Q. Huang, D. Luckey, W. Lustermann et al., *Proof-of-principle of a new geometry for sampling calorimetry using inorganic scintillator plates*, *Journal of Physics: Conference Series* **587** (2015) 012039.