Noname manuscript No.
(will be inserted by the editor)

Pikunda-Munda

Disappearance of Pottery Production in the Western Congo Basin at the end of the Early Iron Age

Dirk Seidensticker

Received: date / Accepted: date

Abstract The history of pottery-producing communities in Central Africa has long been seen as a study of its spread. While this process started about two-and-a-half millennia ago, it is often linked with the so-called 'Bantu Expansion'. Linguistic studies claimed substantial migratory events through the so-called 'Sangha River Interval', which mostly coincides with the Sangha river valley and the western part of the Congo Basin. This region is viewed as a 'gateway' communities followed to cross the equatorial rainforest during their spread south.

This paper presents novel data on the oldest widespread pottery from that region, the Pikunda-Munda style. Its emergence in the last century BCE is equally shrouded in secret as its disappearance in the 5th to 6th century CE. The latter coincides with a distinct period of low human activity (600-1000 CE) observed throughout Central Africa.

New research into the technological decisions or *chaîne opératoire* of the potters' communities that produced Pikunda-Munda pottery revealed that they followed a distinct path, different from that in adjacent regions such as the Inner Congo Basin. Only regarding clay procurement and processing similar preferences for fluvial clay sources rich in sponge spicules can be seen. Drawing of a ring is the primary shaping or roughing-out technique and differences in how the bottoms were attached or closed indicate differences in trans-generational training networks among potters' communities of practice.

The disappearances of the Pikunda-Munda pottery marks an apparent abandonment of pottery production along the middle and lower Sangha river, with knowledge networks established earlier falling apart. There is little evi-

Dirk Seidensticker
Ghent University
Department of Archaeology
UFO, Sint-Pietersnieuwstraat 35
B-9000 Ghent
E-mail: dirk.seidensticker@ugent.be

dence for the persistence of the specific knowledge of Pikunda-Munda potters' communities. All groups encountered after the setback show evidence of them originating from groups found in the Inner Congo Basin. Potters' communities responsible for the Pikunda-Munda pottery were among those whose knowledge transfer was interrupted by the widespread setback in human activity observed throughout the wider region.

Résumé L'histoire des communautés productrices de poterie en Afrique centrale a longtemps été considérée comme une étude de sa propagation. Bien que ce processus ait commencé il y a environ deux millénaires et demi, il est souvent lié à la soi-disant «expansion bantoue». Des études linguistiques ont revendiqué des événements migratoires substantiels à travers le soi-disant «intervalle de la rivière Sangha», qui coïncide principalement avec la vallée de la rivière Sangha et la partie ouest du bassin du Congo. Cette région est considérée comme une «passerelle» des communautés suivies pour traverser la forêt tropicale équatoriale pendant leur propagation vers le sud.

Cet article présente de nouvelles données sur la plus ancienne poterie répandue de cette région, le style Pikunda-Munda. Son émergence au cours du siècle dernier BCE est également enveloppée de secret que sa disparition du 5e au 6ème siècle. Ce dernier coïncide avec une période distincte de faible activité humaine (600-1000 CE) observée dans toute l'Afrique centrale.

De nouvelles recherches sur les décisions technologiques ou l'opératoire de *chaîne opératoire* des communautés des potiers qui produisaient la poterie Pikunda-Munda ont révélé qu'ils suivaient un chemin distinct, différent de celui des régions adjacentes telles que le bassin intérieur du Congo. Ce n'est qu'en ce qui concerne l'approvisionnement en argile et le traitement des préférences similaires pour les sources d'argile fluviale riches en épicules éponges. Le dessin d'un anneau est la principale technique de mise en forme ou de brouillage et les différences dans la façon dont les fonds ont été attachés ou fermés indiquent des différences dans les réseaux d'entraînement transgénérationnels parmi les communautés de pratique des potiers.

Les disparitions de la poterie Pikunda-Munda marquent un abandon apparent de la production de poterie le long de la rivière du milieu et du bas de Sangha, avec des réseaux de connaissances établis plus tôt en train de s'effondrer. Il existe peu de preuves de la persistance de la connaissance spécifique des communautés des potiers de Pikunda-Munda. Tous les groupes rencontrés après le revers montrent des preuves d'eux provenant de groupes trouvés dans le bassin intérieur du Congo. Les communautés des potiers responsables de la poterie Pikunda-Munda faisaient partie de celles dont le transfert de connaissances a été interrompu par le revers généralisé dans l'activité humaine observée dans toute la région plus large.

Keywords Congo Basin · Ceramics · Knowledge transfer · *Chaîne opératoire* · Middle Iron Age Hiatus

1 Introduction

The spread of pottery-producing communities throughout Central Africa is regularly linked with the so-called 'Bantu Expansion' (Bostoen 2018, 2020). The diversity of Bantu-languages spoken today is attributed to demic diffusion (Pakendorf et al. 2011; Bostoen and Gunnink 2022) and linguistic reconstructions of putative pathways favor rapid migrations through the equatorial rainforests of Central Africa (Bostoen et al. 2015; Grollemund et al. 2015, 2023; Koile et al. 2022). To cope with the lack of historicity in modern language data archaeological results are used to temporally 'calibrate' these migratory events. The resulting synopses are based on 'circular reasoning' (Eggert 2016), usually involving the premise that the emergence of pottery in a given region equates with the arrival of Bantu-speakers (Bostoen et al. 2015, 355, 362, 364).

These overreaching linguistic models still influence archaeological research (Eggert 2005, 2012, 2016) and force a stringent examination of (dis)-continuities within the archaeological record. The primary source of information on the material culture of communities living in Central Africa for the past 2.500 years are ceramic finds (Eggert 2014). Comprehensive sequences of pottery production are mainly known from the Congo Basin (Wotzka 1995; Seidensticker 2021) and Gabon (Clist 2004/2005). Research in other regions, such as Cameroon (Gouem Gouem 2010/2011; Nlend Nlend 2013/2014), yielded partial and regional sequences, often with missing details on the younger parts of the sequence. Despite disparate research focuses and lack of data, as vast regions have not been studied at all, a general trend with consecutive 'boom-and-bust' phases within the record of human activity in Central Africa can be reconstructed (Oslisly 1998; Oslisly et al. 2013b,a; de Saulieu et al. 2017, 2021; Seidensticker et al. 2021). A profound setback in human activity dates between the 7th to 10th century CE and divides the Early and Late Iron Ages. This widespread phase of 'low activity' (Seidensticker et al. 2021, Fig. 2) questions the underlying assumption of historical linguists concerning a direct connection between early ceramic finds in a given region and modern Bantu-speech communities (Grollemund et al. 2015; Bostoen et al. 2015) and, with it, the proposed reconstruction of the 'Bantu-Expansion' as a single migratory event (Currie et al. 2013; Koile et al. 2022; Grollemund et al. 2023).

The temporal variability in the activity of ancient pottery-producing communities over the past 3.000 years can best be derived from the available record of radiocarbon dates associated with properly described pottery finds (Seidensticker and Hubau 2021). An empirical summed probability distribution (SPD) computed from these dates, following a rigorous assessment of their 'chronometric hygiene' (Napolitano et al. 2019), already shows a distinct bimodal pattern (Fig. 2B: black line). To constrain the timing of distinct periods of over- or under-representation, the observed SPD can be compared with different models of hypothetical population growth using the rcarbon software (Bevan and Crema 2022). This analysis resulted in four successive periods during which the observed SPD either exceeds or falls short of the population growth trends predicted by four distinct models (Fig. 2B: blue and red shading, respectively).

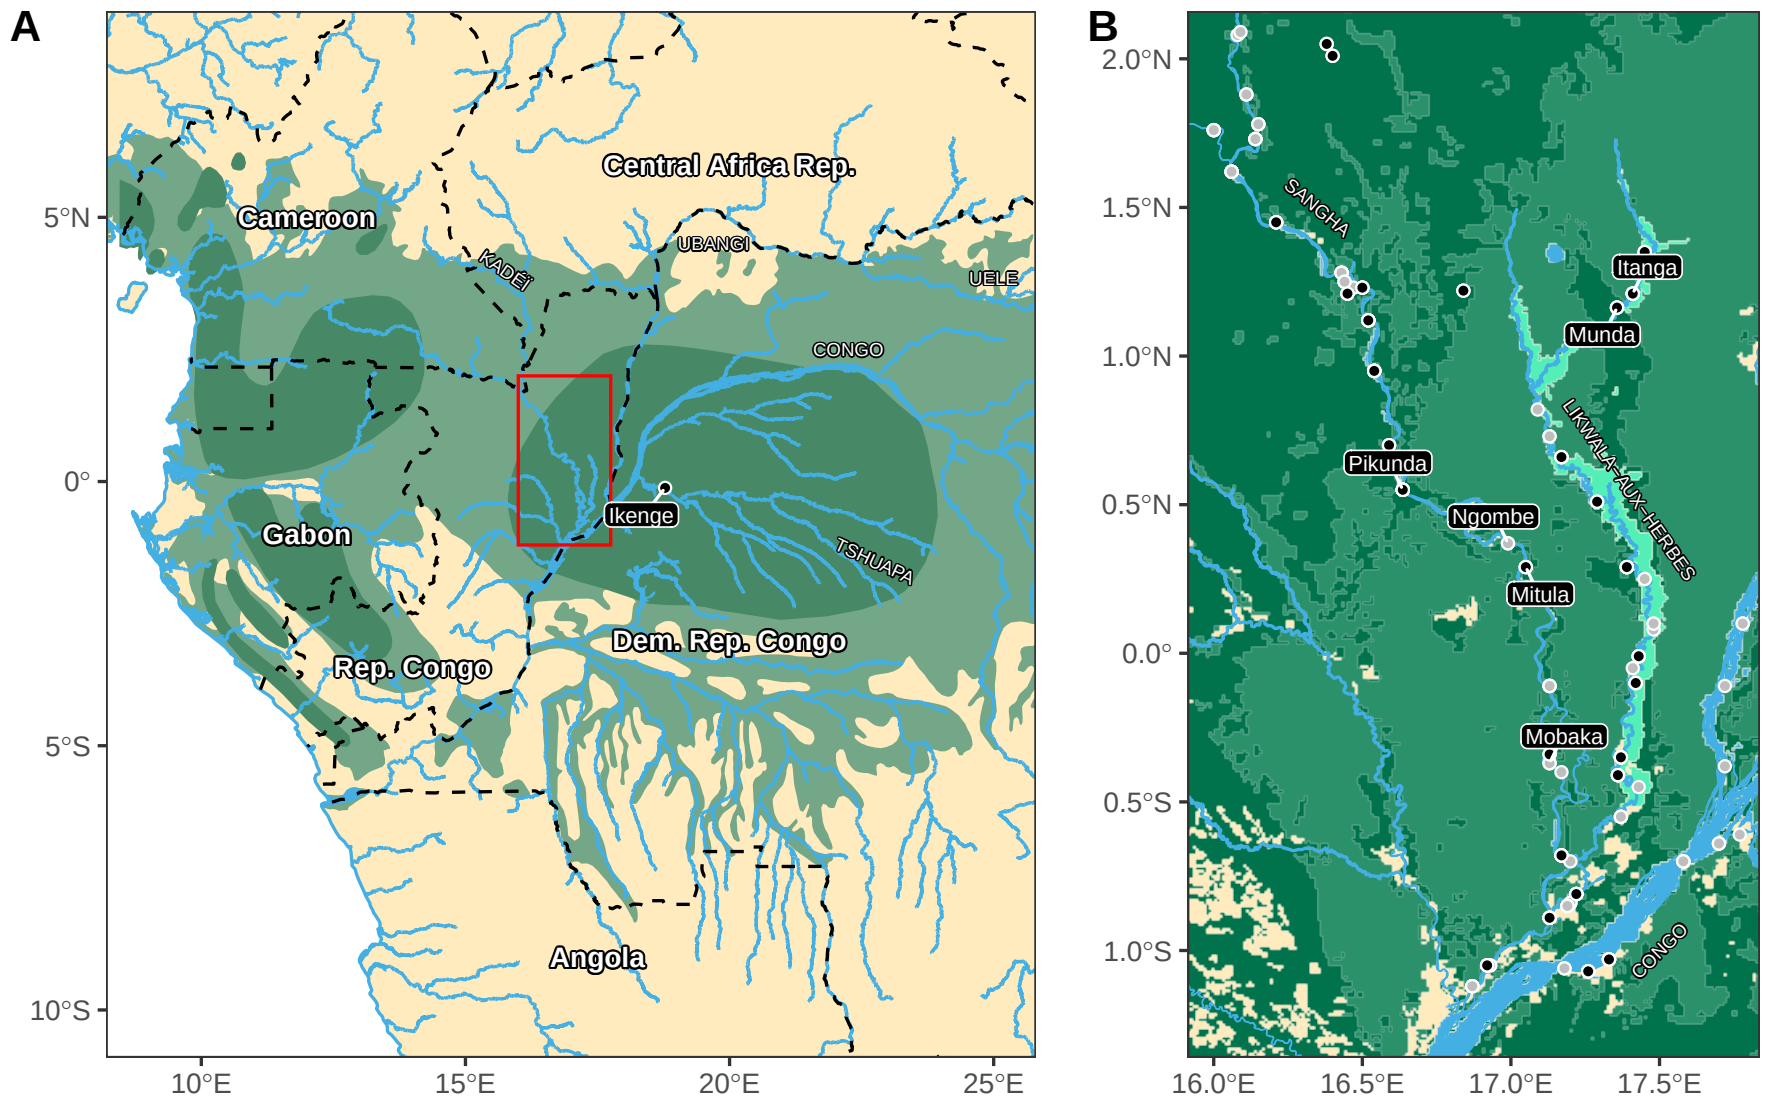

Fig. 1: Map of Central Africa (A) with the distribution of equatorial rainforest (White 1983) (light green) and its putative distribution during the 1st millennium BCE (Bremond et al. 2017; Maley et al. 2017) (dark green). The map of the study area along the rivers Sangha and Likwala-aux-Herbes (B) shows the distribution of landcover types based on satellite data (Mayaux et al. 2003): closed evergreen rainforest vegetation (dark green), swamp forest (medium green), and swamp bush- and grassland (light green). Black dots show sites with Pikunda-Munda style pottery, while grey dots represent sites with other pottery finds (Seidensticker 2021, 11 Fig. 1, 119 Fig. 49).

A logistic growth model (Fig. 2B: grey envelope) is probably most pertinent in the context of the 'Bantu-Expansion', which is often presented as a large-scale and exceptionally rapid process followed by a continuous presence of Bantu-speaking people after the initial expansion (Pakendorf et al. 2011; Grollemund et al. 2015; Bostoen et al. 2015; Bostoen and Gunnink 2022; Koile et al. 2022). Additionally, the empirical SPD was also tested against a 'uniform' model, representing a stable system, and two growth models; one representing 'linear' growth, while the second represents a scenario with 'exponential' growth. While Clist et al. (2023) deem various research biases impeding robust modeling, the combination of all four models provides a clear signal for a distinct setback in human activity throughout the Central African equatorial rainforest, but not complete abandonment, between the 7th and 10th century CE (Seidensticker and Hubau 2021), challenging assumptions of direct continuity between early and modern potters' communities.

Additional corroboration of these findings come from the meta-data of known pottery groups in Central Africa. The summed frequency of contemporaneous sites modeled for each known pottery style using a Gaussian nor-

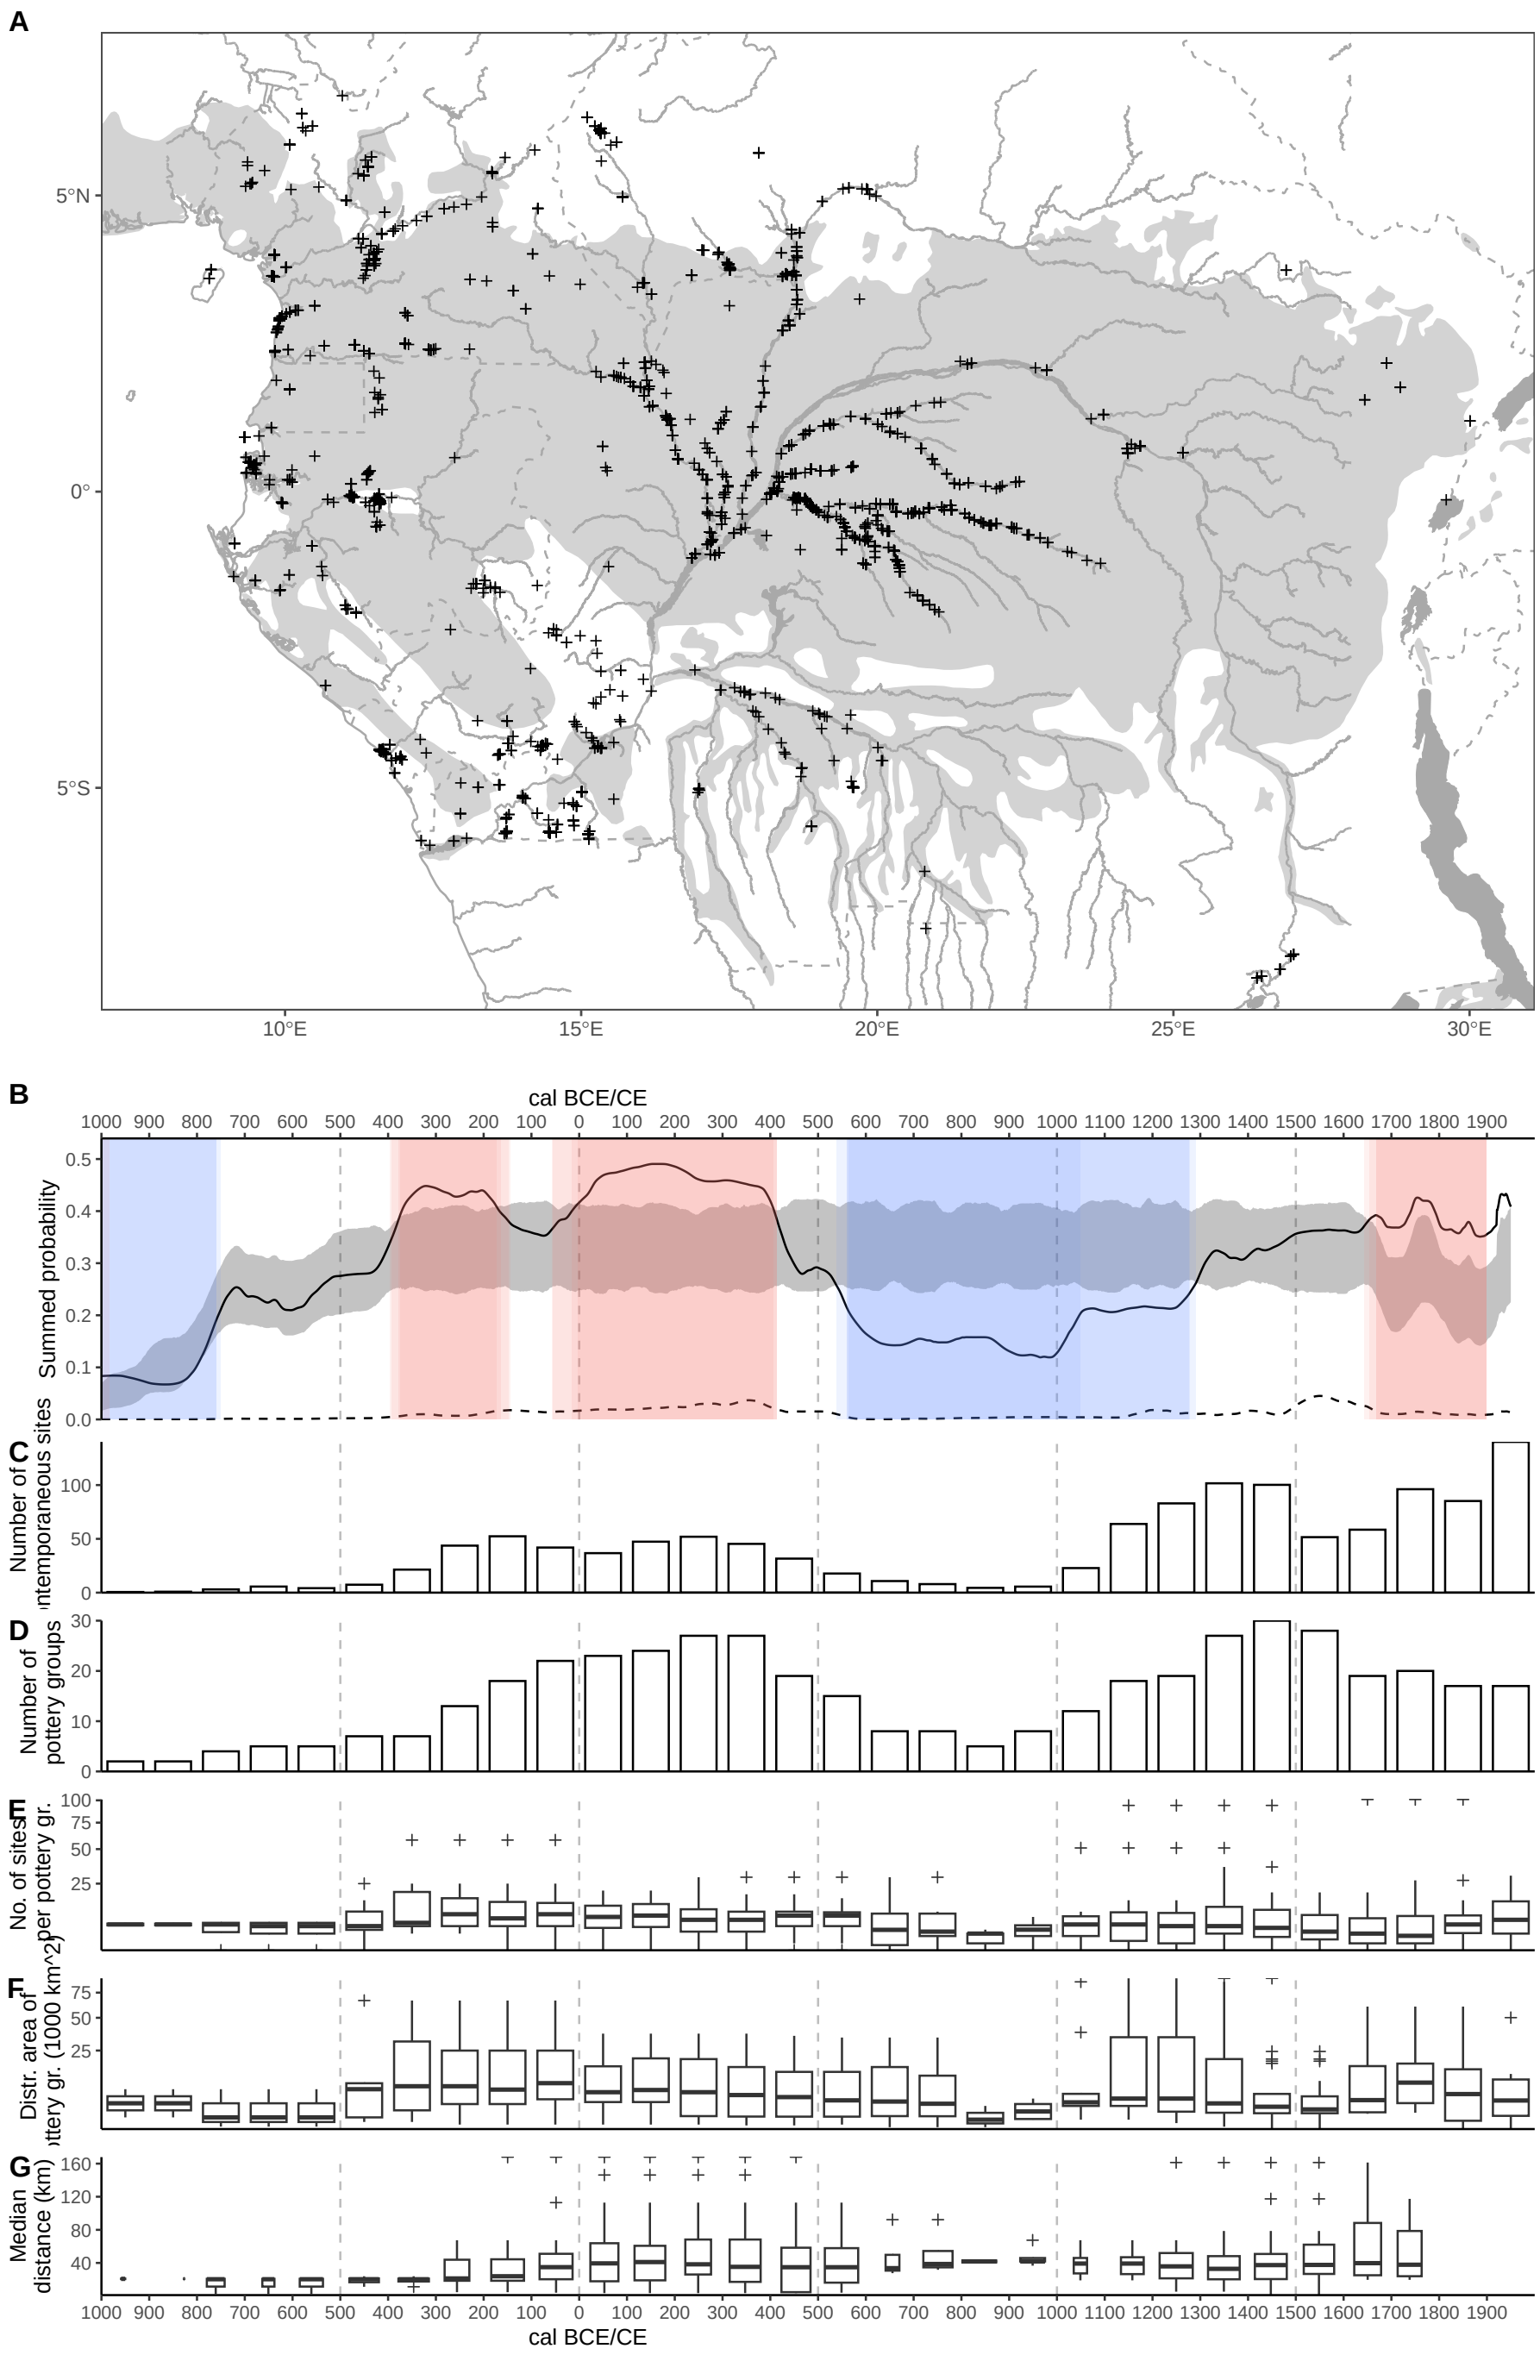

Fig. 2: (Caption next page.)

Fig. 2: **A)** Map of sites with radiocarbon dates or dated pottery finds. Light grey shading shows distribution of equatorial rainforest today (White 1983). **B)** Temporal variation in the activity of ancient pottery-producing communities in the Congo rainforest over the past 3000 years (regions A–H in Seidensticker et al. 2021, Fig. 2). Activity is discussed based on the SPD (full black lines) of all class Ia–c and IIa archaeological 14C dates (n = 1042) (Seidensticker and Hubau 2021), smoothed using a 60-year moving average. The dashed line represents the SPD for sites in the Sangha/Likwala-aux-Herbes region. Grey background shading represents the 95 % uncertainty envelope of summed probability in a logistic model of hypothetical population growth drawn from the same 14C datasets (Bevan and Crema 2022). Color shading demarcates periods of more or less intense human activity, defined as time windows during which the observed SPD surpasses (red; 'heating up') or falls below (red, 'cooling down') one (light shading) or multiple (dark shading) growth models (based on 1000 MC runs). Note that the color scheme has been inverted compared to (Seidensticker et al. 2021, Fig. 2) to correspond to other studies using the same methodology (Crema et al. 2016; Bevan et al. 2017; Riris 2018; Riris and Arroyo-Kalin 2019; Brown and Crema 2019; Arroyo-Kalin and Riris 2021; de Souza and Riris 2021). **C)** Summed frequency of contemporaneous sites. The number of known sites for each pottery style was allocated for each century bin using a hypothesized function, in this case, Gaussian normal distribution, representing changes in saturation during the lifespan of a particular style (Roberts et al. 2012). **D–G)** Evolution of the numerical abundance and geographical distribution of pottery styles in the Congo rainforest (Seidensticker et al. 2021, Fig. 3). Abundance **(D)** is quantified as the number of pottery groups recorded within each century bin; spatial distribution is quantified as the number of sites where each pottery group is found **(E)** and by its total area of distribution **(F)**. **G)** The median distances of sites pertaining to the same pottery group per century bin. Distances were calculated by constructing a network for each pottery group with more than five sites. For each group, sites were connected with their four nearest neighbors (Bivand et al. 2023).

mal distribution Roberts et al. (2012) shows a distinct, bimodal trend as well (Fig. 2C): a surge in the number of sites in the second half of the 1st millennium BCE, that led into a stagnation phase, which is followed by a decline. The number of sites only increases after 1.000 CE again. The same pattern can be observed when viewing the number of pottery styles through time (Fig. 2D). The 'evolution' of pottery producing communities in Central Africa confirms the temporal fluctuations reflected in the supra-regional SPD of archaeological radiocarbon dates (Fig. 2B) and unveils a two-phase pattern during both the Early and Late Iron Age periods. Each starts with a phase of expansion during which stylistically homogeneous pottery groups became widely distributed and ends with a phase of high activity characterized by increasing abundance of

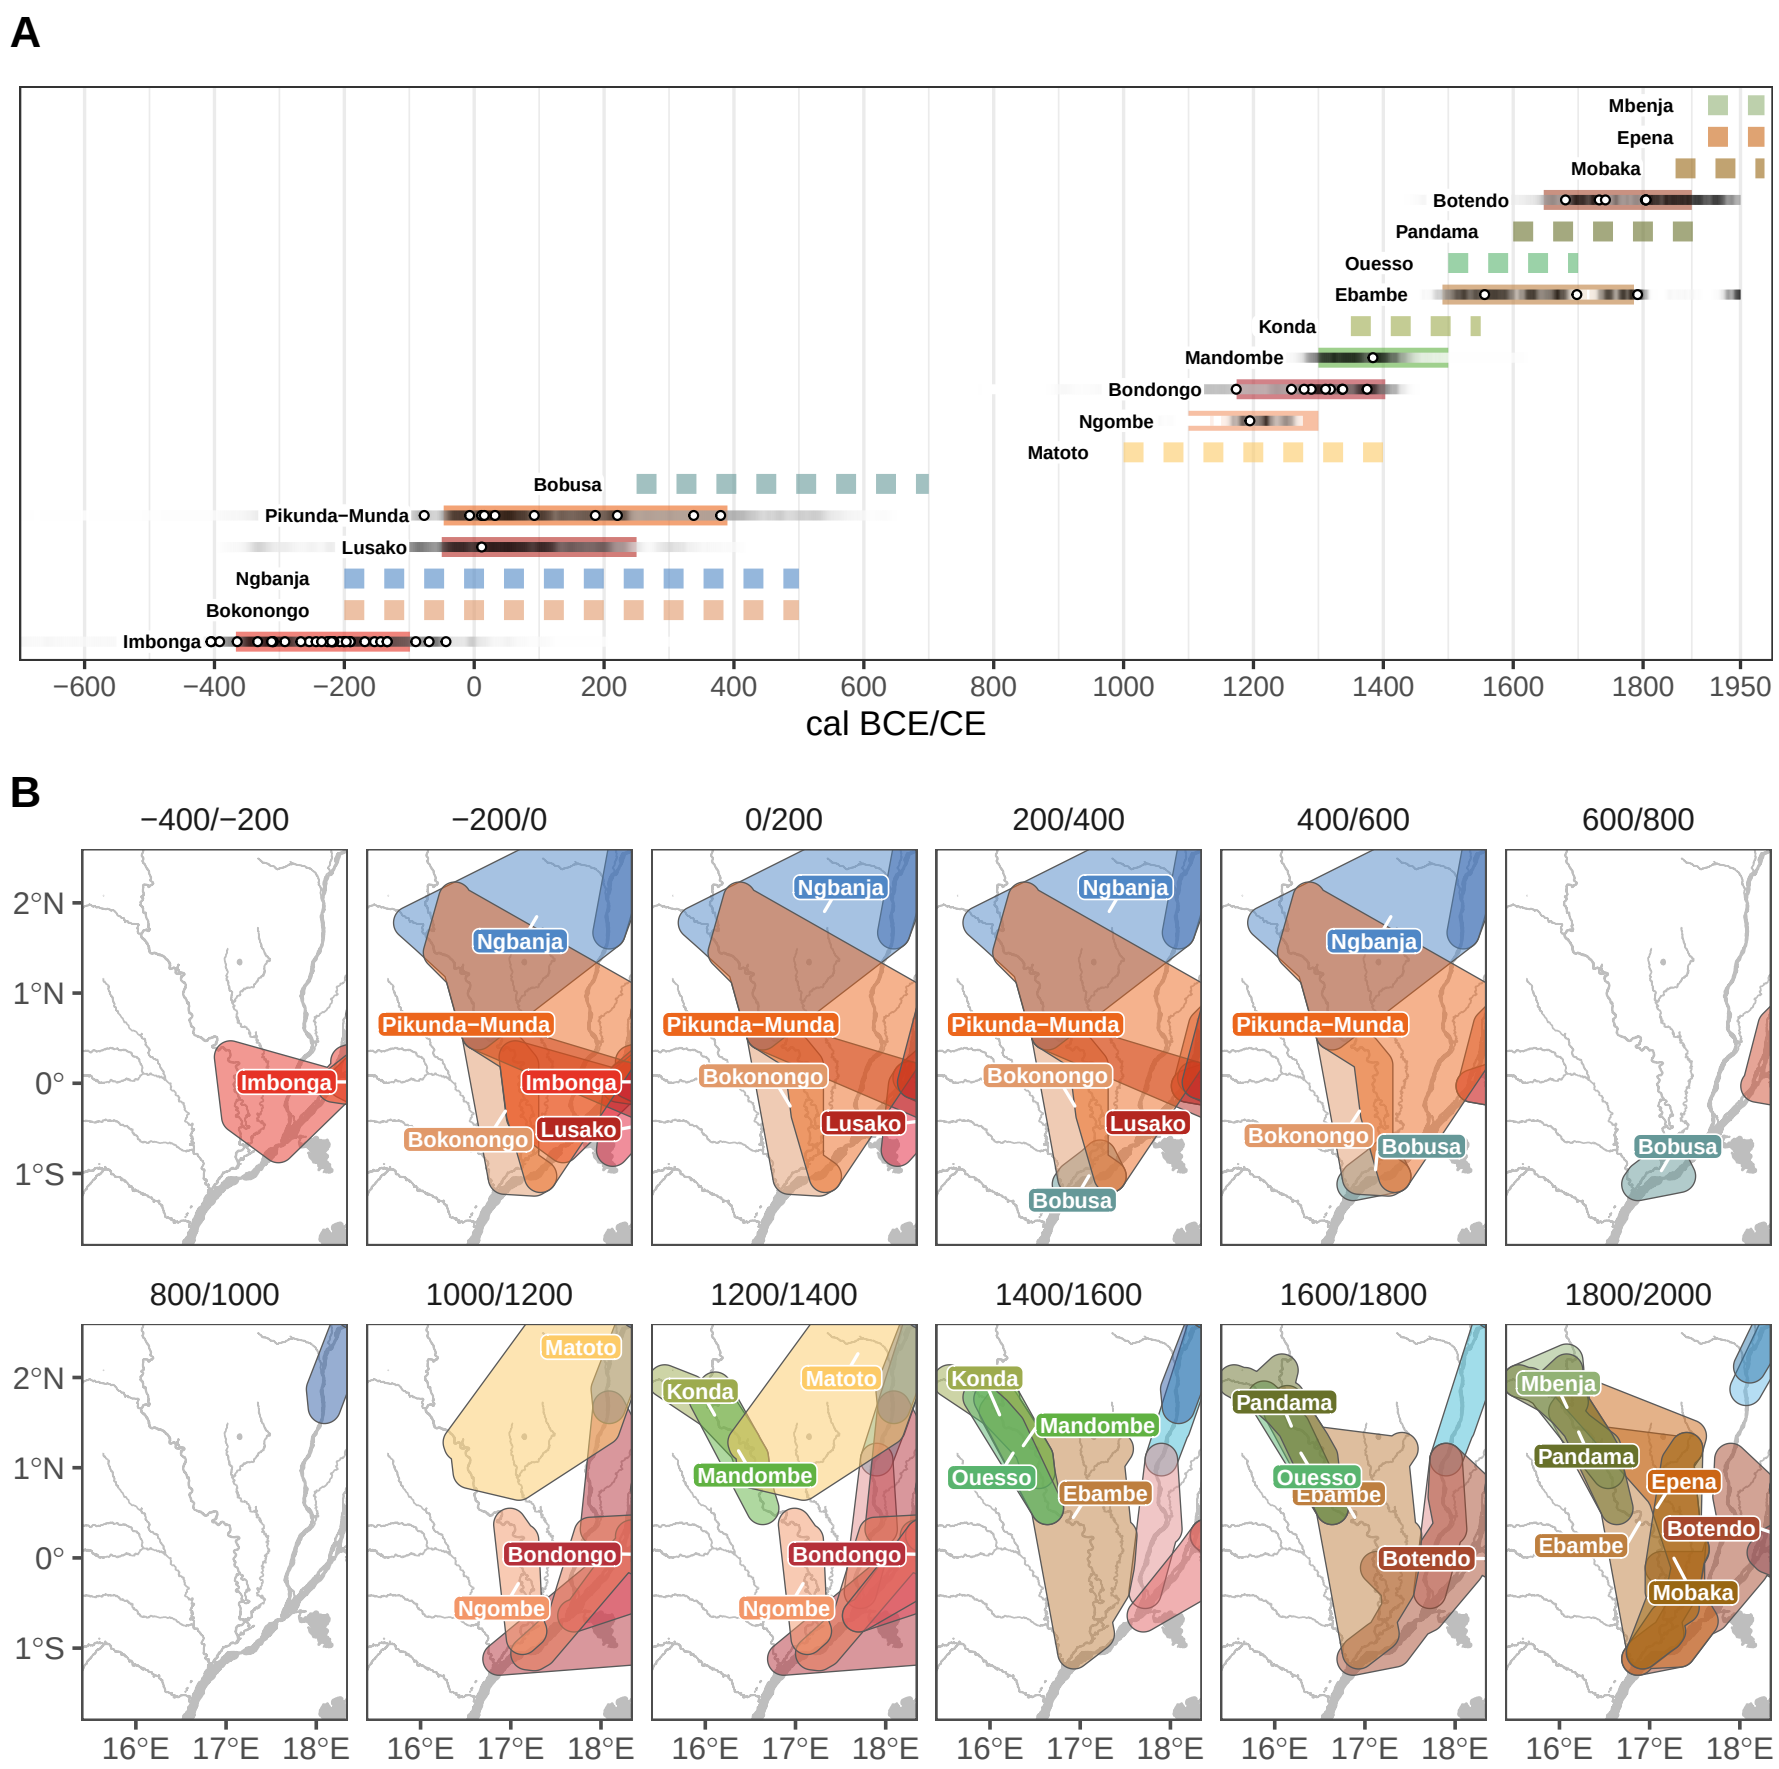

Fig. 3: Spatio-temporal distribution of known pottery styles in the Western Congo Basin (Fig.16) over the past 2600 years. **A)** Circles represent the highest probability of calibrated calendar age of each pottery-linked 14C date. The intensity of grey-shading is proportional to the summed probability of the calendar-age windows of all pottery occurrences by type. Colored bars represent the phase duration of radiocarbon dates pottery styles. For groups with more than two associated radiocarbon dates, the phases' median start and end dates were calculated using a Bayesian model (Crema and Di Napoli 2021; Crema and Shoda 2021; Seidensticker 2024, Fig. S1,Tab. S1). Dashed colored bars indicate estimated bins derived from stylistic resemblance (Seidensticker et al. 2021, Data S2). **B)** Time-sliced maps of occurrences of pottery styles in the Western Congo Basin. Negative numbers indicate calibrated ages BCE, while positive numbers represent calibrated ages CE. Extend per type was calculated as concave hull (Gombin et al. 2017) with a added buffer of 20 km. Colors correspond to **(A)**.

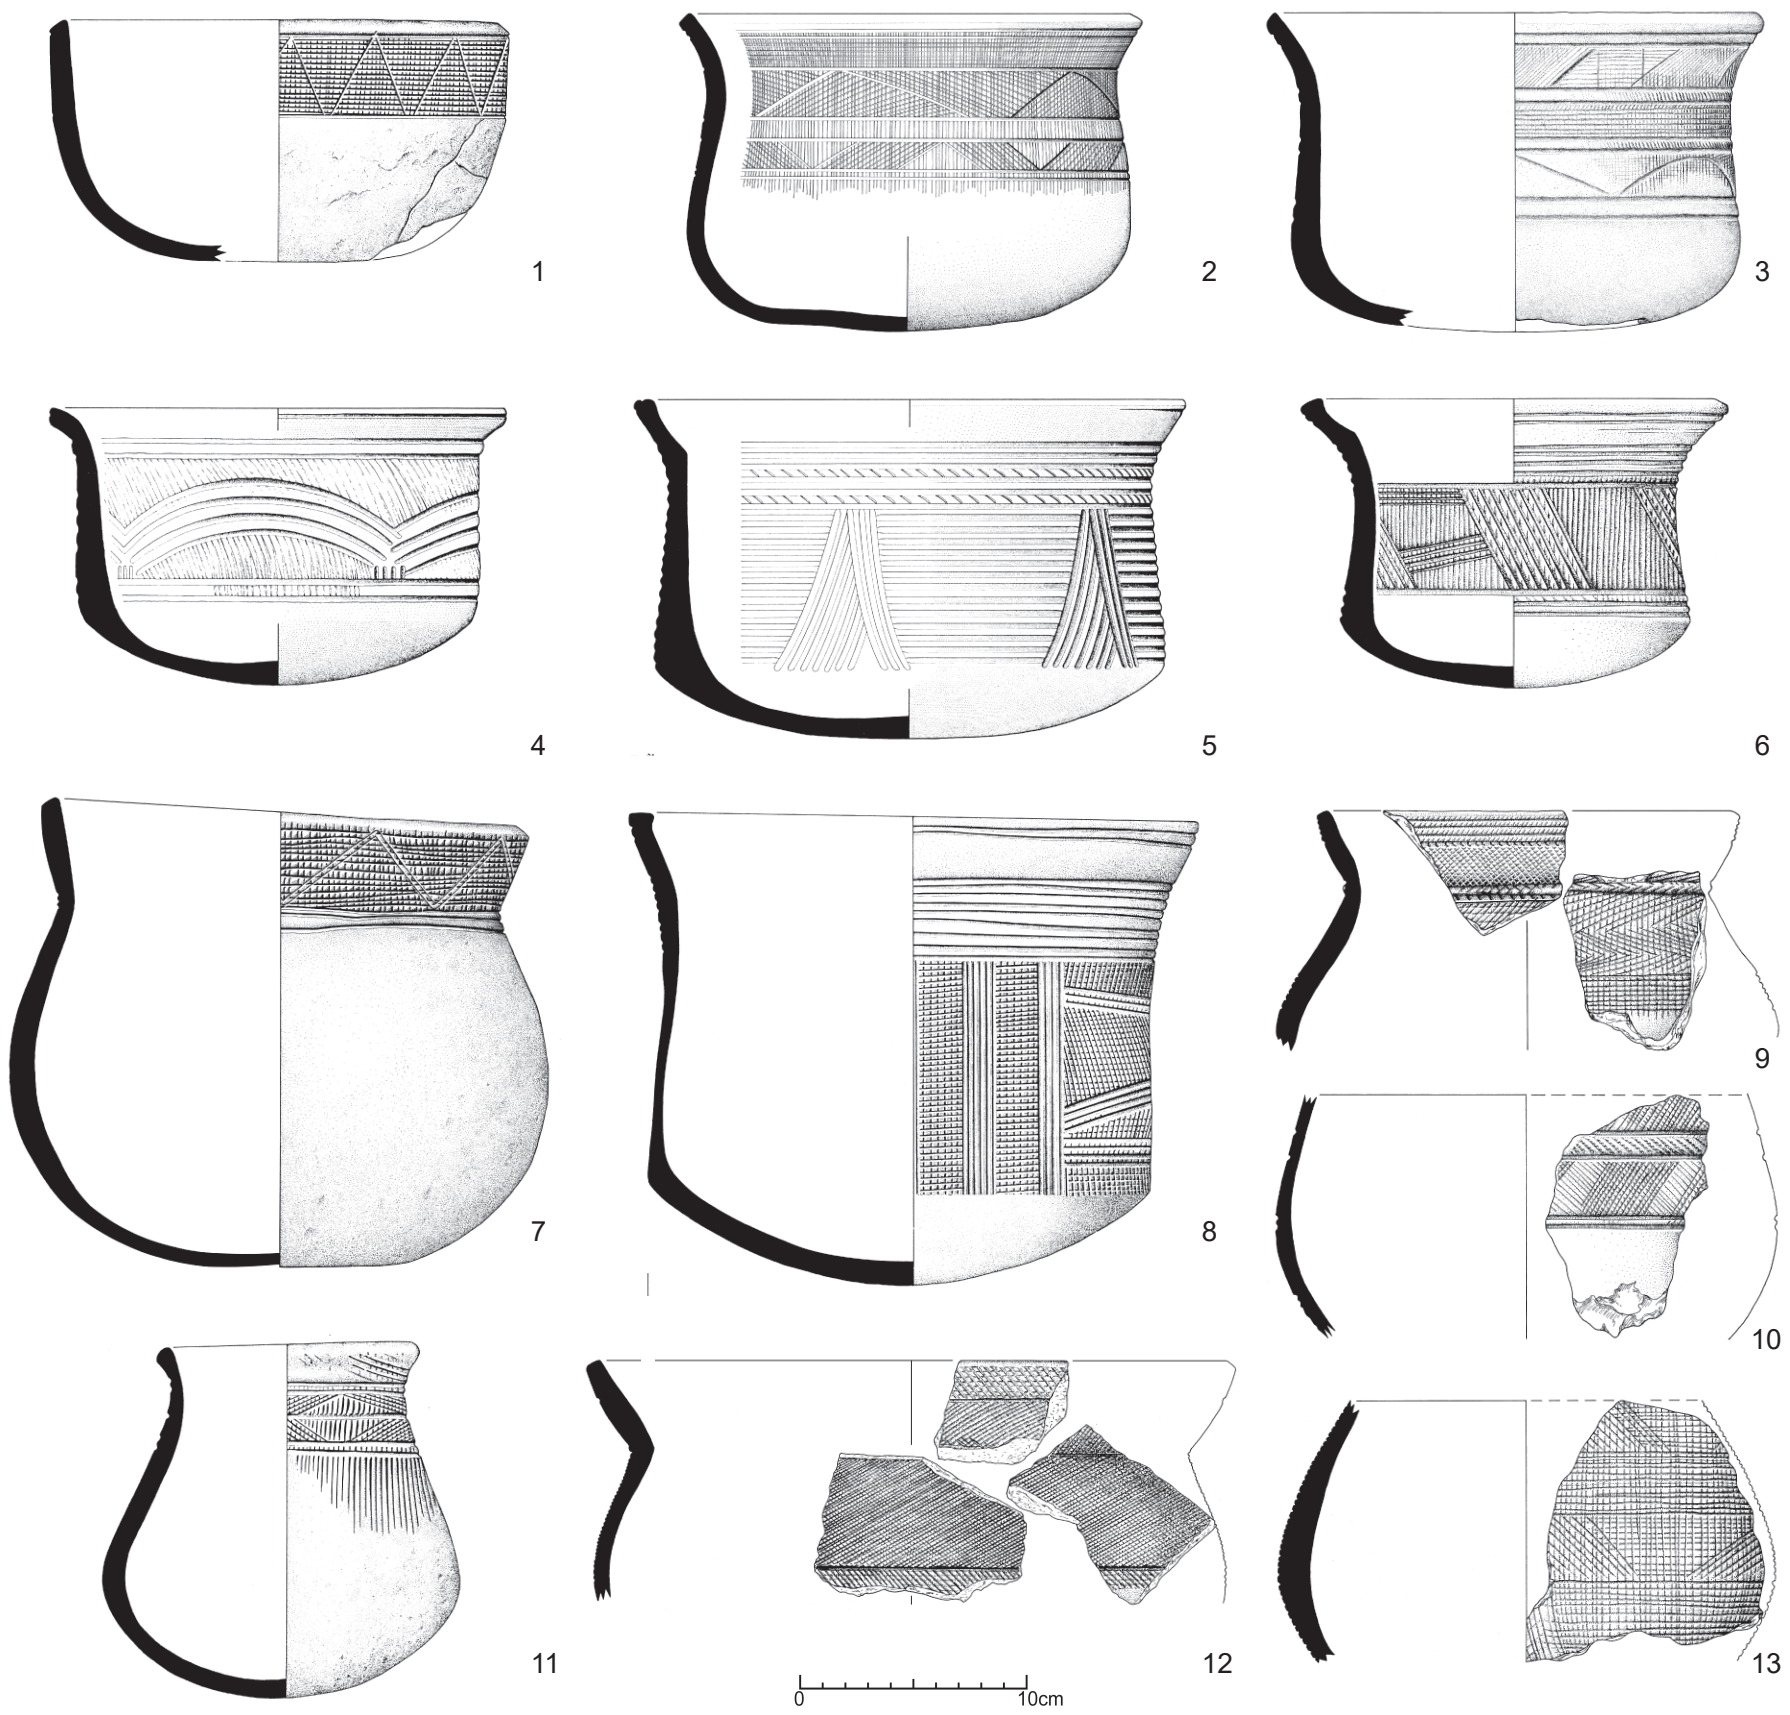

Fig. 4: Characteristic spectra of vessels associated with the Pikunda-Munda style group. (Drawings: Rita Vollbracht)

local pottery styles reflecting a process of regionalization (Seidensticker et al. 2021).

The Pikunda-Munda style (Seidensticker 2021, 114–120), first described by Manfred Eggert (1992, 1993) following fieldwork of the *River Reconnaissance Project* in 1987, is the oldest widespread pottery found throughout the western Congo Basin (Fig. 1B; 3). Only isolated finds of vessel parts associated with the Imbonga style in Mobaka and Mitula are older (Fig. 1B; Seidensticker 2021, 169–172). The distribution area of the Pikunda-Munda style is about 300 to 150 km large (black dots in Fig. 1B). Its main characteristic, or type-species, are wide, open-mouthed bowls with approximately parallel or concave sides, flared rims and rounded bases (Fig. 4). The general ornament scheme is based on linear elements produced through incision and grooving. Rocker-stamp decoration is occasionally present. Stylistically, it shows some similarities to contemporaneous groups of the Inner Congo Basin, such as the styles Lokondola, Lusako, Lingonda, and Bokuma (Wotzka 1995, 107). The available data point towards an interpretation in which the Pikunda-Munda style is a rather distant sub-stream of the Equator-Co style tradition and no fully independent entity (Seidensticker 2021, 192). Based on the current knowledge of the region's archaeology, the style has no known predecessor in the western Congo Basin. It is furthermore remarkable that its characteristics vanish from the region in the 5th to 6th century CE. All subsequent pottery styles found within the distribution area of the Pikunda-Munda style have their origin either in the Equator-Co tradition of the Inner Congo Basin (Wotzka 1995, 222-224 Fig. 4,273) or the Ngoko style tradition originating in south-east Cameroon (Seidensticker 2021, 189–192) (Fig. 3).

Thus, the settlement history of the western Congo Basin follows the general bimodal picture (Seidensticker 2016, 2021, 2024) and the disappearance of pottery in the region after the 5th to 6th century CE underlines the inaccuracies actuated by simple historical projections of modern language data (Grollemund et al. 2015; Bostoen et al. 2015; Koile et al. 2022). It further raises the question of what happened to communities living in the western Congo Basin at the end of the Early Iron Age.

2 Materials and Methods

2.1 Pikunda-Munda style pottery

The Pikunda-Munda pottery style, among the oldest along the rivers Sangha and Likwala-aux-Herbes, was first described by Eggert (1992). Pottery of this style has been excavated at the two eponymous sites: Pikunda along the middle Sangha river and Munda on the upper Likwala-aux-Herbes river (Fig. 1B). In total, 37 complete vessels, or sufficiently preserved pieces allowing reconstruction of the entire profile, belonging to the Pikunda-Munda style have been uncovered (Seidensticker 2021, 114–115). The pottery is known from seven sites in the western Congo Basin (Seidensticker 2021, 119–120 Fig. 49). With some reservations, sherds from another 24 sites, including one in the Inner Congo basin, can be assigned to the Pikunda-Munda style (Fig. 1B; 3). The defining inventories are three pits excavated in 1987: pit B in trench PIK 87/1 at Pikunda (Seidensticker 2021, 288–300) and two ceramic depositions in pits from Munda labeled MUN 87/2-1-1 and MUN 87/2-1-3 (Seidensticker 2021, 321–335). The characteristic open-mouthed bowls with flared rimes, cylindrical or concave upper parts and rounded bases (Eggert 1993, 311-314) can be further divided into two sub-groups: one is characterized by a rounded transition from the wall to the base (Fig. 4.2–3), while the second group shows a distinct carination in the profile (Fig. 4.4–6,8). Bowls of the former type were exclusively found within the older infill of feature MUN 87/2-1-1 as well as the inventory from the neighboring pit MUN 87/2-1-3. Bowls with the characteristic carination were found in the upper infill of MUN 87/2-1-1 and in pit B of trench PIK 87/1 at Pikunda (Seidensticker 2021, 115–117). Lesser represented among the complete vessels, but present in equal numbers in the overall inventory, are slightly globular vessels with everted rims (Fig. 4.7,9–13). Decorations consist of linear elements produced utilizing incision or grooving and rocker-stamping with a comb (Seidensticker 2021, 362 App. 4.12). Nine conventional radiocarbon dates (Seidensticker 2021, 117 Fig. 48, 355–356 App. 2) and one newer AMS date (Seidensticker 2024, Tab. 2: RICH-30864) date the Pikunda-Munda style between the 2nd to 1st century BCE to 5th century CE.

This study focused on 39 vessel units of the Pikunda-Munda style (Tab. 1). Eight originate from the pit at Pikunda (B in PIK 87/1), while the inventories of the two pits at Munda are represented by 13 (MUN 87/2-1-1) and 17 (MUN 878/2-1-3) vessel units respectively. A single Pikunda-Munda sherd found in secondary depositon in the modern pit PIK 87/2 at Pikunda was also included. The main goal of the re-examination was to ameliorate a preliminary study concerning the *chaîne opératoire* of potters' communities, which only included six vessels of the Pikunda-Munda style (Seidensticker 2021, 45–73).

2.2 Pottery fabrics and thin-section petrography

Previous research established a reference system with nine primary macroscopic ceramic fabrics (Seidensticker 2021, 60–69). This system grouped sherds according to criteria observable without technical means other than a magnifier. Each major group was conceptualized as a putative 'recipe' prehistoric potters followed while sourcing and preparing used raw materials, most importantly clay and temper agents (Lange 2006, 49). The main characteristics to differentiate 'fabrics' (cf. Riemer 2011, 38–51) were the composition and texture of the clay matrix and non-plastic components as well as the firing color (Nordström 1972, 34). Differences within the nine main fabrics resulted in a general reference system of 27 macroscopic ceramic fabrics for the western and northern Congo Basin (Seidensticker 2021, 62–65 Tab. 11). Some main macroscopic fabrics correlate with stylistic groups (Seidensticker 2021, 69 Tab. 12). For example, all investigated sherds that are either part of the "West tradition" of the "Equator-Co-style tradition" of the Inner Congo basin (Wotzka 1995, 221–222 Fig. 4) or stylistically closely related to those are part of the same macroscopic fabric group, labeled 'fabric 1'. This fabric is characterized by whitish firing colors and almost no visible non-plastic particles. Pottery from sites along the Likwala-aux-Herbes and lower Sangha river are almost exclusively part of this fabric (Seidensticker 2021, 67 Fig. 21). Thus, in this region, potters followed the same 'recipe' for sourcing and preparing clay since the onset of pottery production in that region in the last centuries BCE. The available qualitative descriptions of the technological aspects of the pottery styles in the Inner Congo Basin by Wotzka (1995, 59–210) indicate that nearly all styles in the western parts of this region would be assigned to the same fabric group 1 as they display comparable characteristics. Only styles that date after the 15th century CE and are part of the Tshuapa, Maringa or northern style tradition in the eastern part of the Inner Congo Basin show higher

Site	Sample	Style	Sherd	M	X	P	Figures	Seidensticker 2021: plates
Munda	MUN 87/2-1-1-2:1	Pikunda-Munda	vessel	x				
Munda	MUN 87/2-1-1-2:2	Pikunda-Munda	vessel-part	x	x	x	5.D-F	91.2
Munda	MUN 87/2-1-1-2:3	Pikunda-Munda		x				
Munda	MUN 87/2-1-1-4:2	Pikunda-Munda	vessel	x	x	x	4.4	91.1
Munda	MUN 87/2-1-1-4:4-21	Pikunda-Munda	vessel	x	x			91.3
Munda	MUN 87/2-1-1-4:7	Pikunda-Munda	wall	x	x		7	91.4
Munda	MUN 87/2-1-1-4:11	Pikunda-Munda		x				
Munda	MUN 87/2-1-1-5:2	Pikunda-Munda	vessel	x	x		4.5; 8	91.5
Munda	MUN 87/2-1-1-5:5	Pikunda-Munda		x				
Munda	MUN 87/2-1-1-7:2	Pikunda-Munda	vessel	x				91.6
Munda	MUN 87/2-1-1-8:1	Pikunda-Munda	vessel	x	x		9	91.8
Munda	MUN 87/2-1-1-8:2	Pikunda-Munda	vessel	x	x		10	
Munda	MUN 87/2-1-1-8:3	Pikunda-Munda	vessel-part	x	x		4.3	91.7
Munda	MUN 87/2-1-3:3	Pikunda-Munda	vessel		x		4.1	92.5
Munda	MUN 87/2-1-3:7	Pikunda-Munda	vessel	x	x			93.1
Munda	MUN 87/2-1-3:8	Pikunda-Munda	vessel	x	x		4.11	92.8
Munda	MUN 87/2-1-3:9	Pikunda-Munda	vessel	x	x			93.4
Munda	MUN 87/2-1-3:10	Pikunda-Munda	vessel	x	x		4.7	93.3
Munda	MUN 87/2-1-3:13a	Pikunda-Munda	vessel	x	x			93.5
Munda	MUN 87/2-1-3-1:1a	Pikunda-Munda	vessel-part	x				92.3
Munda	MUN 87/2-1-3-1:1b	Pikunda-Munda	vessel	x	x			92.1
Munda	MUN 87/2-1-3-1:2	Pikunda-Munda	vessel	x	x			92.2
Munda	MUN 87/2-1-3-4:4	Pikunda-Munda	vessel		x			92.4
Munda	MUN 87/2-1-3-4:11	Pikunda-Munda	vessel-part		x			93.7
Munda	MUN 87/2-1-3-5:5	Pikunda-Munda	vessel		x			92.6
Munda	MUN 87/2-1-3-5:12	Pikunda-Munda	vessel	x	x			93.2
Munda	MUN 87/2-1-3-5:18	Pikunda-Munda			x			92.9
Munda	MUN 87/2-1-3-6:1-2	Pikunda-Munda	vessel-part		x			
Munda	MUN 87/2-1-3-6:6	Pikunda-Munda	vessel	x	x		4.2	92.7
Munda	MUN 87/2-1-3-6:15	Pikunda-Munda	vessel	x	x			93.6
Pikunda	PIK 87/1:1	Pikunda-Munda	wall	x				
Pikunda	PIK 87/1:11-12	Pikunda-Munda	wall	x				
Pikunda	PIK 87/1/I-8:1 /I-9:1	Pikunda-Munda	vessel	x	x		4.8; 6	44.3
Pikunda	PIK 87/1-4:20	Pikunda-Munda	wall	x				46.20
Pikunda	PIK 87/1-5:1 -6:10 -7:12 - 9:6	Pikunda-Munda	wall			x		46.21
Pikunda	PIK 87/1-7:1 -8:4	Pikunda-Munda	vessel-part	x	x			45.2
Pikunda	PIK 87/1-9:5	Pikunda-Munda	wall			x		47.6
Pikunda	PIK 87/1-10:7 -11:1 /I-11:4 /I-12:2	Pikunda-Munda	vessel-part	x				45.1
Pikunda	PIK 87/2-4:73	Pikunda-Munda	wall	x				48.25
Pikunda	PIK 87/1-12:1	Lusako	rim			x		45.16
Pikunda	PIK 87/1-8:1	cf. Ngbanja	wall			x		47.20
Pikunda	PIK 87/1-8:2	cf. Ngbanja	wall			x		47.21
Pikunda	PIK 87/1-9:7	cf. Ngbanja	wall			x		47.19
Pikunda	PIK 87/2-6:77	Mandombe	wall			x		
Pikunda	PIK 87/1-1:35	Mandombe	wall			x	5.J-K	
Pikunda	PIK 87/1-2:3	Mandombe	vessel-part	x	x		13	47.24
Pikunda	PIK 87/1-2:123	Mandombe	rim			x		
Pikunda	PIK 87/1-3:?	Mandombe	wall	x			14	
Pikunda	PIK 87/1-2:70	Ebambe	wall			x	5.A-C	
Ngombe	NGO 87/102:27	Ngombe	vessel	x			11	42.16
Ngombe	NGO 87/102:28-29	Ngombe	vessel	x		x	12	43.1
Munda	MUN 87/1-0-2-6:1	Ebambe	vessel			x	5.G-H	90.2
Itanga	ITN 87/103:11	Epena	vessel			x	5.I	96.3
Pikunda	PIK 87/501:2	modern	vessel	x	x		15	
Pikunda	PIK 87/501:4	modern	vessel	x	x	x	5.L	

Table 1: List of samples included in this study and applied methods. Type of sherds are seperated for complete or nearly complete vessels, vessel parts of which considerable parts are missing but the entire profile from the rim to the base can be reconstructed and wall fragments with either the rim or base missing. The samples were subjected to macro-analysis of surface traces (M), X-raying (X), and petrographic analysis (P).

concentrations of quartz inclusions and would thus be grouped in macroscopic fabric 4 (Seidensticker 2021, 62–65 Tab. 11).

To further elaborate on this preliminary and superficial analysis, a comprehensive study of the mineralogical compositions of pottery sherds from the Congo Basin was started. For this paper, four thin-sections from ceramics of the Pikunda-Munda style (Fig. 5A–F) as well as nine thin-sections from younger pottery from the two main sites Pikunda and Munda (Fig.5G–L) were studied (Tab. 1). The petrographic analysis was conducted using an Olympus BX41 microscope, and the description and interpretation of observations were based on established reference works regarding ceramic petrography (MacKenzie et al. 2017; Quinn 2022).

2.3 Macro-traces and x-radiographs

The shaping technique is the second aspect of the *chaîne opératoire* of Pikunda-Munda potters under investigation in this paper. The shaping process can be sub-divided into two phases: the forming or roughing-out phase, henceforth referred to as the 'primary shaping technique', and the subsequent 'secondary' shaping technique (Shepard 1956 (reprint 1985; Rye 1981; Livingstone Smith 2007a; Livingstone Smith and Viseyrias 2010). Distinct actions of the potter during the shaping process can be deduced through surface features such as fissures, cracks, or breaks and their pattern, defective joints, as well as variations in the texture of the surfaces. Systematically spatially co-occurring features, systematized as configurations following Livingstone Smith (2007a); Livingstone Smith and Viseyrias (2010), are physical remnants of technical behaviors. These are compared and interpreted in reference to available ethnographic descriptions of the potting practices in the immediate study area (Eggert and Kanimba-Misago 1980; Eggert in prep.), as well as from the wider region (Gosselain 1992, 2002; Gosselain and Livingstone Smith 1997; Livingstone Smith 2007b, 2010, 2016; Livingstone Smith and van der Veken 2009; Livingstone Smith and Viseyrias 2010) and other parts of Africa (Gallay et al. 1998; Gaspar Da Silva et al. 2005; Gosselain and Livingstone Smith 2005; Gosselain 2006; Livingstone Smith 2007a; Mayor 2011; Gosselain 2014).

A preliminary study on 28 vessels from the western and northern Congo Basin, including six vessels of the Pikunda-Munda style, could identify three main groups of vessels sharing observed macro-traces and surface features (Seidensticker 2021, 45–60,69–73). The present study included 39 vessel units of the Pikunda-Munda style alone (Tab. 1).

The study of macro-traces was supplemented through x-radiographs that offered insight into the internal micro-structure of the vessels (Stevenson 1953; Rye 1977; Vandiver 1987). Radiographs of 26 vessels pertaining to the Pikunda-Munda group were produced at the Royal Museum for Central Africa (RMCA). The bulk of these vessels originated from the two neighboring pit features MUN 87/2-1-1 (n=8) and MUN 87/2-1-3 (n=16) at Munda on the Likwala-aux-Herbes river. Only two vessel units from the pit PIK 87/1 were sufficiently big enough to the radiographed.

3 Results

3.1 Macroscopic and Petrographic Fabrics

Previous studies Seidensticker (2021, 60–69) established that Pikunda-Munda ceramics unanimously show the same macroscopic fabric: a fine clay paste usually dark or whitish in colour with no or very few macroscopic inclusions. The petrographic analysis corroborated this. Four sherds of vessels of the Pikunda-Munda style group showed strong similarities (Fig. 5A–F). The petro-fabric is based on fine clays showing no or very little birefringence (Fig. 5C,5F). Its main feature is large quantities of sponge spicules. These appear as elongated isotropic rods in plane-polarized light (PPL; Fig. 5A,E,H) and are the remains of the micro-sized, siliceous skeletons of freshwater sponges. Sponges, known as Cauixi in Amazonia, are known to have been added as temper agents to pre-Columbian pottery in the Amazon Basin (Linné 1932, 1957; da Costa et al. 2004; Rodrigues et al. 2017; Villagran et al. 2022), as well as the Orinoco river valley (Lozada Mendieta 2019) and in the Paraná river valley (Ottalagano 2016). They are known to improve the mechanical properties of the vessels after firing by increasing mechanical rigidity (Natalio et al. 2015). In Africa, as in other parts of the world (Cordell 1993; Bloch et al. 2019), they indicate the use of lacustrine or fluvial clay sources. Sponge spicules rich pottery is rarely documented in pottery from sub-Saharan Africa though. Some examples are known from Mali (Brissaud and Houdayer 1986; Mcintosh and MacDonald 1989; Nixon and MacDonald 2017), Sudan (Adamson et al. 1987) and the great lakes region of East Africa (Ashley 2005, 185). Contrasting these few empirical evidence against the wide usage of fluvial clay's among modern potters communities in Africa (Drost 1967, 19 Map 1) exemplifies the novelty of the observation of their wide presence in the Congo Basin. A lack of observed gemmules in the thin sections hampers species identification. A synthesis of spongillofauna in Africa by Manconi and Pronzato (2009) offers some potential candidates: *Metania pottsi* is widely distributed in the region, but spicules often show conules on the surface, and the species is best identified based on their gemmuloscleres (Manconi and Pronzato 2009, 38–47); which are lacking in the archaeological samples. Other species with matching features are either not documented in the western Congo Basin, such as *Eunapius nitens* (Manconi and Pronzato 2009, 149–151), which shows very similar spicules, or are poorly documented, such as *Trochospongilla philottiana* (Manconi and Pronzato 2009, 198–199).

The quartz fraction observed within this fabric consists of sub-angular mono-crystalline grains that are interpreted as natural components of the source clays (Fig. 5C,F). Occasionally clay pellets (Fig. 5C) and evidence for clay mixing (Fig. 5A,I) were observed. Clay mixing results in varying 'opti-

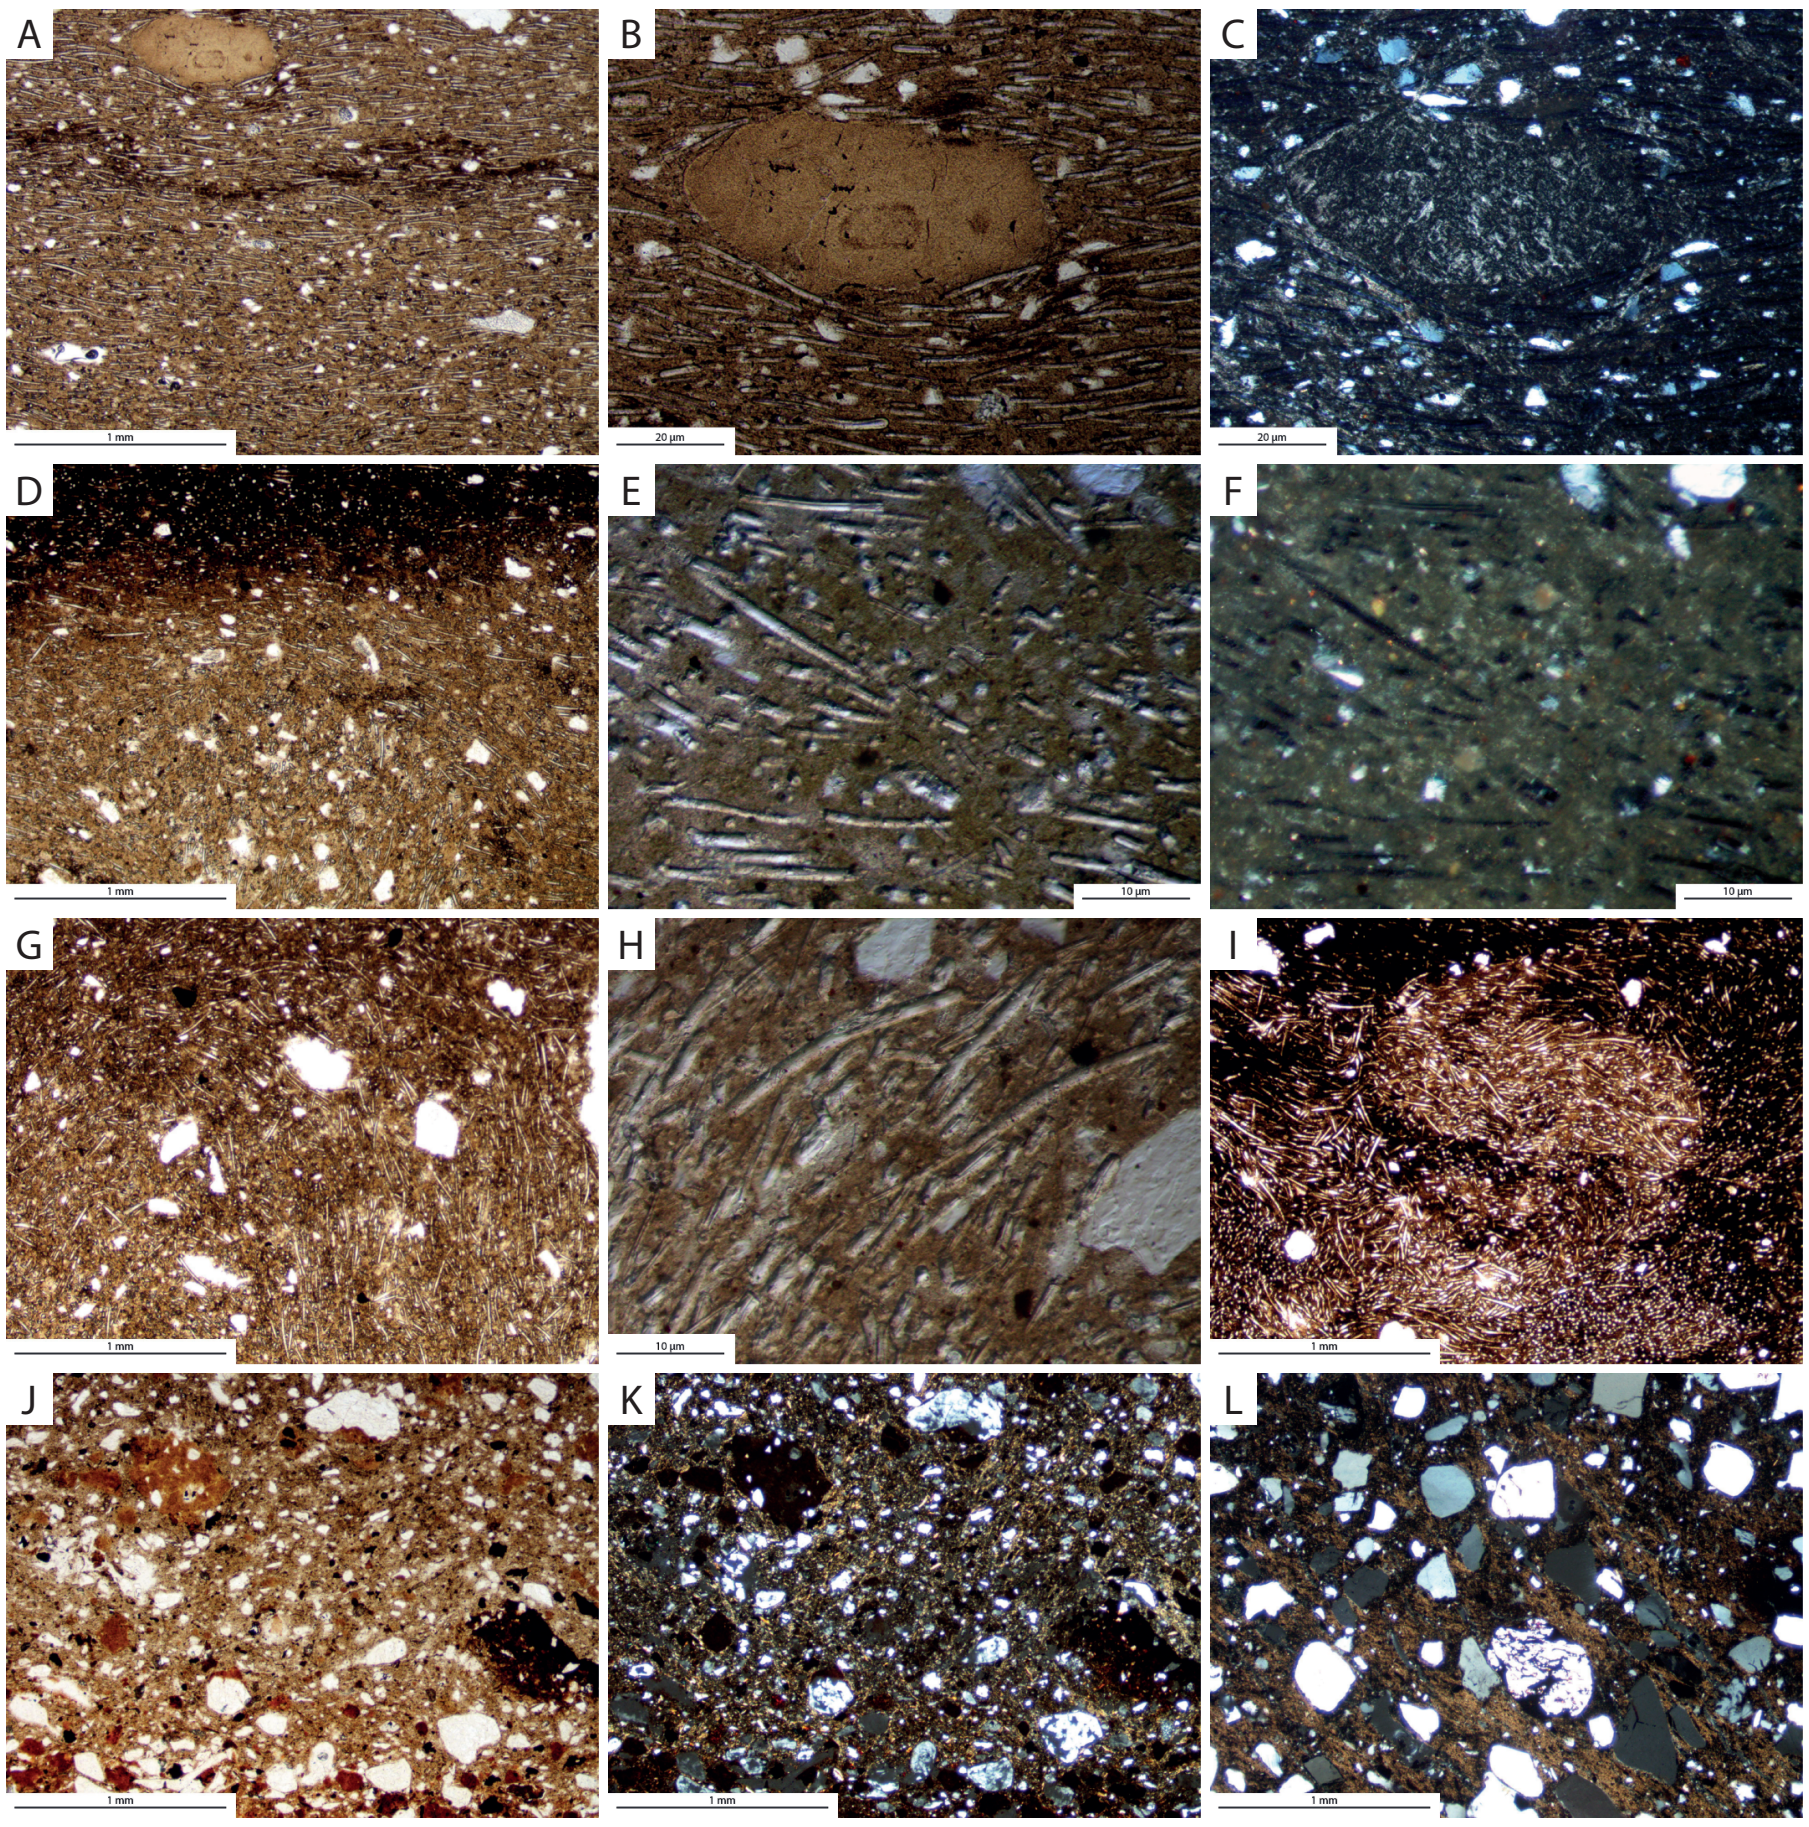

Fig. 5: Photomicrographs of ceramics from Pikunda (A–C, J–L), Munda (D–H) and Itanga (I) (*cf.* Fig. 1B) dating into the Early (A–F) and Late Iron Age (G–L) illustrating the main petro-fabrics encountered (A–B,D–E,G–J in plain-polarized light [PPL]; C,F,K–L in cross-polarized light [XPL]). Pikunda-Munda pottery (A–F) is unanimously produced using fluvial clays rich in sponge spicules (A–H). Samples from Pikunda dating into the Late Iron Age were systemically produced using terrestrial clays void of sponge spicules (J–L). Additional features include clay pellets (B–C) and clay mixing (I).

cal activity' under cross-polarized light (XPL) (Whitbread 1986). In general, only very limited or no birefringence was observed. One sherd from Munda on the upper Likwala-aux-Herbes river (Fig. 5D) showed a zonation separating a clay matrix without birefringence from one with reddish interference colours and slight birefringence. The petro-fabric corresponds to the described fine macroscopic fabric 1 (Seidensticker 2021, 60–69).

While the selection of fluvial clays, rich in sponge spicules and an absence of any additional tempering, can be considered a distinct characteristic among Pikunda-Munda potters, substantial changes can be observed in later times among potters' communities along the middle to upper Sangha river versus those on the lower reaches of the Sangha and along the Likwala-aux-Herbes river. At Pikunda on the Sangha river, potters' approached distinctly different clay sources and tempered their clays (Seidensticker 2016, 2020). There are no indications that fluvial clays rich in sponge spicules were used further. The late Iron Age sherds from Pikunda show distinct birefringence (b-fabric; Fig. 5K–L; Stoops 2021, 131–141). The mineral component is considerably different from that seen in the thin-section of of the Pikunda-Munda sherds: quartz grains are bigger, more angular and occasionally, multi-crystalline rock fragments can be observed (Fig. 5K). Runiquartz (Marcelino et al. 2018, 673 Fig. 6) are regularly present as well (Fig. 5L). They indicate weathering of the quartz and, thus, a highly altered environment. The sherds also contain opaque components (Fig. 5J–K), reminiscent of iron-rich minerals potentially related to lateritic soil formation processes (Scheffer and Schachtschabel 2010, 351–352). Occasionally, organic inclusions are visible. These observations indicate that potters of the late Iron Age preferred terrestrial clay sources that show some relation to soil formation processes and tempered those clays with mineral components and organics.

On the lower Sangha and the Likwala-aux-Herbes river, on the other hand, Late Iron Age potters still use similar or the same fluvial clay sources prevalent in the Early Iron Age pottery. The pottery of the younger styles Ngombe, Ebambe, Epena and Mobaka (Fig. 3) all show the same macroscopic fabric 1 (Seidensticker 2021, 69 Tab. 12), which corresponds with the petro-fabric rich in sponge spicules, indicating the use of fluvial clays. The concentric orientation of sponge spicules in a sherd from Munda (Fig. 5G) indicates either clay mixing or shaping by coiling.

3.2 Shaping techniques

The primary shaping technique of Pikunda-Munda potters has been identified based on macro-traces and radiograph features. Common among Pikunda-Munda vessels, often wide-mouthed bowls with parallel or concave sides, flared rims and round bases, are helical fissures, cracks or breaks (Fig. 7–8, 10, 6). This feature, usually occurring during the drying stage, indicates an upward, rotating movement the potter applies during the primary shaping stage. A similar technique was documented at the potters' village of Ikenge on the Ruki river (Fig. 1; Eggert and Kanimba-Misago 1980). Another common feature is wall-parallel 'lamination', usually visible on the breaks (Fig. 8) or as flaking of the surface. These two features indicate a drawing technique to be applied by Pikunda-Munda potters to shape the upper parts of the vessels.

Nearly all vessels studied showed some signs that their upper parts and bases were pre-shaped separately. While all features of the upper parts of the

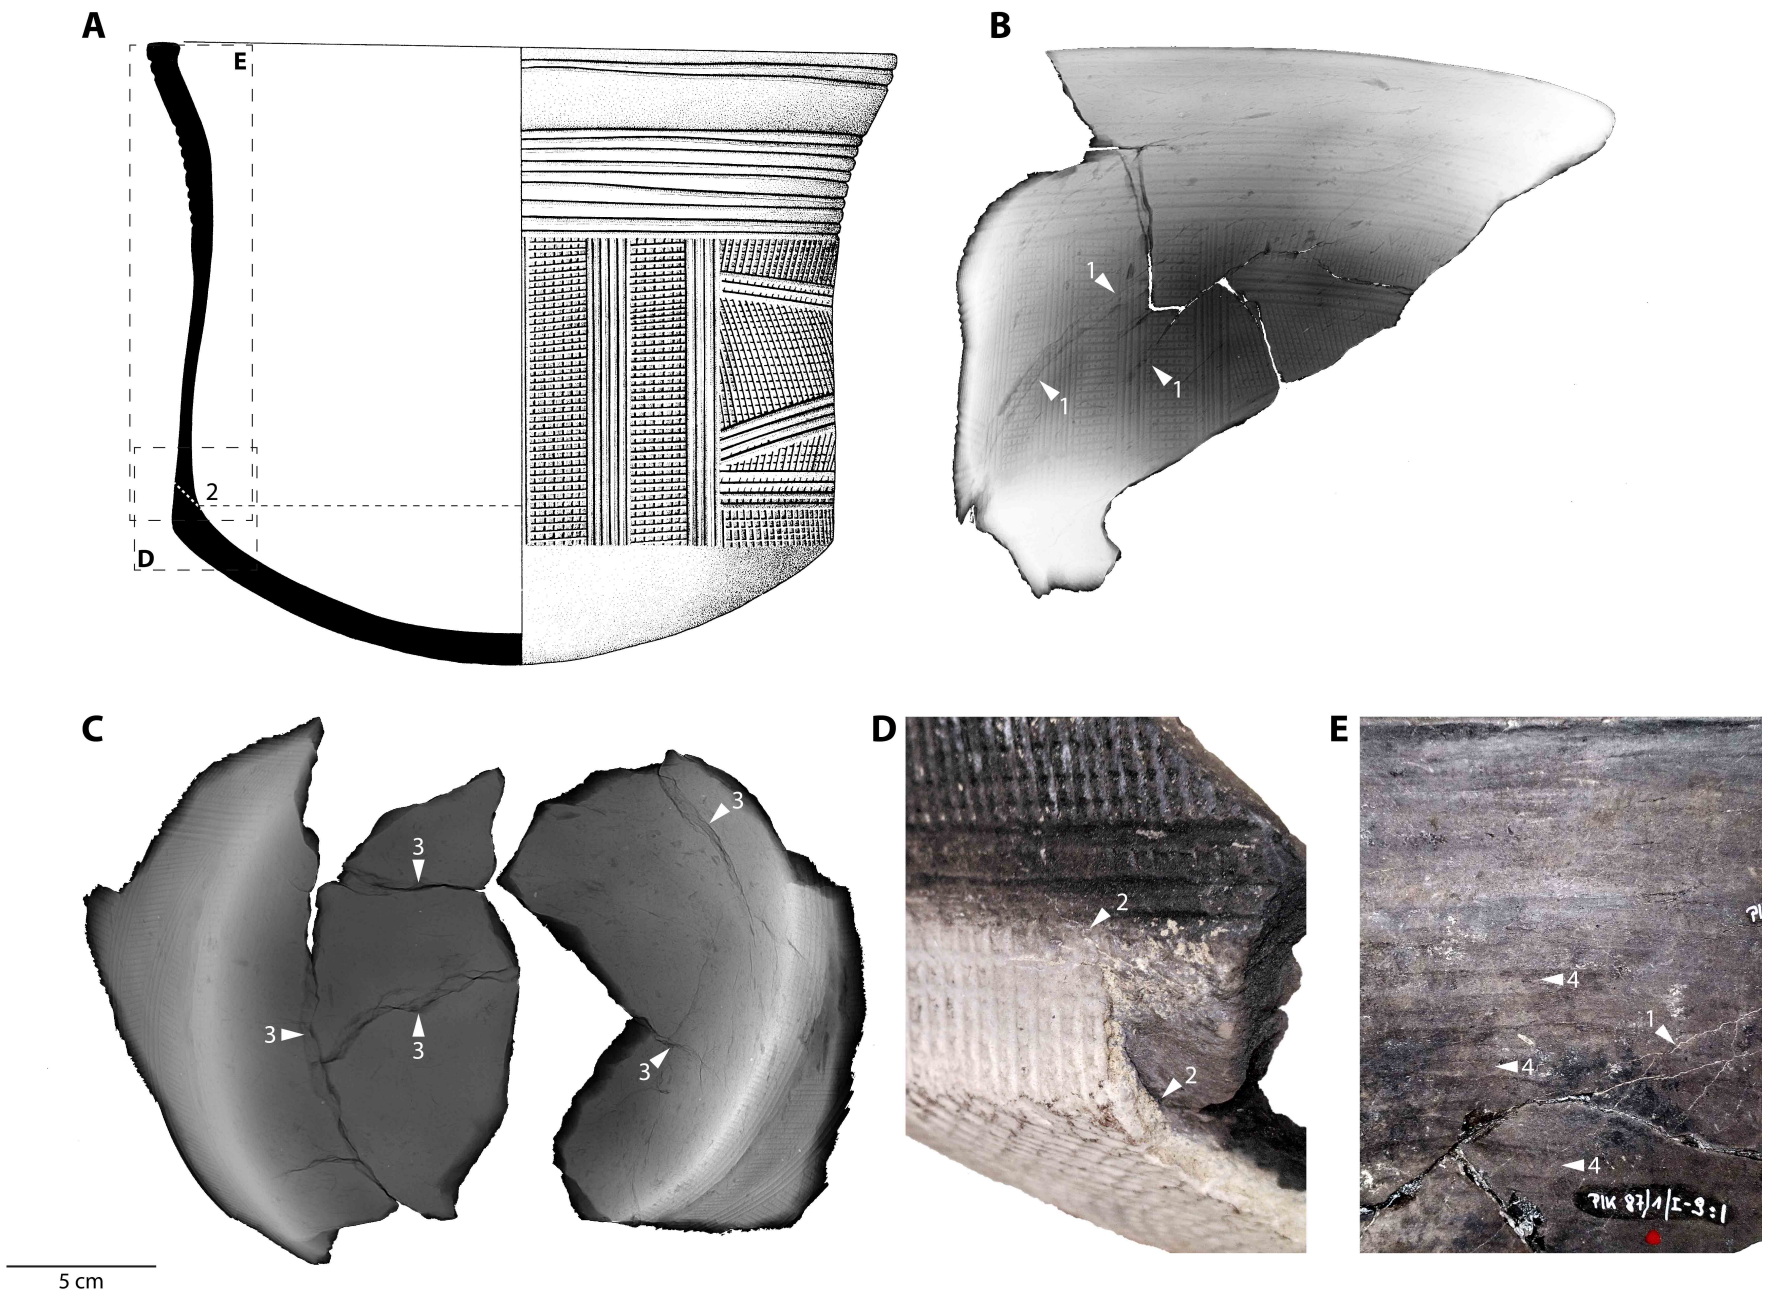

Fig. 6: Technical observations on PIK 87/1-8:1: (1) helical fissures and breaks; (2) joint between the wall and base; (3) radial and concentric fissures and breaks in the base; (4) horizontal polishing facets on the inside; no illustrations availanble: wall-parallel lamination in the breaks and paddle marks on the exterior of the base. (B: X-ray from lateral; C: X-Ray from inferior; D: Detail of carination; E: View of interior surface)

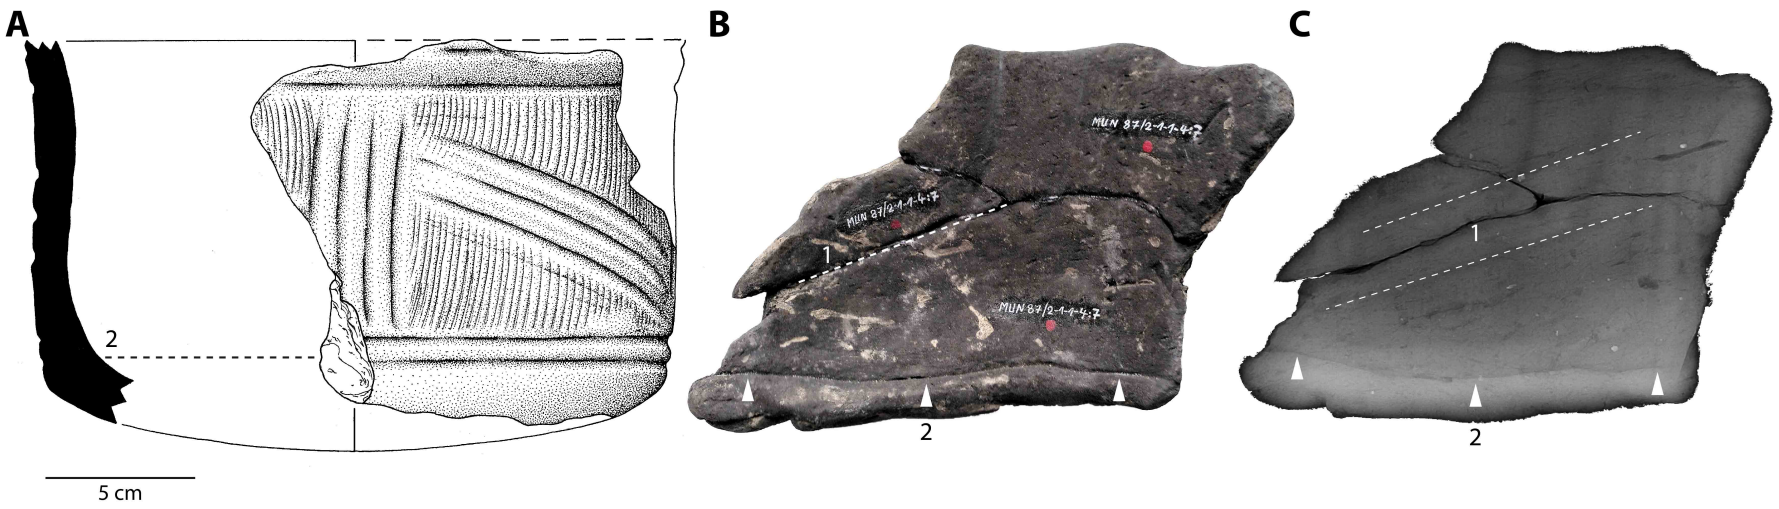

Fig. 7: Technical observations on MUN 87/2-1-1-4:7: (1) helical fissures and breaks; (2) horizontal joint connecting the wall and the base (B: View from posterior; C: X-ray from posterior).

vessels are strikingly similar, indicating that the potters performed similar actions and motions to shape these parts, two modes of constructing the bases were observed. The most widespread configuration of features is radial as well as concentric fissures, cracks or breaks in the base (Fig. 8–10). These are regularly coupled with patchy differences in the densities of the base, as observed in

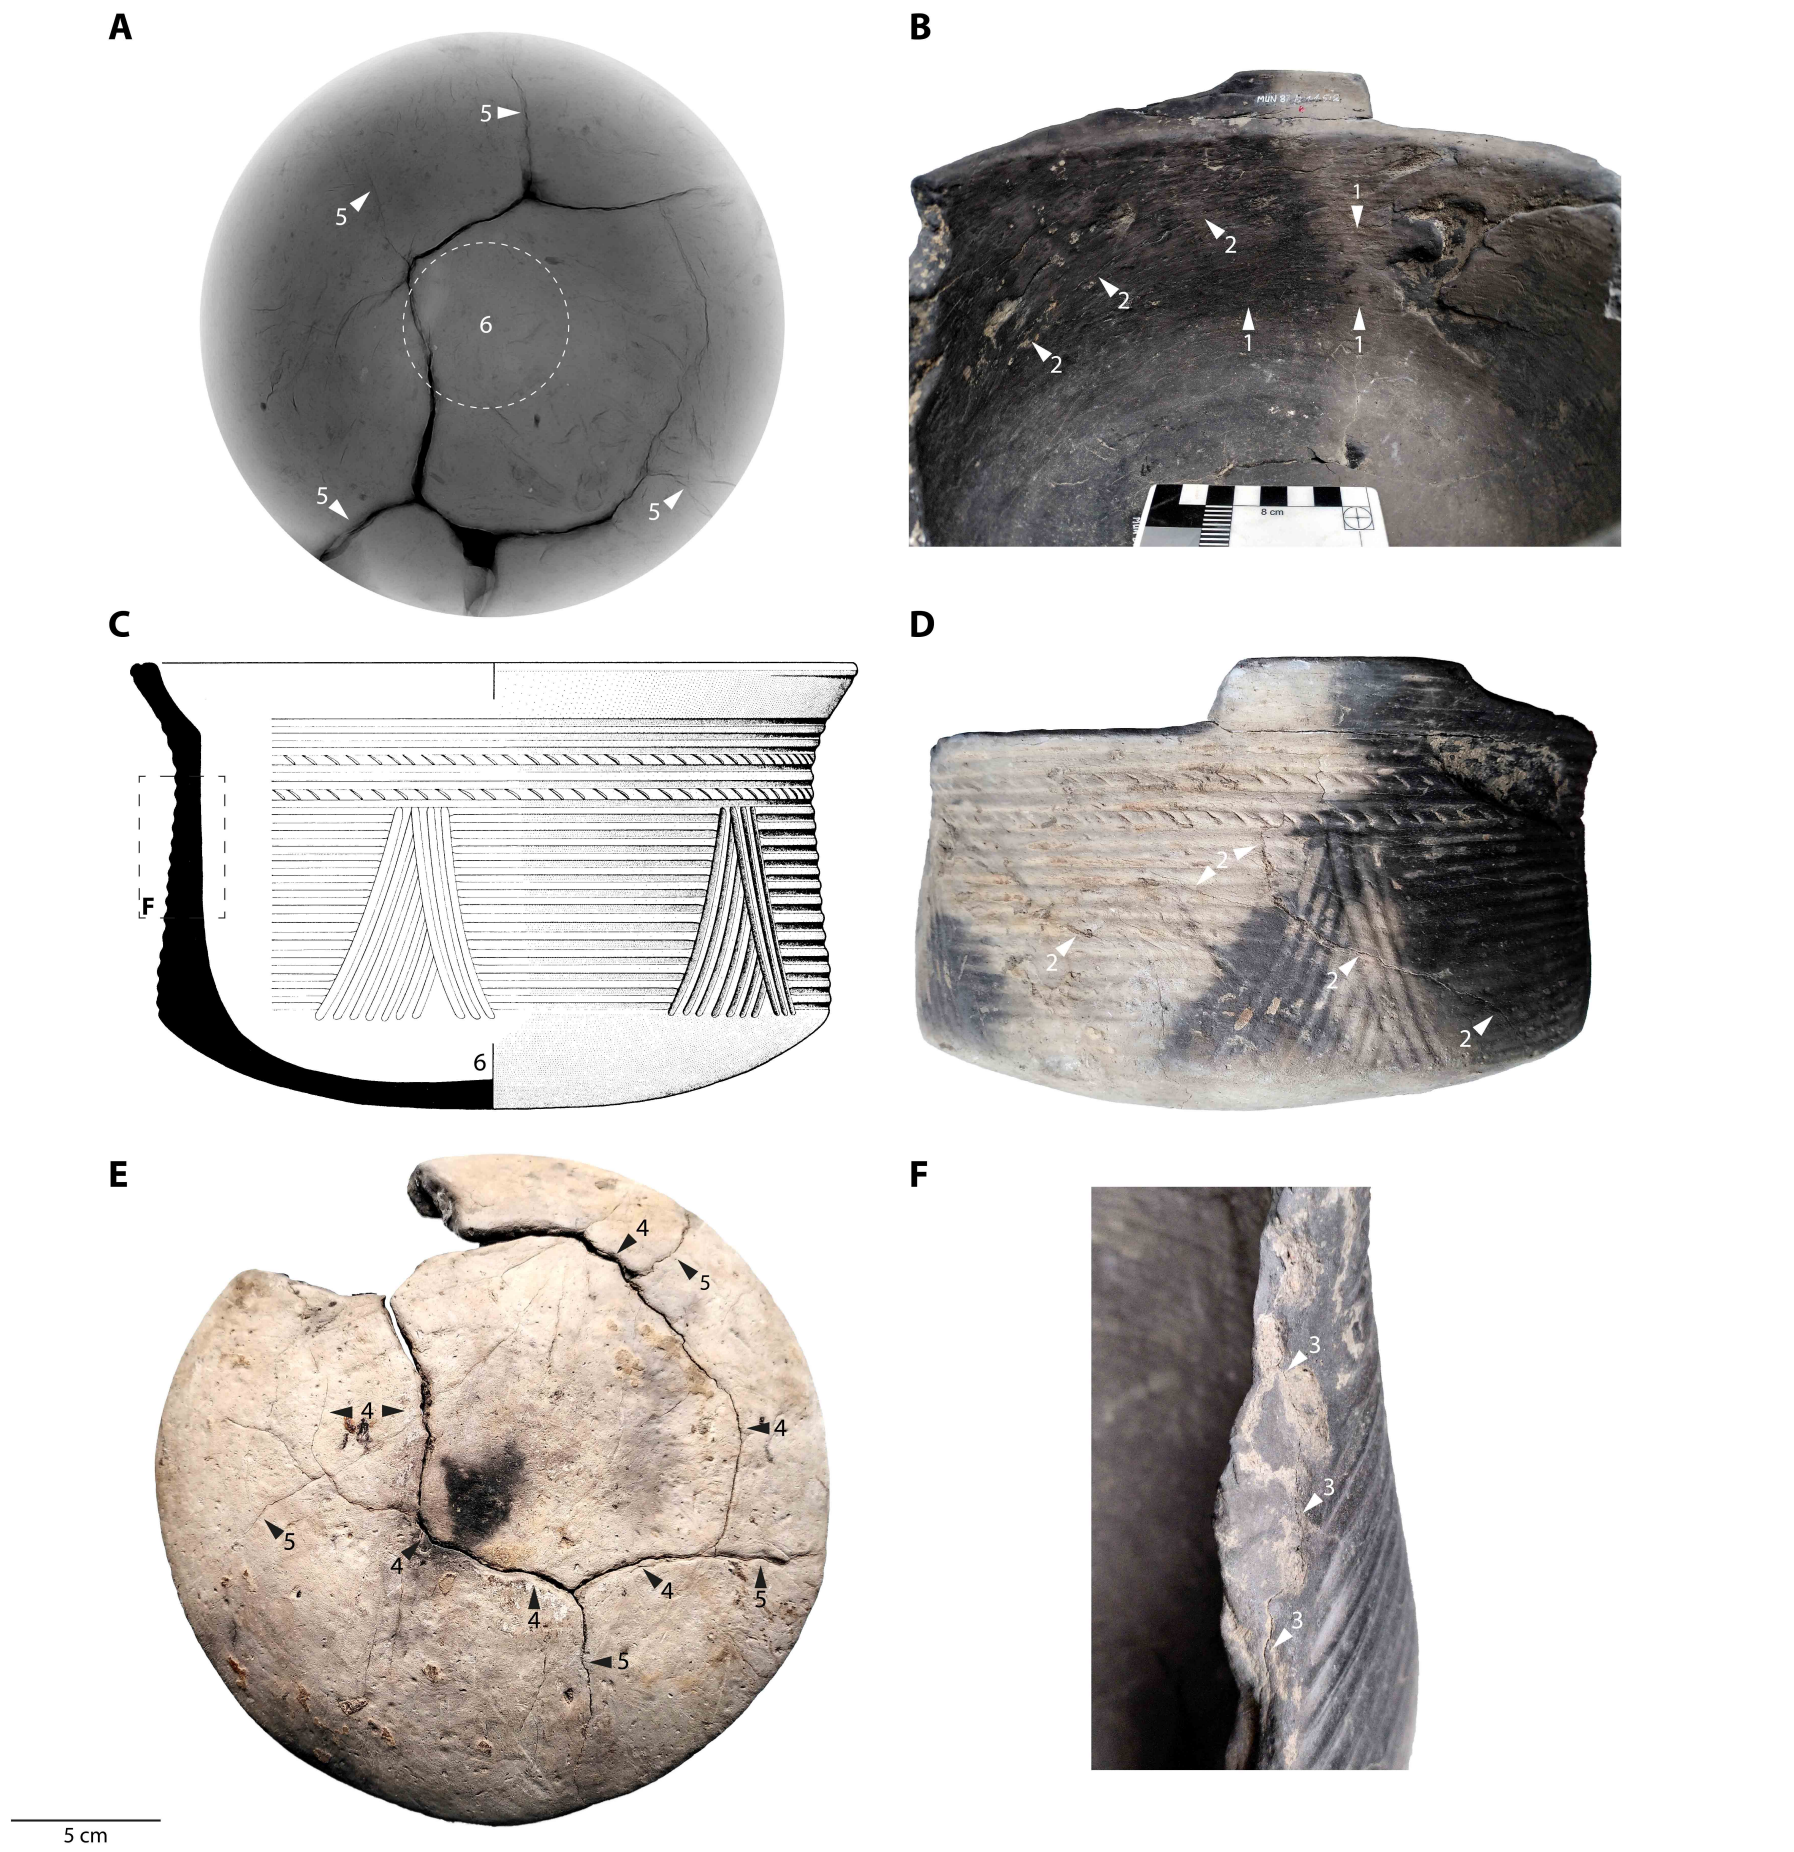

Fig. 8: Technical observations on MUN 87/2-1-1-5:2: (1) horizontal polishing facets; (2) helical fissures and breaks; (3) vertical lamination of the wall; (4) concentric break; (5) radial fissures and cracks; (6) thickening of the base. (A: X-ray from superior; B: View from posterior; D: View from lateral; E: View from inferior; F: Detail of breakage)

the radiographs. This set of co-occurring features is distinct from the features observed at the upper parts. The current working hypothesis is that these features are the remains of additional clay used to 'close' the rough-out. After adding clay, the base was then shaped using pounding and paddling, similar to what Eggert and Kanimba-Misago (1980) documented at Ikenge.

A second, slightly different mode is attested for in two vessels (Fig. 6–7) and characterized by a visible joint between the wall and the base, right at the carination. In one particular case (Fig. 6) the base overlaps the wall, with a small part of the decoration of the upper parts even being covered. This

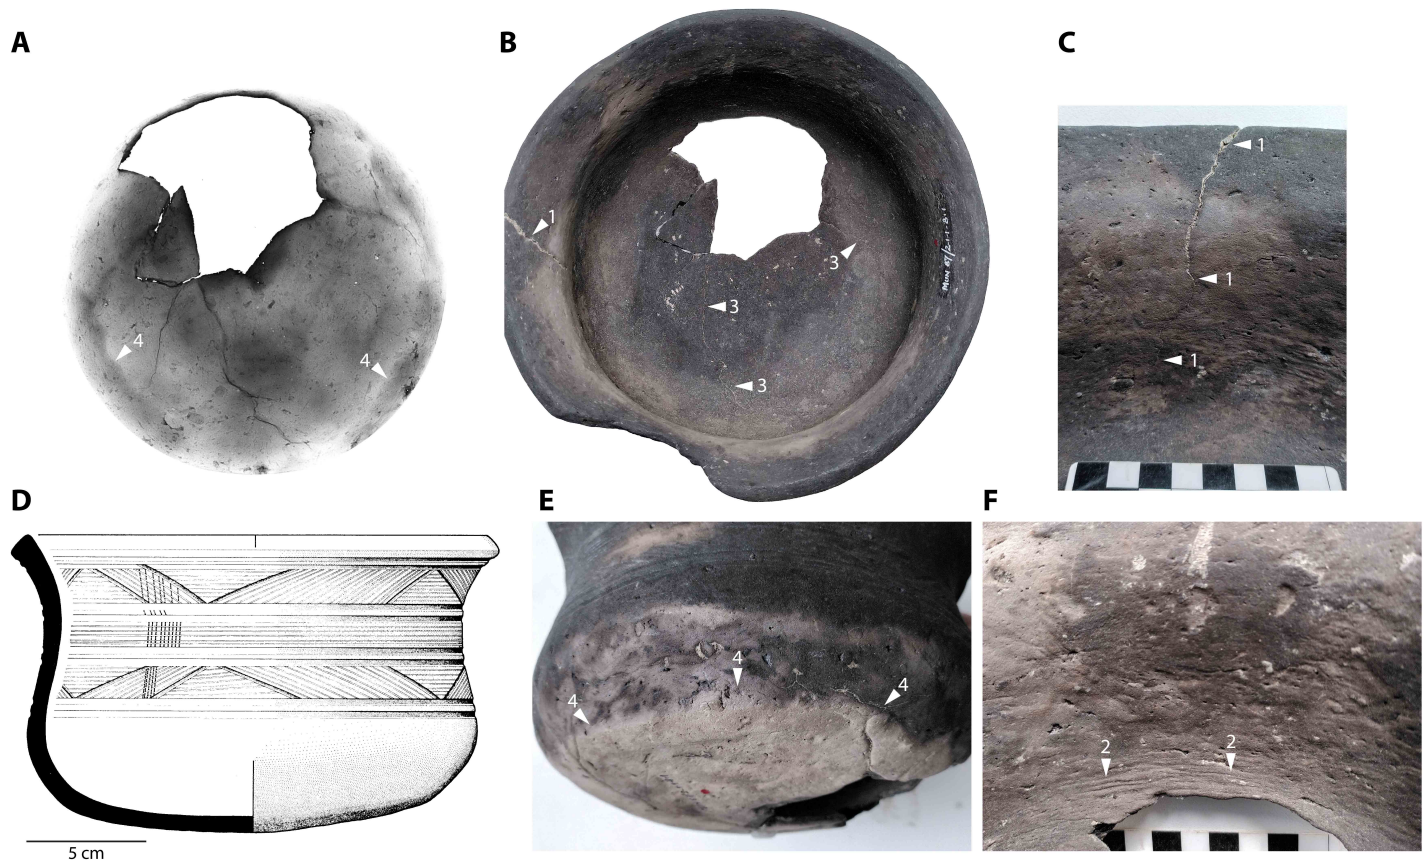

Fig. 9: Technical observations on MUN 87/2-1-1-8:1: (1) single vertical fissure and crack in the wall; (2) horizontal compression folds near the base; (3) radial fissures in the base; (4) thickening on the outside at the base. (A: X-ray from superior; B: View from superior; D: Detail of interior surface; E: Detail of transition of wall to base; F: Detail of interior surface at transition of wall to base)

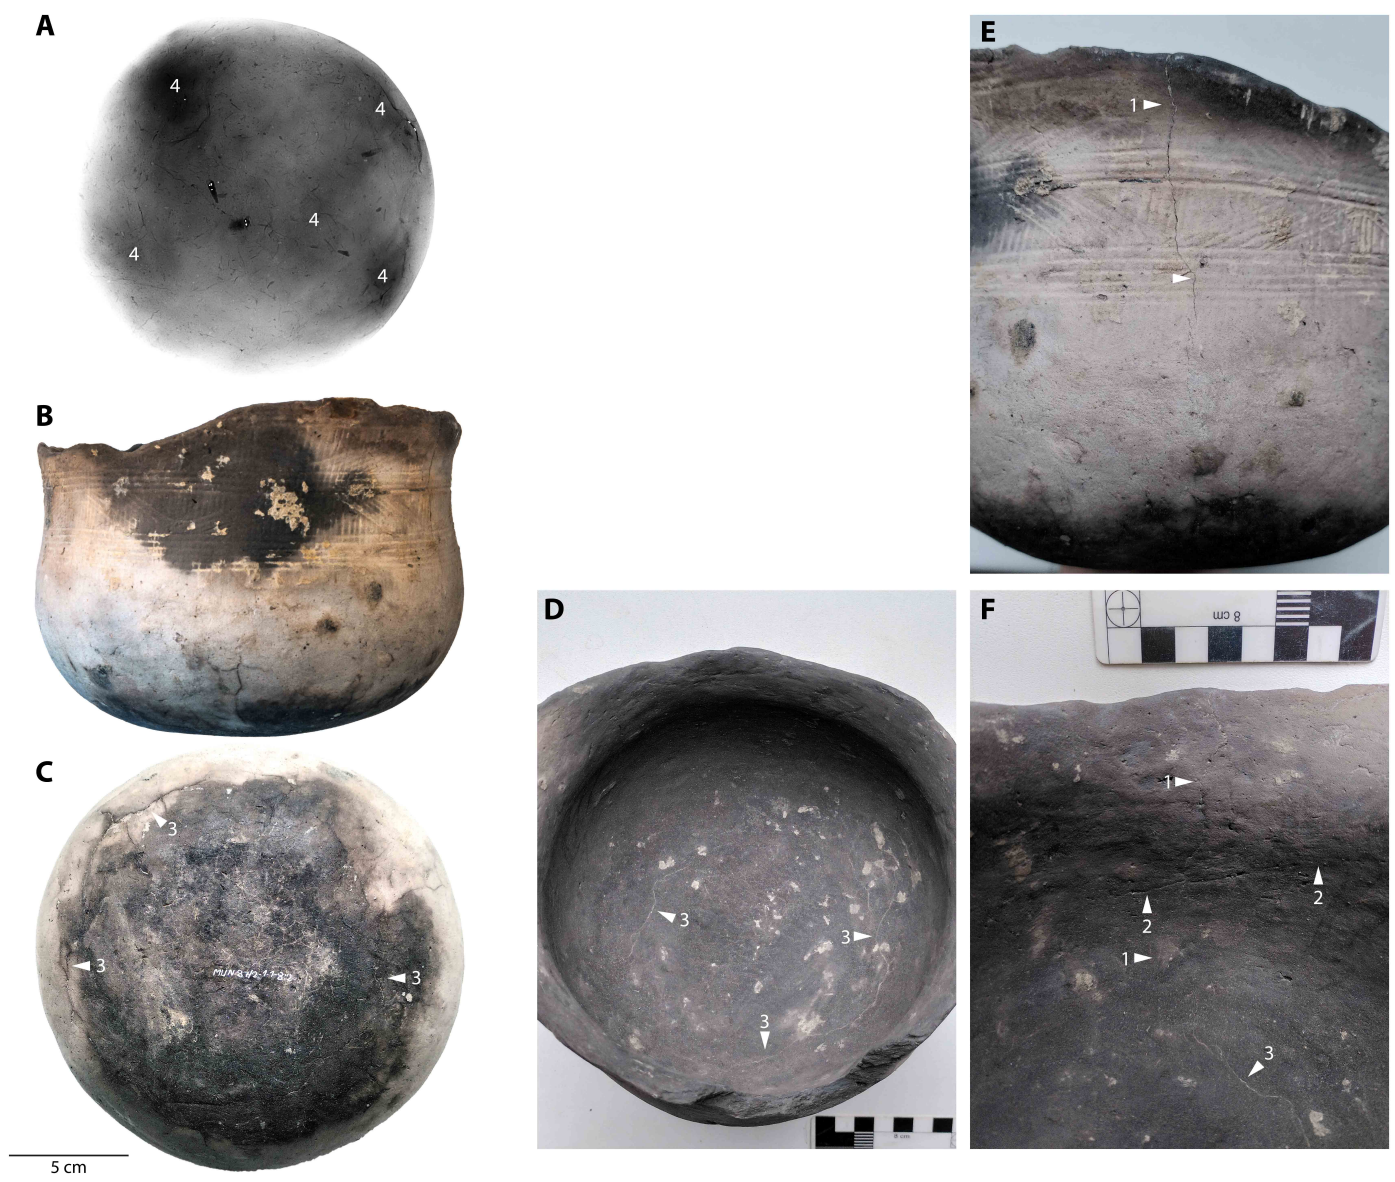

Fig. 10: Technical observations on MUN 87/2-1-1-8:2: (1) single vertical fissure and crack in the wall; (2) helical fissures; (3) concentric fissures; (4) thinning of the base and paddle marks. (A: X-ray from superior; B: View from lateral; C: View from inferior; D: View from superior; E: Detail from lateral; F: Detail of the interior surface)

indicates that the upper part must have been roughed-out, shaped and already decorated before the base, presumably pre-shaped separately, was attached. Thus, this second mode combines the drawing of a ring technique with a slab bottom.

That the initial rough-out was shaped by drawing of a ring (cf. Livingstone Smith 2010), which is a different technique from the pierced lumps observed at Ikenge (Eggert and Kanimba-Misago 1980), can be deduced from singular vertical fissures and cracks in some vessels (Fig. 9–10). This feature is interpreted as a remnant of the construction of the initial ring.

The configuration of features constituting core stages of the *chaîne opératoire* of Pikunda-Munda potters consists of helical fissures, cracks of breaks in the upper part, lamination visible in the breaks and either the addition of clay to close the base, involving usage of pestles and paddles, or slab bottoms.

4 Discussion

A robust theoretical pillar to understanding material objects, on an individual and collective level, is the choices made during their production. The production process is best divided up into phases consisting of sequences of distinct actions and organized sets of operations to retrace the transformative trajectories that progressively alter the state of all used material resources; in the case of pottery, the raw clay and any additional temper materials (Gosselain 2018, 3–4). The integration of all those actions can be summed up using the concept of *chaîne opératoire*, which has already been the predominant analytical approach to behavioral analyses in lithic technology since the 1980s (Tixier et al. 1980; Tixier 1984; Pelegrin et al. 1988). *Chaîne opératoire* approaches enable systematic and structured comparisons between sequences of actions on an intra- and inter-community level, in Africa (Gosselain 1992; Gallay et al. 1998; Gosselain 2002; Livingstone Smith 2007a; Mayor 2011; M'Mbogori 2015; Delvoye et al. 2016; Delvoye 2022) and elsewhere (see for example Manem 2008; Ard 2014; Gomart 2014; Gaffney 2020; Heitz 2023).

Often variations in pottery technology, especially clay procurement and preparation strategies, have been interpreted rather as a result of forced adaptations to constraints imposed by the available raw materials (Braun 1983; Tite 1999; Rice 2015) than a result of the socio-historical heritage of distinct potters' communities (McIntosh 1995; Gosselain 2010; Roux 2017; Gosselain 2018; Roux 2019). Pioneering studies on the socio-cultural nature and putative history of potters' behavior focused on ethno-archaeological observations (Lechtman 1977). With potting practices being learned behaviors, whose knowledge base is transferred within tight-knit social networks, mostly through kinship, the work of individual potters is interrelated through collective knowledge, tools, and materials, all together defining "communities of practice" (Wenger 1998; Lave 1991; Lave and Wenger 1991; Roddick and Stahl 2016). Within such communities, knowledge is transmitted by a lived experience of participation within a social network, and actions are guided by dispositions and

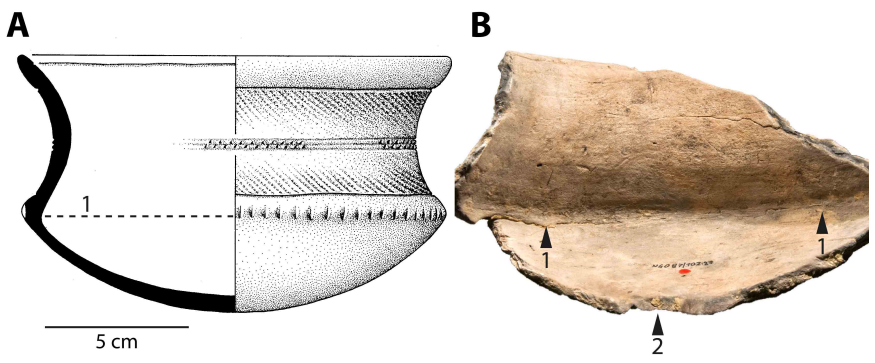

Fig. 11: Technical observations on NGO 87/102:27: (1) horizontal fissures and cracks indicating joining of two parts; (2) concentric break of the base. (B: View of the interior surface)

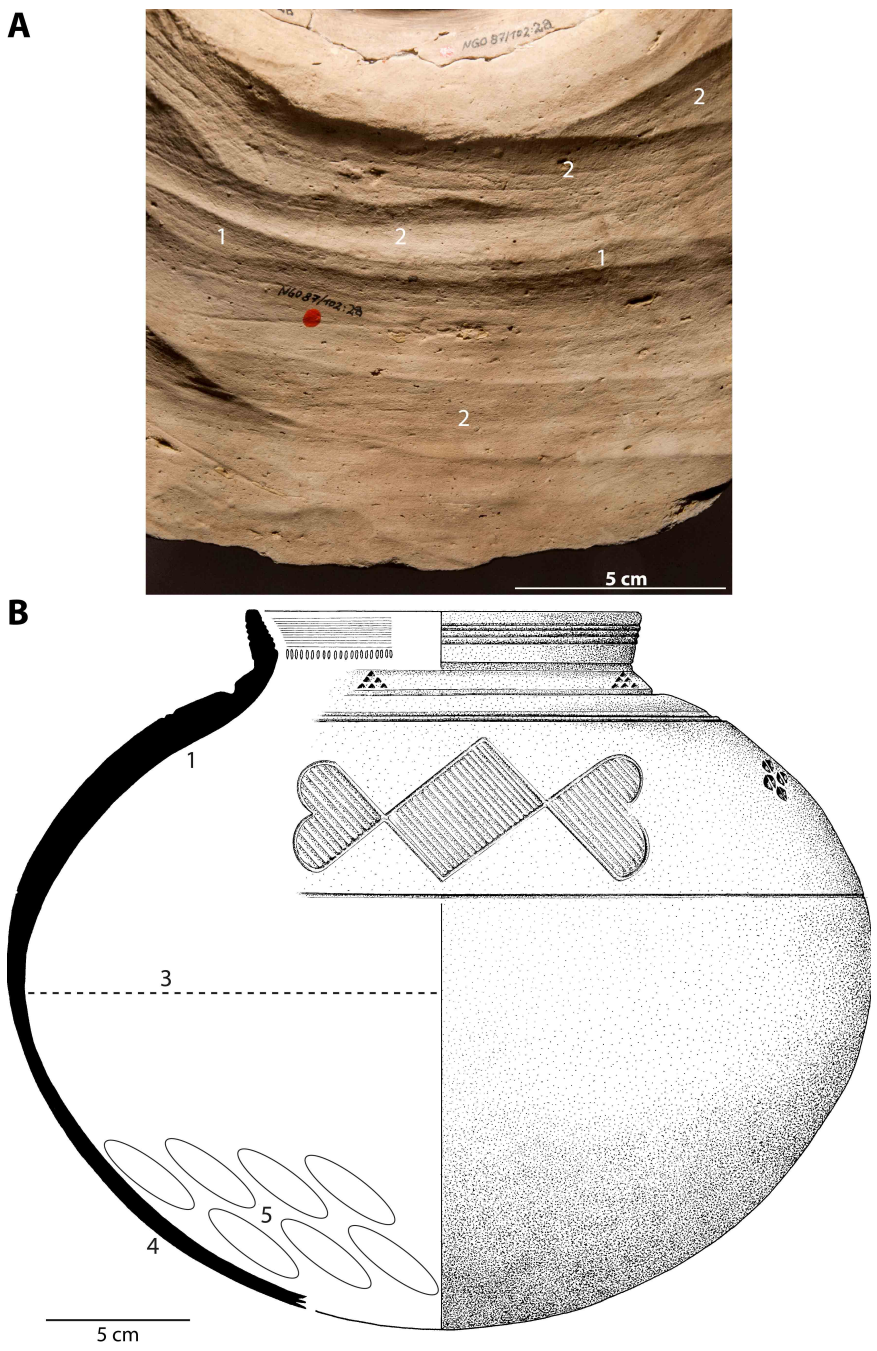

Fig. 12: Technical observations on NGO 87/102:28–29: (1) thickening of the wall; (2) horizontal scraping; (3) horizontal break, indicating joining of two pieces; (4) thinning of th wall; (5) pounding marks and thinning of the wall. (A: Detail of the interior surface at the upper part)

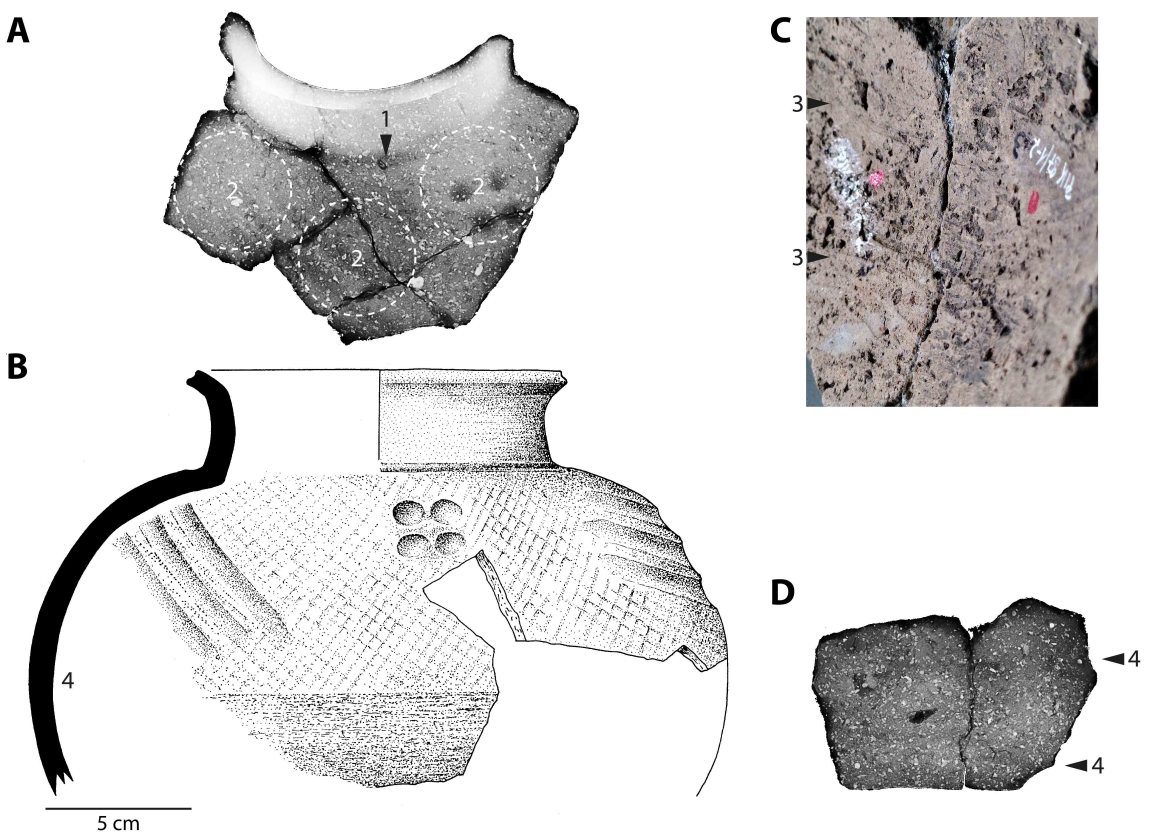

Fig. 13: Technical observations on PIK 87/1-2:3: (1) reduced density indicating join for the rim to the neck; (2) patches of higher and lower density; (3) fine scraping on the interior surfaces; (4) horizontally organized changes in density indicating remants of coils. (A: X-ray from superior; C: Detail of interior surface from D; D: X-ray from lateral)

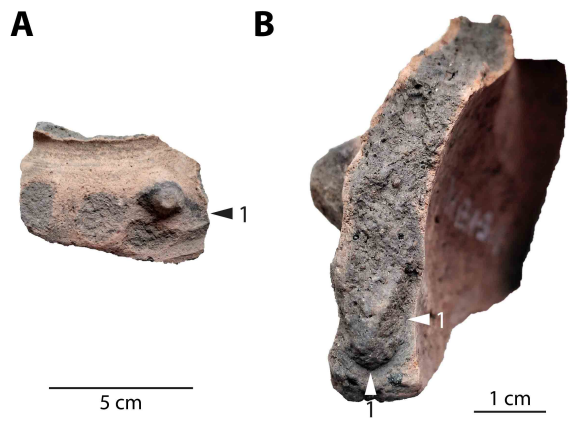

Fig. 14: Technical observations on PIK 87/1-3:? (1) remnants of a coil vissible in the break. (A: View from lateral; B: Detail of breakage)

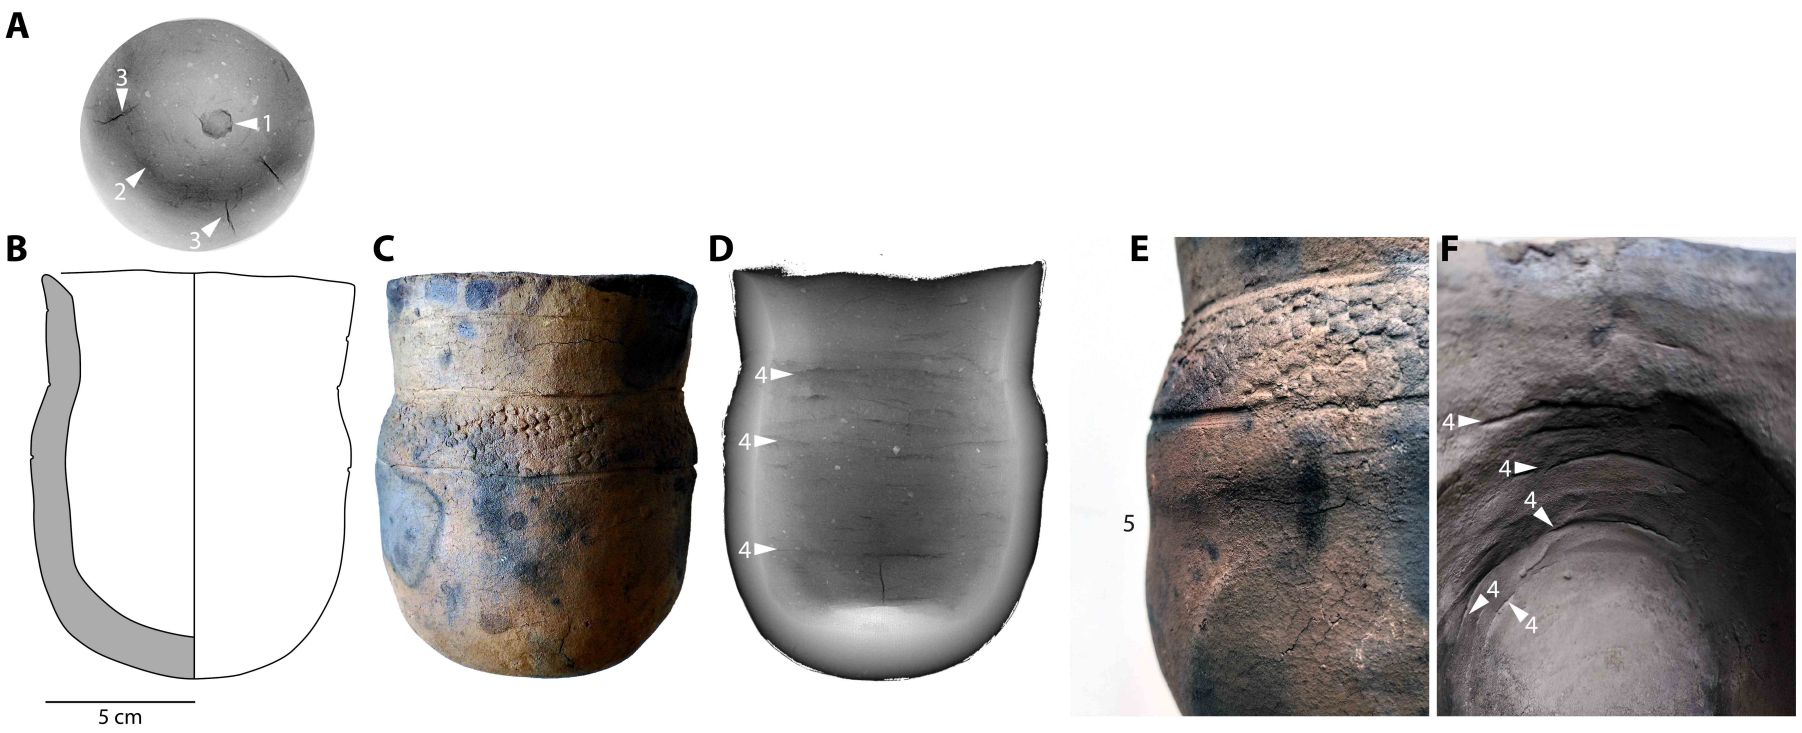

Fig. 15: Technical observations on PIK 87/501:2: (1) remnant of the removed fruit seed used as onset of the coiling; (2) concentric fissures; (3) radial cracks; (4) gaps between coils; (5) horizontally organized variations of the exterior surface of the vessel. (A: X-ray from superior; C: View from lateral; D: X-ray from lateral; E: Detail of exterior surface; F: Detail of interior surface)

cultural competencies (Heitz and Stapfer 2017). Training and learning, on the other hand, happen in continuous loops of applying embodied and cognitive knowledge with the use of specific tools (Kuijpers 2018).

The results presented in this study allow reconstructing key phases within the *chaîne opératoire* of potters producing Pikunda-Munda style vessels. The initial stage concerns the procurement and preparation of the raw materials. All previously studied vessel units of the Pikunda-Munda style (Seidensticker 2021, 114–120) showed a strikingly similar macroscopic fabric (Seidensticker 2021, 62 Tab. 11,69 Tab. 12), indicating similar clay sources. The petrographic analyses presented here further corroborates the macroscopic fabrics as all studied samples of Pikunda-Munda pottery were made using clays extremely rich in sponge spicules (Fig. 5A–F) that must originate from the floodplains of the rivers and smaller streams traversing the study area.

Research by Gosselain and Livingstone Smith (1997, 148) showed that potters usually "satisfy themselves with a very wide spectrum of clays" and that "processing techniques are not justified by techno-functional requirements, but governed by traditions and/or individual perceptions of a particular clay's appropriateness". Thus the observed preferences for specific clay sources and the 'recipe' in which the raw materials are handled represent chosen behaviors linked to the social identity of the potters. The findings of this study corroborate earlier observations (Seidensticker 2016, 123–124) in so far as, despite slightly varying shaping techniques and stylistic characteristics, the preference for fluvial clays among potters' communities responsible for vessels subsumed as Pikunda-Munda style is indicative of some degree of shared social identity. Especially telling is the finding from the Sangha river (Seidensticker 2020): during the Late Iron Age, fluvial clays were not used by potters of the younger Ngoko tradition (greenish colored styles in Fig. 3; 16:13–21;

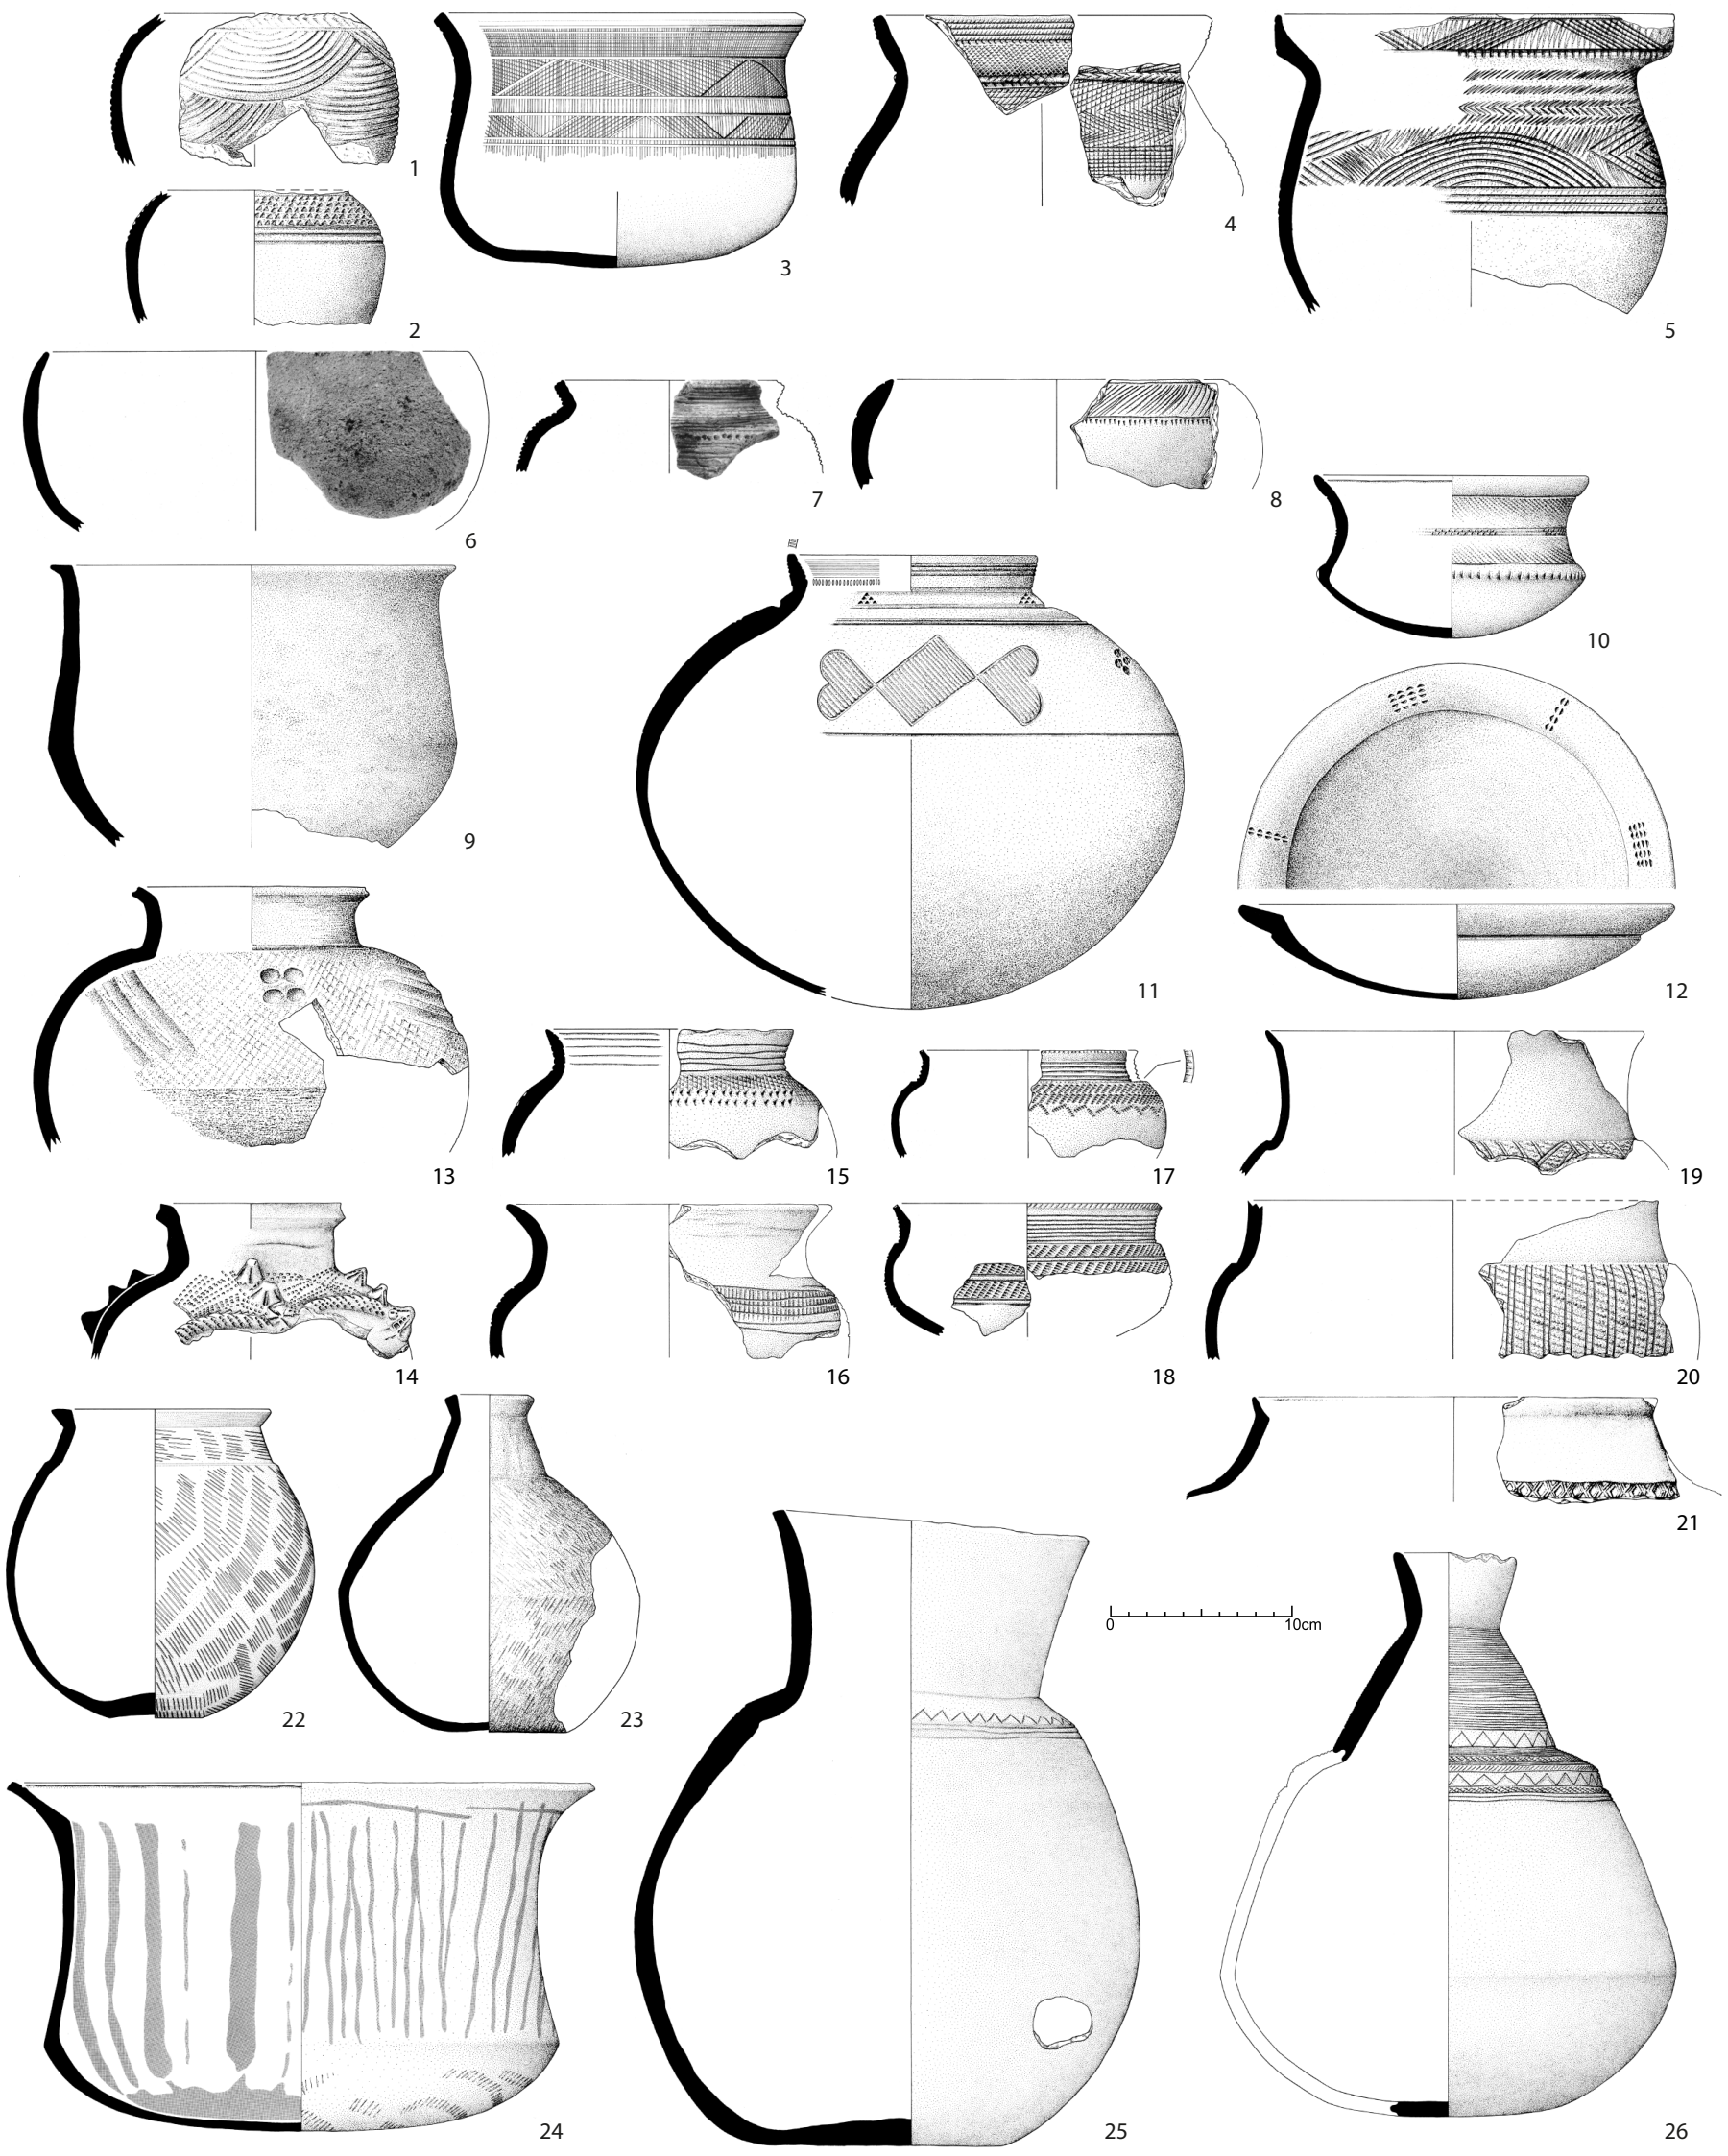

Fig. 16: Examples of pottery styles recorded in the Western Congo Basin in general chronological order: 1–2) Imbonga (Seidensticker 2021, 169–172); 3–4) Pikunda-Munda (ibid. 114–120); 5) Bokonogo (ibid. 120–123); 6–8) Bobusa (ibid. 162–165); 9) Matoto (ibid. 128–131); 10–12) Ngombe (ibid. 124–128); 13–14) Mandombe (ibid. 145–148); 15–16) Konda (ibid. 148–152); 17–18) Ouesso (ibid. 152–155); 19–20) Pandama (ibid. 155-158); 21) Mbenja (ibid. 158–162); 22–23) Ebambe (ibid. 131–136); 24) Mobaka (ibid. 141–144); 25–26) Epena (ibid. 137–141). The chrono-spatial distribution of these ceramics types are displayed in Fig. 3. (Drawings: Rita Vollbracht)

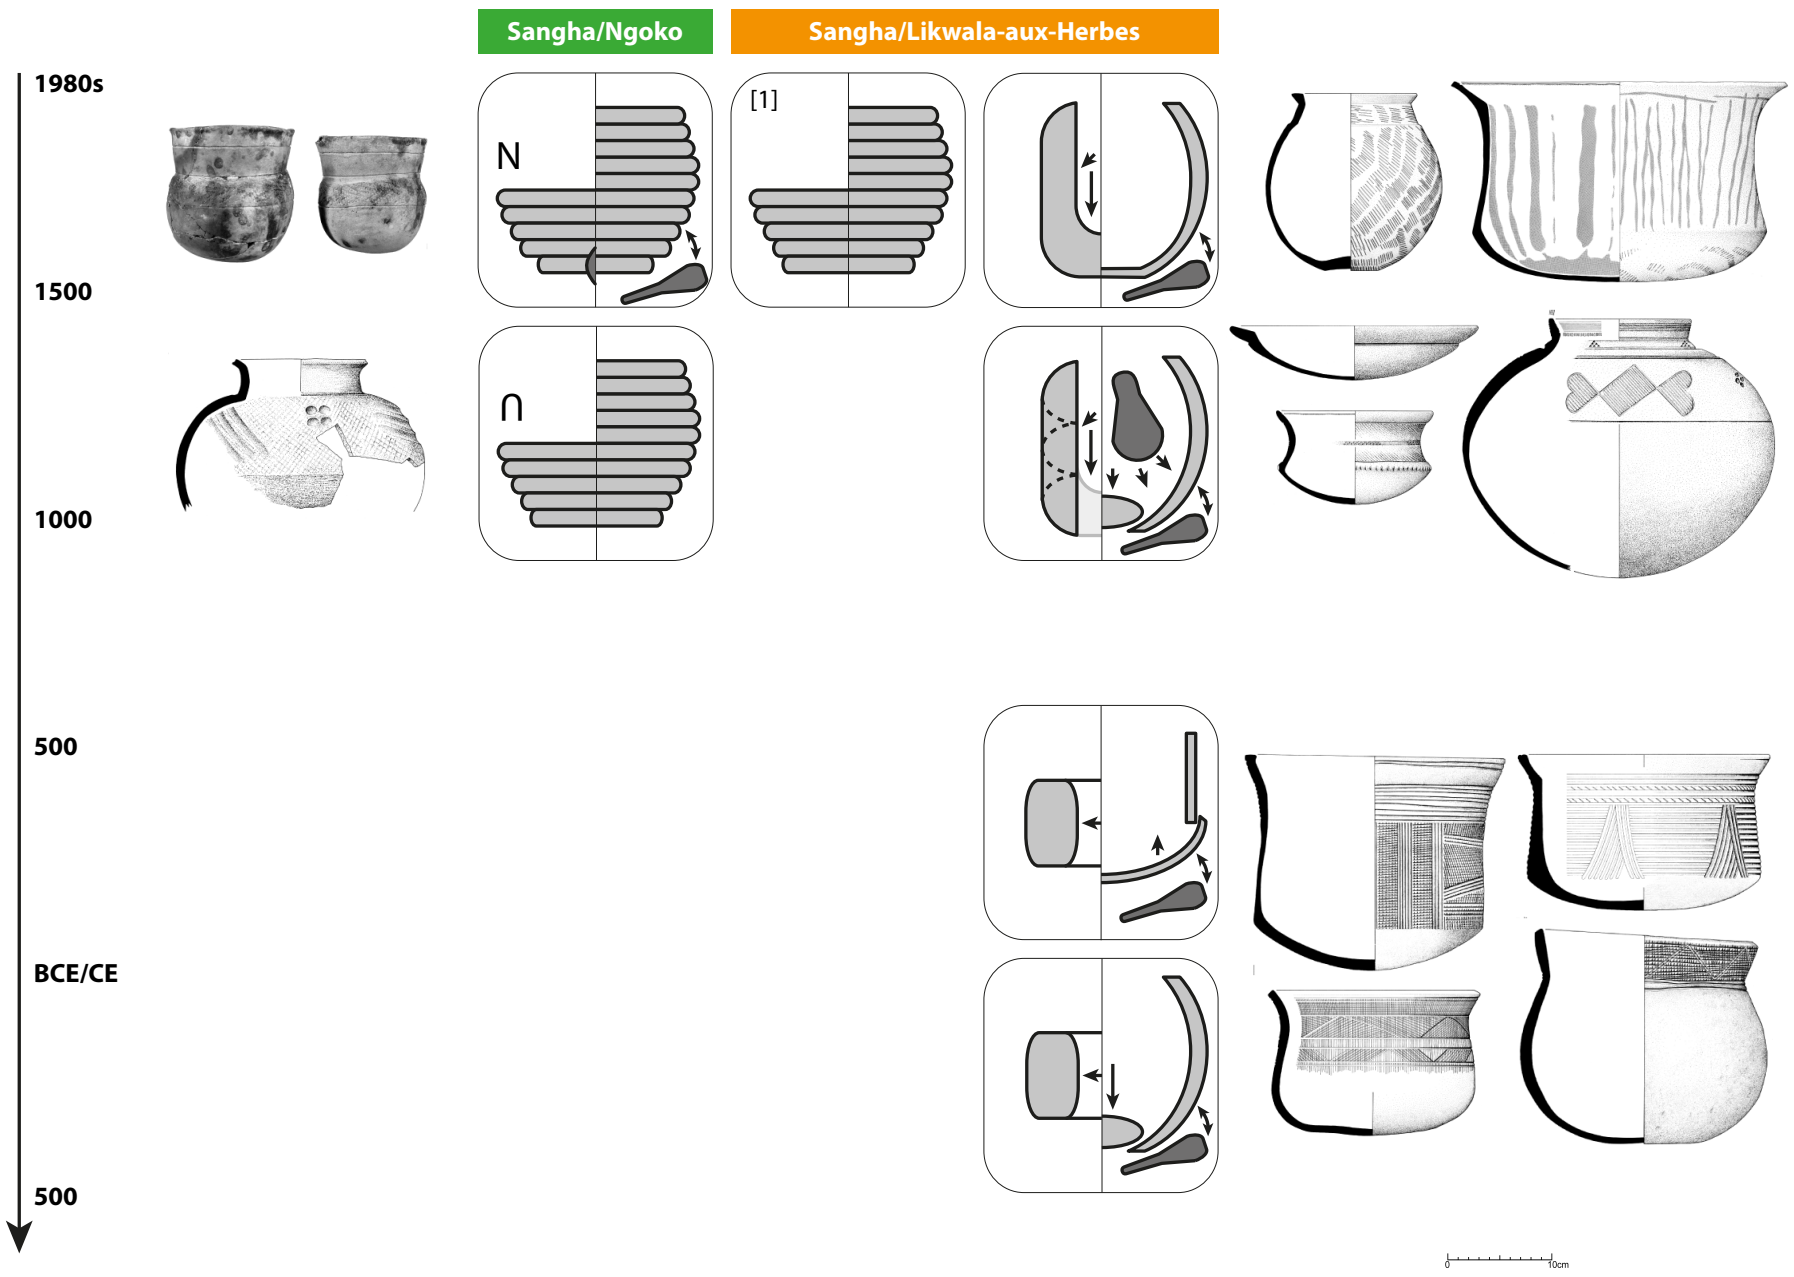

Fig. 17: Schematic overview of changes in primary and secondary shaping techniques along the rivers Ngoko, Sangha and Likwala-aux-Herbes throughout the past 2.000 years as reconstructed based on macro-traces and x-ray-analysis of pottery vessels. Greenish shade represents pottery styles associated with the Ngoko-style-tradition, while orange color represent pottery styles associated with the Pikunda-Munda style and the subsequent pottery styles related to ceramics from the Inner Congo Basin (Fig. 3). Ethnographic records offer insight into modern potting techniques and are either to be published elsewhere (Eggert in prep.) or in reference to Mpika-Ngoma ([1]; 1996, 25–35). Alongside the generalized shaping techniques are representative examples of the produced vessels shows (cf. Seidensticker 2021, 2024)

5:J–L; 13–14; 17), while potters producing other contemporaneous styles such as Ngombe, Ebambe, Epena, or Mobaka (orange-brownish colored styles in Fig. 3; 16:10–12 & 22–26; 5:G–I; 11–12; 17) were still relying exclusively on fluvial clays, similar to Pikunda-Munda potters' earlier. This further underlines that potters of the Ngoko tradition, whose vessels are shaped by coiling (Fig. 13–14; Seidensticker 2021, 53–54 Fig. 16B, 72 Tab. 13), similar to the modern pottery (Fig. 15), do not share any aspect of their potting behavior with preceding communities. On the other hand, potters along the lower Sangha, as well as the Likwala-aux-Herbes river, pertained the preference for fluvial clays (Fig. 5G–I). River clays are also the prevalent source used in the western parts of the Inner Congo Basin, and pottery dating into the Late Iron Age along the lower Sangha and Likwala-aux-Herbes river are, with varying degrees, stylistically related to styles of the West tradition of the Equator-Co style tradition (Wotzka 1995, 221–222 Fig. 4). Future research will test to what degree the preference for fluvial clays is also a hallmark of the Equator-Co tradition.

Additionally, this study provides further insight into the primary and secondary shaping techniques of Pikunda-Munda style pottery. While earlier research (Seidensticker 2021, 47–51 Fig. 13,69–73) already suggested that Pikunda-Munda vessels were produced through drawing, this study could further specify the technique: Pikunda-Munda potters produced their vessels through the drawing of a ring technique and bases were either closed with additional clay or a separately shaped slab bottom (Fig. 17).

While there are no indications for the origin of the Pikunda-Munda pottery and its distinct *chaîne opératoire*, the exact cause for its disappearance is equally unclear. The youngest feature yielding Pikunda-Munda style pottery is a pit connected to an open bowl furnace or smith's hearth at Munda dating into the 3rd to 6th century CE (Seidensticker 2021, 335–339 Fig. 170). The next youngest pottery style identified along the lower Sangha river is the Ngoko style (Fig. 3; Seidensticker 2021, 125–128), recently dated into the late 12th to mid 13th century CE (Seidensticker 2024, Tab. 2: RICH-30864). The vessels of the Ngoko style show substantial stylistic similarities to the Longa and Mbandaka pottery of the Inner Congo Basin (Wotzka 1995, 121–128,139–143). The pottery from Ngombe is made of fluvial clays rich in sponge spicules (Seidensticker 2020) and at least the big globular vessel is shaped via drawing of superimposed rings (Fig. 11–12; Seidensticker 2021, 52–53 Fig. 15). Worth mentioning is the presence of carinated bowls within the Ngombe style (Fig. 16.10; 11), strikingly similar to the characteristics carinated bowls of the Longa pottery from the Inner Congo Basin (Wotzka 1995, 121–128). The main vessel shape, with its flared rims, concave upper parts, and a pronounced carinations leading to round bases (Seidensticker 2021, 197 Fig. 94.1–2) are the only putative typological remnant one might consider to discuss in term of heritage of the Pikunda-Munda bowls.

Along the Likwala-aux-Herbes river, pottery production is only attested for from the 16th century CE onward again (Fig. 3), as represented by the Ebambe style (Fig. 16.22-23; Seidensticker 2021, 131–136). Vessels of that style are very similar to the modern Epena style (Fig. 16.25-26 Seidensticker 2021, 137–141) and both styles are produced exclusively using fluvial clays as well (Seidensticker 2020). Regarding shaping techniques, preliminary research found that vessels of both styles share features indicative of the drawing of a ring or drawing of superimposed rings technique (Fig. 17; Seidensticker 2021, 55–57 Fig. 17–18). Of particular interest in terms of the 'heritage' of the Pikunda-Munda pottery among modern pottery in the region is the Mobaka pottery style (Seidensticker 2021, 141–144). The defining feature of this style are carinated bowls of seemingly the same basic shape as in the Pikunda-Munda group (Fig. 16.24; Seidensticker 2021, 142 Fig. 63.1,64). At this stage, it remains unfortunately unclear why modern potters' producing the Mobaka style bowls choose this particular shape.

Further upstream of Pikunda (Fig. 1), pottery production commences again from the 13th century onward (Fig. 3). The stylistic characteristics are substantially different, and ceramics are part of the Ngoko style tradition consisting of five successive style groups: Mandombe, Konda, Ouoesso, Pandama, and Mbenja (Fig. 16.13–21; Seidensticker 2021, 145–162). Besides globular pots being the dominant vessel shape among these styles, they all have been produced using terrestrial clays void of sponge spicules (Fig. 5.J–K; Seidensticker 2020). Preliminary research on archaeological finds (Fig. 13–14; Seidensticker 2021, 53–54 Fig. 16B) as well as ethnographic records and ceramic vessel (Fig. 15) indicate that coiling is the defining shaping technique within the Ngoko tradition (Fig. 17). Thus, the styles of the Ngoko tradition are considered distinct, potentially originating further upstream along the Sangha and Ngoko/Dja river in south-east Cameroon.

Ethnographic research at Ikenge on the Ruki river (Fig. 1), the foremost potters villages in the Inner Congo Basin, describes a *chaîne opératoire* in which the primary shaping or roughing-out starts with hollowing out of a lump (Eggert and Kanimba-Misago 1980). The pierced lump, now practically converted into a ring of clay, is further shaped by drawing and additional clay is added to shape the base. This process involves pounding of the base on a flat surface and paddling of the outside. Among modern potters along the rivers Tshuapa, Busira, and Maringa, this general approach is slightly altered as a mat is used as pad during the pounding, leaving diagnostic markings (Wotzka 1995, 188,196–197). Preliminary research on the shaping techniques of vessels dating into the Early Iron Age in the Inner Congo basin revealed features more related to a 'pure' drawing of a lump technique, as there are no signs of any addition of clay or separate forming techniques being used for the bases compared to the upper parts. Thus, the distinct drawing of a ring technique employed by Pikunda-Munda potters has no immediate connection to contemporaneous communities further east as far as current research goes. But, in the north-eastern Congo Basin, drawing of a ring technique is practices (Livingstone Smith et al. 2017, 110,115). There, pottery of the early and middle phase has been shaped via this technique. The region saw a substantial change in shaping techniques as all pottery pertaining to the Late Iron Age is produced via pounding on a concave mold (Livingstone Smith et al. 2017, 111,115). In the northern Congo Basin, along the Ubangi river, the *chaîne opératoire* of only the youngest ceramics could be identified. Along the middle part of the river, coiling has been documented, while further north, already in the northern Savannas, pounding on a concave mold is practiced (Seidensticker 2021, 55–60 Fig. 19–20,73). The current patchwork of data on pottery technology in the Congo Basin and its evolvement through time prevents any integration of the *chaîne opératoire* of Pikunda-Munda potters into a wider framework.

The end of the Pikunda-Munda pottery style in the 5th ot 6th century CE corresponds with the supra-regional setback in human activity, which was first described on a regional level Oslisly (1998), and firmly established independently by de Saulieu et al. (2021) and Seidensticker et al. (2021). While at the supra-regional scale a state of 'low activity' with relic populations Seidensticker et al. (cf. 2021, Fig. S4) can be identified, in the western Congo Basin, the region of the Pikunda-Munda style pottery, a complete hiatus, and end of the tradition of Pikunda-Munda potters' communities must be presumed. The pottery inventories themselves offer no signs that any distinct traits of the Pikunda-Munda potters' knowledge persisted, as no subsequent pottery shows any reminiscence of this older pottery. The mentioned similarities in terms of clay sourcing and preparation strategies, specifically the universal sourcing of fluvial clays that are used without tempering, are no characteristic of the Pikunda-Munda pottery alone. With complete *chaînes opératoires* for ceramic production in the Congo Basin largely missing, it must remain a subject of future research what the diagnostic features of the 'recipe' of Pikunda-Munda potters were. A viable candidate for a unique characteristic of their *chaîne opératoire* might be the drawing of a ring technique with slab bottoms, which is not present in any of the subsequent pottery types. But many unknown remain, especially in the way in which the Equator-Co style tradition (Wotzka 1995) constitutes the – at least somewhat 'stable' – backbone of a genealogical network for trans-generational knowledge transfer among potters communities in the wider region. But follow-up examinations (Seidensticker 2021, 193–204) and a novel radiocarbon date (Seidensticker 2024, Tab. 2: RICH-30867) raise chronological issues that need to be resolved before claiming long-lasting continuities spanning the period of 'low activity'.

Despite the regional scope of this study, it highlights a distinctiveness of archaeological research, which research focused on retracing of modern languages or genetic compositions of communities is incapable of: the disappearance of items of material culture accompanied by discontinuities in the genealogical networks of knowledge transfer. While the prevailing hypotheses of the 'Bantu-Expansion' have been critiqued for many decades (de Maret 1989; Robertson and Bradley 2000; Eggert 2005, 2016), 'discontinuity' have not been a focal point of the debate yet, despite the latest set of proposed models (Bostoen et al. 2015; Grollemund et al. 2015, 2023; Koile et al. 2022) necessitate profound continuities. The statistical approaches used to reconstruct past languages from modern datasets is unable to detect contact induced change (Eggert 2016, 86) or inter-community knowledge-transfer as well as estimating the rates of speciation and extinction reliably (Pagel 2020). The reliance on a single strain of material culture, namely pottery production, is a further issue. Not only is any generalization that is based on a single component of the material culture of prehistoric communities inherently insufficient, but the level of research on many facets of the prehistoric communities producing and distributing ceramics in Central Africa, like their networks of trade or trans-communal knowledge transfer among others, is only in its infancy. The available debate on the 'Bantu-Expansion' constitutes discipline-specific "procedural puzzles" (Eggert 2016, 88) devoted to the "separate histories" materialized in modern languages, population genetics (Fortes-Lima et al. 2024) and items of material culture without any ability of deducing the immaterial nature of non-written languages through material traces (Eggert 2016, 85). The current view in which the purely linguistic term 'Bantu' has been transformed to refer "indiscriminately to language, culture, society, and race" (Eggert 2005, 302) must be scrutinized in-depth and untangle where necessary to avoid the circular reasoning plaguing the debate (Ehret 1973; Phillipson 1976a,b, 1977; Heine et al. 1977; Bostoen et al. 2015; Grollemund et al. 2015, 2023; Koile et al. 2022).

5 Conclusions

This paper presents novel data on the pottery of the Pikunda-Munda style, which is among the oldest ceramics found in the western Congo Basin, dating from the 2nd century BCE to the 5th/6th century CE. It thus emerges around 200 years after the Imbonga pottery group, appearing further east and today known as the most ancient pottery in the Congo Basin (Fig. 3; Wotzka 1995, 59–68). Moreover, Pikunda-Munda pottery shares certain characteristics with contemporaneous ceramics of the Inner Congo Basin (Wotzka 1995, 107 Ftn. 4). Besides stylistic similarities, such as the usage of similar tools for decorating and preferences of motives, including rocker-stamping with a comb (Seidensticker 2021, 118 Tab. 14), Pikunda-Munda potters also used fluvial clays rich in sponge spicules without the addition of any temper agents. What sets Pikunda-Munda vessels apart are the shape of the vessels: its carinated bowls with round bases are unique within the Early Iron Age in the Congo Basin. All its characteristics vanish after the 5th to 6th century CE, and they leave little to no trace in any other subsequent pottery nearby. The next youngest pottery in the western Congo Basin, preceding the Pikunda-Munda style, can only be dated to the 12th century CE at the earliest (Seidensticker 2024, Tab. 2: RICH-30864), leaving a 500 year gap with no pottery finds – even tentatively – being dated into (Fig. 3A).

The present research, while still in its infancy, shows that the focus on stylistic changes seen within the archaeological research of the region (Wotzka 1995; Seidensticker 2021) is only scratching the surface. Vessel morphology and decorations depict changes in fashion trends, while the detailed technical analyses shown here enable a reconstruction of decisions made by potters that tie together communities of practices.

Acknowledgements First and foremost, I want to thank Manfred K. H. Eggert for granting me access to the finds from his project and supporting the research. This research was funded by the Fonds Wetenschappelijk Onderzoek - Vlaanderen (FWO; 1287922N). The Commissie Wetenschappelijk Onderzoek (CWO) of Ghent University funded the preparation of an initial set of thin-sections. Many thanks goes to Garin Cael and Alexandre Livingstone Smith for preparing the radiographs at the Royal Museum for Central Africa (RMCA) Tervuren.

All data, images and computer code generated during this research is available here: `https://github.com/dirkseidensticker/PikundaMunda_DissapearingPotteryTraditions_AAR`.

References

Adamson DA, Clark JD, Williams MAJ (1987) Pottery tempered with sponge from the White Nile, Sudan. The African Archaeological Review 5(1):115–127, DOI 10.1007/BF01117087

Ard V (2014) Produire et échanger au Néolithique: Traditions céramiques entre Loire et Gironde au IVe millénaire, Documents préhistoriques, vol 33. Éd. du CTHS, Paris

Arroyo-Kalin M, Riris P (2021) Did pre-Columbian populations of the Amazonian biome reach carrying capacity during the Late Holocene? Philosophical Transactions of the Royal Society B: Biological Sciences 376(1816):20190715, DOI 10.1098/rstb.2019.0715

Ashley CZ (2005) Ceramic variability and change: A perspective from Great Lakes Africa. PhD thesis, University College London, London

Bevan A, Crema E (2022) Rcarbon: Calibration and analysis of radiocarbon dates

Bevan A, Colledge S, Fuller D, Fyfe R, Shennan S, Stevens C (2017) Holocene fluctuations in human population demonstrate repeated links to food production and climate. Proceedings of the National Academy of Sciences of the United States of America 114(49):E10524–E10531, DOI \url{10.1073/pnas.1709190114}

Bivand R, Anselin L, Berke O, Bernat A, Carvalho M, Chun Y, Dormann CF, Dray S, Halbersma R, Lewin-Koh N, et al. (2023) Spdep: Spatial dependence: Weighting schemes, statistics and models. R package version 1.2-8

Bloch L, Wallis NJ, Kamenov G, Jaeger JM (2019) Production origins and matrix constituents of spiculate pottery in Florida, USA: Defining ubiquitous St Johns ware by LA-ICP-MS and XRD. Journal of Archaeological Science: Reports 24:313–323, DOI 10.1016/j.jasrep.2019.01.012

Bostoen K (2018) The Bantu Expansion. Oxford Research Encyclopedia of African History DOI 10.1093/acrefore/9780190277734.013.191

Bostoen K (2020) The Bantu Expansion: Some facts and fiction. In: Crevels EI, Muysken P (eds) Language Dispersal, Diversification, and Contact: A Global Perspective, Oxford University Press, pp 227–239, DOI 10.1093/oso/9780198723813.003.0013

Bostoen K, Gunnink H (2022) The Impact of Autochthonous Languages on Bantu Language Variation: A Comparative View on Southern and Central Africa. In: Mufwene S, Escobar AM (eds) The Cambridge Handbook of Language Contact: Volume 1: Population Movement and Language Change, Cambridge Handbooks in Language and Linguistics, Cambridge University Press, pp 152–186

Bostoen K, Clist B, Doumenge C, Grollemund R, Hombert JM, Muluwa JK, Maley J (2015) Middle to Late Holocene Paleoclimatic Change and the Early Bantu Expansion in the Rain Forests of Western Central Africa. Current Anthropology 56(3):354–384, DOI 10.1086/681436

Braun DP (1983) Pots as Tools. In: Archaeological Hammers and Theories, Elsevier, pp 107–134, DOI 10.1016/B978-0-12-505980-0.50012-4

Bremond L, Bodin SC, Bentaleb I, Favier C, Canal S (2017) Past tree cover of the Congo Basin recovered by phytoliths and d 13 C along soil profiles. Quaternary International 434:91–101, DOI 10.1016/j.quaint.2015.11.150

Brissaud I, Houdayer A (1986) Sponge spicules as a characteristic of ancient African pottery from Mali. Journal of Field Archaeology 13(3):357–359

Brown AA, Crema ER (2019) Māori Population Growth in Pre-contact New Zealand: Regional Population Dynamics Inferred From Summed Probability Distributions of Radiocarbon Dates. The Journal of Island and Coastal Archaeology pp 1–19, DOI 10.1080/15564894.2019.1605429

Clist B (2004/2005) Des premièrs villages aux premiers Européens autour de l'Estuaire du Gabon. Quatre millénaires d'interactions entre l'homme et son milieu. Unpubl. Ph.D. Dissertation. Université Libre de Bruxelles, Academic Year 2004-2005. Universite Libre de Bruxelles, Brussels

Clist B, Denbow J, Lanfranchi R (2023) Using the radiocarbon dates of Central Africa for studying long-term demographic trends of the last 50,000 years: Potential and pitfalls. Azania: Archaeological Research in Africa 58(2):93, DOI 10.1080/0067270X.2023.2215649

Cordell AS (1993) Chronological variability in ceramic paste: A comparison of deptford and savannah period pottery in the st. Marys river region of northeast Florida and southeast Georgia. Southeastern Archaeology 12(1):33–58, 40712986

da Costa ML, Kern DC, Pinto AHE, Souza JRdT (2004) The ceramic artifacts in archaeological black earth (terra preta) from lower Amazon region, Brazil: Mineralogy. Acta Amazonica 34(2):165–178, DOI 10.1590/S0044-59672004000200004

Crema ER, Di Napoli R (2021) nimbleCarbon: Bayesian Analyses of Radiocarbon Dates with NIMBLE

Crema ER, Shoda S (2021) A Bayesian approach for fitting and comparing demographic growth models of radiocarbon dates: A case study on the Jomon-Yayoi transition in Kyushu (Japan). PLOS ONE 16(5):e0251695, DOI 10.1371/journal.pone.0251695

Crema ER, Habu J, Kobayashi K, Madella M, Pinhasi R (2016) Summed Probability Distribution of 14C Dates Suggests Regional Divergences in the Population Dynamics of the Jomon Period in Eastern Japan. PLoS ONE 11(4):e0154809, DOI 10.1371/journal.pone.0154809

Currie TE, Meade A, Guillon M, Mace R (2013) Cultural phylogeography of the Bantu Languages of sub-Saharan Africa. Proceedings of the Royal Society B: Biological Sciences 280(1762):20130695, DOI 10.1098/rspb.2013.0695

de Maret P (1989) Le contexte archéologique de l'expansion Bantu en Afrique Centrale. In: Obenga T (ed) Les Peuples bantu: migrations, expansion et identité culturelle: actes du colloque international, Libreville 1-6 avril 1985, CICIBA ; L'Harmattan, Libreville : Paris, pp 118–138

de Saulieu G, Oslisly R, Nlend Nlend P, Ngouoh F (2017) Deux mille cinq cents ans de traditions céramiques à Dibamba Yassa (Cameroun). Afrique: Archéologie & Arts 13:23–40, DOI 10.4000/aaa.979

de Saulieu G, Garcin Y, Sebag D, Nlend PRN, Zeitlyn D, Deschamps P, Ménot G, Carlo PD, Oslisly R (2021) Archaeological Evidence for Population Rise and Collapse between ~2500 and ~500 cal. yr BP in Western Central Africa. Afrique : Archeologie et Arts 17:11–32, DOI 10.4000/aaa.3029

de Souza JG, Riris P (2021) Delayed demographic transition following the adoption of cultivated plants in the eastern La Plata Basin and Atlantic coast, South America. Journal of Archaeological Science 125:105293, DOI 10.1016/j.jas.2020.105293

Delvoye A (2022) Les traditions céramiques du mégalithisme du Sénégal et de Gambie : Une nouvelle périodisation pour l'Afrique de l'Ouest aux Ier et IIe millénaires de notre ère. Journal of African Archaeology 20(2):230–258, DOI 10.1163/21915784-bja10020

Delvoye A, Laporte L, Bocoum H, Bernard R, Cros JP, Djouad S, Dartois V, Lejay M, Athié A, Cissé F, Quesnel L (2016) L'Art et la manière: Approche technologique des céramiques de dépôt dans le mégalithisme sénégambien – Le cas de la nécropole de Wanar (Sénégal). Journal of African Archaeology 14(2):115–134, DOI \url{10.3213/2191-5784-10289}

Drost D (1967) Töpferei in Afrika: Technologie, Veröffentlichungen des Museums für Völkerkunde zu Leipzig / Museum für Völkerkunde, vol 15. Akademie-Verlag, Berlin

Eggert MKH (1992) The Central African Rain Forest: Historical Speculation and Archaeological Facts. World Archaeology 24:1–24, DOI 10.1080/00438243.1992.9980190

Eggert MKH (1993) Central Africa and the Archaeology of the Equatorial Rainforest. Reflections on Some Major Topics. In: Shaw T, Sinclair P, Andah B, Okpoko A (eds) The Archaeology of Africa. Food, Metal and Towns, One World Archaeology, Routledge, London and New York, pp 289–329

Eggert MKH (2005) The Bantu Problem and African Archaeology. In: Stahl AB (ed) African Archaeology, Blackwell Studies in Global Archaeology, Blackwell Pub., Malden, pp 301–326

Eggert MKH (2012) 'Bantuwanderungen' in der Südhälfte Afrikas: Historische Sprachwissenschaft, Archäologie, Archäobotanik und Archäogenetik. In: Borgolte M, Dücker J, Müllerburg M, Predatsch P, Schneidmüller B (eds) Europa Im Geflecht Der Welt, Europa Im Mittelalter, Akademie, Berlin, pp 193–216

Eggert MKH (2014) The Archaeology of the Central African Rainforest: Its Current State. In: Renfrew C, Bahn PG (eds) The Cambridge World Prehistory, Cambridge University Press, Cambridge, pp 183–203

Eggert MKH (2016) Geneticizing Bantu: Historical Insight or Historical Trilemma? Medieval Worlds 4:79–90, DOI 10.1553/medievalworlds_no4_2016s79

Eggert MKH (in prep.) Pottery Making in Ikenge on the Ruki and Other Villages in the Congo Basin. Edition Historische Kulturwissenschaften, Waxmann, Münster and New York

Eggert MKH, Kanimba-Misago (1980) Aspects d'un métier traditionnel: L'industrie de poterie à Ikenge (Région de l'Equateur, Zaïre). Baesseler-Archiv NF 28:387–430

Ehret C (1973) Patterns of Bantu and Central Sudanic Settlement in Central and Southern Africa (ca. 1000 B.C.-500 A.D.). Transafrican Journal of History 3:1–71

Fortes-Lima CA, Burgarella C, Hammarén R, Eriksson A, Vicente M, Jolly C, Semo A, Gunnink H, Pacchiarotti S, Mundeke L, Matonda I, Muluwa JK, Coutros P, Nyambe TS, Cikomola JC, Coetzee V, De Castro M, Ebbesen P, Delanghe J, Stoneking M, Barham L, Lombard M, Meyer A, Steyn M, Malmström H, Rocha J, Soodyall H, Pakendorf B, Bostoen K, Schlebusch CM (2024) The genetic legacy of the expansion of Bantu-speaking peoples in Africa. Nature 625:540–547, DOI 10.1038/s41586-023-06770-6

Gaffney D (2020) Materialising Ancestral Madang: Pottery Production and Subsistence Trading on the Northeast Coast of New Guinea, University of Otago Studies in Archaeology, vol 29

Gallay A, Huysecom E, Mayor A (1998) Peuples et Ceramiques Du Delta Interieur Du Niger (Mali): Un Bilan de Cinq Années de Missions (1988 - 1993), Terra Archaeologica, vol 3. von Zabern, Mainz am Rhein

Gaspar Da Silva L, Gosselain OP, Livingstone Smith A, Elhadi N (2005) Potières et poterie de Dia. In: Bedaux RMA (ed) Recherches Archéologiques à Dia Dans Le Delta Intérieur Du Niger (Mali), Mededelingen van Het Rijksmuseum Voor Volkenkunde, Research School of Asian, African, and Amerindian Studies, Leiden University, Leiden, pp 315–349

Gomart L (2014) Traditions techniques et production céramique au Néolithique ancien: Étude de huit sites rubanés du nord est de la France et de Belgique. Sidestone Press, Havertown

Gombin J, Vaidyanathan R, Agafonkin V (2017) Concaveman: A Very Fast 2D Concave Hull Algorithm

Gosselain OP (1992) Technology and Style: Potters and Pottery among Bafia of Cameroon. Man (NS) 27(3):559–586

Gosselain OP (2002) Poteries du Cameroun méridionial: styles, techniques et rapports à l'identité. No. 26 in CRA monographies, CNRS éd, Paris

Gosselain OP (2006) Atlas des traditions céramique du Niger. In: Centre de recherches archéologiques (ed) L'archéologie à l'Université Libre de Bruxelles (2001-2005), Études d'archéologie, CReA, Bruxelles, pp 163–173

Gosselain OP (2010) Exploring the dynamics of African pottery cultures. In: Barndon R, Engevik A, Øye I (eds) The archaeology of regional technologies, Edwin Mellen Press, Lewiston, pp 193–224

Gosselain OP (2014) Ceramics in Africa. In: Selin H (ed) Encyclopaedia of the History of Science, Technology, and Medicine in Non-Western Cultures, Springer Netherlands, Dordrecht, pp 1–18, DOI \url{10.1007/978-94-007-3934-5{\textunderscore}8911-2}

Gosselain OP (2018) Pottery chaînes opératoires as Historical Documents. In: Oxford Research Encyclopedia of African History, Oxford University Press, Oxford, DOI 10.1093/acrefore/9780190277734.013.208

Gosselain OP, Livingstone Smith A (1997) The Ceramic and Society Project: An ethnographic and experimental approach to technological style. In: Lindahl A, Stilborg O, Hulthén B (eds) The Aim of Laboratory Analyses of Ceramics in Archaeology, April 7-9, 1995 in Lund Sweden, no. 34 in Konferenser, Kungl. Vitterhets historie och antikvitets akademien ; Distributed by Almqvist & Wiksell International, Stockholm, pp 147–160

Gosselain OP, Livingstone Smith A (2005) The Source: Clay Selection and Processing Practices in sub-Saharan Africa. In: Livingstone Smith A, Bosquet D (eds) Pottery Manufacturing Processes: Actes Du XIVème Congrès UISPP, Université de Liège, Belgique, 2-8 Septembre 2001, Section 2: Archaeometry, Colloque = Symposium 2.1, BAR International Series, Archaeopress, Oxford, pp 33–47

Gouem Gouem B (2010/2011) Des premières communautés villageoises aux sociétés complexes sur le littoral méridional du Cameroun: Dissertation. Universite libre de Bruxelles, Brüssel

Grollemund R, Branford S, Bostoen K, Meade A, Venditti C, Pagel M (2015) Bantu expansion shows that habitat alters the route and pace of human dispersals. Proceedings of the National Academy of Sciences of the United States of America 112(43):13296–13301, DOI 10.1073/pnas.1503793112

Grollemund R, Schoenbrun D, Vansina J (2023) Moving Histories: Bantu Language Expansions, Eclectic Economies, and Mobilities. The Journal of African History 64(1):13–37, DOI 10.1017/S0021853722000780

Heine B, Hoff H, Vossen R (1977) Neuere Ergebnisse zur Territorialgeschichte der Bantu. In: Möhlig WJG, Rottland F, Heine B (eds) Zur Sprachgeschichte und Ethnohistorie in Afrika: Neue Beiträge afrikanischer Forschungen, Reimer, Berlin, pp 57–72

Heitz C (2023) Keramik jenseits von "Kulturen": Mobilität, Verflechtungen und Transformationen im nördlichen Alpenvorland (3950-3800 v.Chr.). Sidestone Press, Leiden

Heitz C, Stapfer R (2017) Mobility and pottery production, what for? Introductory remarks. In: Heitz C, Stapfer R (eds) Mobility and Pottery Production: Archaeological & Anthropological Perspectives, Sidestone Press, Leiden, pp 11–38

Koile E, Greenhill SJ, Blasi DE, Bouckaert R, Gray RD (2022) Phylogeographic analysis of the Bantu language expansion supports a rainforest route. Proceedings of the National Academy of Sciences 119(32):e2112853119, DOI 10.1073/pnas.2112853119

Kuijpers MHG (2018) A Sensory Update to the Chaîne Opératoire in Order to Study Skill: Perceptive Categories for Copper-Compositions in Archaeometallurgy. Journal of Archaeological Method and Theory 25(3):863–891, DOI 10.1007/s10816-017-9356-9

Lange M (2006) Wadi Shaw - Wadi Sahal: Studien zur holozänen Besiedlung der Laqiya-Region (Nordsudan), Africa Praehistorica, vol 19. Heinrich-Barth-Inst, Köln

Lave J (1991) Situating learning in communities of practice. In: Resnick LB, Levine JM, Teasley SD (eds) Perspectives on Socially Shared Cognition., American Psychological Association, Washington, pp 63–82, DOI 10.1037/10096-003

Lave J, Wenger E (1991) Situated Learning: Legitimate Peripheral Participation. Learning in Doing, Cambridge University Press, Cambridge [England] ; New York

Lechtman H (1977) Style in Technology: Some Early Thoughts. In: Lechtman H, Merrill RS, Society AE, (US) CSAS, Association for the Anthropological Study of Play (eds) Material Culture: Styles, Organization, and Dynamics of Technology, Proceedings of the American Ethnological Society ; 1975, West Pub. Co, St. Paul, pp 3–20

Linné S (1932) Contribution a l'étude de la céramique Sudaméricaine. Revista del Instituto de Etnolpogía de la Universidad Nacional de Tucumán 2(2a)

Linné S (1957) Technical Secrets of American Indians. The Journal of the Royal Anthropological Institute of Great Britain and Ireland 87(2):149, DOI 10.2307/2844101, 2844101

Livingstone Smith A (2007a) Chaîne opératoire de la poterie: Références ethnographiques, analyses et reconstitution. Musée Royal de l'Afrique Centrale, Tervuren

Livingstone Smith A (2007b) Technologie de la poterie en Afrique centrale méridionale: Résultats préliminaires d'enquêtes au Katanga (RDC). Nyame Akuma 67:7–13

Livingstone Smith A (2010) Pottery Traditions in Katanga (DRC). A Comparative Examination of Roughing-out Technologies. Anthropos 105(1):179–190, DOI 10.5771/0257-9774-2010-1-179

Livingstone Smith A (2016) Pottery and Politics: Making Sense of Pottery Traditions in Central Africa. Cambridge Archaeological Journal 26(03):471–491, DOI 10.1017/S0959774316000317

Livingstone Smith A, van der Veken A (2009) The Crossing Boders Project: Pottery traditions in Katanga (DRC). Afrique: Archéologie & Arts 5 (2007–2009):141–148

Livingstone Smith A, Viseyrias A (2010) Shaping Kabambian Pottery: Identification and Definition of Technical Features. The Open Anthropology Journal 3:124–141

Livingstone Smith A, Cornelissen E, de Francquen C, Nikis N, Mees F, Tshibamba Mukendi J, Beeckman H, Bourland N, Hubau W (2017) Forests and rivers: The archaeology of the north eastern Congo. Quaternary International 448:95–116, DOI 10.1016/j.quaint.2016.10.010

Lozada Mendieta N (2019) Ancient pots and potters of the Atures Rapids region: Occupation and interaction processes in pre-colonial Middle Orinoco, Venezuela. Doctoral thesis (Ph.D), UCL (University College London), London

MacKenzie WS, Adams AE, Brodie KH (2017) Rocks and Minerals in Thin Section, revised 2nd ed edn. CRC press, Boca Raton

Maley J, Doumenge C, Giresse P, Mahé G, Philippon N, Hubau W, Lokonda MO, Tshibamba JM, Chepstow-Lusty A (2017) Late Holocene forest contraction and fragmentation in central Africa. Quaternary Research 89(1):43–59, DOI 10.1017/qua.2017.97

Manconi R, Pronzato R (2009) Atlas of African Freshwater Sponges. No. v. 295 in Studies in Afrotropical Zoology, Royal Museum for Central Africa, Tervuren

Manem S (2008) Les Fondements Technologiques de La Culture Des Duffaits (Âge Du Bronze Moyen). Thése Présentée à l'Université Paris X Nanterre. Université de Paris X, Nanterre, Paris

Marcelino V, Schaefer CE, Stoops G (2018) Oxic and Related Materials. In: Interpretation of Micromorphological Features of Soils and Regoliths, Elsevier, pp 663–689, DOI 10.1016/B978-0-444-63522-8.00023-1

Mayaux P, Bartholomé E, Massart M, van Cutsem C, Cabral A, Nonguierma A, Diallo O, Pretorius C, Thompson M, Cherlet M, Pekel JF, Defourny P, Vasconcelos M, Di Gregorio A, Fritz S, de Grandi G, Elvidge C, Vogt P, Belward AS (2003) A Land Cover Map of Africa: Carte de l'occupation Du Sol de l'Afrique, EUR / European Commission, vol 20665. EUR-OP / European Commission, Joint Research Centre, Luxembourg

Mayor A (2011) Traditions Céramiques Dans La Boucle Du Niger: Ethnoarchéologie et Histoire Du Peuplement Au Temps Des Empires Précoloniaux, Journal of African Archaeology Monograph Series, vol 2. Africa Magna Verlag, Frankfurt am Main

McIntosh SK (1995) Pottery. In: MacIntosh SK (ed) Excavations at Jenné-Jeno, Hambarketolo, and Kaniana (Inland Niger Delta, Mali), the 1981 season, University of California publications in anthropology, University of California Press, Berkeley, p 130

Mcintosh SK, MacDonald KC (1989) Sponge Spicules in Pottery: New Data from Mali. Journal of Field Archaeology 16(4):489–494, DOI 10.1179/jfa.1989.16.4.489

M'Mbogori FN (2015) Population and Ceramic Traditions: Revisiting the Tana Ware of Coastal Kenya (7th-14th Century AD), Cambridge Monographs in African Archaeology, vol 89. Archaeopress, Oxford

Mpika-Ngoma L (1996) Recherche comparée des céramiques traditionelles du Congo, des origines à nos jours: Ethnoarchéologie: art tradionnel Bantu. Editions Action Culturelle, Brazzaville

Napolitano MF, DiNapoli RJ, Stone JH, Levin MJ, Jew NP, Lane BG, O'Connor JT, Fitzpatrick SM (2019) Reevaluating human colonization of the Caribbean using chronometric hygiene and Bayesian modeling. Science Advances 5(12):eaar7806, DOI 10.1126/sciadv.aar7806

Natalio F, Corrales TP, Wanka S, Zaslansky P, Kappl M, Lima HP, Butt HJ, Tremel W (2015) Siliceous spicules enhance fracture-resistance and stiffness of pre-colonial Amazonian ceramics. Scientific Reports 5(1):13303, DOI 10.1038/srep13303

Nixon S, MacDonald K (2017) Pottery. In: Nixon S (ed) Essouk-Tadmekka: An Early Islamic Trans-Saharan Market Town, no. volume 12 in Journal of African Archaeology Monograph Series, Brill, Leiden ; Boston, pp 117–151

Nlend Nlend PR (2013/2014) Les Traditions ceramiques dans leur contexte archéologique sur le littoral Camerounais (Kribi-Campo) de 3000 à 500 BP: Thèse présentée en vue de l'obtention du grade académique de Docteur en Histoir, art et archéologie. Universite libre de Bruxelles, Brüssel

Nordström HÅ (1972) Neolithic and A-Group Sites, The Scandinavian Joint Expedition to Sudanese Nubia, vol 3. Läromedelsförl, Stockholm

Oslisly R (1998) Hommes et milieux à l'Holocene dans la moyenne vallée de l'Ogooué (Gabon). Bulletin de la Société Préhistorique Française 95(1):93–105

Oslisly R, Bentaleb I, Favier C, Fontugne M, Gillet JF, Morin-Rivat J (2013a) West Central African Peoples: Survey of Radiocarbon Dates over the Past 5000 Years. Radiocarbon 55(3):1377–1382, DOI 10.1017/S003382220004830X

Oslisly R, White L, Bentaleb I, Favier C, Fontugne M, Gillet JF, Sebag D (2013b) Climatic and cultural changes in the west Congo Basin forests over the past 5000 years. Philosophical Transactions of the Royal Society B 368:1–10, DOI 10.1098/rstb.2012.0304

Ottalagano FV (2016) A diachronic study of pre-Hispanic vessels from the middle basin of Paraná River (South America) using a petrographic approach. Journal of Archaeological Science: Reports 9:320–329, DOI 10.1016/j.jasrep.2016.08.012

Pagel M (2020) Can't see the wood for the trees. Nature 580(7804):461–462, DOI 10.1038/d41586-020-01021-4

Pakendorf B, Bostoen K, de Filippo C (2011) Molecular Perspectives on the Bantu Expansion: A Synthesis. Language Dynamics and Change 1:50–88

Pelegrin J, Bodu P, Karlin C, Tixier J (1988) Chaînes opératoires: Un outil pour le préhistorien. Journee d 'Etudes Technologiques en Prehistoire pp 55–62

Phillipson DW (1976a) Archaeology and Bantu Linguistics. World Archaeology 8(1):65–82

Phillipson DW (1976b) The Early Iron Age in Eastern and Southern Africa: A Critical Re-appraisal. Azania: Archaeological Research in Africa 11(1):1–23

Phillipson DW (1977) The Spread of the Bantu Languages. Scientific American 236(4):106–114

Quinn PS (2022) Thin Section Petrography, Geochemistry and Scanning Electron Microscopy of Archaeological Ceramics, 2nd edn. Archaeopress Archaeology, Oxford

Rice PM (2015) Pottery Analysis: A Sourcebook, 2nd edn. University of Chicago Press, Chicago

Riemer H (2011) El Kharafish: The Archaeology of Sheikh Muftah Pastoral Nomads in the Desert around Dakhla Oasis (Egypt), Africa Praehistorica, vol 25. Heinrich-Barth-Institut, Köln

Riris P (2018) Dates as data revisited: A statistical examination of the Peruvian preceramic radiocarbon record. Journal of Archaeological Science 97:67–76, DOI 10.1016/j.jas.2018.06.008

Riris P, Arroyo-Kalin M (2019) Widespread population decline in South America correlates with mid-Holocene climate change. Scientific Reports 9(1):6850, DOI 10.1038/s41598-019-43086-w

Roberts JM, Mills BJ, Clark JJ, Haas WR, Huntley DL, Trowbridge MA (2012) A method for chronological apportioning of ceramic assemblages. Journal of Archaeological Science 39(5):1513–1520, DOI 10.1016/j.jas.2011.12.022

Robertson JH, Bradley R (2000) A New Paradigm: The African Early Iron Age without Bantu Migrations. History in Africa 27:287, DOI \url{10.2307/3172118}

Roddick AP, Stahl AB (eds) (2016) Knowledge in Motion: Constellations of Learning across Time and Place. Amerind Series in Anthropology, The University of Arizona Press, Tucson

Rodrigues IMM, Volkmer-Ribeiro C, Machado VdS (2017) Cauixi em cerâmica arqueológica da região de Lagoa Santa, Minas Gerais: inclusão de esponjas processadas ou exploração de depósitos sedimentares com espículas? Boletim do Museu Paraense Emílio Goeldi Ciências Humanas 12(1):85–100, DOI 10.1590/1981.81222017000100005

Roux V (2017) Ceramic Manufacture: The chaîne opératoire Approach. In: Hunt AM (ed) The Oxford Handbook of Archaeological Ceramic Analysis, pp 101–113

Roux V (2019) Ceramics and Society: A Technological Approach to Archaeological Assemblages. Springer, Cham

Rye OS (1977) Pottery manufacturing techniques: X-ray studies. Archaeometry 19(2):205–211, DOI 10.1111/j.1475-4754.1977.tb00200.x

Rye OS (1981) Pottery Technology: Principles and Reconstruction. Taraxacum, Washington and D.C

Scheffer F, Schachtschabel P (2010) Lehrbuch der Bodenkunde, 16th edn. Spektrum, Akad. Verl., Heidelberg and and Berlin

Seidensticker D (2016) Archaeology and History in Iron Age Settlements in the Congo Basin. In: Sadr K, Esterhuysen A, Sievers C (eds) African Archaeology Without Frontiers, Wits University Press, Johannesburg, pp 114–126

Seidensticker D (2020) Approaching Trans-Generational Training Networks in Central Africa: Using Ceramic Petrography to Retrace Provenance and Technology throughout Two Millennia. Ceramic Petrology Group Meeting (CPG), 9-12 November 2020

Seidensticker D (2021) Archäologische Untersuchungen zur eisenzeitlichen Besiedlungsgeschichte des nordwestlichen Kongobeckens. Tübingen University Press, Tübingen

Seidensticker D (2024) Pikunda-Munda and Batalimo-Maluba: Archaeological Investigations of the Iron Age Settlement History of the Western and Northern Congo Basin. African Archaeological Review DOI 10.1007/s10437-024-09576-7

Seidensticker D, Hubau W (2021) aDRAC (Archive des datations radiocarbones d'Afrique centrale). Zenodo, DOI 10.5281/ZENODO.4530717

Seidensticker D, Hubau W, Verschuren D, Fortes-Lima C, de Maret P, Schlebusch CM, Bostoen K (2021) Population Collapse in Congo Rainforest from AD 400 Urges Reassessment of the Bantu Expansion. Science Advances 7(7), DOI 10.1126/sciadv.abd8352

Shepard AO (1956 (reprint 1985)) Ceramics for the Archaeologist, Publication / Carnegie Institution of Washington, vol 609, repr edn. Carnegie Inst, Washington, DC

Stevenson RBK (1953) Prehistoric Pot-Building in Europe. Man 53:65, DOI 10.2307/2794346, 2794346

Stoops G (2021) Guidelines for Analysis and Description of Regolith Thin Sections, second edition edn. ASA, CSSA, and SSSA Books, Wiley-ACSESS, Hoboken, NJ

Tite MS (1999) Pottery Production, Distribution, and Consumption: The Contribution of the Physical Sciences. Journal of Archaeological Method and Theory 6(3):181–233

Tixier J (ed) (1984) Préhistoire de la pierre taillée II. Économie de débitage laminaire: technologie et expérimentation. No. 2 in Préhistoire de la pierre taillée, CREP diffusion Association pour la promotion et la diffusion des connaissances archéologiques, Antibes Valbonne

Tixier J, Inizan ML, Roche H (1980) Préhistoire de la pierre taillée I. Terminologie et technologie. Cercle de recherches et d'études préhistoriques ; Diffusion, Association pour la promotion et la diffusion des connaissances archéologiques, Antibes/Valbonne

Vandiver PB (1987) Sequential Slab Construction; A Conservative Southwest Asiatic Ceramic Tradition, ca. 7000-3000 B.C. Paléorient 13(2):9–35, DOI 10.3406/paleo.1987.4426

Villagran XS, Alves ML, Kater T, da Silva KBV, Batalla N, da Costa M, Costa J, Erler DMA, Ferreira MP, Magon P, dos Reys AC, Straioto H, Tognoli AR, Strauss A, del Lama EA, Martins L, Teixeira-Bastos M, Neves EG, Zimpel C, Pugliese F (2022) Petrografia de cerâmicas da fase Bacabal (sambaqui Monte Castelo): um dos mais antigos usos de cauixi na Amazônia. Boletim do Museu Paraense Emílio Goeldi Ciências Humanas 17(1):e20200120, DOI 10.1590/2178-2547-bgoeldi-2020-0120

Wenger E (1998) Communities of Practice: Learning, Meaning, and Identity. Learning in Doing, Cambridge University Press, Cambridge, U.K. ; New York, N.Y

Whitbread IK (1986) The characterisation of argillaceous inclusions in ceramic thin sections. Archaeometry 28(1):79–88, DOI 10.1111/j.1475-4754.1986.tb00376.x

White F (1983) The Vegetation of Africa. A Descriptive Memoir to Accompany the Unesco / AETFAT/ UNSO Vegetation Map of Africa. Zenodo

Wotzka HP (1995) Studien zur Archäologie des zentralafrikanischen Regenwaldes: Die Keramik des inneren Zaïre-Beckens und ihre Stellung im Kontext der Bantu-Expansion, Africa Praehistorica, vol 6. Heinrich-Barth-Institut, Köln