
GuitarTap

Tap Tone Analysis Report

Jul 16, 2026 at 3:56 PM

Measurement Name: Plate UMIK-1 Web Mac
Type: Material (Plate)
Frequency Range: 20.0 Hz – 200.0 Hz
Microphone: Umik-1 Gain: 18dB · calibrated (7108913)

Frequency Spectrum

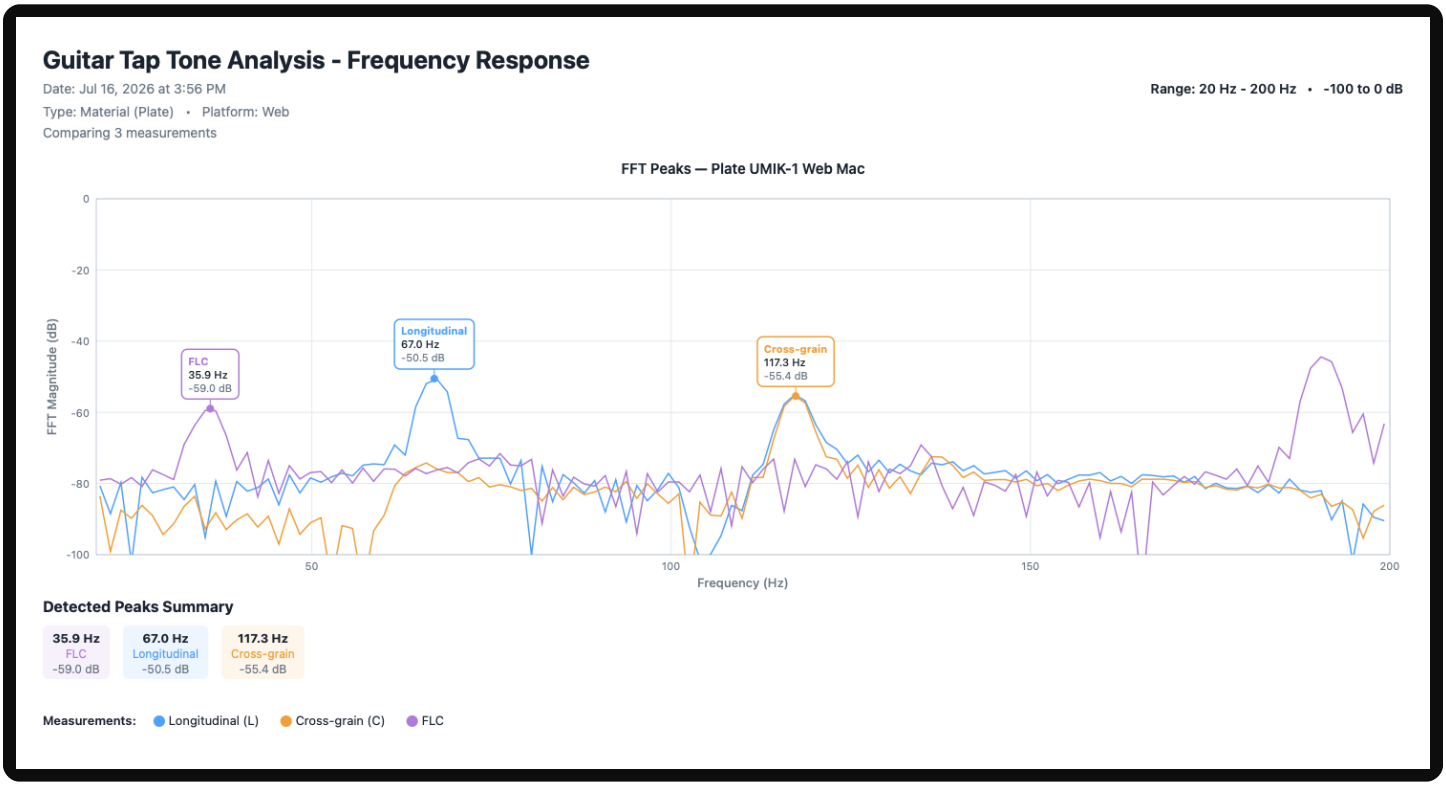

Detected Peaks

Frequency	Magnitude	Note	Q Factor	Role
35.9 Hz	-59.0 dB	D1	8.0	FLC (Diagonal)
67.0 Hz	-50.5 dB	C2	15.3	Longitudinal (L)
117.3 Hz	-55.4 dB	A#2	20.0	Cross-grain (C)

Gore Target Thickness

2.80 mm

Body: 490 × 368 mm · f_vs = 60 (Classical Top)
GLC (Shear Modulus): 0.350 GPa

Plate Properties

Sample Dimensions

Length: **557.5 mm** | Width: **220.5 mm** | Thickness: **4.85 mm**

Mass: **208.0 g** | Density: **0.349 g/cm³**

fL: **67.0 Hz** | fC: **117.3 Hz** | fLC: **35.9 Hz**

Speed of Sound (L): **4180 m/s**

Speed of Sound (C): **1144 m/s**

Young's Modulus (L): **6.09 GPa**

Young's Modulus (C): **0.46 GPa**

GLC (Shear Modulus): **0.350 GPa**

Specific Modulus (L): **17.5** (Fair)

Specific Modulus (C): **1.3** (Very Good)

Radiation Ratio (L): **12.0**

Radiation Ratio (C): **3.3**

Cross/Long Ratio: **0.075**
typical: 0.04–0.08

Long/Cross Ratio: **13.3**
typical: 12–25

Overall Quality: **Good**

Three-Tap Measurement Process:

- **1. Longitudinal (L) Tap**
  Hold plate at 22% from one end along the length, near one long edge (not at the width node). Tap center.
- **2. Cross-grain (C) Tap**
  Rotate 90°. Hold plate at 22% from one end along the width, near one short edge (not at the length node). Tap center.
- **3. FLC (Diagonal) Tap**
  Hold plate at the midpoint of one long edge. Tap near the opposite corner (~22% from both the end and the side). Measures shear stiffness.

The strongest peak from each tap is auto-selected.