

# Data-driven Prediction of Formation Mechanisms of Lithium Ethylene Monocarbonate with an Automated Reaction Network

Xiaowei Xie,<sup>†,‡</sup> Evan Walter Clark Spotte-Smith,<sup>‡,¶</sup> Hetal D. Patel,<sup>‡,¶</sup> Samuel M.  
Blau,<sup>§</sup> and Kristin A. Persson<sup>\*,¶,||</sup>

<sup>†</sup>*Department of Chemistry, University of California, Berkeley, California 94720, United States*

<sup>‡</sup>*Materials Science Division, Lawrence Berkeley National Laboratory, Berkeley, California 94720, United States*

<sup>¶</sup>*Department of Materials Science and Engineering, University of California, Berkeley, California 94720, United States*

<sup>§</sup>*Energy Technologies Area, Lawrence Berkeley National Laboratory, Berkeley, California 94720, United States*

<sup>||</sup>*Molecular Foundry, Lawrence Berkeley National Laboratory, Berkeley, California 94720, United States*

E-mail: kapersson@lbl.gov

## Abstract

Interfacial reactions are notoriously difficult to characterize and robust prediction of the chemical evolution and associated functionality of the resulting surface film is

one of the grand challenges of materials chemistry. The solid–electrolyte interphase (SEI), critical to the operation of Li-ion batteries (LIB), exemplifies such a surface film and despite decades of work, considerable controversy remains regarding the major components of the SEI as well as their formation mechanisms. In this work, we present pioneering results of a newly developed data-driven reaction network addressing the recent question whether lithium ethylene monocarbonate (LEMC) or lithium ethylene dicarbonate (LEDC) is the major organic component of the LIB SEI. Our data-driven, automated methodology is based on a systematic generation of relevant species using a general fragmentation/recombination procedure which provides the basis for our vast thermodynamic reaction landscape, calculated with density functional theory (DFT). The graph implementation of the reaction landscape is subsequently explored using shortest pathfinding algorithms, identifying reactions to LEMC from EC,  $\text{Li}^+$  and  $\text{H}_2\text{O}$  under the electron chemical potential of Li metal. Confirming the viability of our approach, the reaction network automatically recovers previously-proposed formation mechanisms of LEMC from EC and LEDC through hydrolysis, among which the direct hydrolysis of EC under basic conditions is found to be the most kinetically favorable. We also identify several other new reaction pathways to LEMC, illustrating the complex and competitive landscape of possible electrochemical electrolyte decomposition reactions. For example, we recover a LEMC formation mechanism that generates lithium hydride as a by-product and a radical mechanism through breaking the  $(\text{CH}_2)\text{O}-\text{C}(=\text{O})\text{OLi}$  bond in LEDC, neither of which has been proposed previously. Most importantly, we find that all identified paths, which are also kinetically favorable under the explored conditions, require water as a reactant. This condition severely limits the amount of LEMC that can form, as compared to LEDC, a conclusion that has direct impact on our understanding of SEI formation in Li-ion energy storage systems. Finally, we emphasize that our framework demonstrates robust, automated, data-driven predictions of novel interfacial reaction mechanisms and this framework is generally applicable to other reactive systems.

# 1 Introduction

Out-of-equilibrium interfacial reactions which result in functional, transport-selective surface films play a crucial role in materials-based technologies, enabling applications from batteries, capacitors, water splitting, protective coatings, and alloy design. An exemplar in the family of spontaneously-formed, enabling interfaces is the passivation layer which results from the reductive decomposition of electrolytes on the anode of lithium-ion batteries (LIB) during the first few charging cycles. This solid electrolyte interphase (SEI) is considered “the most important but the least understood in rechargeable Li-ion batteries”,<sup>1</sup> due to the complex relationships between battery conditions, SEI composition/morphology, and SEI properties.<sup>2–5</sup> It is generally believed that an ideal SEI should be selectively permeable to the electrochemically active charge carrier, i.e. Li<sup>+</sup>, but also electron-insulating to prevent continuous reduction of the electrolyte species.<sup>6</sup>

Over the last decades, careful bulk and surface characterization techniques, such as X-ray photoelectron spectroscopy (XPS),<sup>7,8</sup> Fourier transform infrared (FTIR) spectroscopy,<sup>9,10</sup> nuclear magnetic resonance spectroscopy (NMR),<sup>11,12</sup> cryo-scanning transmission electron microscopy (cryo-STEM),<sup>13–15</sup> etc., have been employed to elucidate the chemical composition of the SEI on both Li metal and graphite. Critical understanding has been gained as to early SEI formation as well as its aging. However, there are still numerous uncertainties as to specific reaction mechanisms, influence of the electrode chemistry and potential on competing reactions, and even the characterization of fundamental SEI components such as e.g. lithium ethylene dicarbonate (LEDC). LEDC was first proposed to be the major organic constituent of the SEI from the EC electrolyte by Aurbach et al.,<sup>9,16–19</sup> and later investigated extensively by numerous studies including synthetic efforts of the LEDC standards and comparisons with those synthetic standards based on FTIR, XPS, and NMR techniques.<sup>11,20–26</sup> Recent work by Wang et al.<sup>27</sup> cast doubt on the LEDC characterization: it was suggested that common LEDC standards<sup>21,23,25</sup> are comprised of lithium ethylene monocarbonate (LEMC). The authors further suggested that LEMC degrades to ethylene glycol (EG) under D<sub>2</sub>O ex-

traction, thus rendering the  $^1\text{H}$ NMR spectra for LEDC and EG indistinguishable. However, while characterization of LEDC is under debate, questions also remain as to how LEMC forms under typical battery operation conditions and if it truly replaces LEDC as a major early SEI component.

Computational modeling of SEI-relevant reactions has also provided crucial insights into specific reaction mechanisms, including short-lived intermediate products.<sup>28,29</sup> Prominent examples include the early pioneering work from Balbuena and coworkers based on static DFT calculations to clarify the reduction mechanisms of common organic solvents and additives,<sup>30–32</sup> surface calculations,<sup>33–35</sup> *ab initio* molecular dynamics (AIMD) simulations,<sup>36,37</sup> and others. However, currently employed methodologies such as static DFT, *ab initio* and classical molecular dynamics are inherently limited either by chemical intuition, simulation time scales and/or sampling. In particular, more complex, rare, co-operative and combined reaction pathways as well as the competition between different reaction mechanisms are difficult to capture. However, progress has been made in the automated searching for reaction pathways,<sup>38–41</sup> traversing the potential energy surface (PES) using combinations of weighted sampling, heuristic rules and graph theory.<sup>42–50</sup> Recently, a new data-driven methodology was developed to analyze complex electrochemical reactive systems with minimal chemical intuitive bias through the use of computational reaction networks.<sup>51</sup> Using this methodology, pathways from  $\text{Li}^+$  and EC to LEDC under reductive conditions corresponding to Li metal were explored. It was demonstrated that the reaction network automatically recovers previously suggested reaction mechanisms for the formation of LEDC as well as proposed novel, thermodynamically feasible mechanisms that had not previously been reported. Here, we utilize the same framework to identify possible reaction pathways leading to LEMC based on automated pathfinding in a landscape built on ab-initio thermochemistry. We compare the proposed pathways on the basis of their thermodynamics, kinetics, and byproducts. We note that thermodynamic analysis alone is inadequate for assessing the energetic landscape, as kinetics also play a pivotal role in the SEI formation.<sup>36,52</sup> In the present study, we also conduct

static transition state (TS) calculations for the promising paths from the path-finding algorithm using a total thermodynamic cost cutoff, so as to refine the reaction network predicted paths and assess their kinetic feasibility. The purpose of our work is two-fold:

- (1) We implement and demonstrate a systematic and minimally biased methodology for the generation of relevant species and reactions. Subsequently, reaction pathways to a certain product of interest can be obtained in an automated fashion through pathfinding from a reaction network containing these species and reactions. All relevant molecules were generated through a systematic fragmentation/recombination procedure such that all reactions that satisfy a certain constraint (involving  $\leq 5$  bond changes here) were included. The effectiveness of this approach is tested on the formation of the new SEI component of interest, LEMC. We demonstrate that our data-driven methodology recovers not only previously proposed mechanisms, but also discover novel, competitive reaction pathways.
- (2) We assess the reaction network-predicted pathways both in the context of experimental findings and from a comparison with DFT-refined pathways. We note that the advantage of the automatically generated pathways lies in the rapid evaluation of thermodynamically plausible reactions covering a vast electrochemical space and provides a thermochemically informed starting point for more bespoke computational and experimental explorations.

## 2 Methods

### 2.1 Generation of Candidate Molecules and Molecular Intermediates through Fragmentation and Recombination

To generate the constituents of the reaction network, we employ heuristic rules based on thermodynamic data and associated machine-learned bond dissociation and formation, which we denote as the fragmentation and recombination procedure. This approach enables the generation of a large number of candidate molecular structures that represent the out-of-equilibrium, transient landscape of possible molecular fragments that form under electro-

chemical electrolyte decomposition. These candidate structures are subsequently optimized by electronic-structure methods to obtain minimum-energy structures. Molecular species are treated as graphs based on the connectivity of atoms. Fragmentation is defined as breaking one edge in a molecular graph and generating one or two molecular fragments; recombination is defined as forming one edge between two specified atoms on two molecular graphs and forming one recombinant molecular graph. In a one-step fragmentation, fragment molecular graphs are generated from breaking any one bond in the molecule. An n-step fragmentation involves multiple sequential one-step fragmentation processes; at each stage, the fragments from the previous stage undergo a one-step fragmentation, and the fragments from each such one-step procedure are collected. Similar to the fragmentation procedure, a general one-step recombination is conducted by iterating over all the molecular pairs in a given set of species, iterating over all atoms in both molecules, and generating all recombinant molecules by connecting a bond. During the process, a graph isomorphism comparison is applied at each step to check for structural duplicates, which are then removed. To compare and contrast LEDC with LEMC formation pathways as a result of electrochemical decomposition of an open system of  $\text{Li}^+$ , EC,  $\text{H}_2\text{O}$  and electrons, we adopt the following procedure to generate the relevant species (an overview is shown in Figure 1).

(1) All possible unique fragments were generated from 2-step fragmentation of  $\text{Li}^+\text{EC}^-$  and one-step fragmentation of  $\text{H}_2\text{O}$ . An initial filtering of the resulting fragments is conducted to prevent the combinatorial explosion of the number of species. The filtering is done by first constructing a small reaction network with only the original molecules and the fragments, considering one-electron redox and one-bond change reactions, according to the previously reported procedure.<sup>51</sup> Pathfinding to each specie mentioned above enable us to identify which fragments are thermodynamically accessible in the present model conditions by overall exergonic reaction pathways (overall  $\Delta G < 0$ ). However, an exception is made for  $\text{H}_2\text{O}$  to include the fragments OH and H in all charge states, as breaking a bond in water is endergonic in molecular calculations, but will occur favorably in the presence of Li metal

(as will be discussed in Sec 2.3 and Sec 3.1).

(2) All hypothetical recombinant structures were created by connecting one bond between the generated fragment molecules. There were no other criteria imposed except to ensure chemically reasonable valences of the final recombinant products. Recombinant structures that do not satisfy the valence (e.g. a carbon with more than 4 bonds or an oxygen with more than 2 bonds) were discarded.

(3) A recent graph neural network BonDNet<sup>53</sup> was employed to predict the recombination reaction free energy and only those with negative  $\Delta G$  upon recombination were retained. We note that the mean absolute error (MAE) on the prediction of reaction free energies for recombination is 0.45 eV with a high coefficient of determination ( $R^2$ ) value of 0.84 for 449 unique recombination reactions. The higher MAE than that reported in the BondNet paper could originate from (1) examples far away from the regime of the training set, e.g. forming a bond between two tertiary carbons and (2) the larger conformational space of large flexible recombinant molecules, as currently BonDNet is not taking the energies of different conformers into consideration.

(4) The geometries of the resulting molecules were optimized in DFT. The initial guesses for the 3D geometries of the recombinant molecules were generated based only on 2D molecular connectivities from the OPLS\_2005 molecular force field<sup>54</sup> as implemented in the Schrödinger Python Suite.<sup>55</sup> To reduce the computational burden of generating the recombinant molecules, no conformational sampling was conducted. During geometry optimization, a portion of the recombinant molecules changed their connectivities; those molecules were removed from consideration as the results of BonDNet were no longer applicable and they were no longer in the regime of one-step recombination.

We obtained 570 candidate molecules in total through this procedure (45 from fragmentation and 525 from recombination). We note that the generation of the network species is self-contained, such that all fragments and recombinant molecules were generated from the procedure (1)-(4). Specifically we emphasize that no molecules were added from previous

knowledge of Li electrolyte decomposition and that the target molecules LEDC and LEMC were obtained in this automated fashion.

## 2.2 Construction of Reaction Network and Identification of Reaction Pathways

The reaction network was constructed as a connected graph using the same graph representation as described in previous work.<sup>51</sup> Allowing a broad range of reactions between the molecular species, we chose to include “concerted” reactions (reactions that involve multiple, simultaneous bonds breaking or forming) with up to 5 bond changes. Similar constraints (usually  $\leq 2$  bonds breaking and  $\leq 2$  bonds forming) were imposed in other works.<sup>42,46,48</sup> We emphasize that metal coordination reactions, such as Li bonding to a heteroatom, is treated in the same manner regardless of their ionic/dative nature, which motivates an inclusive, upper limit of allowed concerted bond changes. We note, however, the possibility that reactions considered here as concerted, may in reality proceed through multiple elementary steps. Hence, we consider reaction pathways as reasonable guesses for a collection of events that should be refined using quantum chemical calculations.

To efficiently include concerted reactions, a mixed-integer linear programming (MILP) scheme modified from a previous work for atom-mapping<sup>56</sup> was utilized to calculate the minimum chemical distance (CD), i.e. the minimum number of bond changes needed to transform reactants to products, for all possible combinations of (up to two) reactants and products (for details, see SI Sec I). All molecular pairs that satisfy a given stoichiometry were subsequently evaluated based on the minimum number of bond changes required to convert one molecule pair to another. This procedure resulted in a collection of all reactions that can be reached within 5 bond changes, totalling 570 species and 8,973,154 reactions (data included in the SI).

To calculate the free energy for redox reactions relevant in Li-ion batteries, we employed a potential of  $U = 0$  vs Li/Li<sup>+</sup>. Hence, to represent the reaction free energy for an arbitrary

redox reaction, we employ the full-cell reaction  $A + Li(s) \rightarrow A^- + Li^+$ . The absolute electrode potential for the lithium electrode is calculated to be  $\sim 1.40$  V by adding the  $Li/Li^+$  potential relative to standard hydrogen electrode (SHE) to the absolute electrode potential of hydrogen electrode (4.44 V).<sup>57-60</sup> We note that this is equivalent to a chemical potential of -1.40 eV for a Li metal electron. The effect of the electrode potential (or any applied external potential) can be easily accounted for, by shifting the free energy of the electron by  $-eU$ , where U is the potential relative to  $Li/Li^+$ . For instance, the graphite anode in LIBs operates at a potential close to  $U = 0.2$  V vs  $Li/Li^+$  which is equivalent to an electron chemical potential of -1.60 eV.

To identify promising thermodynamic pathways from the nearly 9 million hypothetical reactions, we adopted the same procedure for pathfinding as described in the previous work.<sup>51</sup> This approach provides us with a ranked list of reaction sequences and each reaction sequence connects the starting molecules to the target molecule (LEMC), within a grand canonical thermodynamic ensemble, allowing for a variable number of each specie. A softplus function, i.e.  $\ln(1 + \exp(x))$ , of reaction free energy is used to determine the cost for traversing a reaction in the reaction network based on computational efficiency and the tolerance for slightly endergonic reactions. However, we note that the resulting ranking from the cost function is not used to exclude pathways from consideration. Indeed, after obtaining the representative reaction pathways from the reaction network, we subsequently subject the proposed pathways to a detailed quantum mechanical study to obtain the transition state barriers ( $\Delta G^\ddagger$ ) as well as the reaction energies of the complexes ( $\Delta G$ ) to verify their kinetic/thermodynamic feasibility. This information is intended to refine the pathways obtained from the reaction network which currently does not include any explicit kinetic information. Furthermore, concerted mechanisms are refined in this more thorough exploration.

## 2.3 Computational Methods

DFT calculations were performed using the QChem<sup>61</sup> electronic structure code. The geometry optimizations for the species included in the reaction network used the  $\omega$ B97X-V<sup>62</sup> functional with the def2-TZVPPD basis set.<sup>63,64</sup> Solvent effects were taken into account by SMD implicit solvation models,<sup>65</sup> with user-defined parameters representing the Li-ion electrolyte. Specifically, an experimentally measured dielectric constant (for 3:7 EC/EMC binary mixtures<sup>66</sup>) of 18.5 was used; for all other parameters we used the values for pure EC.<sup>67</sup> For all stationary point geometries, frequency calculations were conducted to ensure they are true local minima on the PES for minimum structures or first-order saddle points for TS structures. Gibbs free energies based on harmonic approximations were used throughout to determine the energy landscape in the reaction pathways.

Geometry optimization and reaction path analysis for the predominant paths were performed at the  $\omega$ B97X-D<sup>68</sup>/def2-SVPD<sup>64</sup> level of theory with the C-PCM implicit solvation model<sup>69</sup> (dielectric constant 18.5, optical dielectric 2.0, which is consistent with the SMD parameters), while single point energies at the stationary points were obtained using the  $\omega$ B97X-V/def2-TZVPPD/SMD level of theory using the same SMD parameters as above. These two levels of theory have been shown to perform well for metal organic systems.<sup>70,71</sup> We used the lower level of theory for computational efficiency in exploring the PES; in our experience, these two levels of theories give good agreements in both molecular geometries and relative energies. Vibrational frequencies were computed using the smaller basis, yielding zero-point energies and thermal corrections. A procedure based on fixed-length steps in the steepest descent direction was performed to verify the TSs connect to the expected reactant(s) and product(s) through a smooth energy-descent path.

Evaluating possible reaction paths to LEMC with and without water is a critical component of this study, however we note that a single water molecule does not spontaneously reduce in the presence of a single Li atom; it requires the presence of a metallic Li surface. Hence, the network, being ignorant of extended surface effects, will extend an endothermic

(potentially artificial) cost to any water splitting reactions. As a consistency check, we verified that our level of theory does reproduce spontaneous water splitting reaction on a Li metal surface from a cluster-based DFT model (see SI Sec III for computational details).

### 3 Results and Discussion

Herein we present and analyze the formation pathways to a recently identified, potential key component of the Li-ion SEI, LEMC.<sup>27</sup> Analyzing the top-ranked 30,000 pathways, first of all, we found that many of them were in fact the same, except for a difference in the order of reactions. These “duplicate” paths exhibit the same cost, and eliminating the paths with identical costs to threshold  $10^{-3}$  resulted in 434 unique paths (the unique paths are included in the SI). We further grouped the paths roughly based on the main molecules involved in the paths and report the representative paths below. While this elimination may exclude subtle mechanistic differences in the paths, we believe that the main features are preserved.

Analyzing the participant molecules in the reaction pathways leading to LEMC formation, interestingly, we found that only 8 paths (among the 434 unique ones) proceeded without water. Furthermore, DFT refinement of these paths suggests none of these pathways are kinetically feasible, with the rate-limiting barriers for the key reactions in the paths exceeding 2 eV (details shown in SI Sec V). This important result indicates that water is likely to be critically important in the formation of LEMC. We note that the presence of kinetically infeasible paths is inevitable: this is a direct consequence of including a broader scope of reaction possibilities. Indeed, the identified infeasible mechanisms were found to include over-complicated concerted mechanisms connecting unstable radical and species, e.g. carbene. Since this artifact may result in missing important non-water mechanisms, we constructed another reaction network with more limited concerted reactions, and the details will be given in Sec 3.3 below. An overview of the two reaction networks considered in this work is given in Figure 2.

The two major pathways that have been proposed in the literature, namely the EC hydrolysis and LEDC hydrolysis reactions, were successfully identified by the reaction network, validating our data-driven approach. Additionally, other possibly interesting pathways were discovered and will be discussed below, such as a pathway that generates lithium hydride, pathways involving new, recombinant compounds that have not been conventionally considered to be important in the SEI formation, and a pathway involving the breakage of the  $(\text{CH}_2)\text{O}-\text{C}(=\text{O})\text{OLi}$  bond in LEDC.

In the following sections, we divide the reaction pathways to LEMC into three categories: (i) direct paths from EC,  $\text{Li}^+$  and  $\text{H}_2\text{O}$ , where only the fragments of LiEC serve as intermediates in the paths, (ii) paths involving recombinant molecules, and (iii) paths without water participation. We present, for each category, both the representative paths predicted from the reaction network and the DFT validated/refined free energy diagrams, with some discussion about the similarities/differences between them. We also discuss the physical implications of those paths in the context of experimental findings.

### 3.1 Direct reaction paths to LEMC from EC, $\text{Li}^+$ and $\text{H}_2\text{O}$

Figure 3 shows a representative set of “direct” paths leading to the formation of LEMC, utilizing EC,  $\text{Li}^+$  and  $\text{H}_2\text{O}$  as the starting molecules. Although differing in the detailed steps, the two major mechanisms identified were (i)  $\text{LiOH}$  or  $\text{OH}^-$  attacking an EC or  $\text{LiEC}^+$  to form LEMC (path A, B, C, E) and (ii) LiEC, water and a second electron react to form LEMC and hydride (path D). Figure 3 presents the energy profiles from DFT (ignoring explicit solvation and surface effects) corresponding to these two mechanisms. We note that the generation of  $\text{LiOH}$  and or  $\text{OH}^-$  species can be corroborated by the known instability of water against Li metal,<sup>72</sup> which is also captured within our level of theory, when an explicit surface is included (see SI Sec III). Since the reaction network does not have any knowledge of water splitting on the Li surface, it used indirect mechanisms for generating  $\text{LiOH}$  and or  $\text{OH}^-$ .

The reaction of LiOH attacking EC to form LEMC was proposed by Wang et al. and also experimentally confirmed by adding anhydrous LiOH to an EC/LiPF<sub>6</sub> solution.<sup>27</sup> In the EC + LiOH → LEMC reaction, we identified two mechanisms through DFT (purple and black paths in Figure 4 (a)): one is a single-step process where LiOH directly attacks the ethylene carbon in the EC; another one is a step-wise process where LiOH attacks the carbonyl carbon to form a tetrahedral intermediate, and a subsequent shoulder bond breaking and proton transfer creates LEMC. The former one-step process has a high barrier of 2.24 eV (Struct 3 → TS 5), whereas the step-wise mechanism exhibits an effective overall barrier of 1.33 eV (Struct 3 → TS 4). The reaction barrier can be significantly lowered if the hydroxide ion is free and not bound to lithium (0.25 eV, Struct 7 → TS 6). This is consistent with the fact that Li<sup>+</sup> is a strong Lewis acid, and the nucleophilicity of bare hydroxide anions is expected to be greatly reduced in the presence of Li<sup>+</sup>.<sup>73,74</sup> Similarly, the electrophilicity of EC would be enhanced by Li<sup>+</sup>, thus also increasing the reactivity between the two species. We consider OH<sup>-</sup> + LiEC<sup>+</sup> → LEMC a more realistic scenario for EC hydrolysis, as (i) LiOH has extremely low solubility in organic solvents, (ii) OH<sup>-</sup> should be expected to be present because the electron-abundant anode represents a highly basic environment,<sup>75</sup> and (iii) LiEC<sup>+</sup> is considered to be abundant in battery electrolytes and the Li<sup>+</sup>-coordinated EC is reduced at a higher potential than the pure solvent.<sup>30</sup>

Path D in Figure 3 as proposed from the reaction network represents another possibility of LEMC formation. In path D, a neutral LiEC is further reduced to LiEC<sup>-</sup> and reacts with water to form LEMC and a hydride ion. (c-EC<sup>2-</sup>)Li<sup>+</sup>, where c-EC<sup>2-</sup> represents the cyclic EC dianion, was proposed previously by Leung et al.,<sup>36</sup> and the reduction rate of c-EC<sup>-</sup> was estimated based on Marcus theory to be significantly higher (at ∼ 10<sup>4</sup> order) than that of EC, but lower than that of o-EC<sup>-</sup>, which is the ring-opened EC anion. Leung et al. also suggested that the doubly reduced (c-EC<sup>2-</sup>)Li<sup>+</sup> favorably ring opens at the shoulder bond and release CO. Regardless of the existence of c-EC<sup>2-</sup> (or its life time), the reaction network suggests a reaction path according to EC + Li<sup>+</sup> + 2e<sup>-</sup> + H<sub>2</sub>O → LEMC

$+ \text{H}^-$ . This poses a possibility of a simultaneous (presumably asynchronous) formation of hydride and LEMC. We anticipate that the hydride will react rapidly with any available  $\text{Li}^+$  ion to form  $\text{LiH}$ , which is likely to - in the presence of water - further react to  $\text{LiOH}$  on its surface. Experimentally,  $\text{LiH}$  was first characterized by IR spectroscopy on Li metal with wet electrolyte solutions,<sup>76</sup> and later observed as a main dendritic product in the Li-anode-SEI by cryo-STEM mapping<sup>15</sup> and XRD experiments.<sup>77</sup>

Examining this hypothetical path more carefully, we obtain a mechanism that resembles the black path in Figure 4 (a). Note that the overall charge state for the structures in the energy profile in Figure 4 (a) is neutral, whereas in Figure 4 (b), the overall charge is -1. We were unable to identify a path that proceeds through  $(\text{c-EC}^{2-})\text{Li}^+$ , presumably because water is more readily reduced than  $\text{c-EC}^-$  (the hydrogen evolution potential occurs at 2.21 V relative to  $\text{Li}/\text{Li}^+$ ,<sup>78</sup> whereas the reduction potential of  $\text{c-EC}^-$  is calculated to be 1.16 V relative to  $\text{Li}/\text{Li}^+$ .<sup>36</sup>). Since the reaction network assigns a potentially overestimated endothermic penalty (depending on the distance to the fresh Li metal surface) to water reduction (see Sec 2.3), it proposes reduction of  $\text{LiEC}$  rather than  $\text{H}_2\text{O}$ . In the DFT refinement, we see a favorable water splitting in the anion state and identify a path corresponding to  $\text{H-Li-OH}^- + \text{EC} \rightarrow \text{LEMC} + \text{H}^-$  (Figure 4 (b)). We include a water splitting step with  $\text{LiEC}^-$  at the beginning only for the sake of completing the energy diagram, however the  $\text{LiEC}^-$  in Struct 1 is  $\text{Li}^-\text{EC}$  in character, as revealed by Mulliken analysis,<sup>79</sup> and the Li in the structure is considered a Li surface proxy, coordinating to EC. A similar argument can be made for the water splitting step in Figure 4 (a), where the Li is neutral in character (Struct 1). As mentioned in Sec. 2.3, metallic surface effects are neglected in the reaction network, and to confirm that water splitting is indeed spontaneous within our level of theory, we used a cluster DFT model consisting of 32 Li atoms and found that the reaction is almost barrierless (see SI Sec III) and consistent with previous work (0.12 eV).<sup>80</sup> We note that although water reduction reactions are usually considered to be equivalent to hydrogen evolution reaction (HER), this is a simplified picture as the detailed mechanisms involve

adsorbed species  $H_{ads}$  and  $OH_{ads}$ .<sup>80,81</sup> Hence, the as-formed hydride ion, most likely created through water splitting on the Li surface, is presumably stabilizing the TS structures along the path and the overall barrier (0.72 eV as the rate-limiting barrier, Struct 4 → TS 3) is much lower than that for the black path in Figure 4 (a). Further investigation is necessary to determine the plausibility of this path and whether cooperative effects could further lower the barrier in this pathway.

Generally comparing our results with previous investigations of water reactivity with Li metal surface, our results are consistent with Shang et al.<sup>80</sup> who found the final products of  $H_2O$  reacting with a Li surface to include  $LiOH$ , a small amount of  $LiH$ ,  $H_2$  gas, and various water complexes.

### 3.2 Reaction paths to LEMC from EC, $Li^+$ and $H_2O$ involving recombinant molecules

By including recombinant molecules into the reaction network, we were able to identify some pathways to LEMC involving new intermediate molecules en route to the formation of LEMC, as shown in Figure 5. Note that the inclusion of LEMC and LEDC, along with other recombinants is a direct consequence of graph enumeration. In other words, those molecules are naturally considered irrespective of any prior knowledge of the SEI components previously studied in the literature.

The hydrolysis reaction of LEDC (path A in Figure 5) was both proposed by Wang et al.<sup>27</sup> and Rinkel et al.<sup>75</sup> This pathway was successfully identified by our reaction network, albeit with a low ranking (ranking 352 among the 434 unique paths), presumably owing to the endergonicity of the last  $LEDC + H_2O \rightarrow LEMC + LiHCO_3$  reaction step (0.07 eV). We also note that the LEDC and LEMC conformers used in the reaction network are linear configurations, due to inadequate sampling of the conformational space. Applying a conformational search under implicit solvation identified a puckered LEDC structure (see Figure 6 (a)), which is lower in energy than the linear conformer by 0.6 eV. While this

puckered conformer obtained here may or may not be representative under explicit solvation (to our knowledge, there is no known crystal structure for LEDC<sup>23,27,82</sup>), the significant energy difference highlights the impact of LEDC conformation to the reaction energetics.

Examining more closely path A and its kinetics, we found that the single-step LEDC hydrolysis step exhibits a high barrier (3.05 eV, Figure S2, Struct 1 → TS 1). However, hydrolysis reactions do not usually proceed in a single step,<sup>83–85</sup> and therefore we attempt to obtain the barrier for a step-wise hydrolysis of LEDC passing through a tetrahedral intermediate, either with neutral water or OH<sup>-</sup>. The rate-limiting barrier of the water version of this path is 1.48 eV (Figure 6 (a), Struct 1 → Struct 4), which is lowered significantly compared to the single-step path. Under basic conditions (starting from OH<sup>-</sup>), the barrier was calculated to be 1.76 eV from the entrance complex (Struct 1 → TS 1), 0.62 eV from the starting materials (LEDC + OH<sup>-</sup> → TS 1) for the black path and 1.09 eV (LEDC + OH<sup>-</sup> → TS 4) for the green path (Figure 6 (b)).

In polymolecular reactions, such as the hydrolysis of LEDC, there is a possibility that the entrance complex before entering the transition state region is lower in energy than the sum of the starting materials, in which case the rate-limiting step may be determined by the energy difference between the TS and the entrance complex. Hence, whenever there is a non-negligible discrepancy between using the sum of the free energies of the individual reactants and the free energy of the entrance complex as the baseline for the barrier height, we included the results for both scenarios.

We observe that the LEDC hydrolysis reactions are less kinetically favorable compared to the EC hydrolysis pathway and the hydride pathway based on our calculations; however, LEDC hydrolysis was found to occur both in DMSO-d<sub>6</sub> solutions (with pure LEDC plus 1.5 equiv. of water) and in the solid state on a time scale of minutes, as evidenced by <sup>1</sup>HNMR and FTIR.<sup>27</sup> Explicit solvation effects, especially in the case of water, are known to significantly impact kinetics<sup>40,86,87</sup> and further investigation is needed to elucidate the fast kinetics of this reaction. Indeed, if the surrounding water plays a pivotal, catalytic role in the

hydrolysis of LEDC to LEMC, it may be less favorable in the battery environments, where water is assumed to be at impurity concentrations. The presence of the DMSO solvent could also be of relevance (pure LEDC can only be synthesized as  $\text{LEDC} \cdot 2 \text{DMSO}$ <sup>27</sup>) as LEDC is highly soluble in DMSO and solvation effects are known to impact reaction thermodynamics as well as kinetics.

Besides the LEDC mediated pathways, two additional representative recombinant molecules were identified in the formation of LEMC: LODEC (lithium 2-(2-oxido-1,3-dioxolan-2-yl)ethyl carbonate) in path B and LODC (lithium 2-oxido-1,3-dioxolan-2-yl carbonate) in path C in Figure 5. These molecules have not been proposed, to our knowledge, in the SEI literature, although LODEC was observed in an AIMD simulation of EC based electrolytes.<sup>88</sup> The reaction network suggest both recombinants to undergo hydrolysis and form LEMC. Examining the mechanistics of both reactions (Figure S3), we are unable to find a single-step hydrolysis reaction for both recombinants. Allowing for multistep reactions, in path B, LODEC and water transform to EC, LEC and LiOH crossing a 1.62 eV barrier and we surmise that EC and LiOH subsequently react according to the path in Figure 4 (a) to create LEMC. For path C, LODC initially decomposes to EC and  $\text{Li}_2\text{CO}_3$  (which may exist as  $\text{LiEC}^+ \text{-} \text{LiCO}_3^-$ ) and  $\text{LiCO}_3^-$  may facilitate water splitting and lead to the formation of a tetrahedral intermediate (Struct 4 in Figure S3 (b)) with the subsequent formation of LEMC. However, this is equivalent to the  $\text{EC} + \text{LiOH} \rightarrow \text{LEMC}$  path (Figure 4 (a)), black path).

### 3.3 Reaction paths to LEMC without water

There are 8 reaction-network-identified paths starting from EC,  $\text{Li}^+$  that do not involve water (see SI Sec V for the paths). However, these paths exhibit highly complex concerted reactions (involving 4 or 5 bond changes) connecting unstable open-shell species, with likely short lifetimes; those reactions were then verified to exhibit high barriers by DFT (see SI Sec V). We note that reactions involving up to 5 bond changes were included in the reaction network to accommodate hydrolysis reaction mechanisms. Hence, to explore non-

water containing reactions, another reaction network was constructed, limiting the concerted reactions to  $\leq 2$  bond changes and this reaction network consisted of 418,640 reactions. This procedure reveals some potentially feasible paths to LEMC starting with EC,  $\text{Li}^+$  only (two representative paths are shown in Figure 7) and are discussed below. We note that these two paths are the two shortest paths from the 2-bond-change reaction network. The range of costs for the paths in this smaller network is 2.39-3.12, which is significantly higher than that for the previous 5-bond-change reaction network (0.88-1.57), thus we considered it unnecessary to analyze the paths beyond the several top-ranking ones.

Path A in Figure 7 proceeds through an H-abstraction from LiEC, resulting in lithium vinyl carbonate (LVC) and a subsequent reaction between the H radical and LEDC creating LEMC and  $\text{LiCO}_2$  (neutral). This pathway is supported by previous findings by Shkrob et al.<sup>89,90</sup> where VC was observed by NMR as a major product when EC undergoes electron radiolysis, and the formation mechanism was suggested to be an H-abstraction of EC by a secondary radical (e.g. ring-opened LiEC) creating  $\text{EC}(-\text{H})\cdot$  (which is a H loss radical from EC), followed by a rapid radical disproportionation reaction. The existence of  $\text{EC}(-\text{H})\cdot$  was confirmed by electron paramagnetic resonance (EPR) spectroscopy. Although radiolytic ionization creates both oxidation and reduction products, a detailed analysis of the relative yield between for the analogous radical and anion of propylene carbonate,  $\text{PC}(-\text{H})\cdot$  and  $\text{PC}\cdot^-$  and laser photoionization experiments (excluding the possibility of oxidation) enabled the authors in that work to conclude that  $\text{PC}(-\text{H})\cdot$  radicals can indeed form through reduction chemistry. Thus a similar scenario should be expected for  $\text{EC}(-\text{H})\cdot$  radicals. We note that, while the reaction network nicely captures the essence of this reaction series, it oversimplifies the first step to be  $\text{LiEC} \rightarrow \text{LVC} + \text{H}\cdot$ , as the process (according to ref. 89) is presumably  $\text{LiEC} \rightarrow \text{o-LiEC}$ , then  $\text{o-LiEC} + \text{EC} \rightarrow \text{LEC} + \text{EC}(-\text{H})\cdot$  and finally  $\text{EC}(-\text{H})\cdot + \text{Li}^+ \rightarrow \text{LVC}$ . The reaction barrier for the second step ( $\text{LED}\text{C} + \text{H}\cdot \rightarrow \text{LEMC} + \text{Li} + \text{CO}_2$ ), is tentatively calculated to be 1.26 eV (Figure 8). However,  $\text{H}\cdot$  is not necessarily involved; we expect  $\text{H}\cdot$  to be unstable and will react rapidly with its neighboring

environment. The favorable thermodynamics of this path suggests that other radical species and/or the Li surface could facilitate a similar bond breakage (a homolytic cleavage of the  $(\text{CH}_2)\text{O}-\text{C}(=\text{O})\text{OLi}$  bond) in LEDC, resulting in a  $(\text{CH}_2)\text{O}\cdot$  moiety which would immediately abstract another  $\text{H}\cdot$  (from for example EC) to form LEMC. Soto et al. reported LEDC decomposition in AIMD simulations, including  $\text{CO}_2^{2-}$  and  $\text{CO}_3^{2-}$  detachment from LEDC, in the absence or presence of radicals in the solution.<sup>91</sup> In fact, the C-O bond breakage of LEDC on the Li (100) surface, creating  $\text{CO}_2^-$  bound to the surface, was calculated from DFT (PBE functional) as  $\Delta E \ddagger = 0.22$  eV and  $\Delta E = -1.94$  eV.<sup>60</sup> The resulting fragment may be further decomposed by breaking the  $-\text{CH}_2-\text{O}$  bond, however with a high associated barrier (1.8 eV). Hence it is reasonable to assume the possibility of  $\text{LiOC(O)OCH}_2\text{OLi}$  undergoing H-abstraction reactions to create LEMC, although further investigations are recommended regarding the  $\text{H}\cdot$  or  $\text{H}^+$  source and the associated reaction barriers.

For path B in Figure 7, we were unable to locate the TS for the last step ( $\text{LiHCO}_3^- + \text{o-LiEC} \rightarrow \text{LEMC} + \text{LiCO}_2^-$ ) with DFT. An overall neutral TS was identified, corresponding to  $\text{LiHCO}_3 + \text{o-LiEC} \rightarrow \text{LEMC} + \text{LiCO}_2$  (Figure S4), however the step exhibits a high barrier of 2.75 eV and hence, under the current modeling conditions, presumably not kinetically feasible.

Finally, we comment on what the presented work means in the likelihood of LEMC being present in the early stage Li metal or graphite SEI, instead of LEDC. All identified, feasible paths to LEMC (the EC hydrolysis path, the hydride path, the LEDC hydrolysis path, the path involving  $(\text{CH}_2)\text{O}-\text{C}(=\text{O})\text{OLi}$  bond breakage in LEDC) either required water and/or LEDC. Indeed, the currently proposed reaction mechanisms for forming LEMC in the literature all require water participation.<sup>27,75</sup> Hence, assuming trace water impurities in commercial electrolytes ( $\sim 10$  ppm of water in rigorously dried electrolyte) would not produce detectable amount of LEMC. However, it is possible that some water may originate from the cross-talk between the positive and negative electrodes, e.g. from the oxidation of EC at the cathode to produce water and  $\text{CO}_2$ .<sup>75,92,93</sup> Our only non-water containing path is

effectively a conversion of LEDC into LEMC, and as such requires LEDC to form first.

## 4 Conclusion

In this work, we developed a graph reaction network based on a database of systematically generated DFT-calculated molecular fragments and recombinants, specifically to explore reaction mechanisms for the formation of LEMC, relevant for the interface formation in lithium-ion batteries. The network allows for reactivity under a grand canonical formalism, treating all species as open. Our constructed reaction network is very dense, consisting of over 570 species and  $\sim 9$  M reactions; this rich data allows us to embrace an unprecedented number of electrochemical reaction possibilities and predict reaction mechanisms without explicit knowledge of intermediates. A cost function based on the Gibbs free energy of the pathways was employed to rank the pathways, which were also manually inspected. Predominant pathways were further evaluated for mechanistic and kinetic feasibility using DFT. All relevant molecules, including our target molecule LEMC, were generated from fragmentation/recombination of the starting materials (EC,  $\text{Li}^+$  and  $\text{H}_2\text{O}$ ) without any bias towards known SEI components. We note that our methodology can in principle be applied to any electrochemical, reactive system, although caution should be applied to avoid the rapid growth of combinatorial complexity. To prune the combinatorial complexity of possible recombinant molecules, machine learning was employed to predict reaction free energies to determine the feasibility of recombinant molecules. However, we emphasize that, in the present work, no other limitations, e.g. a-priori identification of reactive sites, are imposed except for the elimination of recombinants with irregular valence.

Exploring the formation of LEMC with any amount of EC,  $\text{H}_2\text{O}$ ,  $\text{Li}^+$ , and electrons at the Li metal chemical potential, we successfully recovered - automatically - the two major literature-proposed mechanisms, namely EC and LEDC hydrolysis. Based on detailed DFT calculations of the reaction barriers, the direct EC hydrolysis mechanism was identified as

the most kinetically feasible under the current model conditions, with the further suggestion of being significantly accelerated under basic conditions. In addition to these known paths, we also identify a hydride-generating mechanism and a radical mechanism through the  $(\text{CH}_2)\text{O}-\text{C}(=\text{O})\text{OLi}$  bond breakage in LEDC, although those two mechanisms are more likely to be relevant on/near the Li metal surface.

Importantly, we find that nearly all feasible routes to LEMC, identified by the reaction network, require the participation of water, which is consistent with previously proposed mechanisms.<sup>27,75</sup> Since the formation of LEDC does not require water, our results suggest that decreasing or increasing the water concentration at the anode offer control of the SEI LEMC/LEDC ratio. Indeed, trace water impurities in rigorously dried electrolytes ( $\sim 10$  ppm) should not be able to produce detectable amounts of LEMC. However, recent works,<sup>75,92</sup> show that water can originate from EC oxidiation at the cathode to produce water and  $\text{CO}_2$ .

We note that our predicted pathways to LEMC formation assume model conditions, such as the absence of an explicit surface as well as explicit solvation effects; both of which can contribute significantly to the mechanistics of the reactions. Despite these caveats, this work represents the first exploration of reaction pathways to LEMC based on a general, graph network of first-principles thermodynamics. The predicted pathways reproduce both existing, literature-suggested pathways as well as novel ones. Such predictions are critical for understanding the early-stage formation of the SEI and may be leveraged to develop next-generation electrolytes/additives for Li-ion batteries. Our work illustrates that our methodology can be used for discovering novel reaction mechanisms and demonstrate the potential of the chemically-consistent reaction network formalism for automated probing of complex, out-of-equilibrium electrochemical reaction mechanisms.

## Acknowledgement

This work was supported as part of the Joint Center for Energy Storage Research (JCESR), an Energy Innovation Hub funded by the U.S. Department of Energy, Office of Science, Basic Energy Sciences, under Contract No. DE-AC02-06CH11357. Calculations were performed at National Energy Research Scientific Computing Center (NERSC), Lawrencium computational cluster at Lawrence Berkeley National Laboratory (LBNL), the Eagle HPC system at the National Renewable Energy Laboratory (NREL), as well as the UC Berkeley Molecular Graphics and Computation Facility (MGCF) supported by grant NIH S10OD023532. X.X. thanks Dr. David W. Small for assistance with DFT calculations.

## Supporting Information Available

The following files are available free of charge.

- SI.pdf: Details on the MILP algorithm; details on the LEMC paths from the reaction network; details on the water splitting reaction on the Li surface; supplementary free energy diagrams; details on kinetically infeasible LEMC paths without water participation
- geometries.zip: xyz files for all the stationary point structures
- LEMC\_species\_and\_paths.zip: Information on molecules used to construct the reaction network and all unique LEMC paths from the reaction network (more description given in SI.pdf Sec II)
- pathway\_report\_5\_bond\_network.pdf: Visualization of the unique LEMC paths from the 5-bond-change reaction network
- pathway\_report\_2\_bond\_network.pdf: Visualization of the unique LEMC paths from the 2-bond-change reaction network

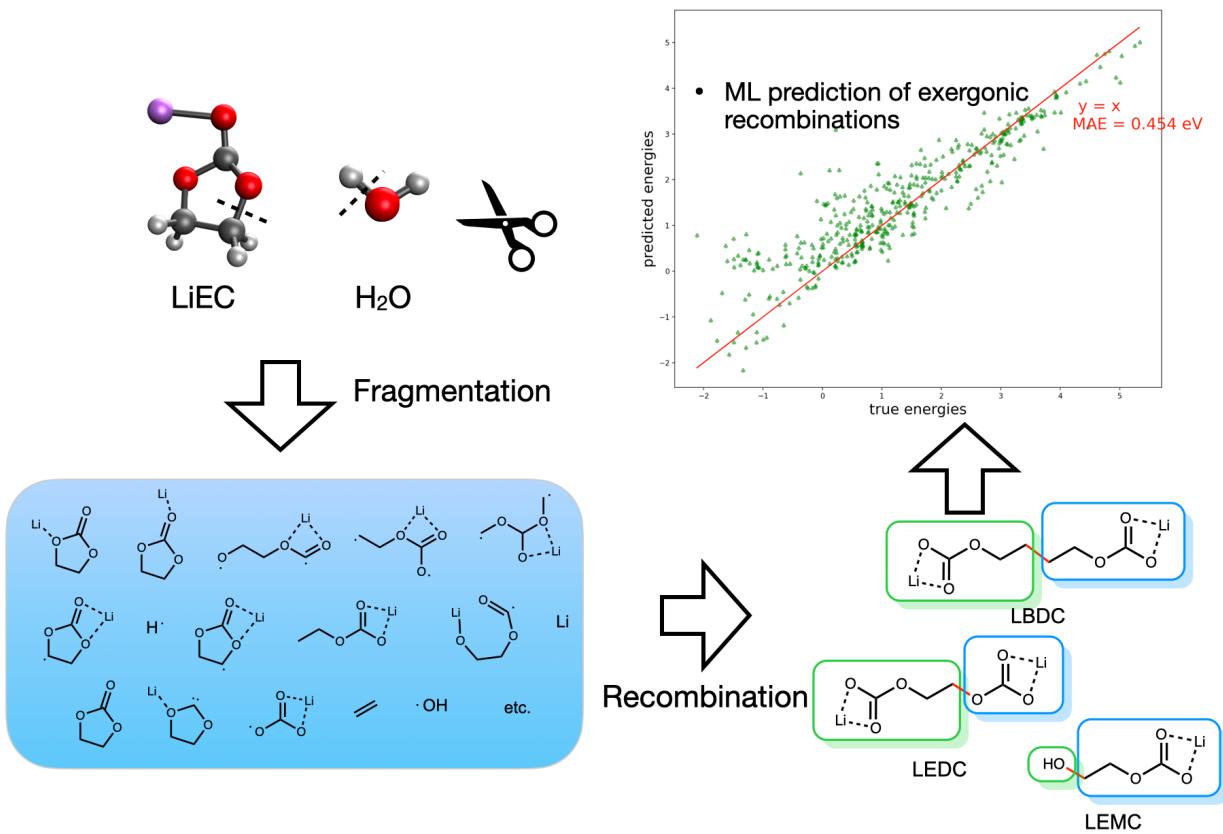


Figure 1: Workflow for generating relevant molecules

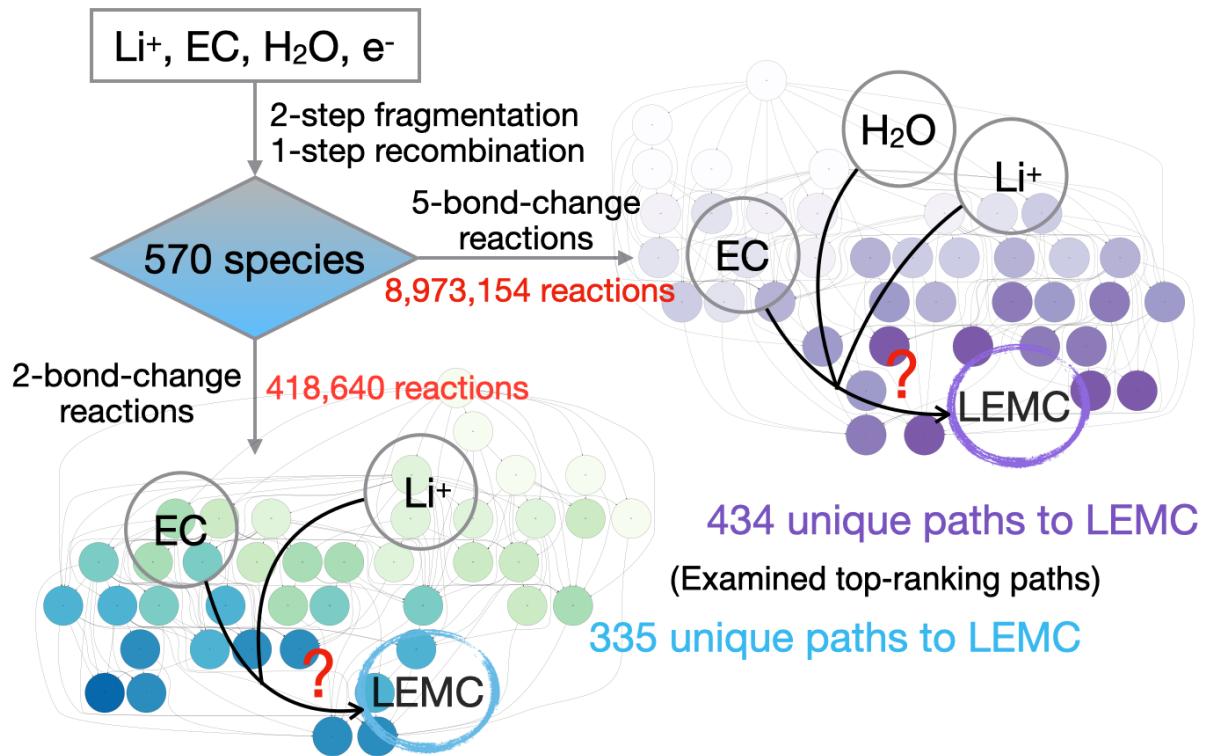


Figure 2: Overview of the reaction networks generated in this work



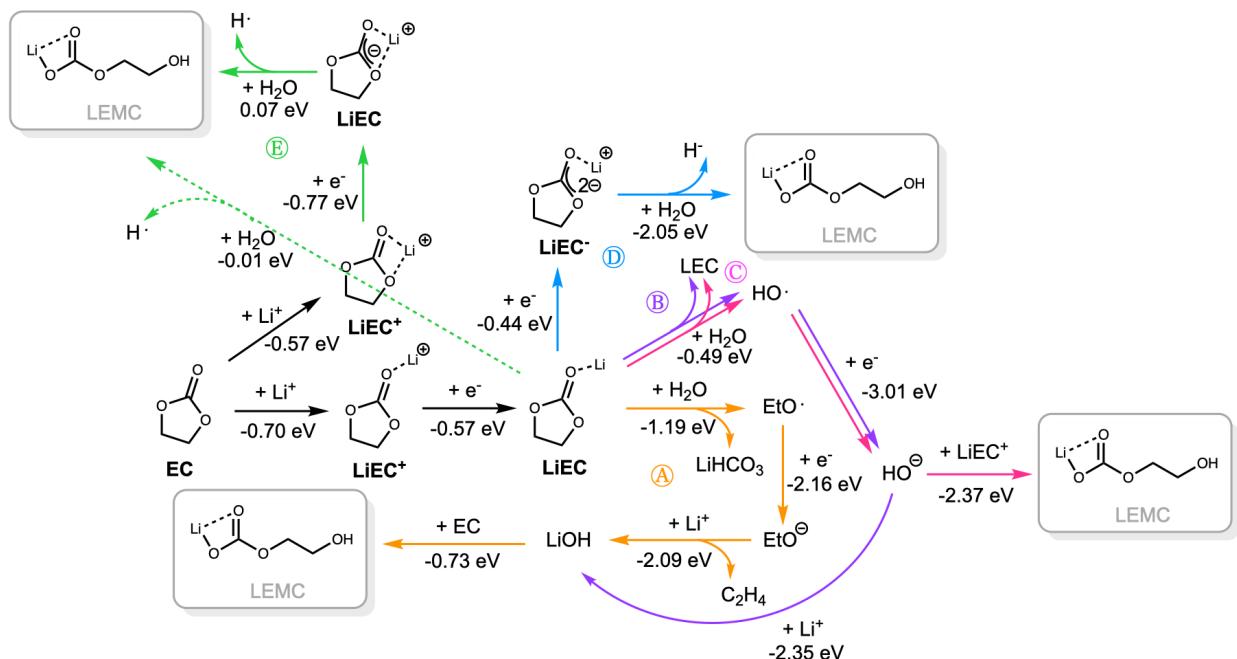


Figure 3: Direct paths to LEMC from EC, Li<sup>+</sup> and H<sub>2</sub>O identified by the reaction network

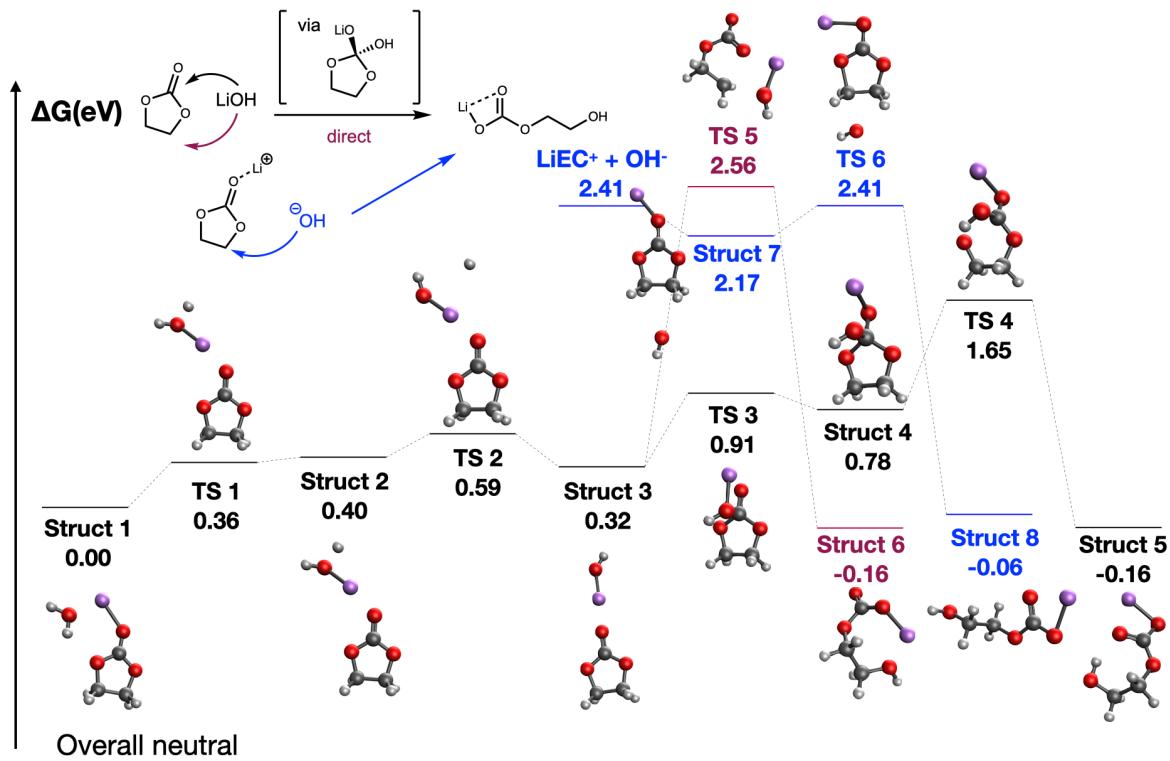

(a) EC hydrolysis paths, corresponding to path A, B, C, E in Figure 3. Note that the free energy of a hydrogen radical was added for the structures to the right of TS 2, such that the energies are comparable.

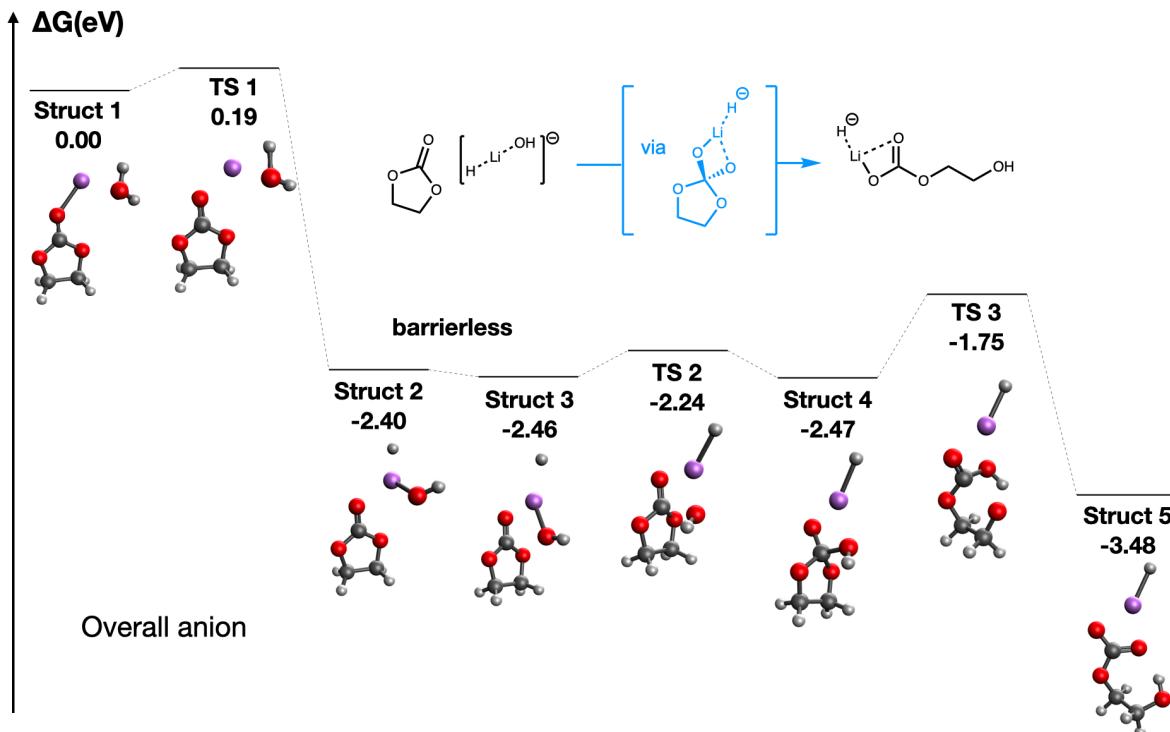

(b) Hydride generating path, corresponding to path D in Figure 3

Figure 4: LEMC<sub>25</sub> paths from DFT



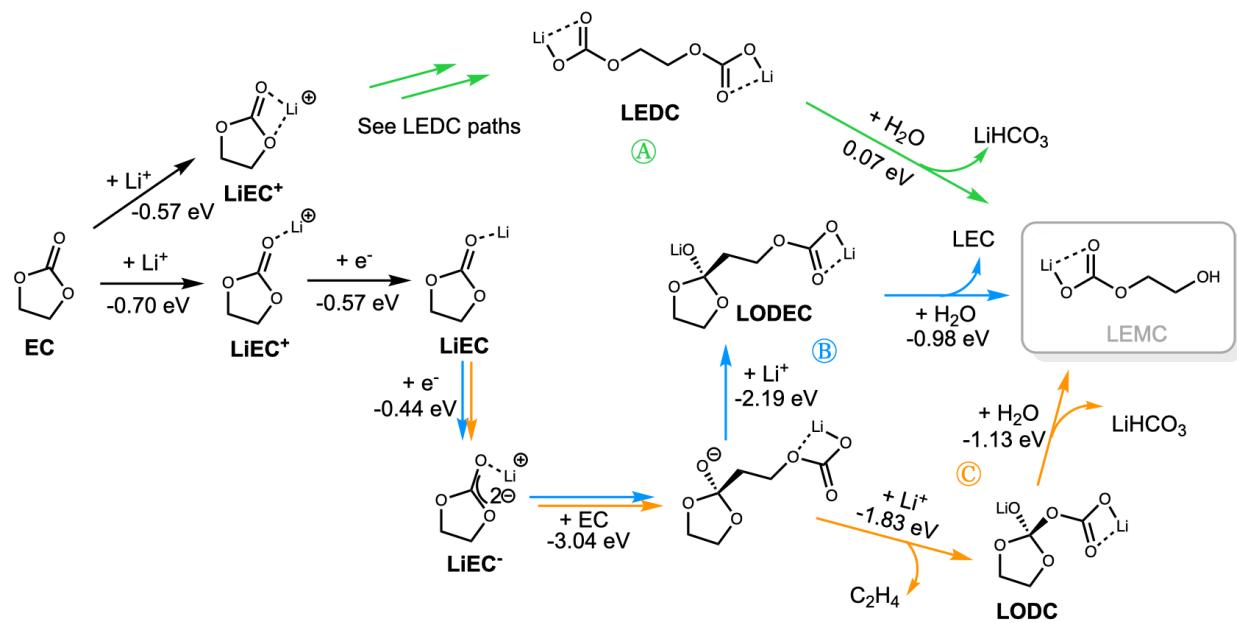


Figure 5: Paths to LEMC involving recombinant molecules from EC,  $\text{Li}^+$  and  $\text{H}_2\text{O}$  identified by the reaction network

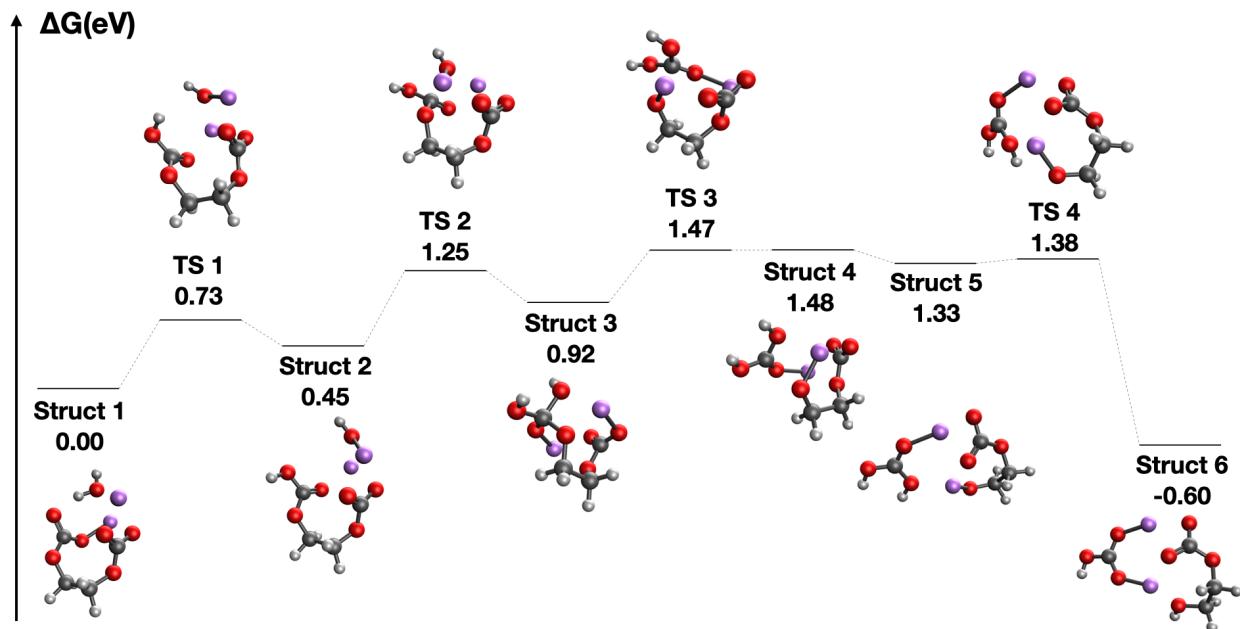

(a) LEDC hydrolysis path from water, corresponding to path A in Figure 5

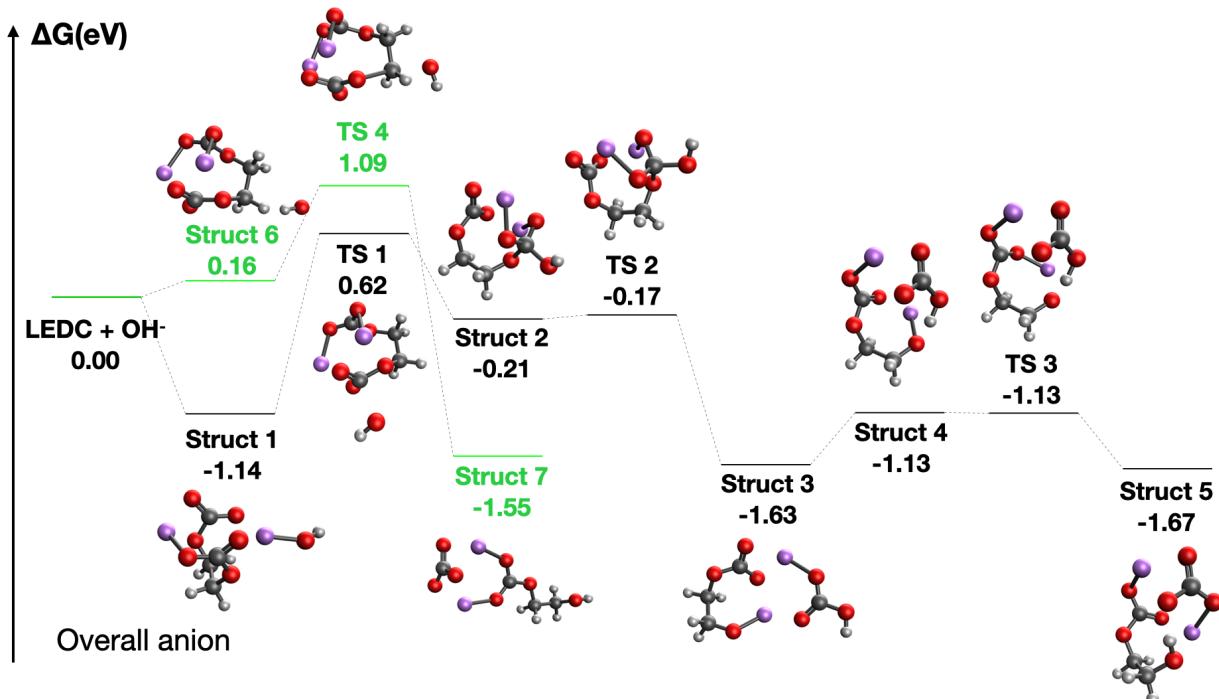

(b) LEDC hydrolysis path from  $\text{OH}^-$ , corresponding to path A in Figure 5

Figure 6: LEMC paths from DFT

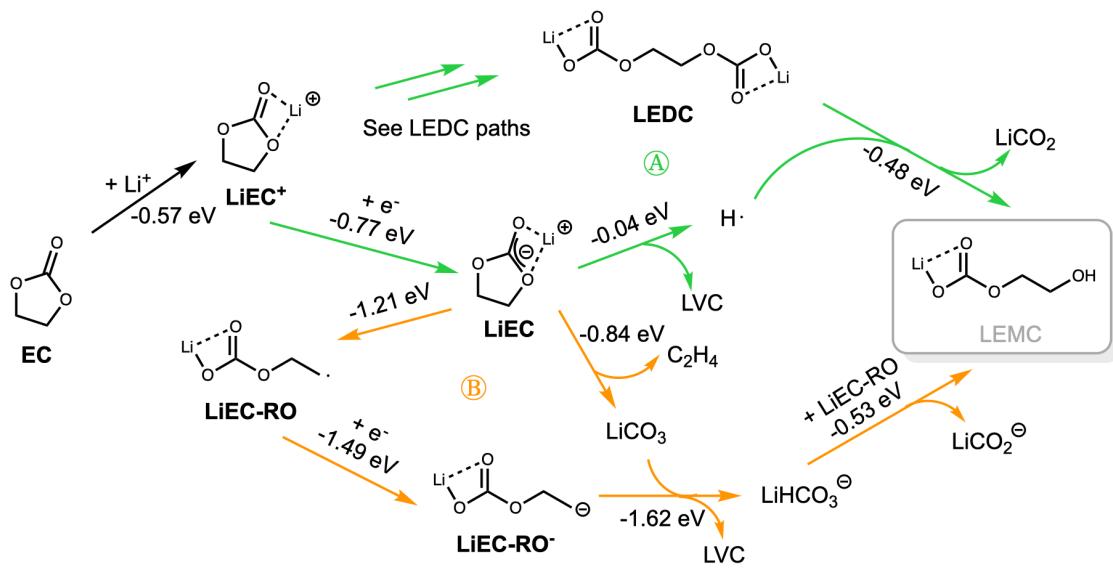


Figure 7: Paths to LEMC with no water participation identified by the 2-bond-change reaction network

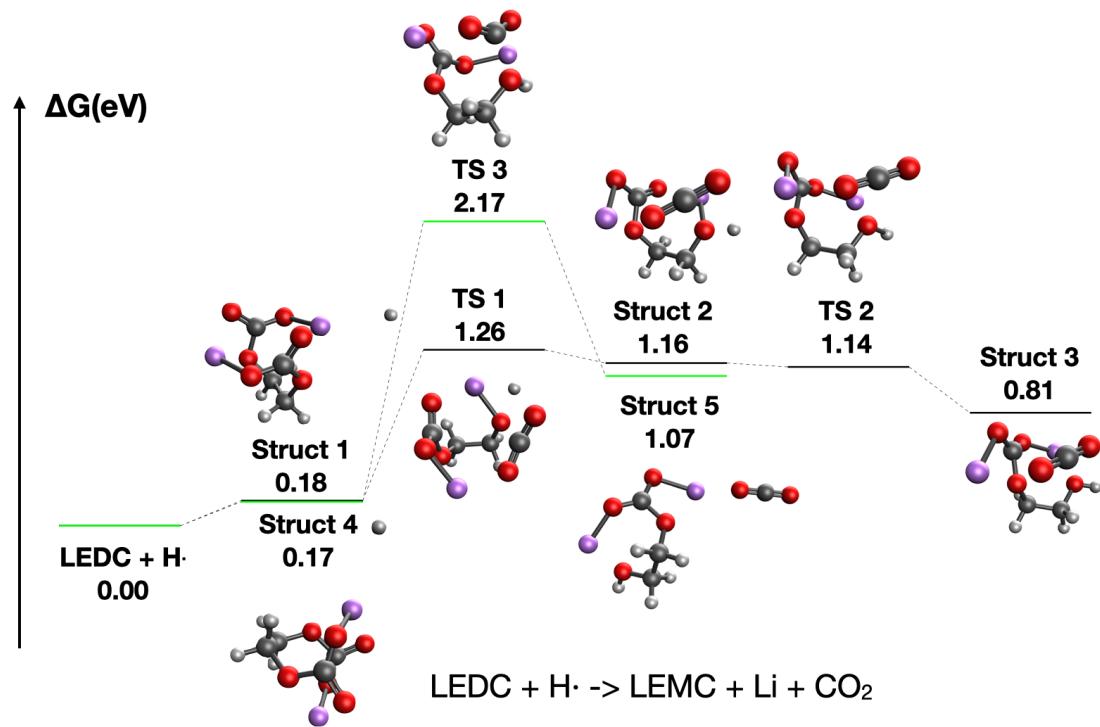


Figure 8: Radical paths, corresponding to key steps in path A in Figure 7

## References

- (1) Winter, M. The solid electrolyte interphase—the most important and the least understood solid electrolyte in rechargeable Li batteries. *Zeitschrift für physikalische Chemie* **2009**, 223, 1395–1406.
- (2) Wu, H.; Jia, H.; Wang, C.; Zhang, J.; Xu, W. Recent Progress in Understanding Solid Electrolyte Interphase on Lithium Metal Anodes. *Advanced Energy Materials* **2020**, 2003092.
- (3) An, S. J.; Li, J.; Daniel, C.; Mohanty, D.; Nagpure, S.; Wood III, D. L. The state of understanding of the lithium-ion-battery graphite solid electrolyte interphase (SEI) and its relationship to formation cycling. *Carbon* **2016**, 105, 52–76.
- (4) Peled, E.; Menkin, S. SEI: past, present and future. *Journal of The Electrochemical Society* **2017**, 164, A1703.
- (5) Xu, K. Electrolytes and interphases in Li-ion batteries and beyond. *Chemical reviews* **2014**, 114, 11503–11618.
- (6) Peled, E. The electrochemical behavior of alkali and alkaline earth metals in nonaqueous battery systems—the solid electrolyte interphase model. *Journal of The Electrochemical Society* **1979**, 126, 2047.
- (7) Lindgren, F.; Xu, C.; Niedzicki, L.; Marcinek, M.; Gustafsson, T.; Björefors, F.; Edström, K.; Younesi, R. SEI formation and interfacial stability of a Si electrode in a LiTDI-salt based electrolyte with FEC and VC additives for Li-ion batteries. *ACS applied materials & interfaces* **2016**, 8, 15758–15766.
- (8) Andersson, A. M.; Henningson, A.; Siegbahn, H.; Jansson, U.; Edström, K. Electrochemically lithiated graphite characterised by photoelectron spectroscopy. *Journal of Power Sources* **2003**, 119, 522–527.

- (9) Aurbach, D.; Markovsky, B.; Shechter, A.; Ein-Eli, Y.; Cohen, H. A comparative study of synthetic graphite and Li electrodes in electrolyte solutions based on ethylene carbonate-dimethyl carbonate mixtures. *Journal of the Electrochemical Society* **1996**, 143, 3809.
- (10) Zhuang, G. V.; Yang, H.; Blizanac, B.; Ross Jr, P. N. A study of electrochemical reduction of ethylene and propylene carbonate electrolytes on graphite using ATR-FTIR spectroscopy. *Electrochemical and Solid State Letters* **2005**, 8, A441.
- (11) Michan, A. L.; Leskes, M.; Grey, C. P. Voltage dependent solid electrolyte interphase formation in silicon electrodes: monitoring the formation of organic decomposition products. *Chemistry of Materials* **2016**, 28, 385–398.
- (12) Michan, A. L.; Divitini, G.; Pell, A. J.; Leskes, M.; Ducati, C.; Grey, C. P. Solid electrolyte interphase growth and capacity loss in silicon electrodes. *Journal of the American Chemical Society* **2016**, 138, 7918–7931.
- (13) Andersson, A.; Edström, K. Chemical composition and morphology of the elevated temperature SEI on graphite. *Journal of the Electrochemical Society* **2001**, 148, A1100.
- (14) Nie, M.; Chalasani, D.; Abraham, D. P.; Chen, Y.; Bose, A.; Lucht, B. L. Lithium ion battery graphite solid electrolyte interphase revealed by microscopy and spectroscopy. *The Journal of Physical Chemistry C* **2013**, 117, 1257–1267.
- (15) Zachman, M. J.; Tu, Z.; Choudhury, S.; Archer, L. A.; Kourkoutis, L. F. Cryo-STEM mapping of solid–liquid interfaces and dendrites in lithium-metal batteries. *Nature* **2018**, 560, 345–349.
- (16) Aurbach, D.; Gofer, Y. The behavior of lithium electrodes in mixtures of alkyl carbonates and ethers. *Journal of the Electrochemical Society* **1991**, 138, 3529.

- (17) Aurbach, D.; Gofer, Y.; Ben-Zion, M.; Aped, P. The behaviour of lithium electrodes in propylene and ethylene carbonate: The major factors that influence Li cycling efficiency. *Journal of Electroanalytical Chemistry* **1992**, 339, 451–471.
- (18) Aurbach, D.; Ein-Eli, Y.; Markovsky, B.; Zaban, A.; Luski, S.; Carmeli, Y.; Yamin, H. The study of electrolyte solutions based on ethylene and diethyl carbonates for rechargeable Li batteries: II. Graphite electrodes. *Journal of The Electrochemical Society* **1995**, 142, 2882.
- (19) Aurbach, D.; Daroux, M.; Faguy, P.; Yeager, E. Identification of surface films formed on lithium in propylene carbonate solutions. *Journal of The Electrochemical Society* **1987**, 134, 1611.
- (20) Yang, C.; Wang, Y.; Wan, C. Composition analysis of the passive film on the carbon electrode of a lithium-ion battery with an EC-based electrolyte. *Journal of power sources* **1998**, 72, 66–70.
- (21) Zhuang, G. V.; Xu, K.; Yang, H.; Jow, T. R.; Ross, P. N. Lithium ethylene dicarbonate identified as the primary product of chemical and electrochemical reduction of EC in 1.2 M LiPF<sub>6</sub>/EC: EMC electrolyte. *The Journal of Physical Chemistry B* **2005**, 109, 17567–17573.
- (22) Dedryvère, R.; Gireaud, L.; Grugéon, S.; Laruelle, S.; Tarascon, J.-M.; Gonbeau, D. Characterization of lithium alkyl carbonates by X-ray photoelectron spectroscopy: experimental and theoretical study. *The Journal of Physical Chemistry B* **2005**, 109, 15868–15875.
- (23) Xu, K.; Zhuang, G. V.; Allen, J. L.; Lee, U.; Zhang, S. S.; Ross Jr, P. N.; Jow, T. R. Syntheses and characterization of lithium alkyl mono-and dicarbonates as components of surface films in Li-ion batteries. *The Journal of Physical Chemistry B* **2006**, 110, 7708–7719.

- (24) Kang, S.-H.; Abraham, D.; Xiao, A.; Lucht, B. Investigating the solid electrolyte interphase using binder-free graphite electrodes. *Journal of Power Sources* **2008**, 175, 526–532.
- (25) Seo, D. M.; Chalasani, D.; Parimalam, B. S.; Kadam, R.; Nie, M.; Lucht, B. L. Reduction reactions of carbonate solvents for lithium ion batteries. *ECS Electrochemistry Letters* **2014**, 3, A91.
- (26) Shi, F.; Ross, P. N.; Zhao, H.; Liu, G.; Somorjai, G. A.; Komvopoulos, K. A catalytic path for electrolyte reduction in lithium-ion cells revealed by in situ attenuated total reflection-Fourier transform infrared spectroscopy. *Journal of the American Chemical Society* **2015**, 137, 3181–3184.
- (27) Wang, L.; Menakath, A.; Han, F.; Wang, Y.; Zavalij, P. Y.; Gaskell, K. J.; Borodin, O.; Iuga, D.; Brown, S. P.; Wang, C., et al. Identifying the components of the solid-electrolyte interphase in Li-ion batteries. *Nature chemistry* **2019**, 11, 789–796.
- (28) Wang, A.; Kadam, S.; Li, H.; Shi, S.; Qi, Y. Review on modeling of the anode solid electrolyte interphase (SEI) for lithium-ion batteries. *NPJ Computational materials* **2018**, 4, 1–26.
- (29) Li, Y.; Leung, K.; Qi, Y. Computational exploration of the Li-electrode| electrolyte interface in the presence of a nanometer thick solid-electrolyte interphase layer. *Accounts of chemical research* **2016**, 49, 2363–2370.
- (30) Wang, Y.; Nakamura, S.; Ue, M.; Balbuena, P. B. Theoretical studies to understand surface chemistry on carbon anodes for lithium-ion batteries: reduction mechanisms of ethylene carbonate. *Journal of the American Chemical Society* **2001**, 123, 11708–11718.
- (31) Wang, Y.; Nakamura, S.; Tasaki, K.; Balbuena, P. B. Theoretical studies to understand surface chemistry on carbon anodes for lithium-ion batteries: how does vinylene

carbonate play its role as an electrolyte additive? Journal of the American Chemical Society **2002**, 124, 4408–4421.

- (32) Yu, J.; Balbuena, P. B.; Budzien, J.; Leung, K. Hybrid DFT functional-based static and molecular dynamics studies of excess electron in liquid ethylene carbonate. Journal of The Electrochemical Society **2011**, 158, A400.
- (33) Ebadi, M.; Brandell, D.; Araujo, C. M. Electrolyte decomposition on Li-metal surfaces from first-principles theory. The Journal of Chemical Physics **2016**, 145, 204701.
- (34) Tasaki, K.; Kanda, K.; Kobayashi, T.; Nakamura, S.; Ue, M. Theoretical studies on the reductive decompositions of solvents and additives for lithium-ion batteries near lithium anodes. Journal of the Electrochemical Society **2006**, 153, A2192.
- (35) Leung, K.; Qi, Y.; Zavadil, K. R.; Jung, Y. S.; Dillon, A. C.; Cavanagh, A. S.; Lee, S.-H.; George, S. M. Using atomic layer deposition to hinder solvent decomposition in lithium ion batteries: first-principles modeling and experimental studies. Journal of the American Chemical Society **2011**, 133, 14741–14754.
- (36) Leung, K. Two-electron reduction of ethylene carbonate: A quantum chemistry re-examination of mechanisms. Chemical Physics Letters **2013**, 568, 1–8.
- (37) Leung, K.; Budzien, J. L. Ab initio molecular dynamics simulations of the initial stages of solid–electrolyte interphase formation on lithium ion battery graphitic anodes. Physical Chemistry Chemical Physics **2010**, 12, 6583–6586.
- (38) Maeda, S.; Harabuchi, Y.; Takagi, M.; Taketsugu, T.; Morokuma, K. Artificial force induced reaction (AFIR) method for exploring quantum chemical potential energy surfaces. The Chemical Record **2016**, 16, 2232–2248.
- (39) Zhang, X.-J.; Liu, Z.-P. Reaction sampling and reactivity prediction using the stochastic surface walking method. Physical Chemistry Chemical Physics **2015**, 17, 2757–2769.

- (40) Wang, L.-P.; Titov, A.; McGibbon, R.; Liu, F.; Pande, V. S.; Martínez, T. J. Discovering chemistry with an ab initio nanoreactor. *Nature chemistry* **2014**, 6, 1044–1048.
- (41) Laio, A.; Parrinello, M. Escaping free-energy minima. *Proceedings of the National Academy of Sciences* **2002**, 99, 12562–12566.
- (42) Zimmerman, P. M. Automated discovery of chemically reasonable elementary reaction steps. *Journal of computational chemistry* **2013**, 34, 1385–1392.
- (43) Zimmerman, P. M. Navigating molecular space for reaction mechanisms: an efficient, automated procedure. *Molecular Simulation* **2015**, 41, 43–54.
- (44) Bergeler, M.; Simm, G. N.; Proppe, J.; Reiher, M. Heuristics-guided exploration of reaction mechanisms. *Journal of chemical theory and computation* **2015**, 11, 5712–5722.
- (45) Simm, G. N.; Reiher, M. Context-driven exploration of complex chemical reaction networks. *Journal of chemical theory and computation* **2017**, 13, 6108–6119.
- (46) Suleimanov, Y. V.; Green, W. H. Automated discovery of elementary chemical reaction steps using freezing string and Berny optimization methods. *Journal of Chemical Theory and Computation* **2015**, 11, 4248–4259.
- (47) Rappoport, D.; Galvin, C. J.; Zubarev, D. Y.; Aspuru-Guzik, A. Complex chemical reaction networks from heuristics-aided quantum chemistry. *Journal of chemical theory and computation* **2014**, 10, 897–907.
- (48) Kim, Y.; Kim, J. W.; Kim, Z.; Kim, W. Y. Efficient prediction of reaction paths through molecular graph and reaction network analysis. *Chemical science* **2018**, 9, 825–835.
- (49) Habershon, S. Sampling reactive pathways with random walks in chemical space: Applications to molecular dissociation and catalysis. *The Journal of Chemical Physics* **2015**, 143, 094106.

- (50) Robertson, C.; Ismail, I.; Habershon, S. Traversing Dense Networks of Elementary Chemical Reactions to Predict Minimum-Energy Reaction Mechanisms. *ChemSystemsChem*
- (51) Blau, S. M.; Patel, H. D.; Spotte-Smith, E. W. C.; Xie, X.; Dwaraknath, S.; Persson, K. A. A chemically consistent graph architecture for massive reaction networks applied to solid-electrolyte interphase formation. *Chemical Science* **2021**, 12, 4931–4939.
- (52) Boyer, M. J.; Hwang, G. S. Kinetic Selectivity of Lithium Alkyl Carbonate Formation from Combination Reactions of Ethylene Carbonate Radical Anions. *The Journal of Physical Chemistry C* **2020**, 124, 25754–25759.
- (53) Wen, M.; Blau, S. M.; Spotte-Smith, E. W. C.; Dwaraknath, S.; Persson, K. A. BonD-Net: a graph neural network for the prediction of bond dissociation energies for charged molecules. *Chemical Science* **2021**, 12, 1858–1868.
- (54) Banks, J. L.; Beard, H. S.; Cao, Y.; Cho, A. E.; Damm, W.; Farid, R.; Felts, A. K.; Halgren, T. A.; Mainz, D. T.; Maple, J. R., et al. Integrated modeling program, applied chemical theory (IMPACT). *Journal of computational chemistry* **2005**, 26, 1752–1780.
- (55) Schrödinger Python API. [http://content.schrodinger.com/Docs/r2020-4/python\\_api/overview.html](http://content.schrodinger.com/Docs/r2020-4/python_api/overview.html), accessed 06/2021.
- (56) First, E. L.; Gounaris, C. E.; Floudas, C. A. Stereochemically consistent reaction mapping and identification of multiple reaction mechanisms through integer linear optimization. *Journal of chemical information and modeling* **2012**, 52, 84–92.
- (57) Trasatti, S. The absolute electrode potential: an explanatory note. *Pure Appl. Chem* **1986**, 58, 955–966.

- (58) Trasatti, S. The “absolute” electrode potential—The end of the story. Electrochimica Acta **1990**, 35, 269–271.
- (59) Borodin, O.; Behl, W.; Jow, T. R. Oxidative stability and initial decomposition reactions of carbonate, sulfone, and alkyl phosphate-based electrolytes. The Journal of Physical Chemistry C **2013**, 117, 8661–8682.
- (60) Leung, K.; Soto, F.; Hankins, K.; Balbuena, P. B.; Harrison, K. L. Stability of solid electrolyte interphase components on lithium metal and reactive anode material surfaces. The Journal of Physical Chemistry C **2016**, 120, 6302–6313.
- (61) Shao, Y. et al. Advances in molecular quantum chemistry contained in the Q-Chem 4 program package. Mol. Phys. **2015**, 113, 184–215.
- (62) Mardirossian, N.; Head-Gordon, M.  $\omega$ B97X-V: A 10-parameter, range-separated hybrid, generalized gradient approximation density functional with nonlocal correlation, designed by a survival-of-the-fittest strategy. Physical Chemistry Chemical Physics **2014**, 16, 9904–9924.
- (63) Weigend, F.; Ahlrichs, R. Balanced basis sets of split valence, triple zeta valence and quadruple zeta valence quality for H to Rn: Design and assessment of accuracy. Physical Chemistry Chemical Physics **2005**, 7, 3297–3305.
- (64) Rappoport, D.; Furche, F. Property-optimized Gaussian basis sets for molecular response calculations. The Journal of chemical physics **2010**, 133, 134105.
- (65) Marenich, A. V.; Cramer, C. J.; Truhlar, D. G. Universal solvation model based on solute electron density and on a continuum model of the solvent defined by the bulk dielectric constant and atomic surface tensions. The Journal of Physical Chemistry B **2009**, 113, 6378–6396.

- (66) Hall, D. S.; Self, J.; Dahn, J. Dielectric constants for quantum chemistry and Li-ion batteries: solvent blends of ethylene carbonate and ethyl methyl carbonate. *The Journal of Physical Chemistry C* **2015**, 119, 22322–22330.
- (67) Qu, X.; Jain, A.; Rajput, N. N.; Cheng, L.; Zhang, Y.; Ong, S. P.; Brafman, M.; Maginn, E.; Curtiss, L. A.; Persson, K. A. The Electrolyte Genome project: A big data approach in battery materials discovery. *Computational Materials Science* **2015**, 103, 56–67.
- (68) Chai, J.-D.; Head-Gordon, M. Long-range corrected hybrid density functionals with damped atom–atom dispersion corrections. *Physical Chemistry Chemical Physics* **2008**, 10, 6615–6620.
- (69) Barone, V.; Cossi, M. Quantum calculation of molecular energies and energy gradients in solution by a conductor solvent model. *The Journal of Physical Chemistry A* **1998**, 102, 1995–2001.
- (70) Dohm, S.; Hansen, A.; Steinmetz, M.; Grimme, S.; Checinski, M. P. Comprehensive thermochemical benchmark set of realistic closed-shell metal organic reactions. *Journal of chemical theory and computation* **2018**, 14, 2596–2608.
- (71) Raju, R. K.; Bengali, A. A.; Brothers, E. N. A unified set of experimental organometallic data used to evaluate modern theoretical methods. *Dalton Transactions* **2016**, 45, 13766–13778.
- (72) Peljo, P.; Girault, H. H. Electrochemical potential window of battery electrolytes: the HOMO–LUMO misconception. *Energy & Environmental Science* **2018**, 11, 2306–2309.
- (73) Yang, C.; Fontaine, O.; Tarascon, J.-M.; Grimaud, A. Chemical recognition of active oxygen species on the surface of oxygen evolution reaction electrocatalysts. *Angewandte Chemie* **2017**, 129, 8778–8782.

- (74) Dubouis, N.; Lemaire, P.; Mirvaux, B.; Salager, E.; Deschamps, M.; Grimaud, A. The role of the hydrogen evolution reaction in the solid–electrolyte interphase formation mechanism for “Water-in-Salt” electrolytes. *Energy & Environmental Science* **2018**, 11, 3491–3499.
- (75) Rinkel, B. L.; Hall, D. S.; Temprano, I.; Grey, C. P. Electrolyte oxidation pathways in lithium-ion batteries. *Journal of the American Chemical Society* **2020**, 142, 15058–15074.
- (76) Aurbach, D.; Weissman, I. On the possibility of LiH formation on Li surfaces in wet electrolyte solutions. *Electrochemistry communications* **1999**, 1, 324–331.
- (77) Shadike, Z.; Lee, H.; Borodin, O.; Cao, X.; Fan, X.; Wang, X.; Lin, R.; Bak, S.-M.; Ghose, S.; Xu, K., et al. Identification of LiH and nanocrystalline LiF in the solid–electrolyte interphase of lithium metal anodes. *Nature Nanotechnology* **2021**, 1–6.
- (78) Lide, D. R. *CRC handbook of chemistry and physics*; CRC press, 2004; Vol. 85.
- (79) Mulliken, R. S. Electronic population analysis on LCAO–MO molecular wave functions. I. *The Journal of Chemical Physics* **1955**, 23, 1833–1840.
- (80) Shang, J.; Shirazian, S. Facilitated Dissociation of Water in the Presence of Lithium Metal at Ambient Temperature as a Requisite for Lithium–Gas Reactions. *The Journal of Physical Chemistry C* **2018**, 122, 16016–16022.
- (81) Fajín, J. L.; DS Cordeiro, M. N.; Gomes, J. R. Density functional theory study of the water dissociation on platinum surfaces: General trends. *The Journal of Physical Chemistry A* **2014**, 118, 5832–5840.
- (82) Borodin, O.; Zhuang, G. V.; Ross, P. N.; Xu, K. Molecular dynamics simulations and experimental study of lithium ion transport in dilithium ethylene dicarbonate. *The Journal of Physical Chemistry C* **2013**, 117, 7433–7444.

- (83) Hori, K.; Ikenaga, Y.; Arata, K.; Takahashi, T.; Kasai, K.; Noguchi, Y.; Sumimoto, M.; Yamamoto, H. Theoretical study on the reaction mechanism for the hydrolysis of esters and amides under acidic conditions. *Tetrahedron* **2007**, 63, 1264–1269.
- (84) Yamabe, S.; Fukuda, T.; Ishii, M. Role of hydrogen bonds in acid-catalyzed hydrolyses of esters. *Theoretical Chemistry Accounts* **2011**, 130, 429–438.
- (85) Zhan, C.-G.; Landry, D. W.; Ornstein, R. L. Energy barriers for alkaline hydrolysis of carboxylic acid esters in aqueous solution by reaction field calculations. *The Journal of Physical Chemistry A* **2000**, 104, 7672–7678.
- (86) Manna, R. N.; Dutta, M.; Jana, B. Mechanistic study of the ATP hydrolysis reaction in dynein motor protein. *Physical Chemistry Chemical Physics* **2020**, 22, 1534–1542.
- (87) Pietrucci, F.; Saitta, A. M. Formamide reaction network in gas phase and solution via a unified theoretical approach: Toward a reconciliation of different prebiotic scenarios. *Proceedings of the National Academy of Sciences* **2015**, 112, 15030–15035.
- (88) Choi, W. I.; Park, M. S.; Shim, Y.; Kim, D. Y.; Kang, Y.-S.; Lee, H. S.; Koh, M. Reductive reactions via excess Li in mixture electrolytes of Li ion batteries: an ab initio molecular dynamics study. *Physical Chemistry Chemical Physics* **2019**, 21, 5489–5498.
- (89) Shkrob, I. A.; Zhu, Y.; Marin, T. W.; Abraham, D. Reduction of carbonate electrolytes and the formation of solid-electrolyte interface (SEI) in lithium-ion batteries. 1. Spectroscopic observations of radical intermediates generated in one-electron reduction of carbonates. *The Journal of Physical Chemistry C* **2013**, 117, 19255–19269.
- (90) Shkrob, I. A.; Zhu, Y.; Marin, T. W.; Abraham, D. Reduction of carbonate electrolytes and the formation of solid-electrolyte interface (SEI) in Lithium-Ion Batteries. 2. Radiolytically induced polymerization of ethylene carbonate. *The Journal of Physical Chemistry C* **2013**, 117, 19270–19279.

- (91) Soto, F. A.; Ma, Y.; Martinez de la Hoz, J. M.; Seminario, J. M.; Balbuena, P. B. Formation and growth mechanisms of solid-electrolyte interphase layers in rechargeable batteries. *Chemistry of Materials* **2015**, 27, 7990–8000.
- (92) Heiskanen, S.; Laszczynski, N.; Lucht, B. L. Perspective—Surface reactions of electrolyte with  $\text{LiNixCoyMnzO}_2$  cathodes for lithium ion batteries. *Journal of the Electrochemical Society* **2020**, 167, 100519.
- (93) Metzger, M.; Strehle, B.; Solchenbach, S.; Gasteiger, H. A. Origin of H<sub>2</sub> evolution in LIBs: H<sub>2</sub>O reduction vs. electrolyte oxidation. *Journal of The Electrochemical Society* **2016**, 163, A798.

# Graphical TOC Entry

