

# Life Cycle Assessment of Distributed Plastic Recycling via Additive Manufacturing

Cristian CACERES MENDOZA<sup>a,1</sup>, Pavlo SANTANDER<sup>b</sup>, Fabio A. CRUZ SANCHEZ<sup>a</sup>, Nadège TROUSSIER<sup>c</sup>, Mauricio CAMARGO<sup>a</sup>, Hakim BOUDAOU<sup>a</sup>

<sup>a</sup> Universite de Lorraine ERPI F-54000 Nancy France

<sup>b</sup> University of Santiago of Chile (USACH) Faculty of Engineering; Industrial Engineering Department Chile

<sup>c</sup> CREIDD UR InSyTE University of Technology of Troyes 12 rue Marie Curie 10010 Troyes France

---

## Abstract

Distributed recycling via additive manufacturing (DRAM) in a closed-loop supply chain (CLSC) emphasizes a technical path to an emerging plastic recycling system. This technical system aims to reduce the environmental impact, and improve the valorization of recycled waste. Major progress has recently been reported in various stages to validate the technical feasibility, environmental impact, and economic viability of the DRAM system. However, little work has been done for the preparation and recovery stages, which involve logistics and the study of the whole recycling network. Thus, this work evaluates the environmental performance of implementing a DRAM system. Using life cycle analysis (LCA), an assessment of potential impacts of 1kg of recycled PLA was carried out, examining the case of a university Fab Lab located in Nancy, France, where the DRAM strategy has been deployed. To evaluate this system, four impact categories were considered : climate change, potential eutrophication, resource depletion, and ion radiation. Three of these categories demonstrated environmentally favorable results due to the implementation of the DRAM system in comparison of a virgin supply chain. This article provides an environmental overview of the benefits and disadvantages of developing a DRAM system in a specific context.

**Keywords :** *LCA ; Distributed Recycling ; Plastic ; Additive Manufacturing, Circular Economy*

---

## 1. Introduction

Since the early 20th century, the invention of plastic, or synthetic organic polymers, has changed the landscape of various industrial sectors. Production increased at a compound annual growth rate of 8.4%, rising from 2Mt in 1950 to 368Mt in 2019 (Geyer et al., 2017). This versatile material stands out thanks to its easy processing and handling in shape, color, texture, thermal and barrier properties, and its mechanical and chemical resistance (Andrade and Neal, 2009 ; Thompson et al., 2009 ). In consequence, 39.6% of the demand comes from the packaging industry, followed by the construction and automotive industries with 20.4% and 9.6% of the production share respectively (Plastic Europe -, 2020). Unfortunately, the main problem is associated with multiple environmental damages throughout its life cycle.

---

\*. Corresponding author

Email address: cristian.caceres@univ-lorraine (Cristian CACERES MENDOZA)

1. Corresponding Author

10 Terrestrial, aquatic, and atmospheric ecosystems are not exempt from the externalities of this  
11 innovation, which represent a major issue (Kumar et al., 2021). Micro-, meso-, and nano-plastic  
12 pollution contribute to the detriment of ecosystem services such as the ability to sequester  
13 carbon (Wang et al., 2022), soil productivity (Zhang et al., 2022), and eutrophication (Vuori  
14 and Ollikainen, 2022).

15 Indeed, plastic pollution in aquatic ecosystems such as standing waters can act as a vector of  
16 toxic chemicals that affect biogeochemical cycles. In 2010, Jambeck et al. (2015) estimated  
17 that between 1.75–4.62% mismanaged plastic waste reached the oceans equivalent to 4.8  
18 to 12.7 million MT in 192 coastal countries. A total of 150 million tons of plastic has been  
19 dumped into the sea to date (Pinto Da Costa et al., 2020). The presence of these solid plastic  
20 wastes has become a threat to marine ecosystems (Shi et al., 2022). Additionally, the transfer  
21 of plastic into the food chain is a clear danger to animals, and certainly to humans as well.  
22 Therefore, reducing the production of plastics is of great importance in the long term.

23 Adequate use and disposal of plastics is a wicked problem, characterized by high complexity  
24 and multifaceted feedback loops. A systemic view of the entire plastics value chain is needed,  
25 including petrochemical companies (de Vargas Mores et al., 2018; Iles and Martin, 2013),  
26 converters (Paletta et al., 2019), brand owners or manufacturers (Gong et al., 2020; Ma et  
27 al., 2020), retailers and consumers (Confente et al., 2020; Filho et al., 2021; Friedrich, 2020),  
28 and recycling operators (Huysveld et al., 2019; Pazienza and De Lucia, 2020), as well as the  
29 influences of policy-makers on wider economic and societal changes (Paletta et al., 2019). The  
30 European Union (EU) intends to develop a circular economy (CE) based on a production and  
31 consumption model with key activities such as “sharing,” “reducing,” “reusing,” “repairing,”  
32 “renewing,” and “recycling” the existing materials and products as many times as possible, in  
33 order to create added value by extending the life cycle of products (European Commission,  
34 2018; Matthews et al., 2020). Several criticisms have been raised, given the thermodynamic  
35 constraints based on biodiversity and thermodynamics, arguments for a fully circular economy  
36 (Corvellec et al., 2021; Giampietro and Funtowicz, 2020). Nevertheless, as part of the European  
37 Green Pact presented on March 20, 2020, there are plans to establish an action plan involving  
38 the circular economy, mainly promoting the development of sustainable products, reducing  
39 waste, and empowering citizens as key players (European Commission, 2018). Considering  
40 the French context, a target was established that by 2025 all plastic waste should be recycled,  
41 but currently recycling statistics in France are only reaching levels close to 25%. Despite these  
42 ambitious objectives, plastics recycling has historically been an expensive process due to the  
43 inherent separate collection, transportation, processing, and remanufacturing (Hopewell et  
44 al., 2009; Singh et al., 2017). The economies of scale have been leveraged to reduce these  
45 costs with centralized and global recycling chains (Kreiger et al., 2013; Kreiger and Pearce,  
46 2013). Nevertheless, in order to carry out this recycling system, multiple steps need to be  
47 accomplished that integrate the sorting phase, long-distance transport, waste treatment, and  
48 remanufacturing. The high costs of these processes and the low selling price (mainly due  
49 to the dependence of the recycled plastic price on the petroleum and virgin prices) seldom  
50 generate benefits and often require costly public subsidies (Hamilton and Steven, 2019). In  
51 addition, these centralized plastic manufacturing and recycling lines lead to soil, water, and  
52 air pollution (Arena et al., 2003; Carlsson Reich, 2005). In addition to the current problems  
53 in the plastic recycling network, we can highlight that supply chains in general are under  
54 increasing pressure from various stakeholders to make decisions from a sustainable perspective;  
55 in other words, based on economic, environmental, and social objectives (Hassini et al., 2012).

56 Additive manufacturing technology (also known as 3D printing) enables the potential

of distributed manufacturing (DM) for products of high added value (Bonnín Roca et al., 2019; Petersen and Pearce, 2017; Woern and Pearce, 2017). Nowadays, the accessibility of freely available designs has increased significantly, together with the development of open-source technologies and the supply of raw materials (virgin and recycled filaments) for 3D printing (Hunt et al., 2015). Distributed manufacturing is defined as the decentralization of production through the installation of multiple production factories with similar technology distributed geographically (Bonnín Roca et al., 2019). It is characterized by local production that thrives on the synergy of the emerging capabilities of digital manufacturing, information, and communication technologies, and the peer-to-peer production approach (Kostakis et al., 2018; Kostakis, 2013; Pavlo et al., 2018). Indeed, DM offers the possibility to decentralize production structures, the flexibility to reflect local customer needs, lower logistics costs, shorter lead times, and lower environmental impacts (Petersen and Pearce, 2017; Woern and Pearce, 2017). Based on the DM paradigm, a new possibility of plastic recycling supported by additive manufacturing, called distributed recycling by additive manufacturing (DRAM), has emerged in the literature (Cruz Sanchez et al., 2020; Hart et al., 2018). Promoted by the development of 3D printing in an open-source context, DRAM is proposed to provide recycled plastic feedstock to the various 3D printers in a DM context. This recycled plastic can take the form of a filament, and recent works have dealt with the validation of a granular form (Alexandre et al., 2020; Justino Netto et al., 2021). The 3D printing feedstock is then obtained via plastic recycling on a local scale using open-source machines such as shredders and extruders (Zhong and Pearce, 2018).

The main feature of DRAM is the reduction of the impact in the collection phase, favoring shorter and simpler supply chains (Despeisse et al., 2017; Garmulewicz et al., 2018). Several works have focused on the validation of the DRAM approach from a technical (López et al., 2022; Mohammed et al., 2022), economic, and environmental perspective (Cañado et al., 2022; Wu et al., 2022). Cruz Sanchez et al. (2020) conducted a systematic literature review to examine the level of development of the different DRAM stages from a technical perspective. Their results show that significant progress has been made in the stages of compounding, feedstock, printing and quality assessment. However, they also show that little work has been done for the preparation and recovery stages in spite of this. In another work, Santander et al. (2020) proposed an initial model to study the economic and environmental feasibility of DRAM from a logistical point of view. Their results have shown the feasibility of the system in economic terms and in the reduction of CO<sub>2</sub> emissions when implementing the system. From an environmental point of view, the DRAM and DM approaches have been evaluated mainly using the Life Cycle Assessment (LCA) approach.

LCA is one of the most widely used environmental impact assessment methodologies. LCA corresponds to an ISO 14040 certified methodology, which has even been used for environmental regulations in different parts of the world. In the context of DM/DRAM-related research, LCA has been applied in various ways. For example, Kreiger and Pearce (2013) conducted a life cycle analysis, in terms of energy consumed and emissions involved, to compare centralized manufacturing and distributed manufacturing using RepRaps (3D printers) for the distributed production of goods. The results showed that the use of Poly Lactic Acid (PLA) in a distributed manufacturing context reduces energy demand and system emissions, which can be greatly diminished if a solar photovoltaic (PV) array is used. Later, Kreiger et al. (2014) explored the environmental benefit of distributed recycling using open-source extruders (RecycleBots), which have been used to obtain 3D printing filament from post-consumer goods. Focusing on the use of High Density Poly-Ethylene (HDPE) for the material, they performed an

104 LCA of energy consumption and CO<sub>2</sub> emissions to compare distributed recycling to standard  
105 centralized recycling. Their results showed that distributed recycling of HDPE uses less energy  
106 than the best-case scenario investigated for centralized recycling, and it can achieve savings  
107 of over 80%. Kerdlap et al. (2021), through a simulation approach, quantified the plastic  
108 life-cycle environmental impact of small-scale sorting and recycling systems in comparison  
109 to traditional large-scale centralized systems in Singapore, with the aim of determining the  
110 conditions under which distributed recycling can be environmentally beneficial. Their results  
111 showed that the environmental impacts in terms of climate change, water depletion and  
112 terrestrial ecotoxicity were higher compared to the centralized systems. Their results showed  
113 that the environmental impacts in terms of climate change, water depletion, and terrestrial  
114 ecotoxicity were higher compared to the centralized systems. However, these results are mainly  
115 related to the means of transport considered for each system (commercial van for distributed  
116 recycling and large trucks for centralized recycling), since the use of large trucks decreases  
117 the total impact.

118 In conclusion, even though different studies have been conducted aiming to validate the  
119 distributed recycling approach from a technical, economic, and environmental perspective,  
120 only the work of Kreiger et al. (2014) is focused on the environmental assessment of distributed  
121 recycling for 3D printing purposes. However, their research is limited to the consideration of  
122 energy and CO<sub>2</sub> emissions as environmental indicators. Therefore, major efforts need to be  
123 made in order to evaluate, in a holistic way, the environmental impacts of the global DRAM  
124 value chain. Thus the contribution of this research lies in the evaluation of environmental  
125 impacts from the implementation of distributed recycling via an additive manufacturing  
126 approach in a territory. Specifically, an environmental evaluation using life cycle assessment  
127 (LCA) is conducted, comparing a distributed plastic recycling system to produce 3D filament  
128 with a traditional production system of virgin plastic filament for 3D printing. From this  
129 evaluation, the environmental impacts (positives or negatives) of implementing DRAM have  
130 been analyzed and discussed.

131 This article is structured as follows. Section 2 presents the system (case study) evaluated.  
132 Section 3 materials and methods, where life cycle analysis methodology is explained. Section 4  
133 presents the life cycle analysis performed. Section 5 presents the discussion of results. Finally,  
134 Section 6 presents the main conclusions and recommendations for future works.

## 135 2. Case study : The Lorraine Fab Living Lab

136 In order to achieve the objectives of this research, a case study with the following  
137 characteristics was selected :

- 138 1. Existence of a favorable context to implement a DRAM recycling system. A favorable  
139 context is defined as a considerable amount of plastic waste to be treated, as well as  
140 initiatives for the widespread use of 3D printing.
- 141 2. Existence of a space dedicated to the recycling of plastic for 3D printing.

142 Under these considerations, the selected context for this study was the Lorraine Fab  
143 living Lab (LF2L)<sup>2</sup>, an innovation space located in Nancy, France. This university laboratory  
144 has been selected mainly for the following reasons : (1) Innovation spaces such as Fablabs,

---

2. <https://lf2l.fr/projects/green-fablab/>

145 Maker spaces, design factories among others have proven to be favorable environments for eco-  
146 innovations facilitating the implementation of circular economy strategies ([Coskun et al., 2022](#)).  
147 Previous studies show that these collaborative environments foster sustainable experimental  
148 learning, provide methodologies and tools for the co-creation of circular solutions, drive the  
149 transition toward sustainable smart cities, foster the creation of new sustainable business  
150 models, and facilitate knowledge exchange on circular solutions ([Kasmi et al., 2021](#)). (2) Since  
151 2014, the LF2L has been studying the possibility of recycling, in their installations, PLA for  
152 reuse in 3D printing. The pilot recycling process present in this center has been developed  
153 in the research work of Cruz Sanchez et al. ([2017](#)), and the possibility of implementing  
154 this recycling process in the region is being evaluated. (3) An investment program has been  
155 launched by the Grand Est region to promote the implementation of Fablabs, and consequently  
156 the use of 3D printers, in the schools and high schools of the region ([Canopé, 2022](#)). The goal  
157 of this investment plan is to ensure that all the schools and high schools in the region will  
158 be equipped with this technology in the near future. This corresponds to the future scenario  
159 evaluated in the work of Santander et al. ([2020](#)). However, in contrast to Santander et al.  
160 ([2020](#)), in our research work a complete environmental evaluation of the scenario is carried out.  
161 Consequently, this case study has been selected because of their experience in experimenting  
162 with the DRAM strategy, as well as the availability of technical and economic data and the  
163 aforementioned scientific publications that provide details on its local implementation.  
164 For this study, the context described above has been simplified in terms of geographical scale,  
165 and the following assumptions are considered.

- 166 — Consideration is given to only one type of plastic waste to be recycled. Specifically,  
167 PLA has been considered. This is mainly because PLA is one of the most used plastics  
168 in 3D printing ([Bikas et al., 2016](#)). For the plastic waste sources, PLA waste from  
169 schools and high schools (who have 3D printers) has been considered. PLA has been  
170 selected as feedstock material due to the fact that (1) in Europe, PLA is considered a  
171 “miscellaneous product” ([Maga et al., 2019](#)) because of its classification as a Bioplastic  
172 and because, at least in Europe, there is no defined recycling strategy for these types  
173 of plastics so they are usually sent to a landfill or are incinerated ; and (2) PLA is one  
174 of the most widely used plastics in 3D printing.
- 175 — The recycling system modeled does not consider the sorting, separation, and cleaning  
176 process because the collected material corresponds to non-contaminated waste : for  
177 example, discarded 3D printing parts used for prototyping.
- 178 — From a geographical point of view, only schools and high schools in the Lorraine region  
179 of France have been considered, and the route of recovery and delivery considered is  
180 obtained in the work of Santander et al. ([2020](#)).
- 181 — Each school and high school requires 1 kg of filament per month.
- 182 — The 3D printing activities carried out in these establishments have the specific purpose  
183 of making product prototypes and mock-ups, which allows them to generate testing  
184 activities, design evaluations, functional evaluations, and corrections. Therefore, after  
185 a short lifetime, 3D printing can be a source of significant amounts of plastic waste  
186 due to printed parts that do not possess the desired quality, unused raw materials, or  
187 products that have already fulfilled their life cycle ([Jaafarnia et al., 2021](#)).

188 3. Material and methods

189 The chosen methodology is Life Cycle Assessment (LCA) because, unlike other analytical  
190 methodologies with an environmental focus, such as Material Flow Analysis (MFA), Substances  
191 Flow Analyses, and Environmental Risk, it allows us to evaluate the environmental impacts  
192 of the system value chain to be modeled ([Mahmud et al., 2021](#); [Pryshlakivsky and Searcy,  
193 2021](#)).

194 The LCA represents a different tool and different techniques created to determine in an  
195 effective and fast way the results to help with managerial decision-making in environmental  
196 terms and in the deepening of the sustainable development policy ([Guinée, 2002](#)). Life Cycle  
197 Assessment (LCA) is a structured, comprehensive and internationally standardized method  
198 in accordance with ISO 14040 and 14044. It defines all the steps for its use : goal and scope  
199 definition, inventory analysis, impact assessment, and interpretation ([Pennington et al., 2004](#)).  
200 LCA is a tool for quantitative evaluation of materials, energy flows, and the potential impact  
201 of products, services, or technologies ([Dehghanian and Mansour, 2009](#)). The analysis takes  
202 into account the entire life cycle of a product : from resource extraction, through production,  
203 use, and recycling, to the disposal of the remaining waste ([IES, 2010](#)). LCA is considered a  
204 legitimate environmental methodology that enables systems analysis for waste policy and  
205 strategy ([Gontard et al., 2022](#)).

206 A life cycle analysis has four main stages : the definition of objectives and approach (Stage  
207 1), inventory analysis (Stage 2), impact assessment (Stage 3), and interpretation (Stage 4)

- 208 1. **Goal and Scope Definition** : This is the first stage and serves to orient the study  
209 bases. It defines the main objectives of the life cycle analysis, the target audience of  
210 this report, the functional unit that is the reference point from which the potential  
211 environmental impacts will be obtained, the limits of the system under study, the  
212 categories of environmental impacts to be evaluated, and the hypotheses to be used in  
213 different stages of the LCA.
- 214 2. **Inventory Analysis** : Inventory is the stage in which the flows are quantified. It sets  
215 out the database used, the energy and material input, the calculations performed, and  
216 how the system was modeled.
- 217 3. **Impact Assessment** : This stage presents the software used and the calculation  
218 methodology used to transform flows and characterize them in the impact categories  
219 evaluated. From this characterization, the impact profile of the system under study is  
220 obtained.
- 221 4. **Interpretation** : This is the conclusion of steps 2 and 3, presenting the results obtained  
222 from the hypotheses used, the considerations, and the functional study that has been  
223 defined. The phases of the life cycle that have the most impact are identified, and  
224 sensitivity analyses can be carried out to evaluate the behavior of the systems according  
225 to the variation of certain parameters. The inter-phase analysis stage is fundamental  
226 for decision-making, as it identifies critical points and provides a basis for future  
227 improvements.

228 The LCA methodology is mostly used in an iterative way, allowing a better definition of  
229 the objectives to be achieved and the system to be analyzed.

230 In the following sections, an LCA is presented for DRAM using the Lorraine Fab Living  
231 Lab as a case study.

232    4. LCA application and results

233    4.1. Goal and Scope Definition

234       The main objective of this life cycle analysis is to compare the potential impacts produced  
235       by a DRAM chain with the impacts produced by a traditional chain of virgin plastic filament  
236       for 3D printing.

237    4.1.1. The functional unit

238       As mentioned above, this study will compare the environmental impact of two PLA 3D  
239       filament supply systems. By way of context for this study, the 3D filament will be supplied to  
240       all schools and high schools located in the city of Nancy, France. To compare two or more  
241       systems, it is necessary to define a functional unit that represents the service delivered by  
242       both systems. In this case the main service consists of the following :

243       “*A monthly delivery of 1 kg of ‘standard’ plastic filament (PLA) to each school and high  
244       school in Nancy during ten months of the year.*”

245    4.1.2. System boundary

246       Figure 2 shows the two systems compared in this study and the processes integrated into  
247       the life cycle analysis. As can be observed, there are three different boundaries represented by  
248       the colors green, blue, and red. The first boundary (green box) corresponds to the Biosphere,  
249       which represents everything related to nature, such as raw materials from natural resources,  
250       ecosystems, and solar energy. The second boundary (dark blue box) corresponds to the  
251       Technosphere limit, representing human activity (e.g. use of electricity, fuel, etc.). Here, we  
252       can observe all the material flows that are considered for the life cycle analysis, the flows  
253       between processes, or the flows that are part of the functional unit mentioned above. Finally,  
254       the boundary in a light blue color represents the limit of the services and processes taken into  
255       consideration in this study. On the one hand, in the upper process flow, we can observe the  
256       processes considered in the system to produce filament from virgin plastic. The process starts  
257       with PLA production, which is followed by PLA transportation, filament production, and  
258       finally product delivery. On the other hand, Fig. 1 shows the recycling process enclosed in  
259       the orange box. The process starts with the collection of waste produced by schools and high  
260       schools, then the plastic recycling process, the production of filament, and the delivery of  
261       filament are carried out.

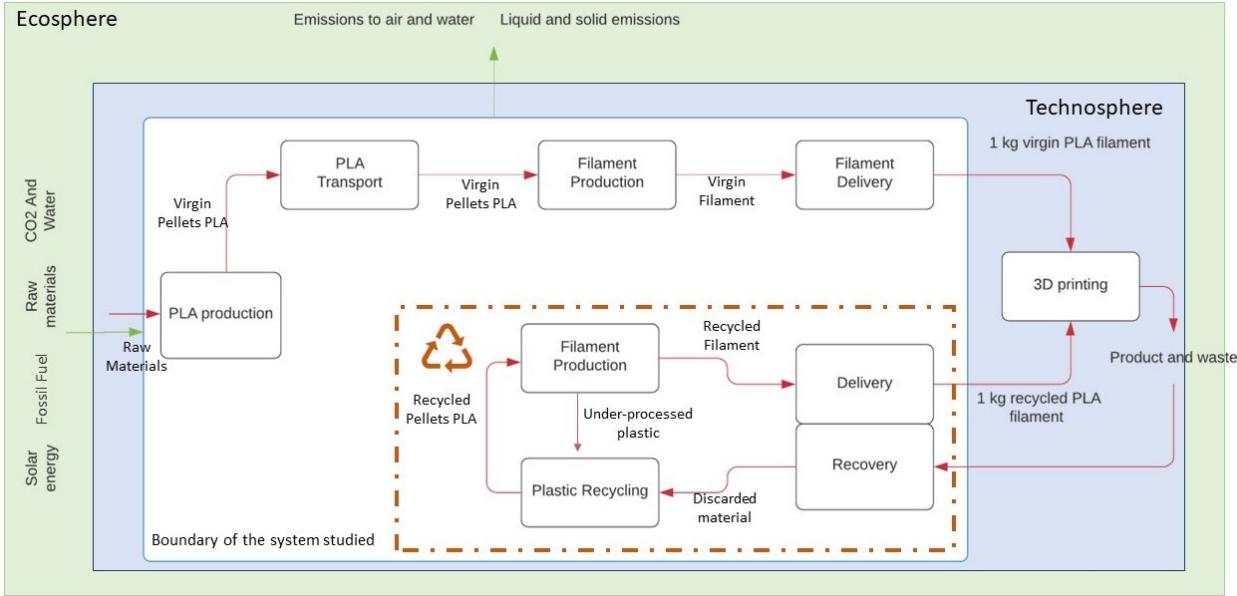


FIGURE 1: System limits for life cycle analysis

#### 262 4.1.3. Selected impact categories

263 The objective of performing a life cycle analysis is to determine and evaluate the potential  
 264 environmental impacts produced at different stages in the life cycle of a product, service,  
 265 activity, or process. However, it is quite difficult to identify, *a priori*, the categories of impacts  
 266 in which the system under study is most detrimental (climate change, eutrophication, etc.).  
 267 To resolve, it was decided to analyse relevant literature of LCA applied on the bioplastics and  
 268 additive manufacturing separately. First, the production of plastics (in this case bioplastics)  
 269 compared to the recycling of plastics. Second, the integration of these materials in additive  
 270 manufacturing as raw material for the subsequent printing of products.

271 Concerning the plastic perspective, Bishop et al. (2021) compared the impact of bioplastics  
 272 (such as PLA) regarding the petrochemical plastics considering the impact categories across  
 273 44 relevant articles that used LCA evaluation. Their results pointed out the most used impact  
 274 category for bioplastics evaluation is climate change, followed by potential eutrophication  
 275 variations, resource depletion, human toxicity, photochemical oxidant formation, ozone de-  
 276 pletion, ecotoxicity, particulate matter formation, energy consumption, land use, and water  
 277 consumption.

278 On the other hand, it was found that the cumulative energy demand (CED) of the  
 279 system is the most evaluated LCA impact category (Cerdas et al., 2017; Kellens et al., 2017;  
 280 Kreiger and Pearce, 2013; Quinlan et al., 2017) in the context of additive manufacturing. In  
 281 addition, It was also considered climate change, potential eutrophication, and human toxicity  
 282 as the main impact categories included in the LCA. In conclusion, it was decided to use the  
 283 predominant impact categories in each of the industries, namely climate change, potential  
 284 eutrophication, and resource depletion (fossil and water) after analyzing the LCA results of  
 285 the two domains .

#### 286 4.1.4. Assumptions and limitations

287 The realization of a full LCA involves the collection of information and data related to  
 288 the different processes, flows, and activities. Due to the difficulty of obtaining the necessary

289 data, it is permissible to formulate hypotheses to partially make up for the lack of data, on  
290 the condition that the hypotheses used, and the conditions under which they are formulated,  
291 are made transparent.

292 The hypothesis formulation was mainly used to model the virgin plastic filament production  
293 system. The main hypotheses used are based on :

- 294 — Location of polylactide acid production : This hypothesis indicates the location where  
295 the polylactic acid production process takes place.
- 296 — Location of filament manufacturer : Due to the uncertainty about filament production,  
297 two companies with different locations that are engaged in the production of plastic  
298 filaments have been modeled.
- 299 — Filament production machine : The machine PEEK 3d Printer Filament Production  
300 Line<sup>3</sup> has been considered, which corresponds to the machine used by the two filament  
301 manufacturers considered.
- 302 — Performance of the filament production machine : The machine selected to carry out  
303 the filament production process has a range of transformation from plastic pellets to  
304 filament. The range of the machine chosen for the evaluation has an output between  
305 20 and 25 kg of filament per hour. This range directly affects power consumption.
- 306 — Type of energy source used to conduct the recycling processes : Each country has its  
307 own technological mix to supply its electrical energy consumption, such as nuclear,  
308 solar, and wind. These different sources of electricity are considered in the evaluation.
- 309 — Transportation of raw material and filament (virgin and recycled) : The different  
310 options for methods of raw material transportation and filament transportation are  
311 considered in the evaluation.

312 Based on these hypotheses, two scenarios were created to model the possible operation of  
313 the virgin plastic filament production system (see Table 1). A third scenario represents the  
314 distributed recycling system for filament production, so the complete system is modeled with  
315 information obtained from the LF2L.

---

3. More information about the machine can be found at [www.accextrusion.com/product/peek-3d-printer-filament-production-line.html](http://www.accextrusion.com/product/peek-3d-printer-filament-production-line.html) (Accessed on 09/09/2022)

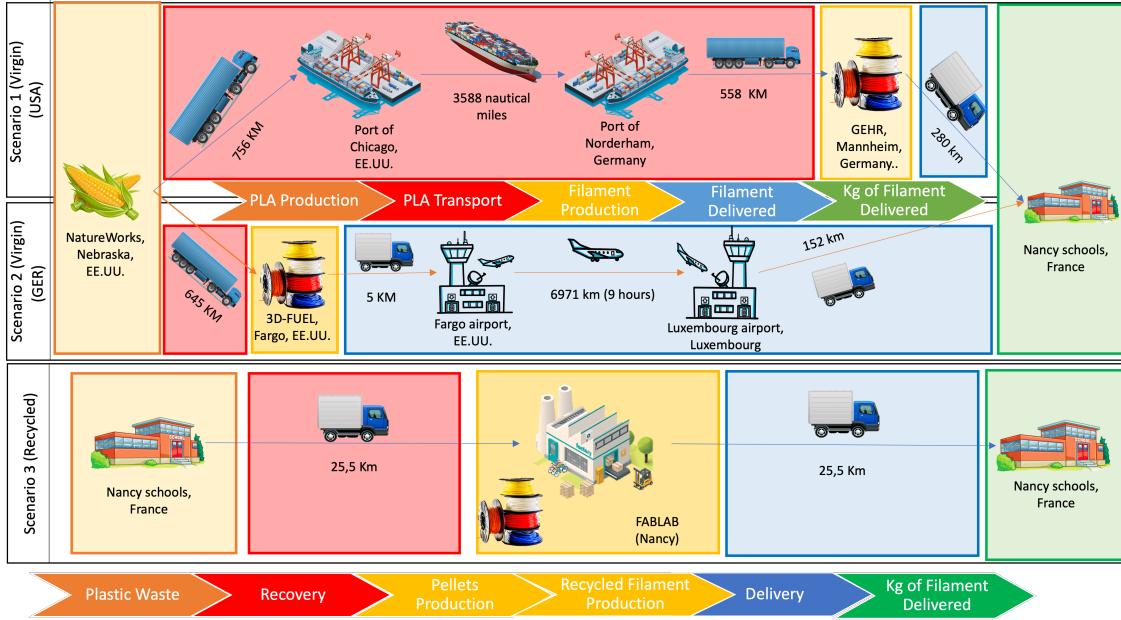


FIGURE 2: Representation of the 3 scenarios

TABLE 1: Scenario definition

Scenario	Description
<b>Virgin Filament</b>	
1	Scenario 1 begins with the production of PLA at the NatureWorks factory in Nebraska, USA. The PLA is transported by a combination of land and sea to bring the plastic from the United States to the filament manufacturing company, called GEHR, which is located in the city of Mannheim in Germany. In Germany, electricity is produced from wind power. From this location, the virgin filament is shipped directly to Nancy by light road transport.
2	factory in Nebraska, USA. The pellets of PLA are transported by road to the filament manufacturing company, called 3D-Fuel, which is located in Fargo, USA. In the United States, electricity is produced from natural gas. From the USA, the filament is shipped directly to Luxembourg by air freight. Then the filament is transported to Nancy using a lightweight vehicle.
<b>Recycled Filament</b>	
3	This scenario starts with the collection of PLA 3D printing waste from the schools and high schools. The PLA waste is transported to the recycling point (Lorraine Fab Living Lab) using light road transport. At this center, the size reduction process and the extrusion process necessary to produce the recycled filament are performed. The recycled filament is then delivered to the same schools and by the same means of transport as where the waste was collected.

316    4.2. Life Cycle Inventory Analysis (LCIA)

317    4.2.1. Data source

318    To obtain the necessary data, different data sources were used to carry out the LCIA.  
 319    On the one hand, for virgin PLA filament production there are various life cycle analyses  
 320    published by NatureWorks (Vink et al., 2003 ; Vink and Davies, 2015), where the results have  
 321    been incorporated into the EcoInvent database. These articles helped us to understand the  
 322    PLA production process, considering the production center in Nebraska, USA. For virgin  
 323    PLA filament manufacturing, NatureWorks proposes a catalog of customers who manufacture  
 324    filament from PLA produced by the company, which facilitated the modeling of the supply  
 325    chain to sell its product in the city of Nancy, France.

TABLE 2: Table of impact indicators and their unit of measure

Impact Category	Methodology		Unit
Climate Change	ReCiPe (H)		$KgCO_2 - Eq$
Resources Depletion	Fossil Depletion	ReCiPe (H)	$KgOil - Eq$
	Water Depletion	ReCiPe (H)	$KgP - Eq$
Eutrophication Potential	Freshwater Eutrophication	ReCiPe (H)	$KgN - Eq$
	Marine Eutrophication	ReCiPe (H)	$m3$

326 On the other hand, for the plastic recycling process the data concerning the input/output  
 327 materials and the machines used in the recycling process were obtained directly from the  
 328 Lorraine Fab Living Lab and from the thesis works conducted at the ERPI laboratory related  
 329 to DRAM ([Cruz Sanchez et al., 2020, 2017; Santander et al., 2020](#)) (see the Appendix A).  
 330 These data allowed us to model and understand the recycling network, its main functions,  
 331 and its limitations in consideration of the case study presented in Section 3.

332 *4.3. Impact Assessment (LCIA)*

333 *4.3.1. Calculation methodology*

334 *4.3.1.1. Choice of software.* The software used to perform this life cycle analysis was OpenLCA  
 335 1.10.3. The main reason for its use was because it is open-source software. This software  
 336 makes it possible to perform full life cycle analysis and carbon footprint analysis, allowing us  
 337 to install a wide variety of databases. For this case, the database used was the EcoInvent 3.5.

338 *4.3.1.2. Choice of calculation methodology and impact indicators.* In analyzing the impact  
 339 methodologies and considering the selected impact categories for this study (see Section 4.1.3),  
 340 ReCiPe (Global-Hierarchist version) has been chosen as the impact calculation methodology.  
 341 The ReCiPe method ([Goedkoop et al., 2009](#)) has been chosen mainly because it is widely used  
 342 in various areas of research ([Dekker et al., 2020](#)). In addition, ReCiPe is an LCIA method  
 343 that is harmonized in terms of modeling principles and choices, offering results at both the  
 344 midpoint and endpoint level ([Goedkoop et al., 2009](#)). In addition, it is used for various life  
 345 cycle analyses in the area of additive manufacturing with a hierarchical cultural perspective  
 346 ([Saade et al., 2020](#)). Finally, the set of impact categories chosen are presented in Table 2.

347 *4.3.1.3. Impact studies.* Table 3 presents the results of the comparison, showing for the  
 348 virgin and recycled scenario the amount of impact that is generated in each impact category  
 349 evaluated. In addition, the percentage reduction (comparing the recycling scenarios with  
 350 the virgin scenario) is presented. To construct this table, the best virgin scenario (least  
 351 impactful) was considered for comparison. As a result, it can be observed that the production  
 352 of filament from recycled plastic has a significant advantage in five of the six impact categories  
 353 (climate change, fossil depletion, freshwater eutrophication, marine eutrophication, and water

TABLE 3: Scenario definition

Impact categories	Scenarios	Impact of each process				Total
		PLA Production	Supply Transport	Filament production	Delivery	
Climate change (kg CO <sub>2</sub> -Eq)	Virgin [1-2]	337.36	[5.69 - 18.19]	[1.94 - 32.60]	[54.43 - 785.24]	[411.92 - 1160.88]
	Recycled	-	5.4523	2.289	4.957	12.699 (-97%)
Fossil Depletion (kg oil-Eq)	Virgin [1-2]	96.79	[2.30 - 6.96]	[0.50 - 13.13]	[19.58 - 285.14]	[123.83 - 397.36]
	Recycled	-	1.961	0.615	1.783	4.359 (-97%)
Freshwater Eutrophication (kg P-Eq)	Virgin [1-2]	0.14	[0.001- 0.002]	[0.001- 0.003]	[0.011- 0.024]	[0.159 0.168]
	Recycled	-	0.0011	0.0016	0.0010	0.004(- 98%)
Ionizing Radiation (kg U235-Eq)	Virgin [1-2]	26.51	[0.45-1.49]	[0.12-0.15]	[4.46- 52.78]	[32.61- 79.86]
	Recycled	-	0.476	122.98	0.406	123.83 (+74%)
Marine Eutrophication (kg N-Eq)	Virgin [1-2]	0.89	[0.004- 0.041]	[0.003- 0.009]	[0.09-1.30]	[1.02-2.20]
	Recycled	-	0.009	0.011	0.008	0.029 (-97%)
Water Depletion (m <sup>3</sup> )	Virgin [1-2]	37.3669	[0.005- 0.028]	[0.008- 0.112]	[0.064- 0.439]	[37.46- 37.92]
	Recycled	-	0.006	0.546	0.006	0.56 (-99%)

depletion), which corresponds to the categories that are considered essential for DRAM. In each of the categories there is a reduction of at least 97% compared to the impact produced by the virgin scenario. For the Ion Radiation category, however, the recycling system has a greater impact than the virgin scenario (best scenario in this case). In the recycling scenario, the amount of ion radiation equals approximately 2.8 times the emissions of the virgin scenario.

Figure 3 presents the impacts obtained for each scenario studied. As can be observed, the distributed recycling system to produce 3D filament (Recycling Scenario or Scenario 3) is the least impactful scenario, taking into account the five categories considered pertinent to DRAM.

The result shows that, in each impact category, the recycling scenario pollutes less than 5% compared to the two scenarios that integrate the production of virgin plastic. In other words, the recycling system to produce 3D filament manages to reduce emissions and impacts by at least 95%.

Regarding the other impact categories present in the ReCiPe methodology, it is necessary to emphasize that the recycling system has a significant impact on the category that measures the radiation of ions equivalent to Uranium 235. As can be seen in Figure 3, even Scenario

370 3, which takes recycling into account, reaches a high radioactive emission compared to the  
 371 scenarios that use virgin filament. Scenario 1 represents approximately 25% of the impact  
 372 produced by the recycling system, while Scenario 2 (pessimistic scenario of virgin filament)  
 373 represents approximately 60% of the impact produced by Scenario 3.

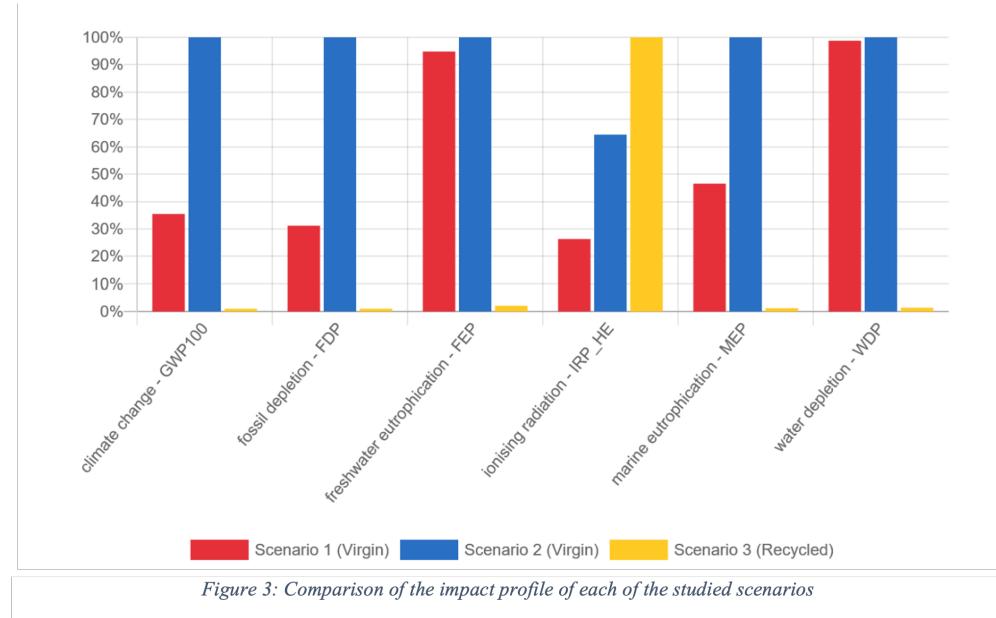


FIGURE 3: Comparison of the impact profile of each of the studied scenarios

#### 374 4.4. Interpretation and Recommendations

##### 375 4.4.1. Sensitivity analysis

376 In order to evaluate the response of each of the systems to context variations, a sensitivity  
 377 analysis has been conducted. The sensitivity analysis consists of analyzing the results of the  
 378 system against the variation of one of the parameters. This activity allows us to identify  
 379 the key contextual parameters that affect the results of the evaluation. These results can  
 380 be favorable as well as negative, being able to identify the effect called transfer of impacts.  
 381 This effect consists in the fact that while in a specific impact category a reduction in the  
 382 level of emissions is achieved through a change of parameters (technology, raw material,  
 383 process, type of energy), at the same time there is one or multiple impacts in which an  
 384 increase in the emissions or impacts produced can be reflected. This effect (impact transfer)  
 385 is fundamental when proposing improvements in products or services. In this study, to have a  
 386 better visualization of the transfer of impacts, the complete set of impacts evaluated by the  
 387 ReCiPe (H) methodology have been taken into account.

388 4.4.1.1. Location of PLA production. A recent project by Total Corbion has been proposed in  
 389 Grandpuits (Seine-et-Marne). The purpose of this project is to build a polylactic acid (PLA)  
 390 production plant with a capacity of up to 100,000 tons per year. This first European plant is  
 391 to be installed in France<sup>4</sup>. Considering this, a sensitivity analysis has been performed for this  
 392 scenario. In this new scenario, the PLA production facility is situated in France at Total's  
 393 Grandpuits facility.

4. <https://www.usinenouvelle.com/article/bientot-du-pla-made-in-france.N1216857>

394     Figure 4 shows the result of the change in the location of the PLA production plant  
 395 (from the United States to France). To represent the sensitivity of the system, only the first  
 396 scenario was considered because it has a logistics chain with less impact than Scenario 2.  
 397 Thus, it is interesting to see the changes with respect to this scenario. As can be observed,  
 398 the result has a relatively small variation. Even though an improvement was obtained in  
 399 some categories, such as particle formation, use of fossil raw materials, or ozone depletion,  
 400 the result is relatively small. The impact was not greatly reduced with respect to Scenario 1  
 401 because PLA production is the main source of impact in this scenario.

402     In conclusion, it was observed that there is a slight improvement in the environmental  
 403 performance of the production system, but it is not sufficiently attractive with respect to the  
 404 level of impact obtained in the recycling of plastic to produce filament. To obtain a significant  
 405 improvement, it is necessary to continue optimizing the PLA production process, which is  
 406 enabled mainly by technological advances. This can be a great solution only if it manages to  
 407 identify a slight transfer of impacts.

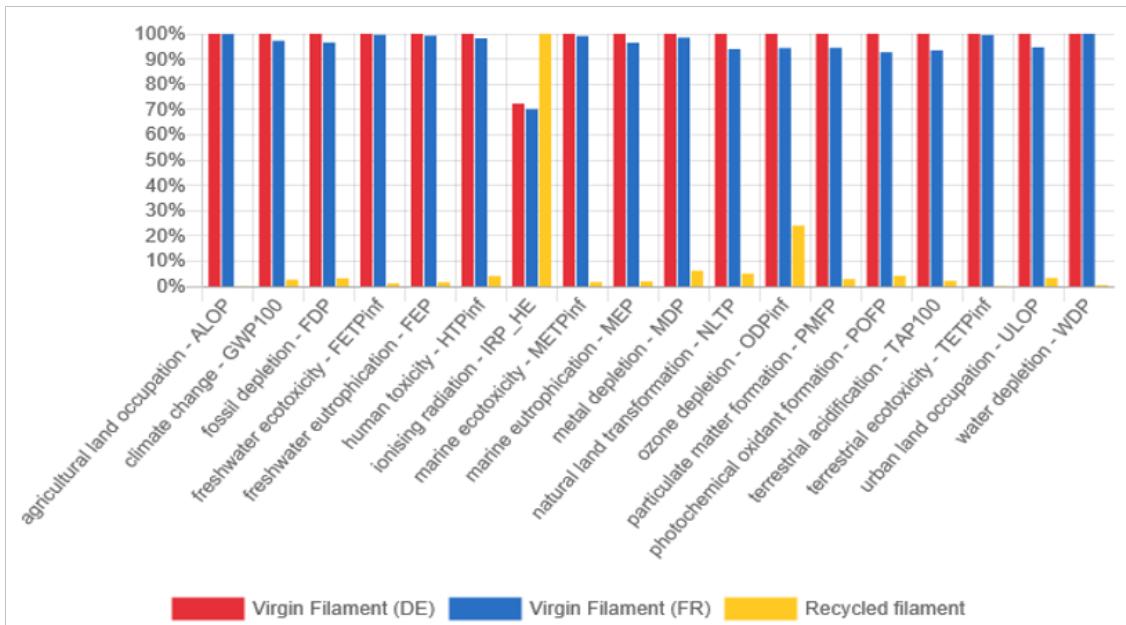


FIGURE 4: Comparison of the impact profile of each of the studied scenarios

408     *4.4.1.2. Energy Source.* The results presented in Section 4.3.1.3 have shown that distributed  
 409 plastic recycling to produce filament demonstrates broad environmental advantages compared  
 410 to production from virgin plastic. In almost all impact categories it had an impact of less  
 411 than 5% of the impact caused by virgin filament production systems, except in the category  
 412 related to the emission of radioactive particles. These emissions are closely related to the  
 413 production of electricity from nuclear energy, which in France accounts for 77.5% of the total  
 414 energy produced in the country. Currently, the french electricity system produce is 77.7%  
 415 nuclear, 9.7% hydro power, 3.8% wind power, 3.5% natural gas, 2.2% coal, 1.5% solar PV,  
 416 1.3% biofuels and wastes, and 0.3% oil (Pereira and Marques, 2020). For this reason, it is key  
 417 to see the response of the system and the possible transfer of impacts when using other forms  
 418 of energy production, including mainly the use of clean energy (solar and wind). Figure 5  
 419 presents the environmental performance of the recycling system using three different types of  
 420 energy (nuclear, wind, and solar).

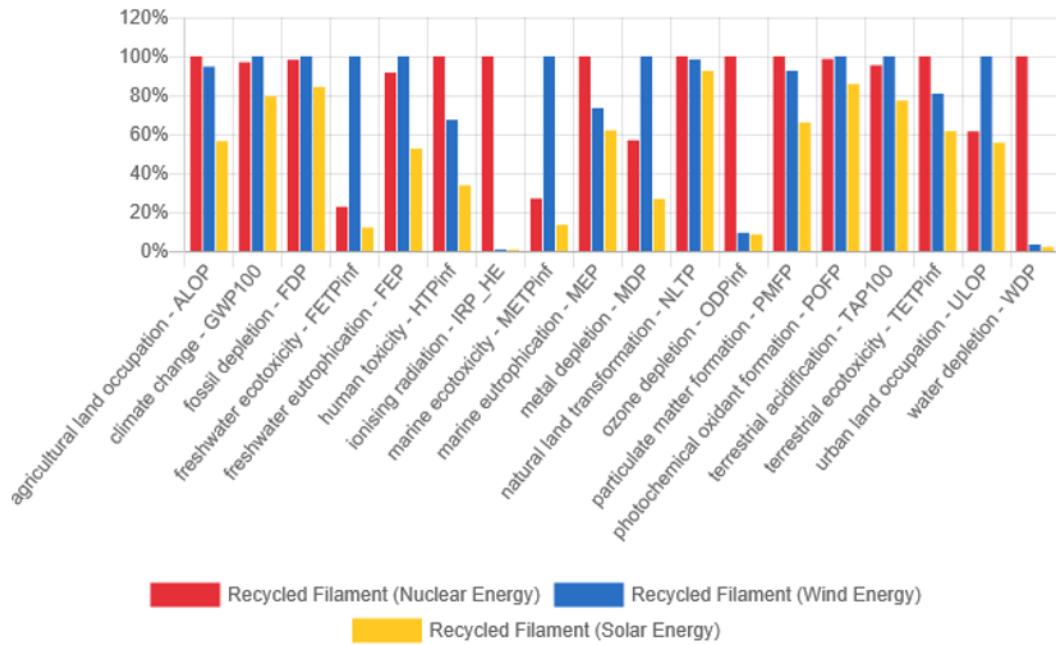


FIGURE 5: Sensitivity analysis respect to the type of energy used

421 As can be observed in Figure 5, solar energy and wind energy have different responses  
 422 with respect to the use of nuclear energy. On the one hand, the solar energy (shown in  
 423 yellow) considerably improves the environmental performance of the system, especially in the  
 424 category of radioactive emissions, which are reduced by approximately 98%. It is important  
 425 to remember that this category is the critical point in the comparison of the two filament  
 426 production systems. In addition, a considerable improvement can be observed in the categories  
 427 that consider ozone depletion and water use, with reductions of more than 70%. No transfer of  
 428 impacts is observed in any of the impacts evaluated. According to the impacts assessed, there  
 429 is no transfer of impacts to other categories, this being a more environmentally friendly option  
 430 than the use of nuclear energy. On the other hand, wind energy (shown in blue) also achieves  
 431 significant reductions in the categories of impacts related to radioactive ion emissions, ozone  
 432 depletion, and water use. However, on this occasion, a transfer of significant impacts can be  
 433 observed since the impact category measuring, for example, ecotoxicity in water (marine and  
 434 fresh) increases its impact by 80% with respect to the use of nuclear energy, while the need  
 435 for metals increases by 40%.

436 In conclusion, the use of solar energy may seem the best option among the energy sources  
 437 evaluated. This type of energy presents a circumstantial improvement in the critical point of  
 438 the use of nuclear energy without suffering a transfer of impacts. The use of wind energy does  
 439 not have the same result; although it manages to reduce radioactive emissions, the use of this  
 440 type of energy increases the toxicity present in the water, which can directly affect various  
 441 ecosystems as well as human health. To determine if this type of energy is suitable for the  
 442 recycled filament production system, it is necessary to deepen the comparison between these  
 443 two ways of producing electricity.

444 5. Discussion

445 Distributed recycling via additive manufacturing (DRAM) is been considered by different  
446 authors as an additional path to increase the low plastic recycling rates given the major  
447 democratization of material extrusion based systems ([Beltrán et al., 2021](#); [Pinho et al., 2020](#);  
448 [Wu et al., 2022](#)). Several researchers have studied this recycling approach from a technical and  
449 logistical perspective ([Mohammed et al., 2022](#); [Stefaniak et al., 2022](#); [Wu et al., 2022](#)). Other  
450 studies that evaluated the environmental impact of this recycling approach only took the  
451 recovery and recycling stages into consideration ([Kerdlap et al., 2021](#); [Kreiger et al., 2014](#);  
452 [Kreiger and Pearce, 2013](#)). However, an assessment of the positive and negative environmental  
453 impacts of implementing this plastic recycling approach with consideration for the whole chain  
454 (recovery, recycling, and use) had not been conducted, until now. In this study, a life cycle  
455 assessment has been conducted in order to evaluate the environmental impact of implementing  
456 a DRAM system to produce recycled PLA filament, compared to traditional virgin PLA  
457 filament production systems. In order to carry out this case study, a favorable context was  
458 defined in which a considerable amount of plastic is treated, 3D printing is widely used, and  
459 there is a dedicated space for plastic recycling via 3D printing.

460 The results of the environmental assessment of this system have shown that the recycling  
461 system for filament production reduces the impacts produced by the best scenario of filament  
462 production from virgin plastic by at least 97%. The categories of impacts considered were  
463 greenhouse gas emissions (climate change), consumption of fossil materials (fossil depletion),  
464 overfeeding of aquatic ecosystems (potential eutrophication), and water consumption (water  
465 depletion). On the other hand, there is a transfer of significant impacts that is not considered  
466 in the relevant impacts of the production system, since, due to the use of nuclear energy to  
467 produce electricity in France, the emissions of radioactive ions increased by 280%, which means  
468 that the recycling process has worse environmental performance in this category. Despite the  
469 assumptions made, the scenarios related to virgin filament production have a major drawback,  
470 which is that their most impactful or most influential phase in multiple categories is the  
471 production of plastic. For this reason, the change in the location of the production plant  
472 only produces a minor environmental improvement. This means that, in order to improve the  
473 environmental performance of these systems, it is essential to develop new technologies and  
474 optimize the polylactide acid production processes.

475 For the recycling system, the sensitivity analysis performed has shown that the integration  
476 of solar energy can greatly reduce the impacts produced using nuclear energy, making it an  
477 extremely viable alternative for the recycling system. Wind energy, on the other hand, has a  
478 significant transfer of impact to the toxicity present in different types of water, which does not  
479 allow us to define in the first instance whether it would be more convenient. In addition, the  
480 results showed that the DRAM approach is advantageous considering other energy sources  
481 (other than nuclear) that are used in other parts of the world. The environmental assessment  
482 carried out in this study extends the results obtained by Kreiger et al. ([2014](#)) and Kerdlap et  
483 al. ([2021](#)), showing, based on LCA indicators, the environmental benefits posed by distributed  
484 plastic recycling, and more specifically, by implementing a DRAM system. In addition, the  
485 environmental benefits are independent of the energy source considered. Therefore, this study  
486 indicates that, in environmental terms and under certain conditions, the implementation of  
487 DRAMs would have a positive impact on the area of application and could have positive  
488 impacts in other contexts. Most notably, to the best of our knowledge, this is the first study to  
489 investigate the multidimensional environmental impact of implementing DRAM. The results

490 show a huge potential, in environmental terms, of implementing DRAM and suggest the  
491 application of this recycling approach in different contexts, mainly due to the results obtained  
492 when considering various energy sources. However, this study is not exempt of limits to be  
493 considered in future works. For this reason, the following recommendations can be followed :

- 494 — In order to reduce the complexity of the system studied, in different hypotheses, such  
495 as in the recycling system, we considered only one material collected in a clean state  
496 and fixed demand from schools. However, in the virgin production system the entire  
497 supply and production chain was formulated through hypotheses. Future research could  
498 conduct an environmental assessment incorporating these complexities.
- 499 — This study is limited to the comparison of DRAM with virgin filament production. It  
500 would be interesting to evaluate the environmental performance of a DRAM system  
501 with respect to other possible life-ends for PLA, such as incineration, landfill, or even a  
502 system where virgin material is incorporated into the recycling process. This is because  
503 the mixture of virgin and recycled material allows for considerable improvement in  
504 filament properties and printing quality.
- 505 — Finally, this evaluation was carried out by placing the DRAM system in the specific  
506 context of a developed country. It could be interesting to perform the same analysis in  
507 developing countries, which currently have major problems in the treatment of plastic  
508 waste.

## 509 6. Conclusions

510 Using the LCA methodology, this work evaluated the environmental benefits of a distri-  
511 buted closed-loop supply chain network for plastic recycling using open-source 3D printing  
512 technologies in a specific context. The use of polylactic acid (PLA) in the context of Nancy,  
513 France considered in the analysis based on three scenarios (two virgin and one recycled). The  
514 impact categories studied were climate change, resources depletion (fossil and water) and  
515 eutrophication potential (freshwater and marine). The results shown that distributed plastic  
516 recycling to produce filament demonstrates broad environmental advantages compared to  
517 production from virgin plastic. The comparison shows a reduction of up to 97% in most of the  
518 impacts considered for the study. However, given the french electrical mix, the recycling system  
519 has a greater impact than the virgin scenario for the Ion Radiation category. Additionally,  
520 the sensitivity analysis suggested minor environmental benefits if the production of virgin  
521 PLA is placed from USA to France.

522 The results obtained by the application of the LCA methodology to the case study  
523 and its sensitivity analysis suggest the application of this recycling approach in various  
524 energy contexts (solar, wind, and nuclear), acting in parallel to the existing centralized plastic  
525 recycling networks in order to increase plastic recycling rates, which are currently low. It seems  
526 interesting for future works to reduce the assumptions used with respect to the production of  
527 virgin filament and to integrate the current complexity of carrying out the plastic recycling  
528 process. Furthermore, assessing the impacts of this system in various areas allows us to obtain  
529 a global vision of the performance of this system and to determine which context would be  
530 most favorable for its development.

## 531 7. Acknowledgements

532 This project has received funding from the European Union's Horizon 2020 research and  
533 innovation programme under the grant agreement No 869952 and from the ICEEL Carnot

<sup>534</sup> Institute in France under the reference « Everest Bio » project.

<sup>535</sup> **Declaration of Competing Interest**

<sup>536</sup> The authors declare that they have no known competing financial interests or personal  
<sup>537</sup> relationships that could have appeared to influence the work reported in this paper.

538 8. References

- 539 Alexandre, A., Cruz Sanchez, F.A., Boudaoud, H., Camargo, M., Pearce, J.M., 2020. Me-  
540 chanical Properties of Direct Waste Printing of Polylactic Acid with Universal Pel-  
541 lets Extruder : Comparison to Fused Filament Fabrication on Open-Source Desktop  
542 Three-Dimensional Printers. *3D Printing and Additive Manufacturing* 3dp.2019.0195.  
543 <https://doi.org/10.1089/3dp.2019.0195>
- 544 Andrade, A.L., Neal, M. a, 2009. Applications and societal benefits of plastics. *Philosophical*  
545 *transactions of the Royal Society of London. Series B, Biological sciences* 364, 1977–1984.  
546 <https://doi.org/10.1098/rstb.2008.0304>
- 547 Arena, U., Mastellone, M.L., Perugini, F., 2003. Life Cycle assessment of a plastic packaging  
548 recycling system. *The International Journal of Life Cycle Assessment* 8, 92–98. <https://doi.org/10.1007/BF02978432>
- 549 Beltrán, F.R., Arrieta, M.P., Moreno, E., Gaspar, G., Muneta, L.M., Carrasco-Gallego,  
550 R., Yáñez, S., Hidalgo-Carvajal, D., de la Orden, M.U., Urreaga, J.M., 2021. Technical  
551 evaluation of mechanical recycling of pla 3d printing wastes. *Polymers* 13. <https://doi.org/10.3390/polym13081247>
- 552 Bikas, H., Stavropoulos, P., Chryssolouris, G., 2016. Additive manufacturing methods and  
553 modelling approaches : A critical review. *The International Journal of Advanced Manufac-  
554 turing Technology* 83, 389–405. <https://doi.org/10.1007/s00170-015-7576-2>
- 555 Bishop, G., Styles, D., Lens, P.N.L., 2021. Environmental performance comparison of bioplastics  
556 and petrochemical plastics : A review of life cycle assessment (LCA) methodological  
557 decisions. *Resources, Conservation and Recycling* 168, 105451. <https://doi.org/10.1016/j.resconrec.2021.105451>
- 558 Bonnín Roca, J., Vaishnav, P., Laureijs, R.E., Mendonça, J., Fuchs, E.R.H., 2019. Tech-  
559 nology cost drivers for a potential transition to decentralized manufacturing. *Additive  
560 Manufacturing* 28, 136–151. <https://doi.org/10.1016/j.addma.2019.04.010>
- 561 Cañado, N., Lizundia, E., Akizu-Gardoki, O., Minguez, R., Lekube, B., Arrillaga, A., Iturron-  
562 dobeitia, M., 2022. 3D printing to enable the reuse of marine plastic waste with reduced  
563 environmental impacts. *Journal of Industrial Ecology* n/a. <https://doi.org/10.1111/jiec.13302>
- 564 Canopé, 2022. « FabLab à l'école » : un atelier de fabrication dans votre établissement [WWW  
565 Document]. URL <https://www.reseau-canope.fr/academie-de-nantes/atelier-canope-44-nantes/actualites/article/fablab-a-lecole-un-atelier-de-fabrication-dans-votre-etablissement-4.html> (accessed 9.20.2022).
- 566 Carlsson Reich, M., 2005. Economic assessment of municipal waste management systems—case  
567 studies using a combination of life cycle assessment (LCA) and life cycle costing (LCC).  
568 *Journal of Cleaner Production, Environmental Assessments and Waste Management* 13,  
569 253–263. <https://doi.org/10.1016/j.jclepro.2004.02.015>
- 570 Cerdas, F., Juraschek, M., Thiede, S., Herrmann, C., 2017. Life Cycle Assessment of 3D  
571 Printed Products in a Distributed Manufacturing System. *Journal of Industrial Ecology*  
572 21, S80–S93. <https://doi.org/10.1111/jiec.12618>
- 573 Confente, I., Scarpi, D., Russo, I., 2020. Marketing a new generation of bio-plastics products  
574 for a circular economy : The role of green self-identity, self-congruity, and perceived value.  
575 *Journal of Business Research* 112, 431–439. <https://doi.org/10.1016/j.jbusres.2019.10.030>
- 576 Corvellec, H., Stowell, A.F., Johansson, N., 2021. Critiques of the circular economy. *Journal*

- 584 of Industrial Ecology. <https://doi.org/10.1111/JIEC.13187>
- 585 Coskun, A., Metta, J., Bakırlioğlu, Y., Çay, D., Bachus, K., 2022. Make it a circular city :  
586 Experiences and challenges from European cities striving for sustainability through pro-  
587 moting circular making. Resources, Conservation and Recycling 185, 106495. <https://doi.org/10.1016/j.resconrec.2022.106495>
- 588 Cruz Sanchez, F.A., Boudaoud, H., Camargo, M., Pearce, J.M., 2020. Plastic recycling  
589 in additive manufacturing : A systematic literature review and opportunities for the  
590 circular economy. Journal of Cleaner Production 264, 121602. <https://doi.org/10.1016/j.jclepro.2020.121602>
- 591 Cruz Sanchez, F.A., Boudaoud, H., Hoppe, S., Camargo, M., 2017. Polymer recycling in an  
592 open-source additive manufacturing context : Mechanical issues. Additive Manufacturing  
593 17, 87–105. <https://doi.org/10.1016/j.addma.2017.05.013>
- 594 de Vargas Mores, G., Finocchio, C.P.S., Barichello, R., Pedrozo, E.A., 2018. Sustainability and  
595 innovation in the Brazilian supply chain of green plastic. Journal of Cleaner Production  
596 177, 12–18. <https://doi.org/10.1016/j.jclepro.2017.12.138>
- 597 Dehghanian, F., Mansour, S., 2009. Designing sustainable recovery network of end-of-life  
598 products using genetic algorithm. Resources, Conservation and Recycling 53, 559–570.  
599 <https://doi.org/10.1016/j.resconrec.2009.04.007>
- 600 Dekker, E., Zijp, M.C., van de Kamp, M.E., Temme, E.H.M., van Zelm, R., 2020. A taste  
601 of the new ReCiPe for life cycle assessment : Consequences of the updated impact  
602 assessment method on food product LCAs. Int J Life Cycle Assess 25, 2315–2324. <https://doi.org/10.1007/s11367-019-01653-3>
- 603 Despeisse, M., Baumers, M., Brown, P., Charnley, F., Ford, S.J., Garmulewicz, A., Knowles,  
604 S., Minshall, T.H.W., Mortara, L., Reed-Tsochas, F.P., Rowley, J., 2017. Unlocking value  
605 for a circular economy through 3D printing : A research agenda. Technological Forecasting  
606 and Social Change 115, 75–84. <https://doi.org/10.1016/j.techfore.2016.09.021>
- 607 European Commission, 2018. A european strategy for plastics in a circular economy, COM  
608 (2018). European Commission, Brussels. <https://doi.org/10.1021/acs.est.7b02368>
- 609 Filho, W.L., Salvia, A.L., Bonoli, A., Saari, U.A., Voronova, V., Klöga, M., Kumbhar,  
610 S.S., Olszewski, K., De Quevedo, D.M., Barbir, J., 2021. An assessment of attitudes  
611 towards plastics and bioplastics in Europe. Science of The Total Environment 755, 142732.  
612 <https://doi.org/10.1016/j.scitotenv.2020.142732>
- 613 Friedrich, D., 2020. How regulatory measures towards biobased packaging influence the  
614 strategic behaviour of the retail industry : A microempirical study. Journal of Cleaner  
615 Production 260, 121128. <https://doi.org/10.1016/j.jclepro.2020.121128>
- 616 Garmulewicz, A., Holweg, M., Veldhuis, H., Yang, A., 2018. Disruptive Technology as an  
617 Enabler of the Circular Economy : What Potential Does 3D Printing Hold ? California  
618 Management Review 60, 112–132. <https://doi.org/10.1177/0008125617752695>
- 619 Geyer, R., Jambeck, J.R., Law, K.L., 2017. Production, use, and fate of all plastics ever made.  
620 Science Advances 3, e1700782. <https://doi.org/10.1126/sciadv.1700782>
- 621 Giampietro, M., Funtowicz, S.O., 2020. From elite folk science to the policy legend of the  
622 circular economy. Environmental Science and Policy 109, 64–72. <https://doi.org/10.1016/j.envsci.2020.04.012>
- 623 Goedkoop, M., Heijungs, R., Huijbregts, M., 2009. Report I : Characterisation 132.
- 624 Gong, Y., Putnam, E., You, W., Zhao, C., 2020. Investigation into circular economy of  
625 plastics : The case of the UK fast moving consumer goods industry. Journal of Cleaner  
626 Production 244, 118941. <https://doi.org/10.1016/j.jclepro.2019.118941>

- 631 Gontard, N., David, G., Guilbert, A., Sohn, J., 2022. Recognizing the long-term impacts  
632 of plastic particles for preventing distortion in decision-making. *Nat Sustain* 5, 472–478.  
633 <https://doi.org/10.1038/s41893-022-00863-2>
- 634 Guinée, J.B., 2002. *Handbook on Life Cycle Assessment: Operational Guide to the ISO  
635 Standards*. Springer Science & Business Media.
- 636 Hamilton, L.A., Steven, F., 2019. *Plastic & Climate: The hidden costs of a plastic planet |  
637 Policy Commons*. Center for International Environmental Law.
- 638 Hart, K.R., Frketic, J.B., Brown, J.R., 2018. Recycling meal-ready-to-eat (MRE) pouches into  
639 polymer filament for material extrusion additive manufacturing. *Additive Manufacturing*  
640 21, 536–543. <https://doi.org/10.1016/j.addma.2018.04.011>
- 641 Hassini, E., Surti, C., Searcy, C., 2012. A literature review and a case study of sustainable  
642 supply chains with a focus on metrics. *International Journal of Production Economics,  
643 Sustainable Development of Manufacturing and Services* 140, 69–82. <https://doi.org/10.1016/j.ijpe.2012.01.042>
- 644 Hopewell, J., Dvorak, R., Kosior, E., 2009. Plastics recycling : Challenges and opportunities.  
645 Philosophical Transactions of the Royal Society B : Biological Sciences 364, 2115–2126.  
646 <https://doi.org/10.1098/rstb.2008.0311>
- 647 Hunt, E.J., Zhang, C., Anzalone, N., Pearce, J.M., 2015. Polymer recycling codes for distributed  
648 manufacturing with 3-D printers. *Resources, Conservation and Recycling* 97, 24–30. <https://doi.org/10.1016/j.resconrec.2015.02.004>
- 649 Huysveld, S., Hubo, S., Ragaert, K., Dewulf, J., 2019. Advancing circular economy benefit  
650 indicators and application on open-loop recycling of mixed and contaminated plastic  
651 waste fractions. *Journal of Cleaner Production* 211, 1–13. <https://doi.org/10.1016/j.jclepro.2018.11.110>
- 652 IES, 2010. *International Reference Life Cycle Data System (ILCD) Handbook :general guide  
653 for life cycle assessment : Detailed guidance*. Publications Office of the European Union,  
654 LU.
- 655 Iles, A., Martin, A.N., 2013. Expanding bioplastics production : Sustainable business innovation  
656 in the chemical industry. *Journal of Cleaner Production* 45, 38–49. <https://doi.org/10.1016/j.jclepro.2012.05.008>
- 657 Jaafarnia, M., Shende, A., Boroomand, S., 2021. The Redesign Decision-Making Cycle : A  
658 perspective on predicting prosumer household 3D printer waste. *Sustainable Production  
659 and Consumption* 27, 1349–1356. <https://doi.org/10.1016/j.spc.2021.03.012>
- 660 Jambeck, J.R., Geyer, R., Wilcox, C., Siegler, T.R., Perryman, M., Andrade, A., Narayan,  
661 R., Law, K.L., 2015. Plastic waste inputs from land into the ocean. *Science* 347, 768–771.  
662 <https://doi.org/10.1126/science.1260352>
- 663 Justino Netto, J.M., Idogava, H.T., Frezzatto Santos, L.E., Silveira, Z. de C., Romio, P.,  
664 Alves, J.L., 2021. Screw-assisted 3D printing with granulated materials : A systematic  
665 review. *The International Journal of Advanced Manufacturing Technology* 1–17. <https://doi.org/10.1007/s00170-021-07365-z>
- 666 Kasmi, F., Osorio, F., Dupont, L., Marche, B., Camargo, M., 2021. Innovation Spaces as  
667 Drivers of Eco-innovations Supporting the Circular Economy : A Systematic Literature  
668 Review. *Journal of Innovation Economics & Management Prépublica, Ij-XLII*. <https://doi.org/10.3917/jie.pr1.0113>
- 669 Kellens, K., Baumers, M., Gutowski, T.G., Flanagan, W., Lifset, R., Duflou, J.R., 2017.  
670 Environmental Dimensions of Additive Manufacturing : Mapping Application Domains  
671 and Their Environmental Implications. *Journal of Industrial Ecology* 21, S49–S68. <https://doi.org/10.1007/s10247-017-1132-0>
- 672
- 673
- 674
- 675
- 676
- 677

- 678       [//doi.org/10.1111/jiec.12629](https://doi.org/10.1111/jiec.12629)
- 679 Kerdlap, P., Purnama, A.R., Low, J.S.C., Tan, D.Z.L., Barlow, C.Y., Ramakrishna, S.,  
680       2021. Comparing the environmental performance of distributed versus centralized plastic  
681       recycling systems : Applying hybrid simulation modeling to life cycle assessment. *Journal  
682       of Industrial Ecology*. <https://doi.org/10.1111/jiec.13151>
- 683 Kostakis, V., 2013. At the Turning Point of the Current Techno-Economic Para-digm :  
684       Commons-Based Peer Production , Desktop Manufac-turing and the Role of Civil Society  
685       in the Perezian Frame-work 11, 173–190.
- 686 Kostakis, V., Latoufis, K., Liarokapis, M., Bauwens, M., 2018. The convergence of digital  
687       commons with local manufacturing from a degrowth perspective : Two illustrative cases.  
688       *J. Clean. Prod.* 197, 1684–1693. <https://doi.org/10.1016/j.jclepro.2016.09.077>
- 689 Kreiger, M.a., Mulder, M.L., Glover, A.G., Pearce, J.M., 2014. Life cycle analysis of distributed  
690       recycling of post-consumer high density polyethylene for 3-D printing filament. *Journal of  
691       Cleaner Production* 70, 90–96. <https://doi.org/10.1016/j.jclepro.2014.02.009>
- 692 Kreiger, M., Anzalone, G.C., Mulder, M.L., Glover, A., Pearce, J.M., 2013. Distributed  
693       Recycling of Post-Consumer Plastic Waste in Rural Areas. *MRS Proceedings* 1492, 91–96.  
694       <https://doi.org/10.1557/opl.2013.258>
- 695 Kreiger, M., Pearce, J.M., 2013. Environmental Impacts of Distributed Manufacturing from  
696       3-D Printing of Polymer Components and Products. *MRS Proceedings* 1492, 85–90.  
697       <https://doi.org/10.1557/opl.2013.319>
- 698 Kumar, R., Verma, A., Shome, A., Sinha, R., Sinha, S., Jha, P.K., Kumar, R., Kumar, P.,  
699       Shubham, Das, S., Sharma, P., Vara Prasad, P.V., 2021. Impacts of Plastic Pollution  
700       on Ecosystem Services, Sustainable Development Goals, and Need to Focus on Circular  
701       Economy and Policy Interventions. *Sustainability* 13, 9963. <https://doi.org/10.3390/su13179963>
- 702 López, V.M., Carou, D., Cruz S, F.A., 2022. Feasibility study on the use of recycled materials  
703       for prototyping purposes : A comparative study based on the tensile strength. *Proceedings  
704       of the Institution of Mechanical Engineers, Part B : Journal of Engineering Manufacture*  
705       09544054221113378. <https://doi.org/10.1177/09544054221113378>
- 706 Ma, X., Park, C., Moultrie, J., 2020. Factors for eliminating plastic in packaging : The  
707       European FMCG experts' view. *Journal of Cleaner Production* 256, 120492. <https://doi.org/10.1016/j.jclepro.2020.120492>
- 708 Maga, D., Hiebel, M., Thonemann, N., 2019. Life cycle assessment of recycling options for  
709       polylactic acid. *Resources, Conservation and Recycling* 149, 86–96. <https://doi.org/10.1016/j.resconrec.2019.05.018>
- 710 Mahmud, R., Moni, S.M., High, K., Carbajales-Dale, M., 2021. Integration of techno-economic  
711       analysis and life cycle assessment for sustainable process design – A review. *Journal of  
712       Cleaner Production* 317, 128247. <https://doi.org/10.1016/j.jclepro.2021.128247>
- 713 Matthews, C., Moran, F., Jaiswal, A.K., 2020. A Review on European Union's Strategy  
714       for Plastics in a Circular Economy and its Impact on Food Safety. *Journal of Cleaner  
715       Production* 283, 125263. <https://doi.org/10.1016/j.jclepro.2020.125263>
- 716 Mohammed, M., Wilson, D., Gomez-Kervin, E., Petsiuk, A., Dick, R., Pearce, J.M., 2022.  
717       Sustainability and feasibility assessment of distributed E-waste recycling using additive  
718       manufacturing in a Bi-continental context. *Additive Manufacturing* 50, 102548. <https://doi.org/10.1016/j.addma.2021.102548>
- 719 Paletta, A., Leal Filho, W., Balogun, A.L., Foschi, E., Bonoli, A., 2019. Barriers and challenges  
720       to plastics valorisation in the context of a circular economy : Case studies from Italy. *Journal  
721       of Industrial Ecology*. <https://doi.org/10.1111/jiec.13151>
- 722
- 723
- 724

- of Cleaner Production 241, 118149. <https://doi.org/10.1016/j.jclepro.2019.118149>
- Pavlo, S., Fabio, C., Hakim, B., Mauricio, C., 2018. 3D-Printing Based Distributed Plastic Recycling : A Conceptual Model for Closed-Loop Supply Chain Design, in : 2018 IEEE International Conference on Engineering, Technology and Innovation (ICE/ITMC). IEEE, pp. 1–8. <https://doi.org/10.1109/ICE.2018.8436296>
- Pazienza, P., De Lucia, C., 2020. The EU policy for a plastic economy : Reflections on a sectoral implementation strategy. Business Strategy and the Environment 29, 779–788. <https://doi.org/10.1002/bse.2445>
- Pennington, D.W., Potting, J., Finnveden, G., Lindeijer, E., Jolliet, O., Rydberg, T., Rebitzer, G., 2004. Life cycle assessment Part 2 : Current impact assessment practice. Environment International 30, 721–739. <https://doi.org/10.1016/j.envint.2003.12.009>
- Pereira, D.S., Marques, A.C., 2020. Could electricity demand contribute to diversifying the mix and mitigating CO<sub>2</sub> emissions ? A fresh daily analysis of the French electricity system. Energy Policy 142, 111475. <https://doi.org/10.1016/j.enpol.2020.111475>
- Petersen, E., Pearce, J., 2017. Emergence of Home Manufacturing in the Developed World : Return on Investment for Open-Source 3-D Printers. Technologies 5, 7. <https://doi.org/10.3390/technologies5010007>
- Pinho, A.C., Amaro, A.M., Piedade, A.P., 2020. 3D printing goes greener : Study of the properties of post-consumer recycled polymers for the manufacturing of engineering components. Waste Management 118, 426–434. <https://doi.org/10.1016/j.wasman.2020.09.003>
- Pinto Da Costa, J., Rocha-Santos, T., Duarte, A.C., Chemistry, D. of, CESAM, Aveiro, U. of, Portugal, 2020. **The environmental impacts of plastics and micro-plastics use, waste and pollution: EU and national measures.**
- Plastic Europe -, 2020. Plastics – the Facts 2020 An analysis of European Production demand and waste data [WWW Document]. URL <https://plasticseurope.org/knowledge-hub/plastics-the-facts-2020/> (accessed 3.7.2022).
- Pryshlakivsky, J., Searcy, C., 2021. Life Cycle Assessment as a decision-making tool : Practitioner and managerial considerations. Journal of Cleaner Production 309, 127344. <https://doi.org/10.1016/j.jclepro.2021.127344>
- Quinlan, H.E., Hasan, T., Jaddou, J., Hart, A.J., 2017. Industrial and Consumer Uses of Additive Manufacturing : A Discussion of Capabilities, Trajectories, and Challenges. Journal of Industrial Ecology 21, S15–S20. <https://doi.org/10.1111/jiec.12609>
- Saade, M.R.M., Yahia, A., Amor, B., 2020. How has LCA been applied to 3D printing ? A systematic literature review and recommendations for future studies. Journal of Cleaner Production 244, 118803. <https://doi.org/10.1016/j.jclepro.2019.118803>
- Santander, P., Cruz Sanchez, F.A., Boudaoud, H., Camargo, M., 2020. Closed loop supply chain network for local and distributed plastic recycling for 3D printing : A MILP-based optimization approach. Resources, Conservation and Recycling 154, 104531. <https://doi.org/10.1016/j.resconrec.2019.104531>
- Shi, H., Yu, D., Yin, L., Sui, Y., Liu, Y., Qiao, S., Wang, W., Zheng, W., Ding, D., 2022. Source-sink process of microplastics in watershed-estuary-offshore system. Journal of Cleaner Production 338, 130612. <https://doi.org/10.1016/J.JCLEPRO.2022.130612>
- Singh, N., Hui, D., Singh, R., Ahuja, I.P.S., Feo, L., Fraternali, F., 2017. Recycling of plastic solid waste : A state of art review and future applications. Composites Part B : Engineering 115, 409–422. <https://doi.org/10.1016/j.compositesb.2016.09.013>
- Stefaniak, A.B., Bowers, L.N., Cottrell, G., Erdem, E., Knepp, A.K., Martin, S.B., Pretty, J.,

- 772 Duling, M.G., Arnold, E.D., Wilson, Z., Krider, B., Fortner, A.R., LeBouf, R.F., Virji,  
773 M.A., Sirinterlikci, A., 2022. Towards sustainable additive manufacturing : The need  
774 for awareness of particle and vapor releases during polymer recycling, making filament,  
775 and fused filament fabrication 3-D printing. Resources, Conservation and Recycling 176,  
776 105911. <https://doi.org/10.1016/j.resconrec.2021.105911>
- 777 Thompson, R.C., Swan, S.H., Moore, C.J., vom Saal, F.S., 2009. Our plastic age. Philosophical  
778 Transactions of the Royal Society B : Biological Sciences 364, 1973–1976. <https://doi.org/10.1098/rstb.2009.0054>
- 780 Vink, E.T.H., Davies, S., 2015. Life Cycle Inventory and Impact Assessment Data for 2014  
781 Ingeo™ Polylactide Production. Industrial Biotechnology 11, 167–180. <https://doi.org/10.1089/ind.2015.0003>
- 783 Vink, E.T.H., Rábago, K.R., Glassner, D.A., Gruber, P.R., 2003. Applications of life cycle  
784 assessment to NatureWorks™ polylactide (PLA) production. Polymer Degradation and  
785 Stability 80, 403–419. [https://doi.org/10.1016/S0141-3910\(02\)00372-5](https://doi.org/10.1016/S0141-3910(02)00372-5)
- 786 Vuori, L., Ollikainen, M., 2022. How to remove microplastics in wastewater ? A cost-effectiveness  
787 analysis. Ecological Economics 192, 107246. <https://doi.org/10.1016/J.ECOLECON.2021.107246>
- 789 Wang, C., Huang, R., Sun, R., Yang, J., Dionysiou, D.D., 2022. Microplastics separation  
790 and subsequent carbonization : Synthesis, characterization, and catalytic performance of  
791 iron/carbon nanocomposite. Journal of Cleaner Production 330, 129901. <https://doi.org/10.1016/J.JCLEPRO.2021.129901>
- 793 Woern, A., Pearce, J., 2017. Distributed Manufacturing of Flexible Products : Technical  
794 Feasibility and Economic Viability. Technologies 5, 71. <https://doi.org/10.3390/technologies5040071>
- 796 Wu, H., Mehrabi, H., Karagiannidis, P., Naveed, N., 2022. Additive manufacturing of recycled  
797 plastics : Strategies towards a more sustainable future. Journal of Cleaner Production 335,  
798 130236. <https://doi.org/10.1016/j.jclepro.2021.130236>
- 799 Zhang, J., Wang, X., Xue, W., Xu, L., Ding, W., Zhao, M., Liu, S., Zou, G., Chen, Y.,  
800 2022. Microplastics pollution in soil increases dramatically with long-term application of  
801 organic composts in a wheat–maize rotation. Journal of Cleaner Production 356, 131889.  
802 <https://doi.org/10.1016/J.JCLEPRO.2022.131889>
- 803 Zhong, S., Pearce, J.M., 2018. Tightening the loop on the circular economy : Coupled distributed  
804 recycling and manufacturing with recyclebot and RepRap 3-D printing. Resources,  
805 Conservation and Recycling 128, 48–58. <https://doi.org/10.1016/j.resconrec.2017.09.023>

## Annex 1 Table of reference flows

*Scenario 1 Virgin filament System:*

Phase	Process	Transport (km)	Transport Type	weight (kg)	weight (t)	t*km
Transport to the filament producer	Plant-Port	756	transport, freight, lorry >32 metric ton, EURO6	1	0,001	0,756
	Port-Port	5.774	Container ship	1	0,001	5,774326
	Port-Plant	558	transport, freight, lorry >32 metric ton, EURO6	1	0,001	0,558

Phase	Machine	Process	Flux	Rate used (kg/h)	Puissance (kw)	Temps d'utilisation (h)	Energie Consomation (kwh)
Filament Product	PEEK 3d Printer Filament Production Line	Extrusion	électricité	20	15	0,05	0,75
				25	15	0,04	0,6

Phase	Process	Transport (km)	Transport Type	weight (kg)	weight (t)	t*km
Filament Transport to the Client	Plant-Client	280	small cargo vehicle	1	0,001	0,28

*Scenario 2 Virgin filament System:*

Phase	Process	Transport (km)	Transport Type	weight (kg)	weight (t)	t*km
Transport to the filament producer	Plant-Plan	645	transport, freight, lorry >32 metric ton, EURO6	2,1	0,0021	1,3545

Phase	Machine	Process	Flux	Rate used (kg/h)	Puissance (kw)	Temps d'utilisation (h)	Energie Consomation (kwh)
Filament Product	PEEK 3d Printer Filament Production Line	Extrusion	électricité	20	15	0,05	0,75
				25	15	0,04	0,6

Phase	Process	Transport (km)	Transport Type	weight (kg)	weight (t)	t*km
filament Transport to the client	Plant-Airport	5	transport, freight, lorry >32 metric ton, EURO6	2	0,002	0,01
	Airport-Airport	6.971	Airplane	2	0,002	13,942
	Airport-client	152	Cargo truck	2	0,002	0,304

*Scenario 3 Recycled filament system:*

Phase	Machine	Process	Flow	Power (kw)	Time of Use (h)	Energie Consomation (kwh)		
					Min	Max	Min	Max
Production Pellets	Retsch SM 300	Size reduction	Electricity	3	0,05	0,08	0,15	0,24
Filament Product	Nostek Xcalibur	Extrusion	Electricity	1,6	0,3	1	0,48	1,6

Phase	Transport(km)	Process	Transport type	Weight (fonctional unit) (kg)	Weigth (t)	t*km
Collection/ Delivey	25,52	Recovery Transport	Light Commercial Vehicle	1	0,001	0,02552
		Produit Transport		1	0,001	0,02552

*Transport route for the recycling scenarios:*

