



MICHELIN AIRCRAFT TIRE CARE & SERVICE MANUAL



Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

For

MICHELIN® AIRCRAFT TIRES AND TUBES

Commercial

Regional

General Aviation

Military

Document

MAT-CSM 32-45-01

Revision

D

Date

15 December 2011

The information contained herein is PROPRIETARY to Michelin. It is intended for the benefit and use of owners and maintenance personnel of Michelin Aircraft Tires.

Contact Michelin for reproduction authorization.

Reproduction for other commercial purpose is not permitted.

Important Note: Any copy of this document may not be the updated document currently in effect.

The current version is located on the Michelin aircraft tire website: www.airmichelin.com.

This document, MAT-CSM 32-45-01, Revision D supersedes
all previous Aircraft Tire Care and Service Manuals.

Revision History:

<u>Document</u>	<u>Revision</u>	<u>Date</u>
MAT-CSM 01	C	2001
MAT-CSM 95	B	1995
MAT-CSM 95	A	1995
MAINT-0013	Original	1991



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

TABLE OF CONTENTS

SUBJECT TITLE	PAGE
INTRODUCTION	1
1. General	1
2. Installation Approval	1
3. Warnings for the Full Manual	1
4. Related Source Documents	2
5. Related Source Organizations	2
6. Michelin Contacts	3
7. Cage Code	4
CHAPTER 1 AIRCRAFT TIRE DESCRIPTION/CONSTRUCTION	101
1. General	101
2. Tire Zones	102
3. Aircraft Tire Construction (Bias and Radial)	103
4. Components Unique to MICHELIN® Radial Aircraft Tires	104
5. Components Unique to MICHELIN® Bias Aircraft Tires	105
6. Sidewall Venting	107
7. Chine Tires	109
CHAPTER 2 AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (Branding)	201
1. Tire Terminology	201
2. Tire Sizes	201
3. Tire Markings (Branding)	202
4. Retread Markings	211
5. Tube Markings	213
CHAPTER 3 RECEIVING AND STORING AIRCRAFT TIRES	301
1. Handling of Tires and Tubes	301
2. Storage of Unmounted Tires and Tubes	303
CHAPTER 4 MOUNTING INSTRUCTIONS (Assembly)	401
1. WARNINGS and NOTES for This Chapter	401
2. Materials	402
3. Tools, Fixtures and Equipment	403
4. Pre-Assembly Checklist for the Tire/Wheel Assembly (Hub)	404
5. Mounting (Assembly) – Tubeless Tires	407
6. Mounting (Assembly) – Tube-Type Tires	409
7. Inflation of a Tire/Wheel Assembly to Operational Pressure	411



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

TABLE OF CONTENTS

CHAPTER 4 MOUNTING INSTRUCTIONS (Assembly)	<i>Continued</i>
8. Pressure Retention Check (Leak Check) – After Mounting	412
9. Investigation for the Cause of Pressure Loss	419
10. Transportation of an Inflated Tire/Wheel Assembly	420
11. Storage of an Inflated Tire/Wheel Assembly	421
12. Periodic Re-inspection of an Inflated Tire	422
13. Mounting the Tire/Wheel Assembly on the Aircraft	422
CHAPTER 5 OPERATION ON AIRCRAFT	501
1. Proper Inflation Pressure Maintenance	501
2. WARNINGS, CAUTIONS, and NOTES for This Chapter	501
3. Daily Pressure Check	502
4. Measure the Pressure When Tires Are "Cold"	503
5. Maintenance Action	504
6. Hot Tire Pressure Checks	506
7. Normal Wear Removal Criteria	506
8. Tire Damage to the Tread	508
9. Tire Damage to the Sidewall	519
10. Operating Conditions and Considerations	522
11. Matching and Mixability of Aircraft Tires	528
12. Tire Creep	529
13. Static Discharge	529
14. Tire Marking Tools	529
15. Military Arresting Cables	529
CHAPTER 6 DISMOUNTING (Disassembly)	601
1. General	601
2. WARNINGS and CAUTIONS for This Chapter	601
3. Track the Reasons for Tire Removal	601
4. Tools, Fixtures, and Equipment	602
5. Disassembly (Dismounting) of the Tire From the Wheel	606
6. Troubleshooting Disassembly (Dismounting) Issues	609
7. Tire Inspection After Dismounting	611
CHAPTER 7 RETREAD/REPAIR	701
1. General	701
2. Retreading Aircraft Tires	702
3. Repairing Aircraft Tires	702



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

INTRODUCTION

1. General

This manual is presented as a guide to help aircraft owners and maintenance personnel obtain maximum service life from their MICHELIN® aircraft tires. Unless specifically noted otherwise, it applies to radial and bias tires, both new and retreaded. Topics include:

- Aircraft tire description and terminology
- Storage and handling
- Mounting, inflation, and dismounting
- In-service procedures including inflation pressure maintenance
- Troubleshooting guidelines

This manual is intended to supplement the specific instructions issued by aircraft and wheel manufacturers. These include the Pilot's Operating Handbook/Airplane Flight Manual (POH/AFM), Aircraft Maintenance Manuals (AMM), and Component Maintenance Manuals (CMM). Any user of this manual who finds an apparent conflict between this manual and manufacturer guidelines should contact their Michelin representative.

The use of MICHELIN® Aircraft tires on ground vehicles is not recommended. Aircraft tires are designed and manufactured for use only on aircraft. Michelin shall not be responsible for any loss or damage caused by unauthorized use of MICHELIN® Aircraft tires.

Carefully read and obey all **WARNING** and **CAUTION** statements given in this manual.

- A **WARNING** is given to prevent personal injury or when an action can affect safety of flight.
- A **CAUTION** is given to prevent damage to equipment or parts.
- A **NOTE** is used to provide information to make a task easier.

2. Installation Approval

The existence of an Airworthiness approval does not automatically constitute the authority to install and use the tire on an airplane. The conditions and tests required for Airworthiness approval of an aircraft tire are minimum performance standards. It is the responsibility of those desiring to install an aircraft tire on a specific type or class of airplane to determine that the airplane operating conditions are within the capacity of the tire demonstrated in accordance with the Airworthiness Standards.

3. Warnings for the Full Manual

WARNING: AIRCRAFT TIRE AND WHEEL ASSEMBLIES MAY OPERATE UNDER HIGH PRESSURES IN ORDER TO CARRY THE LOADS IMPOSED ON THEM. THEY SHOULD BE TREATED WITH THE SAME RESPECT THAT ANY OTHER HIGH PRESSURE VESSEL WOULD BE GIVEN.

WARNING: AIRCRAFT TIRES IN AMBIENT TEMPERATURE CAN BE OPERATED UP TO OR AT RATED INFLATION PRESSURE. EXTREMELY HIGH INFLATION PRESSURES MAY CAUSE THE AIRCRAFT WHEEL OR TIRE TO EXPLODE OR BURST, WHICH MAY RESULT IN SERIOUS OR FATAL BODILY INJURY.

WARNING: AIRCRAFT TIRES MUST ALWAYS BE INFLATED WITH A PROPERLY REGULATED INFLATION SOURCE. INFLATING WITHOUT A PRESSURE REGULATOR PRESENTS A RISK OF PERSONAL INJURY AND/ OR DAMAGE TO EQUIPMENT. DIRECT HIGH PRESSURE SHOULD NEVER BE USED. EXTREMELY HIGH INFLATION PRESSURES MAY CAUSE THE AIRCRAFT WHEEL OR TIRE TO EXPLODE OR BURST, WHICH MAY RESULT IN SERIOUS OR FATAL BODILY INJURY.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

INTRODUCTION

4. Related Source Documents

- 4.1. Title 14 of the Code of Federal Regulations (14 CFR)
 - 4.1.1. Part 21, subpart O, Technical Standard Order Authorizations
- 4.2. FAA AC 145-4, Inspection, Retread, Repair and Alterations of Aircraft Tires
- 4.3. Technical Standard Orders
 - 4.3.1. FAA TSO-C62 (current), Aircraft Tires
 - 4.3.2. ETSO-C62 (current), Aircraft Tires
- 4.4. Airworthiness Directives
 - 4.4.1. AD 87-08-09, Airbus Industrie, Boeing, British Aerospace, Lockheed, McDonnell Douglas; Specified Models
- 4.5. Industry Documents
 - 4.5.1. RMA Aircraft Tire Service Bulletins
 - 4.5.1.1. Aircraft Tire Recommended Operating Inflation Pressure Maintenance Criteria
 - 4.5.1.2. Use of Aircraft Tires and Wheels in Other Than Aircraft Service
 - 4.5.1.3. Aircraft Tire and Tube Storage Recommendations
 - 4.5.1.4. Aircraft Tire Bursts
 - 4.5.1.5. Aircraft Tire/Wheel Compatibility
 - 4.5.1.6. Interchangeability/Mixing of Aircraft Radial and Bias Tires
 - 4.5.1.7. Aircraft Tire Conductivity
 - 4.5.2. SAE-ARP 4834, Aircraft Tire Retreading Practice – Bias and Radial
 - 4.5.3. SAE-ARP 5265, Minimum Operational and Maintenance Responsibilities for Aircraft Tire Usage

5. Related Source Organizations

- The European Tyre and Rim Technical Organisation (ETRTO) (www.etrto.org)
- The Tire and Rim Association, Inc. (T&RA) (www.us-tra.org)
- Rubber Manufacturers Association (RMA) (www.rma.org)
- SAE International (www.sae.org)

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

INTRODUCTION

6. Michelin Contacts

6.1. World Headquarters

6.1.1. Michelin Aircraft Tyre
23, Place des Carmes-Dechaux
63040 Clermont-Ferrand Cedex 9
France
Tel: +33 (0) 4 73 32 61 06
Fax: +33 (0) 4 73 32 76 44

6.2. Commercial Offices

6.2.1. *North, Central and South America*

Michelin Aircraft Tire Company
One Parkway South
Greenville, SC 29615
U.S.A.

Tel: +1-877-503-8071
Fax: +1-864-458-6746

6.2.2. *Europe, CIS, Middle East, Africa*

Michelin Aircraft Tyre
23, Place des Carmes-Dechaux
63040 Clermont-Ferrand Cedex 9
France
Tel: +33 (0) 4 73 32 76 28
Fax: +33 (0) 4 73 32 76 44

6.2.3. *Far East and Oceania*

Michelin Siam Co.
Aircraft Tyre Operations
SPE Tower 11th Floor
252 Phaholyothin Road
Samsaen Nai, Payathai
Bangkok 10400
Thailand
Tel: +66 (2) 619-3524
Fax: +66 (2) 619-3529

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

INTRODUCTION

7. Cage Code

CAGE CODE		
F0635	0A1K8	SGV30
Manufacture Française Des Pneumatiques Michelin	Michelin North America DBA Michelin Aircraft Tire Company	Michelin Siam Group Co.
Michelin Aircraft Tyre 23, Place des Carmes-Dechaux 63040 Clermont-Ferrand Cedex 9 France Tel: +33 (0) 4 73 32 61 06 Fax: +33 (0) 4 73 32 76 44	Michelin Aircraft Tire Company One Parkway South Greenville, SC 29615 U.S.A. Tel: +1-877-503-8071 Fax: +1-864-458-6746	Michelin Siam Co. Aircraft Tyre Operations SPE Tower 11th Floor 252 Phaholyothin Road Samsaen Nai, Payathai Bangkok 10400 Thailand Tel: +66 (2) 619-3524 Fax: +66 (2) 619-3529



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

101

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

CHAPTER 1 - AIRCRAFT TIRE DESCRIPTION/CONSTRUCTION

1. General

- 1.1. An aircraft tire must withstand a wide range of operational conditions. While on the ground, it must support the weight of the aircraft. During taxi, it must provide a stable, cushioned ride while resisting heat generation, abrasion, and wear. During take-off, the tire structure must be able to endure not only the aircraft load, but also the forces generated at high angular velocities. Landing requires the tire to absorb impact shocks while also transmitting high dynamic braking loads to the ground. All of this must be accomplished while providing a long and reliable service life.
- 1.2. These extreme demands require a tire that is highly engineered and precisely manufactured. The tire is a composite of a number of different rubber compounds, fabric material and steel. Each component and rubber compound serves a specific purpose in the performance of the tire.
 - 1.2.1. All MICHELIN® manufactured aircraft tires are certified for in-service operation to -55°C (-67°F) ambient.
- 1.3. Two different and distinct aircraft tire constructions are produced and provided on the market. Both nomenclatures describe the differences in casing construction.
 - 1.3.1. The Bias tire (cross-ply construction).
 - 1.3.2. The Radial tire.
- 1.4. Many of the components of bias and radial tires have the same terminology. However, the technologies and process assemblies utilized are quite different requiring different design parameters, compounds, and materials.
- 1.5. This chapter describes the different components that make up the construction of an aircraft tire. Understanding these components and their purpose will help with the understanding of the MICHELIN Aircraft Tire Care and Service Manual and the recommendations contained herein.
- 1.6. While the technologies between bias tire and radial tire perform very differently, their in-service maintenance procedures and removal limit criteria remain similar.
- 1.7. An aircraft tire is received as a complete component.
NOTE: A visual inspection of the tire is required to assure no handling damage has occurred during transport.
- 1.8. The tire must be mounted on a wheel to form a tire/wheel assembly prior to service use.
NOTE: Refer to Chapter 4 – MOUNTING INSTRUCTIONS (Assembly), in this manual.
- 1.9. Many aircraft tires are designed to be retreaded. Retreading is the process of renewing the tread products of the tire allowing the casings to be used multiple times. Tires damaged in service may also be repairable. Retreading and repairing extends the service life of a casing, reducing operational costs and minimizing environmental impact. Refer to Chapter 7, RETREAD/REPAIR.
- 1.10. The FAA, EASA and regulatory organizations in other countries require that retreading and/or repair of aircraft tires be performed only by a certified facility. The certification is determined by the governing authority under which the operator is authorized.
- 1.11. Michelin meets or exceeds all testing requirements of the FAA/EASA for retreaded aircraft tires.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

102

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

CHAPTER 1 - AIRCRAFT TIRE DESCRIPTION/CONSTRUCTION

2. Tire Zones

Figure below describes the different zones of a tire.

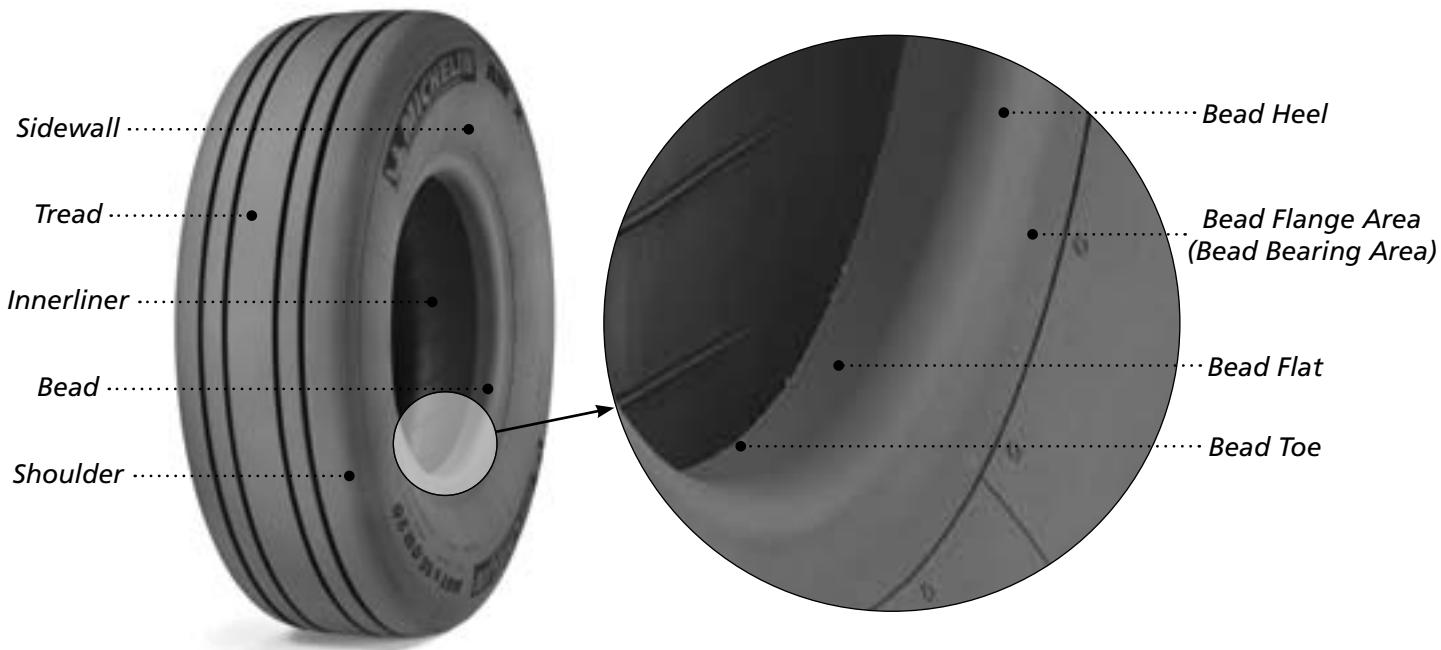


Figure 101. Tire Zones and Tire Bead Zones

- 2.1. The Tread or Crown Zone extends from the shoulder on one side of the tire to the opposite shoulder side.
- 2.2. The Shoulder Zone is between the Tread and Sidewall.
 - 2.2.1. The shoulder is a subpart of the Tread or Crown and encompasses the area from the upper sidewall to the tread.
- 2.3. The Sidewall Zone extends from the molded shoulder ring toward the bead area in the vicinity of the top of the wheel flange. Most tires have a molded ring in this area.
- 2.4. The Bead Zone extends from the lower molded ring to the bead toe area.
 - 2.4.1. The Bead Flange area (Bead Bearing area) is the portion of the Bead Zone that is in contact with the wheel flange.
 - 2.4.2. The Bead Heel is the radius that forms the intersection of the sidewall and bead flat. It rests in the radius between the wheel flange and the flat portion of the rim base.
 - 2.4.3. The Bead Flat is the area of the tire that is in contact with the rim seating surface of the wheel.
 - 2.4.4. The Bead Toe forms the intersection of the bead flat and interior of the tire.
- 2.5. The Interior Zone encompasses the interior area from bead toe on one side to bead toe on the opposite side.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

103

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

CHAPTER 1 - AIRCRAFT TIRE DESCRIPTION/CONSTRUCTION

3. Aircraft Tire Construction (Bias and Radial)

- 3.1. Tread: The tread refers to the part of the tire that comes in contact with the ground.
 - 3.1.1. The tread rubber compound is formulated to resist wear, abrasion, cutting, cracking, and heat buildup. It prolongs the life of the casing by protecting the underlying tire structure.
- 3.2. Tread Groove: Most MICHELIN® tires are designed with circumferential grooves molded into the tread surface during fabrication. The depth of these grooves is referred to as "Skid." These grooves:
 - 3.2.1. Act as a visual indicator of tread wear by allowing easy depth perception of the skid depth to the bottom of the groove.
 - 3.2.2. Provide a mechanism to channel water from between the tire and runway surface.
- 3.3. Tread Ribs are the rubber between the tread grooves.
- 3.4. Undertread
 - 3.4.1. Undertread is the rubber layer between the bottom of the grooves and the top of the reinforcing plies on bias tires and the top of the protector ply on radial tires.
 - 3.4.2. For tires designed to be retreaded, it allows for buffing the worn tread and provides the liaison with the new retread products.
- 3.5. Casing Ply
 - 3.5.1. The term casing ply and carcass ply are sometimes used interchangeably. For the purpose of this document the term casing ply will be used. In general, a casing ply consists of fabric cords between two layers of rubber representing an individual ply.
 - 3.5.2. The casing plies give the tire its primary strength.
 - 3.5.3. Casing plies are anchored around bead wires forming "ply turn-ups."
 - 3.5.4. Multiple layers of casing plies are bonded together, as necessary, to form the casing and give the tire the capability to hold the inflation pressure.
 - 3.5.5. The term "Casing" refers to a grouping of casing plies and other tire components. It represents the structural part of the tire. That is, all parts of the tire except the tread zone.
- 3.6. Bead
 - 3.6.1. Bead wires anchor the tire to the wheel and transfer the load to the wheel.
- 3.7. Liner (Innerliner)
 - 3.7.1. Replaces the inner tube in tubeless tires.
 - 3.7.2. A thin layer of rubber specially compounded to resist the permeation of air or nitrogen through to the casing plies.
 - 3.7.3. It extends from bead to bead.
- 3.8. Sidewall
 - 3.8.1. A layer of rubber covering the outside of the casing. Its purpose is to protect the casing.
 - 3.8.1.1. The sidewall also provides the surface for tire markings.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

104

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

CHAPTER 1 - AIRCRAFT TIRE DESCRIPTION/CONSTRUCTION

4. Components Unique to MICHELIN® Radial Aircraft Tires

(All components shown may not be in all tires, due to design criteria.)

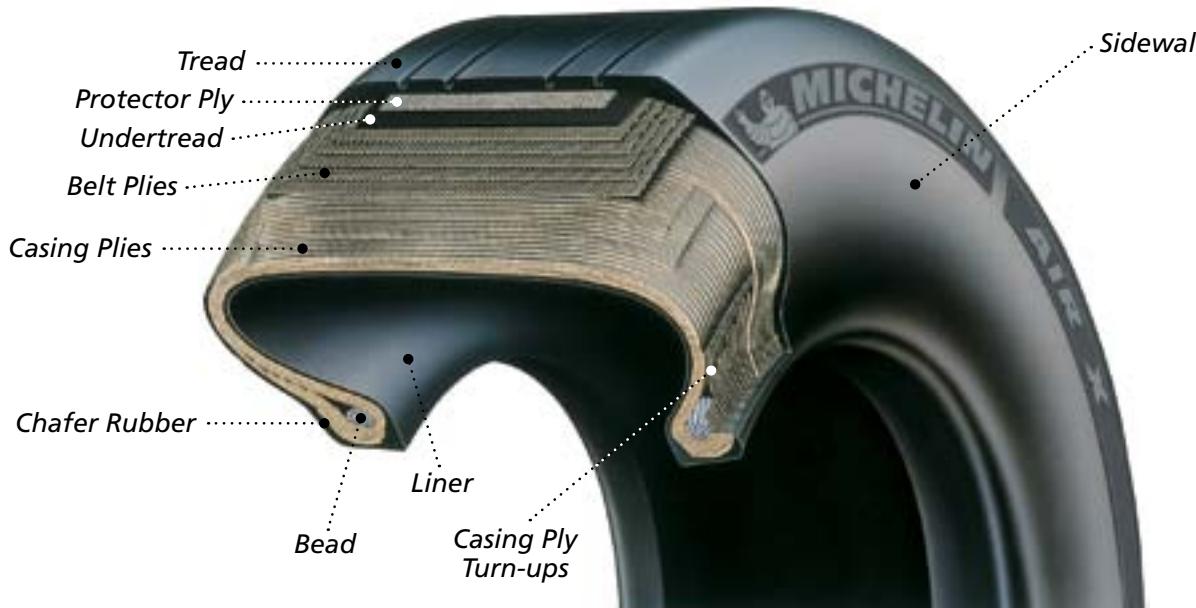


Figure 102. Radial Aircraft Tire

4.1. Protector Ply

- 4.1.1. Single layer of steel or nylon fabric positioned underneath the tread.
- 4.1.2. The protector ply provides cut resistance protection to the underlying belt plies and casing plies.
- 4.1.3. Typically it is only found in retreadable tires, but may not be found in all of them.

4.2. Belt Plies

- 4.2.1. Belt plies are nylon or special fabric cords that are laid on top of the casing plies.
- 4.2.2. Belt plies restrain the outer diameter of the tire, providing a tread surface with greater resistance to squirm and wear as well as providing a more uniform pressure distribution in the footprint for improved landing performance.

4.3. Casing Ply

- 4.3.1. In radial constructed tires, each nylon casing ply is laid at an angle approximately 90° to the centerline or direction of rotation of the tire.

NOTE: Radial constructed tires of the same size have a fewer number of casing plies than tires of a bias construction because the radial tire uses the casing cords more efficiently.

4.4. Bead

- 4.4.1. Radial tires are constructed with 2 bead wire bundles (1 per side).
- 4.4.2. Beads are fabricated from high strength steel wires layered together to form a bundle.

4.5. Chafer Rubber

- 4.5.1. Protective rubber laid over the outer casing plies in the bead area of the tire.
- 4.5.2. Its purpose is to protect the casing plies from damage when mounting or dismounting and to reduce the effects of wear and chafing (light abrasion) between the wheel and the tire bead.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

105

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

CHAPTER 1 - AIRCRAFT TIRE DESCRIPTION/CONSTRUCTION

- 4.6. Near Zero Growth (NZG)
 - 4.6.1. NZG technology is a development by Michelin for radial tires. This technology uses a newly developed ultra-high tensile composite cord with less elongation than nylon cords.
 - 4.6.2. Tires constructed with NZG cord may use fewer plies to achieve the same tire strength and capability. As such, NZG tires are lighter in weight and grow less than nylon constructed tires. The technology results in better resistance to foreign object damage (FOD) and landing performance, in addition to the lighter weight.
 - 4.6.3. The use of NZG technology is not currently identified in the sidewall marking.

5. Components Unique to MICHELIN® Bias Aircraft Tires

(All components shown may not be in all tires, due to design criteria.)



Figure 103. Bias Aircraft Tire

- 5.1. Tread Dimples (very limited applications):
 - 5.1.1. Half-sphere depressions molded in the tread rubber, in place of grooves, to act as a wear indicator.
 - 5.1.2. This tread design is limited to high flotation tires that are intended for landing on grass or unimproved runways.
- 5.2. Fabric Tread (very limited applications)
 - 5.2.1. Fabric tread is a unique development for application on high speed military aircraft.
 - 5.2.2. Multiple plies of nylon cords are layered throughout the tread rubber.
- 5.3. Spiral Wrap (very limited applications)
 - 5.3.1. Spiral Wrap is a technique used with retreaded tires.
 - 5.3.2. Individual textile cords are laid within the replacement tread rubber as it is applied to the tire casing.
 - 5.3.3. Due to their circumferential orientation, the textile cords provide added resistance to the cutting and tearing action associated with chevron cutting.
 - 5.3.4. Cords can be visible during wear on the tread.

**MICHELIN
AIRCRAFT TIRE
CARE AND SERVICE MANUAL**

106

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

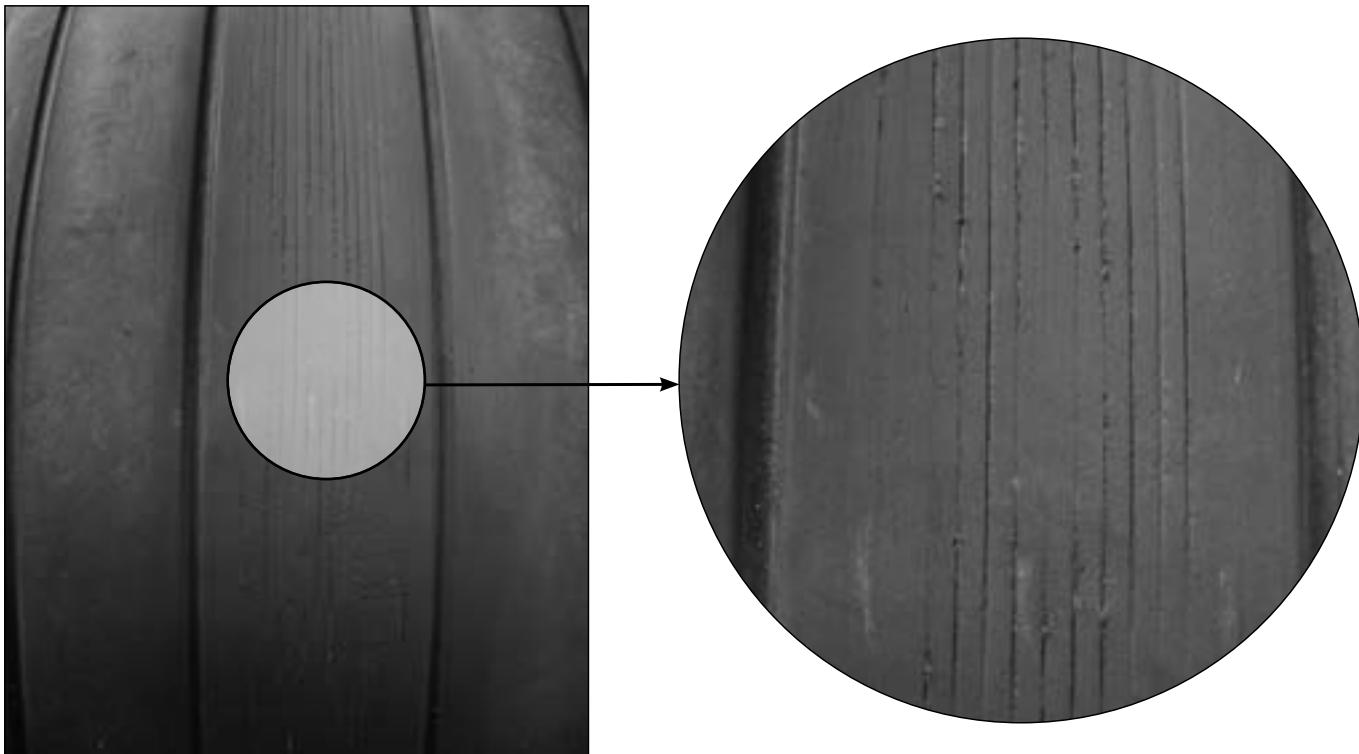


Figure 104. Spiral Wrap

- 5.4. Tread Reinforcing Ply
 - 5.4.1. Single or multiple layers of a special nylon fabric positioned underneath the tread.
 - 5.4.2. These plies help to strengthen and stabilize the crown area by reducing tread distortion under load and increasing high speed stability. They also offer resistance of the tread to puncture and cutting which helps protect the casing body.
 - 5.4.3. It is typically only found in retreadable tires, but may not be found in all of them.
- 5.5. Casing Ply
 - 5.5.1. In bias constructed tires, nylon casing plies are laid at angles between 30° and 60° to the centerline, or direction of rotation of the tire. Succeeding plies are laid with cord angles opposite to each other to provide balanced casing strength.
 - 5.5.2. In some bias designs, supplemental plies are used to reinforce the casing in the tread area of the tire.
- 5.6. Bead
 - 5.6.1. They are constructed from high-strength steel wires layered together to form a bundle.
 - 5.6.2. Bias tires are constructed with 2 to 8 bead bundles (1 to 4 per side), depending on the size and design application.
- 5.7. Chafer Strips
 - 5.7.1. Strips of protective fabric or rubber laid over the outer casing plies in the bead area of the tire.
 - 5.7.2. Their purpose is to protect the casing plies from damage when mounting or dismounting and to reduce the effects of wear and chafing (light abrasion) between the wheel and the tire bead.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

107

CHAPTER 1 - AIRCRAFT TIRE DESCRIPTION/CONSTRUCTION

5.8. New Bias Technology (NBT)

NBT technology is a development unique to some MICHELIN® Bias constructions. It consists of a casing crown reinforcement placed on the inside of the tire located under the tread. This provides strength and a more uniform pressure distribution in the footprint slowing the rate of wear and improving landing performance.



Figure 105. NBT Bias Technology

6. Sidewall Venting

- 6.1. Aircraft tires have traditionally been designed to permit any air or nitrogen trapped in the internal cord body, or that diffuses through the innerliner or tube, to escape through designed sidewall vents.
- 6.2. Vent holes exist on both sides of the tire.
- 6.3. Not all tires require vent holes due to materials, design and fabrication. This is particularly true for some physically smaller radial tires used in the General Aviation and high performance Military applications.
- 6.4. Tires requiring vent holes have them placed in the lower sidewall. The location of each vent hole is indicated by a colored paint dot when required. Refer to Figure 106.
 - 6.4.1. A Green color is used for tubeless tires.
 - 6.4.2. A White color is used for tube-type tires.
 - 6.4.3. Paint dots are applied to new tires. It is not required that they be refreshed on retreaded tires.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

108

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

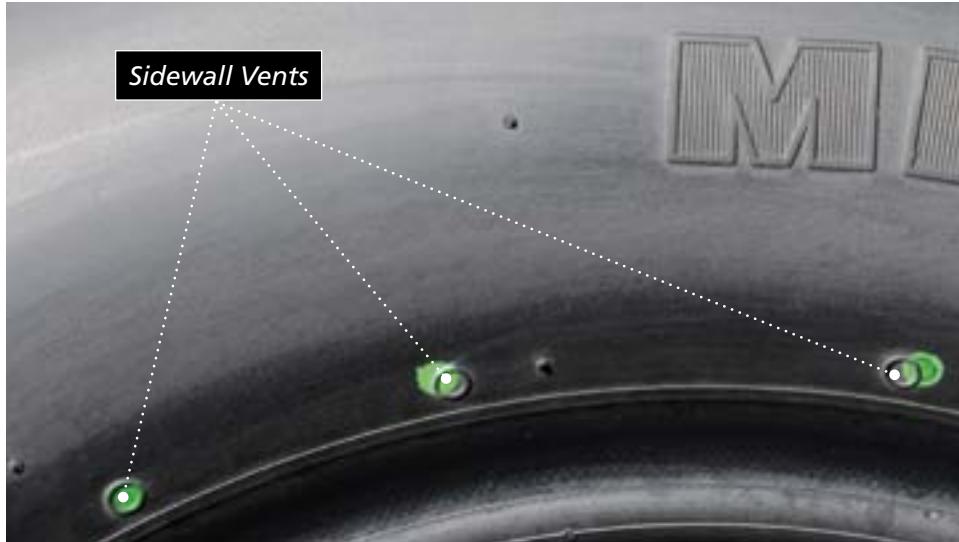


Figure 106. Lower Sidewall Vents

NOTE: It is normal to see bubbles at the tire vent holes, just above the wheel flange, any time while the tire is inflated. Refer to Figure 107.

NOTE: Do not identify a tire as leaking solely on the rate of bubbles from the vent holes. A leaking tire/wheel assembly should be determined by the pressure loss, as measured with a calibrated gauge, over a period of time.



Figure 107. Appearance of Bubbles From Tire Vents

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

109

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

CHAPTER 1 - AIRCRAFT TIRE DESCRIPTION/CONSTRUCTION

7. Chine Tires

- 7.1. The "chine" tire is a nose wheel tire designed to deflect water and slush to the side and away from the intakes on aft-fuselage mounted jet engines.
- 7.2. Chine tires have a protrusion on the upper sidewall which deflects the spray pattern of water or slush displaced by the tire's contact with the runway.
- 7.3. A tire can have a single chine for dual nose wheel tire configurations or double chine for single nose wheel tire configurations. Refer to Figure 108.
- 7.4. The chine tire is used on some commercial, regional and private jets. It is retreadable when specified.

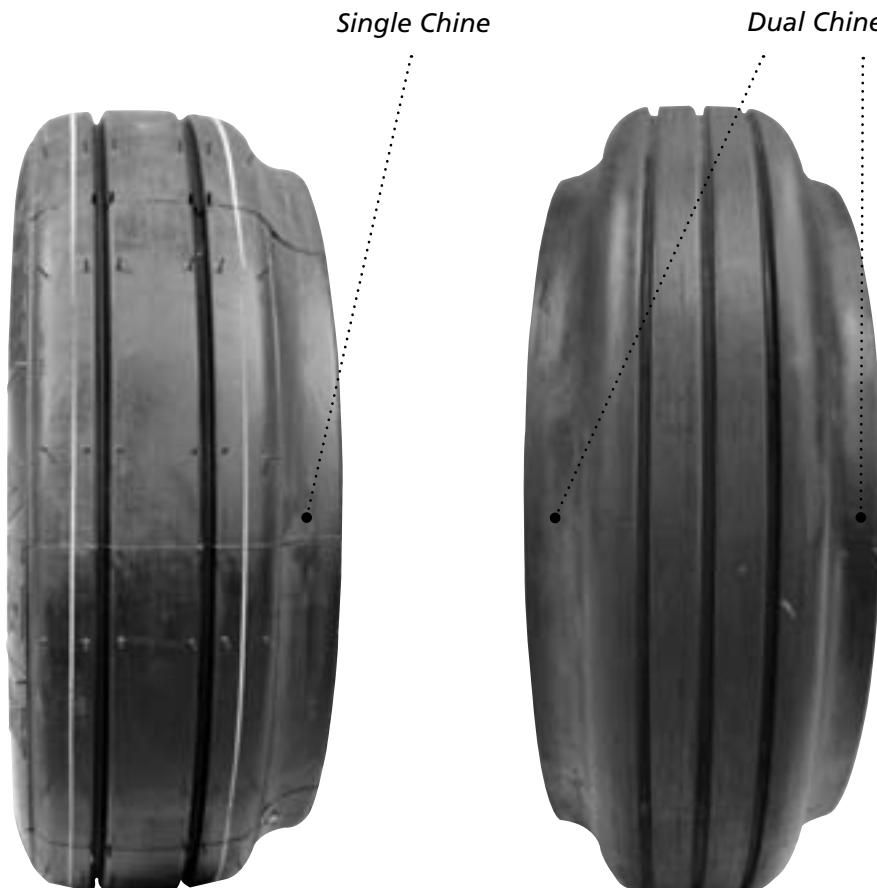


Figure 108. Chine Nose Tire



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

1. Tire Terminology

- 1.1. This section provides basic information related to tire terminology used to describe and understand tire capabilities.
- 1.2. A "New Tire" is a tire that has been stretched to its dimensions by inflating to the specified pressure and that has not been placed in service on an aircraft.
- 1.3. A "Grown" tire has been stretched to its maximum dimensions during its service life, as a result of inflation pressure, heat, and rotational forces.
- 1.4. "B" or "H" prefix in the size designation indicates a rim width to section width ratio.
- 1.5. Maximum Outside Diameter is maximum diameter of a new inflated tire measured on the center of the tread.
 - 1.5.1. Do = Nominal overall diameter expressed in inches or millimeters.
- 1.6. Section Width is the overall width at the widest point of a new inflated tire. The section width dimension does not include the chine for tires with chine.
 - 1.6.1. W = Nominal section width expressed in inches or millimeters.
- 1.7. The Construction code is placed between the section width and the rim diameter.
 - 1.7.1. "-" for bias tires.
 - 1.7.2. "R" for radial tires.
- 1.8. Rim Diameter is the specified rim diameter.
 - 1.8.1. D = Rim diameter expressed in inches or millimeters.
- 1.9. Static Loaded Radius is the distance between the center of the wheel axle and the flat surface, on which the tire is loaded, when supporting its rated load while inflated to its rated pressure (at ambient temperature).
- 1.10. Tire Deflection is the difference between half the outside diameter and the static loaded radius.

2. Tire Sizes

- 2.1. Tires are described by a combination of their physical dimensions. Depending on their intended application the dimensions used to describe the tire are different.
- 2.2. Tire size dimensions are standardized for a tire mounted on the proper rim, inflated to rated pressure at ambient temperature.
- 2.3. Dimensional tolerances are set by the Tire and Rim Association (T&RA) and/or the European Tyre and Rim Technical Organization (ETRTO) and may also be found in each organization's year book.
 - 2.3.1. Bias tire dimensions are for a "New" tire that has been inflated to the specified pressure for 12 hours minimum.
 - 2.3.2. Radial tire dimensions are for a "Grown" tire that has been rolled the equivalent of 50 TSO-C62 takeoff cycles.
- 2.4. TYPE III tires size designation: High flotation, low pressure. Maximum speed usually 160 mph or less.
 - 2.4.1. Tire Size designation is shown as W – D. (Nominal section width - Rim diameter)
 - 2.4.2. Examples:
 - 5.00 – 5
 - 8.50 – 10



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

- 2.5. TYPE VII tire size designation: High pressure, narrow section widths for high speed aircraft.
 - 2.5.1. Tire Size designation is shown as Do x W. (Overall Diameter x Nominal section width)
 - 2.5.2. Examples:
 - 26 x 6.6
 - 49 x 17
- 2.6. THREE PART Nomenclature: Used for all recent and newly designed tire sizes, all applications.
 - 2.6.1. Size designation: Do x W – D. (Overall Diameter x Nominal section width – Rim diameter)
 - 2.6.2. Bias Size Examples:
 - 27 x 7.75 – 15
 - H44.5 x 16.5 – 21 ("H" type)
 - 2.6.3. Size designation: Do x W R D.
 - 2.6.4. Radial Size Examples:
 - 50 x 20.0 R 22
 - 1400 x 530 R 23 (metric)
 - H41 x 16.0 R 20 ("H" type)
- 2.7. TUBES are sized and identified the same way as the tire size for which they are to be used.
 - 2.7.1. Examples:
 - 6.00 – 6
 - 15x6.0 – 6

3. Tire Markings (Branding)

- 3.1. This section provides information on typical tire markings for both new and retread tires along with common terminology.
- 3.2. Markings are molded into the rubber surface during manufacturing and remain there throughout the tire's life.
 - 3.2.1. Markings provide information that describes the tire, its design capabilities, manufacturing information, and certification.
 - 3.2.2. Tire Markings will vary depending on the market application, whether bias or radial, and reflect the requirements in place at the time of certification.
- 3.3. New Tire Markings and Descriptions:
 - 3.3.1. New Tire Markings appear on both sidewalls (Refer to Figures 201 - 205) and are to remain on at least one sidewall of the tire throughout its service life.
 - 3.3.2. Ply Rating (PR) for a given size is an index indicating the maximum load rating in relationship with the inflation pressure.

NOTE: Ply rating is an index number. It may not indicate the actual number of casing plies applied in the tire construction.
 - 3.3.3. Load Rating is the maximum static load for a tire, approved by a standardized body, at rated pressure. Ratings may be expressed in kilograms (kg.) or pounds (lbs.).
 - 3.3.4. Rated Inflation Pressure is required to carry the rated load at ambient temperature. It is not branded onto the tire.
 - 3.3.4.1 The rated inflation pressure is often provided for an unloaded tire (without any deflection).
 - 3.3.4.2 A loaded tire will deflect and reduce its internal volume which increases the inflation pressure about 4%.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

- 3.3.4.3 Inflation pressure is given in Bars or Pounds per Square Inch (psi) (1 Bar = 14.5 psi).
 - 3.3.4.4 Specified Service Inflation Pressure is required for a tire, at maximum aircraft load, to maintain the designed loaded radius. It is determined by the airplane manufacturer and not branded onto the tire.
 - 3.3.5. Speed Rating is the maximum allowable speed for which the tire is certified. Speed Ratings are given in Miles per Hour (MPH). (Some military tires use knots.)
 - 3.3.6. Molded Skid is the depth of the center grooves and is molded into the tread rubber during manufacturing.
 - 3.3.6.1 Measured groove depth will be slightly less due to thermal contraction.
 - 3.3.6.2 Values are given as 100th of an inch (example: 0.45 inch).
 - 3.3.7. Casing Construction Code Identification is used for some radial and bias tires to provide the actual construction.
 - 3.3.7.1 Radial Example: 1NC07NB09SP1
 - 1 = number of bead wires for each side of the tire
 - NC07 = 7 nylon casing plies
 - NB09 = 9 nylon belt plies
 - SP1 = 1 steel protector ply
 - 3.3.7.2 Bias Example: N12-1A
 - N = Nylon
 - 12 casing plies
 - 1 breaker ply
 - Modification "A"
 - 3.3.7.3 Tread Construction Code Example: F2A
 - F = Fabric
 - 2 reinforcing plies
 - Modification "A"
- NOTE:** AEA (Association of European Airlines) Codes are no longer supported by the AEA. These codes have been used to identify the actual number of casing plies, breaker plies and tread reinforcing plies in a bias tire as well as the modification status of the tire design. These codes may be branded on the new tire or by the retread manufacturer.

203

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)


Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL


CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

- 3.3.8. Serial Number is a unique identification number for each tire manufactured.
The Michelin Serial Number also provides the fabrication plant and date.

3.3.8.1. Radial Serial Number Definition

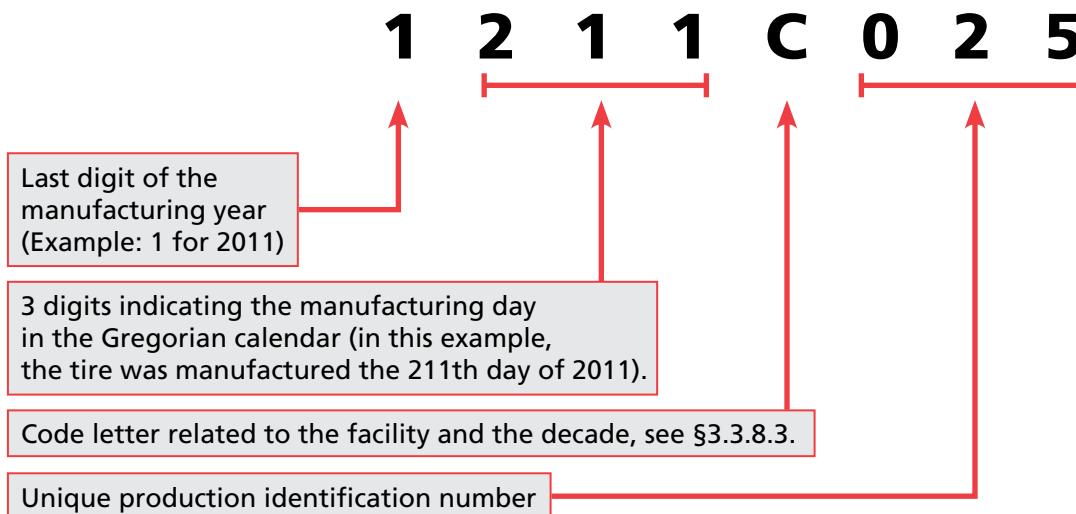

3.3.8.2. Bias Serial Number Definition

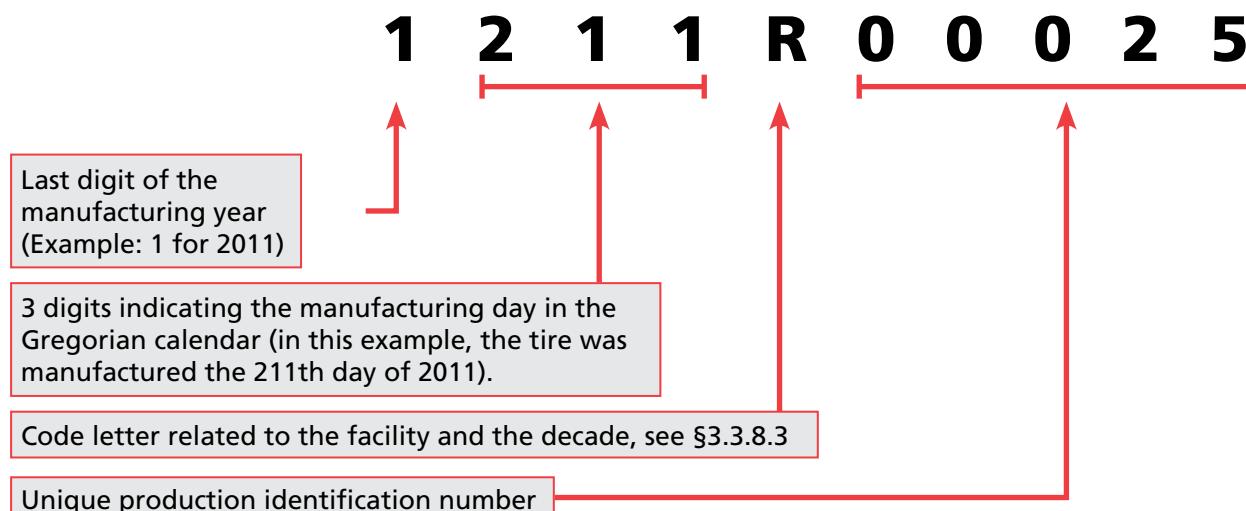

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

3.3.8.3. Letter Signification

The letter code in the tire serial number is used to identify both the manufacturing facility and the decade of manufacture. It follows the matrix below:

	Through Dec. 31, 1995 included	From Jan. 01, 1996 to Dec. 31, 1999 included	From Jan. 01, 2000 to Dec. 31, 2009 included	From Jan. 01, 2010 to Dec. 31, 2019 included	From Jan. 01 2020 to Dec. 31, 2029 included
Bourges (France)	B	B	A	C	B
Clermont-Fd (France)	F	F	G	N/A	N/A
Norwood (USA)	N	P	U	R	P
Nong Khae (Thailand)	T	T	W	S	T
Greenville (USA)	K	K	L	J	K

- 3.3.9. TSO-C62 is the Federal Administration Agency (FAA) technical standard order (TSO) used to define the minimum performance standards for aircraft tires.
- 3.3.9.1. Aircraft tires approved under a previous TSO/LODA (Letter of Design Approval) may still be manufactured under the provisions of their original approval. Tires may not be marked having a speed rating above 160 mph with TSO number TSO-C62, TSO-C62a, or TSO-C62b. A tire may not be manufactured having a speed rating above 160 mph approved before December 31, 1970, under its original approval.
- 3.3.10. ETSO-C62 is the European Aviation Safety Agency (EASA) equivalent of the FAA TSO-C62. It is also used to define the minimum performance standards for aircraft tires.
- 3.3.11. A Qualification Standard is the basis for approval. This normally would be either TSO or ETSO and will be branded on the tire's sidewall.
- 3.3.12. A Part Number (PN) is a unique manufacturer identification for each aircraft tire size/ply rating/speed rating.
 - 3.3.12.1 MICHELIN® bias tire format = XXX-XXX-X.
 - 3.3.12.2 Bias tires with branding or approval paperwork in which the 7th digit of the PN is not there; this 7th digit is a zero (0).
 - 3.3.12.3 MICHELIN® radial tire format = MXXXXX, MXXXXXX or MXXXXX-XX.
 - 3.3.12.4 Radial tires may have an indices (IND) number located near the PN. This IND number may be part of the PN and identifies a minor change to the tire design.
 - Example: IND 01
- 3.3.13. Tube-Type identifies a tire designed to be mounted and inflated with an inner tube.
- 3.3.14. Tubeless identifies an aircraft tire designed for fitment without an inner tube on an appropriate rim.
- 3.3.15. Equipment Identification is a number used to describe manufacturing equipment.
- 3.3.16. Typical Markings are shown in the figures below. Not all markings are on all tires.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

206

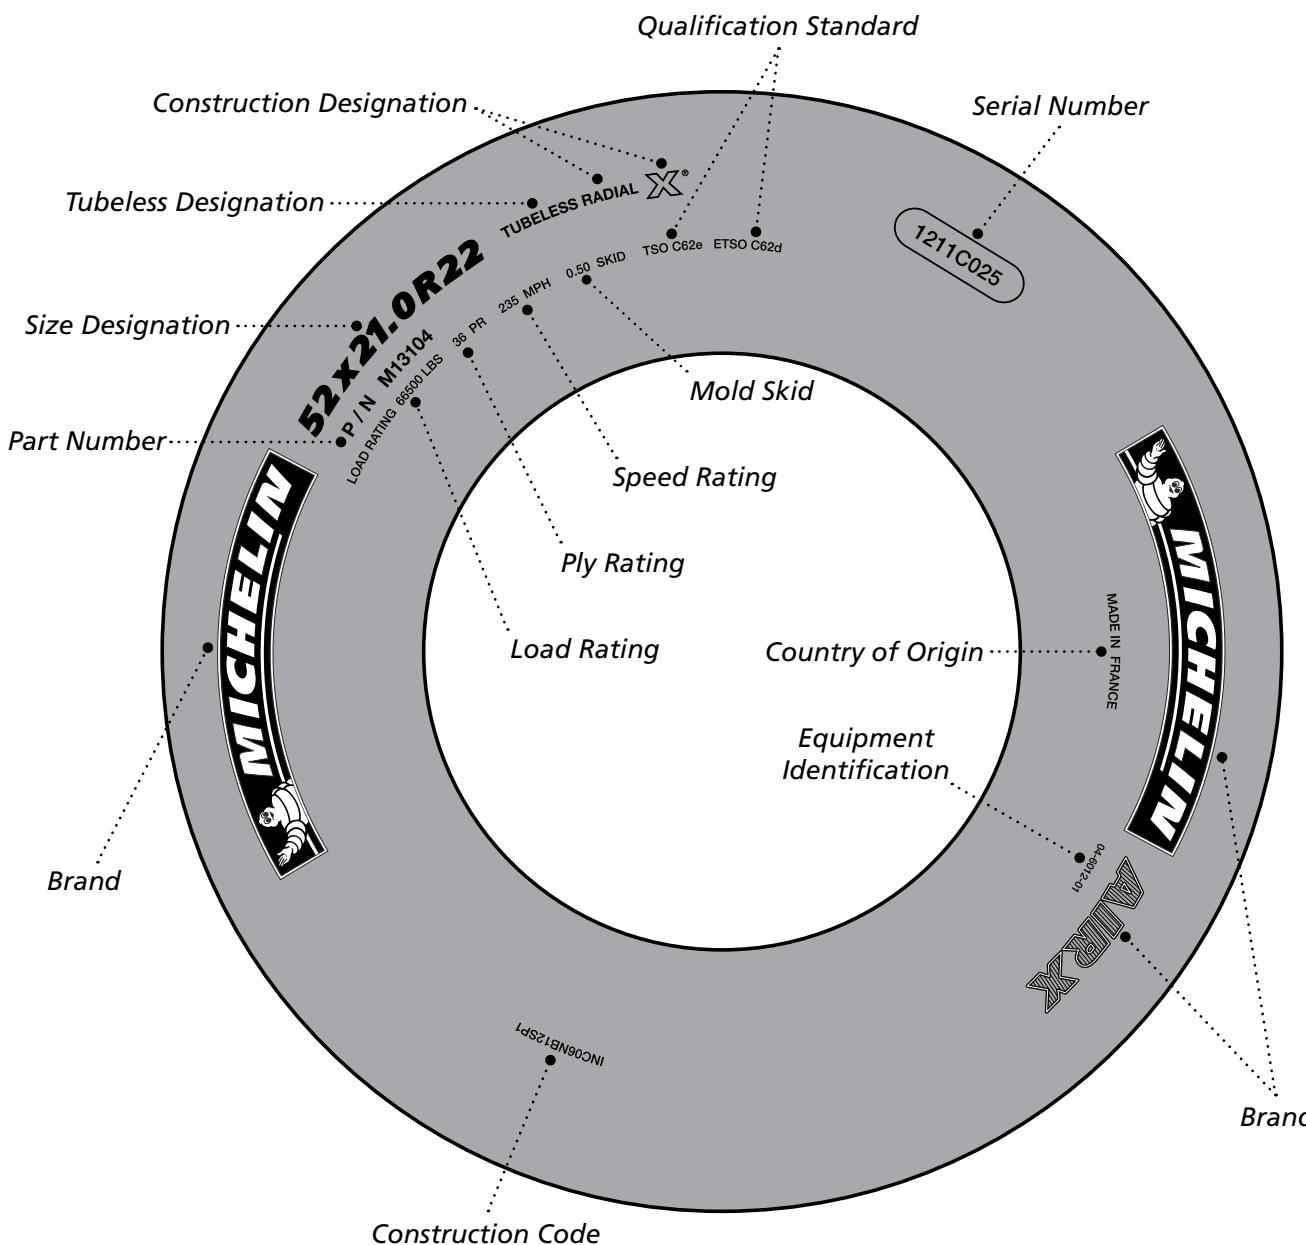


Figure 201. Typical Aircraft Tire Markings – Civil Radial

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

207

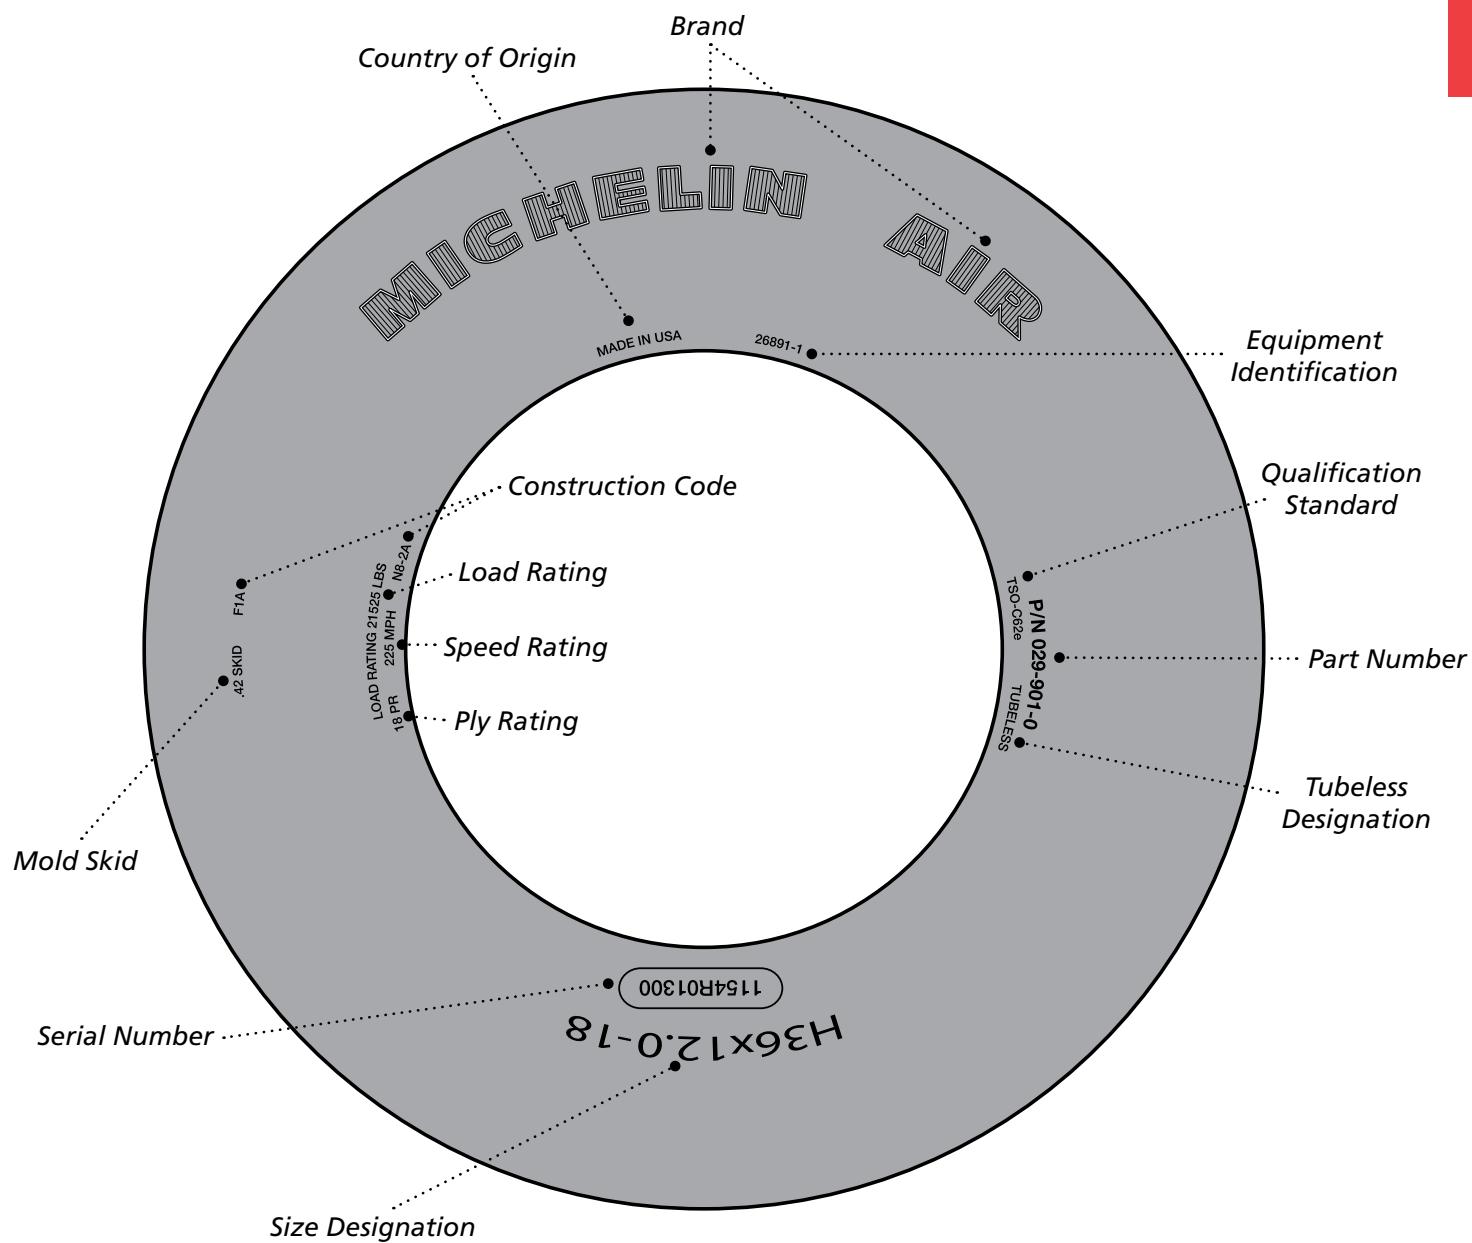


Figure 202. Typical Aircraft Tire Markings – Civil Bias

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

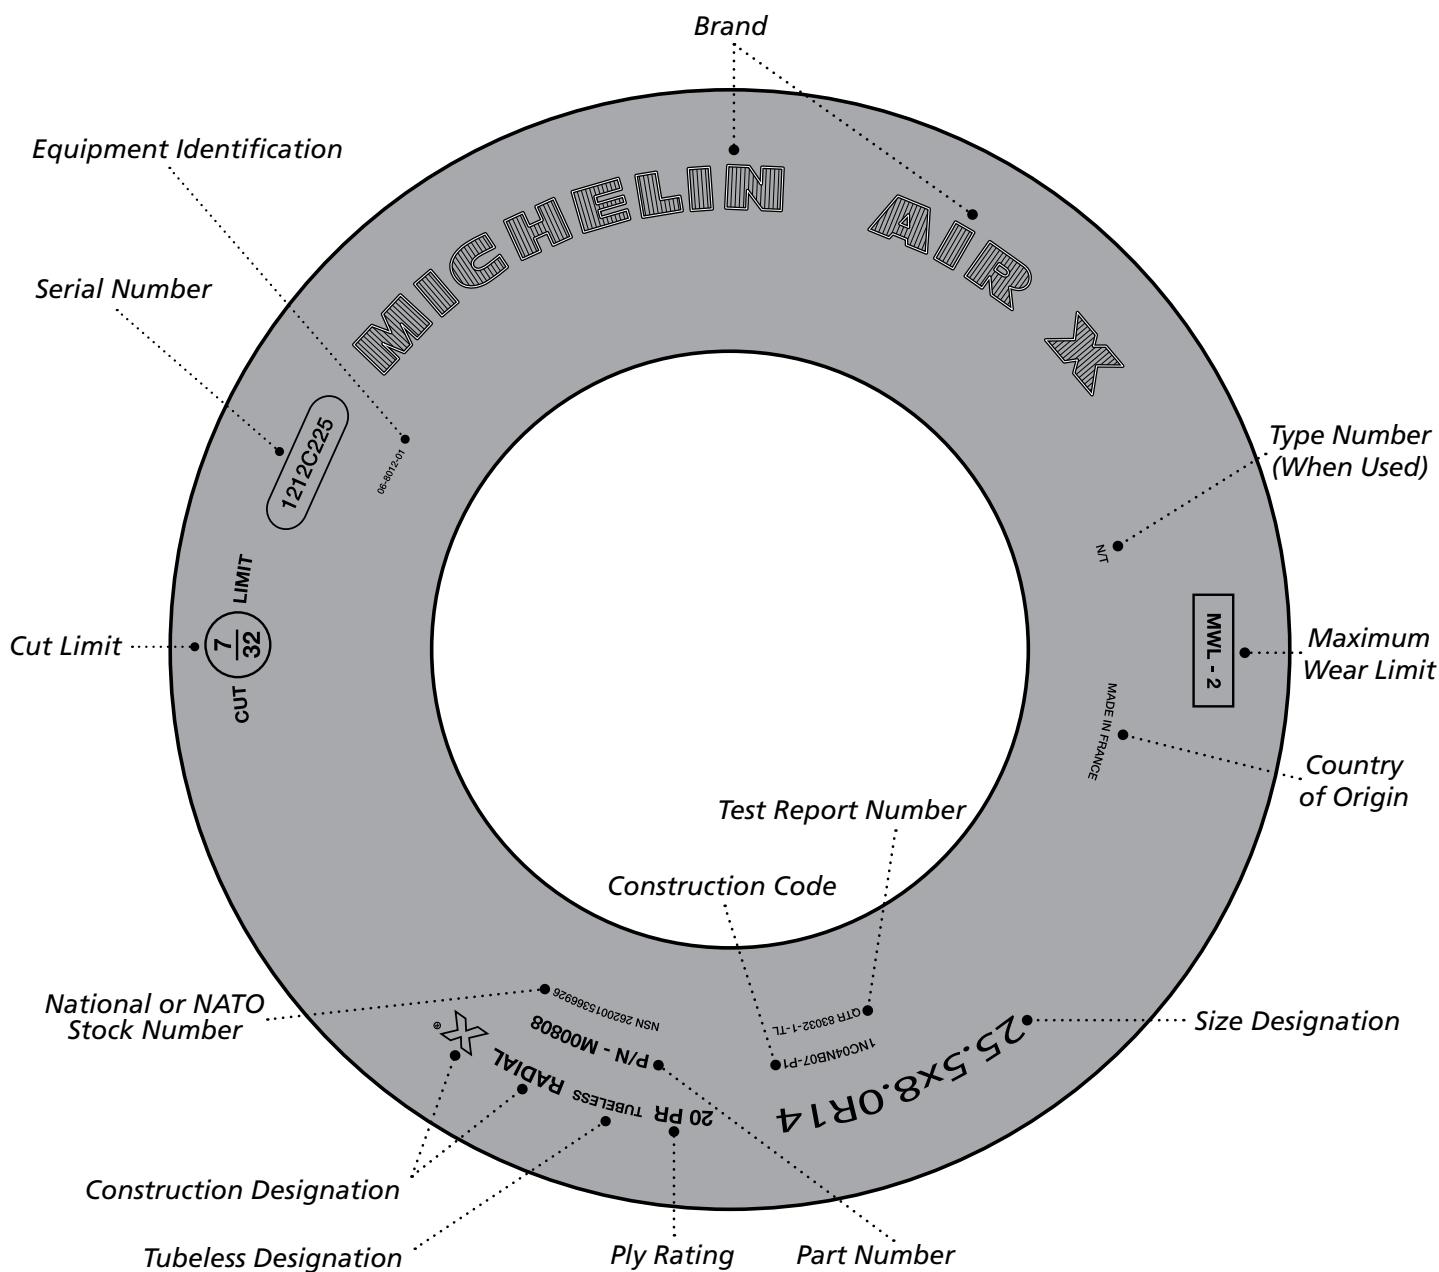


Figure 203. Typical Aircraft Tire Markings – Military Radial, US

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

209

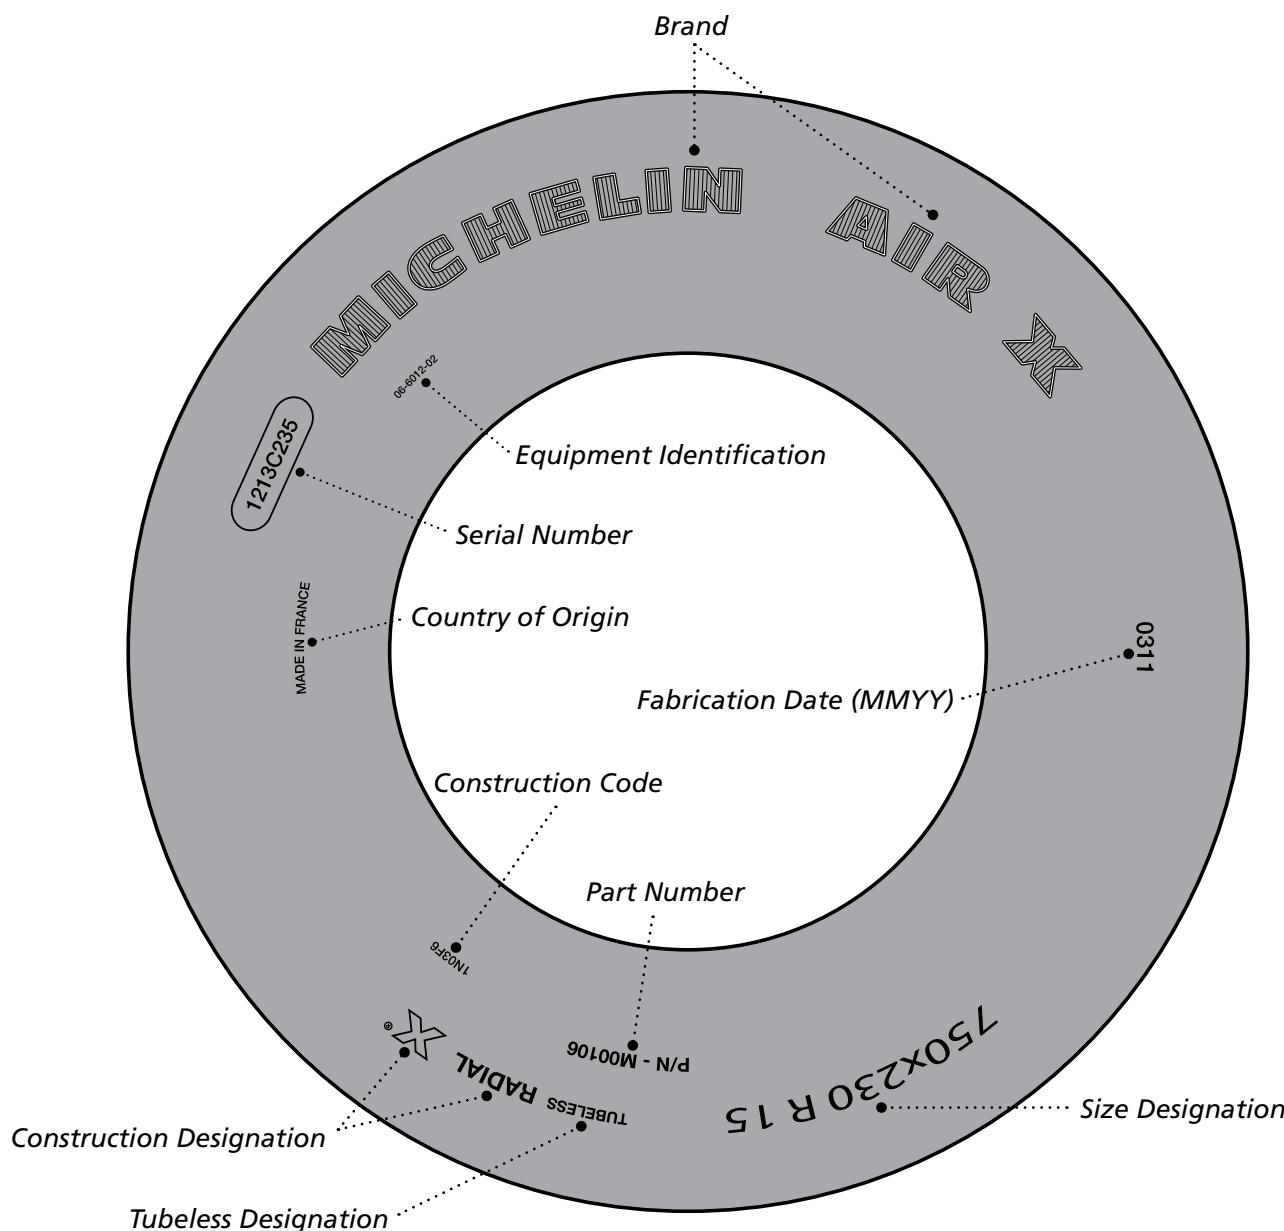


Figure 204. Typical Aircraft Tire Markings – Military Radial, Non-US

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

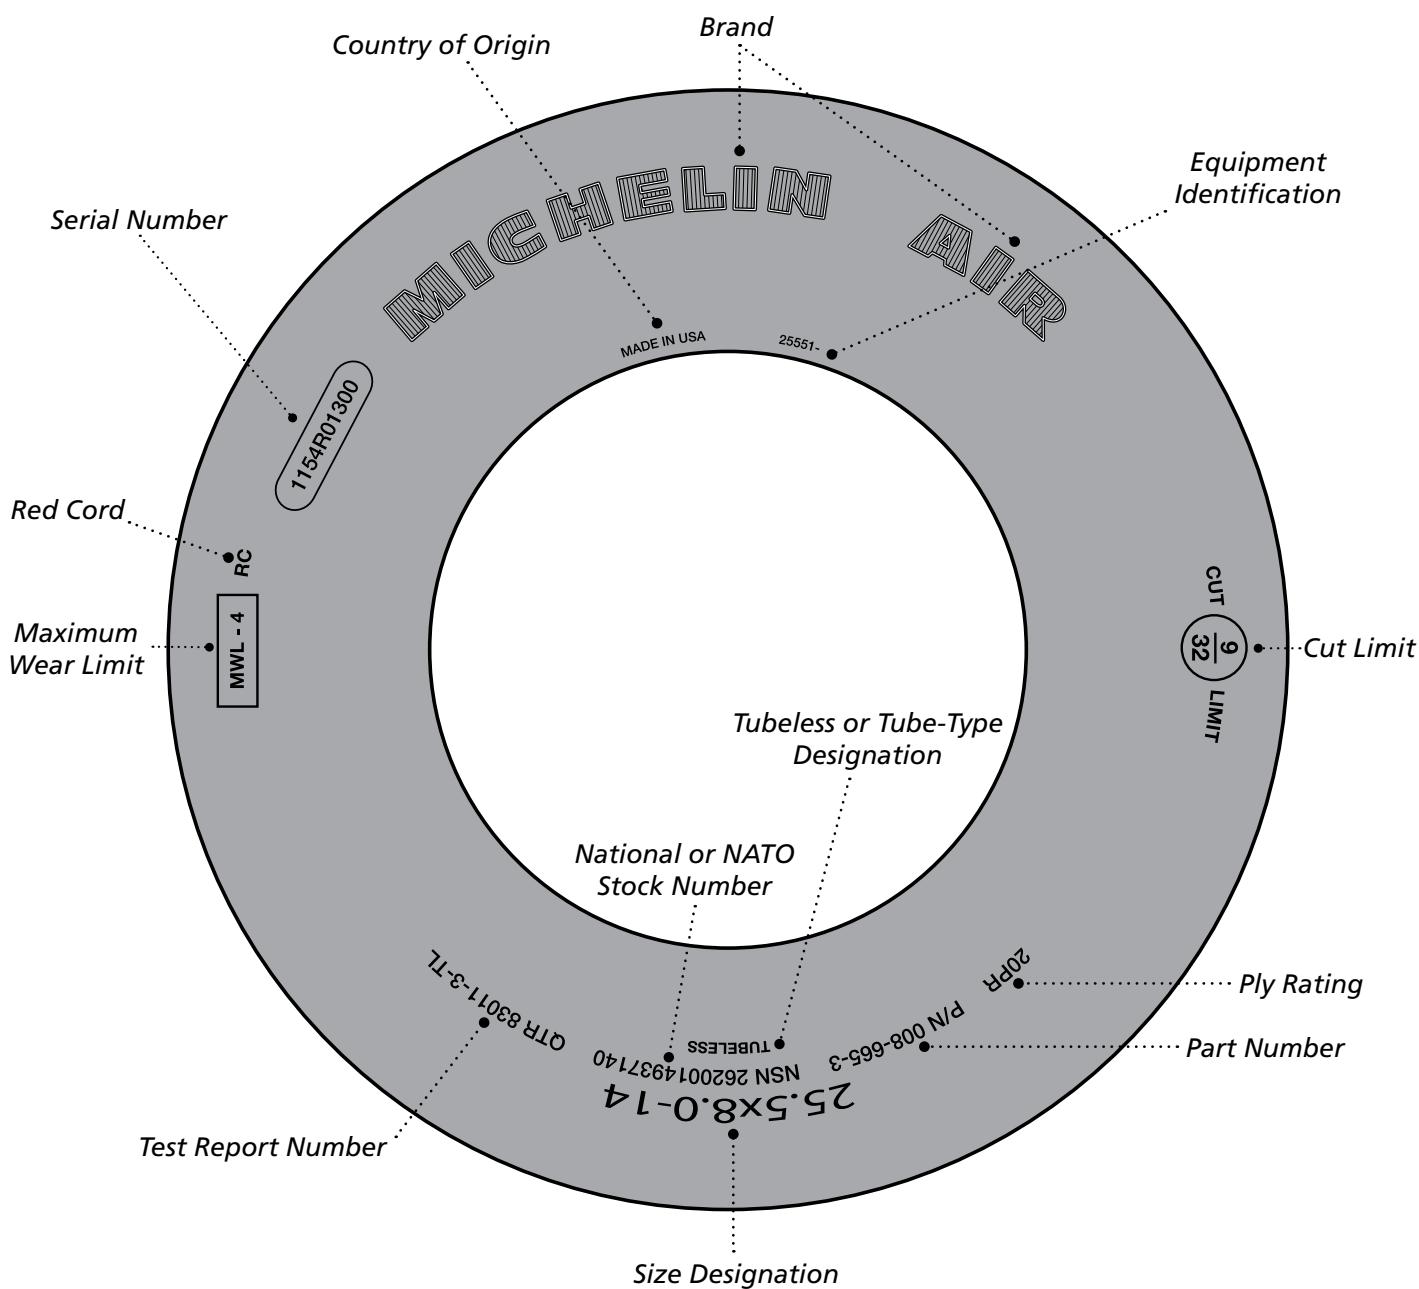


Figure 205. Typical Aircraft Tire Markings – Military Bias



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

4. Retread Markings

- 4.1. Retread brandings provide information related to the retread and are molded into the shoulder. New tire branding will remain on the sidewall of a retreaded tire. Some retreads will have additional brandings applied to the sidewall during the retread process. Retread brandings may include some or all of the following markings.
 - 4.1.1. Retread brandings are removed and replaced at each retread.
 - 4.1.2. Some retread brandings repeat information molded on the sidewall to ensure it is readable over time.
 - 4.1.3. Brand – retread manufacturer (MICHELIN).
 - 4.1.4. Tire Size/Ply Rating/Speed Rating.
 - 4.1.5. Retread Groove Depth (Skid) in 100th of an inch.
 - 4.1.6. Casing Manufacturer 2-Digit code when MICHELIN® retreads bias tires from other manufacturers. (Radial tires are retreaded only by the original manufacturer.)
MA = MICHELIN® Air
GY = Goodyear
DU = Dunlop
BR = Bridgestone
 - 4.1.7. Airline code – 3 digit ICAO airline code.
 - 4.1.7.1. In some cases, Michelin assigns a unique 3-digit code.
 - 4.1.8. Casing original Serial Number is included in the shoulder area of bias tires only.
 - 4.1.9. Retread Level (example: R04).
 - 4.1.10. MM/YY of retreading (example: 02/08).
 - 4.1.11. Retread Facility Code.
MKC = Michelin Kansas City (USA)
MNK = Michelin Nong Khae (Thailand)
MBO = Michelin Bourges (France)
MNW = Michelin Norwood (USA)
 - 4.1.11.1. Retread: Typical brandings for bias and radial retreaded tires are shown in Figure 206.

211

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

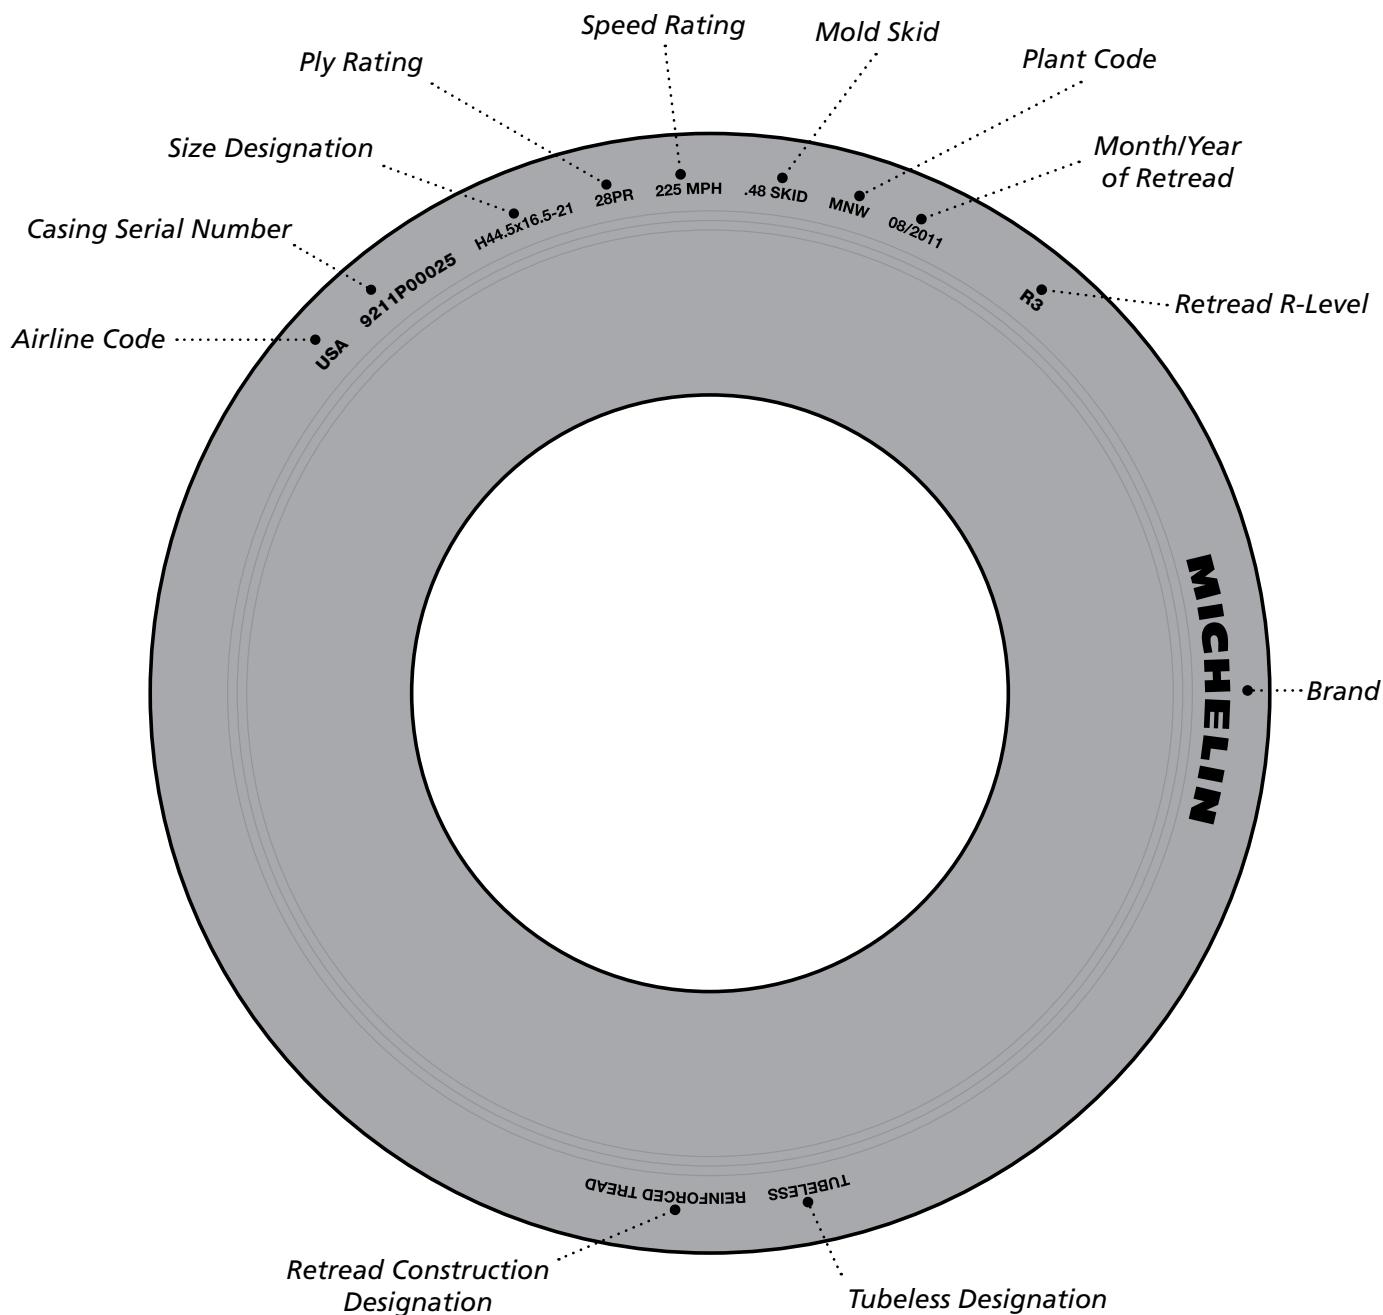


Figure 206. Typical Retread Aircraft Tire Markings

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 2 - AIRCRAFT TIRE TERMINOLOGY AND TIRE MARKINGS (BRANDING)

5. Tube Markings



Figure 207. Typical Aircraft Tube Markings



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 3 - RECEIVING AND STORING AIRCRAFT TIRES

1. Handling of Tires and Tubes

- 1.1. Tires are designed to be tough, durable, and to withstand large loads and high speeds. However, they can be damaged or cut by sharp objects or if excessive force is used improperly.
- 1.2. Avoid lifting tires with conventional two prong forks of material handling lift trucks. Bead areas and innerliners are easily damaged by this means. Use a round pipe attached to the forks when lifting tires through the center (Figure 301, Right).



Figure 301. Damage From Lift Truck Forks (Left). Tires Can Be Lifted Through the Center (Right).

- 1.3. Avoid contact with sharp objects such as nails protruding from pallets or steel edges of shipping containers or trucks which can cause sidewall damage. Refer to Figure 302 and Figure 303.

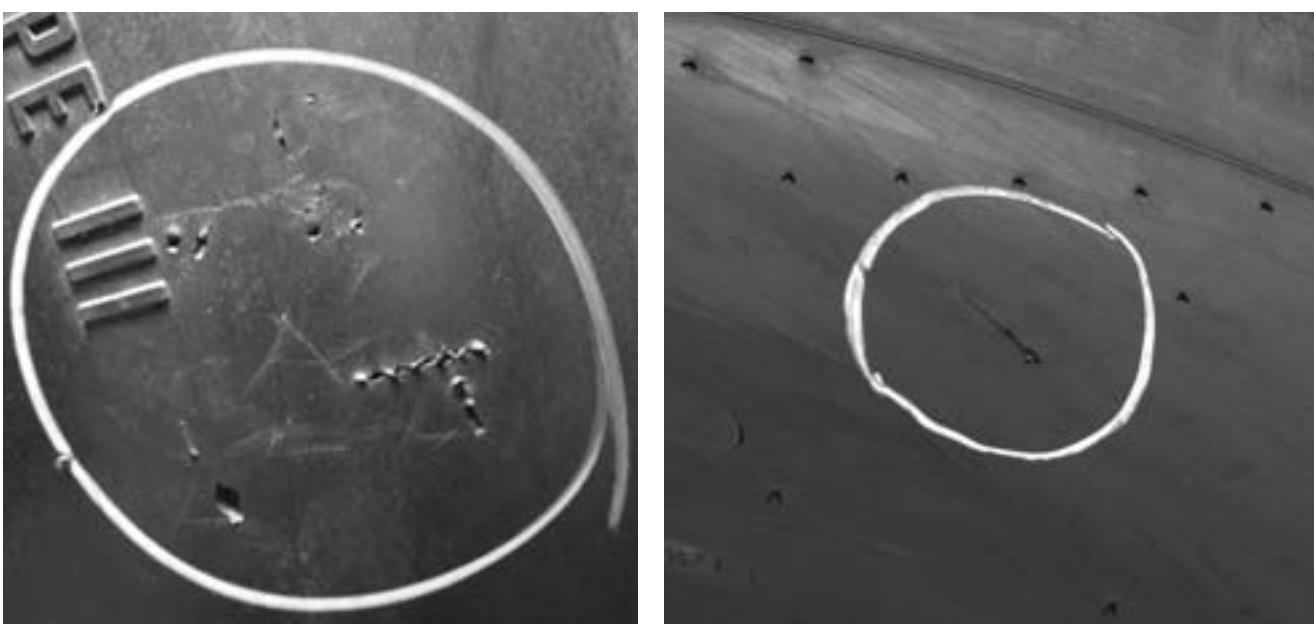


Figure 302. Damage From Contact With Sharp Object - Serviceable

**MICHELIN
AIRCRAFT TIRE
CARE AND SERVICE MANUAL**

CHAPTER 3 - RECEIVING AND STORING AIRCRAFT TIRES



Figure 303. Damage From Contact With Sharp Object – Not Serviceable

- 1.4. Use caution when removing plastic wrap used in shipping. A knife cut can easily make a tire unserviceable. Refer to Figure 304.

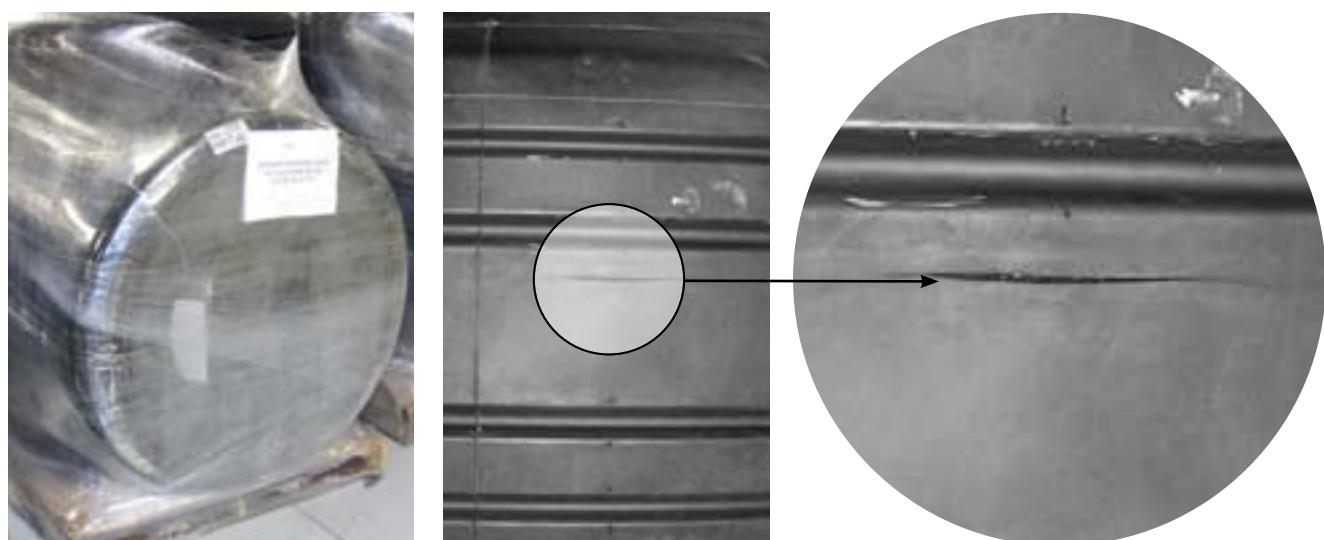


Figure 304. Damage From a Knife Cut



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 3 - RECEIVING AND STORING AIRCRAFT TIRES

2. Storage of Unmounted Tires and Tubes

- 2.1. Proper storage of a tire will extend its serviceable life, reducing costs and helping to avoid reliability issues.
- 2.2. The ideal location for tire and tube storage is a cool, dry and reasonably dark location, free from air currents and dirt.
- 2.3. Tire or tube age limit
 - 2.3.1. MICHELIN® aircraft tires or tubes have no age limit and may be placed in service, regardless of their age, provided all inspection criteria for service/storage/mounting and individual customer-imposed restrictions are met.
- 2.4. Storage conditions
 - 2.4.1. Avoid concentrations of ozone. Sources of ozone include: fluorescent lights, electric motors, battery chargers, electric welding equipment, electric generators and similar electrical devices, since they all create ozone.
NOTE: Most natural and synthetic elastomers used in aircraft tires are susceptible to ozone attack. Ozone breaks the molecular bonds, degrading the rubber and causing cracks.
NOTE: Ozone cracking is most likely to appear in the tread grooves when tires are stored for an extended period of time in an environment with high ozone concentration.
 - 2.4.2. Avoid strong air currents as these bring in fresh sources of ozone.
 - 2.4.3. Air conditioning, exhaust fans, or other sources of ventilation should not be used as the air currents contain new sources of ozone.
 - 2.4.4. Storage rooms should be dark.
 - 2.4.4.1. Avoid direct sunlight. Sunlight is a source of ultraviolet rays.
 - 2.4.4.2. Darken windows with paint or black plastic.
 - 2.4.5. Avoid wet or moist conditions.
CAUTION: DO NOT STORE TUBES IN EXTREME COLD (<0°C/32°F). CRACKS MAY DEVELOP ALONG RUBBER PACKAGING FOLDS CAUSING POTENTIAL LOSS OF PRESSURE WHEN PLACED IN SERVICE.
 - 2.4.6. Store tires and tubes between 0°C/32°F and 40°C/104°F.
 - 2.4.6.1. Room temperatures consistently above 40°C/104°F are detrimental and should be avoided.
 - 2.4.7. Avoid contact with hydrocarbon-based contaminants such as oil, gasoline, jet fuel, hydraulic fluids, brake fluids, or other similar solvents. Hydrocarbon contaminants will deteriorate rubber.
 - 2.4.8. If tires become contaminated, wash them with denatured alcohol and then with a soap and water solution. If the rubber is soft or spongy, the tire is not suitable for service.
 - 2.4.9. Store tires vertically in tire racks. Refer to Figure 305.
 - 2.4.9.1. The surface of the tire rack on which the weight of the tire rests should be flat and, if possible, 7 to 10 cm (3 to 4 in) wide to prevent permanent distortion of the tire.

303

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 3 - RECEIVING AND STORING AIRCRAFT TIRES



Figure 305. Store Tires Vertically in Racks (Left). Tires Stacked Horizontally (Too many tires) (Right).

- 2.4.9.2. When tires are stored for long term (approximately 1 year or longer), it is recommended that tires be rotated periodically to prevent distortion in the tread area.
- 2.4.9.3. If tires must be stacked on top of each other, sidewall to sidewall, they should not be stacked for more than 6 months.
- 2.4.9.4. The maximum stacking height:
 - 2.4.9.4.1. 3 tires high for tire diameter 40 inches (1 meter) or greater.
 - 2.4.9.4.2. 4 tires high if tire diameter is less than 40 inches (1 meter).

NOTE: When tires are stacked horizontally they may become distorted or the beads may become compressed so closely together that difficulties will be encountered during mounting. In extreme cases, it will not be possible to inflate the tire on the wheel.

NOTE: Tires stacked on top of each other, sidewall to sidewall, have increased stresses in the tread grooves. Refer to Figure 305.
- 2.4.10. Store tubes in their original cartons to protect them from light and air currents.

CAUTION: DO NOT HANG TUBES OVER NAILS, PEGS, OR ANY OTHER OBJECT THAT MIGHT CAUSE A CREASE IN THE TUBE. A CREASE WILL EVENTUALLY PRODUCE A CRACK IN THE RUBBER AND CAUSE TUBE FAILURE.

 - 2.4.10.1. If the original carton is damaged, wrap the tube in several layers of heavy paper or store in a sealed plastic bag with most of the air removed.
 - 2.4.10.2. Tubes may be slightly inflated (not more than 1 psi (0.06 bar)) and inserted in the correct size tire.
 - 2.4.10.3. Before mounting a tire with a tube inside, always remove the tube from the tire and inspect the inside of the tire to avoid foreign material which could cause irreparable damage to both the tire and tube, if not removed.

Refer to Chapter 4 for storage of mounted tires.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

This Chapter includes the necessary procedures for installing (mounting), inflating, and verifying pressure retention of an aircraft tire prior to releasing the tire/wheel (hub) assembly for service. The following warnings and cautions apply whenever tires are being mounted and inflated for installation.

1. WARNINGS and NOTES for This Chapter.

- WARNINGS:** AIRCRAFT TIRES SHOULD BE MOUNTED ONLY WITH THE PROPER EQUIPMENT, INSTRUCTIONS, AND OPERATOR TRAINING. SERIOUS INJURY MAY OCCUR AS A RESULT OF IMPROPER EQUIPMENT OR PROCEDURES.
- WARNINGS:** FOLLOW THE INSTRUCTIONS AND PROCEDURES OF THE WHEEL MANUFACTURER FOR THE ASSEMBLY OF THE WHEEL (HUB) COMPONENTS TO ENSURE PROPER SERVICING OF AIRCRAFT TIRE/WHEEL ASSEMBLIES. FAILURE TO USE THE PROPER PROCEDURES WILL INCREASE THE RISK OF DAMAGE OR PERSONAL INJURY.
- WARNINGS:** AIRCRAFT TIRES MUST ALWAYS BE INFLATED WITH A PROPERLY REGULATED INFLATION SOURCE. REGULATE THE SUPPLY LINE TO A PRESSURE NO GREATER THAN 1.5 TIMES THE OPERATING INFLATION PRESSURE. INFLATING A TIRE WITHOUT A PRESSURE REGULATOR PRESENTS A RISK OF PERSONAL INJURY AND/OR DAMAGE TO EQUIPMENT.
- WARNINGS:** USE A SUITABLE INFLATION CAGE WHEN INFLATING A NEWLY MOUNTED TIRE WHEEL (HUB) ASSEMBLY. ANY DAMAGE TO THE TIRE, THE WHEEL, AND WHEEL BOLTS OR IMPROPER PROCEDURE, MAY CAUSE THE TIRE/WHEEL ASSEMBLY TO BURST DURING THE INFLATION PROCESS, WHICH MAY RESULT IN SERIOUS OR FATAL INJURY.
- WARNINGS:** AIRCRAFT TIRE AND WHEEL ASSEMBLIES SHOULD BE TREATED WITH THE SAME CARE AS ANY OTHER HIGH PRESSURE VESSEL. IMPROPER HANDLING MAY LEAD TO SERIOUS INJURY.
- NOTE:** Wheel manufacturers publish specific instructions in their Component Maintenance Manuals (CMM). Follow the recommendations and procedures for equipment, materials, and proper wheel assembly in accordance with the applicable CMM.

401

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

2. Materials

- 2.1. Refer to Figure 401 for a list of materials necessary to assemble a tire on an aircraft wheel (hub). These materials are commercially available.

Name	Specification	Use
Cleaning Towels	Shop Towels	Clean Tire
Solvent	Denatured Alcohol	Clean Tire Mounting Area
Leak Detector	<ul style="list-style-type: none"> • Soap/Water Solution • Leak-Detection Fluid 	Test for Leakage
Nitrogen ^(*)	Dry, 97% purity or better	Tire Inflation Gas
Mounting Lubricant	Do NOT use petroleum-based products	Mounting aid for Bias tires only; Use is not required
Tire Talc or Soapstone		An aid used when installing the tube in tube-type tires and act as a lubricant between the tire and the tube
Tire Marking Pen/Crayon		Mark tire for information

Figure 401. Materials

* Federal Aviation Regulation (FAR) §25.733 and EASA certification specifications (CS) §25.733 require that for "aircraft with a maximum certified takeoff weight greater than 75,000 lbs, tires mounted on braked wheels must be inflated with dry nitrogen or other gases shown to be inert so that the gas mixture in the tire does not contain oxygen in excess of 5 percent by volume..."

FAA Airworthiness Directive 87-08-09 addresses this subject and specific aircraft models.

AD 87-08-09 may be downloaded at the following web site: <http://www.airweb.faa.gov>

FAR §25.733.e may be downloaded at the following web site:
http://www.faa.gov/regulations_policies

CS-25.733.e may be downloaded at the following web site:
http://www.easa.europa.eu/ws_prod/g/rg_certspeccs.php

NOTE: Michelin recommends that all tires, regardless of position or aircraft rating, be inflated with dry nitrogen of at least 97% purity. Some OEM (airframers) recommend 99.5% purity.

NOTE: When adding 97% pure nitrogen to an "empty" tire, the nitrogen concentration will end up about 95% when the pressure reaches about 125 psi.

NOTE: When the operating pressure is less than 125 psi and the desired concentration is \geq 95% nitrogen by volume, use a double inflation process if the source nitrogen is 97% purity.

NOTE: A double inflation requires that the tire be inflated with nitrogen to operational pressure, then fully deflated, then inflated a second time to operational pressure.

402

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

- CAUTION:** DO NOT USE A MOUNTING LUBRICANT WITH RADIAL-CONSTRUCTED TIRES. IN-SERVICE TIRE/WHEEL SLIPPAGE MAY RESULT. THE USE OF A MOUNTING LUBRICANT IS LIMITED TO BIAS-CONSTRUCTED TIRES ONLY.
- CAUTION:** DO NOT USE MOUNTING LUBRICANT WITH MAGNESIUM ALLOY WHEELS. MOUNTING LUBRICANT MAY DAMAGE THE WHEEL. CONSULT THE WHEEL CMM.
- CAUTION:** DO NOT USE LUBRICANTS MANUFACTURED FROM A PETROLEUM BASE. HYDROCARBONS HAVE A KNOWN DETRIMENTAL EFFECT ON RUBBER COMPOUNDS. TIRES EXPOSED TO HYDROCARBON CHEMICALS SHOULD BE IMMEDIATELY WASHED WITH DENATURED ALCOHOL FOLLOWED BY A SOAP/WATER SOLUTION.
- CAUTION:** CONFIRM ALL CHEMICALS USED ON THE TIRE AND WHEEL. IT IS POSSIBLE THAT UNDER THE HIGH PRESSURES AND LOAD EXERTED BY THE TIRE ON THE WHEEL, NORMALLY INERT CHEMICALS MAY CONTRIBUTE TO RAPID CORROSION AND/OR ABRASION OF THE WHEEL, OR DETERIORATION OF THE RUBBER SURFACE.

3. Tools, Fixtures and Equipment

- 3.1. Most modern aircraft wheels are of two types:
Split wheel type (i.e., two "halves" joined by removable tie bolts), or the removable flange type.
Both designs facilitate the mounting (and dismounting) of the tire.
- 3.2. Refer to Figure 402 for a list of tools and equipment necessary or helpful to assemble a tire on an aircraft wheel (hub).

NOTE: Equivalent alternatives can be used.

403

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

Tool	Specification	Use
Pressure Gauge	A calibrated gauge with a tolerance of $\pm 2\%$ of full scale ⁽¹⁾ , ± 1 least significant digit, or better. The gauge should have a scale suitable to pressure range being monitored.	Measure tire inflation pressure
Safety Inflation Cage	Free-standing metal structure sized to contain an aircraft tire/wheel assembly in case of failure during inflation	Guard against the effect of tire or wheel failure during initial inflation
Bead Seater		Assist seating of tire beads on wheel when unusual difficulty is experienced
Inert gas (less than 3% oxygen by volume) for inflation (nitrogen) Storage, valve, regulator, pressure gauge, hose, and device to attach to the tire	Proper system for storing and regulating inflation gas for tire/wheel inflation	To confirm that tires are inflated with a properly regulated pressure source

⁽¹⁾ SAE ARP 5265

NOTE: Michelin recommends a digital gauge with a tolerance of $\pm 0.25\%$, of full scale accuracy or better.

NOTE: The materials are all commercially available.

Figure 402. Tools and Equipment

4. Pre-Assembly Checklist for the Tire/Wheel Assembly (Hub)

WARNING: CAREFUL ATTENTION TO PROPER MOUNTING PROCEDURES IS NECESSARY TO SUCCESSFULLY MOUNT AIRCRAFT TIRES. MAKE SURE YOU ARE THOROUGHLY FAMILIAR WITH THE PROCEDURES AND INSPECT ALL KEY WHEEL PARTS BEFORE BEGINNING TO MOUNT A TIRE. IMPROPER PROCEDURES OR DAMAGED COMPONENTS CAN LEAD TO SERIOUS INJURY OR DAMAGE TO EQUIPMENT.

- 4.1. Refer to the Aircraft Maintenance Manuals (AMM) and the wheel manufacturers Component Maintenance Manuals (CMM), if available. Both documents take precedence over the following procedure in the event of a conflict.
- 4.2. Confirm that the O-Rings are of the proper material, as specified by the wheel manufacturer for the intended application and temperature conditions. Use a new O-Ring seal with the correct part number when mounting a tubeless tire.
- 4.3. Inspection of the wheel (hub): Follow the wheel manufacturer's instructions and procedures for inspecting and assembling the wheel (hub) components. Pay particular attention to the following:
 - 4.3.1. The bead seating area of the wheel must be clean and uncontaminated. Examine O-Ring sealing grooves in the wheel halves for damage or other debris that would prevent the O-Ring from properly seating.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

- 4.3.2. Nicks, burrs, small dents, or other damage that could prevent the surfaces from properly mating or sealing must be repaired.
- 4.3.3. Painted or coated surfaces should be in good condition; not badly chafed, chipped, etc.
- 4.3.4. Confirm that the fuse plugs, overinflation plugs, inflation valves and wheel plugs are in good condition, properly sealed against loss of pressure. Consult the manufacturer's instructions for proper torque values.
- 4.3.5. Replace O-Rings that have cracks, cuts, permanent deformations, or other damages.
- 4.4. Inspection of the tire: Confirm that the tire is correct for the intended application.
 - 4.4.1. Confirm the size, ply rating, speed rating, and part number. Refer to Chapter 2, as required.
NOTE: Refer to the Chapter 5 for serviceability criteria.
 - 4.4.2. Examine the outside of the tire and reject it for service if any of the following conditions are found:
 - 4.4.2.1. Cuts, tears, cracks, or foreign objects that penetrate the external rubber and expose ply cords.
 - 4.4.2.2. Permanent deformations.
 - 4.4.2.3. Cuts on the bead seating surfaces.
 - 4.4.2.4. Debris on the bead seating surfaces that cannot be removed with reasonable cleaning effort.
 - 4.4.2.5. Bead distortions.
 - 4.4.2.6. Contamination from foreign substances (oil, grease, brake fluid, hydraulic fluid, etc.).
NOTE: Contaminated rubber will be soft and may have blisters or swelling of the rubber.
 - 4.4.3. Examine the inside of the tire and remove any debris (trash, screws, rivets, etc.) from inside the tire. The tire is serviceable if there is no damage to the innerliner rubber.
CAUTION: OPERATING A TIRE WITH FOREIGN MATERIAL LEFT IN THE INTERIOR MAY DAMAGE THE INNERLINER RUBBER CAUSING A PRESSURE LOSS AND POSSIBLE TIRE FAILURE WHILE IN SERVICE.
CAUTION: DO NOT REMOVE THE BALANCE PAD. REMOVAL MAY DAMAGE THE INNERLINER RUBBER CAUSING A PRESSURE LOSS AND POSSIBLE TIRE FAILURE WHILE IN SERVICE.
NOTE: It is normal and acceptable to see a balance pad (Figure 403) attached to the interior of some aircraft tires. This pad is applied at the factory and brings tire balance within industry and regulatory standards. Do not confuse this pad with a repair.
NOTE: The writing on the MICHELIN® radial pad indicates the mass of the balance pad and a date that has no meaning after installation at the factory. The bias balance pad indicates the mass of the pad only. Refer to Figure 403.

405

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)



Figure 403. Balance Pad

- 4.4.4. Wipe the bead area of the tire with a clean towel. Confirm that the area is free of all dirt or foreign material. If necessary, clean this area with denatured alcohol or a soap/water solution.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

5. Mounting (Assembly) – Tubeless Tires

WARNING: REVIEW ALL WARNINGS, CAUTIONS, AND NOTES IN §1 AND §2 OF THIS CHAPTER.

NOTE: Use a new O-Ring seal with the correct part number when mounting a tubeless tire. Follow the specifications of the wheel manufacturer. Consult the CMM for the wheel.

- 5.1. Apply lubricant to the O-Ring as specified by the wheel manufacturer. Avoid excess lubricant. The excess may cause pollution damage.
CAUTION: APPLY ONLY LUBRICANTS SPECIFIED BY THE WHEEL MANUFACTURERS TO O-RINGS. AN INCORRECT LUBRICANT CAN CAUSE DAMAGE TO AN O-RING.
- 5.2. Install the O-Ring in the sealing groove of the inner wheel half assembly. Refer to Figure 404. Make sure the O-Ring is not twisted. Discard an O-Ring that is loose in the sealing groove.

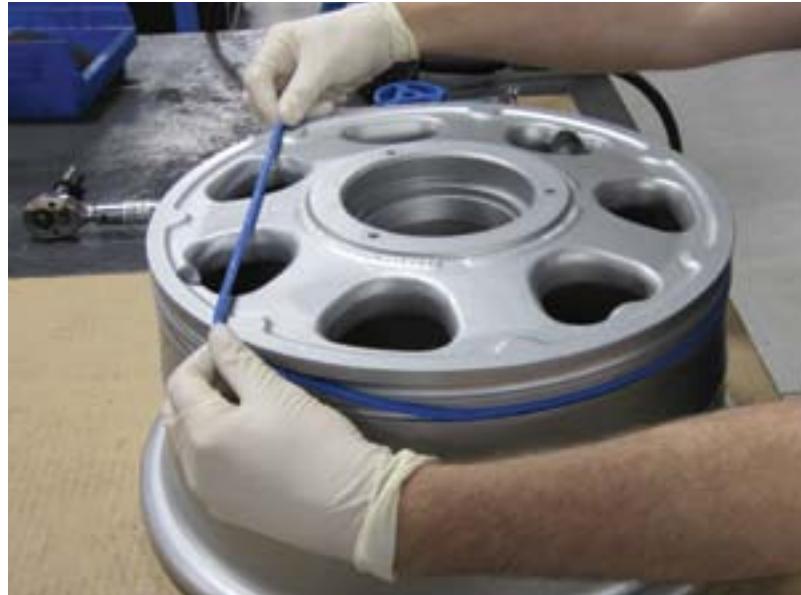


Figure 404. Installation of O-Ring on Inner Wheel Half

- 5.2.1. The Tire Bead area must be free of all dirt or foreign material.
 - 5.2.1.1. If necessary, clean this area with denatured alcohol or a soap/water solution. Allow drying time prior to assembly.
CAUTION: DO NOT USE A MOUNTING LUBRICANT WITH RADIAL TIRES. IN-SERVICE TIRE/WHEEL SLIPPAGE MAY RESULT. THE USE OF A MOUNTING LUBRICANT IS LIMITED TO BIAS-CONSTRUCTED TIRES ONLY.
- 5.3. For a BIAS tire – lubricate the beads if necessary.
CAUTION: DO NOT USE MOUNTING LUBRICANT WITH MAGNESIUM ALLOY WHEELS. MOUNTING LUBRICANT MAY DAMAGE THE WHEEL. CONSULT THE WHEEL CMM.
- 5.4. Install the tire on the inner wheel half.
 - 5.4.1. Mount the tire so that the serial number will show (away from the strut) when the tire is installed on the aircraft.

407

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

- 5.4.2. Press against the tire sidewalls to begin to seat the bead on the inner wheel half tube well. Center the tire on the inner wheel half so that the bead toe is in complete contact with the tube well (360 degrees).

NOTE: The tire will not completely seat against the wheel flange at this time.

CAUTION: WHEN ALIGNING THE WHEEL HALVES, BE CAREFUL NOT TO DAMAGE THE O-RING IN THE WHEEL BASE WHICH SEALS THE WHEEL HALVES. A DAMAGED O-RING MAY ALLOW THE ASSEMBLY TO LOSE PRESSURE.

- 5.5. Position the outer wheel half in the tire and on the inner wheel half.

NOTE: Some wheel manufacturers mark the light spot on each wheel half. (Refer to the wheel manufacturer's Component Maintenance Manual.) Wheel halves are assembled with these light spots approximately 180 degrees apart.

- 5.5.1. Align the red balance mark on the lower sidewall of the tire with the heavy spot on the wheel, unless otherwise specified by the wheel manufacturer.

NOTE: The red balance mark on the lower sidewall of the tire indicates the light point of the tire's balance. The red dot is not required on all tires. Refer to Figure 405.

NOTE: A properly balanced tire/wheel assembly improves the tire's overall wear characteristics. In addition to severe vibration, an unbalanced assembly will cause irregular and localized tread wear patterns that can reduce the overall performance life of the tire.

- 5.5.2. In the absence of specific wheel markings, align the tire's red balance mark with the wheel inflation valve.

- 5.5.3. In the absence of a tire balance mark, align the tire's serial number with the wheel inflation valve or wheel light spot.



Figure 405. Tire's Red Balance Mark

MICHELIN

AIRCRAFT TIRE

CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

- 5.6. Install tie bolts and complete the wheel assembly per the manufacturer's instructions.

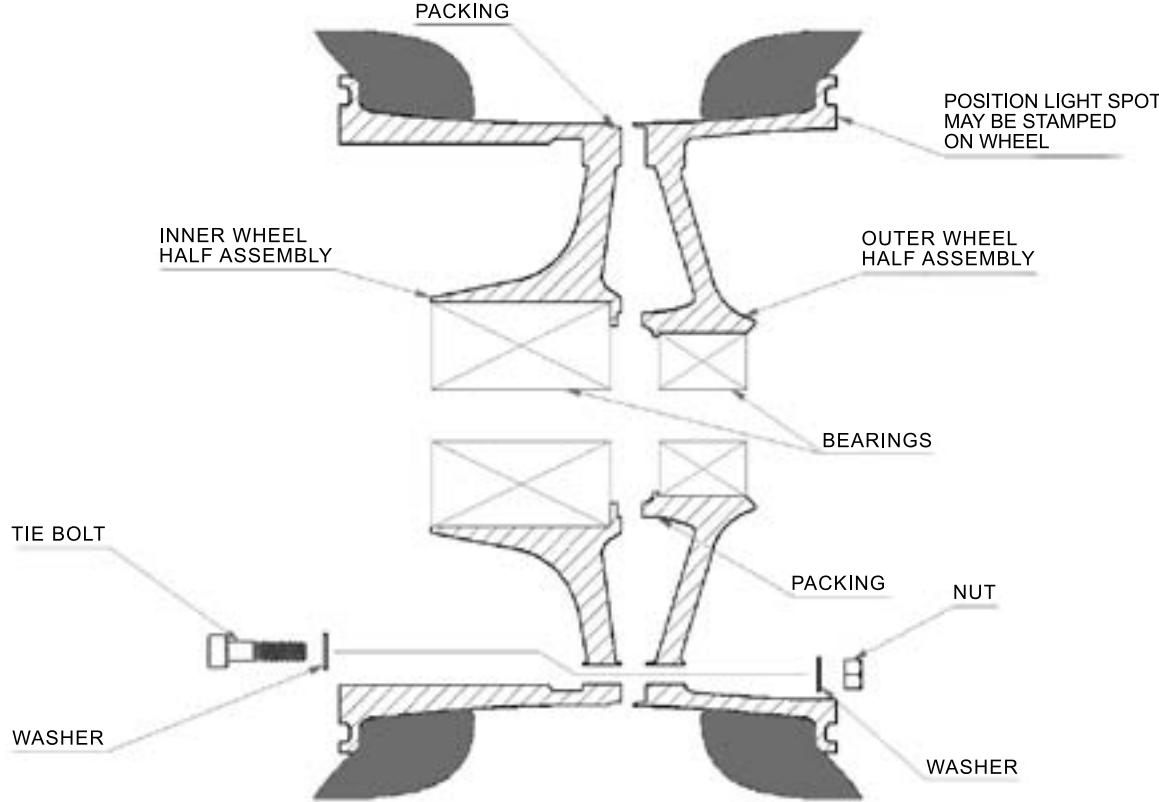


Figure 406. Aircraft Tire/Wheel Assembly

- 5.7. Refer to §7, in this Chapter for Initial Tire Inflation.

NOTE: The weight of the wheel may be sufficient to partially collapse the sidewalls of some radial tires that are not yet inflated when the assembly is upright. The flexible sidewall may make it difficult to roll the tire/wheel assembly prior to inflation.

6. Mounting (Assembly) – Tube-Type Tires

WARNING: REVIEW ALL WARNINGS, CAUTIONS, AND NOTES IN §1 AND §2 OF THIS CHAPTER.

- 6.1. Inspect the inside of the tire and remove any foreign objects or contaminants. Verify that the tire innerliner is free of any damage or cracks.

CAUTION: REMOVE ANY MANUFACTURING STICKERS FOUND ON THE INNERLINER. THE LABEL CAN CAUSE DAMAGE TO A TUBE AND RESULT IN LOSS OF INFLATION PRESSURE.

CAUTION: A NEW TUBE SHOULD BE USED WHEN INSTALLING A NEW TIRE. A USED TUBE WILL GROW IN SERVICE AND MAY BE TOO LARGE TO USE IN A NEW TIRE. A TUBE THAT IS TOO LARGE MAY CAUSE A FOLD OR CREASE, WHICH COULD DEVELOP INTO A SPLIT THAT WILL CAUSE THE RELEASE OF PRESSURE.

NOTE: Aircraft tires can be expected to grow as much as 12% in service. In addition, tubes are manufactured slightly smaller than the tire cavity to prevent folds and wrinkles at installation. Combining both growth factors, a used tube may be as much as 25% larger than the original size. The excess size of a used tube may cause a fold or crease. Refer to Figure 407. The crease could cause the tube to fail.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

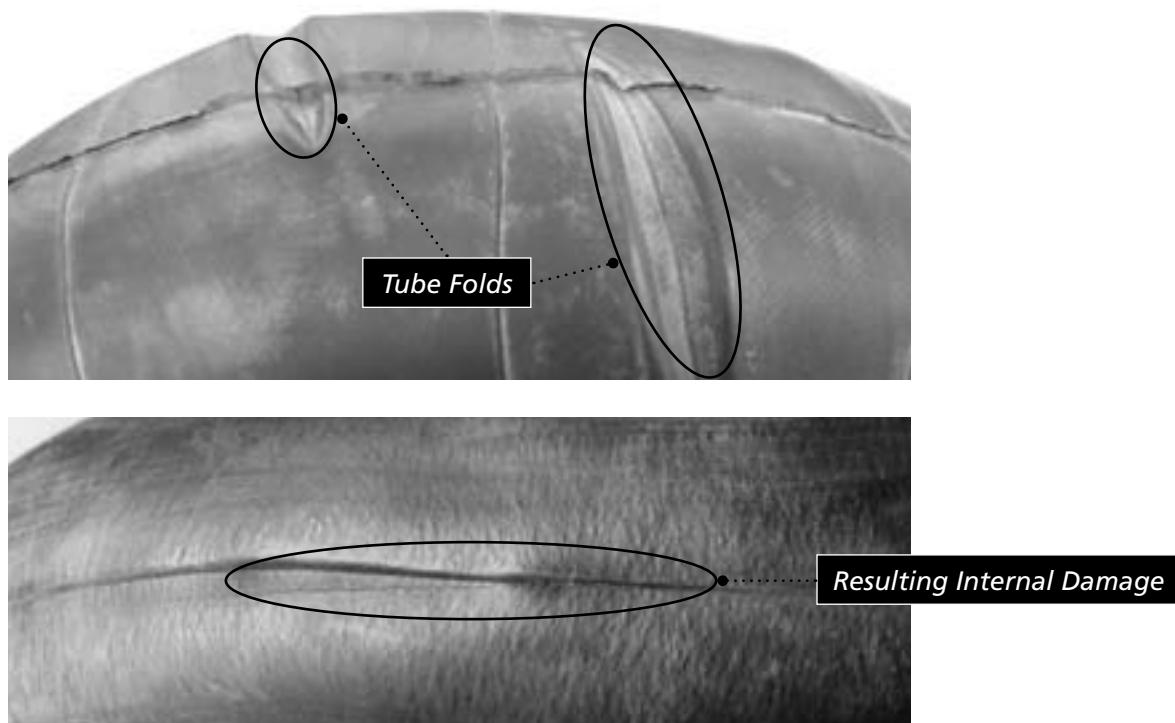


Figure 407. Example of Tube Folds

NOTE: Bias Tires: All MICHELIN® bias (cross ply) tires, including tubeless tires, are suitable for operation with tubes approved for the particular tire size and application on tube type wheels.

CAUTION: ALL MICHELIN® RADIAL AIRCRAFT TIRES ARE OF TUBELESS DESIGN. DO NOT USE A TUBE IN AN AIRCRAFT RADIAL TIRE. DO NOT MOUNT A MICHELIN® RADIAL TIRE ON A TUBE TYPE WHEEL. IMPROPER ASSEMBLY MAY CAUSE DAMAGE TO THE TIRE.

- 6.2. Examine the tube for any cuts, cracks, or other damages. Do not use a tube that appears to be damaged.
- 6.3. Dust the tube and inside of the tire with Tire Talc or Soapstone.
NOTE: Dusting with Talc or Soapstone prevents the tube from sticking to the inside of the tire, reduces abrasion, and lessens the chances of wrinkling or folds.
- 6.4. Partially inflate the tube until it begins to take shape without stretching.
- 6.5. Install the tube into the new tire with the valve stem on the serial number side of the tire next to the red mark that indicates the light spot of the tire.
- 6.6. Industry-practices recommend that tires are mounted with the serial number to the outboard wheel half.
- 6.7. Inflate the tube until it just begins to assume the shape of the tire. Feel for wrinkles/creases between tube and tire. Using the valve, move the tube back and forth slightly within the tire to remove any wrinkles. If the tube does not move easily, deflate slightly. If necessary repeat the process.
CAUTION: DO NOT OVERSTRETCH THE RUBBER AT THE BASE OF THE VALVE. DAMAGE TO THE RUBBER COULD CAUSE THE TUBE TO FAIL.
- 6.8. Install the tire/tube assembly on the inner wheel half.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

- CAUTION:** DO NOT FASTEN THE VALVE TO THE RIM UNTIL AFTER FINAL INFLATION. OVERSTRETCH OF THE ADJACENT RUBBER MAY RESULT.
- 6.9. Position the outer wheel half in the tire and on the inner wheel half. When marked, the wheel light spots should be assembled approximately 180 degrees apart (refer to the wheel manufacturer's CMM).
NOTE: Many wheel manufacturers today mark the light spot on each wheel half.
NOTE: Confirm that the tube valve stem (heavy spot) or the wheel light spot is aligned with the tire's red mark (light spot).
NOTE: A properly balanced tire/wheel assembly improves the tire's overall wear characteristics. In addition to severe vibration, an unbalanced assembly will cause irregular and localized tread wear patterns that can reduce the overall performance life of the tire.
- 6.9.1. Install tie bolts and complete the wheel assembly per the manufacturer's instructions.

7. Inflation of a Tire/Wheel Assembly to Operational Pressure

- 7.1. **WARNINGS, CAUTIONS, and NOTES** for this section.

WARNING: AIRCRAFT TIRES, AT AMBIENT TEMPERATURE, CAN BE OPERATED UP TO OR AT RATED INFLATION PRESSURE. EXTREMELY HIGH INFLATION PRESSURES MAY CAUSE THE AIRCRAFT WHEEL OR TIRE TO BURST, WHICH MAY RESULT IN SERIOUS OR FATAL BODILY INJURY.

WARNING: FOLLOW THE INSTRUCTIONS AND PROCEDURES OF THE WHEEL MANUFACTURER FOR THE ASSEMBLY OF THE WHEEL (HUB) COMPONENTS TO ENSURE PROPER SERVICING AIRCRAFT TIRE/WHEEL ASSEMBLIES. FAILURE TO USE THE PROPER PROCEDURES WILL INCREASE THE RISK OF DAMAGE OR PERSONAL INJURY.

WARNING: AIRCRAFT TIRES MUST ALWAYS BE INFLATED WITH A PROPERLY REGULATED INFLATION SOURCE. REGULATE THE SUPPLY LINE TO A PRESSURE NO GREATER THAN 1.5 TIMES THE OPERATING INFLATION PRESSURE. INFLATING A TIRE WITHOUT A PRESSURE REGULATOR PRESENTS A RISK OF PERSONAL INJURY AND/OR DAMAGE TO EQUIPMENT.

WARNING: USE A SUITABLE INFLATION CAGE WHEN INFLATING A NEWLY MOUNTED TIRE WHEEL (HUB) ASSEMBLY. ANY DAMAGE TO THE TIRE, THE WHEEL, AND WHEEL BOLTS OR IMPROPER PROCEDURE, MAY CAUSE THE TIRE/WHEEL ASSEMBLY TO BURST DURING THE INFLATION PROCESS, WHICH MAY RESULT IN SERIOUS OR FATAL INJURY.

CAUTION: CONFIRM THAT ALL WHEEL TIE BOLTS, VALVES, OVERINFLATION PLUGS, FUSE PLUGS, ETC. HAVE BEEN PROPERLY INSTALLED AND TORQUED TO WHEEL MANUFACTURER'S SPECIFICATIONS BEFORE BEGINNING INFLATION. IMPROPER ASSEMBLY COULD ALLOW THE ASSEMBLY TO LEAK.

WARNING: THE INFLATION PRESSURE SOURCE SHOULD BE LOCATED 10 METERS (30 FEET) AWAY FROM THE SAFETY CAGE WITH A VALVE, REGULATOR, AND PRESSURE GAUGE INSTALLED AT THAT POINT. THE INFLATION LINE SHOULD THEN BE RUN TO THE SAFETY CAGE AND ATTACHED TO THE WHEEL VALVE. PERSONNEL NEAR THE SAFETY CAGE INCREASES THE RISK OF INJURY.

CAUTION: REFER TO THE AIRCRAFT MAINTENANCE MANUAL (AMM) TO DETERMINE THE OPERATING PRESSURE. DIFFERENT OPERATING PRESSURES ARE USED DEPENDING ON TIRE SIZE, AIRCRAFT LOADS, AND OPERATING CONDITIONS. INCORRECT OPERATING PRESSURE CAN CAUSE DAMAGE TO TIRES, WHEELS, AND AIRCRAFT.

- 7.2. Initial Inflation of tire/wheel assemblies.
- 7.2.1. Place the tire/wheel assembly into a suitable safety cage for inflation.
NOTE: A suitable inflation safety cage must consider the largest tire size and greatest operational inflation pressure.
- 7.2.2. Attach the inflation line to the valve stem.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

- 7.2.3. Inflate the tire/wheel assembly to the correct operating pressure for the intended use.
NOTE: Some tire/wheel assemblies may be suitable for different aircraft. Confirm the recommended pressure for the aircraft on which it is to be mounted.
- 7.2.4. Additional steps for tube type tires:
 - 7.2.4.1. Completely deflate the tube/tire.
 - 7.2.4.2. Re-inflate the tube/tire to the correct operating pressure.
NOTE: This procedure helps to remove any wrinkles in the tube and allows any trapped air between the tire and tube to escape.
 - 7.2.4.3. If required, fasten the valve to the wheel with washer and lock ring or lock nut.
 - 7.2.4.4. Check pressure in 24 hours. Re-inflate to operating pressure (assumes trapped air escaped). Repeat each day until all trapped air has escaped and pressure stabilizes.
NOTE: Tube-type tires require special pressure maintenance for several days after being placed in service due to air possibly being trapped between the tube and the tire. Once the tire is placed in service, this trapped air escapes through the valve stem hole of the wheel. The trapped air that escapes will reduce the gauge pressure.
- 7.2.5. Complete the pressure retention check.

8. Pressure Retention Check (Leak Check) – After Mounting

WARNING: REVIEW ALL **WARNINGS, CAUTIONS, AND NOTES** IN §1, §2, AND §7 OF THIS CHAPTER.

- 8.1. Refer to Figures 401 and 402, for materials, tools, and equipment.
- 8.2. Pressure-retention checks are designed to make sure that tire/wheel assemblies meet industry-accepted standards for pressure retention prior to releasing them for service on aircraft. This important process confirms the tire/wheel assembly is ready for service on the aircraft and helps avoid damages due to underinflation conditions.
NOTE: The pressure check validates the ability of both the tire and wheel to hold pressure. Attention must be directed to both the tire and wheel if a pressure loss is detected.
 - 8.2.1. The procedure is essentially the same for all aircraft tires: bias, radial, tubeless, and tube-type.
 - 8.2.2. Tire stretch - It is normal for aircraft tires to become larger (stretch or grow) when inflated to operating pressure. Any procedure used to properly check for tire leakage must allow for tire stretch.
 - 8.2.2.1. Tire stretch can take up to 12 hours. Tire stretch increases the internal volume of the tire, which reduces the inflation pressure.
 - 8.2.2.2. Tire stretch and temperature must be stable in order to know if any pressure change is a result of leakage.
- 8.3. Three (3) pressure-retention procedures are described below:
 - **Industry Standard** procedure
 - **Alternate** procedure
 - **Emergency** procedure
 - 8.3.1. The **Industry Standard**-retention procedure has been the standard of the aircraft tire industry for many years. It is designed to provide a complete check of tire/wheel assembly pressure retention prior to releasing them for use on aircraft. This procedure requires a 12-hour stretch period and a 24-hour period to measure pressure loss. It is recommended by most airframers.
NOTE: Airbus SIL 32-119 and Boeing SL of 6 December 2006, titled "Suggested Shop Maintenance Procedures for Wheel and Tire Assemblies," recommend the 12-hour stretch and the 24-hour leak check.

412

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

- 8.3.2. The **Alternate**-retention procedure is used by some operators in order to reduce the time required for the process. The time allocated for stretch, and the time for the leak check are reduced. The tolerance allowed is also reduced. This procedure requires a calibrated gauge with a tolerance of $\pm 0.25\%$ of full scale, or better, and with a scale suitable to the pressure range being monitored (Note that the tolerance here is less than the tolerance recommended in Figure 402.)
- 8.3.3. The **Emergency**-retention procedure may be used to perform a pressure retention check on a newly mounted tire/wheel assembly when time does not allow the Industry Standard or Alternative procedure to be used.
 - 8.3.3.1. The **Emergency** procedure should be used only when faced with an Aircraft on Ground (AOG) type situation. This procedure requires a calibrated gauge with a tolerance of $\pm 0.25\%$ of full scale, or better. The gauge should have a scale suitable to the pressure range being monitored (Note that the tolerance here is less than the tolerance recommended in Figure 402.)
- 8.4. Industry Standard Pressure-Retention Procedure

WARNING: REVIEW ALL **WARNINGS, CAUTIONS, AND NOTES** IN §1, §2, AND §7 OF THIS CHAPTER.

 - 8.4.1. Inflate the newly mounted tire/wheel assembly to operating pressure (P_N) for the aircraft application as specified in the Aircraft Maintenance Manual (AMM).

NOTE: Refer to Figure 409.
 - 8.4.2. Store the inflated tire/wheel assembly for 12 hours to allow for tire stretch.
 - 8.4.3. After the 12-hour stretch period, **measure** the inflation pressure (P_G). Confirm that the ambient temperature of the tire/wheel assembly has not changed by more than 3°C (5°F).

NOTE: Changes in ambient temperature will cause a corresponding change in inflation pressure (gauge pressure). A 3°C (5°F) decrease in temperature will result in a 1% decrease in inflation pressure. An increase in temperature will cause an increase in the inflation pressure. Refer to Figure 409.
 - 8.4.4. A pressure drop of less than or equal to (\leq) 10% during the stretch period is considered normal. Any loss more than that may indicate a leakage problem.
 - 8.4.5. Re-inflate the tire to the specified operating pressure (P_N).
 - 8.4.6. Wait 24 hours to allow for any pressure loss.
 - 8.4.7. After a 24-hour wait, **measure** the inflation pressure (P_G). Confirm that the ambient temperature of the tire/wheel assembly has not changed by more than 3°C (5°F).
 - 8.4.7.1. If inflation pressure (P_G) is **equal to or greater than** (\geq) 95% of the specified operating pressure (P_N), **accept** the tire/wheel assembly for in-service usage or line maintenance storage. (Refer to §12, in this chapter, for recommendations on line maintenance storage.)

Or

 - 8.4.7.2. If the inflation pressure (P_G) is **less than** ($<$) 95% of the specified operating pressure (P_N), **inspect** the tire/wheel assembly for leaks. Refer to §9, in this chapter.
 - Use a soap solution on tire beads and other susceptible wheel components (valves, fuse plugs, over-pressurization plugs, wheel half parting line, etc.). If soap bubbles or leaks are found. Repair any leak.
 - Return to 8.4.1.

NOTE: It is normal to see bubbles at the tire vent holes, just above the wheel flange, any time while the tire is inflated. Refer to Chapter 1, §6, Figure 107.

NOTE: Do not identify a tire as leaking solely on the rate of bubbles from the vent holes. A leaking tire/wheel assembly should be determined by the pressure loss, as measured with a calibrated gauge, over a period of time.

413

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

Or

- 8.4.7.3. If the source of pressure loss cannot be determined, reject the tire/wheel assembly.
- Do not accept a tire/wheel assembly into service until the source of the leak is identified and corrected.

NOTE: A maximum daily pressure loss of 5% or less is considered acceptable for a 24-hour period (TSO, AC 20-97B, SAE ARP5265). Some airframers recommend a maximum leak rate of less than (<) 3%. Typical leak rates are < 3% for a 24-hour period.

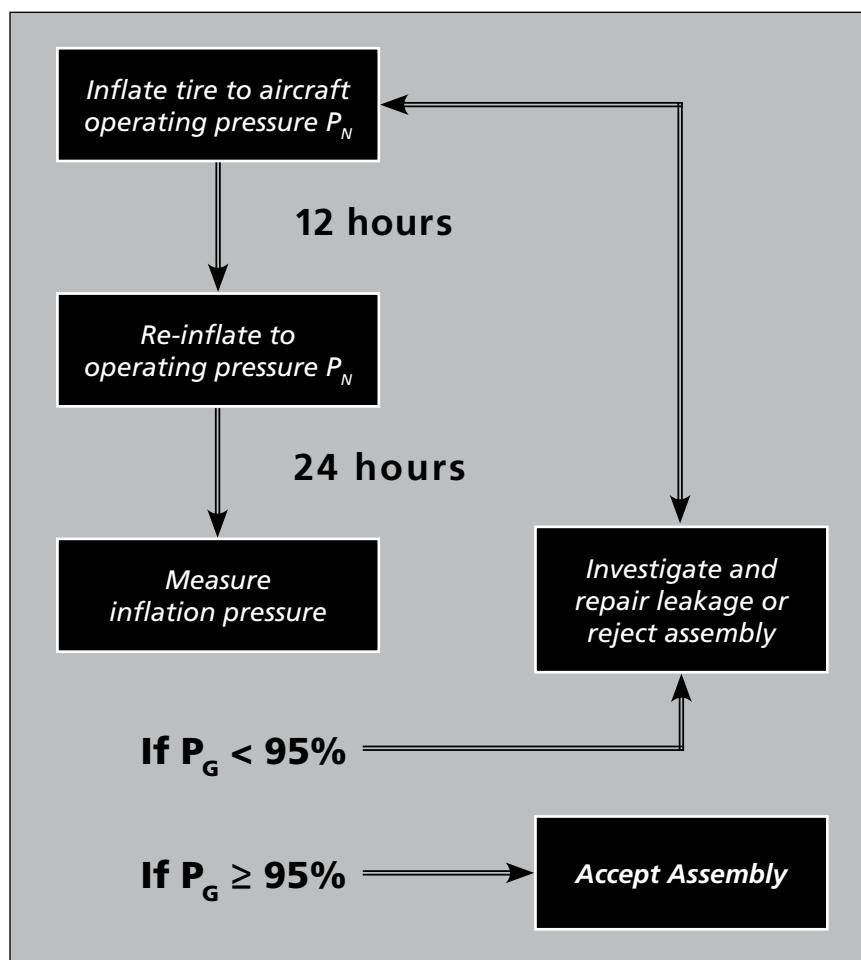


Figure 409. Industry Standard Pressure-Retention Procedure

8.5. Alternate Pressure Retention Procedure

WARNING: REVIEW ALL WARNINGS, CAUTIONS, AND NOTES IN §1, §2, AND §7 OF THIS CHAPTER.

- 8.5.1. Inflate the newly mounted tire/wheel assembly to operating pressure for the aircraft application as specified in the Aircraft Maintenance Manual (AMM).

NOTE: Refer to Figure 410.

- 8.5.2. Store (Stage) the inflated tire/wheel assembly for three (3) hours to allow for partial tire stretch.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

415

- 8.5.3. After the three (3)-hour stretch, **measure** the inflation pressure (P_G). Confirm that the ambient temperature of the tire/wheel assembly has not changed by more than 3°C (5°F).
 - 8.5.3.1. If inflation pressure (P_G) is **equal to or greater than** (\geq) 90% of the specified operating pressure (P_N), proceed to §8.5.4.
Or
 - 8.5.3.2. If inflation pressure (P_G) is **less than** ($<$) 90% of the specified operating pressure (P_N), **inspect** the tire/wheel assembly for leaks. Refer to §9, in this chapter.
 - Use a soap solution on tire beads and other susceptible wheel components (valves, fuse plugs, over-pressurization plugs, wheel half parting line, etc.). If soap bubbles or leaks are found, repair any leak.
 - Return to §8.5.1, in this chapter.

NOTE: It is normal to see bubbles at the tire vent holes, just above the wheel flange, any time while the tire is inflated. (Refer to Chapter 1, §6.)

NOTE: Do not identify a tire as leaking solely on the rate of bubbles from the vent holes. A leaking tire/wheel assembly should be determined by the pressure loss, as measured with a calibrated gauge, over a period of time.
 - 8.5.4. Re-inflate the tire to the specified operating pressure (P_N).
 - 8.5.5. Wait 12 hours to allow for any pressure loss.
 - 8.5.6. After 12-hour storage period, **measure** inflation pressure (P_G). Confirm that the ambient temperature of the tire/wheel assembly has not changed by more than 3°C (5°F).
 - 8.5.6.1. If inflation pressure (P_G) is **equal to or greater than** (\geq) 97.5% of the specified operating pressure (P_N), **accept** the tire/wheel assembly for in-service usage or line maintenance storage.
 - 8.5.6.2. Re-inflate the tire to the specified operating pressure (P_N). (Refer to §12, in this chapter, for recommendations on line maintenance.)
Or
 - 8.5.6.3. If the inflation pressure (P_G) is **less than** ($<$) 97.5% of the specified operating pressure (P_N), re-inflate the tire to operating pressure, then wait 24 hours to allow for any pressure loss.
 - 8.5.7. After 24-hour wait, **measure** the inflation pressure (P_G). Confirm that the ambient temperature of the tire/wheel assembly has not changed by more than 3°C (5°F).
 - 8.5.7.1. If inflation pressure (P_G) is **equal to or greater than** (\geq) 95% of the specified operating pressure (P_N), **accept** the tire/wheel assembly for in-service usage or line maintenance storage. (Refer to §12, in this chapter, for recommendations on line maintenance.)
Or
 - 8.5.7.2. If the inflation pressure (P_G) is **less than** ($<$) 95% of the specified operating pressure (P_N),
 - Reject the tire/wheel assembly.**Or**
 - Use a soap solution on tire beads and other susceptible wheel components (valves, fuse plugs, over-pressurization plugs, wheel half parting line, etc.). If soap bubbles or leaks are found, repair any leak.
 - Return to §8.5.1.
 - 8.5.7.3. Record the measured pressure loss (psi/bar) and time.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

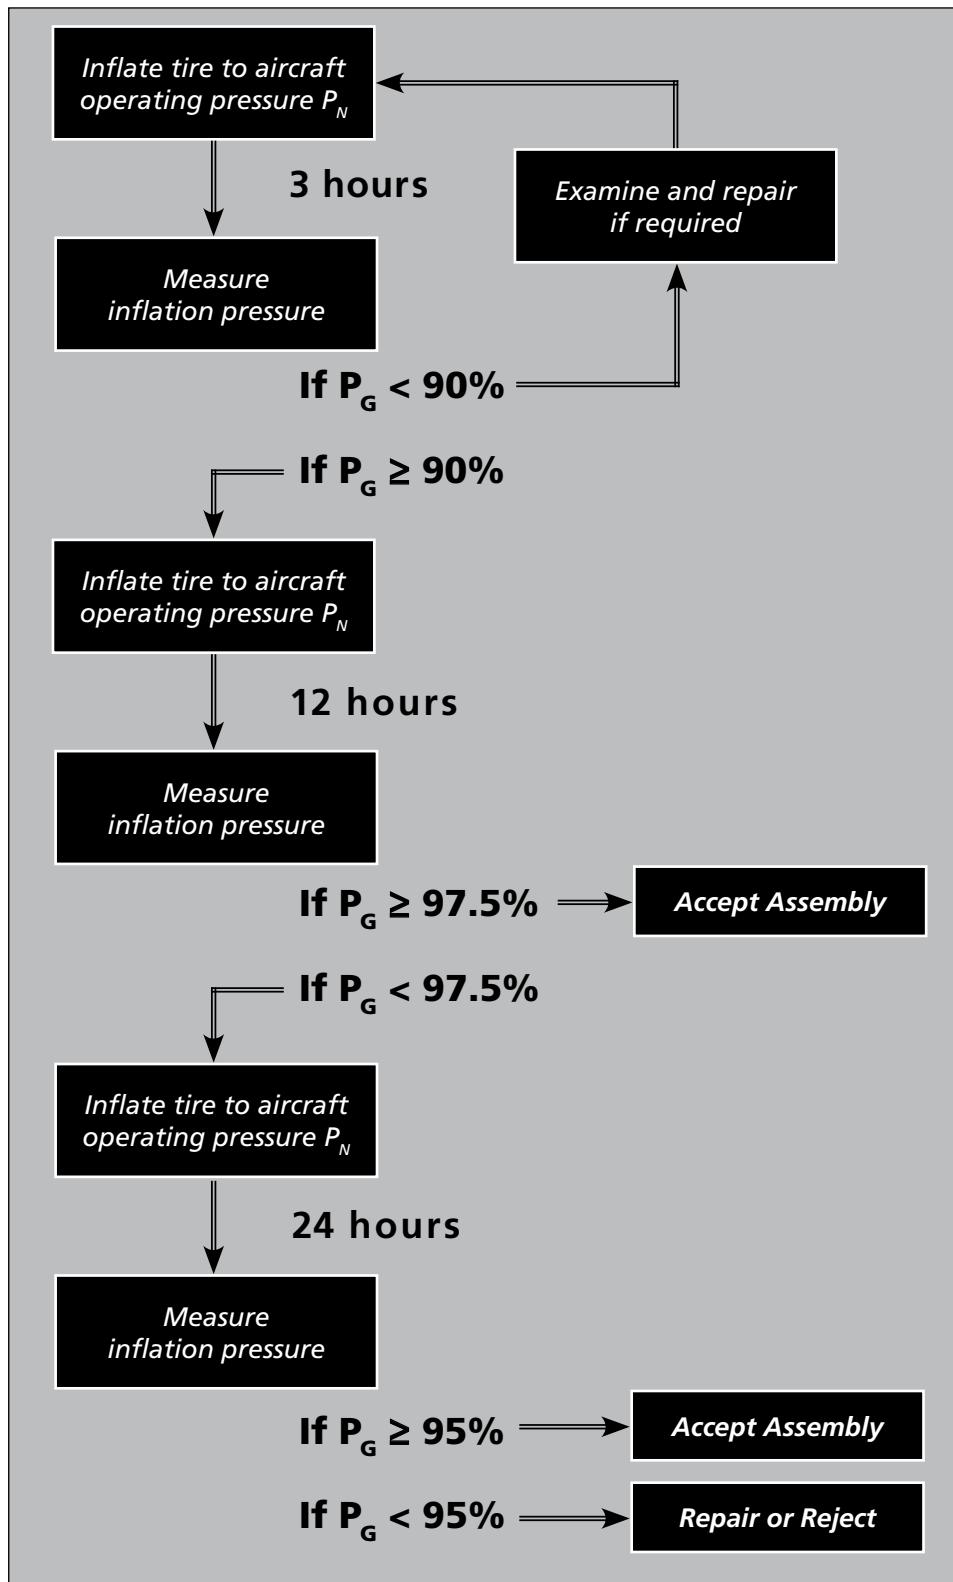


Figure 410. Alternate Pressure-Retention Procedure



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

8.6. Emergency Pressure-Retention Procedure

WARNING: REVIEW ALL WARNINGS, CAUTIONS, AND NOTES IN §1, §2, AND §7 OF THIS CHAPTER.

NOTE: This procedure should only be used when faced with an AOG situation. This procedure requires a calibrated gauge with a tolerance of $\pm 0.25\%$ of full scale, or better, and with a scale suitable to the pressure range being monitored (Note that the tolerance here is less than the tolerance recommended in Figure 402.)

NOTE: This procedure requires a cold tire inflation check every 24 hours during the first 48 hours of service for the assembly. Refer to Chapter 5, §3 for normal daily pressure checks.

NOTE: Refer to Figure 411.

8.6.1. Inflate the newly mounted tire/wheel assembly to operating pressure for the aircraft application as specified in the aircraft maintenance manual. Refer to §7 in this chapter for inflation and safety procedures.

8.6.2. Wait at least 30 minutes.

8.6.3. Spray the complete tire/wheel assembly with a leak-detection solution. Inspect the tire beads and wheel components (valves, fuse plugs, over-pressurization plugs, wheel half parting line, etc.). Look for soap bubbles.

8.6.3.1. If no bubbles are found on wheel components, Conditionally Accept the assembly. Record the measured pressure loss (psi/bar) and time period.

Or

8.6.3.2. If leaks are found, repair any leak. Refer to §9, in this chapter. If the assembly is repaired and placed back in service return to §8.6.1 of this chapter.

Or

- Reject the tire/wheel assembly.

NOTE: It is normal to see bubbles at the tire vent holes, just above the wheel flange, any time while the tire is inflated. Refer to Chapter 1, §6.

NOTE: Do not identify a tire as leaking solely on the rate of bubbles from the vent holes. A leaking tire/wheel assembly should be determined by the pressure loss, as measured with a calibrated gauge, over a period of time.

8.6.4. If the tire is Conditionally Accepted, inflate the tire to 105% of the operating inflation pressure (unloaded) and install the tire/wheel assembly on the aircraft. The +5% inflation pressure is to compensate the tire stretch.

8.6.5. Measure the inflation pressure before each flight over the next 48 hours.

8.6.5.1. Accept the assembly if $P_g \geq 90\% P_n$. Apply the rules of inflation pressure maintenance contained in Chapter 5, Operation, §5.

8.6.5.2. Remove the assembly (and mate) if $P_g < 90\%$ following the inflation pressure maintenance schedule. Refer to Chapter 5, §5, Figure 503.

NOTE: There will be additional tire stretch during the first few flights resulting in lower gauge pressure, after allowing for any temperature change.

417

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

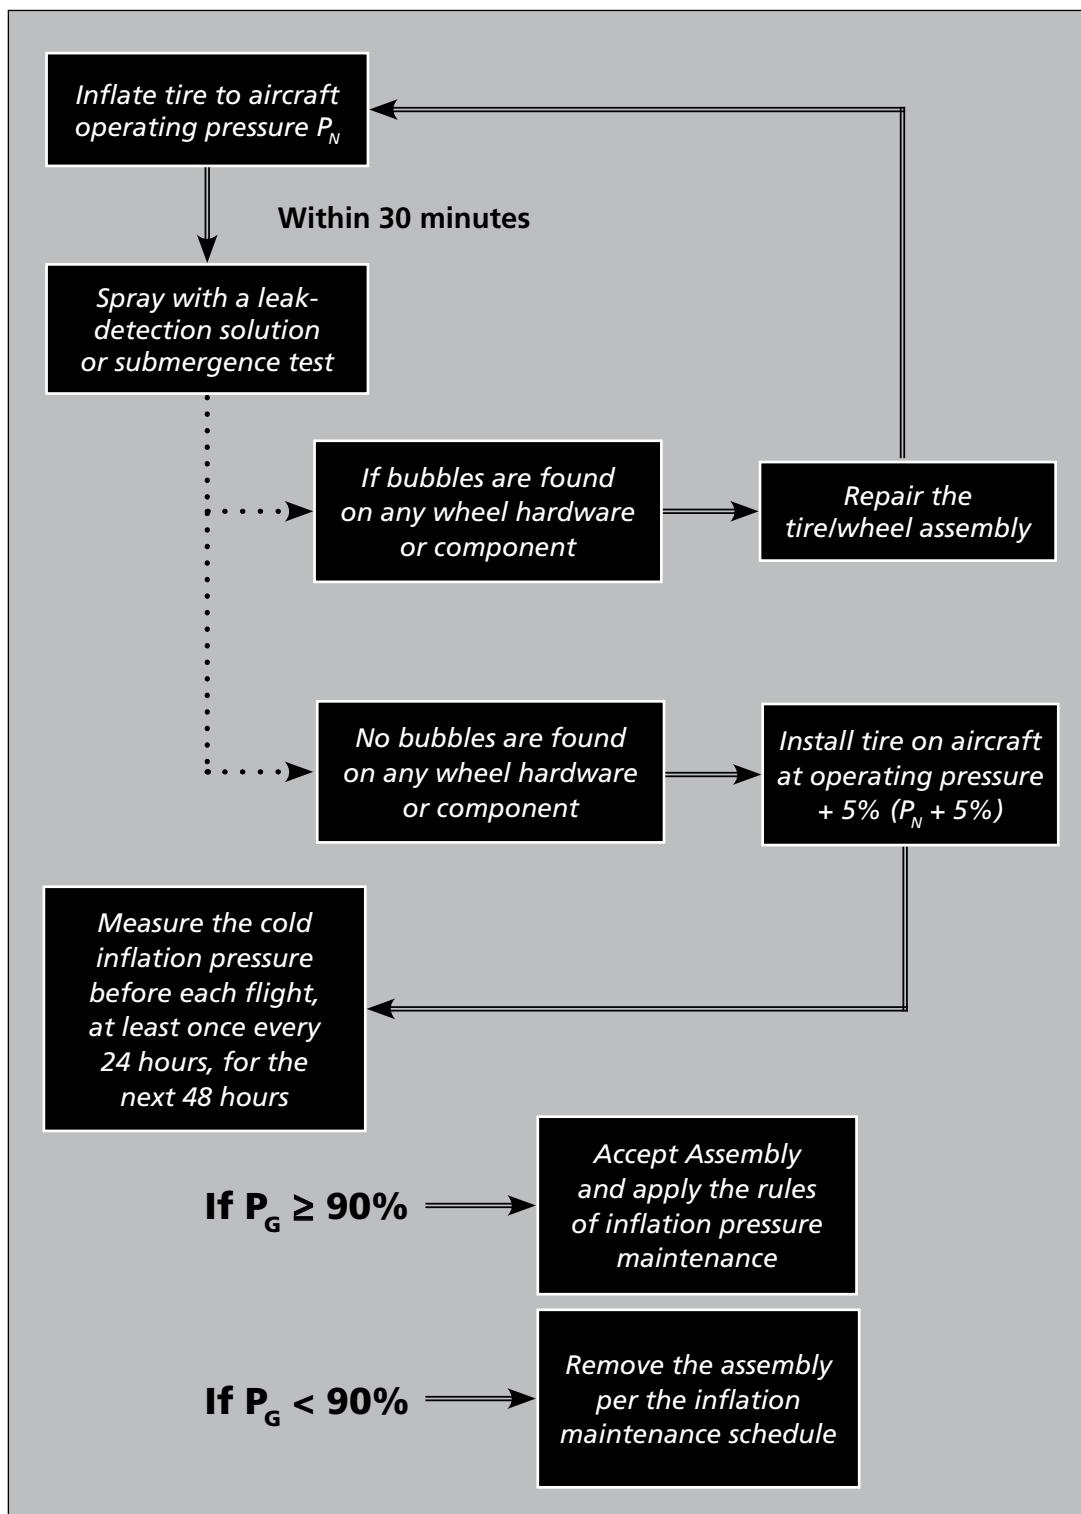


Figure 411. Emergency Pressure-Retention Procedure



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

9. Investigation for the Cause of Pressure Loss

- 9.1. Tire wheel assemblies that fail pressure-retention tests (>5% pressure loss in 24 hours), should be investigated for the cause of the pressure loss. Follow the guidelines below.
- NOTE:** Some airframers recommend a maximum leak rate of 3% in 24 hours.
- NOTE:** Assume that the pressure loss can be caused by any piece of the tire/wheel assembly.
- CAUTION:** DO NOT RETURN THE ASSEMBLY TO SERVICE IF THE INVESTIGATION FINDS PRESSURE LOSS GREATER THAN 5% IN A 24-HOUR PERIOD. REMOVE THE TIRE AND HAVE A CERTIFIED REPAIR STATION VALIDATE THE SERVICEABILITY OF THE TIRE.
- NOTE:** The source of a pressure loss can often be determined by applying leak detector solution (soap solution) to suspected areas of leakage or by total immersion of the tire/wheel assembly in a water bath.
- 9.2. Begin with the most simple checks first.
- 9.2.1. Confirm that the measurement is not affected by a change in ambient temperature before assuming an assembly should be removed for low pressure.
- 9.2.2. Apply a small amount of leak solution on the end of the valve stem.
- 9.2.2.1. If bubbles appear, replace the valve core and recheck.
- NOTE:** Each valve should have a valve cap on it to prevent contaminants from entering and damaging the valve core and to act as a secondary seal.
- 9.2.3. Apply leak solution to the fuse plugs.
- 9.2.3.1. If bubbles appear, replace the fuse plug.
- 9.2.4. Apply leak solution to the tread and sidewall areas.
- 9.2.4.1. If bubbles appear, circle the area and dismount the tire.
- NOTE:** It is normal to see bubbles at the tire vent holes, just above the wheel flange, any time while the tire is inflated. Refer to Chapter 1, §6, Figure 107.
- 9.2.5. Totally immerse the tire/wheel assembly in a water bath, if feasible. Where a water bath is not available, apply leak-detector solution to the entire tire/wheel assembly. Bubbles appearing anywhere other than at the vents on the lower sidewall indicate a leak.
- 9.2.5.1. Check the wheel base area for leaks from fatigue cracks.
- 9.2.5.2. Check the O-Ring seal of the wheel halves.
- 9.2.5.3. Check for bubbles in the wheel base area, parting half O-Ring, over-pressurization plug.
- 9.2.6. If no other leak source can be found, dismount the tire from the wheel.

419

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

Check	All Cases	Mounted Tire/ Wheel Assembly	Dismounted Tire and Tube	Dismounted Wheel
Initial Stretch Period (12-hour tire stretch)	X			
Changes in Ambient Temperature	X			
Venting of Tubeless Tires	X	X		
Release of Trapped Air in Tube-Type Tires	X	X		
Cut or Puncture		X	X	
Damaged Beads			X	
Improperly Seated Beads		X		
Leaking Valve Core		X		
Other Valve Problems		X		X
Improper Installation of O-Rings				X
Faulty Thermal Fuse Plug		X		X
Porous Wheels		X		X
Improperly Torqued Tie Bolts		X		
Wheel Gouges and Scratches		X		X
Corrosion or Wear on Bead Ledge Area				X
Knurls ⁽¹⁾				X
Damaged Sealing Surfaces		X		X
Wheel Assembly Holes				X
Wheel Cracks		X		X

⁽¹⁾ Knurls are diamond-shaped patterns on metal resulting from a machining process.

Figure 412. Pressure Loss Troubleshooting Chart

10. Transportation of an Inflated Tire/Wheel Assembly

CAUTION: NON-SERVICEABLE TIRE/WHEEL ASSEMBLIES SHOULD BE TRANSPORTED WITHOUT INFLATION PRESSURE. A DAMAGED ASSEMBLY COULD BURST, CAUSING DAMAGE OR PERSONAL INJURY.

CAUTION: TRANSPORT SERVICEABLE TIRE/WHEEL ASSEMBLIES IN ACCORDANCE WITH THE APPLICABLE REGULATORY BODY FOR THE AIRLINE.

NOTE: Transportation of a serviceable-inflated aircraft tire is covered by the U.S. Department of Transportation Code of Federal Regulations, 173.307 and 175.10, the International Air Transport Association (IATA). These regulations permit the transportation of serviceable aircraft tire/wheel assemblies at pressures not exceeding their rated pressures.

10.1. Serviceable tire/wheel assemblies may be transported fully pressurized in the cargo area of an aircraft.

NOTE: Operators may wish to consult their own regulatory agency to determine if there are any restrictions concerning the transportation of inflated tire/wheel assemblies in an airplane.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

- 10.2. If desired, an operator may reduce the inflation pressure to approximately 25% of operating pressure or approximately 40 psi to 50 psi (2.75 to 3.5 bar), whichever is the lower pressure.

NOTE: Sufficient pressure must be maintained in the tire/wheel assembly to keep the bead seated on the wheel. The reduced inflation pressure also reduces the potential energy of the compressed gas in the tire/wheel assembly in the event of damage during shipment.

- 10.3. Re-inflate the tire to operating pressure in accordance with the AMM, before placing the tire into service.

NOTE: If the tire wheel assembly has been shipped at reduced pressure (25% of operational pressure) and the pressure is adjusted back to operational pressure, allow for tire stretch or inflate the tire to 105% of operational pressure (unloaded).

11. Storage of an Inflated Tire/Wheel Assembly

- 11.1. Tires should be stored in a cool, dry, dust-free location between 32°F and 104°F (0°C and 40°C). Prolonged high storage temperatures accelerate the aging process of rubber components.

- 11.2. Michelin recommends reducing the inflation pressure to approximately 25% of operating pressure or approximately 40 psi to 50 psi (2.75 to 3.5 bar), whichever is less, to minimize the effects of ozone attack. Refer to §11.9, in this chapter and the note that follows.

- 11.3. Do not store the tire exposed to direct sunlight or to high ozone concentrations. Ultraviolet rays generate ozone. Ozone can cause cracking of exposed rubber.

- 11.4. Do not store tire/wheel assemblies near electrical equipment such as generators that generate a high concentration of ozone. Avoid fluorescent lighting or ensure that the lighting is off except when required.

- 11.5. Avoid contact with contaminants (oil, grease, jet fuel, and other hydrocarbon based materials). They will cause damage to rubber.

- 11.6. Tire/wheel assemblies should be stored in a vertical position. The surface of the tire rack on which the weight of the tire rests should be flat, 3 to 4 inches (7.5 to 10 cm) wide to prevent distortion of the tire.

- 11.7. Michelin has no limitation on storage time of an inflated tire. The serviceability of a properly stored tire/wheel assembly is based on visual inspection.

- 11.8. Michelin recommends that the tire be inspected every 12 months to confirm continued serviceability in accordance with this Care and Service Manual.

11.8.1. This storage and re-inspection interval can be repeated multiple times as long as the tire meets all serviceability criteria.

- 11.9. The tire/wheel assembly must be inflated to operating pressure, in accordance with the AMM, before being placed in service. Refer to Figure 413.

NOTE: If the tire/wheel assembly has been stored at reduced pressure (approximately 25% of operational pressure) or if the tire has been in storage and the inflation pressure is less than 50% of operational pressure (unloaded), inflate the tire to 105% of operational pressure (unloaded) (operating pressure times 1.05) to allow for tire stretch.

- 11.10. To maximize tire life, it is recommended that replacement stock be rotated. FIFO: First-In, First-Out.

421

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

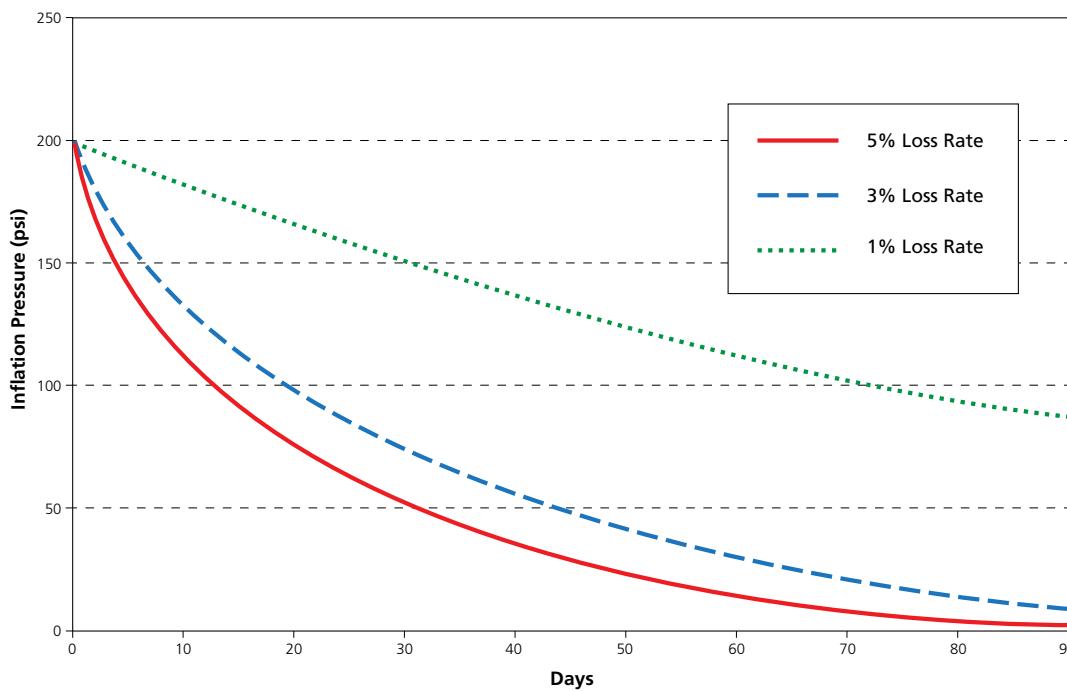


Figure 413. Tire Pressure Loss Over Time

12. Periodic Re-inspection of an Inflated Tire

- 12.1. Measure tire inflation pressure.
 - 12.1.1. If the tire pressure is to be adjusted, refer to the AMM for the correct operational pressure. Refer to the **WARNINGS**, **CAUTIONS**, and **NOTES**, in §1, 2 and 7, in this chapter.
 - 12.1.2. If the measured pressure is less than storage pressure (25% or 40 psi (2.75 bar) of operational pressure), inflate to storage pressure in accordance with operator policy.
- 12.2. Visually inspect the exterior of the tire for cracking, damages, or any other condition. Refer to aircraft AMM and §4, in this chapter.
 - 12.2.1. If all visual serviceability criteria are met - Accept the tire.
 - 12.2.2. If serviceability criteria have been exceeded - Reject the tire.
 - 12.2.2.1. Circle the area of concern with a suitable tire marker.
 - 12.2.2.2. Dismount the tire from the wheel and return to the supplier.

13. Mounting the Tire/Wheel Assembly on the Aircraft

- 13.1. Visually inspect the tire for any damage from handling, storage, or contaminants.
 - 13.1.1. If serviceability criteria have been exceeded - Reject the tire.
- NOTE:** Some radial tires may show a slight deformation in the sidewall after being mounted on the wheel and inflated. The deformation results from a small amount of extra rubber at the splice of sidewall rubber. It is normally less than 15 mm (0.6 inch) wide and may extend the full height of the sidewall. It is orientated approximately 15° from the radial direction. The deformation has no impact on tire performance.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 4 - MOUNTING INSTRUCTIONS (ASSEMBLY)

- 13.2. Install the tire/wheel assembly on aircraft in accordance with the AMM.
- 13.3. Confirm that the tire inflation pressure is set in accordance with the AMM using a calibrated gauge with a tolerance of $\pm 2\%$ of full scale, or better.
- 13.4. Set the pressure to consider changes in ambient temperature.

NOTE: Changes in ambient temperature will cause a corresponding change in inflation pressure (gauge pressure). A 3°C (5°F) decrease in temperature will result in a 1% decrease in inflation pressure. An increase in temperature will cause a corresponding increase in the inflation pressure. (Example: A temperature drop of 28°C (50°F) will result in a pressure loss of 10%).

NOTE: The ambient temperature will vary over the course of the day, from location to location, and from season to season. The tire inflation pressure specified by the airframe manufacturer for each aircraft configuration is required to carry the load of the aircraft. This pressure value is needed regardless of the ambient temperature. While it is not practical to make small adjustments, the pressure should be set for the most adverse conditions (coldest temperature expected for operation).

NOTE: Tire pressure maintenance operations in cold climates must consider the effect of performing tire pressure maintenance on aircraft in a hangar that is warmer than the ambient temperature for normal operations. When the tire pressure is measured in a warm hangar and the aircraft is parked outside in a colder ambient temperature, the pressure will decrease.

NOTE: If the inflation pressure is set with the weight on the wheels, the inflation pressure is 4% greater than if the aircraft is on jacks (Operational Inflation Pressure Loaded = 1.04 x Operational Inflation Pressure Unloaded).

NOTE: If the tire wheel assembly has been stored at reduced pressure (approximately 25% of operational pressure) or if the tire has been in storage and the inflation pressure is less than 50% of operational pressure, inflate the tire to 105% of operational pressure to allow for stretch.

423

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

1. Proper Inflation Pressure Maintenance

Aircraft tires MUST be inflated and MAINTAINED at the proper inflation pressure. That is the most important factor in any tire preventative maintenance program.

- 1.1. Confirm the inflation pressure specified in the Aircraft Maintenance Manual (AMM), Pilot's Operating Handbook/Airplane Flight Manual (POH/AFM), or the appropriate operator documentation.
- 1.2. Follow the recommendations and procedures in the aircraft AMM and/or wheel manufacturer's Component Maintenance Manual (CMM), when installing, removing, or maintaining wheel assemblies on aircraft.

NOTE: The rated pressure may not be the correct operating pressure.

2. WARNINGS, CAUTIONS, and NOTES for This Chapter

WARNING: AIRCRAFT TIRES SHOULD BE MOUNTED ONLY WITH THE PROPER EQUIPMENT, INSTRUCTIONS, AND OPERATOR TRAINING. SERIOUS INJURY MAY OCCUR AS A RESULT OF IMPROPER EQUIPMENT OR PROCEDURES

WARNING: USE A SUITABLE INFLATION CAGE WHEN INFLATING A NEWLY MOUNTED TIRE WHEEL (HUB) ASSEMBLY. ANY DAMAGE TO THE TIRE, THE WHEEL, AND WHEEL BOLTS OR IMPROPER PROCEDURE, MAY CAUSE THE TIRE/WHEEL ASSEMBLY TO BURST DURING THE INFLATION PROCESS, WHICH MAY RESULT IN SERIOUS OR FATAL INJURY. REFER TO CHAPTER 4, FOR INITIAL MOUNTING PROCEDURES.

WARNING: ALWAYS APPROACH A TIRE/WHEEL ASSEMBLY MOUNTED ON AN AIRCRAFT FROM AN OBLIQUE ANGLE (DIRECTION OF THE TIRE'S SHOULDER). REFER TO FIGURE 501.



501

Figure 501. Recommended Angle of Approach



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

WARNING: AIRCRAFT TIRE AND WHEEL ASSEMBLIES SHOULD BE TREATED WITH THE SAME CARE AS ANY OTHER HIGH PRESSURE VESSEL. IMPROPER HANDLING MAY LEAD TO SERIOUS INJURY.

WARNING: AIRCRAFT TIRES MUST ALWAYS BE INFLATED WITH A PROPERLY REGULATED INFLATION SOURCE. REGULATE THE SUPPLY LINE TO A PRESSURE NO GREATER THAN 1.5 TIMES THE OPERATING INFLATION PRESSURE. INFLATING A TIRE WITHOUT A PRESSURE REGULATOR PRESENTS A RISK OF PERSONAL INJURY AND/OR DAMAGE TO EQUIPMENT.

CAUTION: BE CAREFUL WHEN HANDLING, ASSEMBLING, AND DISASSEMBLING WHEEL COMPONENTS TO AVOID DAMAGE.

WARNING: DO NOT PROBE CUTS OR EMBEDDED OBJECTS WHILE A TIRE IS INFLATED. SUCH ACTION COULD FURTHER DAMAGE A TIRE CAUSING IT TO RUPTURE RESULTING IN PERSONAL INJURY OR EQUIPMENT DAMAGE.

WARNING: A TIRE/WHEEL ASSEMBLY THAT HAS KNOWN DAMAGE SHOULD BE ALLOWED TO COOL TO AMBIENT TEMPERATURE (A MINIMUM OF 3 HOURS) BEFORE THE TIRE IS DEFLATED.

WARNING: USE CARE WHEN REMOVING THE VALVE CORE FROM AN INFLATED TIRE. USE OF A VALVE CORE REMOVAL TOOL IS RECOMMENDED. THE VALVE CORE OF AN INFLATED TIRE CAN BE PROJECTED AT A HIGH SPEED AND POSSIBLY CAUSE INJURY.

3. Daily Pressure Check

Use a calibrated gauge with a minimum tolerance of $\pm 2\%$ of full scale, or better, and with a scale suitable to the pressure range being monitored. Michelin recommends the use of a calibrated gauge with a tolerance of $\pm 0.25\%$ of full scale. Refer to Chapter 4, §3.

- 3.1. Check the inflation pressure before the first flight of aircraft that fly daily.

NOTE: Any measurement below 95% of nominal inflation pressure requires maintenance action (refer to Figure 503). Underinflation increases the deflection of the tire which may result in overheating, abnormal tire wear, shortened tire life, and possible tire failure.

NOTE: Overinflation can increase tread cutting, foreign object damage (FOD), abnormal tread wear, and stress on the wheel.

- 3.2. Confirm that the pressure required is specified for "weight on wheels" or with the tire unloaded. (The tire/wheel assembly is not installed on the aircraft or the aircraft is on jacks.) A loaded tire will have an inflation pressure 4% higher than when unloaded (loaded pressure = 1.04 times unloaded pressure).

- 3.3. Set the pressure to consider changes in ambient temperature.

NOTE: Changes in ambient temperature will cause a corresponding change in inflation pressure (gauge pressure). A 3°C (5°F) decrease in temperature will result in a 1% decrease in inflation pressure. An increase in temperature will cause a corresponding increase in the inflation pressure. (Example: A temperature drop of 28°C (50°F) will result in a pressure loss of 10%).

NOTE: The ambient temperature will vary over the course of the day, from location to location, and from season to season. The tire pressure specified by the airframe manufacturer for each aircraft configuration is required to load of the aircraft. This pressure value is needed regardless of the ambient temperature. While it is not practical to make small adjustments, the pressure should be set for the most adverse conditions (coldest temperature expected for operation).

NOTE: Other methods exist in the tire industry that may be used to estimate the pressure adjustment due to changes in temperature. They will provide a value that may slightly different due to rounding.

502

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

NOTE: Tire pressure maintenance operations in cold climates must consider the effect of performing tire pressure maintenance on aircraft in a hangar that is warmer than the ambient temperature for normal operations. When the tire pressure is measured in a warm hangar and the aircraft is parked outside in a colder ambient temperature, the pressure will decrease.

4. Measure the Pressure When Tires Are "Cold"

- 4.1. A "cold" tire is generally defined as a tire which is the same temperature as the surrounding air (ambient temperature). That is, one that has not rolled (taxied or takeoff/landing) for a minimum of three (3) hours.
- 4.2. A "hot" tire is one that has rolled (taxi) under load on the aircraft and has not been allowed to cool to ambient temperature. Refer to §6.
- 4.3. Tires operating on the same axle or bogie should be operated at the same pressure $\pm 5\%$. When tires are operated at unequal pressures the tire with the higher inflation pressure will carry a greater load. This can cause shorter life on both tires due to casing fatigue or abnormal wear.
 - 4.3.1. Refer to Figure 502 for an example. Example: Two (2) tires on an axle have different pressures. One tire is at 100% of operational pressure and the other tire is at 75% of operational pressure. Because both tires will deflect the same, tire at 100% operational pressure will carry approximately 110% of the load. The tire at 75% pressure will only carry about 90% of the load.
 - 4.3.2. When pressures on dual mounted tires are found to be different by more than 5%, action should be taken.
 - 4.3.2.1. Inspect the tires for leakage, if none is found, follow the steps below.
 - 4.3.2.2. Inflate both tires to their proper pressure.
 - 4.3.2.3. Make a log book entry indicating the original pressure difference, the ambient temperature, date, and time.
 - 4.3.2.4. Consult the log book at subsequent pressure checks. If the same tire continues to lose pressure requiring action, it should be checked for leaks.

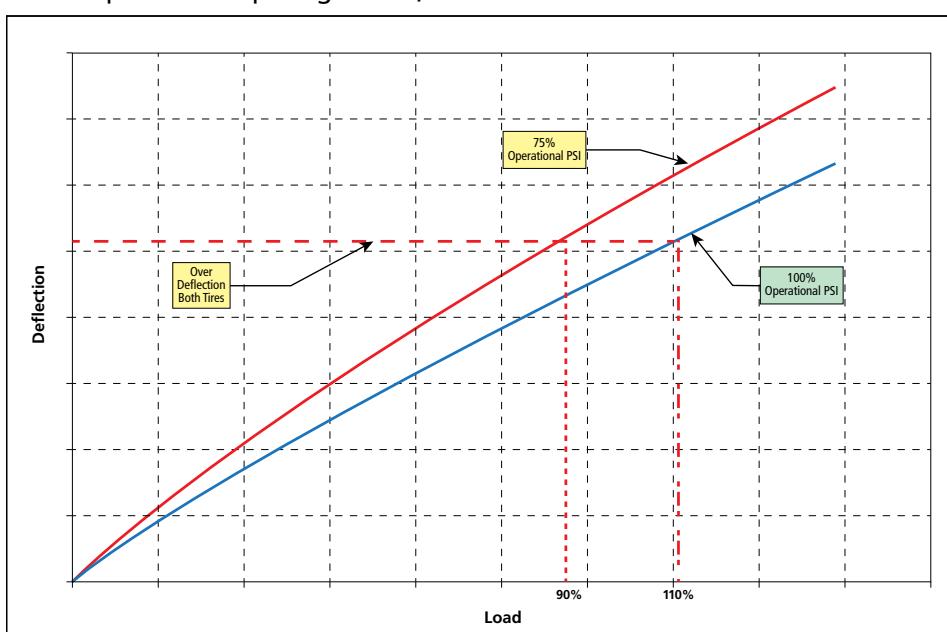


Figure 502. Effect of Unequal Pressure on Tire Loads



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

- 4.4. Effects of Underinflation:
 - 4.4.1. Underinflation or underinflation over time can cause casing fatigue which can result in partial or full tire failure.
 - 4.4.2. Reduced retreadability.
 - 4.4.3. Excessive shoulder wear.
 - 4.4.4. Tires can creep or slip on the wheel during braking. Valve stems on tube-type tires can be damaged or sheared off and the tire, tube or complete wheel assembly can be damaged.
 - 4.4.5. High lateral (side) forces or landing impact may cause the wheel to pinch the tire, strike the runway or the tire to interfere with other landing gear components.
- 4.5. Tire Pressure Monitoring System (TPMS) may be used to check inflation pressure provided the TPMS is calibrated periodically.

5. Maintenance Action

Action is required if the pressure is not within the range specified for the operational pressure. The action required depends on the pressure measured and should be accomplished in accordance with the AMM, or a maintenance procedure approved by the proper authority.

- 5.1. Figure 503 provides maintenance action based on measured cold (ambient temperature) pressure as a percentage of operating pressure. Gauge accuracy and calibration should be confirmed. A course of action is provided for each percentage range. Figure 503 is applicable to all aircraft tires.

NOTE: When the inflation pressure is set in the warm hangar and aircraft is parked outside in a colder ambient temperature, the inflation pressure should be adjusted to compensate for the drop in pressure resulting from the change in temperature. Refer to Note in §3.3 in this chapter.

504

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

Measured Pressure as % of Cold Operating Pressure	Tire Condition	Required Action
More than 105%	Overinflated	<ol style="list-style-type: none"> Record pressure and ambient temperature in aircraft log. Make a 2nd reading confirming the 1st reading at a similar ambient temperature. Adjust pressure as required.
105% – 100%	Normal Operating Pressure Range	<ol style="list-style-type: none"> No action required, Normal Range.
99% – 95%	Acceptable Daily Pressure Loss	<ol style="list-style-type: none"> Inflate to the maximum of the Normal Operating Pressure Range.
94% – 90%	Underinflated (Exceptional Pressure Loss)	<ol style="list-style-type: none"> Inspect for cause of pressure loss. Inflate to the maximum of the Normal Operating Pressure Range. Record the tire pressure and the ambient temperature in the log book. Continued operation is permitted. Check tire pressure 24 hours after pressure adjustment. <ol style="list-style-type: none"> If tire pressure is within Normal Operating Pressure Range ($\leq 5\%$ loss over 24 hours), continued operation is acceptable. If tire pressure loss is again greater than 5% loss over 24 hours, remove tire/wheel assembly from the aircraft and investigate the cause of pressure loss.
89% – 80%	Unacceptable Pressure Loss	<ol style="list-style-type: none"> Remove tire/wheel assembly from the aircraft. Investigate the cause of pressure loss. The tire should be removed from the wheel and thoroughly inspected for damage. Final disposition of the tire to be determined after inspection by a qualified repair station.
Less than 80%	Unacceptable Pressure Loss	<ol style="list-style-type: none"> Remove tire/wheel assembly from aircraft. If mounted in twin or dual configuration, remove the adjacent (mate) tire/wheel assembly from aircraft. Replace both tires. (See Note below.)
0% (See Note Below)	Flat	<ol style="list-style-type: none"> If pressure loss occurred while rolling, scrap the tire and mate.

Figure 503. Tire Pressure Maintenance Schedule and Actions

NOTE: A maximum daily pressure loss of 5% or less is considered acceptable for a 24-hour period (TSO, AC 20-97B, SAE ARP5265) (At same ambient temperature).

CAUTION: IF THE WHEEL FUSE PLUG HAS MELTED OR THE OVER PRESSURE PLUG HAS RELEASED, REMOVE THE TIRE FROM SERVICE. THE TIRE MAY HAVE DAMAGE THAT IS NOT VISIBLE BY EXTERNAL INSPECTION.

NOTE: Do not reduce the pressure in a cold tire that is subjected to frequent changes in ambient temperature. Refer to §3.3 in this chapter for changes in ambient temperature.

5.2. If an aircraft has not moved for a long period of time, the tires must be checked and properly inflated.

NOTE: It is normal for a tire to lose pressure over time. Aircraft tires can remain in service provided that the inflation pressure does not drop below 50% of the operating pressure and the tires have not rolled in this condition.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

6. Hot Tire Pressure Checks

It is recognized that some operational circumstances may require a hot tire pressure check and some AMM offer recommendations.

WARNING: IF A HOT TIRE IS MEASURED AND THE PRESSURE IS MORE THAN 1.75 TIMES THE UPPER RANGE OF THE SPECIFIED OPERATING PRESSURE, ALLOW THE TIRE TO COOL, REMOVE IT FROM THE AIRCRAFT, AND INVESTIGATE THE CAUSE OF THE ABNORMALLY HIGH PRESSURE.

CAUTION: DO NOT REDUCE THE PRESSURE OF A HOT TIRE. THIS COULD RESULT IN LOW PRESSURE WHEN THE TIRE COOLS TO AMBIENT TEMPERATURE. THE INFLATION PRESSURE WILL DECREASE AS THE TIRE COOLS.

- 6.1. The following recommendations and precautions should be considered when it is absolutely necessary to check the inflation pressure of a hot tire.

NOTE: It is not possible to know the correct "cold" pressure of a "hot" tire unless the temperature of the internal gas is known. See Note following §3.3 in this chapter.

 - 6.1.1. The corresponding "cold" inflation pressure should be equal to or greater than the specified loaded operating pressure. If the "hot" inflation pressure is less than operational inflation pressure, but $\geq 95\%$ of operational inflation pressure, inflate to 105% of operational inflation pressure.
 - 6.1.2. If a tire has less than ($<$) 95% of the specified loaded operating pressure, but equal to or greater than (\geq) 90% of operational inflation pressure, inflate to 105% of operational inflation pressure, record the pressures in the log book, and recheck after 24 hours.
 - 6.1.3. If a tire has less than 90% of the specified loaded operating pressure, remove the tire from the aircraft.
- 6.2. Pressures measured on tires mounted on the same landing gear, should be of the same magnitude if they are properly maintained.
 - 6.2.1. Differences in brake temperatures may contribute to unequal tire pressures.

7. Normal Wear Removal Criteria

- 7.1. Normal Wear: A tire with normal wear will show even wear of the center grooves. Shoulder grooves may still be visible. Even tread wear indicates a properly maintained tire. Refer to Figure 504.



Figure 504. Normal Removal Wear



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

- 7.2. Removal criteria for normal wear is based on remaining tread rubber as determined by groove depth or exposure of textile/steel ply material.
- 7.3. Refer to Chapter 1, Aircraft Tire Description/Construction for the explanation of tire components.
- 7.4. Refer to the airframer AMM. In the absence of removal criteria from the airframer, the following criteria are based on the fastest wearing location.
 - 7.4.1. Remove the tire when the level of wear reaches the bottom of any groove along more than 1/8 of the circumference on any part of the tread.
 - OR
 - 7.4.2. Remove the tire when the protector ply (radial) or reinforcing ply (bias) is exposed for more than 1/8 of the circumference at a given location.

NOTE: In some military applications, the removal point of a tire is indicated by a Max Wear Limit (MWL) molded on tire's sidewall. The value given is the number of exposed plies at removal. In some cases, MWL=RC (Red Cord), which indicates exposure of a red cord, is built into the tire.

NOTE: Local airworthiness authorities may have specific wear removal requirements that may be different from those given above. In those cases, follow the requirements of the local airworthiness authority.
- 7.5. Wear beyond limits occurs when tires are worn into the top belt plies (radial) or top casing plies (bias).

CAUTION: If the wear reaches the top belt ply (radial) or top casing ply (bias), the tire should be removed, without further service. Refer to Figure 505.

- 7.5.1. For return to base operation only, do not exceed more than five (5) normal landings when the protector ply (radial) or reinforcing ply (bias) is exposed for more than 1/8 of the circumference at a given location.

NOTE: Tires worn beyond normal limits may not be retreadable. Continued operation of a tire after the top belt plies (radial) or top casing plies (bias) have been exposed, increases the possibility of chunking of the tread and rib stripping.



Figure 505. Wear Beyond Limits

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

8. Tire Damage to the Tread

- 8.1. Damage removal limits may be provided in specific documentation such as the AMM, military technical documentation (T.O.4-1-3), airline operation manuals or documentation provided by the airframer or operator. The following guidelines can be used in the absence of specific damage removal documentation.
- 8.2. Mark all damages with a tire marking pen or crayon. Many damages easily visible on an inflated tire can be difficult to see when the tire is not inflated. Refer to Figure 506. Tires removed for reasons other than wear should have a tag affixed to the tire with reason for removal clearly stated.

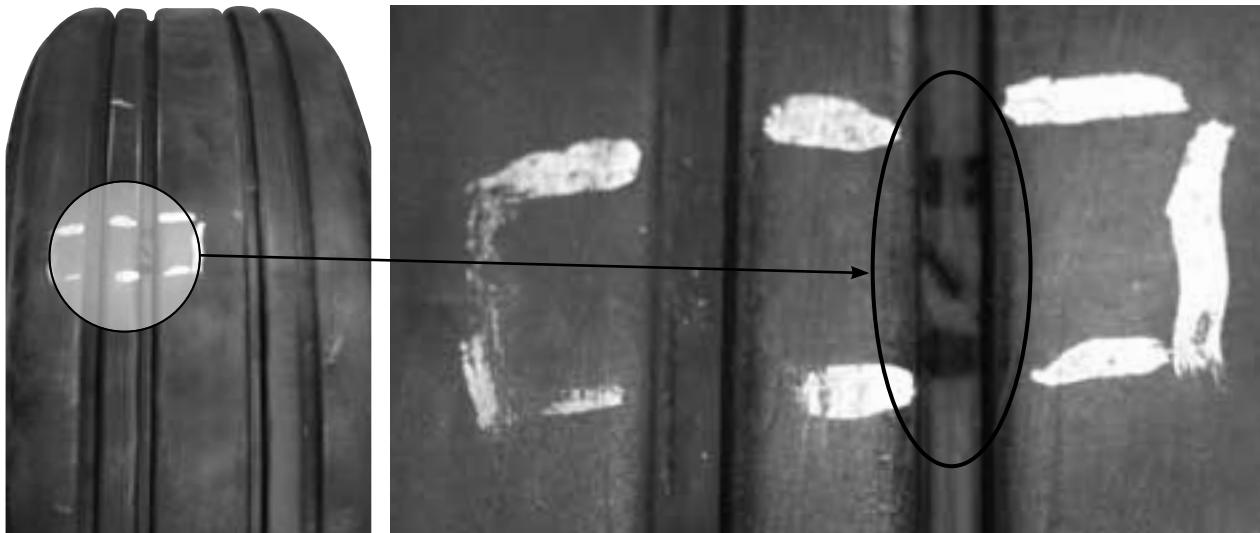


Figure 506. Marked Damage

CAUTION: DO NOT USE STAPLES TO ATTACH A TAG TO A TIRE. STAPLES CAN DAMAGE UNDERLYING PLY CORDS AND LEAVE HOLES ALLOWING MOISTURE OR OTHER CONTAINMENTS TO ENTER THE CASING PILES. USE AN ADHESIVE TAG OR SOME OTHER METHOD TO ATTACH THE TAG.

- 8.3. Overinflation Wear (center wear)
 - 8.3.1. Description: The center of the tread appears to be abnormally worn when compared to the wear on the shoulders.
 - 8.3.2. Cause: The tire is operated with higher pressure than specified or the aircraft is being operated at very light loads. Overinflation accelerates center wear. Tire cord is visible before the center grooves reach zero depth.
 - 8.3.3. Apply Normal Wear removal criteria. Refer to §7, in this chapter.
- 8.4. Underinflation Wear (shoulder wear)
 - 8.4.1. Description: The shoulders of the tire appear to be abnormally worn when compared to the wear in the center of the tread.
 - 8.4.2. Cause: A tire operated with consistently with low pressure will develop excessive shoulder wear. Frequent high speed turning will also cause excessive shoulder wear. Refer to Figure 507.
NOTE: Any measurement below 95% of nominal inflation pressure requires maintenance action. Refer to Figure 503. Underinflation increases the deflection of the tire which may result in overheating, abnormal tire wear, shortened tire life, and possible tire failure.
 - 8.4.3. Apply Normal Wear removal criteria. Refer to §7, in this chapter.

508



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT



Figure 507. Shoulder Wear due to Underinflation

- 8.5. Flat Spots
- 8.5.1. Description: Localized tread wear normally in the center of the tread.
 - 8.5.2. Cause: Skidding (sliding) without rotation. Brake lock or aggressive braking on moist runways. Large steer angle can result in sliding of the nose gear tires. If the nose gear is turned to a large angle prior to the aircraft rolling, the tires may slide before they develop sufficient cornering force to turn the aircraft resulting in flat spots. Pilots should be instructed to start the aircraft rolling before turning nose tires in the direction of desired travel.
 - 8.5.3. Flat Spotting on nose tires can lead to potential vibration complaints.
 - 8.5.4. Apply Normal Wear removal criteria. Refer to §7, in this chapter.
 - 8.5.5. If flat spotting does not reach the protector ply (radial) or reinforcing ply (bias), the tire can be left in service.
 - 8.5.6. If the localized loss of rubber results in vibration complaints, even though no textile or steel is exposed, the tire should be removed from service. Refer to Figure 508.

509

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT



Exposed Reinforcing Plies

Flat Spot Causing Rupture

Figure 508. Flat Spot - Bias

8.5.7. Excessive flat spot can result in "skid through" and tire rupture. Refer to Figures 508 and 509.



Figure 509. Flat Spot Resulting in Tire Rupture - Radial

510

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

8.6. Asymmetrical Wear

- 8.6.1. Description: Uneven wear that occurs more on one side of the tread than the other side. It is more generalized than scallop wear. Refer to §8.7.
- 8.6.2. Cause: Asymmetrical wear is caused when a tire has been operated under prolonged yaw and/or camber.
- 8.6.3. In some cases, the steel protector ply (radial) of textile reinforcing ply (bias) may be visible in the shoulder area. Refer to Figure 510.
- 8.6.4. Apply the Normal Wear removal criteria for bottom of groove or exposed steel or textile.



Figure 510. Asymmetrical Wear

- 8.6.5. Camber angle can be induced through the landing gear deformations or manufacturer's settings or tolerances. Refer to Figure 511.
 - Negative camber → inside shoulder wear
 - Positive camber → outside shoulder wear

511

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT



Figure 511. Camber Angle – Negative Camber

- 8.6.6. A yaw angle is created when the tire does not roll in the direction of travel. Refer to Figure 512. It can be induced through axle flexing under aircraft load or during braking. Faster wear will consistently be on the strut side shoulder of the tire regardless of wheel position. The tread may have a feathered appearance on the rib edges. This is often called "Toe Wear."
- Toe-out → wear is more rapid on the inside shoulder
 - Toe-in → wear is more rapid on the outside shoulder
- NOTE:** Yaw will have a greater impact on wear than will Camber.

512

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

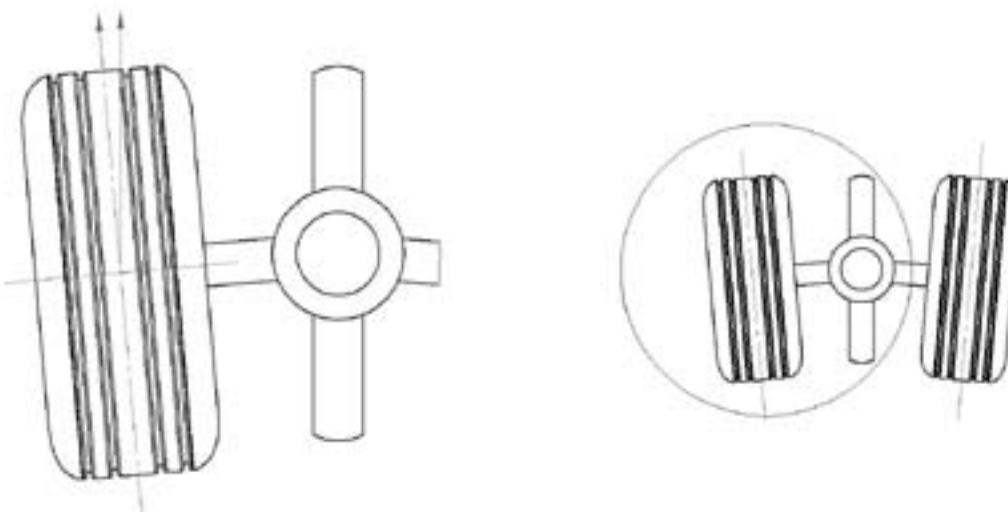


Figure 512. Yaw Angle – Toe-Out

- 8.6.7. Taxiing with one engine or high speed cornering will induce a yaw angle.
 - 8.6.8. If asymmetrical wear is noted, it is recommended that tires be operated at the maximum operating pressure specified in the AMM.
 - 8.6.9. A tire with asymmetrical wear that does not expose any fabric, can be dismounted, and reversed on the wheel, to extend the wear life.
 - 8.6.10. Apply Normal Wear removal criteria. Refer to §7, in this chapter.
- 8.7. Scallop Wear
- 8.7.1. Description: It is localized wear that occurs on the shoulder of a tire. It is sometimes referred to as "potato" wear. The localized wear can appear in one or more areas of the shoulder. Refer to Figure 513.
 - 8.7.2. Cause: There are different causes. It is seen most often on main landing gear tires of private/corporate jet aircraft.
 - 8.7.3. Apply Normal Wear removal criteria. Refer to §7, in this chapter.



Figure 513. Scallop Wear

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

8.8. Chevron Cutting

- 8.8.1. Description: They are normally surface cuts in a "V" shape and are normally in small groups (in the form of chevrons). There may be several groups around the circumference of the tread.
- 8.8.2. Cause: Most of the cutting occurs during aircraft touchdown at "spin-up" on high pressure aircraft tires. The forces required to accelerate the tire to ground speed generates a tearing action which creates the chevron in the tread ribs. Chevron cuts can also be caused during turning or braking.
- 8.8.3. Remove from service if cutting causes the tread to chunk or exposes the tread reinforcing ply (bias) or protector ply (radial) more than $6 \text{ cm}^2 (1.0 \text{ in}^2)$ or the full width of the rib.

NOTE: Chevron cutting not exposing textile can be left in service. Refer to Figure 514.

NOTE: Cross-groove cutting of runways is common at many airports around the world. It improves water drainage, reducing the probability of standing water and decreasing the risk of hydroplaning. The groove edges can increase the chevron cutting of the tread ribs.

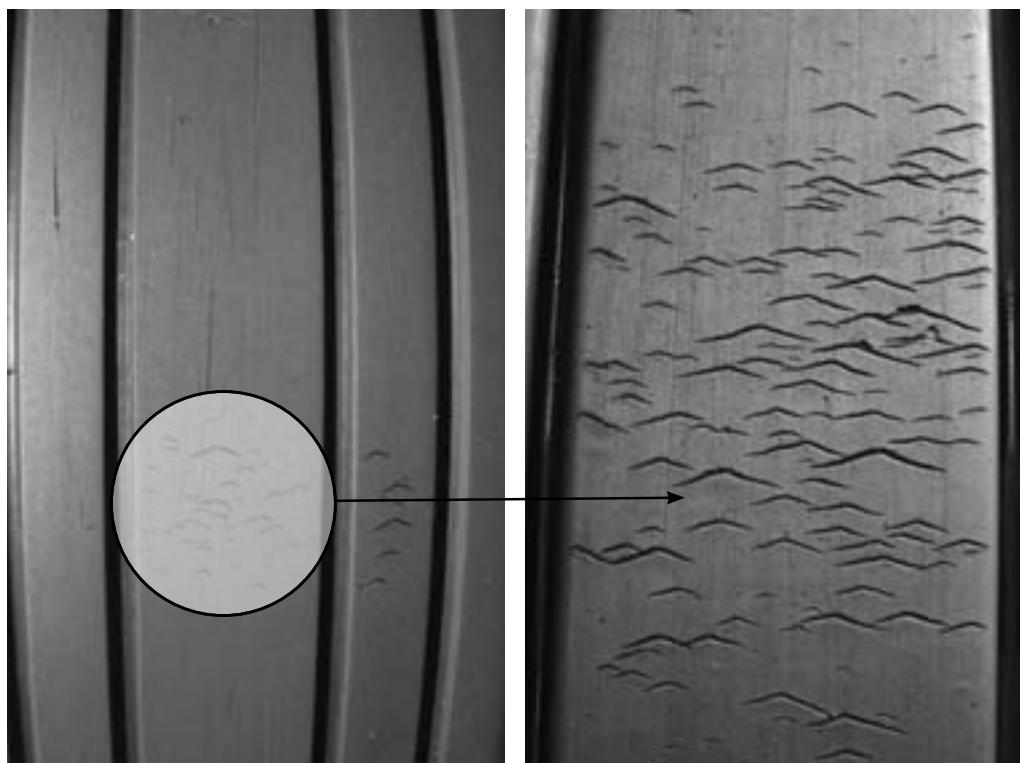


Figure 514. Chevron Cutting

- 8.8.4. The appearance and severity of chevron cutting is greatest when ambient temperatures and aircraft landing speeds are high causing greater tire acceleration at "spin-up."
- 8.8.5. Remove the tire if the reinforcing plies (bias) or protector ply (radial) are exposed. Refer to Figure 515.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT



Figure 515. Chevron Cutting – Exposed Ply

- 8.9. Aggressive Wear
 - 8.9.1. Description: A very rough appearance of the tread surface.
 - 8.9.2. Cause: Aggressive braking on rough runway surfaces can cause surface tearing of the tread rubber. Refer to Figure 516.
 - 8.9.3. Remove the tire if the reinforcing plies (bias) or protector ply (radial) are exposed. Refer to §7.5.



Figure 516. Aggressive Wear from Heavy Braking

- 8.10. FOD (Foreign Object Damage) or Tread Cuts
 - 8.10.1. Description: Localized tread cut or damage from an object.
 - 8.10.2. Cause: Rolling a tire over foreign objects on the runway or taxiway. Impact from an external object or source.
 - 8.10.3. Remove tires from service if:
 - 8.10.3.1. Cuts, embedded objects, or other injuries expose or penetrate the reinforcing plies (bias) or protector ply (radial).
 - 8.10.3.2. Cuts, embedded objects or other injuries that do not expose or penetrate the reinforcing plies (bias) or protector ply (radial) if:
 - A cut extends entirely across a tread rib (any depth).
 - A round object is greater than 9.5 mm (0.375 in).
 - 8.10.3.3. Refer to Figure 517.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT



Figure 517. FOD

NOTE: To help reduce foreign object damage (FOD), make sure that ramps, parking areas, taxi strips, runways, and other paved surfaces are regularly cleaned and cleared of all debris.

8.11. Tread Chipping and Chunking

- 8.11.1. **Description:** Areas of tread rubber removed from surface areas. Most commonly adjacent to tread grooves. Refer to Figure 518.
- 8.11.2. **Cause:** High lateral (side) loads placed on the tire during operation such as landing in a high cross wind, high speed turns, and tight turns during maneuvering.



Figure 518. Groove Edge Chunking

- 8.11.3. Remove from service if the chipping/chunking exposes the reinforcing ply (bias) or the protector ply (radial). Refer to §7.5.

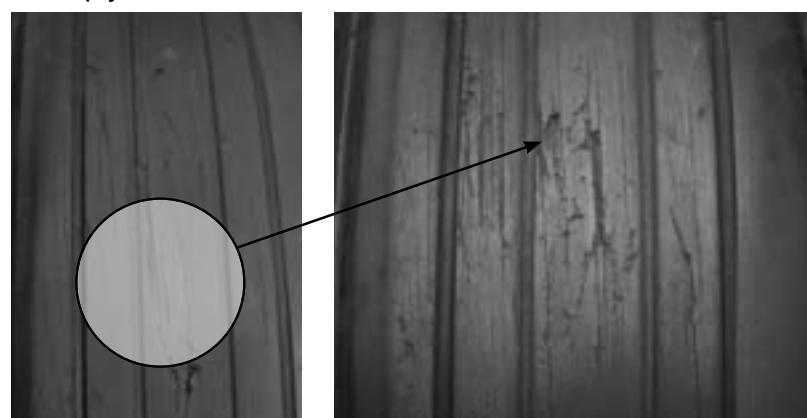


Figure 519. Tread Chunking



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

8.12. Groove Cracking

- 8.12.1. Description: Cracks that form in the bottom of tread grooves. Refer to Figure 520.
- 8.12.2. Cause: Exposure to higher than normal levels of ozone or mechanical stress caused by aggressive maneuvering or low inflation pressure.
- 8.12.3. Remove from service:
 - 8.12.3.1. If the groove cracking exposes the reinforcing ply (bias) or the protector ply (radial) for more than 6 mm (1/4 in).
NOTE: Authorization is given to return to a maintenance base (no more than 5 normal flights) to replace tires meeting the above criteria if there is no continuous cracking exposing textile or steel greater than 25 mm (1 in) in length.
 - 8.12.3.2. If the cracking extends under a rib.



Figure 520. Groove Cracking

8.13. Rib Undercutting

- 8.13.1. Description: Lateral tearing of the tread rubber along one or more grooves that extends under the adjacent tread rib. With continued use, it may lead to chunking, peeled rib, or a thrown tread. Refer to Figure 521.
- 8.13.2. Cause: Rib undercutting is a result of lateral (side) forces on the tread from aggressive maneuvering such as high speed turns or tight cornering during aircraft movement. It generally is accompanied by a coarse rubber surface texture, rounding of groove edges, and lateral scratches.
- 8.13.3. Remove from service if the undercutting extends under a rib.

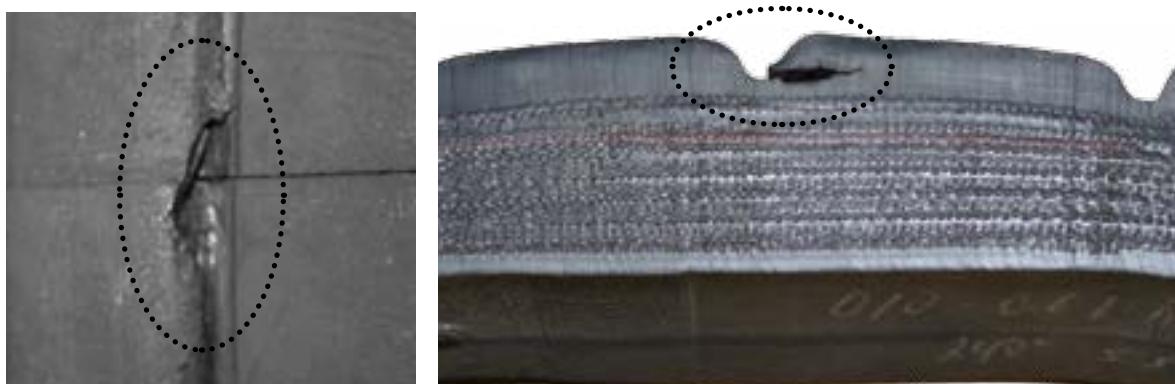


Figure 521. Rib Undercutting



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

8.14. Open Tread Splice

- 8.14.1. Description: An opening in the tread rubber that is orientated at an angle to the ribs. It usually extends across several or all ribs. Refer to Figure 522.
- 8.14.2. Cause: Contamination that prevents the tread splice from bonding properly during the manufacturing process. Abrasion pulls the joint open during operation.
- 8.14.3. Remove the tire from service.



Figure 522. Open Tread Splice

8.15. Stripped Rib

- 8.15.1. Description: A partial or full loss of the tread rubber between adjacent grooves. Refer to Figure 523.
- 8.15.2. Cause: The most likely cause is a FOD cut in the rib that reaches the top reinforcing ply (bias) or protector ply (radial). A stripped rib may also be caused by heavy chevron cutting that touches the top ply allowing centrifugal force to pull and detach the tread rib.
- 8.15.3. Remove the tire from service.



Figure 523. Peeled Rib

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

8.16. Tread Bulges or Separations

- 8.16.1. Description: An irregular raised area of the tread surface.
- 8.16.2. Causes: Excessive heat build-up, low inflation pressure, overload, poor repairs, etc.
- 8.16.3. A bulge usually indicates a separation of internal tire components. During high speed rotation, even small areas of separation can grow into partial or full tread rubber loss.
- 8.16.4. Remove the tire from service.
- 8.16.5. Mark these areas with a tire marking pen or crayon before deflating. Once deflated, these areas will be difficult to locate.

8.17. Thrown Tread

- 8.17.1. Description: The partial or complete loss of the tread rubber.
- 8.17.2. Causes: Cuts, excessive heat build-up, low inflation pressure, overload, poor repairs, contamination during retreading, etc.
- 8.17.3. Early signs of separations of internal components may appear as bulges, uneven wear, or localized rubber splits. It is important to remove tires from service when any evidence of separation is first seen. During high speed rotation, even small areas of separation can grow into partial or full tread rubber loss.
- 8.17.4. If the tire is still inflated, it is important to record the pressure after it has cooled to ambient temperature (allow at least 3 hours).
- 8.17.5. Remove the tire from the aircraft without additional service.

NOTE: Collect pieces of tread rubber ejected by the tire from the runway surfaces. These pieces can be an important part of any investigation.

9. Tire Damage to the Sidewall

9.1. Description: Cuts or penetrations in the sidewall rubber:

- 9.1.1. Causes include:
 - 9.1.1.1 Handling: contact from lift truck forks.
 - 9.1.1.2 Transporting: resting the tire against a sharp metal object.
 - 9.1.1.3 Storage: contact with a sharp metal object in storage racks.
 - 9.1.1.4 Aircraft Operation: contact with objects that extend into the sidewall area of the tire or running off the edge of a taxiway surface.
- 9.1.2. Remove the tire from service if sidewall cords are exposed or damaged.
- 9.1.3. Cuts that do not reach the cord may remain in service. Refer to Figure 524.

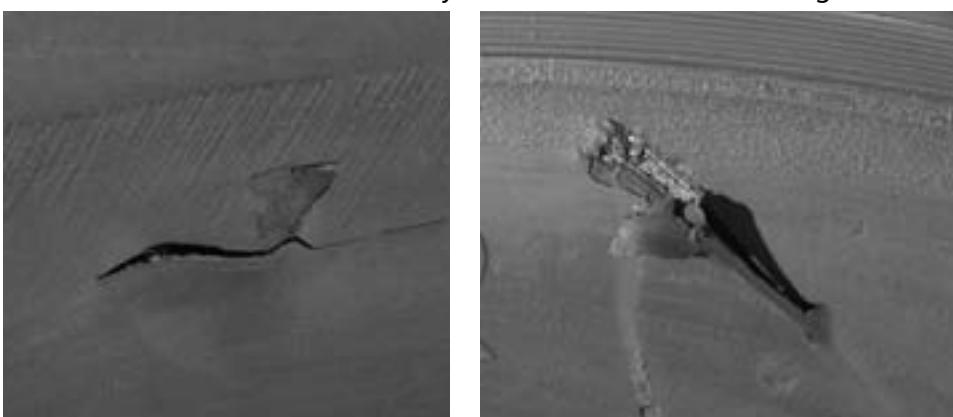


Figure 524. Sidewall FOD – Remove From Service (exposed cords)



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

- 9.2. Sidewall Bulge/Blister/Separation
 - 9.2.1. Description: An irregular, raised area of the sidewall.
 - 9.2.2. Cause: A separation of internal tire components.
 - 9.2.3. Remove the tire from service.
 - 9.2.4. Mark these areas with a tire marking pen or crayon before deflating. Once deflated, these areas may be difficult to locate.
NOTE: Some radial tires may show a slight deformation in the sidewall after being mounted on the wheel and inflated. The deformation results from a small amount of extra rubber at the splice of sidewall rubber. It is normally less than 15 mm (0.6 inch) wide and may extend the full height of the sidewall. It is orientated approximately 15° from the radial direction. The deformation has no impact on tire performance.
- 9.3. Sidewall Rubber Cracking
 - 9.3.1. Description: Cracking of the rubber. Refer to Figure 525.
 - 9.3.2. Causes: Exposure to high levels of ozone or ultraviolet rays (UV). Sources of ozone or UV can be welders, battery chargers, direct sunlight, and excessively high storage temperatures.
 - 9.3.3. Remove from service only if the cracking exposes ply cords.
NOTE: Cracks that do not reach/expose ply cords are not detrimental to tire performance and are not reason for removal. Tires showing only surface cracking can be left in service.

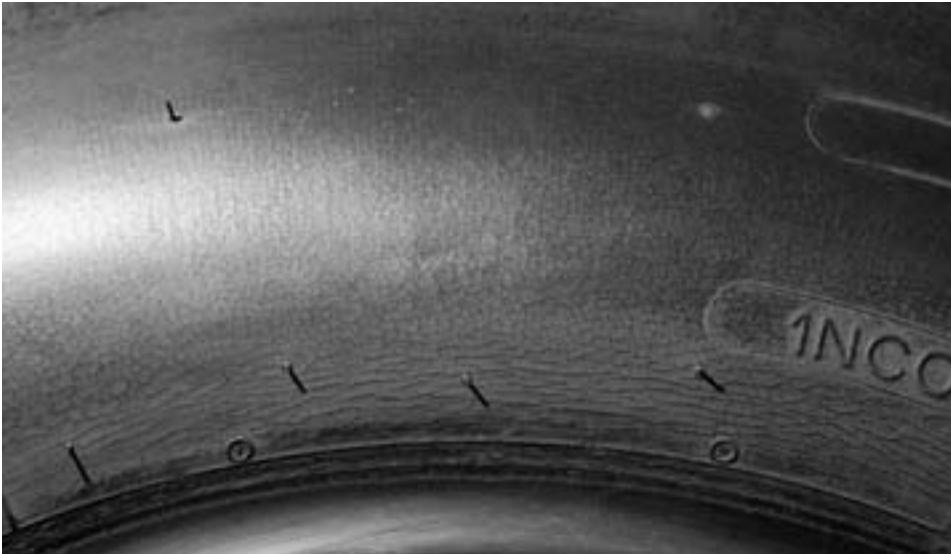


Figure 525. Sidewall Rubber Cracking

- 9.4. Chine Tire Damage
 - 9.4.1. Description: A cut or tear in the chine.
 - 9.4.2. Cause: Normally caused by FOD or impact with an object.
 - 9.4.3. Remove a tire from service if any cut severs or extends across the chine and is more than 1/2 the width of the chine. Refer to Figure 526.
NOTE: Chine tires are nose position tires with a water deflector. Refer to Chapter 1, Aircraft Tire Description/Construction.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

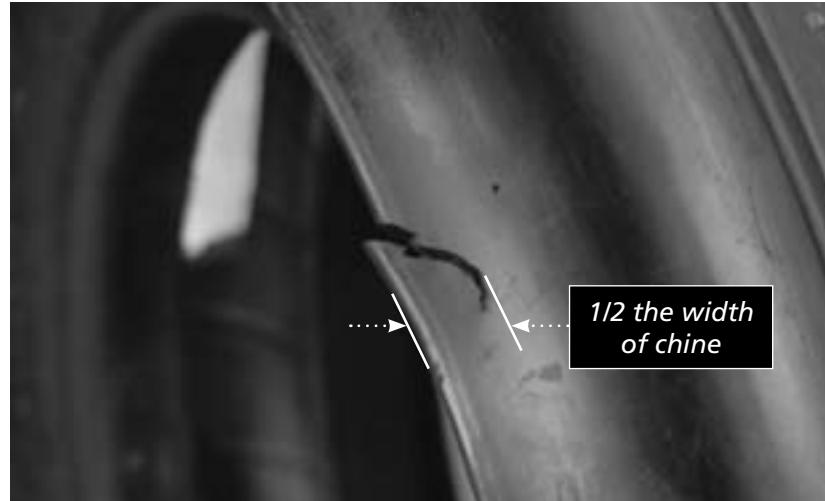


Figure 526. Damage to Chine Tire

9.5. Sidewall Rubber Discolored

9.5.1. Description: A noticeable difference in the black color of the sidewall rubber.

9.5.2. Cause: Migration of anti-oxidant waxes to the surface of the rubber. This condition may be seen on tires that have been stored for a long period of time whether mounted or un-mounted.

NOTE: Anti-oxidant waxes are part of the sidewall rubber compound. They protect the rubber from ozone. By design, they slowly migrate to the surface replacing anti-oxidant waxes that have been removed due to normal weather conditions. Refer to Figure 527.



Figure 527. Wax Blooming

9.5.3. Tires are fully serviceable and can be used without issue.



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

10. Operating Conditions and Considerations

- 10.1. Aircraft tire performance is based on a "cycle" (taxi, takeoff, landing, taxi). Many factors cause differences in tire wear. Caution should be exercised in comparing individual tire performance to allow for the effects of the factors below.
 - 10.1.1. Tire technology: Radial tires, in general, obtain significantly more Landings Per Tread (LPT) than an equivalent bias tire. MICHELIN® NZG technology tires have demonstrated additional improvement over the standard nylon radial.
 - 10.1.2. Temperature/Altitude Effect: Warm air is less dense than cool air. Aircraft performance is reduced by the less dense air. The result is longer aircraft roll distances from higher takeoff and landing speeds. There may be as much as 30% to 50% difference in landing performance between summer and winter operations (more landings in the winter). Caution should be shown when comparing tire performance between seasons. High altitude airports have the same effect on tire wear as warm weather. The air is less dense at high altitude airports.
 - 10.1.3. Runway types: Different materials used for taxiways and runways will wear tire tread rubber differently, particularly rough and abrasive materials. Coral is an example of an abrasive material used in some runways.
 - 10.1.4. Usage: Fast turns, heavy braking, hard landings, and long roll distances are examples of operating conditions that will have a negative impact on tire wear.
 - 10.1.4.1. High taxi speeds (> 40 mph) and long taxi distances can cause greater tread wear, greater heat buildup, and more lateral scuffing during turns. Refer to Figure 528.
 - 10.1.5. Aircraft Type/Landing Gear Design: Heavy, turbofan aircraft generally get fewer LPT's than lighter, turboprop aircraft. Landing gear alignment and flexing can cause irregular wear such as inboard shoulder wear.
 - 10.1.6. Pivot Turns: Large, heavy aircraft may need to perform pivot turn in order to utilize the entire runway. Some landing gear configurations may cause some tires to be dragged sideways. These turns should be avoided when possible.
 - 10.1.6.1. Make wide turns where possible. Pivot turns can wear flat spots on tires resulting in premature replacement. Pivot turns also place significant strain on the tire tread, tread shoulder and upper sidewall. Refer to Figure 528.

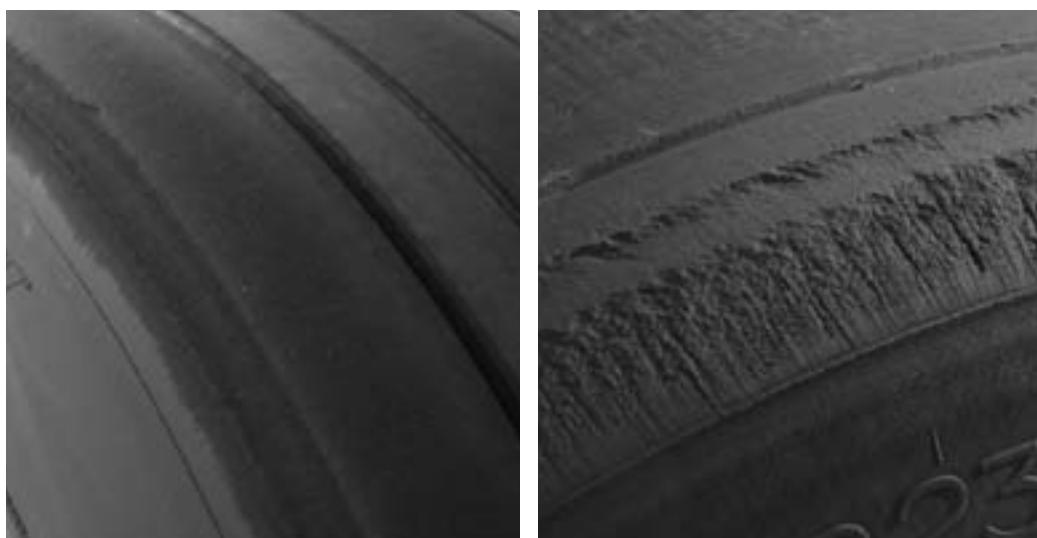


Figure 528. Lateral Scuffing, High Speed Turns, Pivot Turns



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

- 10.2. Thermal-Flat-Spotting on Nylon Casing (cold flat spots): Nylon aircraft tires will develop temporary flat spots under static load. The level of this flat-spotting will vary according to:
 - 10.2.1. The temperature of the tire when the aircraft arrived to park.
 - 10.2.2. The inflation pressure in the tire.
 - 10.2.3. The load on the tire while the aircraft is parked.
 - 10.2.4. The length of time the tire is subjected to the above conditions.
 - 10.2.5. The type of construction, shape, and aspect ratio.
 - 10.2.6. Normally this type of flat-spotting will disappear once the tire rolls and begins to warm up. It is usually gone by the end of the taxi run. Under similar conditions radial tires develop less flat-spotting than bias tires.
- 10.2.7. Aircraft Maintenance cannot prevent nylon flat-spotting but some actions may reduce the effect.
 - 10.2.7.1. Keep inflation pressure at specified operating pressure and minimize the aircraft load during the static period.
 - 10.2.7.2. Aircraft that are to remain parked for longer than 3 days should be moved every 72 hours or supported so that no weight is on the tires. Aircraft in storage (out of service for more than 14 days) should be supported so there is no weight on the tires.
- 10.2.8. In the unusual case where deep flat-spotting has occurred, additional taxing is recommended prior to takeoff.
- 10.3. Hydroplaning is a complex phenomenon. The summary here is only intended to provide a basic understanding.
 - 10.3.1. Tire hydroplaning is a condition that occurs when a tire is operated at speed on a partially flooded surface. At some speed, the tire becomes supported (totally or partially) by the fluid pressure generated as the fluid is being removed from under the footprint. At a critical speed, the water cannot be removed fast enough and the tire will be completely lifted from the surface.
 - 10.3.2. Hydroplaning is influenced by many factors:
 - Depth of fluid (water, snow, slush...)
 - Density of the fluid (water, snow, slush...)
 - Tire inflation pressure
 - Tire footprint length and width
 - Surface texture
 - Pavement grooves
 - Pavement crown
 - Speed of the vehicleThe tire inflation pressure is the most important tire parameter affecting the critical speed.
 - 10.3.3. There are two types of hydroplaning. Refer to Figure 529.
 - Dynamic Hydroplaning
 - Viscous Hydroplaning

523

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT



Figure 529. Hydroplaning

- 10.3.4. Dynamic Hydroplaning is a high speed phenomenon which occurs on any surface and requires a minimum fluid thickness.
 - 10.3.4.1. Considering the various fluids reasonably encountered by aircraft tires, slush is the most likely to cause dynamic hydroplaning. It is less dense than water, but is deeper due to its viscosity. Slush, along with snow or ice, deserves particular attention.
- 10.3.5. Viscous Hydroplaning results when a thin film of fluid (water) on the runway becomes a lubricant. It may mix with the contaminants present or the water alone may be sufficient if the surface texture of the runway is smooth as on a painted portion of the runway markings. Generally the irregular condition of the runway surface is sufficient to break up this film.
- 10.3.6. An aircraft tire experiencing hydroplaning may form an area of tread rubber reversion or skid burn in the tread due to lack of wheel rotation. This area will be oval in shape similar to a flat spot. If the reinforcing ply (bias) or protector ply (radial) is not exposed the tire can be left in service. If any vibration resulting from the flat spot is acceptable, the tire can be left in service.

NOTE: The most effective method to minimize the effects of water on traction is to reduce the water depth. Many airport runways are cross-grooved to improve water drainage.

524

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

NOTE: A similar tread rubber reversion can occur if the tire slides on ice for any distance.
Refer to Figure 530.



Figure 530. Hydroplane Damage

- 10.3.7. Apply the Normal Wear removal.
- 10.3.8. Remove the tire if a vibration problem is experienced.
- 10.4. Tire Contamination from Hydrocarbons creates a soft or "spongy" feel to the rubber surface. The deterioration is a consequence of prolonged exposure rubber to hydrocarbon based materials: oils, grease, brake fluids, hydraulic fluid, solvents, cleaning fluids, etc.
 - 10.4.1. When working on engines or landing gears, tires should be covered to prevent contamination from spills, leaks, etc. Refer to Figure 531.
 - 10.4.2. Remove contaminating fluid from the tire. Do not allow the fluid to soak into the tire. Wash the contaminated area first with denatured alcohol, then with a soap and water solution as quickly as practical after contact with a hydrocarbon substance.
 - 10.4.3. If the rubber is soft or "spongy" when probed with a blunt object in the contaminated area, when compared to the adjoining uncontaminated area, remove the tire from service.



Figure 531. Protect Tires From Contaminants

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT



Figure 532. Contamination From Hydrocarbons

- 10.5. Hard Landing:
 - 10.5.1. Consult the AMM if a hard landing is recorded or is known to have occurred.
 - 10.5.2. A hard landing can damage the tires if the dynamic load causes a tire to "bottom." The tire bottoming point is the point at which the sidewall of the tire is fully deflected and beginning to compress the lower sidewall structure. Over compression of the sidewall structure can damage the tire.
 - 10.5.3. In the absence of an AMM the following should be taken into consideration.
 - 10.5.4. Inspect the tires for any obvious signs of damage such as cuts, splits in the rubber that could be evidence of bottoming. A bulge may indicate damage to the casing plies and the tire should be removed from service.
 - 10.5.5. A more thorough inspection may call for removing the tires and inspecting the inner lining for evidence of damage.
NOTE: If there is doubt, remove the tires and send them to an authorized repair station for inspection.
- 10.6. High Energy Rejected Takeoff:
 - 10.6.1. Wait 30 minutes minimum to allow tire/brake cooling.
 - 10.6.2. If the fuse plug has released or over pressure release plug has been activated, remove the tire from service and have it scrapped. If the tires are returned to a repair station, label the tire as RTO and SCRAP.
 - 10.6.3. Remove the tires and scrap them if normal landing speeds were exceeded and high braking energy was experienced. If the tires are returned to a repair station, label the tire as RTO and SCRAP.
NOTE: Tires may remain in service when aircraft speed remains below normal landing speeds and only normal braking energies are experienced.
- 10.7. Over Speed Takeoff occurs when the takeoff speed exceeds the rated speed of the tires.
 - 10.7.1. Remove all tires from the aircraft that exceeded the tire rated speed. Label tires as "over speed takeoff" and return them to a repair station for inspection and disposition.

526

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

10.8. Vibration and Balance

NOTE: Vibration is the act of moving back and forth rapidly. Vibration is caused by a rapidly changing force. Operating conditions such as flat-spotting can cause the rotating tires to generate a force that will initiate a vibration.

NOTE: Vibration can be blamed on improper tire balance. Imbalance is easily understood as a cause for vibration, but in many cases, improper balance may not be the cause. There are a number of factors of the tire, wheel, and landing gear assembly which contribute to aircraft vibration. A systematic approach should be taken to isolating the cause.

NOTE: Some aircraft may be more sensitive to vibration than others and may require that tire wheel assemblies be balanced. Wheel weights may be added when needed.

10.8.1. If vibration (shake or shimmy) is unacceptable to flight operations, remove the tire from service. For dual tires in nose positions, both tires should be removed unless vibration can be linked to just one tire.

10.8.2. Check that the tire has the proper inflation pressure, using a calibrated gauge. Follow the airframer's recommendations for the proper pressure. If the tires are mounted in twin or dual configuration, confirm the pressure in both tires.

10.8.3. Inspect the tire for flat-spotting, out of round, bulges, or other damage. If found, remove the tire(s) from service.

10.8.4. Verify that tires have been properly mounted and that the tire was allowed to stretch 12 hours at operating pressure.

10.8.5. Check that the beads of the tire are properly seated. The small circular mold line on the lower sidewall of the tire should be equal distant from the top of the wheel flange (concentric). If the distance is not uniform, on either side, remove the tire/wheel assembly from the aircraft and send it to the wheel shop for further examination.

10.8.6. If there is insufficient time to change nose tires, a temporary fix may be to jack the nose of the aircraft, rotate one (1) tire 180 degrees then lower the aircraft. This may offset imbalance enough to allow flight operations to continue.

10.8.7. Check the wheel for damage.

10.8.8. Check the wheel for incorrect assembly that would cause it to be out of balance.

10.8.9. Check that the red balance mark on the lower sidewall of the tire is aligned with the wheel valve, unless specified otherwise by the wheel manufacturer.

10.8.10. Check for a loose wheel bearing caused by an improperly torqued axle nut.

10.8.11. Check for worn or loose landing gear components.

10.8.12. Check for worn hydraulic components, particularly steering control units.

10.8.13. Check for poor gear alignment as evidenced by uneven tire wear.

10.8.14. Additional steps for Tube-Type Tires include a check for trapped air between the tire and tube.

10.8.14.1. Use a soapy solution to check for leakage at the base of the tube valve stem where it exits the wheel.

10.8.14.2. Rolling the tire by taxiing will generally work any trapped air out from between the tube and tire.

10.8.14.3. Check if the tube is wrinkled because of improper mounting/inflation procedures. Refer to Chapter 4 §6 for mounting tube-type tires.

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

11. Matching and Mixability of Aircraft Tires

- 11.1. Matching aircraft tires assures that tires mounted on the same aircraft are the proper size to meet design criteria. The landing gear is normally designed to allow all tires on any one gear strut to carry the same load.
- 11.2. Mixability of aircraft tires is most often used when authorizing tires of different technology or different part number on the same aircraft, or on multi-wheel landing gear configurations.
NOTE: The terms matching or mixing do NOT imply installation authority. Installation authority must come from the airframer.
NOTE: Some airframers restrict mixability. Consult the airframer AMM or appropriate documentation, to confirm proper mixing of tires on specific aircraft.
NOTE: The term "Interchangeability" is frequently used when substituting one authorized Part Number for another authorized Part Number. It is sometimes used when referring to mixing, as defined above.
- 11.3. Whenever mixing is authorized, "matching criteria" must be respected to assure that tires carry equal loads. The matching criteria are based on the standards for size and tolerance for each tire covered by the standards.
 - 11.3.1. Industry standards for size and tolerance are defined by:
 - The Tire and Rim Association (T&RA)
 - European Type and Rim Technical Organisation (ETRTO)
 - MIL-T-5041, Military Specification of Aircraft Tires
 - AIR-8505-A, French Civil and Ministry of Defense Certification Standards for Aircraft Tires
 - 11.3.2. Meeting industry sizing standards ensures equal distribution of aircraft load on all tires.
- 11.4. It is common practice to mix the following combinations on both the aircraft and on the same landing gear or bogie.
 - Bias – Bias
 - Radial – Radial
- 11.5. Mixability of bias tires and radial tires on the same aircraft is determined by the airframer. The possible combinations are:
 - 11.5.1. Bias tires on the nose landing gear and radial tires on the main landing gear.
 - 11.5.2. Radial tires on the nose landing gear and bias on the main landing gear.
 - 11.5.3. Bias tires on one main landing gear and radial tires on the other main landing gear. (The nose landing gear could have either bias or radial.)
 - 11.5.4. On a landing gear with twin tires (or dual tires), or for landing gear with tandem configuration: A bias tire on one axle and a radial tire on another axle.
- 11.6. Tires approved for the same application must have the same Static Loaded Radius (SLR) (within standards) to respect the matching criteria. It is acceptable if they appear to have different overall diameters when stood side by side, properly inflated.
- 11.7. Mixing New Tires and Retreaded Tires: It is acceptable to mount both new and retreaded tires on the same axle and/or landing gear if both are designed to the same standard and meet matching criteria.
 - 11.7.1. The guidelines for mixability of new and retreaded tires for bias tires and radial tires on the same aircraft are the same as for new tires. Mixability of bias and radial tires is determined by the airframer.

528

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 5 - OPERATION ON AIRCRAFT

12. Tire Creep

A small amount of relative circumferential movement between the tire and the wheel is commonly known as tire creep.

- 12.1. Some tire creep may be observed on a new assembly. Up to five (5) cycles may be necessary to properly position the tire bead on the wheel.
- 12.2. Tire creep is not an issue for tubeless tires as long as the tire does not rotate on the wheel to an extent where the braking capability is in question or causes air loss.
- 12.3. Underinflated tires can creep or slip on the wheel under stress or when brakes are applied.
- 12.4. SAE ARP5507 recommends a maximum of 20 degrees following installation. ARP 5507 further recommends that tires which move in excess of 20 degrees should be disassembled and evaluated for appropriate action.

13. Static Discharge

Tires are not designed to discharge the buildup of static electricity.

14. Tire Marking Tools

Tools for marking tires are available from commercial sources. Tire marking pens or crayons are commonly used. Michelin has no data to suggest tire damage from marking pens or crayons.

15. Military Arresting Cables

Some airports may have military arresting cables as emergency standby gear for arresting hook equipped aircraft. The cable is nominally 31.74 mm (1 1/4 inches) or 35 mm (1 3/8 inches) in diameter and installed approximately 457 to 610 m (1500 ft. to 2000 ft.) from the end of the runway. It is supported off of the runway surface approximately 14 to 18 cm (5 to 7 inches). Michelin has no data to suggest tire damage from cable roll over.

NOTE: Do not confuse cable roll over with cable crush that is associated with landing on an aircraft carrier.

529

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)

1. General

This chapter includes the necessary information and procedures for dismounting (disassembly of) aircraft tires when removing them from service or for retread. The following warnings and cautions apply whenever tires are being dismounted.

- 1.1. Reference the Aircraft Maintenance Manuals (AMM) and the wheel manufacturers Component Maintenance Manuals (CMM), if available. The AMM and CMM documents take precedence over these recommendations in the event of a conflict.

2. WARNINGS and CAUTIONS for This Chapter

- WARNING:** AIRCRAFT TIRE AND WHEEL ASSEMBLIES MAY OPERATE UNDER HIGH PRESSURES IN ORDER TO CARRY THE LOADS IMPOSED ON THEM. THEY SHOULD BE TREATED WITH THE SAME RESPECT THAT ANY OTHER HIGH PRESSURE VESSEL WOULD BE GIVEN.
- WARNING:** ALWAYS APPROACH A TIRE/WHEEL ASSEMBLY FROM AN OBLIQUE ANGLE (DIRECTION OF THE TIRE'S SHOULDER).
- WARNING:** DO NOT PROBE CUTS OR EMBEDDED OBJECTS WHILE A TIRE IS INFLATED. SUCH ACTION COULD FURTHER DAMAGE A TIRE CAUSING IT TO RUPTURE RESULTING IN PERSONAL INJURY OR EQUIPMENT DAMAGE.
- WARNING:** DEFATE ANY DAMAGED OR NON-SERVICEABLE WHEEL ASSEMBLY BEFORE REMOVING IT FROM THE AIRCRAFT. HANDLING DAMAGED ASSEMBLIES WHILE INFLATED INCREASES THE RISK OF ACCIDENTAL BURST OR FAILURE. SERVICEABLE UNITS MAY BE LEFT INFLATED.
- WARNING:** USE CARE WHEN REMOVING THE VALVE CORE FROM AN INFLATED TIRE. USE OF A VALVE CORE REMOVAL TOOL THAT CAPTURES THE VALVE CORE IS RECOMMENDED. THE VALVE CORE OF AN INFLATED TIRE CAN BE PROJECTED AT A HIGH SPEED AND POSSIBLY CAUSE INJURY.
- WARNING:** FULLY DEFATE THE TIRE BEFORE LOOSENING THE TIE BOLTS THAT HOLD THE WHEEL HALVES TOGETHER. WHEEL PARTS COULD COME APART WITH FORCE CAUSING PERSONAL INJURY.
- CAUTION:** FOLLOW THE WHEEL MANUFACTURER'S INSTRUCTIONS, PROCEDURES, MATERIALS AND EQUIPMENT FOR DISASSEMBLING THE WHEEL COMPONENTS. IMPROPER PROCEDURES CAN CAUSE DAMAGE TO THE WHEEL OR ASSOCIATED COMPONENTS.

3. Track the Reasons for Tire Removal

Tracking the reasons for removal helps the repair station take appropriate corrective action decisions concerning inspections and the future use of the tire.

- 3.1. Use a tag or label attached to the tire with self-sticking adhesive or by use of a heavy string. Figure 601 lists the information requested.
- 3.2. Apply a self-sticking label to the lower sidewall of the tire, but above the bead area. This will protect the label from rubbing against other tires during transport.

CAUTION: DO NOT USE STAPLES OR OTHER METAL DEVICES FOR AFFIXING TAGS OR LABELS TO TIRES OR INNER TUBES. THESE DEVICES CAN DAMAGE INTERNAL PLY CORDS RESULTING IN POSSIBLE TIRE FAILURE.

601

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)

3.2.1. Information requested to be sent with the tire or sent to the Michelin representative:

Information Requested	Information
Name of operator	
Aircraft model number	
Aircraft tail number	
Wheel position on aircraft	
Tire part number	
Tire serial number	
Retread level	
Reason for removal	
Date tire is removed	
Date tire mounted on aircraft	
Number of tire landings	

Figure 601. Tire Change Information

4. Tools, Fixtures, and Equipment

Below are some of the equipment commonly used to loosen the tire from the wheel bead seats.

- 4.1. Most modern aircraft wheels are of two types.
 - 4.1.1. The split wheel type has two "halves" joined by removable tie bolts.
 - 4.1.2. The removable flange type allows only the flange to be demounted from the wheel.
- 4.2. Follow the instructions in the wheel manufacturer's CMM when disassembling the wheel components.
- 4.3. Aircraft tires require special equipment to separate the tire bead from the wheel. Proper use of this equipment is necessary to avoid damage to the tire/wheel assembly and difficulties in releasing tire beads.

CAUTION: CARE MUST BE USED WHEN HANDLING AND DISASSEMBLING WHEEL COMPONENTS TO AVOID DAMAGE TO CRITICAL SURFACES.

CAUTION: ALWAYS USE APPROPRIATE DISMOUNTING (BEAD BREAKING) EQUIPMENT DESIGNED FOR SEPARATING TIRES FROM WHEEL BEAD SEATS.

CAUTION: DO NOT USE HAMMERS, PRY BARS, TIRE IRONS, OR ANY SHARP TOOLS TO LOOSEN TIRE BEADS. IMPROPER EQUIPMENT MAY DAMAGE THE TIRE, WHEEL, OR CAUSE PERSONAL INJURY.

- 4.4. Various types of bead breaking equipment exist. General descriptions are provided for five (5) common types. Refer to the respective operating manual for proper use of each.
 - 4.4.1. Manual, lever arm type bead breaker primarily used in the General Aviation industry for small tires. Refer to Figure 602.

602

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)



Figure 602. Lever Arm Bead Breaker

- 4.4.2. Ring-type bead breakers use a moveable adapter ring to press against the lower sidewall 360 degrees around one side of the tire, near the bead. The opposite side normally consists of a stationary adapter ring that contacts the lower sidewall of the tire. Pneumatic/hydraulic pressure is normally used to apply force. Refer to Figure 603.
- 4.4.2.1. The adapter rings must be designed for the particular tire/wheel assembly to be dismounted due to differences in wheel diameter and flange design.
- 4.4.2.2. The part of the ring that contacts the tire should be without sharp edges and of sufficient thickness to press on the tire without damage.
- 4.4.2.3. Recommended radial clearance between the top of the wheel flange and adapter ring is 10 mm (0.4 in).
- 4.4.2.4. The travel of the adapter ring should be at least 100 mm (4 in) to ensure complete separation of the tire from the wheel.
- 4.4.2.5. It is desirable that the adapter rings be designed with small windows such that the tire can be observed while pressure is being applied to ensure satisfactory ring contact and progress.

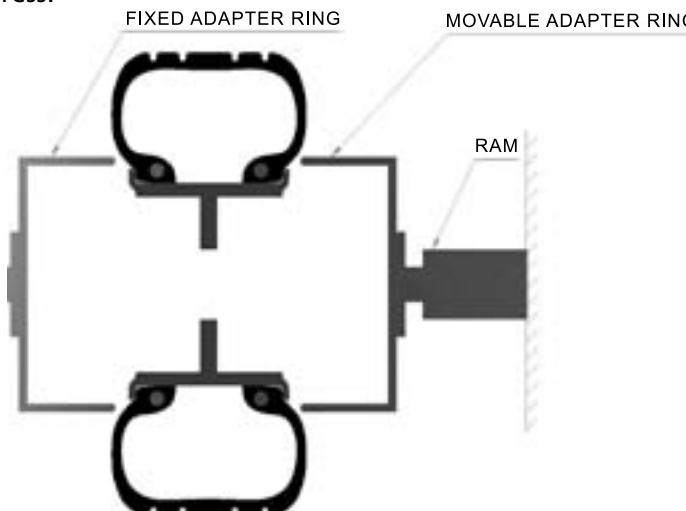


Figure 603. Ring-Type Bead Breaker



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)

- 4.4.3. Finger-type bead breakers are much like the "Ring-Type" except that the adapter rings are replaced with adjustable multiple fingers for pressing against the tire's lower sidewall. There should be a pad at the end of each finger that will "mate" properly to the sidewall of the tire to minimize the stress when pressing the tire from the wheel. Refer to Figure 604.
 - 4.4.3.1. Recommended radial clearance between the top of the wheel flange and press pads is 10 mm (0.4 in).
 - 4.4.3.2. The finger pad that contacts the tire should be without sharp edges and of sufficient size to press on the tire without damage.
 - 4.4.3.3. The pads should be sufficiently large to reduce the stress on the sidewall when the tire is pressed for removal. The size of the pad will depend on the tire sizes being dismounted.
 - 4.4.3.4. The travel of the adapter ring should be at least 100 mm (4 in) to ensure complete separation of the tire from the wheel.



Figure 604. Finger-Type Bead Breaker

- 4.4.4. Pincher-type bead breakers use two arms with press pads at the ends to press in a localized area against both lower sidewalls of the vertically standing tire. A pressing action partially moves the tire away from the wheel flange. The tire is rotated and the process repeated until both beads are completely loose from the wheel. Refer to Figure 605.
 - 4.4.4.1. The tire is positioned by an adjustable cylinder so that the press pads contact the tire's lower sidewall just above the wheel flange.
 - 4.4.4.2. Recommended radial clearance between the top of the wheel flange and press pads is 10 mm (0.4 in).
 - 4.4.4.3. The press pads should be sufficiently large to reduce the stress on the sidewall when the tire is pressed for removal. The size of the pad will depend on the tire sizes being dismounted.

604



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)

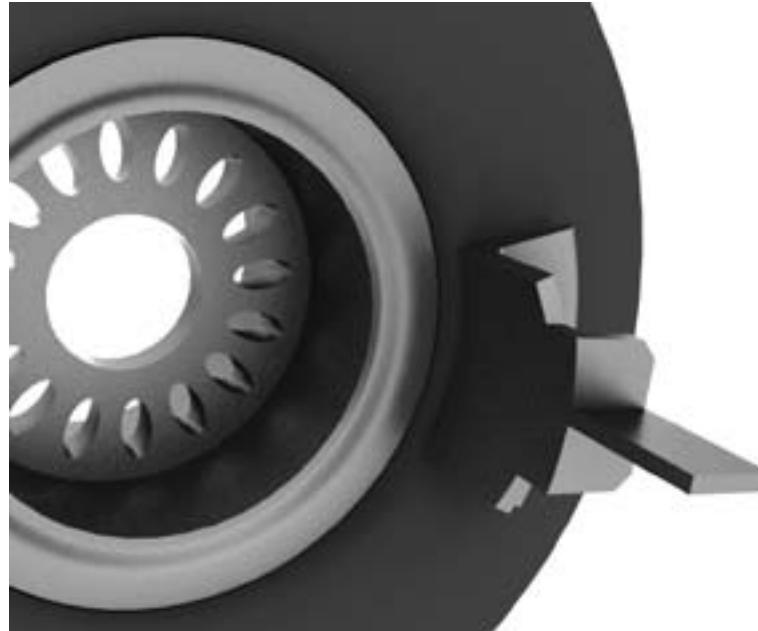


Figure 605. Pincher-Type Bead Breaker

- 4.4.5. Roller Disk-type bead breakers use a shaped roller to press against the vertically rotating tire. Some roller-disk machines will press on only one side. Some machines will press both sides at the same time. Pressing occurs while the tire/wheel assembly is slowly rotated. Refer to Figure 606 and Figure 607.
- 4.4.5.1. Recommended radial clearance between the top of the wheel flange and roller disk is 10 mm (0.4 in).

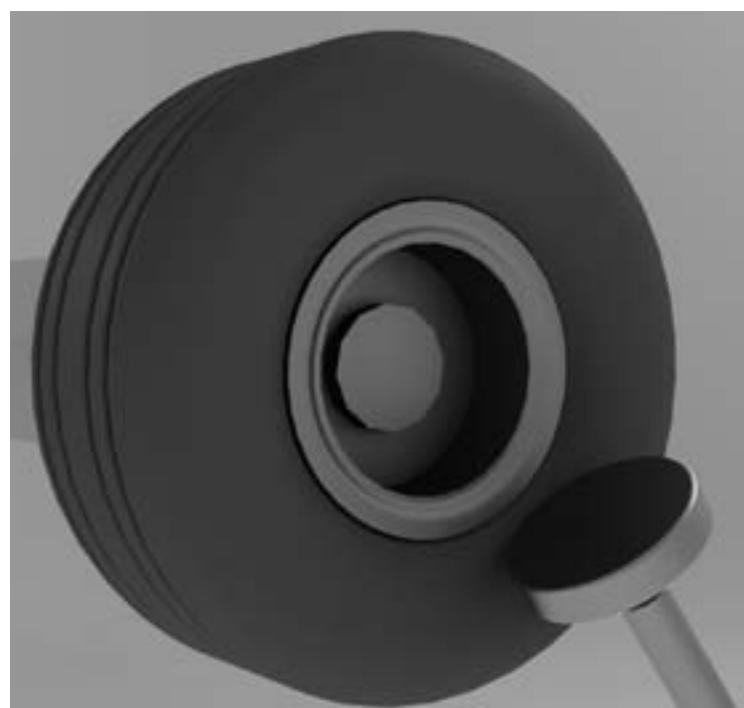


Figure 606. Conical Roller Bead Breaker – Single Roller



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)



Figure 607. Conical Roller Bead Breaker – Two Rollers

5. Disassembly (Dismounting) of the Tire From the Wheel

- 5.1. The methods used for dismounting tubeless bias, tube-type bias and radial aircraft tires are essentially the same.
- 5.2. Radial tires have a single bead cable which requires a smaller bead flat area. As a result radial tires generally have a more flexible sidewall than bias tires. It is important that the equipment be set up and operated properly.
- 5.3. Mark all damages with a tire marking pen or crayon before deflating.
- 5.4. Completely deflate the tire or tube by removing the valve core.
 - 5.4.1. If damage has occurred, a tire/wheel assembly should be deflated in a protective steel cage.
- 5.5. Use appropriate dismounting (bead breaker) equipment to loosen tire beads from both wheel halves. Follow the operating instructions for the specific equipment.

NOTE: Applying pressure too rapidly can cause sidewall distortion. Heavy distortion may damage the internal tire components, and may also begin to “roll” the beads making dismounting more difficult.
- 5.6. Pincher-Type Bead Breaker
 - 5.6.1. Align the press pads so that they are matched to the curvature of the wheel flange. The pincher arm should be within 10 mm (0.4 in) of the flange. Refer to Figure 608 for proper alignment.

606

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)


Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)

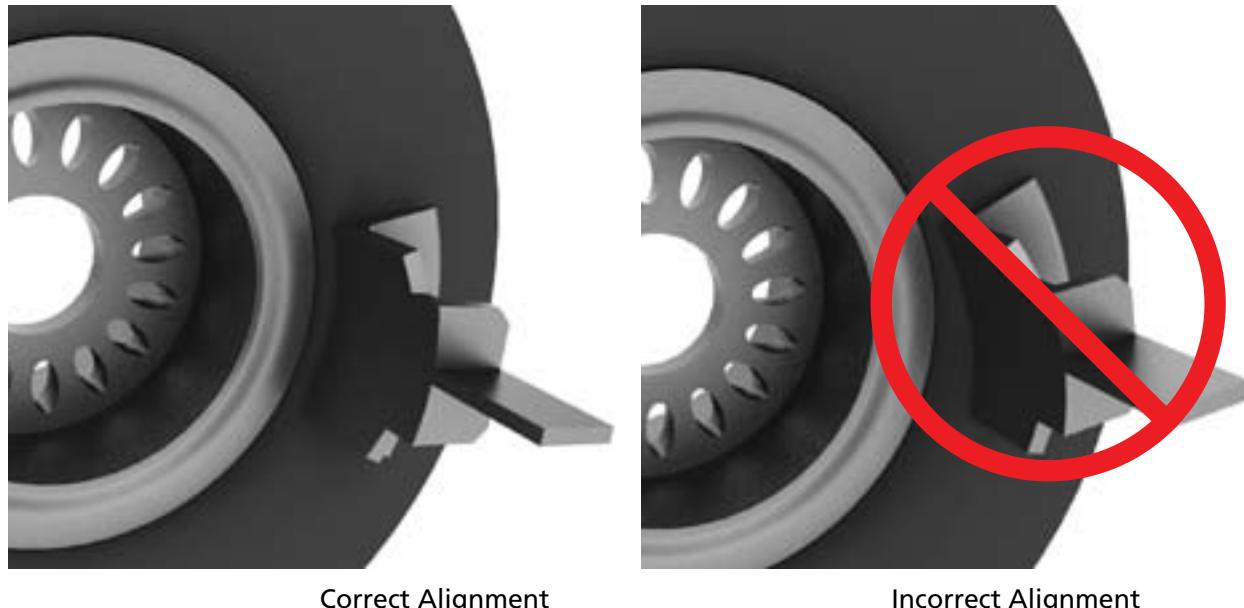

Correct Alignment

Incorrect Alignment

Figure 608. Correct/Incorrect Alignment of Press Pads

5.6.2. Apply pincher arm pressure slowly to allow the beads time to move. Allow 2-3 seconds of hold time for the beads to move partially away from the wheel flange.

5.6.3. Release pincher pressure.

5.6.4. Rotate the tire/wheel assembly the length of the press pads. Refer to Figure 609.

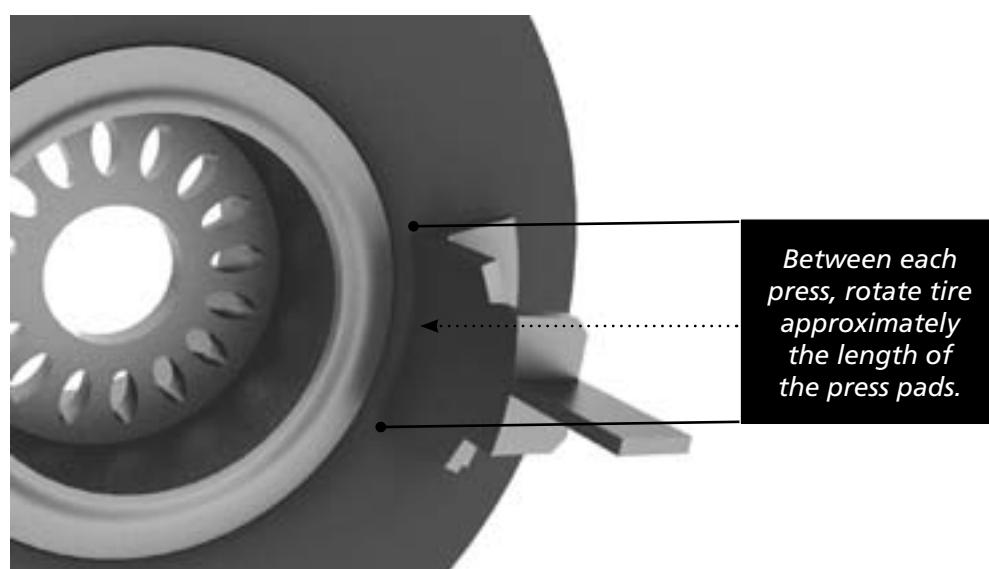


Figure 609. Rotation Between Pressings

607

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)

- 5.6.5. Slowly apply pincher arm pressure in the new sector for 2-3 seconds to allow the beads to move partially away from the wheel flange.
 - 5.6.5.1. If necessary, non-metallic blocks (wood or rubber) may be placed between the tire's bead and wheel flange before releasing the pressing action. These blocks will hold the tire bead in the pressed position and may facilitate bead release. The blocks should have no sharp edges. Refer to Figure 610.
 - 5.6.5.2. Another aid is to apply tire mounting lubricant between the tire bead and wheel flange before releasing the pressing action.

NOTE: Bead breaking is most efficient when the tire/wheel assembly is rotated no more than 30 degrees between each pressing operation.

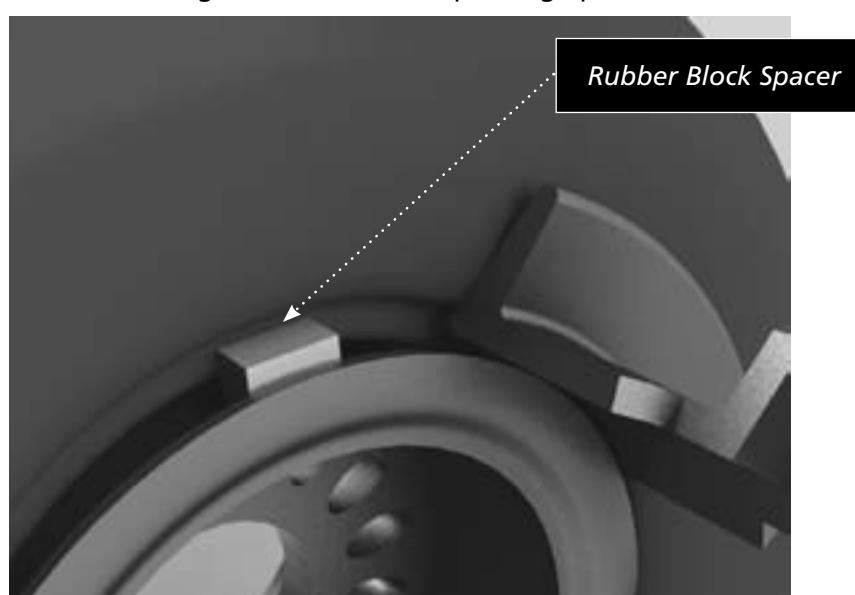


Figure 610. Rubber Block Holding Bead From Wheel Flange

- 5.6.6. Repeat the steps §5.6.1 through §5.6.4 around the bead area of the tire until the bead is free of the wheel.

NOTE: The most common cause of problems using the pincher-type bead breaker occurs when attempts are made to press tire beads too quickly by using a rapid pincher force or by rotating the tire too much between pincher actions.

- 5.6.7. Remove the tire/wheel assembly from the pincher bead breaker machine.
- 5.6.8. Remove tie bolts and separate wheel halves in accordance with the wheel manufacturer's CMM.

5.7. Single Roller Disk Equipment

- 5.7.1. The tire/wheel assembly is vertically mounted and affixed on the machines rotating axle.
- 5.7.2. Align the disk head against the lower sidewall of the tire within 10 mm (0.4 in) of the wheel flange.
- 5.7.3. Slowly rotate the tire/wheel assembly while applying disk pressure against the lower sidewall of the tire.
- 5.7.4. During several rotations, the tire bead will slowly release from the wheel.
- 5.7.5. Move the roller disk head to the opposite side of the tire.
- 5.7.6. Repeat steps §5.7.2, §5.7.3, §5.7.4 above.
- 5.7.7. Dismount the tire/wheel assembly from the bead breaker machine.
- 5.7.8. Remove tie bolts and separate wheel halves in accordance with the wheel manufacturer's CMM.

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)

- 5.8. Double Roller Disk Equipment
 - 5.8.1. The tire/wheel assembly is vertically mounted and affixed on the machines rotating axle.
 - 5.8.2. Align the disk heads against both lower sidewalls of the tire within 10 mm (0.4 in) of the wheel flange.
 - 5.8.3. Slowly rotate the tire/wheel assembly while applying disk pressure against the lower sidewalls of the tire.
 - 5.8.4. During several rotations, the tire beads will slowly release from the wheel.
 - 5.8.5. Dismount the tire/wheel assembly from the bead breaker machine.
 - 5.8.6. Remove tie bolts and separate wheel halves in accordance with the wheel manufacturer's CMM.
- NOTE:** When using a roller disk machine, as the tire begins to move away from the wheel flange, the roller disk should slide lower on the tire's sidewall such that the disk is actually below the wheel flange. This allows the disk to press on a more rigid part of the tire and facilitates bead release.

6. Troubleshooting Disassembly (Dismounting) Issues

WARNING: REVIEW ALL WARNINGS, CAUTIONS, AND NOTES IN §2 OF THIS CHAPTER.

- 6.1. Tire Beads will not release from the wheel.
 - 6.1.1. The most common problem in releasing tire beads is "bead roll-over" when attempts are made to press tire beads too quickly. Refer to Figure 611.
 - 6.1.2. As pressure is applied to the tire, a flexible sidewall and a small bead flat may allow the bead to rotate around the bead wire causing the bead toe to contact the wheel surface and block movement of the bead. This action impedes the movement of the bead away from the flange.

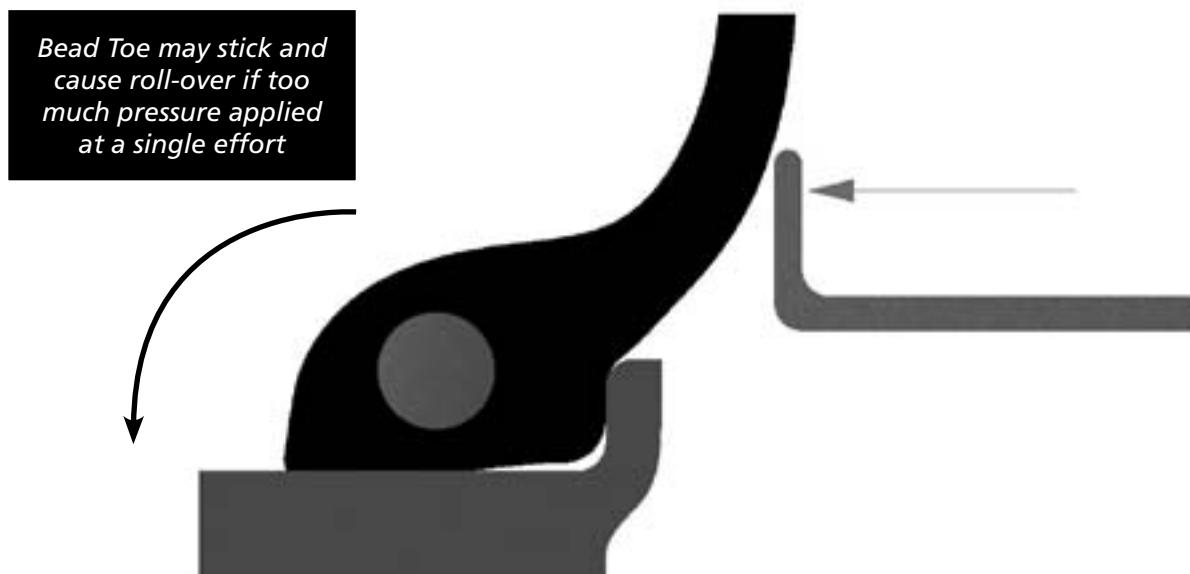


Figure 611. Bead Roll-over

609

MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)

- 6.1.3. If bead roll-over begins to occur, release the ram pressure.
- 6.1.4. Apply a soap solution or other non-hydrocarbon lubricant approved by the wheel manufacturer, between the tire/wheel interface.

NOTE: Refer to wheel CMM for approved lubricants.

- 6.1.4.1. Allow several minutes for the solution to penetrate between the tire and wheel.

- 6.1.5. Reapply a reduced hydraulic pressure to the tire.

- 6.1.6. Repeat several times if necessary.

- 6.1.7. If the tire remains fast:

- 6.1.7.1. Remove the tire/wheel assembly from the bead breaker machine. It will be necessary to reinflate the tire.

WARNING: AIRCRAFT TIRES MUST ALWAYS BE INFLATED WITH A PROPERLY REGULATED INFLATION SOURCE. REGULATE THE SUPPLY LINE TO A PRESSURE NO GREATER THAN 150% OF THE OPERATING PRESSURE. INFLATING WITHOUT A PRESSURE REGULATOR PRESENTS A RISK OF PERSONAL INJURY AND/OR DAMAGE TO EQUIPMENT.

WARNING: USE A SUITABLE INFLATION CAGE WHEN INFLATING A TIRE WHEEL ASSEMBLY. UNNOTICED DAMAGE TO THE TIRE, THE WHEEL, WHEEL BOLTS AND/OR IMPROPER PROCEDURE, MAY CAUSE THE TIRE/WHEEL ASSEMBLY TO BURST DURING THE INFLATION PROCESS, WHICH MAY RESULT IN SERIOUS OR FATAL BODILY INJURY.

- 6.1.7.2. Place the assembly in a proper safety cage.

- 6.1.7.3. Reinflate the tire until the bead moves back to its correct position.

- 6.1.7.4. Deflate the tire.

- 6.1.7.5. Repeat the dismounting procedure until the bead dismounts from the wheel.

- 6.1.8. Remove tie bolts and separate wheel halves in accordance with the wheel manufacturer's CMM.

- 6.1.9. Below is an example of a modified press pad to help prevent bead roll-over with pincher-type bead breakers.

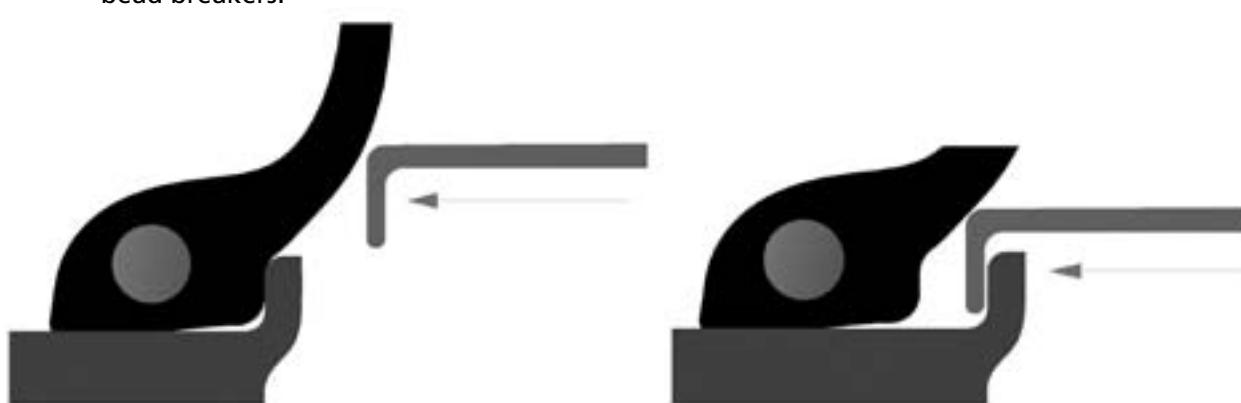


Figure 612. Modified Press Pad for Pincher-Type Bead Breakers

610

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 6 - DISMOUNTING (DISASSEMBLY)

7. Tire Inspection After Dismounting

- 7.1. Tires should be inspected by trained technicians to determine the disposition of the tire.
- 7.2. Tires provided under a supplier contract should be returned to the supplier in accordance with that contract.
- 7.3. Tires owned by the operator should be inspected for possible retreading or disposed of properly. If in doubt, it is best to forward tires to a certified repair station for disposition.
- 7.4. The following examples of damages may cause a tire to be rejected for retreading. In some cases, a determination of serviceability is necessary by a trained technician at an authorized repair station.
 - 7.4.1. Injuries to the bead area except those limited to the bead cover or finishing strip (an exposed chafer strip will cause no trouble and is serviceable).
 - 7.4.2. Weather-checking or cracking that exposes ply cords.
 - 7.4.3. Protruding bead wire or kinked (bent) bead.
 - 7.4.4. Ply separations.
 - 7.4.5. Internal damage or broken ply cords.
 - 7.4.6. Flat spots and skid burns that penetrate to the top casing ply (bias) or top belt ply (radial).
 - 7.4.7. Punctures or cuts that penetrate the innerliner.
 - 7.4.8. Brake heat damage, particularly if the fuse plug has released.
 - 7.4.9. Tires heavily soaked in fuel, hydraulic fluid, oil, or other contaminating fluid.
 - 7.4.10. Tires that have experienced a major pressure loss.
 - 7.4.11. Tires with a wrinkled innerliner.

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

611



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 7 - RETREAD AND REPAIR

1. General

This Chapter includes information concerning retreading and repair of aircraft tires.

- 1.1. The term retreading refers to the method of restoring a worn retreadable tire to operational condition by renewing the tread rubber or by renewing the tread rubber plus the reinforcing plies (bias) or protector ply (radial).
- 1.2. During the retread process, the old tread products are removed and replaced with new materials. The tread rubber extends beyond the shoulder of the tire by several inches. By design, a buffed or roughened surface will be visible where the old products were removed and the new products join the sidewall. Refer to Figure 701.
- 1.3. Cross retreading – cross retreading is the practice of one manufacturer retreading tire casings of other tire manufacturers, in addition to its own casings. This practice is based upon customer agreements and manufacturer restrictions.
- 1.4. The current practice of cross retreading applies only to bias casings. Michelin will cross retread bias tires, as do other manufacturers. The practice of cross retreading does not apply to radial aircraft tires. Michelin retreads its own radial casings and other manufacturers retread their own casings.
- 1.5. Normal retread buffed surface in Figure 701.



Figure 701. Retread Buffed Surface

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

701



MICHELIN AIRCRAFT TIRE CARE AND SERVICE MANUAL

CHAPTER 7 - RETREAD AND REPAIR

Aircraft Tire Description/
Construction

Aircraft Tire Terminology
and Tire Markings

Receiving and Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation on Aircraft

Dismounting
(Disassembly)

Retread and Repair

2. Retreading Aircraft Tires

- 2.1. The FAA, EASA and regulatory organizations in other countries require retreading and/or repair of aircraft tires to be performed only by a certified facility. The certification is determined by the governing authority under which the operator is authorized.
- 2.2. All Michelin repair facilities are certified by the appropriate governing authority.
- 2.3. Each casing is thoroughly inspected to ensure it meets retreading specifications. Non-destructive inspection methods are used including:
 - 2.3.1. Visual inspection by a trained, certified technician following established procedures and under a quality system.
 - 2.3.2. Air needle testing.
 - 2.3.3. Shearography.

3. Repairing Aircraft Tires

- 3.1. Tires with sidewall cuts, snags, scuffs, and cracking from ozone can remain in service if the casing ply is not exposed.
- 3.2. Many tires with damage may be repaired during the retread process depending upon the location and/or severity of the damage.
- 3.3. Damages that expose casing plies may be repaired by an approved repair station.
- 3.4. Any damage that is repaired must be within limits specified by the tire manufacturer in accordance with established referential.

NOTE: Repair limits generally exceed serviceability limits because service removal limits are set to ensure safe operation and retreadability of the casing.


- 3.5. Non-Repairable/Retreadable Aircraft Tires.

NOTE: All aircraft tires provided under a supplier's contract should be returned to that vendor for disposition.

- 3.5.1. Following is a non-exhaustive list of the main damages that may prevent a tire from being retreaded.
 - Exposed bead wire or kinked (bent) bead.
 - Injuries to the bead area except those limited to the bead cover or finishing strip (an exposed chafer strip will cause no trouble and is serviceable).
 - Cracking that exposes ply cords.
 - Sidewall cuts or punctures that expose the ply cords.
 - Ply separations or a visible bulge or deformed tire.
 - Internal damage or broken ply cords.
 - Flat spots and skid burns that penetrate to the top casing ply (bias) or top belt ply (radial).
 - Punctures or cuts that penetrate the innerliner.
 - Brake heat damage, particularly if the fuse plug has released.
 - Tires that have evidence of hydro-carbon contamination (oil soaked).
 - Tires that have experienced a major pressure loss (operated with less than 80% of specified operating pressure).
 - Tires with a wrinkled innerliner.
- 3.5.2. If in doubt, it is best to send the tires to a certified repair station for examination by a trained technician.

702

MICHELIN BRINGS TOP-QUALITY SERVICE AROUND THE GLOBE

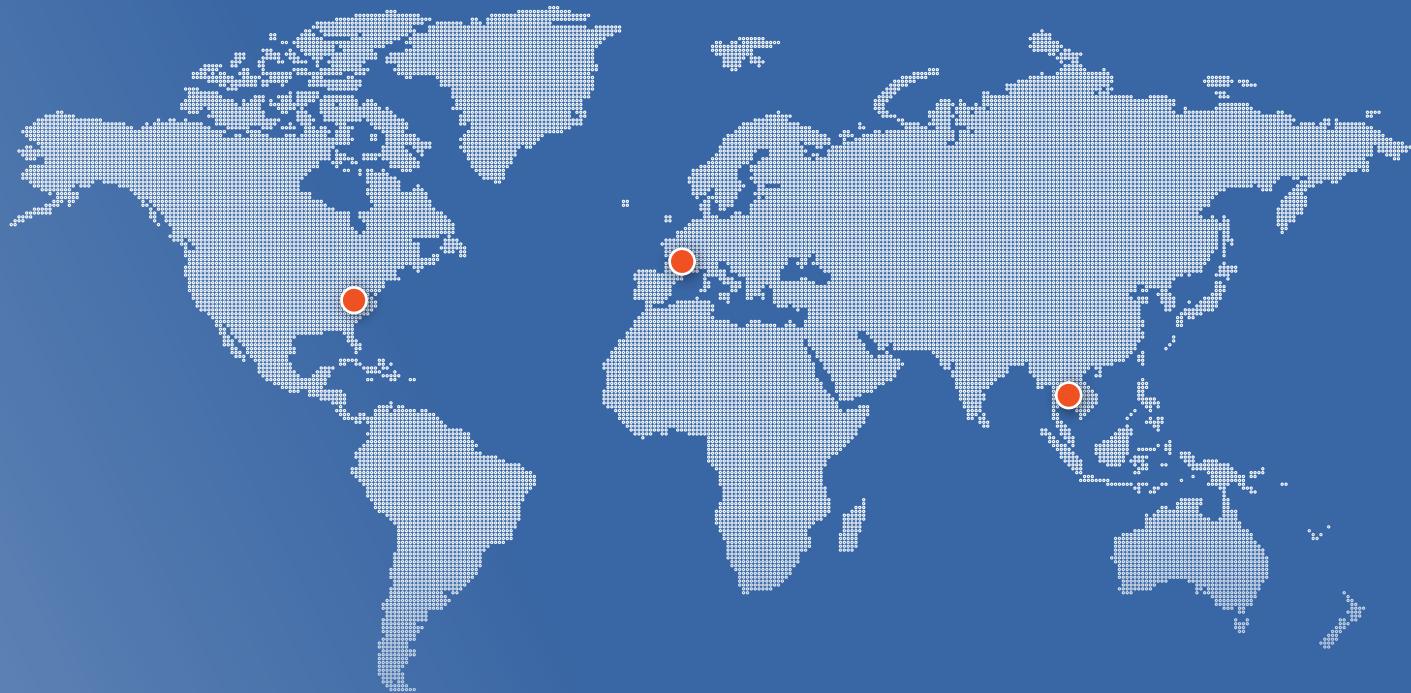

MICHELIN MAIN OFFICES:

Europe, CIS, Middle East & Africa

Michelin Aircraft Tyre
23, Place des Carmes-Déchaux
63040 Clermont-Ferrand Cedex 9
France
Ph : +33 (0) 4 73 32 61 06
Fax : +33 (0) 4 73 32 76 44

North, Central & South America

Michelin Aircraft Tire Company
One Parkway South
Greenville, South Carolina 29615
USA
Ph: +1-877-503-8071
Fax: +1-864-458-6746

Asia & Oceania

Michelin Siam Co. Ltd.
Aircraft Tyre Operations
SPE Tower 11th Floor
252 Phaholyothin Road
Samsaen Nai, Payathai
Bangkok 10400
Thailand
Ph: +66 (2) 619-3524
Fax: +66 (2) 619-3529

www.airmichelin.com

\$35.00 US

Copyright ©2011 Michelin North America, Inc. All Rights Reserved. The Michelin Man is a registered trademark of Michelin North America, Inc. ©Michelin-T. Gromik.



Aircraft Tire Description/
Construction

Aircraft Tire Terminology/
And Tire Markings

Receiving And Storing
Aircraft Tires

Mounting Instructions
(Assembly)

Operation On Aircraft

Dismounting
(Disassembly)

Retread And Repair