

Carbopol® Ultrez 21 Polymer

INCI name: Acrylates/C10-30 alkyl acrylate crosspolymer

Technical Data Sheet

Product Overview

Carbopol® Ultrez 21 Polymer is a hydrophobically modified crosslinked polyacrylate polymer designed to efficiently impart thickening, stabilizing, and suspending properties to a variety of personal care applications. The polymer incorporates patented technology, which allows it to quickly and easily self-wet – without any mixing required. (Please note that typical mixing/agitation is needed to make a final product).

Physical Properties

Physical properties of Carbopol Ultrez 21 polymer are listed in Table 1 and indicate typical values and properties; they are not intended to be used as product specifications.

Table 1

Carbopol® Ultrez 21 Polymer Typical Properties (not to be used as specification)	
• Appearance	white powder
• Odor	mild acrylic odor
• Total solids	100%
• pH (in water)	3
• 0.5% mucilage* viscosity at 20 rpm	55,000 mPa·s
• 0.5% dispersion wetting time	3 minutes
• 0.5% mucilage* clarity (% Transmission):	~ 95

* A mucilage is defined as an active polymer dispersion in water neutralized with a base, preferably NaOH, to a specified pH.

Benefits

In addition to the benefits that all powdered Carbopol polymers provide, which include thickening, yield value, shear thinning rheology and favorable toxicology profile, Carbopol Ultrez 21 polymer offers the following benefits:


- **Rapid wetting ...**

Carbopol Ultrez 21 polymer has self-wetting properties similar to Carbopol Ultrez 10 polymer. Dispersion of 0.5% Carbopol Ultrez 21 polymer can self-wet within minutes without any mixing.

- **High thickening efficiency ...**

Carbopol Ultrez 21 polymer provides more efficient thickening than other Carbopol polymers, such as Carbopol 934, Carbopol 940 and Carbopol 980 polymers (See Figure 1). For instance, a reduction of about 15% polymer is recommended when using Carbopol Ultrez 21 polymer to achieve a similar viscosity in most emulsion formulas.

Figure 1 – Mucilage Viscosity

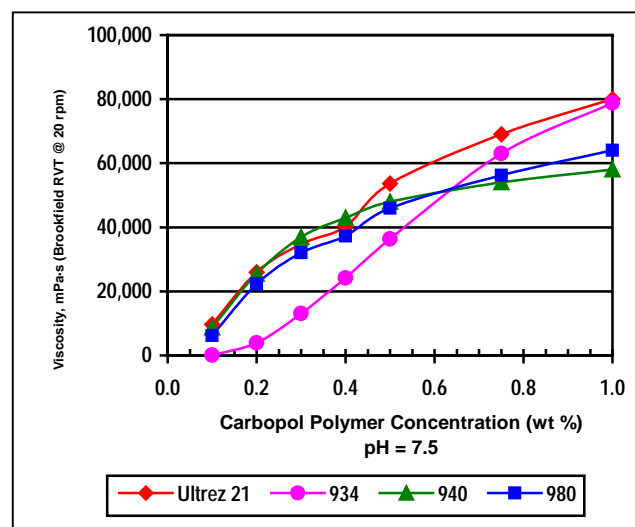

- **Improved electrolyte tolerance ...**

Carbopol® Ultrez 21 polymer provides superior electrolyte tolerance compared to most Carbopol polymers, resulting in improved clarity and higher viscosity in electrolyte containing systems.

- **Excellent clarity ...**

Carbopol Ultrez 21 polymer provides excellent clarity to applications such as hair gels and hand sanitizers.

- **Smooth aesthetic appearance ...**

Carbopol Ultrez 21 polymer provides a non-grainy glossy appearance to gels and emulsions similar to gels and emulsions made with Carbopol 940 and 934 polymers.

- **Superior skin feel ...**

Carbopol Ultrez 21 polymer is less tacky than other Carbopol polymers.

- **Broad application use ...**

Carbopol Ultrez 21 polymer has the best overall performance in a wide variety of applications when compared with other Carbopol polymers.

Suggested Applications

Carbopol Ultrez 21 polymer can be used in a wide variety of applications, such as:

- Hair Styling Gels
- Hand and Body Lotions
- Baby Lotions
- Hand Sanitizers
- Moisturizing Gels
- Sunscreen Lotions
- Bath Gels
- Shampoos

Processing Guidelines

The development of the self-wetting technology has greatly improved the dispersability of Carbopol polymers - especially in water. These polymers behave differently in their dispersion as well as hydration rates and need to be processed and handled in a slightly different manner.

Using No Agitation (Self-Wetting) - Preferred

This is the preferred method of dispersion and will result in less entrapped air.

In most situations, Carbopol Ultrez 21 polymer can simply be “sprinkled” onto the surface of the water without any special equipment or handling.

The powder will wet and drop below the surface in minutes. When there is no visible white powder on the water surface, mixing can begin.

Using Moderate to High Agitation

Dispersions can also be prepared by slowly sifting the polymer into the vortex of a rapidly stirred solution, although this technique may entrap more air.

Techniques or devices which sprinkle the powder as discrete particles are the most effective. The ideal method should efficiently sprinkle the polymer at a controlled rate as well as break-up the soft agglomerates of dry powder formed by static electricity or humid conditions. This allows each particle to completely wet out in the water vortex.


In general, high shear rates disperse the polymer very rapidly; however, extremely high shear mixers or homogenizers should be carefully employed because they can break down the polymer molecule - resulting in permanent viscosity loss. Moderate agitation equipment is the preferred choice. Conventional impellers such as propellers or turbines are recommended.

Wetting Time, Dispersion Viscosity, and Others

The total wetting time is dependent upon the amount of Carbopol Ultrez 21 polymer added, vessel geometry, and most importantly, water temperature. When the Carbopol Ultrez 21 polymer dispersion is first neutralized, the surface texture may have a grainy “applesauce” appearance. Over the next 30-60 minutes, the neutralized gel clusters continue to relax and expand. Light mixing will yield a smooth gel.

Some users choose to predisperse Carbopol Ultrez 21 polymer in water and then add this dispersion to their formulation mix tank. Unlike the traditional Carbopol polymers, Carbopol Ultrez 21 polymer can be dispersed at concentrations up to 6% and still remain pumpable. See Figure 2

Figure 2 – Dispersion Viscosity

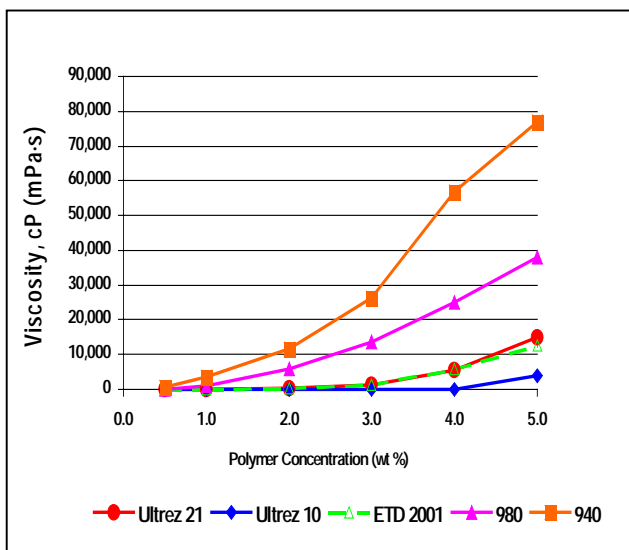

Under high shear agitation, dispersions of Carbopol® Ultrez 21 polymer can stabilize entrapped air. Antifoam, at use levels of 0.02 - 0.05%, can be added to the water prior to the Carbopol Ultrez 21 polymer in order to minimize or eliminate foaming.


Formulating Guidelines

In most situations, Carbopol Ultrez 21 polymer should be added to the water at the start of the batch cycle. This will allow it time to thoroughly wet out and disperse. At this point, the pH will be about 3 with a very low viscosity.

Neutralization

Upon neutralization, the Carbopol Ultrez 21 polymer instantly thickens as shown in Figure 3.

Figure 3 – Effect of pH on Viscosity

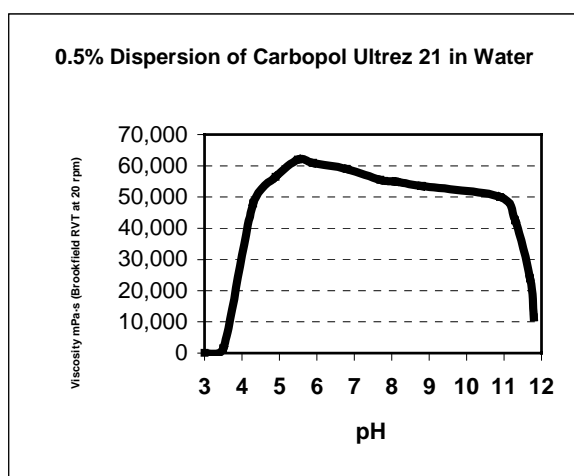

Because of the high viscosity, the addition of the neutralizing agent is often best added towards the end of the batch cycle. For formulations with high levels of electrolytes or surfactants, the addition of a small amount of the neutralizer to the Carbopol Ultrez 21 polymer dispersion is beneficial (partial neutralization).

Different neutralizers can be used, and different amounts are needed for the dispersion to reach a pH value of 7.0. Table 2 provides the weight ratios of commonly used neutralizers vs. Carbopol Ultrez 21 polymer to achieve pH 7.

For a complete list of neutralizers that can be used with Carbopol polymers, see TDS-237 - Neutralizing Carbopol® and Pemulen® Polymers in Aqueous and Hydroalcoholic Systems.

Table 2

Weight ratios of commonly used neutralizers vs. Carbopol Ultrez 21 polymer to achieve pH 7

Neutralizer Trade Name/Supplier	Neutralizer INCI Name	Weight Ratio – Neutralizer / Carbopol Ultrez 21
TEA (99%)	Triethanolamine	1.5 / 1.0
AMP-95® / Angus	Aminomethyl Propanol	0.9 / 1.0
Neutrol® TE / BASF	Tetrahydroxypropyl Ethylenediamine	2.3 / 1.0
NaOH (18%)	Sodium Hydroxide	2.3 / 1.0
Diisopropanolamine / Dow	Diisopropanolamine	1.2 / 1.0

Preservation

Carbopol Ultrez 21 polymer does not support bacteria or fungal growth, but neither does it prevent such growth on nutrients found in normal water systems. The addition of a preservative is recommended for applications inclined to these issues.

Carbopol Ultrez 21 polymer is compatible with most preservatives, such as Germaben II, DMDM Hydantoin, Dowicil 200, Parabens and Phenonip. Phenonip has limited solubility in clear gel formulations, which may result in reduced clarity.

Compatibility

The viscosity of products with Carbopol Ultrez 21 polymer is moderately sensitive to ions. Increased levels of monovalent ions (like sodium) will result in a decrease in application viscosity. The effect can be minimized by the use of potassium salts or amine neutralizing agents. Di- and multi-valent ions (like calcium and magnesium) will precipitate Carbopol polymers. Therefore, formulating with deionized (or at least soft) water is highly recommended.

Due to its anionic nature, Carbopol Ultrez 21 polymer has limited compatibility with cationic formulating materials.

Handling and Storage

Carbopol Ultrez 21 polymer is supplied in 20-kilogram cardboard boxes.

In the dry form, Carbopol Ultrez 21 polymer is stable for a long period of time. It is important, however, to keep the containers tightly closed to prevent moisture pick-up.

See the Material Safety Data Sheet for Carbopol Ultrez 21 polymer for further information on the proper handling and safety aspects of this product.