



FORT WAYNE METALS

9609 Ardmore Ave | Ft Wayne, IN | 46809
260-747-4154

Wednesday, February 11, 2026 3:03:40 PM

Customer	
Quality Order Number	
Production Order Number	
Alloy Type	
Sales Order Number	
Purchase Order Number	
Operator	
Production Machine	
Instron	TT-
Load Cell Used	
Method description	216- Lake 6% Strain 3% Measured
Gage Length	5.00000 in

	Serial Number	Diameter [in]	Breakload [lbf]	Tensile Strength [psi]	Elongation [%]	Upper Plateau Load [lbf]	Upper Plateau Stress [psi]	Lower Plateau Load [lbf]	Lower Plateau Stress [psi]
1		0.01962	38.343	126823	6.2	-----	-----	-----	-----
2		0.01812	27.352	106068	3.5	-----	-----	-----	-----
3		0.01772	31.959	129592	5.5	-----	-----	-----	-----
4		0.01765	33.121	135371	6.8	-----	-----	-----	-----
5		0.01778	29.009	116837	9.6	-----	-----	-----	-----
6		0.01774	36.641	148241	6.2	-----	-----	-----	-----
7		0.01778	39.631	159616	6.4	-----	-----	-----	-----
8		0.01772	43.001	174366	7.1	-----	-----	-----	-----
9		0.01750	27.593	114719	3.1	-----	-----	-----	-----
Mean		0.01796	34.072	134626	6.1	-----	-----	-----	-----
Standard deviation		0.00064	5.63028	22372.45059	1.92622	-----	-----	-----	-----
Mean + 3 SD		0.01989	50.963	201743	11.8	-----	-----	-----	-----
Mean - 3 SD		0.01603	17.181	67509	0.3	-----	-----	-----	-----
Minimum		0.01750	27.352	106068	3.1	-----	-----	-----	-----
Maximum		0.01962	43.001	174366	9.6	-----	-----	-----	-----

	Yield Load [lbf]	Yield Strength [psi]	Permanent Set [%]	Modulus [Msi]	Visual Surface s Prim	Visual Surface s Sec	Straightness	Out of Roundness
1	-----	-----	1.28	17.826				



FORT WAYNE METALS

9609 Ardmore Ave | Ft Wayne, IN | 46809
260-747-4154

Wednesday, February 11, 2026 3:03:40 PM

	Yield Load [lbf]	Yield Strength [psi]	Permanent Set [%]	Modulus [Msi]	Visual Surface s Prim	Visual Surface s Sec	Straightness	Out of Roundness
2	-----	-----	1.12	16.883				
3	-----	-----	1.17	16.707				
4	-----	-----	1.30	17.293				
5	-----	-----	1.36	19.167				
6	-----	-----	1.10	18.493				
7	-----	-----	1.08	20.088				
8	-----	-----	0.93	18.721				
9	-----	-----	0.69	22.671				
Mean	-----	-----	1.11	18.650				
Standard deviation	-----	-----	0.20748	1.86929				
Mean + 3 SD	-----	-----	1.74	24.258				
Mean - 3 SD	-----	-----	0.49	13.042				
Minimum	-----	-----	0.69	16.707				
Maximum	-----	-----	1.36	22.671				

Results Table 2

	Spool Number	Operator
1	697-7 1200C/1FPM tested after 4 days	
2	697-7 1200C/2FPM H2	
3	697-7 1200C/4FPM argon	
4	697-7 1200C/2FPM argon	
5	697-7 1200C/0.8FPM argon	
6	697-7 1200C/8FPM argon	
7	697-7 1200C/12FPM argon	
8	697-7 1200C/20FPM argon	
9	697-7 1200C/25FPM H2	




FORT WAYNE METALS


9609 Ardmore Ave | Ft Wayne, IN | 46809
260-747-4154

Wednesday, February 11, 2026 3:03:40 PM

Tensile Test

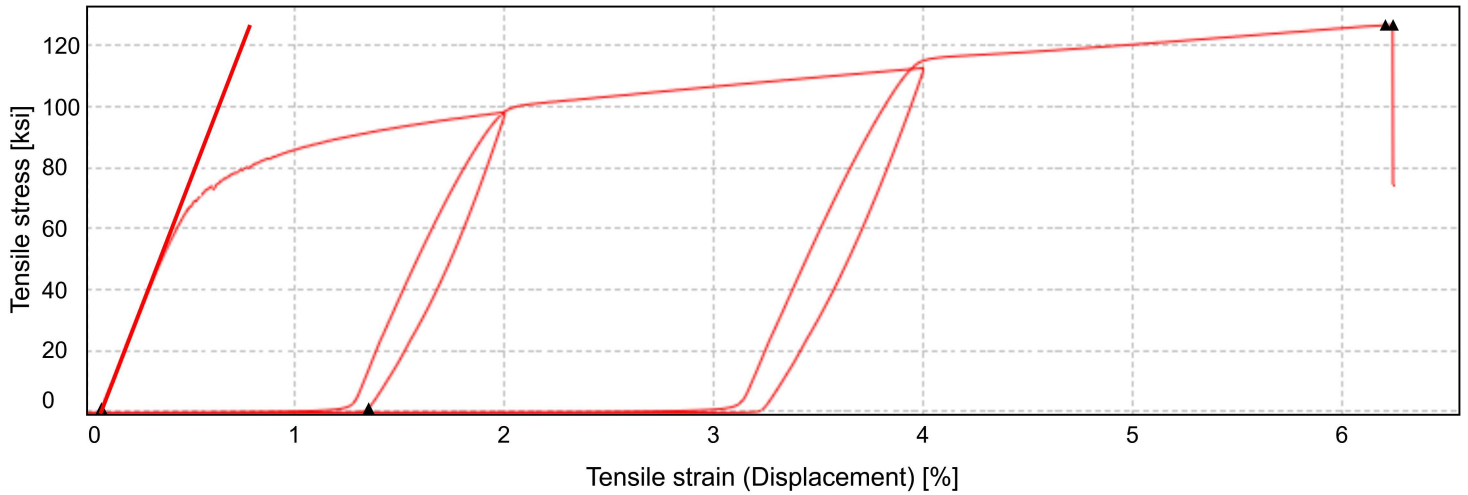

Tensile Test

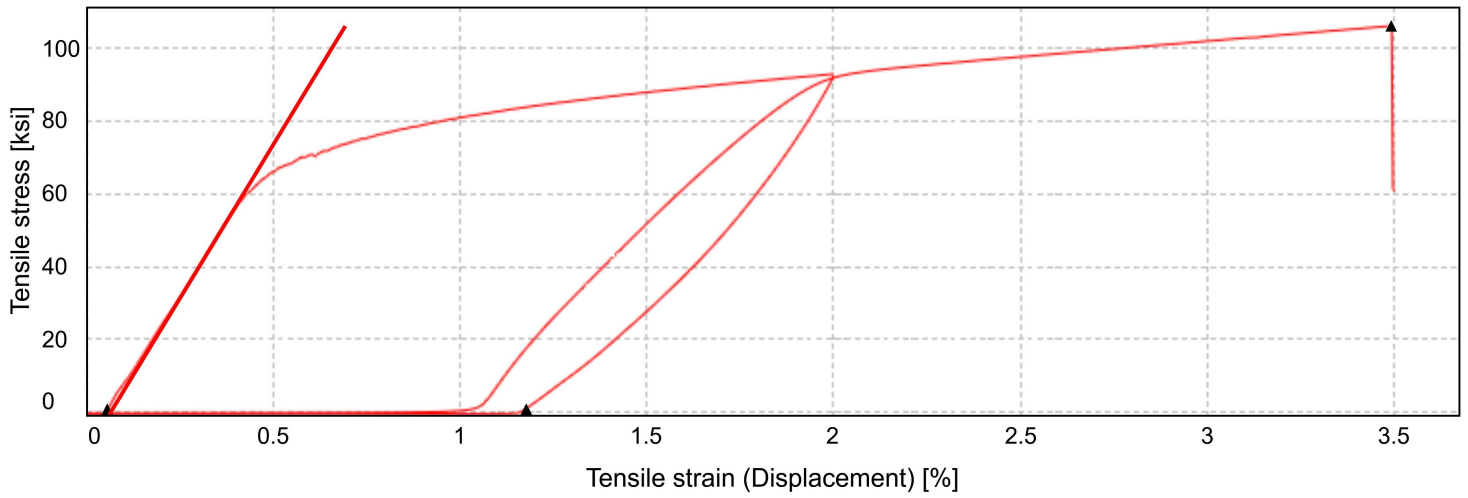




FORT WAYNE METALS


9609 Ardmore Ave | Ft Wayne, IN | 46809
260-747-4154

Wednesday, February 11, 2026 3:03:40 PM

Tensile Test

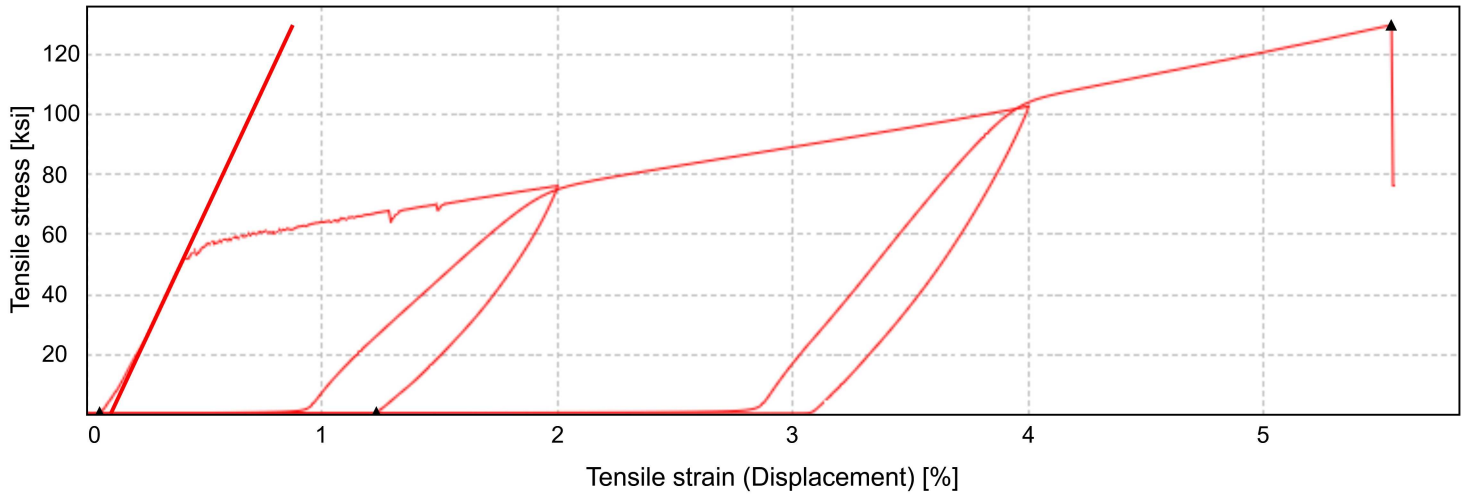

Tensile Test

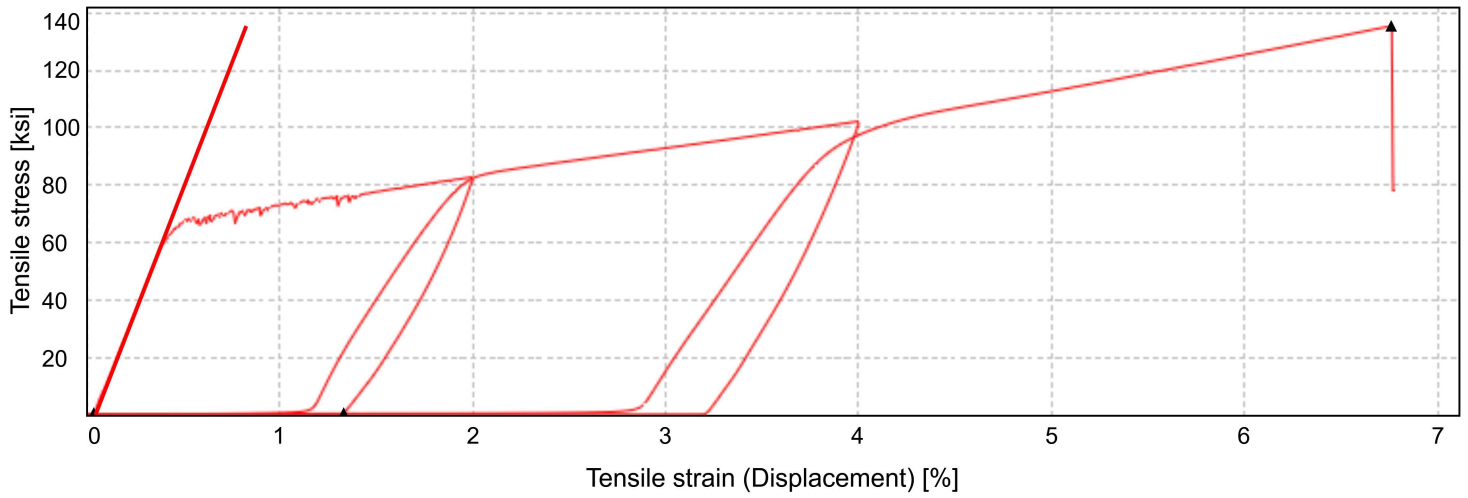




FORT WAYNE METALS


9609 Ardmore Ave | Ft Wayne, IN | 46809
260-747-4154

Wednesday, February 11, 2026 3:03:40 PM

Tensile Test

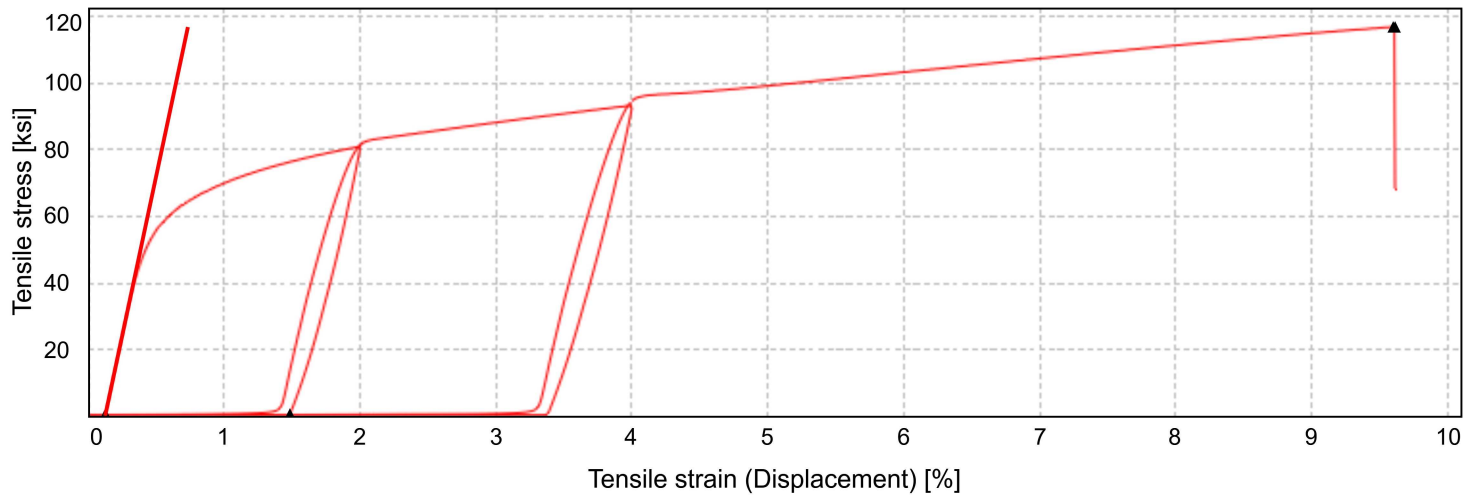

Tensile Test

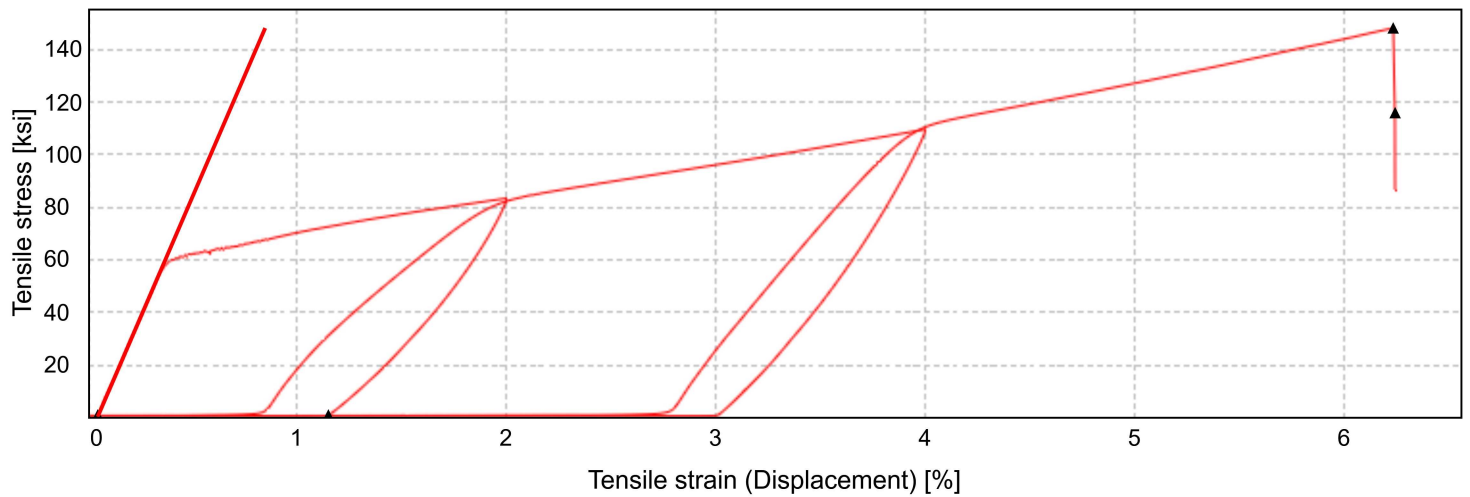




FORT WAYNE METALS


9609 Ardmore Ave | Ft Wayne, IN | 46809
260-747-4154

Wednesday, February 11, 2026 3:03:40 PM

Tensile Test

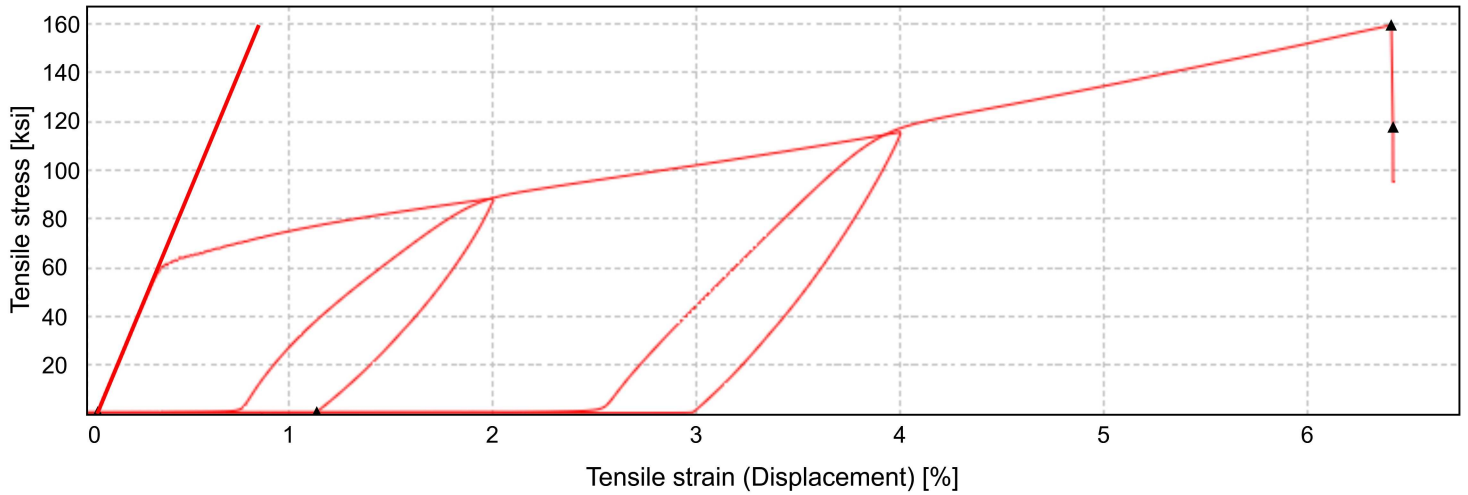

Tensile Test

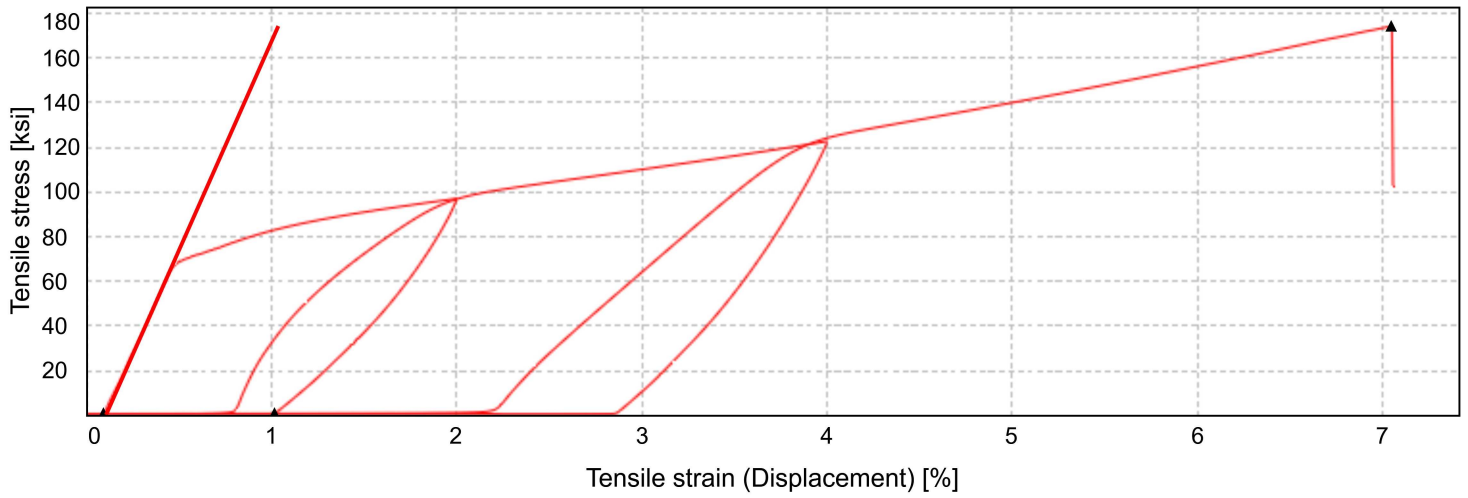



FORT WAYNE METALS

9609 Ardmore Ave | Ft Wayne, IN | 46809
260-747-4154

Wednesday, February 11, 2026 3:03:40 PM

Tensile Test

