Guangzhou Building Materials Institute Limited Company

中国认可
国际互认
检测
TESTING
CNAS L0057

Test Report

GML-V001

Client:	DONGGUAN TECH FREE AIR CONDITIONING MFY, LTD.	Laboratory:	(Stamp)
Project Name:	----		
Position of Construction:	----	Report No.:	V03-19000089 (E)
Test Standard:	EN 13501-1：2007+A1：2009	Sample Number:	1V0319000103
Supervision:	----	Type of Test:	Sample delivered by client
Date Received: 2019-05-20	Date Tested: 2019-06-20	Date of Issue:	2019-06-24

Sample Information					
Sample Name	Profile intermediate rubber strip -Type I 28	Sample Type	S-128 PA66GF25/2mm	Sample Number	1.5m*1m2/ bundle
Productor	FOSHAN CITY LONGYAOJIN METAL TECHNOLOGY CO,. LTD (Brand: TIANLONG)			Date Product	----

Test Information

Test Items	Measure Unit	Test Standard	Technical Requirement		Test Results	Individual Judgment
$FIGRA_{0.4MJ}$	W/s	BS EN 13823:2010+A1:2014	D	≤750	371	Compliant
Fs	mm	ISO 11925-2:2010		≤150	42	Compliant
SMOGRA	m^2/s^2	BS EN 13823:2010+A1:2014	s2	≤180	18	Compliant
TSP_{600s}	m^2	BS EN 13823:2010+A1:2014		≤200	152	Compliant
Flaming droplets / particles in 600s	---	BS EN 13823:2010+A1:2014	d0	NO	NO	Compliant
Ignition of the filter paper in 60s	---	ISO 11925-2:2010		NO	NO	Compliant
Conclusion	The inspected items are satisfied the technical requirements of BS EN 13501-1:2007+A1:2009 about class D-s2, d0.					
Remark	Brand: longyaojin					

Laboratory address: No.2, Keyan Road, Guangzhou, Guangdong, China

A000

1WT0319000169

Certified by: Checked by: 邹玉龙 Tested by: 高世杰

Guangzhou Building Materials Institute Limited Company

Test Report (Continue)

Report No.: V03-19000089 (E)

Description of BS EN 13823:2010+A1:2014 specimen:

1. According BS EN 13823:2010+A1:2014, the specimen is composed with long wing and short wing, the dimension of long wing is 1500mm×1000mm and short wing is 1500mm×500mm.

2. According BS EN 13823:2010+A1:2014, The sample is mechanically mounted on the backing board. The backing board is calcium silicate boards with a density of 900 kg/m^3 and a thickness of 12mm.

Specimen photos before and after the test

Before the test

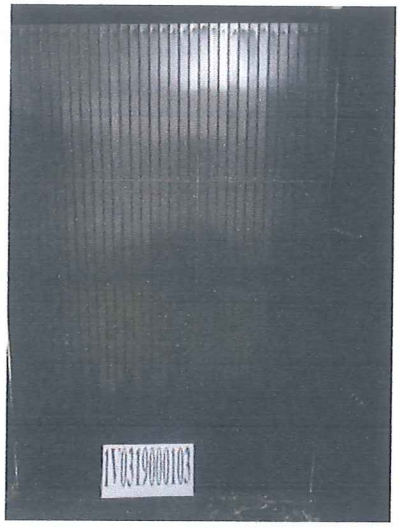

Long wing (left)

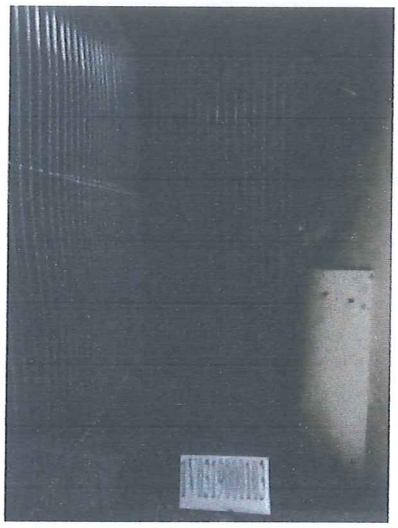

Short wing (right)

After the test

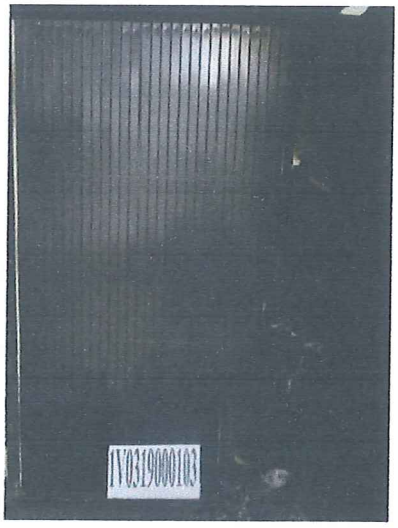

Long wing (left)

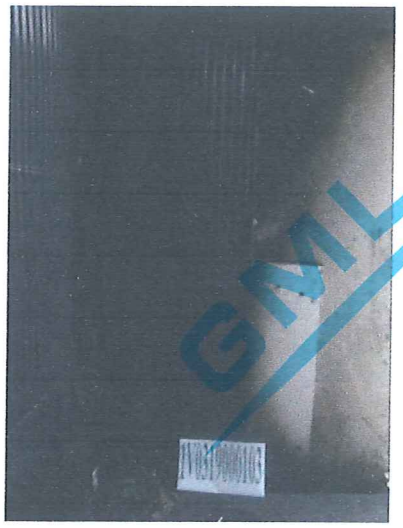

Short wing (right)