# Guangzhou Building Materials Institute Limited Company

中国认可
国际互认
TESTING
CNAS L0057

# Test Report

GML-V020

Client: DONGGUAN TECH FREE AIR CONDITIONING MFY, LTD.

Laboratory: (Stamp)

Project Name: ---

Position of Construction: ---

Report No: V02-1800255 (E)

Test Standard: BS EN 13501-1：2007+A1：2009

Sample Number: 1V021800157

Supervision: ---

Type of Test: Sample delivered by client

Date Received: 2018-12-19

Date Tested: 2018-12-30

Date of Issue: 2019-01-04

| Sample Information | | | | | |
|---|---|---|---|---|---|
| Sample Name | Panel rubber strip - L | Sample Type | ABS-H-36/2mm | Sample Number | 3 PCS |
| Productor | Dongguan Shipai Duanxin plastic products factory | | | Date Product | --- |

Test Information

| Test Items | Measure Unit | Test Standard | Technical Requirement | | Test Results | Individual Judgment |
|---|---|---|---|---|---|---|
| $FIGRA_{0.4MJ}$ | W/s | BS EN 13823:2010+A1:2014 | C | ≤250 | 172 | Compliant |
| LFS | m | BS EN 13823:2010+A1:2014 | | < the edge of the specimen | YES | Compliant |
| $THR_{600s}$ | MJ | BS EN 13823:2010+A1:2014 | | ≤15 | 14.0 | Compliant |
| Flame spread in 60s(Fs) | m | ISO 11925-2:2010 | | ≤150 | 36 | Compliant |
| SMOGRA | $m^2/s^2$ | BS EN 13823:2010+A1:2014 | s2 | ≤180 | 398 | s3 |
| $TSP_{600s}$ | $m^2$ | BS EN 13823:2010+A1:2014 | | ≤200 | 1720 | |
| Flaming droplets/particles in 600s | --- | BS EN 13823:2010+A1:2014 | d0 | NO | NO | Compliant |
| Ignition of the filter paper in 60s | --- | ISO 11925-2:2010 | | NO | NO | Compliant |
| Conclusion | The burning behavior of the sample is satisfied the technical requirements of BS EN 13501-1:2007+A1:2009 about class C-s3,d0. | | | | | |
| Remark | Brand: Rui Zhan | | | | | |

Laboratory address: No.2, Keyan Road, Guangzhou, Guangdong, China A000

1WT021811222

Certified by: Checked by: 邵玉书 Tested by: 高世杰

# Guangzhou Building Materials Institute Limited Company

# Test Report (Continue)

Report No: V02-1800255 (E)

Description of BS EN 13823:2010+A1:2014 specimen:

1.According BS EN 13823:2010+A1:2014, the specimen is composed with long wing and short wing, the dimension of long wing is 1500mm×1000mm and short wing is 1500mm×500mm.

2.According BS EN 13823:2010+A1:2014, The sample is mechanically mounted on the backing board. the backing board is calcium silicate boards with a density of 900 kg/m$^3$ and a thickness of 12mm.

BS EN 13823:2010+A1:2014 Specimen photos before and after the test

Before the test

Long wing(left)

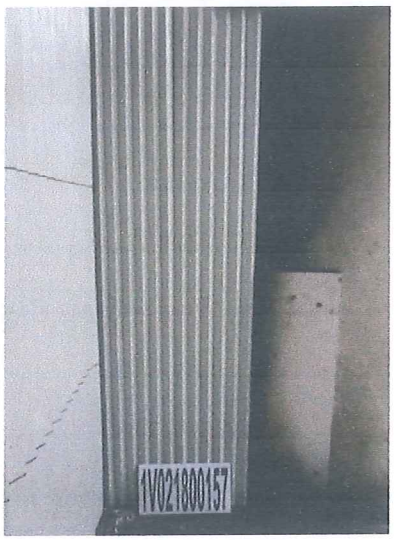


Short wing(right)

After the test

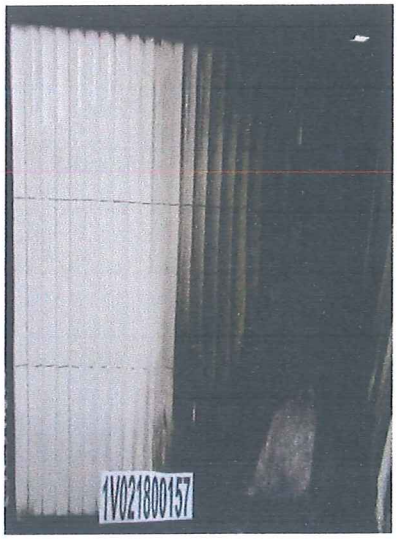


Long wing(left)

Short wing(right)