

Life cycle assessment of asphalt and cement pavements: Comparative cases in Shanxi Province

Xinxing Zhou^{a, b, *}, Xiaorui Zhang^c, Yuan Zhang^d, Sanjeev Adhikari^e

^aKey Laboratory of Highway Construction and Maintenance Technology in Less Region of Ministry of Transport, Shanxi Transportation Technology Research & Development Center, Taiyuan 03002 China

^bState Key Laboratory of Silicate Materials for Architecture, Wuhan University of Technology, Wuhan 430070 China

^cSchool of Transportation, Southeast University, Nanjing 211189 China

^dDepartment of Civil Engineering & Transportation, South China University of Technology, Guangzhou 510641 China

^eCollege of Architecture and Construction Management, Kansas State University, Manhattan 66506, USA

ARTICLE INFO

Article history:

Received 4 June 2021

Received in revised form 10 November 2021

Accepted 16 November 2021

Keywords:

Lifecycle assessment

Energy consumption

Environmental pollution emission

Freshwater toxicity

ABSTRACT

In order to understand the energy consumption and environmental pollution level of Shanxi highway construction, the life cycle environmental and energy impact assessment of asphalt mixture and cement concrete were conducted. One representative cement concrete pavement and two asphalt mixtures highways were selected for quantitative evaluation and LCA analysis. The total energy consumption values of Taichang highway are 20% higher than that of the Dayun highway. The global warming potential indicators of Taichang (asphalt mixture), Dayun (asphalt mixture), and Deda (cement concrete) are 181 kgeq CO₂, 285 kgeq CO₂ and 330 kgeq CO₂ respectively during the materials production stage. The results indicated that the environmental effects of global warming had the biggest impact on the lifecycle of the asphalt mixtures and the respective highways. Based on the study results, environmental pollution was highest on the Taichang highway whilst the Deda highway had the highest values of freshwater toxicity. Furthermore, energy consumption during the construction stage and environmental impacts at the end-of-life stage were found to be alarmingly high. Thus, reducing the energy consumption during the material preparation and highway construction stages as well as controlling the environmental pollutants and emissions during service are key to conserving energy, preserving the surrounding environment, and optimizing the lifecycle of Shanxi highways.

© 2021

1. Introduction

With the economic development, the transportation development of Shanxi Province has met a tremendous development opportunity. As of 2020, Shanxi Province had a total of 30 major highways. Taichang (Taiyuan to Changzhi and Jincheng), Dayun (Taiyuan to Datong and Yuncheng) and Deda (Deshengkou to Datong city) are the three principal highways of Shanxi Province. Due to the high energy consumption and construction/maintenance costs associated with these highways, it is necessary to comparatively evaluate and quantify their sustainability (both economically and environmentally) through conducting a life cycle assessment (LCA) [1–2].

LCA can be used for evaluating potential environmental pollutants and energy consumption throughout a product or structure's life [3–4].

Recent studies have shown that energy consumption at the usage stage of asphalt pavements is affected by various factors including materials type, functional layer structure and pavement thickness [5–6]. Aside from the associated costs and high potential for resources depletion, energy consumption will also lead to severe greenhouse (CO₂) emissions. Reducing CO₂ emissions in the transportation field has thus become one of the key remedies of mitigating national carbon emissions for many countries [7].

Numerous studies have been carried out in China to evaluate the environmental impacts of asphalt pavements using LCA in China [8]. From their findings rubber modified asphalt pavements showed high environmental impacts compared to reclaimed asphalt pavements [9]. Similarly, Azari-Jafari et al. [10] studied the human toxicity potential, metal release and the hazardous waste of recycled asphalt pavements and found that the contaminant (Cd, Cr, Se and Ag) transported from the bottom ash resulted in a very low unsaturated zone. The “cradle-to-grave” LCA always involves many stages and activities that result in different energy and environmental paradigms [11–12]. Asphalt pave-

* Corresponding author at: Room 218, 27 Wuluo Street, Xiaodian District, Taiyuan, China.

E-mail address: zx0943233@whut.edu.cn (X. Zhou).

ment preservation such as use of thin overlays is not only cost-effective, but also brings significant environmental benefits [13–14]. Likewise, use of bio-asphalt materials could significantly reduce the energy consumption factor and environmental pollutants [15]. The literature shows that CO₂ emissions and environmental impacts related to the roads and highways are just one magnitude lower than that of bridges and tunnels [16]. Asphalt pavement can affect significantly the environment and economy of China [17–19]. Although there are many researches about LCA of asphalt pavement, there are lack of LCA of cement concrete pavement, and LCA analysis method of Shanxi highways based on the various stages of energy and environmental assessment are not clear.

Based on the above background, as a step towards minimizing energy consumption and reducing the environmental pollution, the LCA of representative highways in Shanxi Province, were comparatively evaluated in this study, with a focus on quantifying the energy and environmental impacts. The functional units, boundary conditions, life cycle inventory and data acquisition of LCA of Shanxi highway were proposed. LCA energy consumption evaluation included impacts of different highways and pavement types and impacts of different highway life cycle stages were investigated. Further, a life-cycle analysis method was also formulated based on the various stages of energy and environmental assessment. This study proposed the four environmental impact indicators (Global warming potential, Acidification potential, Freshwater toxicity, and Human toxicity) and its detailed evaluation compounds, which were used to verify the environmental impact indicators whether were suitable with the typical highways in Shanxi Province.

2. Study methodology

The LCA in this study was conducted in accordance with the ISO standard 14040/14044 [20] using the 2019 Chinese energy data. Three major highways, namely Taichang, Deda, and Dayun, respectively, in Shanxi Province of China were selected and used as the case study. The respective highway construction data were obtained from Shanxi Transportation Holdings Group CO., LTD.

As discussed in the subsequent text, the study methodology incorporated defining the scope of work and the corresponding research tasks. The study functional units, boundary conditions, and highway pavement structures are also discussed in this section of the paper.

2.1. Scope of work and research tasks

LCA is a useful tool for evaluating the energy consumption and the impacts of environmental pollution. Within this framework, the scope of work and research tasks for this study involved addressing the following objectives:

- Energy consumption assessment, mainly focusing gasoline and diesel usage;
- Evaluation of the environmental impacts of each stage of the LCA which included CO₂, CO, CH₄, SO₂, NO_x, NMVOC and PM_{2.5} emissions; and
- Identification of the potential environmental improvements by analyzing different types of asphalt mixture pavements and cement concrete pavements from a life cycle point of view.

As previously mentioned, the selection of the highway types to be studied was based on considering that there are three major highways in Shanxi Province (China), namely:

- a) Taichang (asphalt mixtures pavement),
- b) Deda (cement concrete pavement) and
- c) Dayun (asphalt mixtures pavement)

2.2. Study functional units and boundary conditions

The selected study functional units, which represents the fundamental unit throughout the whole LCA study, were each 1.0 km length of a highway pavement section. The pavement layer thicknesses for the different highways were different and were evaluated as such. The study included all the stages and activities that encompass materials production, transportation, construction, operations and maintenance work, and end-of-life during the life cycle process as per the “cradle-to-grave” method [21]. The “cradle-to-grace” method is that everything ranges from raw material acquisition to production, use and disposal.

The total pavement width for each of the three selected highways (namely Taichang, Deda, and Dayun), incorporating all the lanes, was about 27.5 m. The corresponding pavement structures, mostly comprising of the surface course, binder course, unbound base course, and sub-grade course, are shown in Table 1.

Other highway structures such as embankments, drainage systems and road markings were not included in this study because their contributions is negligible for highway construction and LCA [22].

The pavement surface layer thickness of the Taichang, Deda, and Dayun highways are 17 cm, 28 cm, and 16 cm, respectively. The boundary conditions and the flow sequence adopted for the study are shown in Fig. 1.

From Fig. 1, the flow sequence for LCA and the boundary conditions can be summarized as bullet-listed below:

- Materials production including raw materials and energy supplements.
- Transportation including raw materials transportation, earthwork removal/transportation and equipment transportation.
- Construction, which is made up of the pavement and base, or sub-base construction and includes all the stages of the road construction.
- Operations and maintenance work including maintenance, demolition, and reconstruction of the pavement, in order to ensure functionality, in terms of the bearing capacity, surface layer or thin overlay over the lifespan of the pavement construction.
- End-of-life, which consists of recycling, reuse, or disposal of solid waste, or regenerated material.

To sustain and maintain the average life span of road pavements, there is often a need (including preventive maintenance) to ensure suitable levels of service. The fundamental data of road pavement showed as Table 2 and these data obtained from Chinese Reference Life Cycle Database (CLCD) [23]. The database is that a national background LCI database consists of ca. 600 LCI datasets for key materials and chemicals, energy carriers, transport, and waste management. In this study, the useful lifetime of Taichang and Dayun highway pavements (asphalt) was assumed to be 15 years while that of Deda highway pave-

Table 1
Highway pavement structures.

Structure layer	Taichang	Deda	Dayun
Upper layer	Material type 4 cm SMA-13 (asphalt)	28 cm cement concrete	4 cm SMA-13 (asphalt)
Middle layer	6 cm AC20	—	5 cm AC16
Lower layer	7 cm AC25	20 cm cement stabilized macadam	7 cm AC20
Base layer	33 cm cement stabilized macadam	36 cm ash stabilized soil	20 cm cement stabilized macadam
Sub-base	20 cm composite stabilized soil	20 cm gravel	20 cm cement stabilized macadam

Legend: AC = asphalt concrete, SMA = stone matrix (mastic) asphalt.

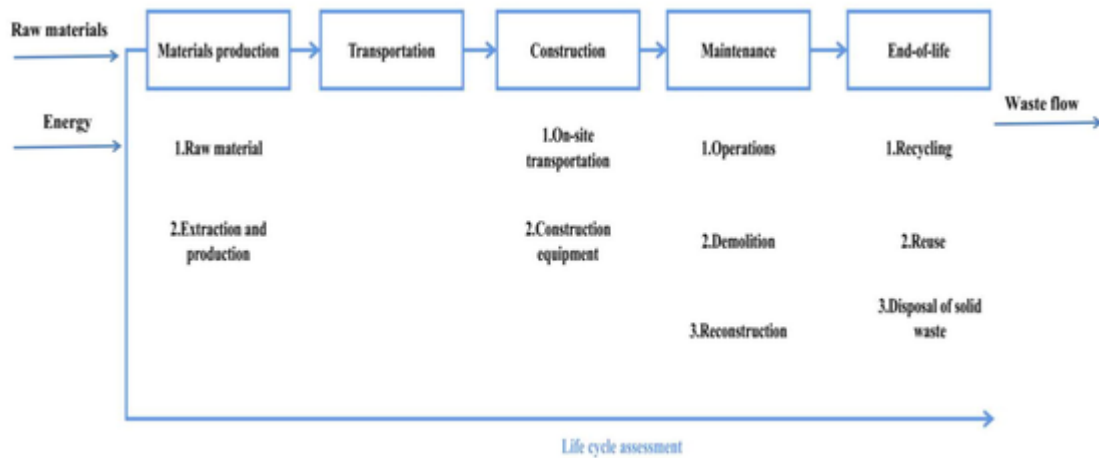


Fig. 1. Life cycle stages diagram

Table 2
The fundamental data of road pavement

Data of raw materials		
Raw materials	Energy consumption (MJ/t)	Environmental pollutants (kg/t)
Base asphalt	280760	18120
SBS modified asphalt	541220	23040
Rubber	3590	0970
Aggregate	31990	238163
Cement	340000	79850
Data of material production (mixtures production)		
Mixture type	Energy consumption (MJ/t)	Environmental pollutants (kg/t)
SMA-13	33670	28260
AC13	33490	27810
AC16	32580	28050
AC20	33490	27810
AC25	33780	28260
Data of Transportation stage		
Transportation method	Energy consumption (MJ/t)	Environmental pollutants (kg/t)
30t heavy diesel truck	0804	0075
Data of construction stage (Paving process of mixtures)		
Mixture type	Energy consumption (MJ/t)	Environmental pollutants (kg/t)
SMA-13	15860	1180
AC13	1320	0980
AC16	11580	0750
AC20	8810	0660
AC25	7340	0530
Data of construction stage (Rolling process of mixtures)		
Mixture type	Energy consumption (MJ/t)	Environmental pollutants (kg/t)
SMA-13	18600	1380
AC13	1320	0980
AC16	12850	0960
AC20	12480	0930
AC25	10390	0770
Data of maintenance stage		
Mixture type	Energy consumption (MJ/t)	Environmental pollutants (kg/t)
SMA-13	18290	306330
AC13	15970	267520
AC16	15250	255830
AC20	14800	247890
AC25	7970	11930

ment (concrete) was assumed to be 20 years. Maintenance stage, maintenance or preventive maintenance of the top layer of the pavement structure included an ultra-thin wearing course or skid-resistant surface layer, which was assumed to occur at the third of the asphalt pavements' service life (i.e., per 5 years/maintenance).

3. LCA formulation and data assembly

The LCA formulation including the software method used and the environmental impact indicators considered in the study are discussed in this section of the paper. The life cycle inventory and data acquisition for LCA are also discussed in this section.

3.1. LCA method used and environmental impact indicators

Life cycle assessments were computed using the materials balance method whilst the life cycle environmental impacts indicators were formulated using the ReCipe method and OpenLCA LCA methods 1.5.7. In this study, the LCA was evaluated using the openLCA1.10.3 software [24]. Life cycle energy consumption and emission data were used based on the database of CML 2015. The fundamental energy consumption lists included carbon emission values (g/MJ), specific energy consumption (Q_{he} MJ/kg), and emission factors (g/t). The eco-indicator for climate change was CO₂ emission while the eco-indicator for air acidification was SO₂.

The main eco-indicator of human toxicity were NO_x, CO, NMVOC, PM_{2.5}, NH₃ and heavy metals which can be represented by 1,4-dichlorobenzene equivalent. The eco-indicator for freshwater toxicity was hydrocarbon and heavy metal which could be represented by 1,4-dichlorobenzene equivalent. The eco-indicator for terrestrial ecotoxicity was part of NMVOC, hydrocarbon and heavy metals, which could be represented by 1,4-dichlorobenzene equivalent. In this study, the energy and environmental indicators or categories were evaluated and showed as follows:

- Global energy consumption (MJ);
- Global warming potential (GWP, kg eq CO₂);
- Acidification potential (AP, kg eq SO₂);
- Freshwater toxicity (FT, kg eq 1,4-dichlorobenzene included hydrocarbon and heavy metals); and
- Human toxicity (HT, kg eq 1,4-dichlorobenzene included NMVOC + PM_{2.5} + NO_x).

3.2. Life cycle inventory and data acquisition

Life cycle inventory (LCI) was conducted to quantitatively evaluate the energy and environmental inputs and outputs of the LCA system. The LCI data is shown in Table 3.

The specific energy consumption of natural gas, crude oil, coal, gasoline, and uranium are 48.0 MJ/kg, 42.3 MJ/kg, 26.7 MJ/kg, 45.3 MJ/kg, and 8.5×10^4 MJ/kg, respectively. The specific gravity of the raw material for (1 t) asphalt production were 20.1 kg/t (natural gas), 40.9 kg/t (crude oil), 1.03 kg/t (coal), 25.8 kg/t (gasoline), and 0.0001 kg/t (uranium), respectively. The energy consumption was calculated as the cumulative energy demand (MJ). The inventory data for the raw materials were obtained from the Ecoinvent database (Version 3.6).

Asphalt mixture or cement concrete pavement process is not only energy energy-consumption, but also includes environmental pollutants emissions such as CO₂, CO, CH₄, SO₂, NO_x, NMVOC and PM2.5. The LCI of environmental pollutants are showed in Table 4.

The emission factors of the environmental pollutants listed in Table 4 are very important for evaluating the LCA of the pavement. The total energy consumption of the raw materials for all the stages of the LCA are shown in Table 5.

The different highways had different data of raw material consumption. These data were the basis for calculating the total energy consumption and environmental pollutants. The fundamental data for energy requirements of the machinery during mixture production, construction (mixing), and transposition were all obtained from the standard of JTGT 3832-2018 "Highway Engineering Budget Quota".

The fuel consumption quota of the construction machinery of 1 work day is shown in Table 6. Using this table, the total fuel consumption and energy consumption of the construction machinery were calculated. Thereafter, the environmental pollutants arising from construction machinery were estimated.

Table 3
LCI data for raw materials and energy.

Energy	Oil (MJ/kg)	Asphalt (kg/t)	Cement (kg/t)
Natural gas	480	201	–
Crude oil	423	409	–
Coal	267	103	960
Gasoline	453	258	–
Uranium	85×10^4	0.0001	0.0005
Electricity	327 × 10 ³	–	–
Total energy consumption of asphalt production	490 × 10 ³	–	–

Table 4
LCI of emissions factors for the environmental pollutants

Emission factor	Asphalt (g/t)	Cement (g/t)
CO ₂	17424	6500
SO ₂	78	13
NO _x	70	16
NMVOC	33	36
PM2.5	16	95

Table 5
Fuel consumption quota of the construction machinery for 1 work day

Type	Taichang	Dayun	Deda
Crude oil (kg)	12808	145215	12558
Gasoline	1065	10626	2525
Diesel oil	5761	4878	12518
Electricity (kWh)	80902	78646	92565

Table 6
Total energy consumption of the raw materials and machine values

Type	Taichang	Deda	Dayun
Workday (d)	16230	25212	2525
Final aggregate asphalt mixture (t)	36000	0	32500
Cement concrete (t)	0	42068	0
Asphalt (t)	3460	0	3651
Fiber (t)	2924	0	3868
Aggregate chips (t)	16932	18215	12223
Crushed aggregate (t)	33152	62548	36255
Wheeled loader (d)	1977	2515	2102
Mixing equipment (d)	740	625	780
Paving equipment (d)	879	548	915
Road roller (d)	5007	1246	5102
Dump truck (d)	799	622	812
Sprayer truck (d)	123	1284	125

4. Results and discussions

The LCA results are presented, analyzed, synthesized, and discussed in this section of the paper. These results and analyses include energy consumption and environmental impact evaluations.

4.1. LCA energy consumption evaluation

The energy consumption evaluation included LCA for different highways and life cycle stages. These results for these LCA evaluations with respect to energy consumption are presented and discussed in this subsection of the paper.

4.1.1. Impacts of different highways and pavement types

The life cycle energy consumption impacts of different pavement types and different stages on emission were analyzed and compared to the traditional pavements. Reducing energy consumption and decreasing environmental pollution constitute some of the key measures to ensure sustainable development [25]. The energy consumption of the highways is shown in Fig. 2.

As shown in Fig. 2(a), the total energy consumption of the Deda highway is smaller than that of Taichang highway and Dayun highways. These results demonstrate that Deda highway, with a cement concrete pavement structure had the smallest energy consumption and that cement concrete can be rated as a low energy consumption pavement technology when compared to asphalt.

Furthermore, the total energy consumption values of Taichang highway is greater than that of Dayun highway. According to the highways construction experts, Taichang highway and Dayun highway are comprised of almost similar pavement structures, particularly the upper surfacing layer - see Table 1. Therefore, they should ideally have similar total energy consumption. However, the results (Fig. 2(a)) show that the total energy consumption values of Taichang highway are 20 % higher than that of the Dayun highway. As evident in Table 1, the main reason for this is that the middle and base layer thickness of the Taichang highway are greater than that of Dayun highway, leading to an increase in then energy consumption.

According to the literature, the total average energy consumption of Chinese highways is 152524.42 MJ [26]. Compared to this study, the highways in Shanxi Province consume a lot of energy. The main reason is the unprofessional supervision [27]. To mitigate this situation, the government can use a public tender and impose energy consumption policies/regulations on designers, builders, inspectors, and clients. Unified training for the construction team can also be mandated.

4.1.2. Impacts of different highway life cycle stages

The life cycle was divided into five stages that included materials production, transportation, construction, operations/maintenance work, and end-of-life. As shown in Fig. 2(b), the energy consumption

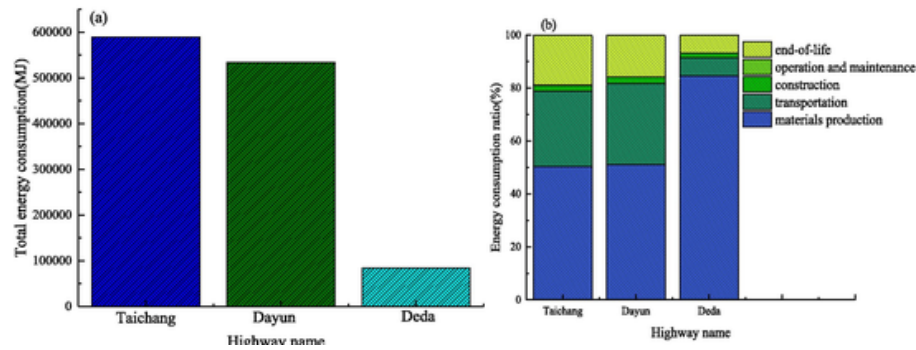


Fig. 2. Energy consumption (a) highway total energy consumption, (b) energy consumption at different life cycle stages

for materials production is the largest whilst the operation and maintenance stage has the smallest energy consumption values. Due to low energy consumption values, the numerical column for the operation and maintenance stage in Fig. 2(b) almost invisible.

From Fig. 2(b), it can also be observed that the combined energy consumption ratio for materials production and transportation stages was above 70 % of the whole life cycle of the highways. This illustrates that transportation and material production stages are the primary energy consumers during the life cycle of these three Shanxi highways. Compared with energy consumption of Inner Mongolia highways [28], the primary energy consumers stages are different during the life cycle. However, the energy consumption ratios for the different stages were different in the three highways. Compared to the energy consumption of the Deda highway with respect to materials production, the energy consumption values of other two highways (i.e., Dayun highway and Changda highway) were small. However, the energy consumption with respect to the construction stage seem to be similar for all the highways.

Overall, the results in Fig. 2(b) indicate that the energy consumption of cement concrete-based highways is significantly higher than that of asphalt mixtures-based highways in terms of materials production. Furthermore, it can also be concluded that materials production is the main energy consumption stage in the cement concrete-based highways, such as Deda, followed by transportation and end-of-life stages.

Likewise, materials production was similarly found to be the largest energy consumer in the asphalt-based highways (but numerically lower than the concrete-based highways) consecutively followed by the transportation and end-of-life stages. For all the three highways, Fig. 2(b) shows similar energy consumption for construction and negligible (i.e., less than 1.00 %) for the end-of-life stage. In comparison to asphalt-based highways, materials production and end-of-life stages were associated with the highest and least energy consumption, respectively, for concrete-based highways.

4.2. LCA environmental impacts evaluation

As discussed in the subsequent text, the environmental impacts evaluation included LCA for global warming, acidification potential, freshwater toxicity, and human toxicity.

4.2.1. Global warming potential (GWP) impacts

The factors responsible for global warming include truck, raw materials production, and paver emissions (CO_2) during the highway construction process. Minimizing CO_2 emissions is thus one of the key remedies to reduce global warming potential. The global warming potential (GWP) results are shown in Fig. 3(a).

As shown in Fig. 3(a), the global warming potential indicators of Taichang, Dayun, and Deda are 181 kg eq. CO_2 , 285 kg eq. CO_2 and 330 kg eq. CO_2 respectively during the materials production stage. It is apparent from this figure that material production is the biggest potential CO_2 emission stage in as far as global warming is concerned. In

terms of highway comparison, the global warming potential of Dayun highway was found to be the highest, whilst despite both being asphalt-based, Dayun exhibited greater global warming potential than Taichang highway. The probable reason for this is that the CO_2 emissions, as illustrated in Fig. 3(a), mainly arises from the raw materials production process, which, in the case of Deda highway has more carbon elements in the combined cement and asphaltic materials. By contrast, Taichang and Dayun highways are only associated with asphaltic raw materials.

Based on the materials balance perspective, there are various CO_2 emissions at the materials production stage. However, the three highways have a similar level and proportion of global warming potential at the each stage of the life cycle. The reason for this is that the total carbon source is the same for all the three highways.

Overall, it is apparent from Fig. 3(a) that concrete-based highways, such as Deda, are detrimentally associated with more global warming potential than asphalt-based highways. As theoretically expected, the materials production stage exhibited the greatest threat to global warming potential followed by the transportation stage. For all the three highways evaluated, operation and maintenance were the least detrimental stages to global warming seconded by construction and end-of-life stages for the asphalt-based and concrete-based highways, respectively.

4.2.2. Acidification potential (AP) impacts

As shown in Fig. 3(b), based on the life cycle impact assessment results, a hypothesis can be inferred that Dayun highway, at 50 % regenerated asphalt pavement and 3 cm of the wearing course, is the most environmentally friendly alternative among the three highways evaluated, with the lowest acidification potential (AP) values.

From Fig. 3(b), the total acidification potential values of Taichang highway, Deda highways and Dayun highway are 122.56 kg eq. SO_2 , 72.18 kg eq. SO_2 and 96.52 kg eq. SO_2 respectively. These results indicate that Taichang highway has the highest quantitative value of acidification potential indicator and is not an environmentally friendly highway. Based on the relatively low values of Deda highway, Fig. 3(b) also indicates that cement concrete pavements has more potential to reduce acidification than asphalt-based highway pavements.

Compared to the acidification values of the different life cycle stages, the AP values associated with the end-of-life stage are the largest in magnitude, followed by the materials production stage. This means that the end-of-life stage is detrimentally more impactful in terms of highway acidification and is seconded by the materials production stage. On the other hand, the operation and maintenance stage exhibited the least highway acidification potential with the smallest AP values.

4.2.3. Freshwater toxicity (FT) impacts

Water is an essential natural occurring resource, particularly in freshwater [29]. Regrettably, freshwater toxicity (FT) is on an increas-

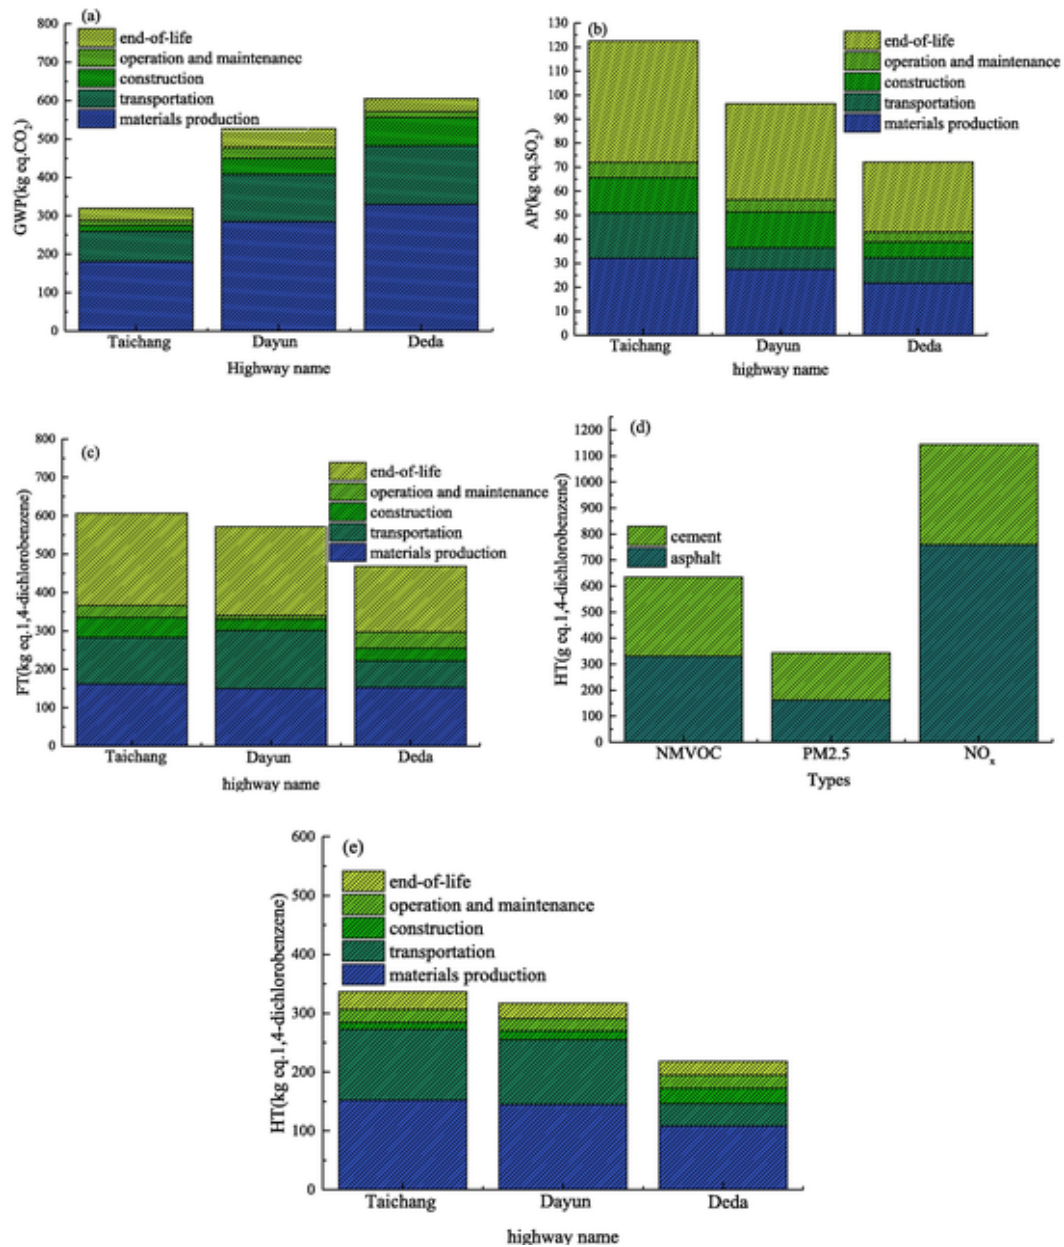


Fig. 3. Environmental pollution (a) highway global warming potential (GWP = Global Warming Potential), (b) highway acidification results (AP = Acidification Potential), (c) Highway freshwater toxicity (FT = Freshwater Toxicity), (d) human toxicity (HT) of materials, (e) human toxicity (HT) of highway components.

ing trajectory and is continuously impacted by the activities of modern civilization including environmental pollutants arising from highways. Under sunlight irradiation, FT converts to an unstable state that is undesirably detrimental to the human health [30]. As illustrated in Fig. 3 (c), Taichang highway has the largest overall freshwater toxicity (FT) values closely followed by Dayun highway, with the end-of-life stage being the most impactful stage for all the highways during their life cycle. This is probably because the highway was built using asphalt mixtures and asphalt mixtures contain heavy metals and lots of hydrocarbons that potentially contribute to polluting the water – and hence, high overall FT values. This also may partly explain why the overall FT values of Taichang and Dayun highways, both asphalt-based pavements, are close to each and not significantly different.

From Fig. 3(c), it can also be observed that end-of-life is the most impactful stage with the highest FT proportional contribution for all the three highways. This is because high-content FT materials are usually wasted, demolished, and/or recycled at the end-of-life stage – thus,

heavily contributing to freshwater pollution. On the other hand, Taichang highway and Dayun highways have almost similar overall FT values but different values for different stages of the life cycle. Although they are both comprised of asphalt-based highways, the slight differences in the pavement structure could be a contributing factor.

Whilst the total FT is relatively lower, the individual FT values for materials production stages and end-of-life stages of Deda highway (Fig. 3(c)) are comparable to those of asphalt-based highways, namely Taichang and Dayun. However, a significant difference exists for the construction stage with the asphalt-based highways being higher than the concrete-based Deda highway. Fig. 3(c) also shows relatively higher FT values for the construction, operation/maintenance, and end-of-life stages for the Taichang highway than Dayun highway and vice versa for the transportation stage. By contrast, the FT impact of materials products appeared to be similar in all the three highways evaluated. Overall, these FT results indicate that the materials production and end-of-life

stages were the dominant sources of freshwater pollution and toxicity, followed by the transportation stage.

4.2.4. Human toxicity (HT) impacts

In this study, the human toxicity (HT) impacts were evaluated using the 1,4-dichlorobenzene equivalent method. 1,4-dichlorobenzene equivalent method used the NO_x , NMVOC, and $\text{PM}_{2.5}$ contents to evaluate the HT impacts. The bigger the NO_x , NMVOC, and $\text{PM}_{2.5}$ contents, the bigger the HT impacts. As shown in Fig. 3(d), the content of NO_x is the highest in magnitude and therefore, most impactful with respect to HT. By contrast, the contents of NMVOC and $\text{PM}_{2.5}$ are comparatively small and therefore, hardly impactful with respect to HT. As shown in Fig. 3(e), the different highways have the different characteristics of HT impacts. Compared to Deda, Dayun and Taichang highways have the comparatively higher HT impacts. The reason for this may be that there are the emissions of VOC and NO_x in the asphalt mixtures-based highways. This is because there is a production of VOC and NO_x when the asphalt is heated above 100 °C. Overall, these results (Fig. 3(d-e)) indicates that compared to cement concrete-based highways, asphalt-based highways have comparatively greater HT impacts. The results (i.e., Fig. 3(d)) further demonstrate that asphalt is more detrimental to the human healthy than cement.

To reduce HT impacts, a recommendation can be made that the government gives more consideration to building the eco-friendly cement concrete-based highways. As shown in Fig. 3(e), the different stages of HT impacts in life cycle shows that the materials production and transportation stages are more impactful and severe than the other stages. Their combined impact proportion is over 85 %. There is a need to be cautious with the materials production and transportation stages during the highway construction process, especially for asphalt-based highways.

Fig. 3(d-e) indicates that there are some HT impacts in the operation and maintenance stage. These emissions mainly happens at the maintenance stage because this stage is associated with regenerating and heating the asphalt. The maintenance stage emits HT gas such as NMVOC and NO_x . The HT at the end-of-life stage is largely associated with the demolishing activities, pavement material removal, truck exhaust emissions, dismantling equipment, etc.

5. Conclusions

In this study, the life cycle assessment (LCA) of three representatives in Shanxi Province, namely Taichang, Dayun, and Deda, was comparatively evaluated. Based on the study results and findings, the following conclusions and recommendations were made:

- Deda highway had the smallest energy consumption indices, with its cement concrete pavement technology rating as a kind of low-energy consumption' pavement technology. The transportation stage and materials production and transportation stages were found to be the primary energy consumers during the life cycle of the highway. The combined energy consumption ratio for these two life cycle stages was over 70 %.
- The global warming potential indicator (Taichang = 181 kg eq. CO_2 , Dayun = 285 kg eq. CO_2 and Deda = 330 kg eq. CO_2) had the largest CO_2 emission during the materials production stage. On the other hand, Taichang highway exhibited the greatest potential (AP = 122.56 kg eq. SO_2) for the acidification which suggested that Taichang is not an environmentally friendly highway. Further, the study findings indicated that cement concrete pavement had potential to reduce the acidification potential impact.
- Freshwater toxicity during the materials production stage and end-of-life stages were dominated on Deda highway and Taichang highways, whilst different levels of freshwater toxicity existed on

Dayun highway. Compared to the cement concrete-based highway, asphalt based highways exhibited comparatively higher human toxicity impacts. The materials production and construction stages were found to play a significant role in the human toxicity impacts during the life cycle of highways, with combined HT ratio exceeding 85 %.

- Search for replaced or regenerate materials of petroleum-based asphalt;
- Generalize the new energy-saving paving technology.

CRedit authorship contribution statement

Xinxing Zhou: Writing – original draft, Investigation, Formal analysis. **Xiaorui Zhang:** Writing – review & editing. **Yuan Zhang:** Writing – review & editing. **Sanjeev Adhikari:** Writing – review & editing.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgments

This work was supported by the National Natural Science Foundation of China (No.52008235), and Special Foundation of Achievements Transformation Guide of Department of Science and Technology of Shanxi Province (No.201804D131034), and Science and Technology Project of Shanxi Transportation Holdings Group CO., LTD (No.19-JKKJ-55 and 20-JKKJ-43).

References

- [1] T. Gupta, M. Mishra, F. Patò, A lifecycle scenario analysis of different pavement technologies for urban roads, *Sd. Tot. Environ.* 673 (2019) 545–559, <https://doi.org/10.1016/j.scitotenv.2019.04.046>.
- [2] B. Karabulut, G. Feroz, B. Rossi, Lifecycle cost assessment of high strength carbon and stainless steel girder bridges, *J. Environ. Manage.* 277 (2021) 111460, <https://doi.org/10.1016/j.jenvman.2020.111460>.
- [3] J. Vázquez-Hernández, C. García-Mazón, J. Fere González, D. Vivas, Environmental rebound effect of energy efficiency improvements in Colombian households, *Energy Policy* 145 (2020) 111607, <https://doi.org/10.1016/j.enpol.2020.111607>.
- [4] J. Heikkinen, K. Aho, A. Sen, A. Bado, W. M. Zefi, Assessing public acceptance of the lifecycle of CO₂ based fuels: Desirability in the market, *Energy Policy* 145 (2020) 111606, <https://doi.org/10.1016/j.enpol.2020.111606>.
- [5] H. Wang, C. Talaka, X. Chen, S. Muel, Lifecycle assessment of airport pavement design alternatives for energy and environmental impacts, *J. Clean. Prod.* 133 (2016) 163–171, <https://doi.org/10.1016/j.jclepro.2016.05.091>.
- [6] E. Sánchez-Cabe, L. Fuentes, G. Martínez-Aguiles, H. Quintana, J. Santos, A. Plam, P. Sainza, F. Giusi, Recycling waste plastics in roads: A lifecycle assessment study using primary data, *Sd. Tot. Environ.* 746 (2020) 14842, <https://doi.org/10.1016/j.scitotenv.2020.14842>.
- [7] Y. Wang, S. Tavakoli, V. Klam, Lifecycle impact and benefit trade-offs of a food production and land use change scenario, *Environ. Sci. Technol.* 52 (2018) 1395–1405, <https://doi.org/10.1021/acs.est.8b0377>.
- [8] Z. Leng, L. Al-Qadi, R. Cao, Lifecycle economic and environmental assessment of warm mix emulsified asphalt, *Transportation A: Transport, Science* 14 (7) (2019) 562–575, <https://doi.org/10.1080/23249935.2019.1630707>.
- [9] S. Besi, J. Santos, M. Gupta, L. Pires, D. Pesti, A comparative lifecycle assessment of asphalt mixtures for railway sub-balls containing alternative materials, *Resour. Conserv. Recycl.* 137 (2019) 7688, <https://doi.org/10.1016/j.resconrec.2019.05.028>.
- [10] H. Azari, A. Yahi, B. Amor, Removing shadows from consequential LCA through independent modeling approach, *Environ. Sci. Technol.* 53 (3) (2019) 1871–1877, <https://doi.org/10.1021/acs.est.8b02850>.
- [11] Y. Liu, Y. Wang, D. Li, Q. Yu, Lifecycle assessment for carbon dioxide emissions from heavy construction in mountainous area: Primary source cut-off determination of system boundary, *Resour. Conserv. Recycl.* 140 (2019) 3644, <https://doi.org/10.1016/j.resconrec.2019.09.009>.
- [12] P. Hou, O. Jolani, J. Zhi, M. Xu, Estimating toxicity characterization factors for chemicals in lifecycle assessment using machine learning models, *Environ. Int.*

- 15 (2020) 15393 <https://doi.org/10.1016/j.jenvint.2019.105393>
- [13] L. Wubia T. Scullion Thin HMA overlay in Texas: Mix design and laboratory material property characterization (No. FHWA/TX-0805981) Texas A&M Transportation Institute (TTI), College Station, TX USA. <http://tti.tamu.edu/documents/055981.pdf>
- [14] H. Wang, I. Al-Said, P. Lu, A. Jain, Quantifying greenhouse gas emission of asphalt pavement preservation construction and use stages using lifecycle assessment, *International Journal of Sustainable Transportation* 14(1) (2020) 2534 <https://doi.org/10.1080/15633820.2015.1086>
- [15] X. Zhou, T. Moghaddam, M. Chen, S. Wu, S. Adhikari, S. Xu, C. Yang, Lifecycle assessment of binder modified by asphalt derived from biomass, *ACS Sustainable Chem Eng.* 8 (2020) 1468–1475, <https://doi.org/10.1021/acscschemeng.0c0355>
- [16] Y. Badi, S. Segen, Review of energy storage systems for vehicles based on technology, environmental impacts, and costs, *Renew. Sustan. Energy Rev.* 135 (2021) 11085 <https://doi.org/10.1016/j.rser.2021.11085>
- [17] K. Zulu, R. Singh, F. Shah, Environmental and economic analysis of selected pavement preservation treatments, *Civil, Engineering Journal* 6 (2020) 210–224, <https://doi.org/10.2891/cj-2020-039465>
- [18] A. Al-Hassan, R. Baanmakishuan, M. Alarawneh, Eco-friendly asphalt approach for the development of sustainable road, *Journal of Human, Earth and Future* 1 (2020) 97–111, <https://doi.org/10.2891/hief-2020-10301>
- [19] A. Raji, A. Abayaj, The suitability of baken method for design of road asphalt concrete mixture, *Civil, Engineering Journal* 7 (2021) 827–839, <https://doi.org/10.2891/cj-2021-039493>
- [20] ISO, 2021 ISO 14040:2006 Environmental management. Lifecycle assessment—Principles and framework. <https://www.iso.org/standard/37435.html>, January, 2021
- [21] E. Bage, E. Benon, Comparative lifecycle assessment of biomass utilization for electricity generation in the European Union and the United States, *Energy Policy* 128 (2019) 26–27, <https://doi.org/10.1016/j.enpol.2019.01.006>
- [22] D. Land, M. Maori, E. Baci, M. Genari, Comparative lifecycle assessment of standard cellular reinforced and end of life tires fiber-reinforced hot mix asphalt mixtures, *J. Clean Prod.* 248 (2020) 119295 <https://doi.org/10.1016/j.jclepro.2020.119295>
- [23] China's Life Cycle Database (LCDB) Sichuan University, China, 2021 <https://github.com/ThirdPartyDatabases/CICD>
- [24] GreenDelta, 2020 openLCA 1103, open source software, <http://greenDelta.com>
- [25] H. Mkućić, J. Bada, J. J. Kereš, Sustainability through combined development of energy water and environment systems, *J. Clean Prod.* 251 (2020) 119277 <https://doi.org/10.1016/j.jclepro.2020.119277>
- [26] V. Farzita, S. Long, G. Sdzio, M. Celina, C. Cezano, Primary data collection and environmental energy audit of food market production, *Energies* 13(8) (2020) 2045 <https://doi.org/10.3390/en13082045>
- [27] J. Yangli, Effect of professional supervision on durability of building, *Science and Engineering Ethics* 24 (2018) 331–332, <https://doi.org/10.1007/s11980-017-98719>
- [28] F. Wang, J. Xie, S. Wu, J. Li, D. M. Barberi, L. Zhang, Lifecycle energy consumption by road and associated interpretative analysis of sustainable practices, *Renew. Sustan. Energy Rev.* 14 (2021) 110823 <https://doi.org/10.1016/j.rser.2021.110823>
- [29] B. Z. Roussq, E. Berbre, R. Sevat, D. P. Hanlon, A systematic literature review of forecasting and predictive models for cyanobacteria blooms in freshwater lakes, *Water Res.* 182 (2020) 115959 <https://doi.org/10.1016/j.watres.2020.115959>
- [30] J. Zhao, F. Ning, X. Cao, H. Yao, Z. Wang, B. Xing, Phototransformation of graphene oxide in the presence of coexisting metal ions regulated its toxicity to freshwater algae, *Water Res.* 176 (2020) 115735 <https://doi.org/10.1016/j.watres.2020.115735>

