

Rare-earth chalcogenide perovskites: A promising class of materials for optoelectronic applications

Surajit Adhikari^{1,*} and Priya Johari^{1,†}

¹*Department of Physics, School of Natural Sciences,
Shiv Nadar Institution of Eminence, Greater Noida,
Gautam Buddha Nagar, Uttar Pradesh 201314, India*

Chalcogenide perovskites have attracted significant attention for optoelectronic applications due to their nontoxic composition, robust phase stability, and excellent optoelectronic properties. Among them, rare-earth chalcogenide perovskites have recently emerged as promising candidates for next-generation devices. However, their excitonic and polaronic properties remain largely unexplored due to the high computational cost of accurate theoretical treatments. In this work, we present a comprehensive first-principles investigation of excitonic dynamics and polaronic effects in a series of III-III rare-earth chalcogenide perovskites ABX_3 ($A = Y, La$; $B = Sc, Y$; $X = S, Se$), along with their structural stability and optoelectronic properties, using state-of-the-art density functional theory in conjunction with many-body perturbation theory within the G_0W_0 and Bethe-Salpeter equation (BSE) frameworks. All investigated compounds satisfy the dynamical and mechanical stability criteria, although several are thermodynamically metastable at 0 K and may require kinetic stabilization and/or finite-temperature effects for experimental realization. They exhibit quasi-particle band gaps in the range of 2.75–4.47 eV, and the BSE calculations reveal strong optical absorption spanning the visible to ultraviolet regions. The computed excitonic properties indicate intermediate-to-large exciton binding energies (0.148–0.517 eV), moderately localized excitons, and strong electron-hole wavefunction overlap, indicative of favorable radiative recombination characteristics and enhanced light-matter interaction. Furthermore, analysis based on the Fröhlich model demonstrates intermediate-to-strong carrier-phonon coupling, with electron-phonon interactions generally stronger than hole-phonon interactions. Notably, charge-separated polaronic states are energetically less favorable than bound excitonic states in most compounds, with the exception of $La(Sc, Y)Se_3$, while hole polarons exhibit significantly higher mobilities (up to $\sim 40 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$) compared to electron polarons. Overall, rare-earth chalcogenide perovskites ABX_3 exhibit a compelling combination of structural stability, tunable optoelectronic properties, pronounced excitonic effects, and favorable polaronic transport, positioning them as promising lead-free materials for next-generation optoelectronic devices, including light-emitting devices and photodetectors.

I. INTRODUCTION:

Over the last decade, inorganic-organic halide perovskites (IOHPs) have attracted extraordinary interest owing to their outstanding electronic and optical characteristics [1–4]. This intense research focus has led to remarkable progress in perovskite solar cells, with the power conversion efficiency (PCE) rising rapidly from an initial value of 3.8% to a record 27% [1, 5]. However, despite these impressive achievements, significant challenges remain. Most high-performance IOHPs are lead (Pb)-based, giving rise to serious toxicity concerns. Moreover, their practical applicability is hindered by poor long-term stability, including degradation and thermal and chemical instability associated with the organic constituents [6, 7]. These limitations have motivated extensive efforts toward the development of environmentally benign, stable perovskite alternatives, opening new pathways for next-generation optoelectronic materials.

Recently, chalcogenide perovskites have emerged as a novel class of functional materials. Owing to their high

structural stability, suitable band gaps, and excellent optoelectronic properties, several members of this family have been identified as promising candidates for light-absorbing and light-emitting applications [8–12]. Among them, the II-IV chalcogenide perovskites with the general formula ABX_3 (where $A = Ca, Sr, Ba$; $B = Ti, Zr, Sn, Hf$; and $X = S, Se$) are the most extensively studied to date [10, 11, 13–17]. Further diversification of this materials family can be achieved by exploring alternative elemental combinations at the cationic sites. In this context, the III-III chalcogenide perovskites, although already synthesized, remain largely unexplored as functional materials [18–21]. For optoelectronic applications, access to a broader materials palette is highly advantageous, as it enables precise tuning of critical parameters such as band gaps, band alignments, and structural properties, including lattice constants required for epitaxial growth. Consequently, the exploration of III-III chalcogenide perovskites composed of environmentally benign, non-toxic elements is highly desirable, as these materials can effectively complement the existing family of II-IV chalcogenide perovskites.

Recent studies on III-III chalcogenide perovskites have unveiled promising opportunities for the design of stable and environmentally benign optoelectronic materials. For instance, Zhang *et al.* theoretically predicted

* sa731@snu.edu.in

† priya.johari@snu.edu.in

the orthorhombic $Pnma$ (No. 62) crystal structure of $YScS_3$, reporting an indirect G_0W_0 band gap of 3.16 eV [22]. Subsequently, through density functional theory calculations, Zhang *et al.* not only predicted but also experimentally synthesized a light-emitting III-III- S_3 perovskite, $LaScS_3$, exhibiting a direct band gap of 2.62 eV [18]. Furthermore, they also reported the prediction and experimental realization of the direct band gap material $LaScSe_3$, with a G_0W_0 band gap of 2.96 eV [19]. In addition, the $P2_1/m$ crystal structure of the $LaYS_3$ perovskite has been both theoretically predicted and experimentally synthesized, exhibiting an optimal band gap of 2.0 eV, making it a promising wide band gap photoabsorber for tandem solar energy conversion devices [20, 21].

Most of the aforementioned studies have primarily focused on the electronic and optical properties of III-III rare-earth chalcogenide perovskites. In contrast, their excitonic and polaronic properties remain largely unexplored, despite their critical role in determining the performance of optoelectronic devices. Excitonic effects govern fundamental processes such as light absorption, emission, and charge separation. In contrast, polaron formation, arising from carrier-phonon interactions, strongly influences charge transport and carrier mobility [15–17]. A quantitative description of these properties, however, is computationally demanding and has therefore received limited attention. This gap highlights the need for a comprehensive investigation of excitonic and polaronic effects in these compounds, which has not yet been achieved and is addressed in the present work.

In this work, we undertake a systematic and comprehensive investigation of the structural stability, as well as the electronic, optical, excitonic, and polaronic properties of III-III rare-earth chalcogenide perovskites ABX_3 ($A = Y, La$; $B = Sc, Y$; $X = S, Se$) in the orthorhombic $Pnma$ phase, a widely observed and energetically competitive distorted perovskite structure that provides a consistent framework for comparative analysis. Our study is based on first-principles calculations within the frameworks of density functional theory (DFT) [23, 24], density functional perturbation theory (DFPT) [25], and many-body perturbation theory (MBPT) [26, 27]. Initially, the crystal structures are optimized using the semilocal PBE [28] as well as PBEsol [29] exchange-correlation (xc) functionals, and all compounds are found to be both dynamically and mechanically stable. However, several are thermodynamically metastable at 0 K, suggesting that their experimental realization may require kinetic stabilization and/or finite-temperature effects. Subsequently, the electronic properties are investigated using both the HSE06 hybrid xc functional [30] and the G_0W_0 @PBE approach [31, 32], revealing quasiparticle band gaps in the range of 2.75–4.47 eV. Following that, the optical response is computed by solving the Bethe-Salpeter equation (BSE) [33, 34] on top of G_0W_0 @PBE, enabling the evaluation of the dielectric function and exciton binding energies. The results

indicate that these perovskites exhibit intermediate-to-high exciton binding energies, moderately localized excitons, and strong electron-hole wavefunction overlap, suggesting favorable radiative transitions and pronounced light-matter interaction. Finally, we investigate the effects of carrier-phonon coupling and estimate the polaron mobility using the Fröhlich model [35] and the Hellwarth polaron model [36]. The analysis reveals intermediate to strong carrier-phonon coupling, with electron-phonon interactions being more pronounced than those of holes, resulting in lower electron mobility and comparatively higher hole mobility. Overall, this work provides a comprehensive understanding of rare-earth ABX_3 ($A = Y, La$; $B = Sc, Y$; $X = S, Se$) chalcogenide perovskite compounds, highlighting their potential as lead-free perovskites with promising optoelectronic properties for next-generation devices.

II. COMPUTATIONAL DETAILS:

In this work, first-principles calculations were carried out within the framework of density functional theory (DFT) [23, 24], density functional perturbation theory (DFPT) [25], and many-body perturbation theory (MBPT) [26, 27], as implemented in the Vienna ab initio Simulation Package (VASP) [37, 38]. The interaction between valence electrons and ionic cores was described using projector augmented-wave (PAW) pseudopotentials [39]. Structural optimizations were carried out within the generalized gradient approximation (GGA) using the Perdew-Burke-Ernzerhof (PBE) [28] and the PBEsol [29] exchange-correlation (xc) functionals. The inclusion of PBEsol is motivated by its improved accuracy in describing equilibrium properties of solids, particularly lattice constants and structural distortions, which are crucial for reliably assessing dynamical stability and phonon properties. A plane-wave cutoff energy of 400 eV was employed, and the electronic self-consistent field convergence criterion was set to 10^{-6} eV. All structures were fully optimized until the Hellmann-Feynman forces on each atom were less than 0.01 eV/Å. Brillouin zone integrations were carried out using a Γ -centered $7 \times 7 \times 5$ k-point mesh. The optimized crystal structures were visualized using the VESTA package [40]. Phonon dispersion curves were calculated using DFPT as implemented in the PHONOPY package [41], employing $2 \times 2 \times 2$ supercells. To assess the functional dependence of the dynamical stability, the phonon spectra were computed for crystal structures relaxed using both the PBE and PBEsol exchange-correlation functionals.

Electronic band structures were initially obtained using the PBE xc functional including spin-orbit coupling (SOC), which was found to have a negligible impact on the overall band dispersion. To achieve improved accuracy in bandgap estimation, hybrid xc functional calculations using HSE06 [30] and quasiparticle corrections within the G_0W_0 @PBE [31, 32] approach were per-

formed. A Γ -centered $3 \times 3 \times 2$ k-point mesh was employed for the G_0W_0 calculations. This choice is justified by the demonstrated convergence of the quasiparticle band gaps, while the use of denser k-point meshes for the present 20-atom unit cells would incur a substantially higher computational cost and is therefore beyond the scope of the present work (for details, see Sec. X of the SM [42]). The convergence of the quasiparticle bandgap with respect to the number of unoccupied bands (NBANDS), the plane-wave cutoff energy (ENCUT), and the response-function cutoff energy (ENCUTGW) was carefully examined (for details, see Sec. X of the SM [42]). Based on these convergence tests, 640 bands, a plane-wave cutoff energy of 400 eV, and a response-function cutoff energy of 300 eV were adopted, yielding quasiparticle bandgaps converged to within 0.05 eV. Carrier effective masses were calculated using the SUMO code [43] via parabolic fitting near the band extrema. Optical properties were further refined by solving the Bethe-Salpeter equation (BSE) [33, 34] on top of G_0W_0 @PBE, explicitly including electron-hole interactions. The BSE kernel was constructed using 24 occupied and 24 unoccupied bands, based on convergence tests (for details, see Sec. XI of the SM [42]). Elastic and optical properties were post-processed using the VASPKIT package [44], and the ionic contribution to the dielectric constant was obtained from DFPT calculations.

III. RESULTS AND DISCUSSIONS:

In the present study, we conduct a comprehensive investigation of the optoelectronic properties of III-III rare-earth chalcogenide perovskites ABX_3 ($A = Y, La$; $B = Sc, Y$; $X = S, Se$). The following sections provide an in-depth analysis of their structural stability, electronic structure, and transport characteristics, along with their optical response, excitonic behavior, and polaronic effects. These results aim to establish a fundamental understanding of these materials and offer valuable insights to guide future experimental studies.


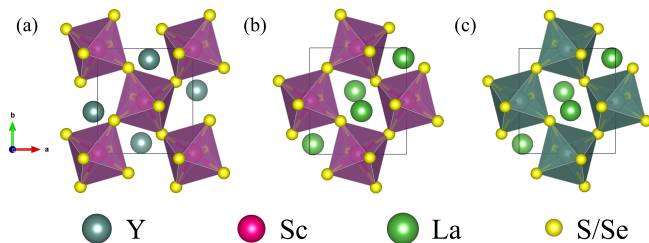


FIG. 1. Crystal structures of rare-earth chalcogenide perovskites (a) $YScX_3$, (b) $LaScX_3$, and (c) $LaYX_3$, respectively, where $X = S, Se$.

A. Structural Properties:

Figure 1 illustrates the orthorhombic crystal structures of rare-earth chalcogenide perovskites ABX_3 ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$), crystallizing in the $Pnma$ space group (No. 62). Owing to the +3 valency of both A- and B-site cations, these materials are categorized as III-III chalcogenide perovskites. The unit cell contains four formula units (20 atoms), comprising 4 A-site cations (Y or La), 4 B-site cations (Sc or Y), and 12 chalcogen anion atoms (S or Se). In this structure, the A-site cations exhibit 12-fold coordination, forming cuboctahedral environments with the surrounding chalcogen atoms. In contrast, the B-site cations are 6-fold coordinated, giving rise to corner-sharing distorted $[BX_6]^{9-}$ octahedra. These octahedra are both tilted and distorted, leading to the characteristic orthorhombic symmetry of the $Pnma$ phase [12]. In this study, we report for the first time the $Pnma$ phase of $YScSe_3$, $LaYS_3$, and $LaYSe_3$ compounds. The lattice parameters of the optimized structures are calculated using both PBE and PBEsol xc functionals and are summarized in Table I. It is found that the lattice parameters of $LaScSe_3$ are in good agreement with the available experimental results ($a = 6.77 \text{ \AA}$, $b = 7.53 \text{ \AA}$, and $c = 10.00 \text{ \AA}$ [19]). Moreover, the PBE functional slightly overestimates the lattice parameters, while PBEsol slightly underestimates them, with both deviations being of comparable magnitude. This indicates that both functionals yield similar accuracy, despite exhibiting opposite systematic deviations. In addition, the octahedral distortion parameters, including the average bond length, polyhedral volume, bond angle variance, and bond-length distortion index, for the BX_6 octahedra in these chalcogenide perovskites are computed using both functionals and presented in Table S1 (for details, see Sec. I of the SM [42]).

To assess the thermodynamic stability against decomposition, we calculated the decomposition enthalpy according to



for these III-III- X_3 compounds that pass the phase stability criteria (for details, see Sec. II of the SM [42]). The decomposition enthalpy (ΔH_D) of these compounds is evaluated using both PBE and PBEsol xc functionals and is tabulated in Table I. The $LaScX_3$ ($X = S, Se$) compounds exhibit positive ΔH_D values with both functionals, indicating thermodynamic stability with respect to the considered decomposition pathway. In contrast, the remaining compounds exhibit negative ΔH_D values, indicating thermodynamic metastability at 0 K with respect to this decomposition pathway. The only exception is $YScS_3$, which yields a positive ΔH_D when using the PBEsol functional. Nevertheless, decomposition enthalpy based on a single reaction does not constitute a complete thermodynamic stability criterion, since alternative competing phases and decomposition pathways

TABLE I. Calculated lattice parameters and decomposition energies (ΔH_D) of ABX_3 ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$) rare-earth chalcogenide perovskites using the PBE and PBEsol xc functional, respectively (PBEsol values in bold).

Configurations	Lattice parameters ($\text{\AA}$)			ΔH_D (meV/atom)
	a	b	c	
YScS ₃	6.39 (6.27)	7.02 (6.97)	9.55 (9.37)	-9.1 (5.0)
YScSe ₃	6.67 (6.54)	7.35 (7.29)	10.00 (9.79)	-28.9 (-6.8)
LaScS ₃	6.59 (6.46)	7.21 (7.16)	9.65 (9.51)	26.0 (26.1)
LaScSe ₃	6.83 (6.68)	7.58 (7.51)	10.08 (9.92)	13.5 (8.8)
LaYS ₃	6.81 (6.70)	7.42 (7.37)	10.06 (9.88)	-2.7 (-19.9)
LaYSe ₃	7.04 (6.90)	7.78 (7.72)	10.48 (10.26)	-15.2 (-25)

may exist. A rigorous assessment therefore requires construction of the convex-hull phase diagram, which compares the energy of a compound against all known competing phases within the corresponding chemical space. Compounds lying on the convex hull are thermodynamically stable, whereas those with positive energy above the hull (E_{hull}) are metastable with respect to decomposition into a combination of lower-energy phases.

To directly address this limitation, we constructed the convex-hull phase diagrams for each A – B – X ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$) chemical space by incorporating all relevant competing binary and ternary phases at the same DFT level. The calculated E_{hull} values are summarized in Table S3, while the corresponding convex-hull diagrams are presented in Figure S1 (for details, see Sec. III of the SM [42]). The results show that $LaScX_3$ ($X = S, Se$) lie on the convex hull with $E_{\text{hull}} = 0$, confirming their thermodynamic stability at 0 K. The remaining compounds possess finite positive E_{hull} values (0.009–0.029 eV), indicating metastability with respect to competing equilibrium phases. It is important to note, however, that a positive energy above the hull does not necessarily preclude experimental realization. Numerous experimentally synthesized materials are known to exist as metastable phases because finite-temperature vibrational and configurational entropy, kinetic barriers, and non-equilibrium synthesis routes can effectively stabilize compounds that are slightly above the convex hull [45]. Consequently, the above-hull compounds identified here should be regarded as metastable candidates that may still be experimentally accessible under suitable synthesis conditions rather than as equilibrium-stable phases. However, thermodynamic stability alone is insufficient to ensure stability of these materials; therefore, dynamical and mechanical stability are also examined.

The dynamical stability of the investigated perovskites serves as a crucial indicator of their structural integrity and suitability for functional applications. It is evaluated through phonon dispersion relations, which describe the vibrational behavior of atoms in the crystal lattice. For a dynamically stable system at 0 K, all phonon frequencies are required to be real and positive across the entire Brillouin zone; the occurrence of imaginary (negative) frequencies signifies possible structural instabilities. To assess this, self-consistent phonon calculations are performed within the DFPT framework using the structures

relaxed with both PBE and PBEsol xc functionals. The computed phonon dispersion curves of ABX_3 ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$), obtained using structures relaxed with the PBE and PBEsol xc functionals, are presented in Figs. S2 and 2, respectively. Within the PBE functional, YScS₃, LaScS₃, LaYS₃, and LaYSe₃ are dynamically stable at 0 K, as confirmed by the absence of imaginary phonon modes, whereas (Y, La)ScSe₃ shows dynamical instabilities, as indicated by the presence of imaginary modes. Specifically, YScSe₃ shows a maximum imaginary frequency of -0.333 THz at the Γ point, while LaScSe₃ exhibits imaginary frequencies of approximately -0.189 THz along the Γ – X direction and -0.349 THz at the U point. The relatively small magnitudes of these imaginary frequencies suggest the presence of soft lattice instabilities rather than pronounced structural instabilities. This interpretation is further supported by the experimental realization of LaScSe₃, indicating that these weak instabilities are unlikely to preclude its synthesis and may instead reflect the sensitivity of the lattice dynamics to the equilibrium structural parameters [19]. In contrast, phonon calculations based on the PBEsol-relaxed structures show no imaginary phonon modes throughout the Brillouin zone for any of the investigated compounds, indicating dynamical stability within the PBEsol framework. Together with the PBE results, these findings suggest that the lattice dynamics of some compounds are sensitive to small variations in the equilibrium lattice parameters and are therefore dependent on the choice of exchange-correlation functional.

Beyond the thermodynamic and dynamical stability discussed above, the mechanical stability and corresponding elastic properties of ABX_3 ($A = Y, La$; $B = Sc, Y$; $X = S, Se$) chalcogenide perovskites are further examined. It is well known that the suitability of a material for practical device applications is strongly influenced by its elastic behavior. The second-order elastic constants (C_{ij}) are calculated using the energy-strain method [46], from which the relevant elastic properties are derived (for details, see Sec. V of the SM [42]). Owing to the orthorhombic symmetry of all considered compounds, nine independent elastic constants (C_{11} , C_{22} , C_{33} , C_{44} , C_{55} , C_{66} , C_{12} , C_{13} , and C_{23}) are sufficient to describe their mechanical stability and elastic behavior. The calculated C_{ij} values, listed in Table S4, satisfy the Born stability criteria [46], thereby confirming the excellent mechanical

stability of these orthorhombic chalcogenide perovskites.

Further, the bulk modulus (B), shear modulus (G), Young's modulus (Y), and Poisson's ratio (ν) are evaluated within the Voigt-Reuss-Hill approximation [47, 48] and are summarized in Table S4. The relatively larger values of B compared to G indicate that the investigated chalcogenide perovskites exhibit greater resistance to volume change than to shear deformation. The comparatively lower values of G and Y further suggest that these materials possess a certain degree of mechanical flexibility. To assess the ductile or brittle nature of these systems, we employ Pugh's criterion based on the B/G ratio [49], along with Poisson's ratio (ν). The obtained values of $B/G > 1.75$ and $\nu > 0.26$ consistently indicate that all the compounds exhibit ductile behavior. These characteristics suggest that the investigated materials are mechanically robust yet sufficiently flexible for potential device applications.

Overall, the synthesizability of these III-III chalcogenide perovskites is established by the combined assessment of thermodynamic, dynamical, and mechanical stability. Notably, LaScX_3 ($X = \text{S}, \text{Se}$), which has already been experimentally synthesized [18, 19], is found to be thermodynamically stable, consistent with its positive decomposition enthalpy. In contrast, the remaining compounds are metastable with respect to decomposition. Nevertheless, the absence of imaginary phonon modes (within PBEsol) and the satisfaction of mechanical stability criteria confirm their dynamical and mechanical stability. These results suggest that, despite thermodynamic metastability, the compounds are likely experimentally accessible through kinetic stabilization or finite-temperature effects, with LaScX_3 serving as a benchmark system validating the reliability of the present approach.

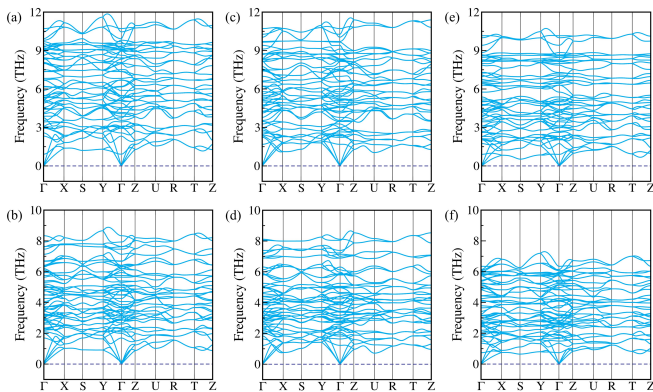


FIG. 2. Phonon dispersion curves of the rare-earth chalcogenide perovskites (a) YScS_3 , (b) YScSe_3 , (c) LaScS_3 , (d) LaScSe_3 , (e) LaYS_3 , and (f) LaYSe_3 , computed using the DFPT method based on PBEsol-relaxed structures.

B. Electronic properties:

Following the assessment of structural stability, the electronic properties, such as the band structure and par-

tial density of states (PDOS) of rare-earth chalcogenide perovskites ABX_3 ($A = \text{Y}, \text{La}$; $B = \text{Sc}, \text{Y}$; and $X = \text{S}, \text{Se}$) are evaluated to gain fundamental insight into their suitability for optoelectronic applications. At first, the electronic band structures of these chalcogenide perovskites are calculated using the semilocal GGA-PBE xc functional, both with and without inclusion of spin-orbit coupling (SOC). The GGA-PBE xc functional is found to underestimate the band gaps due to the self-interaction error of electrons (see Table II). Furthermore, SOC has a negligible effect on the band gap (see Table S5 of the SM [42]), as expected for chalcogenide perovskites [15–17].

Subsequently, the band gaps are computed more accurately using the hybrid HSE06 xc functional and the many-body perturbation theory (MBPT)-based GW approach, specifically at the G_0W_0 @PBE level. Figure 3 presents the band structures of these compounds, calculated using the hybrid HSE06 functional. Our calculated electronic band structures explicitly demonstrate that YScX_3 ($X = \text{S}, \text{Se}$) are indirect band gap materials. In these compounds, the valence band maximum (VBM) is located at the Γ -point, whereas the conduction band minimum (CBM) occurs at the S-point in the Brillouin zone [see Fig. 3(a)-(b)]. This spatial separation of the band extrema confirms the indirect nature of the fundamental band gap, implying that optical transitions near the band edge are phonon-assisted. In contrast, all other compounds investigated in this study exhibit direct band gaps. For these systems, both the VBM and CBM are located at the same high-symmetry k-point, specifically at the Γ -point [see Fig. 3(c)-(f)]. As a result, the fundamental electronic transition is momentum-conserving, leading to a stronger optical absorption onset compared to the indirect-gap counterparts.

The band gaps of these compounds, as calculated using the HSE06 functional and the G_0W_0 @PBE approach, are summarized in Table II. The HSE06 band gaps of these chalcogenide perovskites are found to lie in the range of 2.17–3.45 eV, whereas the G_0W_0 @PBE band gaps are systematically larger, spanning 2.75–4.47 eV. This trend reflects the well-known tendency of many-body perturbation theory within the GW approximation to yield improved quasiparticle energies by explicitly accounting for electron-electron interactions, thereby correcting the band gap underestimation inherent to standard and hybrid density functional approaches. Importantly, the G_0W_0 @PBE results obtained in this work are in good agreement with previously reported theoretical studies [19, 22], confirming the reliability of the present computational framework. The absence of exact quantitative agreement with previous reports can be attributed to the sensitivity of G_0W_0 calculations to the choice of starting functional, convergence parameters, and structural inputs. For the benchmark compound LaScS_3 , the experimentally measured band gap (2.62 eV) is closer to the HSE06 value (2.80 eV) than to the G_0W_0 @PBE value (3.72 eV) [18]. This discrepancy is likely attributable to the inherent starting-point dependence of the single-shot

G_0W_0 approximation, the absence of self-consistency in the GW calculations, residual convergence limitations, and the neglect of finite-temperature and excitonic effects. Although G_0W_0 calculations based on an HSE06 starting point or self-consistent GW schemes could further reduce the starting-point dependence and improve the quantitative accuracy of the quasiparticle energies, such calculations are computationally prohibitive for the large unit cells considered here. Nevertheless, the good agreement with previous theoretical studies supports the reliability of the present G_0W_0 results. Overall, the calculated band gaps place these chalcogenide perovskites in the visible-to-ultraviolet wide-band-gap regime, highlighting their potential for optoelectronic applications. Direct-gap compounds favor efficient light absorption and emission (e.g., LEDs), whereas indirect-gap systems are advantageous for longer carrier lifetime-based applications such as photodetectors and photocatalysis.

To gain deeper insight into the electronic structure, the density of states (DOS) is calculated using the HSE06 xc functional, as shown in Fig. S3 of the SM [42]. For YScS_3 , the VBM is predominantly derived from S-3*p* orbitals, whereas the CBM is mainly contributed by Sc-3*d* orbitals. As expected, the CBM also exhibits hybridization between Y-4*d* and Sc-3*d* states. Similarly, in YScSe_3 , the VBM is primarily composed of Se-4*p* orbitals, while the CBM shows a noticeable downward shift due to enhanced hybridization between Se-4*p* and transition-metal *d* states, leading to the observed reduction in the band gap. In contrast, for LaScX_3 ($X = \text{S, Se}$), the CBM arises from hybridized La-5*d* and Sc-3*d* states. The direct-to-indirect band gap transition primarily arises from the interplay between *d-d* orbital hybridization and structural distortions. In YScX_3 , stronger Y-4*d*–Sc-3*d* coupling and larger octahedral tilting stabilize the CBM at the S-point, resulting in an indirect gap. In contrast, weaker La-5*d*–Sc-3*d* coupling and reduced tilting in LaScX_3 shift the conduction band upward at S-point and favor a minimum at Γ -point, leading to a direct band gap [18]. Furthermore, upon replacing Sc with Y ($\text{LaScX}_3 \rightarrow \text{LaYX}_3$), the direct band gap nature is preserved, while the band gap increases due to the higher energy and modified dispersion of Y-4*d* states relative to Sc-3*d* states, resulting in an upward shift of the CBM in LaYX_3 .

To further substantiate the above interpretation, we have included orbital-projected band structures near the VBM and CBM in Fig. S4 of the SM [42]. These results explicitly identify the orbital character of the band-edge states and confirm that the evolution from a direct to an indirect band gap is governed by changes in the hybridization between Y-4*d*/La-5*d* and Sc-3*d* orbitals, together with the accompanying structural distortions. The orbital-projected bands provide direct microscopic evidence for the orbital interactions responsible for the shift of the CBM between the Γ and S points, thereby supporting the mechanism proposed from the DOS analysis.

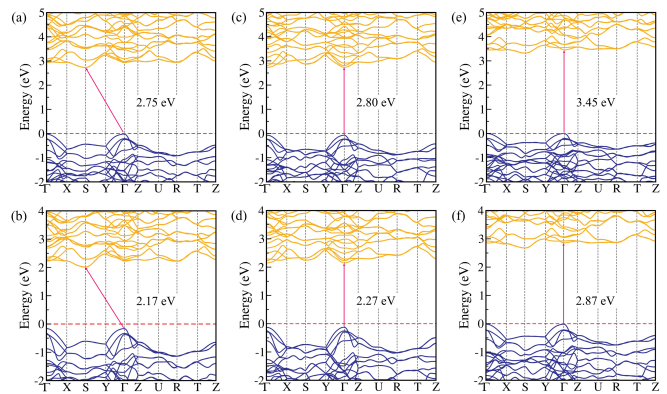


FIG. 3. Electronic band structures of the rare-earth chalcogenide perovskites (a) YScS_3 , (b) YScSe_3 , (c) LaScS_3 , (d) LaScSe_3 , (e) LaYS_3 , and (f) LaYSe_3 , calculated using the HSE06 xc functional. The Fermi level is set to be zero and marked by the dashed line.

To gain insight into charge-carrier transport, we further calculate the effective masses of electrons (m_e^*) and holes (m_h^*) for all compounds by fitting the $E-k$ dispersion obtained from PBE band structures using the formula, $m^* = \hbar^2 [\partial^2 E(k)/\partial k^2]^{-1}$, and the results are summarized in Table II. For the direct band gap compounds, the effective masses are evaluated as the harmonic mean along the Γ –X, Γ –Y, and Γ –Z directions, with results listed in Table S6 of the SM [42]. In contrast, for YScX_3 ($X = \text{S, Se}$), the electron effective masses are obtained by averaging along the S–X and S–Y directions, consistent with the location of the CBM. From Table II, it is evident that m_e^* is significantly larger than m_h^* in these compounds, indicating that holes are expected to possess higher mobility than electrons. This suggests that these materials are more favorable for p-type transport.

C. Optical Properties:

Beyond the electronic structure, the optical response provides key insight into the suitability of these materials for optoelectronic applications. In this work, the optical response is accurately described by capturing many-body effects through the Bethe-Salpeter equation (BSE) built upon G_0W_0 @PBE quasiparticle energies, ensuring a reliable treatment of excitonic contributions to the optical spectra. In this framework, GW calculations determine the fundamental bandgap, which is directly comparable to photoelectron (PES) and inverse photoelectron spectroscopy (IPES) [31, 32], whereas BSE yields the optical bandgap consistent with experimental absorption measurements [33, 34].

To evaluate the optical response of ABX_3 ($A = \text{Y, La}$; $B = \text{Sc, Y}$; and $X = \text{S, Se}$), we focus on the frequency-dependent complex dielectric function, $\epsilon(\omega) = [\text{Re}(\epsilon)] + i[\text{Im}(\epsilon)]$, which governs the interaction of electromagnetic radiation with the material. The imaginary part,

TABLE II. Bandgap (in eV) of ABX_3 ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$) rare-earth chalcogenide perovskites calculated using different methods as well as computed average effective mass of electron (m_e^*) and hole (m_h^*). Here, i , d , t , and e represent indirect, direct, theoretical, and experimental bandgaps, respectively. All values of the effective mass are in terms of free-electron mass (m_0).

Configurations	PBE	HSE06	G ₀ W ₀ @PBE	Previous Work	m_e^*	m_h^*
YScS ₃	1.76 ⁱ (1.88 ^d)	2.75 ⁱ (2.96 ^d)	3.49 ⁱ (3.75 ^d)	3.16 _t (G ₀ W ₀) [22]	1.545	0.494
YScSe ₃	1.30 ⁱ (1.43 ^d)	2.17 ⁱ (2.39 ^d)	2.75 ⁱ (3.00 ^d)		1.622	0.375
LaScS ₃	1.69	2.80	3.72	2.62 _e [18]	0.916	0.457
LaScSe ₃	1.27	2.27	2.94	2.96 _t (G ₀ W ₀) [19]	0.851	0.350
LaYS ₃	2.25	3.45	4.47		1.255	0.542
LaYSe ₃	1.79	2.87	3.70		1.180	0.419

$[\text{Im}(\epsilon)]$, describes interband optical absorption arising from electronic transitions between occupied and unoccupied states and is directly related to the absorption spectrum and optical bandgap. In contrast, the real part, $[\text{Re}(\epsilon)]$, represents the dispersive response and determines key optical properties such as dielectric screening, refractive index, and polarization behavior. Notably, the static limit ϵ_∞ provides insight into the screening strength, which influences excitonic effects and charge-carrier interactions. Together, these components offer a comprehensive description of light-matter interaction and are essential for assessing the suitability of these materials for optoelectronic applications.

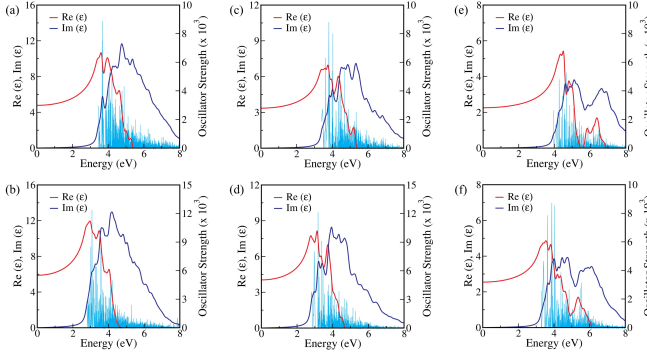


FIG. 4. Spatially averaged real $[\text{Re}(\epsilon)]$ and imaginary part $[\text{Im}(\epsilon)]$ of the electronic dielectric function for rare-earth chalcogenide perovskites (a) YScS₃, (b) YScSe₃, (c) LaScS₃, (d) LaScSe₃, (e) LaYS₃, and (f) LaYSe₃, respectively, calculated using the BSE@G₀W₀@PBE method. Peaks with cyan color represent the oscillator strength.

The imaginary part of the dielectric function, $[\text{Im}(\epsilon)]$, for ABX_3 ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$) perovskite compounds exhibits broad spectral coverage from the visible to the ultraviolet region, as shown in Figure 4. This response reflects the interplay of band structure, momentum selection rules, and electron-hole interactions, where direct gaps enable sharp absorption edges, indirect gaps lead to phonon-assisted onset, and excitonic effects renormalize the optical gap and enhance near-edge spectral features. The oscillator strength spectra further identify the optically allowed excitonic transitions. Strong oscillator strength indicates a large tran-

sition dipole moment and efficient light-matter coupling, giving rise to intense absorption features, whereas weak or nearly vanishing oscillator strength corresponds to optically inactive (dark) excitonic states that contribute negligibly to the optical response. The energy eigenvalue of the first optically active (bright) exciton, which defines the optical band gap (E_o), spans 2.77–3.96 eV across the series, highlighting the substantial influence of excitonic effects. Since the lowest excitonic state is optically active for all compounds investigated in this work, its eigenvalue directly corresponds to the optical absorption onset. Notably, for LaScS₃, the experimentally measured optical gap is 2.62 eV [18], whereas the present BSE optical gap value is 3.40 eV. This discrepancy can be attributed to the idealized nature of the calculations, which neglect temperature effects, carrier-phonon renormalization, and defect-induced band tailing that typically reduce the measured absorption onset. Overall, the strong and compositionally tunable optical absorption highlights the potential of these materials for optoelectronic applications, including photodetectors, light-emitting diodes, and laser devices.

In addition to the optical spectra, the electronic dielectric constant (ϵ_∞), defined as the zero-frequency limit of the real part of the dielectric function, is evaluated as a key descriptor of the optoelectronic response. This quantity governs the screening of Coulomb interactions, where larger ϵ_∞ values reduce electron-hole attraction and suppress carrier recombination, thereby, enhancing device performance [50]. The calculated ϵ_∞ values for ABX_3 ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$), obtained within the BSE framework, span the range of 2.26–5.88, as summarized in Table S13 of the SM [42]. These dielectric constants also serve as essential input parameters for evaluating excitonic and polaronic properties, as discussed in the following sections.

D. Excitonic Properties:

In addition to the aforementioned electronic and optical properties, excitonic properties such as, exciton binding energy (E_B), excitonic temperature (T_{exc}), exciton radius (r_{exc}), and the probability of the wavefunction for the electron-hole ($e-h$) pair at zero separation ($|\phi_n(0)|^2$),

play a crucial role in determining the performance of optoelectronic devices. An exciton is a Coulomb-bound $e - h$ pair formed upon optical excitation, which renormalizes the optical gap and governs near-edge absorption features. The exciton binding energy (E_B) quantifies the energy required to dissociate the exciton into free charge carriers, i.e., an electron in the conduction band and a hole in the valence band. A lower E_B facilitates efficient charge separation at or near room temperature, thereby promoting enhanced photoelectric conversion efficiency, particularly in photovoltaic applications. In contrast, a higher E_B implies stronger Coulomb interaction between electrons and holes, leading to more stable and tightly bound excitons. While this can hinder efficient charge separation and reduce photocurrent generation in photovoltaic devices, it is advantageous for applications that rely on strong radiative recombination, such as light-emitting diodes and laser devices, where enhanced excitonic stability can improve emission efficiency.

The exciton binding energy (E_B) is obtained from first-principles Bethe-Salpeter equation (BSE) calculations as, $E_B = E_g^{dir} - E_o$, where E_g^{dir} is the direct quasiparticle band gap from $G_0W_0@PBE$ and E_o denotes the energy eigenvalue of the first optically active (bright) excitonic state computed within BSE@ $G_0W_0@PBE$ [51, 52]. As summarized in Table III, the calculated E_B values for these chalcogenide perovskites decrease from S- to Se-containing counterparts and lie in the range of 0.148–0.517 eV. Such moderately large binding energies indicate pronounced excitonic effects arising from reduced dielectric screening and enhanced electron-hole interactions, which are favorable for efficient radiative recombination in light-emitting and photodetection applications. Notably, $LaYX_3$ exhibits a clear deviation from the overall trend, showing comparatively enhanced excitonic binding. This behavior can be attributed to its reduced electronic dielectric screening (see Figure 4), which strengthens the Coulomb interaction between electrons and holes. While the absolute values of E_B may be somewhat overestimated due to the use of $G_0W_0@PBE$ and the neglect of temperature- and phonon-induced screening effects, the overall trends and qualitative description of excitonic behavior remain robust. In particular, the systematic variation across the series and the identification of intermediate excitonic character are expected to be reliable, as they are primarily governed by dielectric screening and carrier effective masses captured within the present framework.

It is worth noting that when E_B significantly exceeds the longitudinal optical (LO) phonon energy ($\hbar\omega_{LO}$), dielectric screening is dominated by the electronic contribution, while the ionic component becomes negligible. Consequently, E_B remains largely unaffected by lattice polarization effects [53]. As shown in Tables III and V, the condition $E_B \gg \hbar\omega_{LO}$ is satisfied for the present compounds, justifying the neglect of ionic screening. This behavior is further corroborated by estimates based on the hydrogenic Wannier-Mott model (for details, see Sec.

XII of the SM [42]). From Table S13, it is observed that the upper bounds ($E_{Bu} = 0.102\text{--}1.009$ eV) for these compounds closely match the E_B values obtained using the BSE@ $G_0W_0@PBE$ method, whereas the lower bounds (E_{Bl}) are significantly smaller. This indicates that the ionic contribution to the dielectric constant is negligible, leading to $\epsilon_{eff} \rightarrow \epsilon_{\infty}$. Therefore, at high frequencies, dielectric screening is governed primarily by electronic effects.

TABLE III. Calculated exciton parameters of ABX_3 (A = Y, La; B = Sc, Y; and X = S, Se) rare-earth chalcogenide perovskites.

Configurations	E_g^{dir} (eV)	E_o (eV)	E_B (eV)	T_{exc} (K)	r_{exc} (nm)	$ \phi_n(0) ^2$ (10^{27} m^{-3})
YScS ₃	3.747	3.424	0.323	3745	0.69	0.97
YScSe ₃	3.005	2.772	0.233	2701	1.20	0.19
LaScS ₃	3.721	3.397	0.324	3757	0.58	1.61
LaScSe ₃	2.941	2.793	0.148	1716	0.86	0.50
LaYS ₃	4.472	3.955	0.517	5994	0.32	10.14
LaYSe ₃	3.701	3.286	0.415	4812	0.43	3.87

Further, the calculation of E_B within the standard first-principles BSE framework includes only electronic screening in the $e - h$ interaction kernel and neglects lattice (phonon) contributions. Such a static treatment can be inadequate for polar materials, where carrier-phonon coupling plays a crucial role in screening Coulomb interactions. To address this limitation, we adopt the approach of Filip *et al.* [54, 55], who introduced a correction of phonon-screening under the assumption of isotropic and parabolic band dispersion. The correction to the exciton binding energy is given by

$$\Delta E_B^{ph} = -2\omega_{LO} \left(1 - \frac{\epsilon_{\infty}}{\epsilon_s}\right) \frac{\sqrt{1 + \omega_{LO}/E_B} + 3}{\left(1 + \sqrt{1 + \omega_{LO}/E_B}\right)^3}, \quad (2)$$

where ω_{LO} denotes the characteristic longitudinal optical phonon frequency, and ϵ_{∞} and ϵ_s represent the electronic and static dielectric constants, respectively. The effective ω_{LO} is evaluated using the thermal “B” approach developed by Hellwarth *et al.* [36], which accounts for the spectral contributions of multiple phonon branches through an appropriate averaging scheme (for details, see Sec. XIII of the SM [42]). Table IV shows that phonon screening reduces E_B by 3.20–9.26%, indicating that the overall reduction is not substantial in these rare-earth chalcogenide perovskites. After incorporating the phonon-screening correction, the renormalized exciton binding energy (E'_B) spans 0.134–0.498 eV. This behavior suggests that the electronic contribution to dielectric screening dominates over the ionic (phonon-mediated) component in these systems.

TABLE IV. Calculated exciton binding energy (E_B), phonon screening corrections (ΔE_B^{ph}), percentage of phonon screening contribution to the reduction of exciton binding energy (%), and corrected values of exciton binding energy (E'_B) for ABX₃ (A = Y, La; B = Sc, Y; and X = S, Se) rare-earth chalcogenide perovskites.

Configurations	E_B (eV)	ΔE_B^{ph} (meV)	Reduction of E_B (%)	E'_B (eV)
YScS ₃	0.323	-19.20	5.94	0.304
YScSe ₃	0.233	-13.55	5.82	0.219
LaScS ₃	0.324	-19.41	5.99	0.305
LaScSe ₃	0.148	-13.70	9.26	0.134
LaYS ₃	0.517	-18.67	3.61	0.498
LaYSe ₃	0.415	-13.29	3.20	0.402

Next, several additional excitonic parameters, including the excitonic temperature (T_{exc}), exciton radius (r_{exc}), and the probability of the wavefunction for the $e-h$ pair at zero separation ($|\phi_n(0)|^2$), are evaluated and summarized in Table III. The excitonic temperature (T_{exc}) serves as a useful metric to quantify the thermal stability of bound $e-h$ pairs in semiconductors and insulators. It is defined by relating the exciton binding energy (E_B) to thermal energy via the Boltzmann constant (k_B) as $T_{exc} = E_B/k_B$. Physically, T_{exc} represents the characteristic temperature above which excitons are thermally ionized into free carriers. When T_{exc} significantly exceeds room temperature (~ 300 K), excitons are expected to remain stable under ambient conditions, giving rise to pronounced excitonic features in optical absorption and emission spectra. Conversely, if T_{exc} is comparable to or lower than room temperature, thermal dissociation becomes efficient, and the optoelectronic response is dominated by free carriers. In our study, the rare-earth chalcogenide perovskite compounds exhibit high excitonic temperatures (1716–5994 K), reflecting strongly bound excitons that remain thermally stable far above room temperature and yield pronounced excitonic effects in their optical response. Such robust excitonic stability is advantageous for optoelectronic applications, particularly in light-emitting devices and photodetectors, where strong light-matter interaction and efficient exciton generation are desirable.

The exciton radius (r_{exc}) is evaluated within the hydrogenic Wannier-Mott model as [56, 57]:

$$r_{exc} = \frac{m_0}{\mu_{dir}^*} \varepsilon_{eff} n^2 r_{By}, \quad (3)$$

where μ_{dir}^* is the reduced effective mass at the direct band edge, ε_{eff} denotes the effective dielectric constant, n is the exciton energy level, and r_{By} is the Bohr radius (0.0529 nm). In this work, the high-frequency dielectric constant (ε_∞) is employed as the effective dielectric screening (ε_{eff}), and $n = 1$ is considered, corresponding to the ground-state exciton and yielding the minimum exciton radius. The exciton radius serves as a key descriptor of the spatial extent of the $e-h$ pair, distinguishing between localized and delocalized excitonic

states. In our study, the obtained r_{exc} values (~ 3.2 – 12 Å) indicate moderately to strongly bound excitons with spatial extents ranging from near unit-cell localization to a few lattice constants, suggesting an intermediate character approaching the Wannier-Frenkel crossover regime. Such excitons promote strong light-matter interaction, highlighting the potential of these materials for optoelectronic applications. Within this framework, LaYX₃ stands out by exhibiting a comparatively smaller exciton radius, reflecting enhanced localization of the electron-hole pair. This behavior originates from its relatively weak electronic screening, which strengthens Coulomb interactions and stabilizes more tightly bound excitonic states.

To qualitatively assess the radiative recombination propensity of excitons, we evaluate the probability density of the $e-h$ pair at zero separation, $|\phi_n(0)|^2$, which is given by [56, 57]:

$$|\phi_n(0)|^2 = \frac{1}{\pi(r_{exc})^3 n^3}. \quad (4)$$

Within the framework of radiative recombination, the radiative decay rate is proportional to the $e-h$ overlap, i.e., $\tau_{rad}^{-1} \propto |\phi_n(0)|^2$. Consequently, larger values of $|\phi_n(0)|^2$ indicate stronger $e-h$ overlap and a greater propensity for radiative transitions. In the present case, LaYX₃ exhibits an enhanced $|\phi_n(0)|^2$, consistent with its reduced exciton radius, confirming stronger wavefunction overlap and potentially larger oscillator strength. Since neither radiative nor non-radiative exciton lifetimes are explicitly calculated in this work, $|\phi_n(0)|^2$ is employed only as a qualitative descriptor of the radiative recombination tendency rather than as a direct measure of the exciton lifetime (τ_{exc}). These results indicate pronounced light-matter interaction in the studied systems, which is beneficial for optoelectronic and light-emitting applications.

E. Polaronic Properties:

Understanding the fundamental limits of carrier mobility in these chalcogenide perovskites requires a rigorous treatment of carrier-phonon interactions within a first-principles framework [58, 59]. In polar semiconductors, transport at ambient conditions is primarily limited by scattering with longitudinal optical phonons, arising from the macroscopic electric fields associated with lattice polarization [15, 52]. This interaction leads to the formation of polarons, wherein charge carriers become dressed by lattice distortions, thereby altering their effective mass and transport dynamics. As a consequence, mobility cannot be accurately described within a simple band-like picture of free carriers.

The interaction between charge carriers and polar optical phonons can be effectively described within the framework of the Fröhlich Hamiltonian, which is valid in the

low carrier-density regime [35]. The strength of this interaction is quantified by the dimensionless Fröhlich coupling constant, α , which incorporates the effects of dielectric screening, carrier effective mass, and the longitudinal optical phonon frequency. It is defined as [15, 60]:

$$\alpha = \frac{1}{4\pi\epsilon_0} \frac{1}{2} \left(\frac{1}{\epsilon_\infty} - \frac{1}{\epsilon_s} \right) \frac{e^2}{\hbar\omega_{LO}} \left(\frac{2m^*\omega_{LO}}{\hbar} \right)^{1/2} \quad (5)$$

The calculated carrier-phonon coupling constants (α) for the investigated compounds are summarized in Table V. In general, $\alpha > 10$ signifies strong carrier-phonon coupling, whereas $\alpha \ll 1$ corresponds to the weak-coupling regime [58]. Our results place these materials in the intermediate-to-strong coupling regime, with α values ranging from 1.92 to 10.72. Furthermore, the carrier-phonon interaction is found to be stronger for electrons than for holes, with this trend being particularly pronounced in LaYX_3 ($X = \text{S, Se}$), suggesting more significant polaronic renormalization of electron transport. It should be emphasized that the present analysis is based on the Fröhlich formalism, which provides a physically meaningful description of the long-range interaction between charge carriers and longitudinal optical phonons in polar materials using first-principles quantities, including the dielectric constants, effective carrier masses, and longitudinal optical phonon frequencies. Consequently, the calculated Fröhlich coupling constants provide useful estimates of the strength of the long-range polar electron-phonon interaction and the associated large-polaron characteristics. However, this approach does not explicitly evaluate the momentum- and mode-resolved electron-phonon coupling matrix elements or identify the individual phonon modes and electronic states contributing to the coupling. A comprehensive microscopic treatment based on first-principles electron-phonon coupling calculations using density-functional perturbation theory together with Wannier interpolation would provide such information but is beyond the scope of the present work [61]. Nevertheless, the Fröhlich model remains a widely adopted framework for describing large-polaron behavior in polar semiconductors and is appropriate for the objectives of the present study.

Polaron formation refers to the interaction of a charge carrier, either an electron or a hole, with the surrounding lattice, leading to a local structural distortion. This coupling lowers the quasiparticle (QP) energies, so that both electron and hole states are stabilized during polaron formation. The polaron energy, E_p , can be estimated as follows [15, 56]:

$$E_p = (-\alpha - 0.0123\alpha^2)\hbar\omega_{LO}. \quad (6)$$

The QP gap associated with the polaronic states, obtained from the electron and hole polaron energies (Table V), is compared with the exciton binding energies, E_B , listed in Table III. This comparison reveals that,

for most of the examined chalcogenide perovskites, the energy of the charge-separated polaronic states is lower than that of the bound exciton states, indicating that the bound excitons are energetically more stable. However, in the case of $\text{La}(\text{Sc, Y})\text{Se}_3$, the charge-separated polaronic states become more favorable than the bound exciton states.

Feynman introduced a powerful variational approach to address the Fröhlich Hamiltonian, which describes the interaction between an electron (or hole) and a continuum of independent, harmonically oscillating phonon modes within a quantum field theoretical framework [62]. As the electron (or hole) moves through the lattice, it interacts with the polarization field it induces, which evolves and decays over time. Within this formalism, and in the weak-coupling limit (small α), the polaron effective mass, m_p , can be expressed as [17, 62]:

$$m_p = m^* \left(1 + \frac{\alpha}{6} + \frac{\alpha^2}{40} + \dots \right). \quad (7)$$

As shown in Table V, carrier-phonon coupling leads to a substantial enhancement of the effective mass, with m_p increasing by approximately 41–466%. This significant renormalization indicates the presence of intermediate to strong carrier-lattice interactions in the examined systems.

To further assess the impact of the enhanced polaron effective mass, the polaron mobility is estimated using the Hellwarth polaron model as [36, 57]:

$$\mu_p = \frac{(3\sqrt{\pi}e)}{2\pi c\omega_{LO}m^*\alpha} \frac{\sinh(\beta/2)}{\beta^{5/2}} \frac{w^3}{v^3} \frac{1}{K(a,b)} \quad (8)$$

where e is the electronic charge, $\beta = \hbar c\omega_{LO}/k_B T$, w and v are temperature-dependent variational parameters, and $K(a,b)$ is a function of β , w , and v (for details, see Sec. XIII of the SM [42]). The polaron mobility quantifies the ease with which a polaron propagates through the lattice and is governed by both its effective mass and the strength of carrier-lattice interactions. As the effective mass increases due to strong carrier-phonon coupling, the mobility correspondingly decreases, leading to slower carrier transport. This behavior is evident in the present systems (Table V), where hole polarons exhibit significantly higher mobilities (2.12–39.94 $\text{cm}^2\text{V}^{-1}\text{s}^{-1}$) compared to electron polarons (0.21–3.87 $\text{cm}^2\text{V}^{-1}\text{s}^{-1}$). This indicates stronger electron-phonon coupling and/or larger effective masses for electrons, leading to more localized electron polarons and consequently reduced mobility. In contrast, the relatively lighter and less strongly coupled hole polarons enable more efficient charge transport. Despite the relatively low electron mobility, the favorable hole transport, combined with the structural stability and non-toxicity of these materials, underscores their potential for optoelectronic applications, particularly in devices where hole conduction plays a dominant role.

TABLE V. Calculated polaron parameters of ABX_3 ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$) rare-earth chalcogenide perovskites.

Configurations	ω_{LO} (THz)	α		E_p (meV)		m_p/m^*		μ_p ($\text{cm}^2\text{V}^{-1}\text{s}^{-1}$)	
		e	h	e	h	e	h	e	h
YScS ₃	6.50	4.39	2.48	124.55	68.79	2.21	1.57	2.18	19.04
YScSe ₃	4.86	3.99	1.92	84.25	39.56	2.06	1.41	2.94	39.94
LaScS ₃	5.92	5.56	3.93	145.63	101.01	2.70	2.04	2.27	9.67
LaScSe ₃	4.47	4.94	3.17	97.00	60.97	2.43	1.78	3.87	21.31
LaYS ₃	5.32	10.72	7.04	267.32	168.53	5.66	3.41	0.21	2.12
LaYSe ₃	3.87	10.58	6.30	191.63	108.79	5.56	3.04	0.34	5.05

A broader perspective can be obtained by comparing the present III-III chalcogenide perovskites with the more extensively studied II-IV systems ABX_3 ($A = Ca, Sr, Ba$; $B = Ti, Zr, Sn, Hf$; and $X = S, Se$). The latter typically exhibit smaller band gaps (~ 1.0 – 2.5 eV), larger dielectric screening, and correspondingly weaker excitonic effects, resulting in more delocalized Wannier-type excitons and longer carrier diffusion lengths that are advantageous for photovoltaic applications [13–17]. In addition, relatively weaker carrier-phonon coupling in these systems leads to lighter polarons and higher carrier mobility. In contrast, the III-III compounds investigated here display wider band gaps (2.75–4.47 eV), reduced dielectric screening, and moderately large exciton binding energies, giving rise to more localized excitons with enhanced electron-hole overlap. This enhanced localization is further accompanied by stronger carrier-phonon coupling, leading to heavier polaronic quasiparticles and reduced carrier mobility. While such polaronic effects may limit efficient charge transport and charge separation, they can simultaneously stabilize excitonic states and suppress non-radiative recombination. Consequently, the combination of strong excitonic binding and polaronic localization results in pronounced light-matter interaction and enhanced radiative recombination, making these materials particularly promising for light-emitting and photodetection applications, albeit less favorable for photovoltaic performance.

IV. CONCLUSION:

In summary, we have systematically investigated the ground- and excited-state properties of III-III rare-earth chalcogenide perovskites ABX_3 ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$) using state-of-the-art density functional theory, density functional perturbation theory, and many-body perturbation theory. The calculated phonon band structures and elastic constants confirm the dynamical and mechanical stability of these compounds. Our electronic structure analysis reveals quasiparticle band gaps (G_0W_0 @PBE) in the range of 2.75–4.47 eV, accompanied by lower hole effective masses compared to electrons, indicating favorable p-type transport. The optical properties, computed within the BSE framework, exhibit a strong absorption onset spanning the visible to

ultraviolet region, highlighting their potential for optoelectronic applications. Importantly, these compounds exhibit pronounced excitonic effects, hosting stable excitons as evidenced by their intermediate-to-large binding energies (0.148–0.517 eV), high excitonic temperatures, Wannier-Frenkel crossover character, and strong electron-hole wavefunction overlap, indicative of pronounced light-matter interaction and favorable radiative recombination characteristics. Fröhlich’s mesoscopic analysis indicates appreciable carrier-phonon coupling in these systems, with electron-phonon interactions consistently outweighing their hole counterparts. Remarkably, bound excitonic states dominate over charge-separated polaronic configurations in nearly all compounds, with La(Sc, Y)Se₃ as an exception, while hole polarons demonstrate substantially higher mobilities (reaching up to $\sim 40 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$) than electrons. Overall, the interplay between strong excitonic effects and favorable polaronic transport, combined with excellent structural stability and lead-free composition, establishes rare-earth chalcogenide perovskites ABX_3 as promising candidates for next-generation optoelectronic technologies. These materials are particularly attractive for applications in light-emitting devices and photodetectors, and they offer a viable platform for exploring excitonic optoelectronics in environmentally benign systems.

ACKNOWLEDGMENTS

The authors would like to acknowledge the Council of Scientific and Industrial Research (CSIR), Government of India [Grant No. 3WS(007)/2023-24/EMR-II/ASPIRE] for financial support. The authors acknowledge the High Performance Computing Cluster (HPCC) ‘Magus’ at Shiv Nadar Institution of Eminence for providing computational resources that have contributed to the research results reported within this paper.

DATA AVAILABILITY

The data that support the findings of this article are not publicly available. The data are available from the authors upon reasonable request.

- [1] A. Kojima, K. Teshima, Y. Shirai, and T. Miyasaka, Organometal Halide Perovskites as Visible-Light Sensitizers for Photovoltaic Cells, *J. Am. Chem. Soc.* **131**, 6050 (2009).
- [2] N.-G. Park, Organometal Perovskite Light Absorbers Toward a 20% Efficiency Low-Cost Solid-State Mesoscopic Solar Cell, *J. Phys. Chem. Lett.* **4**, 2423 (2013).
- [3] J. Berry, T. Buonassisi, D. A. Egger, G. Hodes, L. Kronik, Y.-L. Loo, I. Lubomirsky, S. R. Marder, Y. Mastai, J. S. Miller, D. B. Mitzi, Y. Paz, A. M. Rappe, I. Riess, B. Rybtchinski, O. Stafsudd, V. Stevanovic, M. F. Toney, D. Zitoun, A. Kahn, D. Ginley, and D. Cahen, Hybrid Organic-Inorganic Perovskites (HOIPs): Opportunities and Challenges, *Adv. Mater.* **27**, 5102 (2015).
- [4] D. A. Egger, A. M. Rappe, and L. Kronik, Hybrid Organic-Inorganic Perovskites on the Move, *Acc. Chem. Res.* **49**, 573 (2016).
- [5] National Renewable Energy Laboratory (NREL), Best Research Cell Efficiency Chart, <https://www.nrel.gov/pv/cell-efficiency.html>, Accessed 2021-01-07 (2021).
- [6] D. B. Straus, S. Guo, A. M. Abeykoon, and R. J. Cava, Understanding the Instability of the Halide Perovskite CsPbI₃ through Temperature-Dependent Structural Analysis, *Adv. Mater.* **32**, 2001069 (2020).
- [7] A. Babayigit, A. Ethirajan, M. Muller, and B. Conings, Toxicity of organometal halide perovskite solar cells, *Nat. Mater.* **15**, 247 (2016).
- [8] D. Tiwari, O. S. Hutter, and G. Longo, Chalcogenide perovskites for photovoltaics: current status and prospects, *J. Phys. Energy* **3**, 034010 (2021).
- [9] S. Niu, H. Huyan, Y. Liu, M. Yeung, K. Ye, L. Blanke-meier, T. Orvis, D. Sarkar, D. J. Singh, R. Kapadia, and J. Ravichandran, Bandgap Control via Structural and Chemical Tuning of Transition Metal Perovskite Chalcogenides, *Adv. Mater.* **29**, 1604733 (2017).
- [10] X. Wu, W. Gao, J. Chai, C. Ming, M. Chen, H. Zeng, P. Zhang, S. Zhang, and Y.-Y. Sun, Defect tolerance in chalcogenide perovskite photovoltaic material BaZrS₃, *Sci. China Mater.* **64**, 2976 (2021).
- [11] Y.-Y. Sun, M. L. Agiorgousis, P. Zhang, and S. Zhang, Chalcogenide Perovskites for Photovoltaics, *Nano Lett.* **15**, 581 (2015).
- [12] R. Lelieveld and D. J. W. IJdo, Sulphides with the GdFeO₃ structure, *Acta Cryst. B* **36**, 2223 (1980).
- [13] M. Kumar, A. Singh, D. Gill, and S. Bhattacharya, Optoelectronic Properties of Chalcogenide Perovskites by Many-Body Perturbation Theory, *J. Phys. Chem. Lett.* **12**, 5301 (2021).
- [14] P. Basera and S. Bhattacharya, Chalcogenide Perovskites (ABS₃; A = Ba, Ca, Sr; B = Hf, Sn): An Emerging Class of Semiconductors for Optoelectronics, *J. Phys. Chem. Lett.* **13**, 6439 (2022).
- [15] S. Adhikari and P. Johari, Photovoltaic properties of ABSe₃ chalcogenide perovskites (A = Ca, Sr, Ba; B = Zr, Hf), *Phys. Rev. B* **109**, 174114 (2024).
- [16] S. Adhikari, S. Das, and P. Johari, Post-transition metal Sn-based chalcogenide perovskites: a promising lead-free and transition metal alternative for stable, high-performance photovoltaics, *J. Mater. Chem. C* **13**, 7792 (2025).
- [17] S. Adhikari and P. Johari, Optimizing lead-free chalcogenide perovskites for high-efficiency photovoltaics via alloying, *Phys. Rev. B* **112**, 085206 (2025).
- [18] H. Zhang, Y. Pan, Z. Liu, B. Zeng, X. Wu, C. Ming, G. Xin, W. Zhou, H. Zeng, S. Zhang, and Y.-Y. Sun, Indirect-to-direct band gap transition induced by *d*-*d* coupling between cations in rare-earth chalcogenide perovskites, *Phys. Rev. B* **110**, L041201 (2024).
- [19] H. Zhang, X. Wu, K. Ding, L. Xie, K. Yang, C. Ming, S. Bai, H. Zeng, S. Zhang, and Y.-Y. Sun, Prediction and Synthesis of a Selenide Perovskite for Optoelectronics, *Chem. Mater.* **35**, 4128 (2023).
- [20] K. Kuhar, A. Crovetto, M. Pandey, K. S. Thygesen, B. Seger, P. C. K. Vesborg, O. Hansen, I. Chorkendorff, and K. W. Jacobsen, Sulfide perovskites for solar energy conversion applications: computational screening and synthesis of the selected compound LaYS₃, *Energy Environ. Sci.* **10**, 2579 (2017).
- [21] A. Crovetto, R. Nielsen, M. Pandey, L. Watts, J. G. Labram, M. Geisler, N. Stenger, K. W. Jacobsen, O. Hansen, B. Seger, I. Chorkendorff, and P. C. K. Vesborg, Shining Light on Sulfide Perovskites: LaYS₃ Material Properties and Solar Cells, *Chem. Mater.* **31**, 3359 (2019).
- [22] H. Zhang, C. Ming, K. Yang, H. Zeng, S. Zhang, and Y.-Y. Sun, Chalcogenide Perovskite YScS₃ as a Potential p-Type Transparent Conducting Material, *Chinese Phys. Lett.* **37**, 097201 (2020).
- [23] P. Hohenberg and W. Kohn, Inhomogeneous Electron Gas, *Phys. Rev.* **136**, B864 (1964).
- [24] W. Kohn and L. J. Sham, Self-Consistent Equations Including Exchange and Correlation Effects, *Phys. Rev.* **140**, A1133 (1965).
- [25] M. Gajdoš, K. Hummer, G. Kresse, J. Furthmüller, and F. Bechstedt, Linear optical properties in the projector-augmented wave methodology, *Phys. Rev. B* **73**, 045112 (2006).
- [26] H. Jiang, P. Rinke, and M. Scheffler, Electronic properties of lanthanide oxides from the GW perspective, *Phys. Rev. B* **86**, 125115 (2012).
- [27] F. Fuchs, C. Rödl, A. Schleife, and F. Bechstedt, Efficient $\mathcal{O}(N^2)$ approach to solve the Bethe-Salpeter equation for excitonic bound states, *Phys. Rev. B* **78**, 085103 (2008).
- [28] J. P. Perdew, K. Burke, and M. Ernzerhof, Generalized Gradient Approximation Made Simple, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [29] J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, and K. Burke, Restoring the Density-Gradient Expansion for Exchange in Solids and Surfaces, *Phys. Rev. Lett.* **100**, 136406 (2008).
- [30] J. Heyd, G. E. Scuseria, and M. Ernzerhof, Hybrid functionals based on a screened Coulomb potential, *J. Chem. Phys.* **118**, 8207 (2003).
- [31] L. Hedin, New Method for Calculating the One-Particle Green's Function with Application to the Electron-Gas Problem, *Phys. Rev.* **139**, A796 (1965).
- [32] M. S. Hybertsen and S. G. Louie, First-Principles Theory of Quasiparticles: Calculation of Band Gaps in Semiconductors and Insulators, *Phys. Rev. Lett.* **55**, 1418 (1985).

- [33] S. Albrecht, L. Reining, R. Del Sole, and G. Onida, Ab Initio Calculation of Excitonic Effects in the Optical Spectra of Semiconductors, *Phys. Rev. Lett.* **80**, 4510 (1998).
- [34] M. Rohlfing and S. G. Louie, Electron-Hole Excitations in Semiconductors and Insulators, *Phys. Rev. Lett.* **81**, 2312 (1998).
- [35] H. Fröhlich, Electrons in lattice fields, *Adv. Phys.* **3**, 325 (1954).
- [36] R. W. Hellwarth and I. Biaggio, Mobility of an electron in a multimode polar lattice, *Phys. Rev. B* **60**, 299 (1999).
- [37] G. Kresse and J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, *Phys. Rev. B* **54**, 11169 (1996).
- [38] G. Kresse and J. Furthmüller, Efficiency of Ab-initio Total Energy Calculations for Metals and Semiconductors Using a Plane-wave Basis Set, *Comput. Mater. Sci.* **6**, 15 (1996).
- [39] P. E. Blöchl, Projector augmented-wave method, *Phys. Rev. B* **50**, 17953 (1994).
- [40] K. Momma and F. Izumi, *VESTA3* for three-dimensional visualization of crystal, volumetric and morphology data, *J. Appl. Crystallogr.* **44**, 1272 (2011).
- [41] A. Togo, L. Chaput, T. Tadano, and I. Tanaka, Implementation strategies in phonopy and phono3py, *J. Phys. Condens. Matter* **35**, 353001 (2023).
- [42] See Supplemental Material (SM) at [URL will be inserted by publisher] for details of distortion parameters, decomposition energy, convex hull, phonon dispersion curves, mechanical properties, electronic DOS, effect of spin-orbit coupling on bandgap, orbital projected band structures, effective masses of charge carriers, convergence of G_0W_0 and BSE calculations, exciton binding energy obtained using the Wannier-Mott model, calculation of single phonon angular frequency and polaron mobility parameters for rare-earth chalcogenide perovskites ABX_3 ($A = Y, La$; $B = Sc, Y$; and $X = S, Se$).
- [43] A. M. Ganose, A. J. Jackson, and D. O. Scanlon, sumo: Command-line tools for plotting and analysis of periodic ab initio calculations, *J. Open Source Softw.* **3**, 717 (2018).
- [44] V. Wang, N. Xu, J.-C. Liu, G. Tang, and W.-T. Geng, VASPKIT: A user-friendly interface facilitating high-throughput computing and analysis using VASP code, *Comput. Phys. Commun.* **267**, 108033 (2021).
- [45] A. Chakravorty, S. Adhikari, and P. Johari, Unlocking the optoelectronic potential of $AGeX_3$ ($A = Ca, Sr, Ba$; $X = S, Se$): A sustainable alternative in chalcogenide perovskites, *J. Chem. Phys.* **163**, 234708 (2025).
- [46] F. Mouhat and F.-X. Coudert, Necessary and sufficient elastic stability conditions in various crystal systems, *Phys. Rev. B* **90**, 224104 (2014).
- [47] Z.-j. Wu, E.-j. Zhao, H.-p. Xiang, X.-f. Hao, X.-j. Liu, and J. Meng, Crystal structures and elastic properties of superhard IrN_2 and IrN_3 from first principles, *Phys. Rev. B* **76**, 054115 (2007).
- [48] R. Hill, The Elastic Behaviour of a Crystalline Aggregate, *Proc. Phys. Soc. A* **65**, 349 (1952).
- [49] S. Pugh, XCII. Relations between the elastic moduli and the plastic properties of polycrystalline pure metals, *London, Edinburgh Dublin Philos. Mag. J. Sci.* **45**, 823 (1954).
- [50] X. Liu, B. Xie, C. Duan, Z. Wang, B. Fan, K. Zhang, B. Lin, F. J. M. Colberts, W. Ma, R. A. J. Janssen, F. Huang, and Y. Cao, A high dielectric constant non-fullerene acceptor for efficient bulk-heterojunction organic solar cells, *J. Mater. Chem. A* **6**, 395 (2018).
- [51] S. Adhikari and P. Johari, Theoretical insights into monovalent-metal-cation transmutation effects on lead-free halide double perovskites for optoelectronic applications, *Phys. Rev. Mater.* **7**, 075401 (2023).
- [52] S. Adhikari and P. Johari, Capturing optoelectronic properties of $Cs_2AgSbBr_{6-x}Cl_x$ ($x = 0 - 6$) double perovskites using many-body perturbation theory, *Phys. Rev. B* **110**, 014101 (2024).
- [53] M. Bokdam, T. Sander, A. Stroppa, S. Picozzi, D. D. Sarma, C. Franchini, and G. Kresse, Role of Polar Phonons in the Photo Excited State of Metal Halide Perovskites, *Sci. Rep.* **6**, 28618 (2016).
- [54] M. Filip, J. B. Haber, and J. B. Neaton, Phonon Screening of Excitons in Semiconductors: Halide Perovskites and Beyond, *Phys. Rev. Lett.* **127**, 067401 (2021).
- [55] S. Adhikari, S. S. Padelkar, J. J. Jasieniak, A. N. Simonov, and A. Alam, Harnessing Linear and Nonlinear Optical Responses in Ferroelectric $LaMoN_3$ for Enhanced Photovoltaic Efficiency, *Chem. Mater.* **38**, 6271 (2026).
- [56] S. Adhikari and P. Johari, Unveiling the impact of trivalent metal cation transmutation on $Cs_2AgM(III)Cl_6$ double perovskites using many-body perturbation theory, *Phys. Rev. B* **112**, 195208 (2025).
- [57] S. Adhikari, A. Chakravorty, and P. Johari, Optical and polaronic properties of vacancy-ordered double perovskites: A first-principles investigation, *Phys. Rev. B* **113**, 045204 (2026).
- [58] J. M. Frost, Calculating polaron mobility in halide perovskites, *Phys. Rev. B* **96**, 195202 (2017).
- [59] L. M. Herz, Charge-Carrier Mobilities in Metal Halide Perovskites: Fundamental Mechanisms and Limits, *ACS Energy Lett.* **2**, 1539 (2017).
- [60] S. Adhikari and P. Johari, Probing Optoelectronic Properties of Stable Vacancy-Ordered Double Perovskites: Insights from Many-Body Perturbation Theory, *Adv. Theory Simul.* **8**, 2400921 (2025).
- [61] F. Giustino, Electron-phonon interactions from first principles, *Rev. Mod. Phys.* **89**, 015003 (2017).
- [62] R. P. Feynman, Slow Electrons in a Polar Crystal, *Phys. Rev.* **97**, 660 (1955).