

LAMMPS-Modeled Radiation Damage in Nuclear Materials

Henry Huang¹, Jonathan Symonds¹ & Alessandro Verona¹

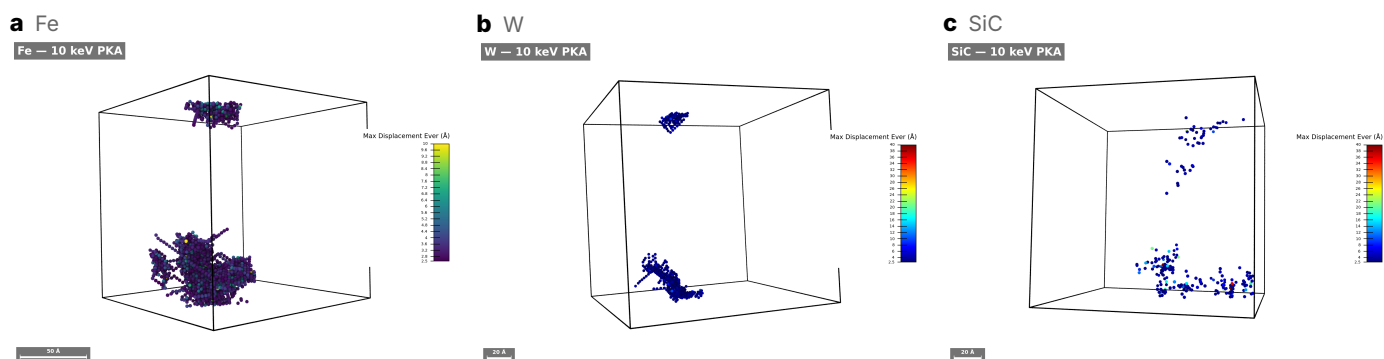


Fig. 1 | Cascade damage at 10 keV in Fe (a), W (b), and SiC (c).

1. What We Did in LAMMPS

- Step 1: Built the crystals. 3C-SiC (262,144 atoms), bcc Fe and W (250,000 each), with published potentials¹.
- Step 2: Fired the cascade. One central atom given 10 keV at 300 K, aimed away from crystal channels.
- Step 3: Counted the damage. Wigner–Seitz.
- Step 4: Measured the stored energy. The potential energy left behind after the cell cools back down, the energy locked into the surviving defects.
- Step 5: Forward-modelled diffraction. Pair distribution functions $G(r)$, the histogram of all interatomic distances, which is exactly what a diffraction beamline measures, so our damaged cells can be compared directly with synchrotron experiments on irradiated SiC.

2. Results

Fig. 1 shows each crystal after its cascade; every dot is an atom that was knocked out of place. In Fe and W the impact melts one small pocket, and when that pocket refreezes the atoms mostly fall back onto their lattice sites, so W ends up with only 12 lasting defect pairs. In SiC the energy scatters into many small damage pockets instead, because carbon atoms are light and easy to knock loose; 152 defect pairs survive, and the crystal traps about six times more energy than either metal.

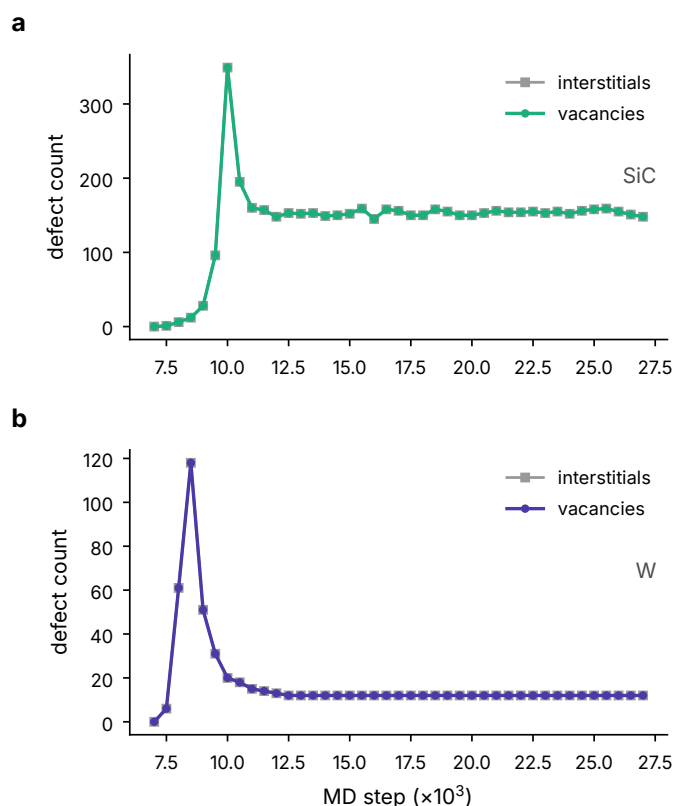


Fig. 2 | Wigner–Seitz defect counts through the spike: SiC (a) peaks at 349 and keeps 148; W (b) peaks at 118 and keeps 12.

¹Garcia Center for Polymers at Engineered Interfaces, Stony Brook University, Stony Brook NY, USA.

Table 1 | Key results.

Quantity	This work	Literature	Match
Stored energy, Fe/W/SiC (eV)	122 / 147 / 898	≤ 1390 J/g at dose ²	✓
Energy per defect pair, Fe (eV)	4.9	5–6 ³	✓
Energy per defect pair, SiC (eV)	5.7	5–7 ¹	✓
Energy per defect pair, W (eV)	12.3	12–13 ⁴	✓
C share of SiC stored energy	57.9%	C-dominated ⁵	✓
C:Si defect population	2:1	35/20 eV thresholds ⁶	✓
In-cascade recombination, SiC	58%	$\sim 60\%$ ⁷	✓
In-cascade recombination, W	90%	$\sim 1/3$ NRT survival ⁸	✓
NRT survival, Fe	0.337	0.364 ⁸	✓
NRT survival, SiC	1.48	1–2 ⁷	✓
NRT survival, W	0.337	~ 0.24 ⁹	✓
$E_d(\text{Si})$ (eV)	36.2 ± 2.0	35 ⁶	✓
$E_d(\text{C})$, soft channel (eV)	20–24	~ 21 ⁶	✓
$E_d(\text{Fe})$ (eV)	52.2 ± 4.1	40 ⁹	✓
$E_d(\text{W})$ (eV)	102 ± 10	83–128 ¹⁰	✓
W clustered interstitial fraction	0.58	0.5–0.7 ¹¹	✓
Partial-PDF damage, Si-Si vs C-C	equal (66.9)	resolved only at dose ¹²	✓
Static disorder ratio, C/Si	1.00	1.25–2.8 with dose ⁵	✓

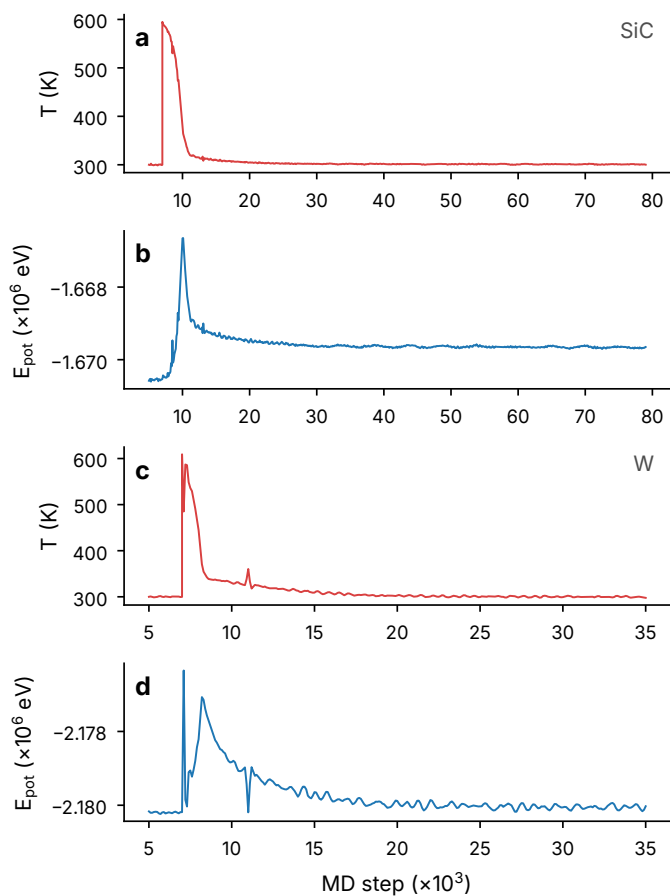


Fig. 3 | Temperature (a, c) and potential energy (b, d) for SiC and W; the energy offset that survives cooling is the stored energy.

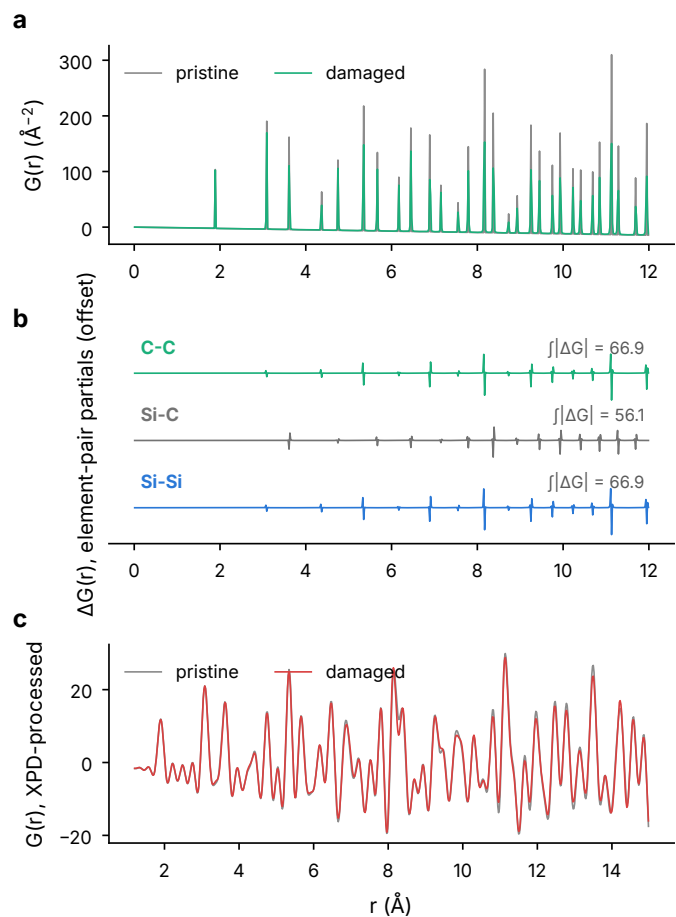


Fig. 4 | Damaged vs pristine $G(r)$ (a), its element-pair partials (b), and the beamline-processed version (c).

3. Visual Heat Strain

Each crystal was also heated in a separate staged NPT test from 300 K to its ramp peak, with every atom colored by how far it has moved from its cold position (Fig. 5), blue near the lattice site, drifting red as thermal vibration and lattice expansion grow. Heating disorders every atom a little and equally, while a cascade (Fig. 1) disorders a few atoms severely, the difference between reversible thermal motion and stored damage.

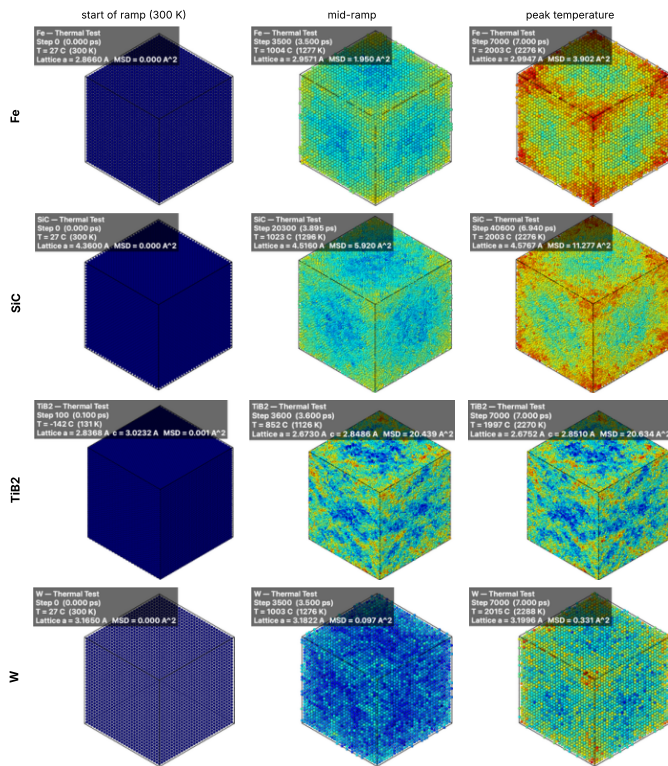


Fig. 5 | Staged heating of Fe, SiC, TiB₂, and W: atom displacement from the cold lattice at the start, middle, and peak of the temperature ramp.

4. References

1. F. Gao and W. J. Weber. Empirical potential approach for defect properties in 3C-SiC. *Nuclear Instruments and Methods in Physics Research B*, 191:504–508, 2002.
2. L. L. Snead, K. A. Terrani, Y. Katoh, T. Koyanagi, K. D. Linton, K. G. Field, and C. M. Petrie. Stored energy release in neutron irradiated silicon carbide. *Journal of Nuclear Materials*, 514:368–385, 2019.
3. C.-C. Fu, F. Willaime, and P. Ordejón. Stability and mobility of mono- and di-interstitials in α -Fe. *Physical Review Letters*, 92:175503, 2004.
4. D. Nguyen-Manh, A. P. Horsfield, and S. L. Dudarev. Self-interstitial atom defects in bcc transition metals: group-specific trends. *Physical Review B*, 73:020101, 2006.
5. D. J. Sprouster, L. L. Snead, T. Koyanagi, and Y. Katoh. Stored energy release and sublattice recovery in neutron-irradiated silicon carbide. *Physical Review Materials*, 5:103601, 2021.
6. R. Devanathan and W. J. Weber. Displacement energy surface in 3C and 6H SiC. *Journal of Nuclear Materials*, 278:258–265, 2000.
7. G. D. Samolyuk, Y. N. Osetsky, and R. E. Stoller. Molecular dynamics modeling of atomic displacement cascades in 3C-SiC: comparison of interatomic potentials. *Journal of Nuclear Materials*, 465:83–88, 2015.
8. D. J. Bacon, A. F. Calder, F. Gao, V. G. Kapinos, and S. J. Wooding. Computer simulation of defect production by displacement cascades in metals. *Nuclear Instruments and Methods in Physics Research B*, 102:37–46, 1995.
9. K. Nordlund, S. J. Zinkle, A. E. Sand, F. Granberg, R. S. Averback, R. Stoller, T. Suzudo, L. Malerba, F. Banhart, W. J. Weber, F. Willaime, S. L. Dudarev, and D. Simeone. Improving atomic displacement and replacement calculations with physically realistic damage models. *Nature Communications*, 9:1084, 2018.
10. M. J. Banisalman, S. Park, and T. Oda. Evaluation of the threshold displacement energy in tungsten by molecular dynamics calculations. *Journal of Nuclear Materials*, 495:277–284, 2017.
11. W. Setyawan, G. Nandipati, K. J. Roche, H. L. Heinisch, B. D. Wirth, and R. J. Kurtz. Displacement cascades and defects annealing in tungsten, part i: Defect database from molecular dynamics simulations. *Journal of Nuclear Materials*, 462:329–337, 2015.
12. D. J. Sprouster, T. Koyanagi, E. Dooryhee, S. K. Ghose, Y. Katoh, and L. E. Ecker. Pair distribution function analysis of neutron-irradiated silicon carbide. *Journal of Nuclear Materials*, 527:151798, 2019.