



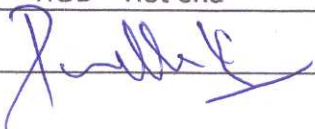


	BOROSIL RENEWABLES LIMITED	DOC. NO: ROM/L4/009
		ISSUE NO. / DATE: 01/08.04.2026
	INSPECTION PLAN FOR ROLLER	REV. NO: 00
		REV. DATE: --

A	POST-LASER ENGRAVING INSPECTION				
#	Characteristics to be checked		Test Method / Measuring instrument	Specification	Remarks
1	Visual Inspection, Check for Any:	Damage mark	Visually	The roller face surface should be free from any line/damage/scratch /crack or other issues.	No presence of any line, scratch or damage
		Dent marks			
		Cracks			
		Visible lines			
		Other issues.			
2	Top Roller Ra	Matt	Surface roughness tester	8 – 9 μm (8.0 – 8.5 μm - roller dia. 270 & 340 mm) 8.5 – 9.0 μm - roller dia. 400 mm) (measurement purpose only)	$\lambda_c = 0.8$ & N = 5
		Matt-Matt	Surface roughness tester	9 $\pm$ 0.4 μm (measurement purpose only)	
3	Bottom Roller Ra	FX 52	Surface roughness tester	12 – 17 μm (measurement purpose only)	$\lambda_c = 0.8$ & N = 5
		Matt-Matt	Surface roughness tester	4.8 $\pm$ 0.4 μm (measurement purpose only)	
4	Depth of the pattern		Depth inspection equipment	100 μm (+10/-0 μm)	

Prepared By	Reviewed By	Approved By	1 Page of 4
Mr. Ripal Rana Sr. Executive	Mr. Prabhakar P HOD – Hot end	Mr. Ajay Singh Plant Head	
			

B PRE DISPATCH INSPECTION					
#	Characteristics to be checked		Test Method / Measuring instrument	Specification	Remarks
1	Roller Diameter		Vernier Caliper	SG#1: 260/270 ±6 mm SG#2: 340 ±6 mm SG#3: 400 ±6 mm	(Roller dia. for SG#1: fickert – 260, Rurex – 270)
2	Roller Face length		Measuring tape	SG#1: 2800 mm SG#2: 2800 mm SG#3: 3000 mm	
3	Visual Condition, Check for Any damage, Dent, Crack, visible lines.		Visually	No presence of any line, scratch or damage	
4	Top Roller Ra	Matt	Surface roughness tester	8 – 9 μm (8.0 – 8.5 μm - roller dia. 270 & 340 mm) 8.5 – 9.0 μm - roller dia. 400 mm)	λc = 0.8 & N = 5
		Matt-Matt	Surface roughness tester	9 ± 0.4 μm	λc = 0.8 & N = 5
5	Bottom Roller Ra	FX 52	Surface roughness tester	12 – 17 μm	λc = 0.8 & N = 5
		Matt-Matt	Surface roughness tester	4.8 ± 0.4 μm	λc = 0.8 & N = 5
6	Roller Run out		Run out gauge	< 0.1 mm	
7	DU shaft/journal roughness		Surface roughness tester	< 0.4 μm	λc = 2.5 & N = 2
8	DU Shaft diameter (for 340 mm & 400 mm Roller)		Vernier Caliper	249.93 to 250.00 mm	
9	DU Shaft diameter (for 260 mm & 270 mm Roller)		Vernier Caliper	209.93 to 210.00 mm	
10	The DU shaft mounting position		Visually	Should be perfectly round fit.	No Oval
11	Circlip grooves		Visually	Should be damage free	
12	Tapped holes threads		Visually & physically	Should be damage free	

Prepared By	Reviewed By	Approved By	2 Page of 4
Mr. Ripal Rana Sr. Executive	Mr. Prabhakar P HOD – Hot end	Mr. Ajay Singh Plant Head	
			

	BOROSIL RENEWABLES LIMITED		DOC. NO: ROM/L4/009
	INSPECTION PLAN FOR ROLLER		ISSUE NO. / DATE: 01/08.04.2026
			REV. NO: 00
			REV. DATE: --

#	Characteristics to be checked	Test Method / Measuring instrument	Specification	Remarks
13	Depth of the pattern	Depth inspection equipment	100 μm (+10/-0 μm)	
14	Chrome coating layer thickness	Elcometer 456 Coating Thickness Gauge	60 μm (± 10 μm)	

Revision History:

Revision No.	Description of Change made	Date	Approved by
00	Initial release	04.08.2026	Plant Head

Prepared By	Reviewed By	Approved By	3 Page of 4
Mr. Ripal Rana Sr. Executive	Mr. Prabhakar P HOD – Hot end	Mr. Ajay Singh Plant Head	
	