



Housing Recovery and Reconstruction Platform-Nepal (HRRP)

Orientation Program for *Partner organizations*

on

Treatment Process: Timber & Bamboo

Organized by:

National Reconstruction Authority(NRA)


MOUD/District Project Implementation Unit (DLPIU)

Housing Recovery and Reconstruction Platform-Nepal (HRRP)

Lists of Hard wood & Soft Wood



HARD Wood	SOFT WOOD
Babul	Chir
Black Siris	Deodar
Dhaman	Jack
Indian Rose Wood(Shisam)	Mango
Jaman	Gobre Salla
Mesua	Simal
Oak	Uttis (Red)
Sain	Uttis (White)
Sal	
Sandan	
Sisso	
Teak	
Khair	

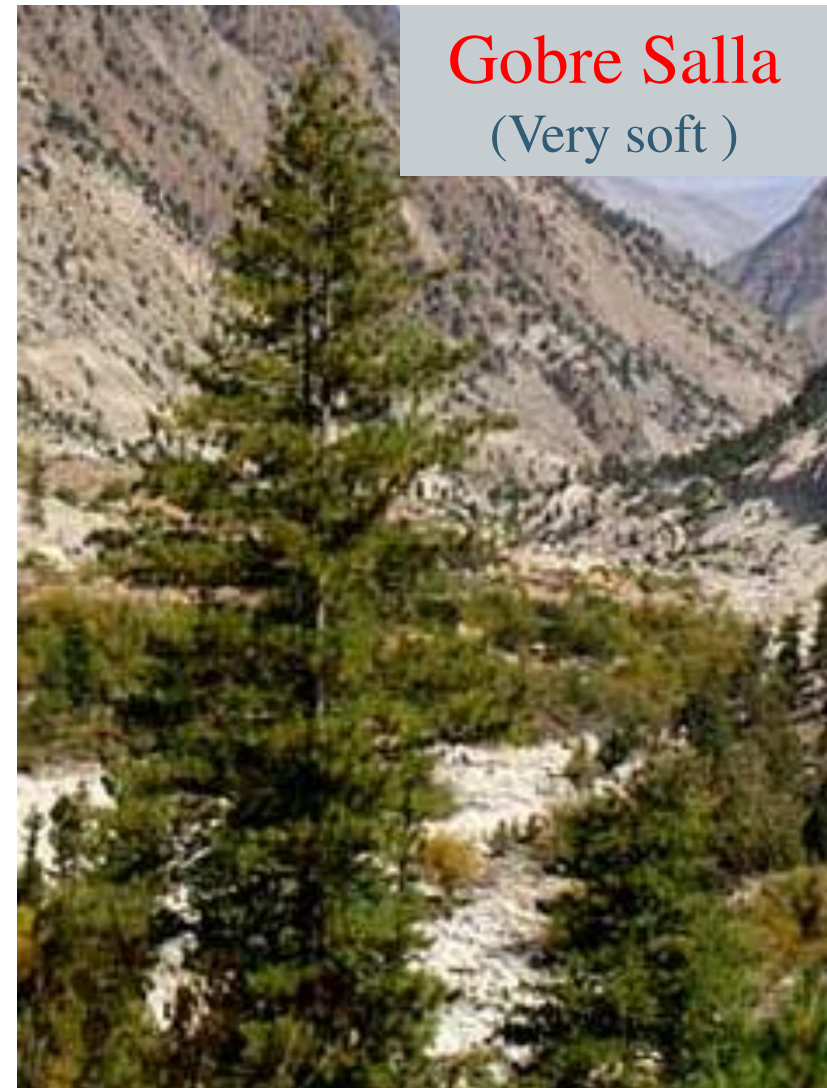

All measures that are taken to ensure a long life of wood

Treatment Process



- Let the wood dry for 3-4 month, in shed
- After that, Varnish Anti-termites(Terminator, Borax etc.) chemical on the wood

Varnishing Method as follows:

- Clean surface of wood
- Varnish one layer anti-termites on the surface.
(For this brush and soft cloth can be used)
- After that Leave the wood for 6-8 hours

(Rs. 300 –400 Per
liter)



Treatment Process Contd.



- After that apply water proof layer of mix. of bitumen & Kerosene. For this boil the bitumen and mix it with Kerosene. Ratio of bitumen and kerosene is 2:1. Put bitumen on Kerosene but never pour Kerosene in bitumen.

Rs. 75-80 Per
liter



Rs.300-400 per
liter



Rs.300-400 per
liter



- Liquid bitumen also available in market

Or

Use black Japan Paint

Normally in two storey residential building it cost roughly 10000 for timber treatment

Treatment Process Contd.



Stone Pad Base of the Timber Post



Bamboo Treatment



- At least three-years old before harvesting.
- Harvest at the beginning of dry Season
- Leave culms standing four to eight weeks in the groves, propped on stakes or rocks, with branches and leaves uncut so as to increase evaporation surface and diminish insect entry points offered by freshly cut skin

Some of the treatment methods

■ Water Leaching method:

Put bamboo completely under water, weighted down in water, preferably in a in running water than Stagnant water .



Reference NBC 204

Bamboo Treatment Contd.



- White Wash and Other Coatings:

- Tar coating
- Lime wash coating

Note: these are effective only to the extent that they gave continuous coating at cut surfaces, exposed internodes, abrasion and slits.

Bamboo Treatment Contd.

■ Boric-Borax Solution

- Place the bamboo against wall & insert the iron rod punch holes through the nodes. Make sure the last nodes is not punctured.



- Prepare Boric-Borax Solution or Tim-bor Solution

- *(Normally Mix ratio Boric Acid and Borax is 1:1.5 with water for Boric -Solution)*
- *Mix 1 bag of Tim-bor (25kg) with 225 litres of water for tim bar solution.*



Bamboo Treatment Contd.

- Fill the bamboo with this Solution by arranging bamboo in vertical position and allow the soak for two weeks.
- Or
- Add Borate Solution to water tight pool and keep the culms submerged by placing weights on top of the poles for two weeks.
- Remove all solution from poles and allow the Bamboo to dry on Prone Position for 4-6 weeks



Thank You!