Abstract

1   Experimental activity

1.1   Injection molding: sample evaluation

Different speciments of unknown polymeric materials have been analysed and identified. They have been produced by injection molding according to specific standards (ISO and ASTM):

- ISO 10.0 × 4.0 × 172 (mm);

- ASTM 12.7 × 3.3 × 165 (mm);

Size of all speciments and the mold cavity have been measured through a caliper in order to evaluate the shrinkage after the process according to Equation 1.

$$Shrinkage = \frac{\Delta x}{x_0} \tag{1}$$

Where Δx is the difference between the initial and final dimension (lenght, width and thickness) and x_0 is the initial dimension (lenght, width and thickness).
ASTM samples (with sprue and bar) have been weighted through the balance METTLER PM 4600 in order to compare the total weight and polymer density (taken from literature [1]).

2   Results and discussion

2.1   Injection molding: sample evaluation

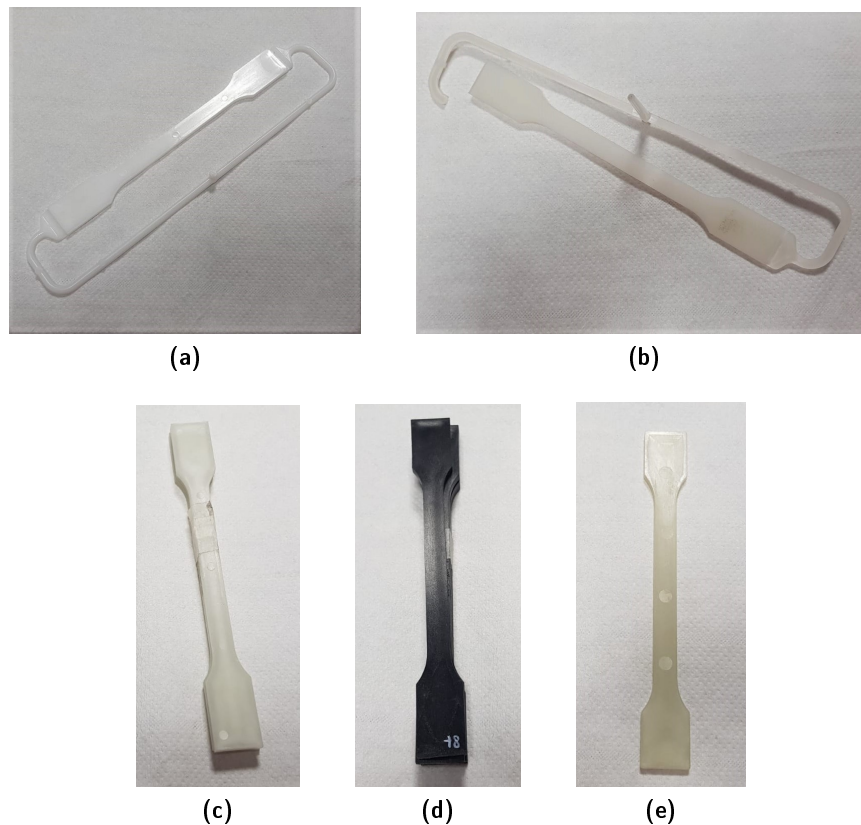ISO speciments are reported in Figure 1.

Figure 1: ISO samples: a) POM; b) PA11; c) PP-GF30; d) PP-GF35; e) PA6-GF50.

In Table 1 different types of ISO speciments are classified with their sizes.

Table 1: ISO speciments and characteristics.

Figure	Material	Size (mm)	Description
a	POM	9.74 × 3.94 × 167.06	white and presence of cold junction
b	PA11	9.86 × 4.05 × 168.98	opaque and white
c	PP-GF30	9.88 × 4.00 × 172.11	white and stiff
d	PP-GF35	9.80 × 4.00 × 171.86	black and stiff
e	PA6-GF50	9.99 × 3.98 × 154.71	very stiff

In Table 2 the values of the shrinkage of ISO samples are reported.
From Table 2 it can be noticed that in reinforced polymers the shrinkage is very small, almost negligible. The presence of glass fibers gives to polymers better dimensional stability during cooling.
ASTM speciments are reported in Figure 2.
In Table 3 different types of ASTM speciments are classified with their sizes.

In Table 4 the values of the shrinkage of ASTM samples are reported.
From Table 4 it can be observed that semycristalline polymers (such as PP, HDPE, PA11) have higher values of shrinkage respect to amourphous polymers (such ABS and COC). Amorphous polymers have random arrangement of molecules that produces little volume changes thus lower shrinkage. The higher values of longitudinal shrinkage in semycristalline polymers are partially compensated by the increase of the thickness (negative values of thickness shrinkage).
In Table 5 weights and densities of ASTM samples are reported.
For PE/PP blend it has been considered a blend constituted by PE/PP 50%. From Table 5 it can be

Table 2: Shrinkage of ISO samples.

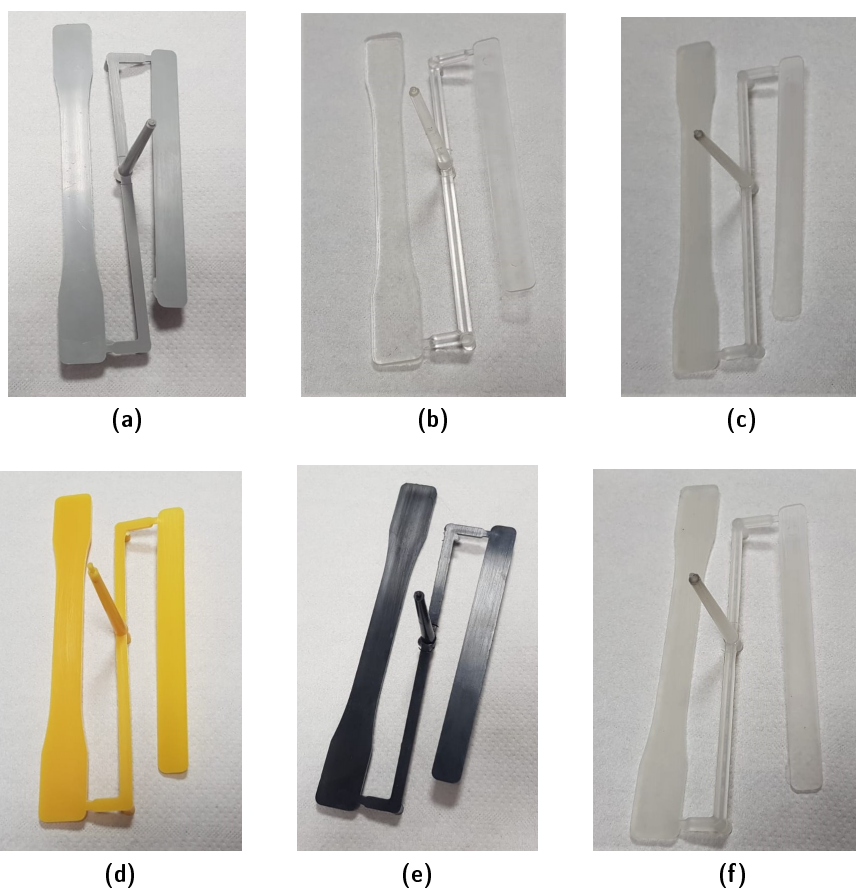| Samples	Longitudinal shrinkage	Transversal shrinkage	Thickness
POM	0.028	0.026	0.015
PA11	0.017	0.014	−0.012
PP-GF30	0	0.012	0
PP-GF35	0.001	0.020	0

Figure 2: ASTM samples: a) ABS; b) COC; c) PP; d) HDPE; e) PE/PP blend; f) PA11.

Table 3: ASTM speciments and characteristics.

Figure	Material	Weight (g)	Size (mm)	Description
a	ABS	14.78	$12.77 \times 3.27 \times 163.55$	grey and flexible
b	COC	14.07	$12.64 \times 3.30 \times 164.04$	transparent and glassy
c	PP	12.28	$12.6 \times 3.35 \times 162.29$	opaque and flexible
d	HDPE	12.73	$12.54 \times 3.33 \times 160.0$	yellow and very flexible
e	PE/PP blend	13.30	$12.66 \times 3.31 \times 161.58$	matt black and flexible
f	PA11	14.00	$12.6 \times 3.35 \times 162.29$	very similar to PP

Table 4: Shrinkage of ASTM samples.

Samples	Longitudinal shrinkage	Transversal shrinkage	Thickness
ABS	0.009	−0.006	0.009
COC	0.006	0.005	0
PP	0.016	0.003	−0.015
HDPE	0.030	0.013	−0.009
PE/PP blend	0.021	0.002	−0.003
PA11	0.016	0.003	−0.015

Table 5: Weight and density of ASTM samples.

Samples	Weight (g)	Density (g/cm^3)
ABS	14.78	$1.04 - 1.12$
COC	14.07	1.02
PP	12.28	$0.85 - 0.94$
HDPE	12.73	$0.93 - 0.97$
PE/PP blend	13.3	$0.86 - 0.95$
PA11	14.00	1.04

noticed that, for the same volume, weights of samples are in accordance with values of densities taken from literature.

3   Introduction

4   Experimental activity

4.1   Compounding (Internal Mixer)

The process has been carried out with the instrument Thermo Haake Rheomix 600.
The processing parameters used are the following:

- Temperature T = 200°C

- time t = 10 min

- Rotation speed ω = 50 rpm

The sample used has the same composition as Plate 1 sample with a mass of 32.05 g.

4.2   Compression molding

Prepared amount of polypropylene mixture has been used for compression molding process. A press by Carver has been used, as illustrated in Figure **??**.
The material to be pressed is put between two stainless steel plates, one having a frame of 12 × 12 mm^2 in order to produce a square plate of some mm of thickness. To avoid any adhesion with the plates, that are used to evenly distribute the pressure and to confine the melt (since the press is able to provide heat), two Mylar$^®$ foils have been put in between the steel and the material. The press has been set to produce a pressure of 8 tons, equivalent to 5.45 MPa, in the frame. The material has undergone an heat treatment under this pressure of 200°C for 10 minutes. After this, the press has been cooled with water circulating in a refrigerating circuit inside of it and the molded piece extracted. Produced plate is then visually analyzed and weighted in order to estimate weight losses.

Figure 3: Carver press for compression molding.

4.2.1 Production of dumbbell specimens

After the analysis of the plate, this has been cut to obtain ISO 527-1BA shaped specimens, that are used in another laboratory activity.

5   Results and discussion

5.1   Compression molding

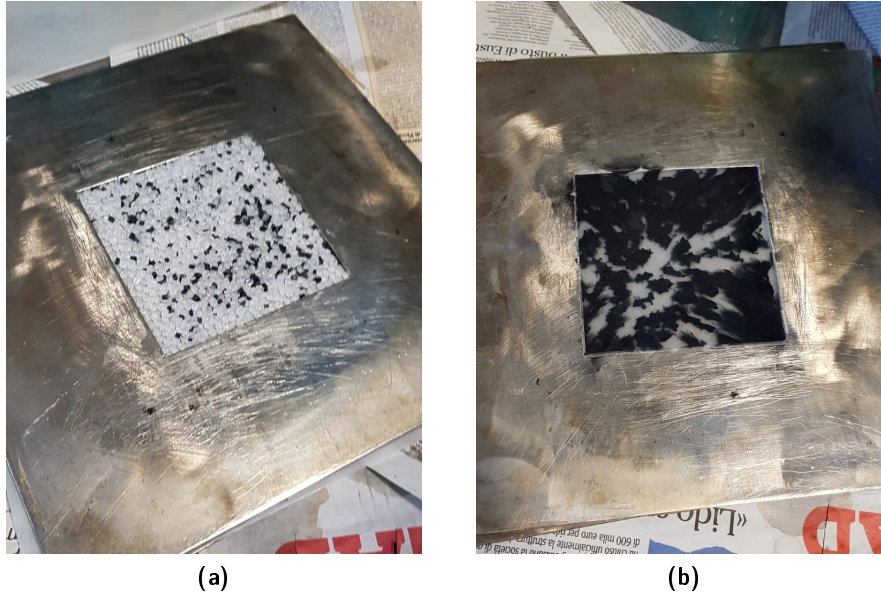The mold before and after pressing is reported in Figure **??**.

Figure 4: Mold (a) before and (b) after compression.

The produced plate after manual mixing is illustrated in Figure **??**.
As it can be easily noted, the distribution of black PP in the white one is absolutely non-homogeneous, typical consequence of a manual mixing of the pellets (without any homogenization mixing in between). The other evident property of the pressed plate is the flash of melt outside of the mold: this is due to the too high amount of polymer inserted in the mold. The weights of the product before and after compression are reported in Table **??**.

Figure 5: Plate produced in compression molding.

Table 6: Mass of the sample before and after pressing.

Mixture mass (g)	Plate mass (g)	Variation (%)
34.00	32.50	−4.41

5.1.1 Production of dumbbell specimens

In Figure **??** the dumbbell specimens produced are displayed.

Figure 6: Produced specimens from compression molding plate.

As it can be seen, these specimens are characterized by low isotropy and homogeneity of the mixture. This will be a probable issue when mechanically testing and in resistance to flame propagation. Since the flame retardant is a weakener of strength (it introduces organics with poor adhesion and thus stress intensifiers), these specimens may have higher deformation at break than the more homogeneous ones produced in melt compounding.

References

[1] Polymer handbook, J. Brandrup, E.H. Immergut, fourth edition, Wiley 2003.