

SVENSK STANDARD

SS-EN 10244-2:2023

Tråd och trådprodukter av stål - Beläggning av icke-järnmetall - Del 2: Beläggning av zink eller zinklegeringar

Steel wire and wire products – Non-ferrous metallic coatings on steel wire – Part 2: Zinc or zinc alloy coatings



Sis Svenska
Institutet för
Standarder

Språk: engelska/English

Utgåva: 3

SIS single user license: Ubiverse AB, Ordered by:
javier@ubillos.org. Date: 2024-05-22



Den här standarden kan hjälpa dig att effektivisera och kvalitetssäkra ditt arbete. SIS har fler tjänster att erbjuda dig för att underlätta tillämpningen av standarder i din verksamhet.

SIS Abonnemang

Snabb och enkel åtkomst till gällande standard med SIS Abonnemang, en prenumerationstjänst genom vilken din organisation får tillgång till all världens standarder, senaste uppdateringarna och där hela din organisation kan ta del av innehållet i prenumerationen.

Utbildning, event och publikationer

Vi erbjuder även utbildningar, rådgivning och event kring våra mest sålda standarder och frågor kopplade till utveckling av standarder. Vi ger också ut handböcker som underlättar ditt arbete med att använda en specifik standard.

Vill du delta i ett standardiseringsprojekt?

Genom att delta som expert i någon av SIS 300 tekniska kommittéer inom CEN (europeisk standardisering) och/eller ISO (international standardisering) har du möjlighet att påverka standardiseringsarbetet i frågor som är viktiga för din organisation. Välkommen att kontakta SIS för att få veta mer!

Kontakt

Skriv till kundservice@sis.se, besök sis.se eller ring 08 - 555 523 10

© Copyright/Upphovsrätten till denna produkt tillhör Svenska institutet för standarder, Stockholm, Sverige. Upphovsrätten och användningen av denna produkt regleras i slutanvändarlicensen som återfinns på sis.se/slutanvandarlicens och som du automatiskt blir bunden av när du använder produkten. För ordlista och förkortningar se sis.se/ordlista.

© Copyright Svenska institutet för standarder, Stockholm, Sweden. All rights reserved. The copyright and use of this product is governed by the end-user licence agreement which you automatically will be bound to when using the product. You will find the licence at sis.se/enduserlicenseagreement.

Upplysningar om sakinnehållet i standarden lämnas av Svenska institutet för standarder, telefon 08 - 555 520 00. Standarder kan beställas hos SIS som även lämnar allmänna upplysningar om svensk och utländsk standard.

Standarden är framtagen av kommittén för Rostfria stål och trådprodukter, SIS/TK 135.

Har du synpunkter på innehållet i den här standarden, vill du delta i ett kommande revideringsarbete eller vara med och ta fram andra standarder inom området? Gå in på www.sis.se - där hittar du mer information.



Europastandarden EN 10244-2:2023 gäller som svensk standard. Detta dokument innehåller den officiella engelska versionen av 10244-2:2023.

Denna standard ersätter SS-EN 10244-2:2009, utgåva 2.

The European Standard EN 10244-2:2023 has the status of a Swedish Standard. This document contains the official version of EN 10244-2:2023.

This standard supersedes the SS-EN 10244-2:2009, edition 2.



LÄSANVISNINGAR FÖR STANDARDER

I dessa anvisningar behandlas huvudprinciperna för hur regler och ytter begränsningar anges i standardiseringsprodukter.

Krav

Ett krav är ett uttryck i ett dokuments innehåll som anger objektivt verifierbara kriterier som ska uppfyllas och från vilka ingen avvikelse tillåts om efterlevnad av dokumentet ska kunna åberopas. Krav uttrycks med hjälpverbet **ska** (eller **ska inte** för förbud).

Rekommendation

En rekommendation är ett uttryck i ett dokuments innehåll som anger en valmöjlighet eller ett tillvägagångssätt som bedöms vara särskilt lämpligt utan att nödvändigtvis nämna eller utesluta andra. Rekommendationer uttrycks med hjälpverbet **bör** (eller **bör inte** för avrådanden).

Instruktion

Instruktioner anges i imperativ form och används för att ange hur något görs eller utförs. De kan underordnas en annan regel, såsom ett krav eller en rekommendation. De kan även användas självständigt, och är då att betrakta som krav.

Förklaring

En förklaring är ett uttryck i ett dokuments innehåll som förmedlar information. En förklaring kan uttrycka tillåtelse, möjlighet eller förmåga. Tillåtelse uttrycks med hjälpverbet **får**. Inom standardiseringen saknas rekommenderad nekande motsats till hjälpverbet **får**, förbud uttrycks med **ska inte** enligt reglerna för krav. Möjlighet och förmåga uttrycks med hjälpverbet **kan** (eller motsatsen **kan inte**).

READING INSTRUCTIONS FOR STANDARDS

These instructions cover the main principles for the use of provisions and external constraints in standardization deliverables.

Requirement

A requirement is an expression, in the content of a document, that conveys objectively verifiable criteria to be fulfilled, and from which no deviation is permitted if conformance with the document is to be claimed. Requirements are expressed by the auxiliary **shall** (or **shall not** for prohibition).

Recommendation

A recommendation is an expression, in the content of a document, that conveys a suggested possible choice or course of action deemed to be particularly suitable, without necessarily mentioning or excluding others. Recommendations are expressed by the auxiliary **should** (or **should not** for dissuasion).

Instruction

An instruction is expressed in the imperative mood and is used in order to convey an action to be performed. It can be subordinated to another provision, such as a requirement or a recommendation. It can also be used independently and is then to be regarded as a requirement.

Statement

A statement is an expression, in the content of a document, that conveys information. A statement can express permission, possibility or capability. Permission is expressed by the auxiliary **may**. There is no recommended opposite expression for the auxiliary **may** in standardization, prohibition is expressed by the use of **shall not** in accordance with the rules for requirements. Possibility and capability are expressed by the auxiliary **can** (its opposite being **cannot**).

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 10244-2

June 2023

ICS 25.220.40; 77.140.65

Supersedes EN 10244-2:2009

English Version

Steel wire and wire products - Non-ferrous metallic
coatings on steel wire - Part 2: Zinc or zinc alloy coatings

Fils et produits tréfilés en acier - Revêtements
métalliques non ferreux sur fils d'acier - Partie 2 :
Revêtement de zinc ou d'alliage de zinc

Stahldraht und Drahterzeugnisse - Überzüge aus
Nichteisenmetall auf Stahldraht - Teil 2: Überzüge aus
Zink oder Zinklegierungen

This European Standard was approved by CEN on 26 May 2023.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

SS-EN 10244-2:2023 (en)**Contents**

	Page
European foreword	3
1 Scope.....	4
2 Normative references.....	4
3 Terms and definitions	4
4 Coating requirements.....	4
4.1 Requirements for the coatings material.....	4
4.2 Requirements relating to coating on the wire.....	5
4.2.1 Coating mass	5
4.2.2 Appearance of coating.....	7
4.2.3 Dipping test.....	7
4.2.4 Special finishes.....	7
4.2.5 Adherence of coating	8
5 Test conditions.....	10
5.1 Selection of samples.....	10
5.2 Determination of mass of coating	10
5.2.1 General.....	10
5.2.2 Gravimetric method.....	10
5.2.3 Gaseous volumetric method.....	11
5.3 Dipping test.....	16
5.3.1 Principle	16
5.3.2 Reagents	16
5.3.3 Preparation of test piece	16
5.3.4 Performing of the test.....	16
5.3.5 Interpretation of results.....	17
Bibliography.....	18

European foreword

This document (EN 10244-2:2023) has been prepared by Technical Committee CEN/TC 459 "ECIIS - European Committee for Iron and Steel Standardization"¹, the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2023, and conflicting national standards shall be withdrawn at the latest by December 2023.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 10244-2:2009.

In comparison with the previous edition, the following technical modifications have been made:

- the reference towards ASTM B750 for Zn-Alu alloys has been changed to ASTM B997;
- dipping test better specified for Zinc-Alu alloy coatings (see Table 3).

This European Standard series for non-ferrous metallic coating on steel wire is made up of the following parts:

- *Part 1: General principles*
- *Part 2: Zinc or zinc alloy coatings*
- *Part 3: Aluminium coatings*
- *Part 4: Tin coatings*
- *Part 5: Nickel coatings*
- *Part 6: Copper, bronze or brass coatings*

Any feedback and questions on this document should be directed to the users' national standards body. A complete listing of these bodies can be found on the CEN website.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and the United Kingdom.

¹ Through its sub-committee SC 6 "Wire rod and wires" (secretariat: AFNOR).

SS-EN 10244-2:2023 (en)

1 Scope

This document specifies the requirement for coating mass, other properties and testing of zinc and zinc alloy coatings on steel wire and steel wire products of circular or other section.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 1179, *Zinc and zinc alloys — Primary zinc*

EN 10218-1, *Steel wire and wire products — General — Part 1: Test methods*

EN 10244-1, *Steel wire and wire products — Non-ferrous metallic coatings on steel wire — Part 1: General principles*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp/>

3.1

wire with zinc or zinc alloy coating

wire to which zinc or zinc alloy coating has first been applied to protect it against corrosion

Note 1 to entry: The coating method may be hot dipping in a bath of molten zinc or by means of an aqueous solution of suitable electrolyte. In the hot dipping process wiping media may be used to modify the mass of coating.

3.2

zinc or zinc alloy coating

zinc to which other elements are deliberately added in order to obtain particular characteristics

Note 1 to entry: In all cases, the quantity of zinc in the alloy shall be minimum 50 %. The most common alloy elements are aluminium, tin and nickel, but other elements may also be considered.

3.3

mass of coating

mass of zinc per unit of surface area expressed in grams per square metre of surface of bare wire

4 Coating requirements

4.1 Requirements for the coatings material

The zinc or zinc alloy used for the coating shall comply with the standard EN 1179. For zinc-alloy grades not mentioned in the EN, the alloy shall be specified at the time of enquiry and order. For Zn-Al alloys, reference is made to ASTM B997.

The ingot of the material used for the zinc coating shall be of minimum 99,95 % purity (according to Z3 of EN 1179) unless otherwise stated in the relevant product standard or other specification in the order. Coatings applied by electrolysis shall contain a minimum of 99 % zinc.

4.2 Requirements relating to coating on the wire

4.2.1 Coating mass

The minimum mass of zinc per unit of surface area of the wire shall comply with the requirements of Table 1.

Table 1 — Mass requirements for a coating of Zn

Diameter d mm	Classes ^a					
	A g/m ²	AB g/m ²	B g/m ²	C g/m ²	D g/m ²	A x 3 ^b g/m ²
0,15 ≤ d < 0,20	—	—	15	—	10	—
0,20 ≤ d < 0,25	30	20	20	20	15	—
0,25 ≤ d < 0,32	45	30	30	25	15	—
0,32 ≤ d < 0,40	60	30	30	25	15	—
0,40 ≤ d < 0,50	85	55	40	30	15	—
0,50 ≤ d < 0,60	100	70	50	35	20	—
0,60 ≤ d < 0,70	115	80	60	40	20	—
0,70 ≤ d < 0,80	130	90	60	45	20	—
0,80 ≤ d < 0,90	145	100	70	50	20	—
0,90 ≤ d < 1,00	155	110	70	55	25	—
1,00 ≤ d < 1,20	165	115	80	60	25	—
1,20 ≤ d < 1,40	180	125	90	65	25	540
1,40 ≤ d < 1,65	195	135	100	70	30	585
1,65 ≤ d < 1,85	205	145	100	75	30	615
1,85 ≤ d < 2,15	215	155	115	80	40	645
2,15 ≤ d < 2,50	230	170	125	85	45	690
2,50 ≤ d < 2,80	245	185	125	95	45	735
2,80 ≤ d < 3,20	255	195	135	100	50	765
3,20 ≤ d < 3,80	265	210	135	105	60	795
3,80 ≤ d < 4,40	275	220	135	110	60	825
4,40 ≤ d < 5,20	280	220	150	110	70	840
5,20 ≤ d < 8,20	290	—	—	110	80	870
8,20 ≤ d ≤ 10,00	300	—	—	110	80	900

^a The coating class with a designation starting with A relates to thick coatings (generally final coating). Designations ending in B relate to classes usually but not always obtained by (zinc coating) and subsequent drawing. Classes C and D are standard classes for low mass coating which are usually produced, but not exclusively produced, by hot zinc dipping and then wiping.

^b A x 3 relates to very high mass requirement three times higher than class A. Other multiples of Class A are possible and these classes will be identified in the same way, e.g. A x 4.

SS-EN 10244-2:2023 (en)

If no class of zinc coating or no coating mass is specified in the coating it shall be called "regular coating". Such a coating shall be not less than 1 g zinc mass per Kg of zinc coated wire (equivalent to the coating mass in g/m² not less than two times the wire diameter expressed in mm).

The requirements for zinc-aluminium coatings are given in Table 2.

Table 2 — Mass requirements for a coating of ZnAl alloy

Diameter mm	Mass of coating^a g/m²			
	A	AB	B	E^b
0,20 ≤ d < 0,25	—	20	20	
0,25 ≤ d < 0,40	—	30	30	
0,40 ≤ d < 0,50	85	55	40	
0,50 ≤ d < 0,60	100	70	50	
0,60 ≤ d < 0,70	115	80	60	40
0,70 ≤ d < 0,80	130	90	60	
0,80 ≤ d < 0,90	145	100	70	
0,90 ≤ d < 1,00	155	110	70	
1,00 ≤ d < 1,20	165	115	80	
1,20 ≤ d < 1,40	180	125	90	
1,40 ≤ d < 1,65	195	135	100	
1,65 < d < 1,85	205	145	100	
1,85 ≤ d < 2,15	215	155	115	
2,15 ≤ d < 2,50	230	170	125	
2,50 ≤ d < 2,80	245	185	125	
2,80 ≤ d < 3,20	255	195	135	60
3,20 ≤ d < 3,80	265	210	135	
3,80 ≤ d < 4,40	275	220	135	
4,40 ≤ d < 5,20	280	220	150	
5,20 ≤ d < 8,20	290	—	—	
8,20 ≤ d < 10,00	300	—	—	

^a The coating class with a designation starting with A relates to thick coatings (generally final coating). Designations ending in B relate to classes usually but not always obtained by (zinc coating) and subsequent drawing.

^b The corrosion resistance of this class E shall be at least equivalent of these from a zinc coating according to Table 1 class B.

For other zinc alloy coatings, the manufacturer and supplier shall agree on the required coating mass.

4.2.2 Appearance of coating

The coating applied to the wire shall be reasonably smooth and as evenly distributed as industrial technology allows and not show discontinuities such as bare patches, dross contamination, etc.

NOTE The zinc-aluminium alloy might show difference in colour and become darker with time. This does not affect the corrosion protection performance.

4.2.3 Dipping test

When specified, the dipping (immersion) test shall be carried out according to the procedure detailed in 5.3. However, it should be pointed out that there is no correlation between the number of dips and the mass of the coating and the result is influenced as much by the conditions of manufacture of the coating as by the uniformity of the coating.

Table 3 gives the minimum number of immersions for coatings of classes A and AB.

The dipping test does not apply to class B, C and D and E.

Table 3 — Minimum number of dips

Nominal diameter mm	Class A of coating		Class AB of coating	
	Number of dips		Number of dips	
	of 1 min ^a	of 1/2 min ^b	of 1 min ^a	of 1/2 min ^b
0,40 ≤ $d < 0,60$	—	1	—	—
0,60 ≤ $d < 0,90$	1	—	—	1
0,90 ≤ $d < 1,00$	1	1	—	1
1,00 ≤ $d < 1,40$	1	1	1	—
1,40 ≤ $d < 1,65$	2	—	1	—
1,65 ≤ $d < 1,85$	2	—	1	—
1,85 ≤ $d < 2,15$	2	—	1	1
2,15 ≤ $d < 2,80$	2	1	1	1
2,80 ≤ $d < 4,40$	3	—	2	—
4,40 ≤ $d < 5,20$	3	1	2	—
5,20 ≤ $d < 8,20$	3	1	—	—
8,20 ≤ $d < 10,00$	4	—	—	—

^a For Zinc-Alu alloy coatings, one dip equals 45 s instead of 1 min.
^b For Zinc-Alu alloy coatings, one dip equals 22 s instead of 1/2 min.

4.2.4 Special finishes

If drawing after galvanizing is required, it shall be stipulated at the time of enquiry and order or in the appropriate product standard. The same also applies for other special finishes, such as wax coating, a polished surface or an exceptionally smooth surface.

SS-EN 10244-2:2023 (en)


4.2.5 Adherence of coating

4.2.5.1 During the test carried out in accordance with EN 10218-1, the coating shall adhere to the steel when subjected to the conditions of wrapping test for adherence. It shall not crack or split to such an extent that slivers of coating can be removed by simply rubbing with the bare fingers. The loosening or detachment during testing of small particles of zinc resulting from mechanical polishing of the surface of the zinc or zinc alloy coating shall not be considered to be a cause for rejection.


The wrapping test is defined in ISO 7802 and specific requirements for wires are defined in EN 10244-1: Adherence test.

4.2.5.2 To assess the adherence of the coating as may be specified in the relevant product standard or for evaluating different conditions of manufacturing, the following procedure may be applied.

Coil the wire around its own diameter and compare to the reference chart (see Figure 1). Allocate a value of 1 to 5 to the quality of adherence of the coating in accordance with the reference chart in Figure 1.

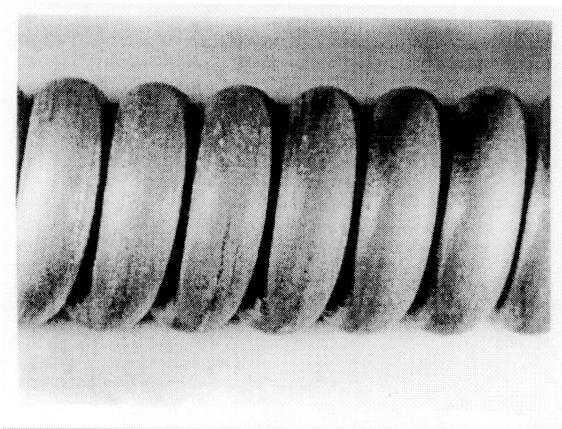


1

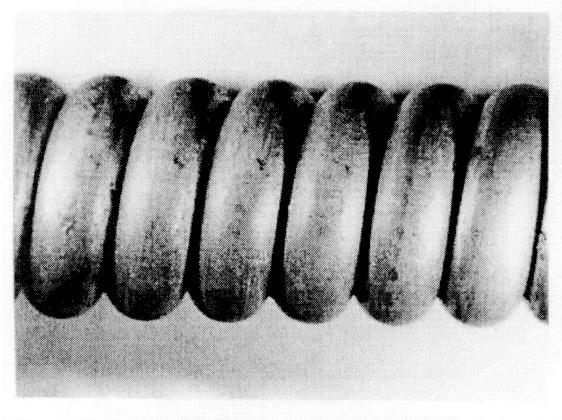


2



3

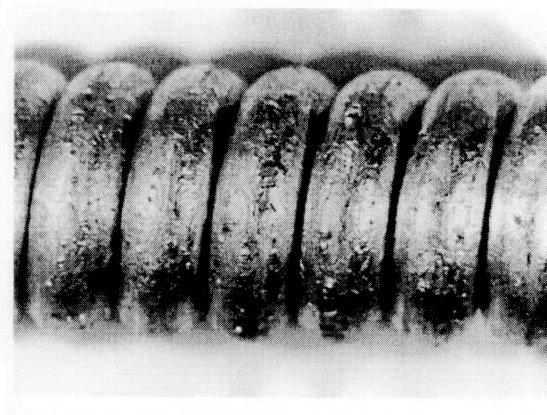

4

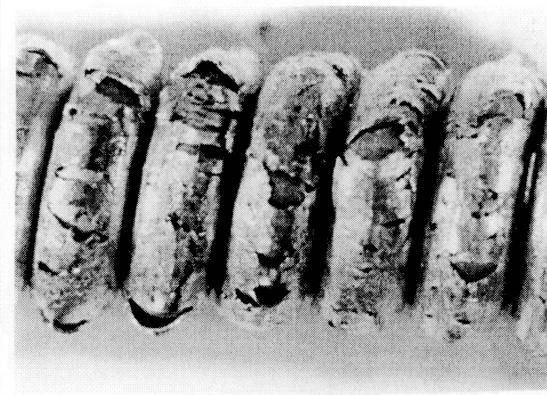

5

Key

Descending scale based on quality of adherence from 1 (highest quality) to 5 (lowest quality) (see 4.2.5.2)

Figure 1 — Assessment of the adherence of the coating

SS-EN 10244-2:2023 (en)

5 Test conditions

5.1 Selection of samples

5.1.1 The number and the basis for the selection of test pieces shall be defined in the product standard. In the absence of such a standard, the manufacturer and purchaser shall agree between them on the degree of sampling.

5.1.2 When taking the samples, care shall be taken to avoid damaging the surface. Parts of the wire which are visibly damaged shall not be used.

5.1.3 A test piece of wire, which is of a suitable length for the specified tests shall be taken from one or both ends of each reel selected for sampling.

In the case of coated wire products, the product standard shall specify the length of the samples to be taken.

5.2 Determination of mass of coating

5.2.1 General

In the case of wire with a zinc or zinc alloy coating, the mass of the coating shall be determined either by the gravimetric method or the volumetric method. The second offers an acceptable degree of accuracy and has the advantage of being quick. This is why it is the preferred method for routine testing of wire of all dimensions which can easily be fitted into the measuring equipment. In the event of any dispute, the gravimetric method shall be used as the reference test method.

The test methods in this standard do not necessarily include in detail all the precautions necessary to satisfy hygiene and safety requirements in the workplace, etc. Care should be taken to ensure that all necessary precautions are taken and procedures are implemented only by people who have received suitable training.

5.2.2 Gravimetric method

5.2.2.1 General

The method shall be applied in accordance with EN 10244-1 with the following additional requirements:

5.2.2.2 Reagents

The stripping solution shall be hydrochloric acid with a concentration of 1,13 g/ml to 1,19 g/ml by density to which an appropriate inhibitor is added. Dissolve 3,2 g of antimony chloride (SbCl_3) or 2 g antimony oxide (III) (Sb_2O_3) in 500 ml concentrated hydrochloric acid ($\rho = 1,190 \text{ g/ml}$). Dilute this solution with distilled water to 1 l. Hexamethylenetetramine ($\text{C}_6\text{H}_{12}\text{N}_4$), formaldehyde (HCHO) or any other suitable inhibitor may be used.

It is recommended that preference be given to inhibitors which do not contain antimony.

5.2.2.3 Calculation of mass of coating

The coating mass of zinc or zinc alloy shall be calculated according to the following formulae:

$$m_A = \frac{\Delta m}{A} \times 10^6 \quad (1)$$

where

A is the coated surface of the sample in mm² (surface of the stripped wire);

Δm is mass loss of the sample by chemical stripping in grams;

m_A is coating mass in g/m².

or

$$m_A = 1\,962 \times d \times \frac{\Delta m}{m_2} \quad (2)$$

where

m_2 is the mass of the sample after chemical stripping expressed in grams;

d is the diameter of (round) wire in mm;

Δm is mass loss of the sample by chemical stripping in grams;

m_A is the coating mass in g/m².

5.2.3 Gaseous volumetric method

5.2.3.1 Principle

The volumetric method for determining the mass of the coating depends on the property by which a metal dissolved in an acid releases a quantity of hydrogen proportional to the mass of metal dissolved, i.e. representing the chemical equivalent of the metal in question.

In the case of zinc, this relationship is very simple. For zinc alloys, each case shall be examined individually on the basis of the metals present in the zinc alloy. The method for zinc and the alloy zinc 95 % — Aluminium 5 % only is described in detail.

By measuring the volume of hydrogen released by dissolving the coating, the quantity of coating can be determined. By relating this result to the surface area of the test piece, measured once the coating has dissolved, the mass of the coating per unit area is obtained.

5.2.3.2 Reagents

Hydrochloric acid: The acid used to dissolve the coating is hydrochloric acid with a density between 1,13 g/ml and 1,19 g/ml.

NOTE The concentration of the acid can affect the result of the volumetric method; a powerful acid will produce slightly lower results.

Inhibitor: An inhibitor shall be added to the stripping solution to protect the steel base against dissolving. The inhibitors may be hexamethylene-tetramine ($C_6H_{12}N_4$), formaldehyde (HCHO) or any other suitable inhibitor.

SS-EN 10244-2:2023 (en)**5.2.3.3 Apparatus (see ISO 7989-2: Apparatus)**

The apparatus used is made up of the following items (see Figure 2):

- the tube shall be graduated in millimetres. The tube has a tap at each end;
- flask with an opening near the bottom, connected by rubber tube to the opening near the bottom of the graduated tube;
- container to hold the test piece once the zinc coating or zinc-alloy coating has been removed.


5.2.3.4 Test pieces

After carefully straightening out the wire samples, cut the test pieces accurately to a suitable length depending on the size of the tube, the diameter of the wire and the assumed mass of the coating. The lengths given in Table 4 are generally applicable for proper gas release. Different lengths may be necessary depending on the release of gas.

Table 4 — Recommended length of test pieces

Dimensions in millimetres

Diameter	Length of sample
$d < 1,00$	300
$1,00 \leq d < 1,50$	150
$1,50 \leq d < 3,00$	100
$3,00 \leq d \leq 5,00$	50

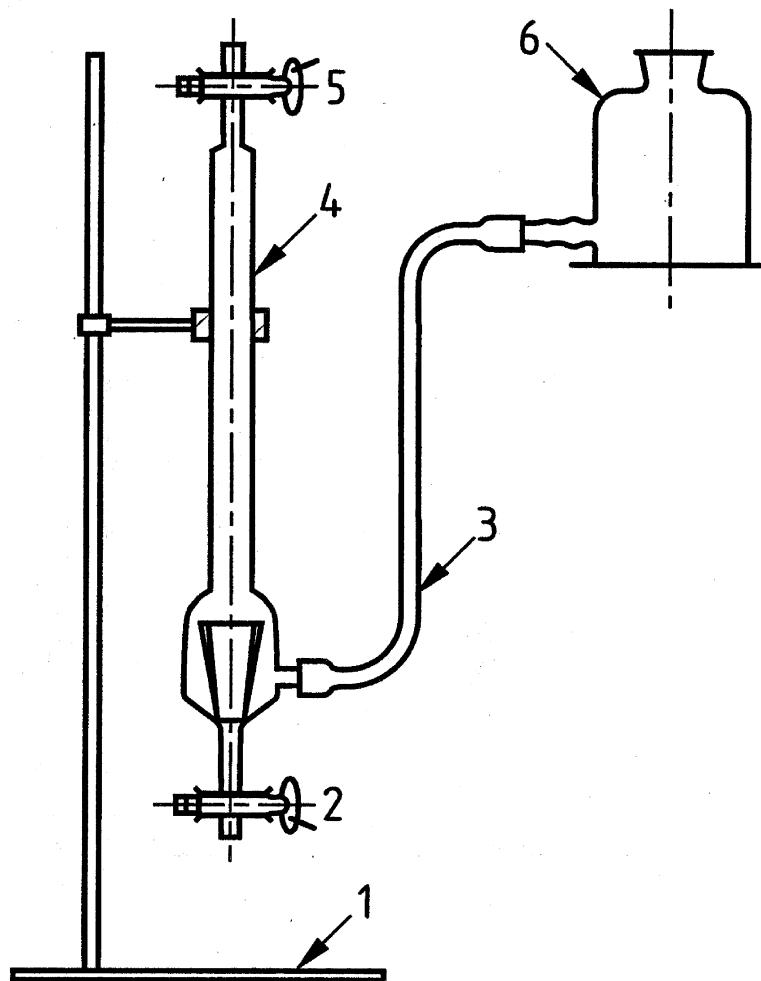**Key**

1	base	4	graduated tube
2	tap B	5	tap A
3	hose	6	flask

Figure 2 — Apparatus for the determination of the mass of coating by the gaseous volumetric method


5.2.3.5 Procedure

With tap B closed, fill the graduated tube and part of the flask with as reagent a hydrochloric acid solution containing a suitable inhibitor.


Raise the level of liquid in the graduated tube to just below A by raising the acid reservoir C. The levels in the tube and flask shall be identical (see Figure 3 a)).

After placing the test piece in the graduated tube through tap A, close tap A and hydrogen released by the action of the acid on the coating will accumulate in the upper part of the graduated tube.

SS-EN 10244-2:2023 (en)

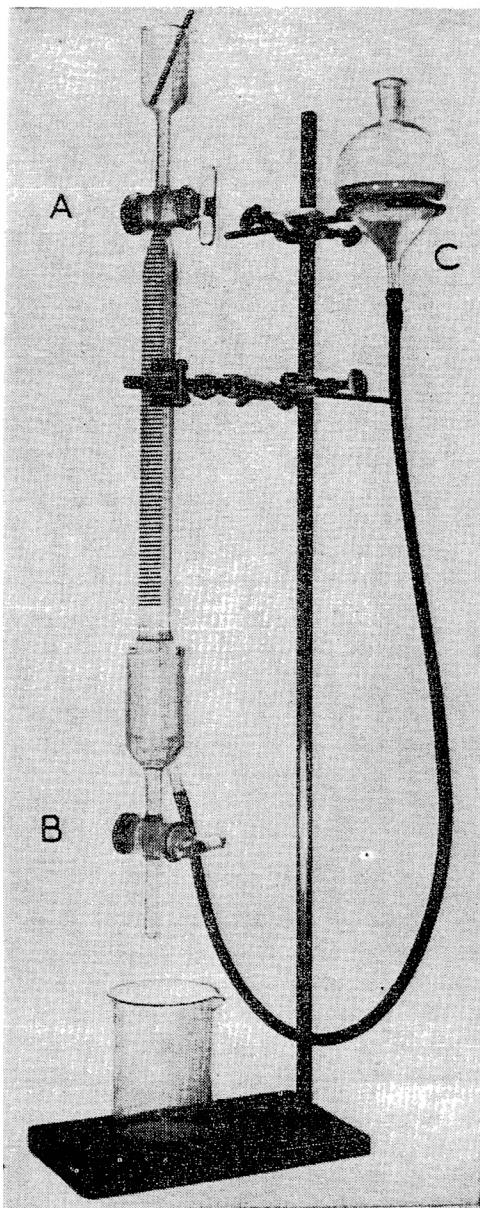

a) Arrangement of apparatus
at start of test

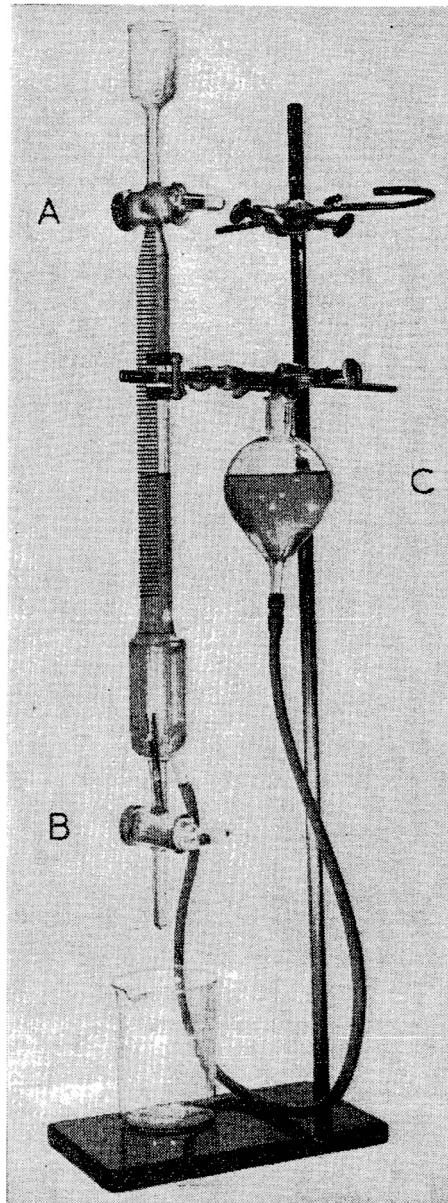

b) Arrangement of apparatus when
measuring volume of hydrogen released

Key

A tap A

B tap B

C acid reservoir

Figure 3 — Apparatus to determine mass of coating by gaseous volumetric method

When the release of hydrogen is completed, apart from a few small bubbles, lower the flask (see Figure 3 b)) in relation to the graduated tube in order to bring the levels of solution in the tube and flask to the same height. The position of the surface of the liquid in the tube then shows the volume of hydrogen released. The volume shall be read from the lower level of the liquid surface to ensure minimum error.

When the test is completed, open tap A and remove all the acid reagent from the tube, placing the flask on a table.

Open tap B so that the test piece can be removed from the tube and placed in the container. The test piece is then washed and carefully wiped before its diameter is measured.

The test shall be carried out on one test piece at a time and the temperature in the tube shall be maintained at $20\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$. The laboratory temperature shall be noted and when necessary a temperature correction shall be applied.

It is not recommended that the volumetric method be used for wire with a diameter greater than 5 mm.

5.2.3.6 Expression of results

The result is determined once the test piece has been tested. The mass of coating depends on the type of alloy. The volume of hydrogen released is directly related to the mass of zinc dissolved by the acid. For a non-alloy zinc coating, the mass of zinc coating per unit area, expressed in grams per square metre, is supplied by the formula:

$$m = \frac{2724 V}{\pi \cdot d \cdot l} \quad (3)$$

NOTE 1 mol of hydrogen equals 24,0 l of hydrogen, corresponding to 65,38 grams of zinc. A volume V of hydrogen expressed in ml corresponds to a mass "m" of zinc expressed in grams.

$$m = \frac{65,38 \cdot V}{24,0 \cdot 10^3} = 2,724 \cdot V \cdot 10^{-3} \quad (4)$$

The mass per unit surface (m_A) in g/m² equals

$$\begin{aligned} m_A &= \frac{2,724 \cdot V \cdot 10^{-3}}{\pi \cdot d \cdot l \cdot 10^{-6}} \text{ g/m}^2 \\ &= \frac{2724 \cdot V}{\pi \cdot d \cdot l} \end{aligned} \quad (5)$$

where

d is the diameter of the wire without coating (in mm);

l is the length of the test piece (in mm);

V is the volume of hydrogen released during each of the tests (in ml).

In the case of shaped wire, then $\pi \cdot d$ is replaced by the circumference of the shape; this is generally obtained from a sketch of the section of the wire.

If the temperature ($t\text{ }^{\circ}\text{C}$) is very different from $20\text{ }^{\circ}\text{C}$, a temperature correction shall be applied for the volume by multiplying the right side of the formula above by the factor:

$$\frac{293}{t + 273}$$

If the atmospheric pressure P is not between 987 mbar and 1 040 mbar, the same formula should be multiplied by:

$$\frac{P}{1,014}$$

SS-EN 10244-2:2023 (en)

In practice, tables can be used to read the mass of zinc per square metre of surface of uncoated wire, as a function of the diameter of the wire, the length of the test piece and the volume of hydrogen released.

In the case of the alloy Zn95Al 5, the mass (m_A) of the alloy is supplied by the formula:

$$m_A = \frac{2405 \cdot V}{\pi \cdot d \cdot l} \text{ g/m}^2 \quad (6)$$

This formula is only valid if the mean aluminium content is between 4,5 % and 5,5 %.

The formula above may be used for circular section wire. In the case of shaped wire, the factor $\pi \cdot d$ shall be replaced by the nominal circumference of the shape.

For other zinc alloys, the volumetric method may be applied in so far as a reliable relationship can be established between the gas released and the weight of the coating.

5.3 Dipping test

5.3.1 Principle

The test consists of immersing a wire sample for a given period once or several times consecutively in a saturated copper sulphate solution which gradually dissolves the zinc coating and reveals the defects in the continuity of this coating.

The dipping test is solely intended to reveal any significant eccentricity defect in the coating or any other significant uniformity defect which could exist even if the mass of zinc per unit of surface area complies with the mass requirements for the coating.

5.3.2 Reagents

The reagent used shall be a saturated copper sulphate solution prepared from copper sulphate crystals ($\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$) "in the pure for analysis state" in a proportion of 314 g of salts to 1 l of de-ionized water at a temperature of $20^\circ\text{C} \pm 2^\circ\text{C}$.

The solution shall be prepared completely from cold. The liquid shall under no circumstances be heated, even to complete the dissolving process. To prevent this operation taking too long, the procedure may be applied as follows: the salts to be dissolved are crushed then reduced bit by bit by successive amounts of the water used. Once the salts have dissolved completely, the various solutions which have been prepared separately are mixed together and stirred. A small quantity of salt shall remain undissolved at the bottom of the container as proof of the state of saturation.

The solution shall be neutralized using an excess of chemically pure copper oxide (1 g per litre of solution) and then the solution shall be left to rest for at least 24 h before decanting for use.

5.3.3 Preparation of test piece

The test piece shall consist of a piece of wire approximately 250 mm long, straightened by hand to a greater or lesser degree. This test piece shall be completely de-greased any suitable degreasing solvent. It is then rinsed in distilled water and wiped with a clean piece of cotton wool. After degreasing, the wire shall only be held at the end which is not to be dipped. In the case of a corroded wire or if other chemical substances remain present on the surface of the wire after degreasing (for example chromate or phosphates), the wire shall first be dipped in a 0,2 % sulphuric acid solution for 15 s and then rinsed.

5.3.4 Performing of the test

The test shall be performed in a glass container of at least 8 cm internal diameter. It is filled with the reagent, prepared as in 5.3.2, to a depth of at least 10 cm. During the test, the temperature shall be kept at $20^\circ\text{C} \pm 2^\circ\text{C}$. The real temperature shall be noted.

The test specimen shall be dipped in the reagent for half a minute if the required number of dips is only half a minute. In all other cases, the test sample shall be dipped in the solution for a period of one minute.

During the period of immersion, the test specimens shall be held vertically; the immersed part shall not touch the wall of the container and shall not be moved. After each dip, any deposited but not adhering copper shall be removed by slightly rubbing with cotton wool under running water.

This procedure shall be repeated with additional dips until the sample shows adherent coating of metallic copper for the first time or until the number of dips in Table 3 is reached, whichever is the smallest. After the last dip, the sample shall be rinsed again under running water and dried with cotton wool.

Where Table 3 prescribes a dip of half a minute the dip shall be done after execution of the prescribed number of one minute dips. The solution used shall be renewed whenever the series of tests carried out has resulted in dissolving a maximum of 5 g of zinc per litre of reagents. In order to save time, several test samples with a maximum of six may be dipped at the same time without touching each other.

5.3.5 Interpretation of results

The test sample shall satisfy the test if the number of dips without adherent copper is equal or larger than the prescribed number of dips in Table 3. Any deposit of metallic copper within 25 mm of the cut end shall be discarded.

In case of doubt about the adherence of the copper, the remaining zinc may be removed by dissolution in hydrochloric acid. If the copper is not adhering to the steel base but is sticking on top of the zinc surface it will be removed together with the zinc.

SS-EN 10244-2:2023 (en)

Bibliography

- [1] ISO 7802, *Metallic materials — Wire — Wrapping test*
- [2] ISO 7989-1, *Steel wire and wire products — Non-ferrous metallic coatings on steel wire — Part 1: General principles*
- [3] ISO 7989-2, *Steel wire and wire products — Non-ferrous metallic coatings on steel wire — Part 2: Zinc or zinc-alloy coating*
- [4] ASTM B997, *Standard Specification for Zinc-Aluminum Alloys in Ingot Form for Hot-Dip Coatings*

Anteckningar/Notes



Globala lösningar för ett smartare samhälle

SIS är en del av ISO och CEN som är nätverk av experter som arbetar med att skapa internationella standarder. Hos oss kan aktörer ta initiativ och samverka för best practice som främjar Sveriges konkurrenskraft och ger smart och hållbar samhällsutveckling. SIS samverkar med alla delar av det svenska samhället, som till exempel industri, akademi, offentlig sektor och frivilligorganisationer.

SIS projektleder det svenska arbetet med att ta fram standarder. Vi verkar för ökat svenskt inflytande i internationella samarbeten och för att best practice sprids och tillämpas i Sverige. Vi erbjuder också utbildningar, tjänster och produkter som hjälper våra kunder att utveckla sina verksamheter och skapa samhällsnytta med hjälp av standarder.

Vill du veta mer eller bidra till att skapa smarta globala lösningar, kontakta oss per telefon eller besök **sis.se**

Svenska institutet för standarder
104 31 Stockholm
Tel 08 - 555 523 10
kundservice@sis.se
sis.se