

# FRACMATH: A fast and vectorized MATLAB framework for continuum damage mechanics with crack-band regularization

Jaykumar Mavani<sup>1</sup> and Madura Pathirage<sup>1</sup>

<sup>1</sup> Gerald May Department of Civil, Construction, and Environmental Engineering, University of New Mexico, Albuquerque, NM, USA  Corresponding author

DOI: [10.xxxxxx/draft](https://doi.org/10.xxxxxx/draft)

## Software

- [Review](#) 
- [Repository](#) 
- [Archive](#) 

Editor: [Open Journals](#) 

## Reviewers:

- [@openjournals](#)

Submitted: 22 June 2026

Published: unpublished

## License

Authors of papers retain copyright and release the work under a Creative Commons Attribution 4.0 International License ([CC BY 4.0](#)).

## Summary

FRACMATH is an open-source MATLAB framework for finite-element simulation of crack-band-regularized continuum damage mechanics (CDM) in quasi-brittle materials. The code uses a scalar isotropic damage variable, the modified von Mises equivalent strain (de Vree et al., 1995), exponential softening, and Oliver's direction-dependent projected crack-band length (Bažant & Oh, 1983; Oliver, 1989). It keeps the solver, plotting, and constitutive update inside MATLAB, with no MATLAB executable (MEX) files, compiled extensions, or separate build system.

The package includes a two-dimensional (2D) notched three-point bending (3PB) benchmark checked against Abaqus/Standard through an Oliver-matched user material subroutine (UMAT), plus two three-dimensional (3D) MATLAB demonstrations: the Nooru-Mohamed mixed-mode test and Brokenshire's notched beam torsion test. The repository stores source code, input decks, results, plotting scripts, and a theory manual at [https://github.com/jaymavani7/JOSS\\_FRACMATH](https://github.com/jaymavani7/JOSS_FRACMATH) under the MIT license.

## Statement of need

MATLAB remains useful in engineering research because students already know its matrix syntax, plotting tools, debugger, profiler, and sparse linear algebra. This matters for fracture modeling, where a user often needs to inspect element-level strain histories, change a softening law, compare crack-band lengths, and immediately visualize the damage field. FRACMATH uses that accessibility to provide a transparent CDM reference implementation rather than a general-purpose finite-element platform.

## State of the field

Open-source finite-element tools already cover many research needs, including OOFEM in C++ (Patzák & Bittnar, 2001), FEniCS for Python/C++ workflows (Logg et al., 2012), Akantu for high-performance fracture simulations (Richart et al., 2024), and CALFEM as a MATLAB teaching toolbox (Austrell et al., 2004). These projects are valuable, but extending them for a new damage formulation can require learning a larger architecture, templated interface, wrapper layer, or compiled user-material workflow. Commercial tools such as Abaqus/Standard are also powerful, but custom CDM models generally require user-material subroutines, such as UMAT for Abaqus/Standard or VUMAT for Abaqus/Explicit, plus careful state-variable handling (Dassault Systèmes Simulia Corp., 2023).

The closest recent Journal of Open Source Software (JOSS) comparison is Parallel-CDM by Eldababy et al. (Eldababy et al., 2025), which provides a MATLAB implementation of 2D local and nonlocal CDM with parallel assembly. FRACMATH is complementary: its emphasis is direction-dependent Oliver crack-band scaling, the same bandwidth formula in MATLAB and Abaqus, a direct UMAT cross-check on an identical 3PB mesh, and reuse of the scalar damage routine for 3D mixed-mode and torsion-driven crack paths.

## Software design

The material model follows standard scalar CDM, where damage variables and equivalent-strain histories are used to represent stiffness degradation in quasi-brittle fracture (Bažant & Planas, 1998; de Vree et al., 1995). Damage degrades the undamaged stiffness as

$$\sigma = (1 - \omega)C_0 : \varepsilon, \quad (1)$$

where  $\omega \in [0, 1]$  is the damage variable. A history variable stores the maximum equivalent strain so damage cannot heal. Exponential softening is scaled element by element so the dissipated fracture energy matches  $G_F$  after crack-band regularization (Bažant & Oh, 1983). Instead of using a fixed mesh length, FRACMATH computes Oliver's projected characteristic length from the element geometry and the current maximum-principal-strain direction (Oliver, 1989). For a three-node triangular finite element (T3),

$$h(\mathbf{n}) = \frac{2}{\sum_{a=1}^3 |\nabla N_a \cdot \mathbf{n}|}. \quad (2)$$

The same idea is used for tetrahedra in 3D. In the Abaqus comparison, a preprocessing script writes the T3 shape-function gradients to `oliver_t3_gradN.dat`; the UMAT then recomputes Equation 2 from the current principal strain direction. This avoids using Abaqus's built-in characteristic element length variable, `CELENT`, as a fixed crack-band length and keeps the regularization consistent with Oliver's characteristic-length construction (Oliver, 1989).

The quasistatic solver uses displacement control with a fixed-secant modified Newton iteration in each increment. The secant stiffness is assembled and factored once, displacement residuals are iterated with that fixed matrix, and damage is updated after the displacement solve. Element strains, equivalent strain, history variables, damage, and crack-band lengths are updated with vectorized MATLAB operations, including page times; sparse linear systems use MATLAB's backslash interface, which dispatches to UMFPACK (Davis, 2004). This design favors readable vectorized kernels, direct plotting, and reviewer-side inspection over a larger compiled framework.

For the Abaqus comparison, FRACMATH includes the input deck, the Fortran UMAT, the Oliver-gradient table generator, and extraction scripts for load-CMOD curves, where CMOD is crack-mouth-opening displacement, and damage fields. The MATLAB and Abaqus paths therefore share the same mesh, boundary conditions, fracture energy, tensile strength, and crack-band bandwidth formula. Differences in the plotted response are primarily solver and implementation differences, not changes in the continuum model.

## Benchmarks


The main quantitative benchmark is the Gregoire notched 3PB beam (Grégoire et al., 2013), modeled with the same refined mesh, material constants, loading, scalar damage law, and Oliver crack-band formula in MATLAB and Abaqus. The 2D mesh uses Abaqus CPS3 elements, where CPS3 denotes a three-node plane-stress triangular element. MATLAB predicts a peak

78 load of 3.63982 kN at CMOD 0.022811 mm; Abaqus predicts 3.60913 kN at CMOD 0.022485  
79 mm. Both simulations localize damage upward from the notch, which is the expected opening-  
80 mode (mode-I) crack path for this geometry (Grégoire et al., 2013). The Abaqus UMAT  
81 independently evaluates the same damage law and Oliver bandwidth inside a commercial  
82 finite-element environment (Dassault Systèmes Simulia Corp., 2023; Oliver, 1989).


83 The stored timing logs for this benchmark run report MATLAB R2024a using one thread and  
84 Abaqus/Standard 2023 using four threads. The MATLAB solver wall-clock time was 547.58 s,  
85 while the Abaqus submit-to-completion time was 1996.25 s. MATLAB time was dominated by  
86 stiffness assembly, not by the sparse solve. The timing should not be read as a universal speed  
87 claim, because solver settings, output requests, hardware, and Abaqus licensing can all change  
88 wall-clock time.

**Table 1:** 2D 3PB comparison using the same mesh, material law, and Oliver T3 crack-band bandwidth.

| Quantity                     | MATLAB   | Abaqus + UMAT |
|------------------------------|----------|---------------|
| Peak load (N)                | 3639.82  | 3609.13       |
| CMOD at peak (mm)            | 0.022811 | 0.022485      |
| Solver/submit wall-clock (s) | 547.58   | 1996.25       |
| End-to-end/internal time (s) | 590.54   | 1968.00       |

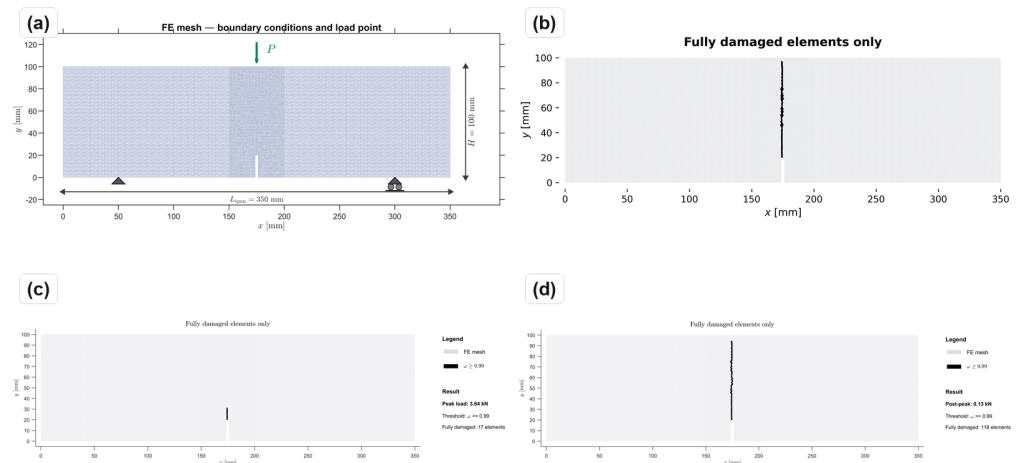


**Figure 1:** 3PB mesh and damage fields: (a) CPS3 mesh and support/load layout; (b) Abaqus UMAT final fully damaged elements; (c) MATLAB damage field at peak load; (d) MATLAB post-peak damage field.

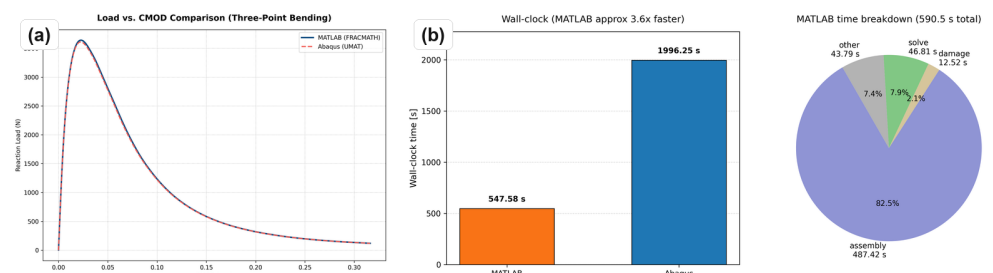


**Figure 2:** 3PB response and timing: (a) MATLAB and Abaqus load-CMOD response; (b) wall-clock comparison and MATLAB timing breakdown.

89 The Nooru-Mohamed benchmark checks mixed-mode 3D cracking in a double-edge-notched  
90 concrete panel under combined tension and shear (Nooru-Mohamed, 1992). The same scalar  
91 CDM routine uses four-node linear tetrahedral (TET4) elements and Oliver crack-band scaling  
92 (Oliver, 1989). The simulated damage bands initiate at the two notch tips and coalesce across  
93 the ligament, matching the qualitative experimental crack-path pattern.

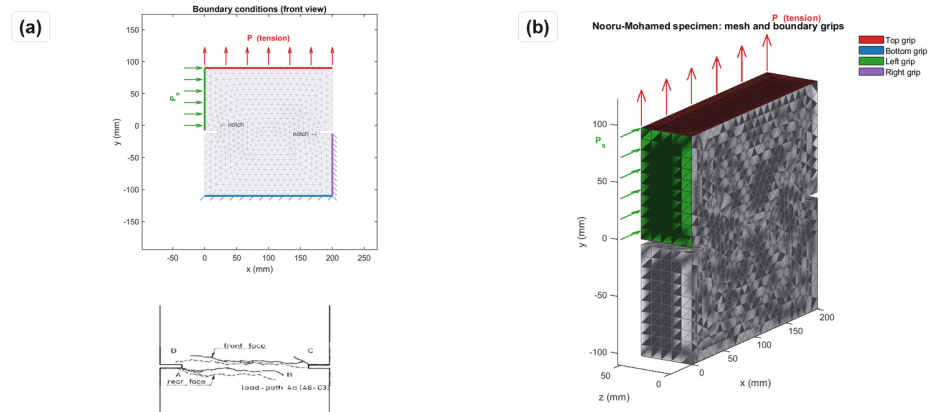

**Figure 3:** Nooru-Mohamed mixed-mode benchmark: (a) boundary conditions with experimental crack-path inset; (b) 3D mesh.


94 This example is included because mixed-mode response is a common failure point for simplified  
95 fracture implementations. In the simulation, the crack-band direction changes as the principal  
96 strain field evolves, so the projected bandwidth is recomputed rather than assigned from a  
97 constant element size. The resulting localization band does not remain a straight mode-I  
98 notch extension; it bends across the ligament in the same qualitative direction as the reported  
99 experimental crack path.

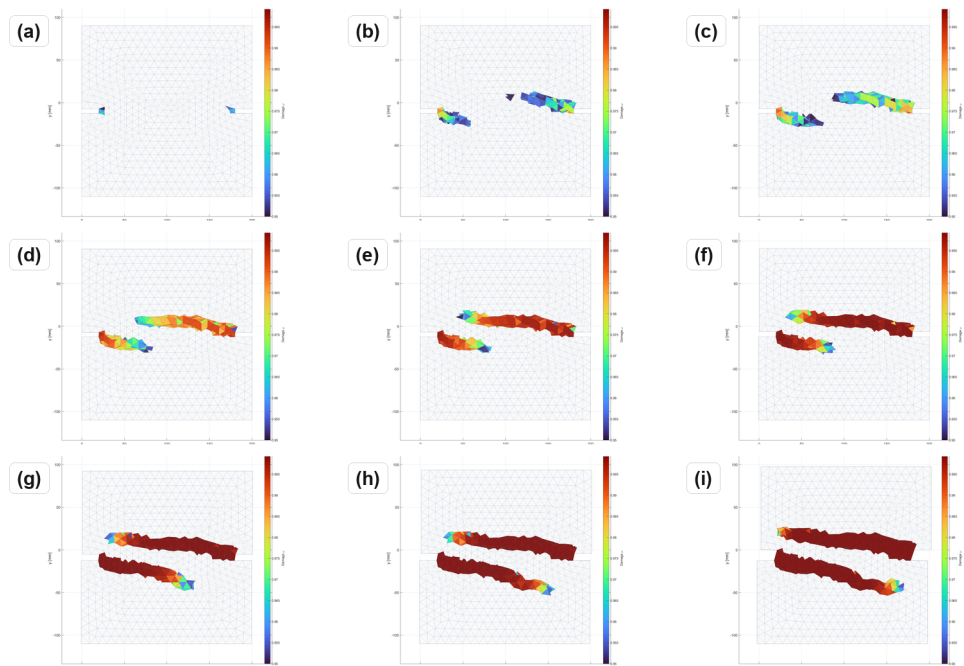

**Figure 4:** Nooru-Mohamed damage evolution from first localization to coalescence in a 3-by-3 sequence.


100 Brokenshire's torsion benchmark tests whether the same formulation can recover a curved 3D

101 fracture surface in a notched plain concrete beam (Jefferson et al., 2004). The model uses a  
102 prescribed twist, TET4 elements, and the same damage update. The computed band nucleates  
103 at the notch front and rotates toward the loaded corner, consistent with the experimentally  
104 recovered fracture surface.

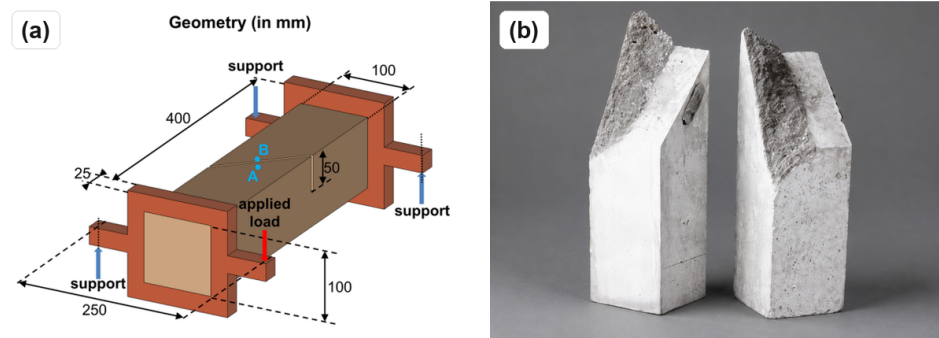

**Figure 5:** Brokenshire torsion benchmark: geometry and experimental fractured specimen from Jefferson et al. (Jefferson et al., 2004).

105 The torsion case is deliberately different from the 3PB validation: it contains out-of-plane  
106 cracking, a nonuniform stress state, and a visibly curved fracture surface. The 3D examples  
107 are intended as qualitative crack-path demonstrations; only the 2D 3PB case is quantitatively  
108 cross-checked against Abaqus.

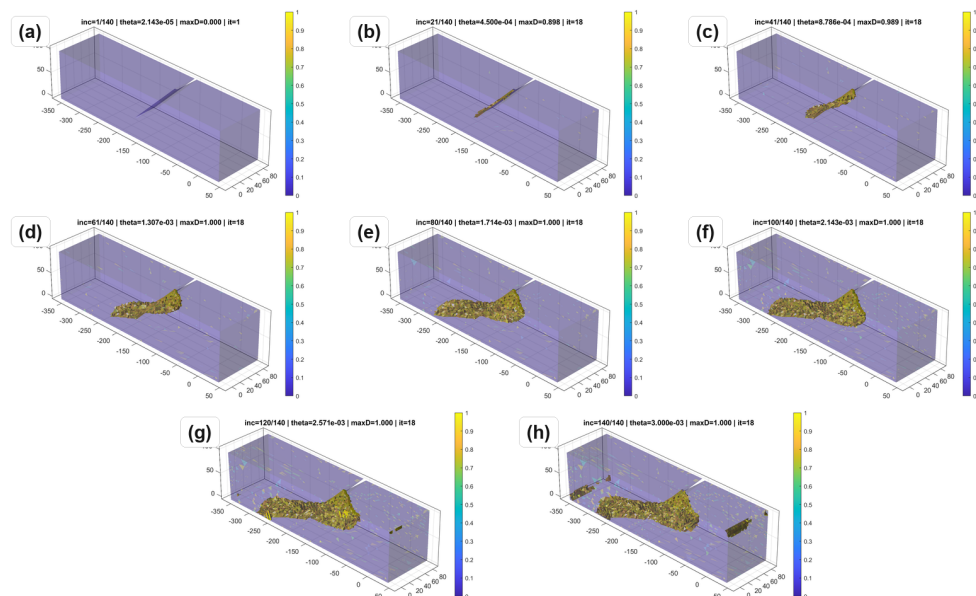

**Figure 6:** Torsion damage evolution over the imposed twist history.

## 109 Research impact statement

110 FRACMATH provides a reproducible reference workflow for CDM and crack-band studies. Its  
111 immediate scholarly value is the paired MATLAB/Abaqus 3PB benchmark, where the MATLAB  
112 solver is cross-checked against an independent Abaqus UMAT on the same mesh and material  
113 data. The repository also provides benchmark inputs, stored output data, plotting scripts,  
114 and 2D and 3D examples that can be reused for teaching, method comparison, and future  
115 extensions of crack-band regularization.



## 116 Software availability

117 The repository contains MATLAB source code, Abaqus UMAT files, benchmark input decks,  
118 plotting scripts, updated results, a theory manual, LICENSE, CITATION.cff, CONTRIBUTING.md,  
119 and reproducibility instructions. Reviewers can run the smoke tests from the repository root with  
120 `matlab -batch "addpath('tests'); run_smoke_checks"`. The test suite has been checked  
121 on MATLAB R2022a, R2023a, and R2024a across Linux, macOS, and Windows. A release  
122 archive digital object identifier (DOI) should be added before final JOSS acceptance.

## 123 Limitations

124 FRACMATH is quasistatic and does not include inertia, rate effects, contact, plasticity, or unilateral  
125 crack closure. Damage is isotropic and scalar, so anisotropic stiffness recovery and cyclic  
126 loading are outside the current scope. Crack-band scaling controls mesh-objective energy  
127 dissipation but does not introduce a physical material length scale.

## 128 AI usage disclosure

129 Generative AI tools were used to assist with manuscript wording and formatting. The scientific  
130 claims, equations, code, numerical results, figures, and references are the responsibility of the  
131 authors.

## 132 Acknowledgements

133 The authors acknowledge support from the National Aeronautics and Space Administration,  
134 the New Mexico Space Grant Consortium under grant 80NSSC22M0044, and the New Mexico  
135 Department of Finance and Administration under grant ZI5044-MG25-109. The opinions and  
136 conclusions are those of the authors and do not necessarily reflect the views of the sponsors.

## 137 References

- 138 Austrell, P.-E., Dahlblom, O., Lindemann, J., Olsson, A., Olsson, K.-G., Persson, K., Petersson,  
139 H., Ristinmaa, M., Sandberg, G., & Wernberg, P.-A. (2004). *CALFEM — a finite element*  
140 *toolbox, version 3.4*. Lund University.
- 141 Bažant, Z. P., & Oh, B. H. (1983). Crack band theory for fracture of concrete. *Matériaux Et*  
142 *Construction*, 16(3), 155–177. <https://doi.org/10.1007/BF02486267>
- 143 Bažant, Z. P., & Planas, J. (1998). *Fracture and size effect in concrete and other quasibrittle*  
144 *materials*. CRC Press.
- 145 Dassault Systèmes Simulia Corp. (2023). *Abaqus/standard user's manual, version 2023*.
- 146 Davis, T. A. (2004). Algorithm 832: UMFPACK V4.3 — an unsymmetric-pattern multifrontal  
147 method. *ACM Transactions on Mathematical Software*, 30(2), 196–199. <https://doi.org/10.1145/992200.992206>
- 148
- 149 de Vree, J. H. P., Brekelmans, W. A. M., & van Gils, M. A. J. (1995). Comparison of nonlocal  
150 approaches in continuum damage mechanics. *Computers & Structures*, 55(4), 581–588.  
151 [https://doi.org/10.1016/0045-7949\(94\)00501-S](https://doi.org/10.1016/0045-7949(94)00501-S)
- 152 Eldababy, H., Saji, R. P., Pantidis, P., & Mobasher, M. (2025). Parallel-CDM: Parallel  
153 implementation of continuum damage mechanics simulations using FEM and MATLAB.  
154 *Journal of Open Source Software*, 10(112), 7610. <https://doi.org/10.21105/joss.07610>

- 155 Grégoire, D., Rojas-Solano, L. B., & Pijaudier-Cabot, G. (2013). Failure and size effect for  
156 notched and unnotched concrete beams. *International Journal for Numerical and Analytical*  
157 *Methods in Geomechanics*, 37(10), 1434–1452. <https://doi.org/10.1002/nag.2180>
- 158 Jefferson, A. D., Bennett, T., & Hee, S. C. (2004). Three-dimensional finite element simulations  
159 of fracture tests using the Craft concrete model. *Computers and Concrete*, 1(3), 261–284.  
160 <https://doi.org/10.12989/cac.2004.1.3.261>
- 161 Logg, A., Mardal, K.-A., & Wells, G. N. (Eds.). (2012). *Automated solution of differential*  
162 *equations by the finite element method: The FEniCS book*. Springer. [https://doi.org/10.](https://doi.org/10.1007/978-3-642-23099-8)  
163 [1007/978-3-642-23099-8](https://doi.org/10.1007/978-3-642-23099-8)
- 164 Nooru-Mohamed, M. B. (1992). *Mixed-mode fracture of concrete: An experimental approach*  
165 [PhD thesis]. Delft University of Technology.
- 166 Oliver, J. (1989). A consistent characteristic length for smeared cracking models. *International*  
167 *Journal for Numerical Methods in Engineering*, 28(2), 461–474. [https://doi.org/10.1002/](https://doi.org/10.1002/nme.1620280214)  
168 [nme.1620280214](https://doi.org/10.1002/nme.1620280214)
- 169 Patzák, B., & Bittnar, Z. (2001). Design of object-oriented finite element code. *Advances*  
170 *in Engineering Software*, 32(10–11), 759–767. [https://doi.org/10.1016/S0965-9978\(01\)](https://doi.org/10.1016/S0965-9978(01)00027-8)  
171 [00027-8](https://doi.org/10.1016/S0965-9978(01)00027-8)
- 172 Richart, N., Anciaux, G., Gallyamov, E., Frérot, L., Kammer, D., Pundir, M., Vocialta,  
173 M., Ramos, A. C., Corrado, M., Müller, P., Barras, F., Zhang, S., Ferry, R., Durussel,  
174 V., & Molinari, J.-F. (2024). Akantu: An HPC finite-element library for contact and  
175 dynamic fracture simulations. *Journal of Open Source Software*, 9(94), 5253. [https:](https://doi.org/10.21105/joss.05253)  
176 [//doi.org/10.21105/joss.05253](https://doi.org/10.21105/joss.05253)