TEST REPORT - SINWOO (TMED2 SLEEVE)

Member IMC Group

Header

Customer No.	8682
Product Line	2 - IsoTurn
Industry	A1 - Cars
Test Date (DD/MM/YYYY)	12/03/2026
Test Reason	2 - Tool life
Stage	3 - Completed
Test Result	1 - Positive
Branch	ULSAN

Machine Information

Type	4 - Multi Spindle
Brand & Model	STAR SR-38B
Adaptation	
Max. RPM	7,000

Cutting Condition

	Actual	Actual	Proposal 1	Proposal 2		
Manufacturer	7 - Sumitomo	7 - Sumitomo	1 - Iscar	1 - Iscar		
Tool	PDJNR1616-11	PDJNR1616-11	NQCH16-PTJNR-16S-JHP	NQCH16-PTJNR-16S-JHP		
Insert	DNMG110408N-SU	DNMG110404N-SU	D6NMG 160408-M3P	D6NMG 160404-F3P		
Carbide Grade	AC630M	T1500A	IC8250	IC8250		
External Starting Diameter (mm)	52.2	52.2	52.2	52.2		
Internal Starting Diameter (mm)						
Cutting Speed (m/min)	**393**	**377**	**393**	**377**		
Spindle Speed (rpm)	2400	2300	2400	2300		
Feed (mm/rev)	0.2(외경) / 0.15(단면)	0.2(외경) / 0.15(단면)	0.2(외경) / 0.15(단면)	0.2(외경) / 0.15(단면)		
Depth of Cut (mm)	1.5	0.5	1.5	0.5		
Number of Passes	2	1	2	1		
Length of Cut (mm)						
Parts per Cutting Edge	100~110pcs	100~110pcs	150~170pcs	150~170pcs		
Wear	2 - Crater Wear	2 - Crater Wear	2 - Crater Wear	2 - Crater Wear		
Reason for Stopping the Test	2 - Wear	8 - Dimensional Stability	2 - Wear	8 - Dimensional Stability		
Remark	황삭	정삭	황삭	정삭		

Material & Fixture

Part Name	TMED2 SLEEVE
Raw Material	3 - Casting
Group	3 - Non-alloy steel and cast steel, free cutting steel
Std. Code	8 - JIS
Material	S45C
Hardness	
Unit	
Rigidity	1 - Stable

Test Result

1. 경쟁사 Tool Life 및 칩 분절 문제, 경쟁사 황삭 Pecking 가공으로 칩 분절 유도 (홀더 내부 급유 타입 X)
2. ISCAR Pecking 프로그램 삭제 및 NQCH-JHP 내부 급유 홀더 사용하여 칩 처리 원활
3. Tool Life 증가 및 인서트 각 300개, NQCH 홀더 6개 주문 완료
4. 선삭 타 공정 ISCAR 추가 검토 예정

TEST REPORT - SINWOO (TMED2 SLEEVE)
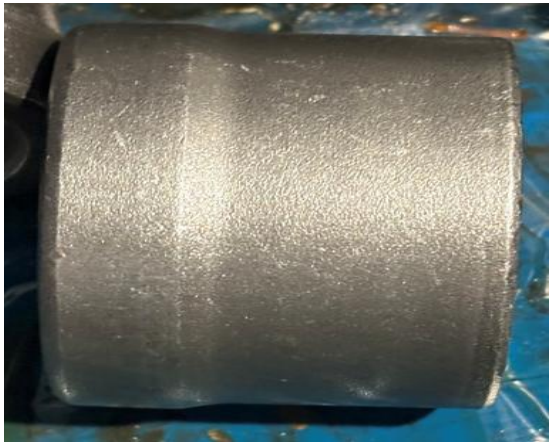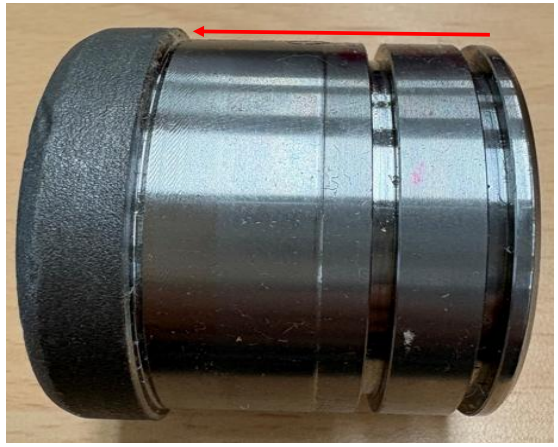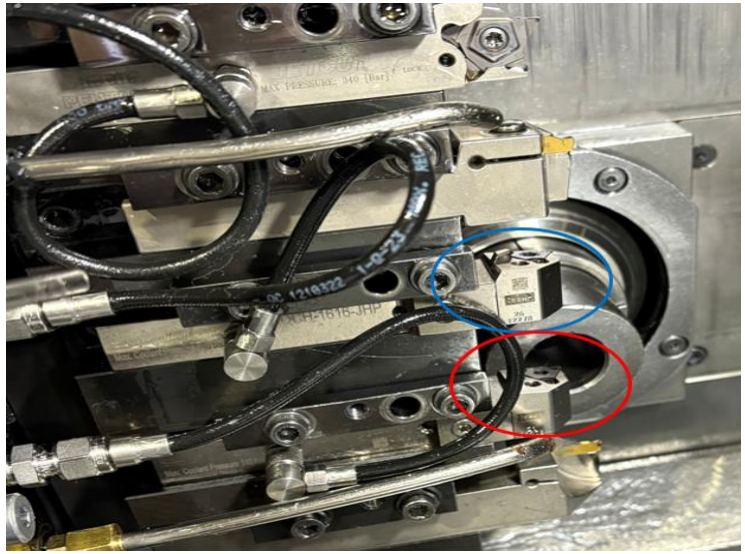
Member IMC Group