TEST REPORT - HOSEONG (SLEEVE, SUS316L)

Member IMC Group

Header

Customer No.	80155
Product Line	5 - Drilling
Industry	A1 - Cars
Test Date (DD/MM/YYYY)	25/03/2026
Test Reason	1 - Productivity
Stage	3 - Completed
Test Result	1 - Positive
Branch	TAEGU

Machine Information

Type	3 - Turning Machine
Brand & Model	WIA SKT100
Adaptation	
Max. RPM	6,000

Cutting Condition

		Actual	Proposal 1	Proposal 2	Proposal 3	Proposal 4	Proposal 5
Manufacturer		215 - YG1	1 - Iscar				
Drill		DPPA02120	DCN 120-060-16A-5D				
Insert			ICM 120				
Insert Grade			IC908				
Hole Diameter (mm)		12	12				
Pre Hole Diameter (mm)							
Required Hole Tolerance (mm)		0.03	0.03				
Speed	Cutting Speed (m/min)	37	56				
	Spindle Speed (rpm)	**1000**	**1500**				
Feed	Feed (mm/rev)	0.05	0.1				
	Table Feed (mm/min)	**50.0**	**150.0**				
Depth of Cut (mm)		57	57				
Hole Type (Blind/Through)		Blind	Blind				
Coolant		1 - Internal	1 - Internal				
Cutting Time		5	2				
Tool Life (pcs)							
Spindle Load (%)							
Remark		C/T 단위는 (분) 입니다.	C/T 단위는 (분) 입니다.				

Material & Fixture

Part Name	SLEEVE
Raw Material	3 - Casting
Group	14 - Stainless steel and cast steel
Std. Code	8 - JIS
Material	SUS316L
Hardness	
Unit	HRC
Rigidity	2 - Semi Stable

Test Result

1. 기존 초경 드릴 사용 중이나, 치수 및 조도를 위한 황/정삭 보링 공정 필요
2. SUMOCHAM 사용을 통한 C/T 단축 목표 TEST 진행
3. TEST 초기 안정성을 위한 낮은 이송(f 0.1)로 진행
4. C/T 약 50% 이상 감소 성공

TEST REPORT - HOSEONG (SLEEVE, SUS316L)

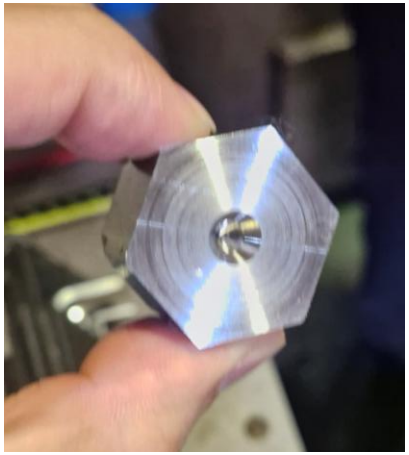

사진 1. 원소재

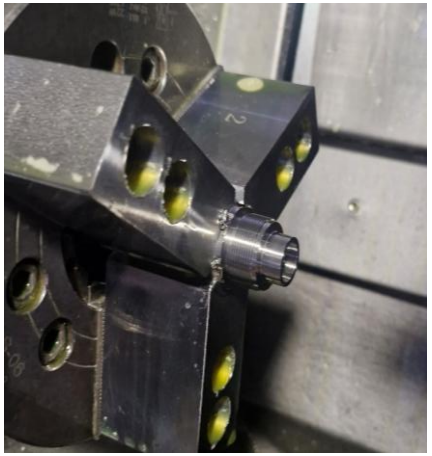

사진 2. 지그 체결 시

사진 3. 기존 공구

사진 4. TEST 후 내부 조도