PG® Products

Menor espesor, Único desempeño Balístico .

PG® ULTRA®

Resistencia balística adicional a armas largas.

PG ULTRA es un cristal blindado con todas las características de un nivel bajo, que suma una destacable resistencia balística a munición de nivel superior.



- Composicion exclusiva PG.
- Adicion minima de espesor y peso.
- PG Ultra está, probado y certificado.
- Compatible a cualquier modelo de vehiculo.


PG® Products

www.pgproducts.com.br

PG® ULTRA®

Caracteristicas: Vidrio blindado con resistencia balistica segun la norma NIJ 0108.01 para el nivel NIJ III-A

Balistica :



Adicionalmente:



4 Impactos Munición:
7,62x39mm FMJ a 30 cms

ó



1 Impacto Munición:
5,56x45 M193 en el centro

Espesor:






***Compatible con SteelGlass®**

*** Certificados balísticos disponibles**
pruebas realizadas en laboratorios reconocidos.



H.P. White Laboratory, Inc.
An Intertek Company

Ballistic Resistance – Test Report

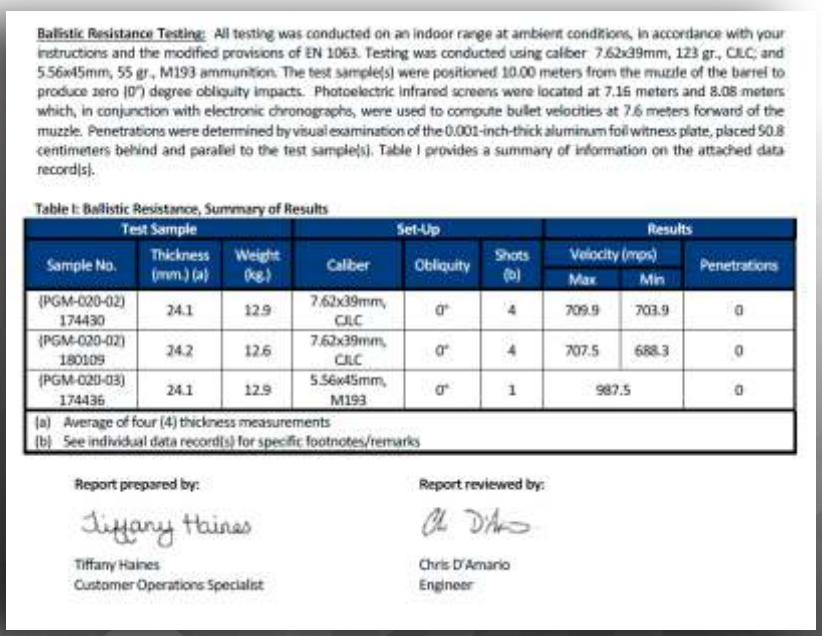

Ballistic Resistance Testing: All testing was conducted on an indoor range at ambient conditions, in accordance with your instructions and the modified provisions of EN 1063. Testing was conducted using caliber 7.62x39mm, 123 gr., CJLC; and 5.56x45mm, 55 gr., M193 ammunition. The test sample(s) were positioned 10.00 meters from the muzzle of the barrel to produce zero (0°) degree obliquity impacts. Photoelectric infrared screens were located at 7.16 meters and 8.08 meters which, in conjunction with electronic chronographs, were used to compute bullet velocities at 7.6 meters forward of the muzzle. Penetrations were determined by visual examination of the 0.001-inch-thick aluminum foil witness plate, placed 50.8 centimeters behind and parallel to the test sample(s). Table I provides a summary of information on the attached data record(s).

Table I: Ballistic Resistance, Summary of Results

Test Sample			Set-Up			Results		
Sample No.	Thickness (mm.) (a)	Weight (kg.)	Caliber	Obliquity	Shots (b)	Velocity (mps) Max	Velocity (mps) Min	Penetrations
(PGM-020-02) 174430	24.1	12.9	7.62x39mm, CJLC	0°	4	709.9	703.9	0
(PGM-020-02) 180109	24.2	12.6	7.62x39mm, CJLC	0°	4	707.5	688.3	0
(PGM-020-03) 174436	24.1	12.9	5.56x45mm, M193	0°	1	987.5		0

(a) Average of four (4) thickness measurements
(b) See individual data record(s) for specific footnotes/remarks

Report prepared by:
Tiffany Haines
Customer Operations Specialist

Report reviewed by:
Chris D'Amario
Engineer