

Cooling Test Report No. 7

Specimen S355 ring, outer diameter 2400 mm, wall thickness 60 mm. Cooled in still air from 1100 C. Hardness measured after 24 h.

Position	Cooling rate (C/s)	Hardness (HV10)
Outer surface	2.8	198
Mid wall	1.1	172
Inner surface	0.6	161

Conclusion: the hardness gradient across the wall is 37 HV10.

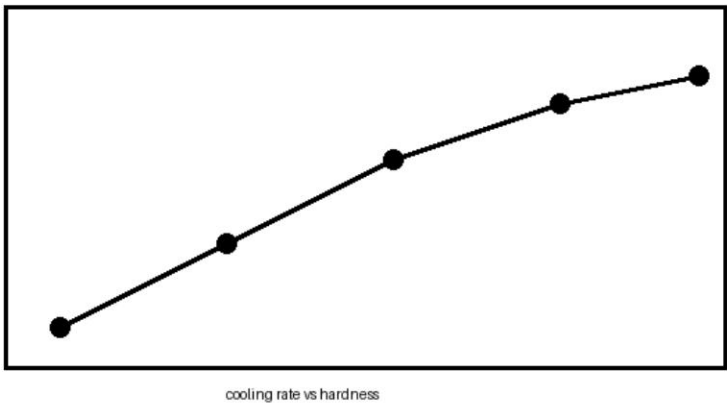


Figure 1: measured hardness against local cooling rate.