

STRUCTURE FORMING PROCESSES IN
MESOSCOPIC POLYMER SYSTEMS

by

TOMAS KOCI

(Under the direction of Michael Bachmann)

ABSTRACT

This is going to be the best abstract ever :)

INDEX WORDS: Polymer Aggregation, Monte Carlo Simulations, Parallel Tempering,
Multicanonical Sampling, Canonical Analysis, Microcanonical
Inflection-Point Analysis, Flexible Polymer, Structural Transitions,
Finite Systems, Finite-Size Effects

STRUCTURE FORMING PROCESSES IN
MESOSCOPIC POLYMER SYSTEMS

by

TOMAS KOCI

B.A., The Juilliard School, 2008

A Dissertation Submitted to the Graduate Faculty
of The University of Georgia in Partial Fulfillment
of the

Requirements for the Degree

DOCTOR OF PHILOSOPHY

ATHENS, GEORGIA

2016

©2016

Tomas Koci

All Rights Reserved

STRUCTURE FORMING PROCESSES IN
MESOSCOPIC POLYMER SYSTEMS

by

TOMAS KOCI

Approved:

Major Professor: Michael Bachmann

Committee: Steven P. Lewis
Heinz-Bernd Schuttler

Electronic Version Approved:

Alan Dorsey
Dean of the Graduate School
The University of Georgia
July 2016

Acknowledgments

Contents

1	Introduction	1
2	Elements of Statistical Mechanics	2
2.1	The microcanonical ensemble	3
2.2	The canonical ensemble	10
2.3	Alternative definitions of the density of states	17
3	Computational Methods	25
3.1	Markov chain Monte Carlo	25
3.2	Generalized ensemble Monte Carlo	25
3.3	Simple Monte Carlo updates	25
4	Coarse-grained Homopolymer Model	26
4.1	Flexible elastic homopolymer	26
4.2	Interacting homopolymers	26
5	Confinement Effects on Structural Transitions in Flexible Homopolymers	27
5.1	Introduction	27
5.2	Canonical analysis	27
5.3	Inflection-point analysis	27
5.4	Hyper-phase diagrams	27

6	Impact of Bonded Interactions on the Ground-State Geometries of Flexible Homopolymers	28
6.1	Structural order parameters	28
6.2	15-mer	28
6.3	55-mer	28
7	Aggregation of Flexible Elastic Homopolymers	29
7.1	Introduction	29
7.2	Microcanonical analysis	29
8	Summary and Outlook	30
	Bibliography	30

List of Figures

2.1	Microcanonical inflection-point analysis of the inverse microcanonical temperature $\beta(E)$. The prominent back-bending region in $\beta(E)$, together with the positive-valued peak in its energy derivative $\gamma(E)$ at $E \approx -15$, indicates a first-order transition. The negative-valued peak at $E \approx -24$ corresponds to a second-order transition.	7
2.2	The convex region of the microcanonical entropy $S(E)$ and the back-bending of the microcanonical inverse temperature $\beta(E)$ are prominent indicators of <i>first-order</i> transitions. The slope of the double-tangent Gibbs hull $\mathcal{H}(E)$ defines the transition temperature β_{tr} . The Maxwell construction, defined by equal areas of s_o and s_d , is itself positioned at β_{tr} . The transition energy E_{tr} indicates the location of the largest separation between $\mathcal{H}(E)$ and $S(E)$, which signifies maximal entropic suppression of the transition states. The latent heat ΔQ corresponds to the width of the transition region between E_d and E_o	8
2.3	(a) The jump discontinuity in the canonical entropy S , (b) and the delta peak in the specific heat C_V , are characteristic of a first order phase transition. . .	13

2.4	Second order transitions are characterized by discontinuities in response quantities, such as the specific heat. (a,b) In the case of a critical second order transition, the entropy S attains an infinite slope at T_c accompanied by a divergence in the specific heat C_V . (c,d) So called <i>lambda</i> transitions are characterized by a jump discontinuity in C_V and a cusp singularity in entropy.	14
2.5	(a) The peak in the specific heat C_V indicates a region of heightened thermodynamic activity. (b) The two peaks in the bimodal canonical energy distribution correspond to the ordered and disordered pseudophases, energetically separated by the latent heat ΔQ . Pseudophase coexistence and latent heat are reliable indicators of a first-order pseudophase transition. (c) Second-order transitions are marked by wide unimodal energy distributions at the transition point.	16
2.6	Results of a Monte Carlo simulation of a short flexible homopolymer of length $N = 13$. The average kinetic energy $\langle E_k \rangle$ and the kinetic contributions $C_{V,\text{kin}}$ towards the specific heat are plotted as points on top of their respective theoretical curves (blue). The average potential energy $\langle E_c \rangle$ and the configurational specific heat $C_{V,\text{conf}}$ (green) were obtained by sampling of the configurational space. Sampling of the full phase space was performed to obtain the total average energy U and the combined specific heat C_V (red). As expected, the combined specific heat is identical to $C_{V,\text{conf}}$, except for a trivial additive constant.	20

2.7	Comparison of microcanonical results from a Monte Carlo simulation of a flexible homopolymer of length $N = 55$. (a) The combined S , conformational S_c , and kinetic S_k entropy curves. (b) The kinetic inverse temperature β_k is a strictly convex function and the application of the inflection-point analysis reveals no transition signals. The conformational inverse temperature β_c clearly differs from $\beta(E)$, however both indicate a first-order pseudophase transition at virtually the same temperature.	23
2.8	Comparison of the inverse microcanonical temperature $\beta(E)$ (red) and the conformational inverse temperature $\beta_c(\bar{E}_p)$ (blue) evaluated at the most probable potential energy \bar{E}_p . The approximation introduced in equation 2.41 holds except in the back-bending region of the first-order pseudophase transition. The inverse transition temperature β_{trans} obtained from the two quantities is virtually identical.	24
8.1	Example of a figure.	30

List of Tables

8.1	Example of a table.	31
-----	-----------------------------	----

Chapter 1

Introduction

Kickass intro...

Chapter 2

Elements of Statistical Mechanics

Statistical mechanics aims at explaining the microscopic origins of macroscopic properties of systems with large numbers of degrees of freedom. The exact solution for the time evolution of every particle in a single complex system requires enormous computational efforts, and in most cases provides little insight. In contrast to the chaotic motion of particles at the microscopic level, collective system properties such as entropy, pressure, or temperature, for the most part exhibit relatively simple behavior. The formalism of statistical mechanics allows us to study these properties by considering the average behavior of a large number of identically prepared systems, i.e., the statistical ensemble. It is well established, that for very large systems near the thermodynamic limit, all ensembles become equivalent. However this is emphatically not true in the case of intrinsically finite systems for which the choice of an ensemble is non-trivial [1]. Therefore, I shall briefly discuss several prominent statistical ensembles, starting with arguably the most fundamental one, the *microcanonical ensemble*.

2.1 The microcanonical ensemble

Let us consider a mechanically and adiabatically isolated system with a constant number of particles (N), volume (V), and energy (E). At any given moment, the system is to be found in a particular microstate μ , which is represented by a point in a $6N$ dimensional phase-space. At a fixed energy E , the accessible microstates are constrained to the surface of constant energy $\mathcal{H}(\mu) = E$, where \mathcal{H} is the Hamiltonian of the system. The total number of microstates corresponding to a macrostate with a fixed energy E is obtained by calculating the density of states¹

$$g(E) = \int \mathcal{D}\mathcal{P}\mathcal{D}\mathcal{Q} \delta(E - \mathcal{H}(\mathcal{P}, \mathcal{Q})), \quad (2.1)$$

where

$$\mathcal{D}\mathcal{P}\mathcal{D}\mathcal{X} = \prod_{n=1}^N \frac{d^3 p_n d^3 x_n}{(2\pi\hbar)^3} \quad (2.2)$$

is the Lebesgue measure over phase space [2]. In computational studies, the energy space is by necessity discretized into intervals of width ΔE , and the density of states $g(E_i)$ is obtained by counting the microstates within a thin shell of width ΔE . Formally, $g(E_i)$ is a discrete function defined as

$$g(E_i) = \int_{E_i - \Delta E/2}^{E_i + \Delta E/2} g(E) dE, \quad (2.3)$$

where $g(E)$ in the integrand is the continuous density of states [1].

Assuming that no additional quantities are conserved, i.e. the system is ergodic, all accessible microstates have equal a priori probabilities [3]. The microcanonical equilibrium probability distribution is given by

$$p(\mu)_E = \begin{cases} 1/g(E), & \text{if } \mathcal{H}(\mu) = E \\ 0, & \text{if } \mathcal{H}(\mu) \neq E, \end{cases} \quad (2.4)$$

¹Please refer to section 2.3 for detailed discussion of alternative definitions of the density of states.

and the expectation value of an observable O at a fixed energy E is found by averaging over the surface of constant energy

$$\langle O \rangle_E = \int \mathcal{D}\mathcal{P} \mathcal{D}\mathcal{Q} \, O(\mathcal{P}, \mathcal{Q}) \, \delta(E - \mathcal{H}(\mathcal{P}, \mathcal{Q})). \quad (2.5)$$

The density of states of a typical mesoscopic system can easily span several thousands of orders of magnitude. It is therefore convenient to define the microcanonical equilibrium entropy

$$S(E) = k_B \ln g(E), \quad (2.6)$$

as an *extensive* quantity with dimensions of energy over temperature.²

2.1.1 Microcanonical temperature

Temperature is one of the most fundamental concepts of statistical mechanics. Traditionally, it has been defined in terms of average kinetic energies of particles in a system [4]. In the following, we wish to motivate a more fundamental definition and introduce temperature as an intrinsic system property which can be obtained directly from the microcanonical density of states. For this purpose, let us consider an adiabatically isolated system composed of two weakly interacting subsystems, S_1 and S_2 . The energy of the combined system is constant and can be written as the sum of the energies of the two subsystems $E = E_1 + E_2$. At a fixed system energy E , the probability density for subsystem S_1 to contain energy E_1 is written as

$$\rho(E_1)_E = \frac{g_1(E_1)g_2(E - E_1)}{g(E)}. \quad (2.7)$$

²If temperature is measured in the more natural units of energy, entropy becomes a unitless quantity and the Boltzmann constant equals to unity.

The density of states of the combined system is given by the convolution of the subsystem densities

$$g(E) = \int dE_1 g_1(E_1) g_2(E - E_1). \quad (2.8)$$

In systems with many degrees of freedom, the probability density $\rho(E_1)_E$ is a sharply peaked distribution around the equilibrium energy \bar{E}_1 ³. Hence the convolution in Eq. 2.8 can be well approximated by the maximum value of the integrand [5]. The maximum is found when the derivative of the integrand with respect to E_1 is set to zero. It follows that

$$\left. \frac{1}{g_1} \frac{dg_1}{dE_1} \right|_{\bar{E}_1} = \left. \frac{1}{g_2} \frac{dg_2}{dE_2} \right|_{E-\bar{E}_1}, \quad (2.9)$$

or alternatively in terms of the microcanonical entropy

$$\left. \frac{dS_1}{dE_1} \right|_{\bar{E}_1} = \left. \frac{dS_2}{dE_2} \right|_{E-\bar{E}_1}. \quad (2.10)$$

In analogy to the familiar observation that interacting systems at thermal equilibrium have equal temperatures, we define the microcanonical temperature as

$$T(E) = \left(\frac{dS(E)}{dE} \right)^{-1}. \quad (2.11)$$

Frequently, it is more convenient to consider instead the inverse microcanonical temperature

$$\beta(E) = \frac{dS(E)}{dE}. \quad (2.12)$$

³The energy fluctuations per particle around the equilibrium energy \bar{E}_1 scale as $N^{-1/2}$ [5].

2.1.2 Microcanonical analysis of phase transitions

A macrostate of a system is specified by a set of macroscopic variables and possesses the characteristics of the predominant microstates. Macrostates are said to belong to the same thermodynamic phase, if in a given range of some external control parameters⁴ all of the system's thermodynamic observables are analytic, i.e. have convergent Taylor expansions. Singularities in the observables signify the presence of phase transitions between distinct phases, typically marked by abrupt changes in macroscopic properties in response to minute variations of external control parameters. Phase transitions can be roughly divided into two categories. *Abrupt* transitions are characterized by the coexistence of two distinct phases and discontinuities in most physical properties. *Continuous* transitions, although less common in nature, have been the object of most intense research. They are marked by diverging correlation lengths, large fluctuations, and scale invariance [5].

Divergences and singularities in thermodynamic observables and their derivatives are only found in systems which satisfy the thermodynamic limit. In mesoscopic systems⁵, due to finite size effects, divergences are replaced by peaks and discontinuities are smoothed over [1]. For clarity, we designate the term *pseudophase transition* to represent significant conformational changes in finite systems. Likewise, thermodynamic phases in finite systems shall be referred to as *pseudophases*. In the following, we present a powerful formalism for the analysis of pseudophase transitions in the microcanonical ensemble; the microcanonical inflection point analysis.

⁴Some common examples of external control parameters are the canonical temperature, pressure, or the chemical potential.

⁵Typical length scales in mesoscopic systems are of the order of $\sim 10^3$ nanometers. In this regime, exact quantum many-body interactions can be replaced by effective classical potentials, and cooperative effects dominate structure formation processes. Mesoscopic systems are distinct from macroscopic systems due to the presence of significant finite-size effects, which disallow the simplifying assumptions of the thermodynamic limit.

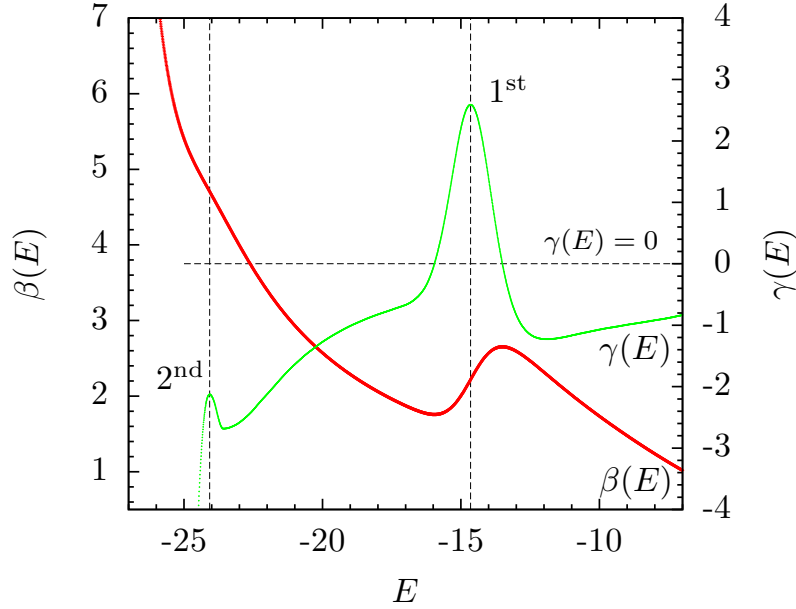


Figure 2.1: Microcanonical inflection-point analysis of the inverse microcanonical temperature $\beta(E)$. The prominent back-bending region in $\beta(E)$, together with the positive-valued peak in its energy derivative $\gamma(E)$ at $E \approx -15$, indicates a first-order transition. The negative-valued peak at $E \approx -24$ corresponds to a second-order transition.

Microcanonical inflection-point analysis

Unlike its canonical counterpart – the heat-bath temperature – the microcanonical inverse temperature is an inherent property of the system, derived directly from the fundamental microcanonical quantities $S(E)$ and E . We assert that all essential information about energetically and entropically driven thermodynamic processes is contained in its curvature. Hence the microcanonical inverse temperature is an ideal starting point for a comprehensive analysis of pseudophase transitions [6].

In analogy to the principle of minimal sensitivity [7], structural transitions between pseudophases occur when $\beta(E)$, or one of its energy derivatives, respond least sensitively to variations in energy [8]. In particular, first-order transitions are associated with inflection

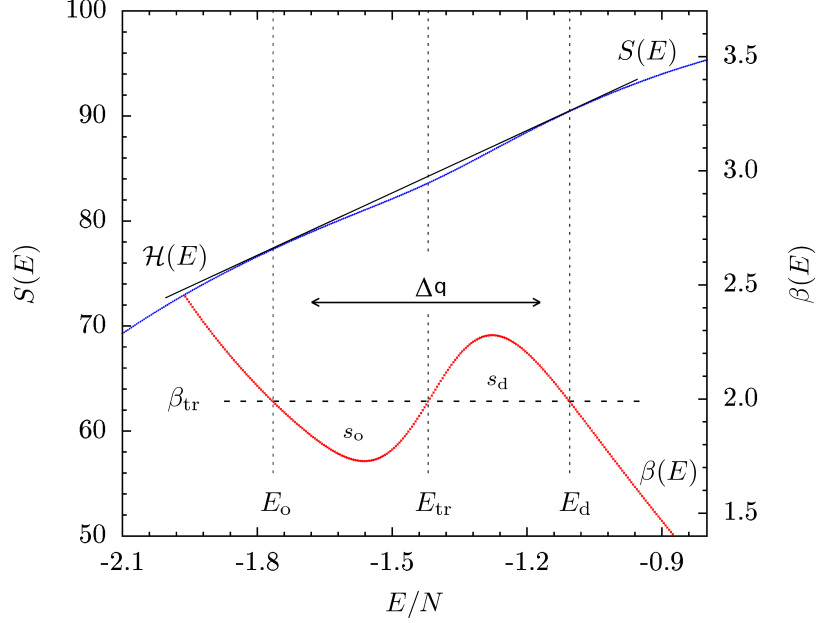


Figure 2.2: The convex region of the microcanonical entropy $S(E)$ and the back-bending of the microcanonical inverse temperature $\beta(E)$ are prominent indicators of *first-order* transitions. The slope of the double-tangent Gibbs hull $\mathcal{H}(E)$ defines the transition temperature β_{tr} . The Maxwell construction, defined by equal areas of s_o and s_d , is itself positioned at β_{tr} . The transition energy E_{tr} indicates the location of the largest separation between $\mathcal{H}(E)$ and $S(E)$, which signifies maximal entropic suppression of the transition states. The latent heat ΔQ corresponds to the width of the transition region between E_d and E_o .

points in $\beta(E)$ that have a positive slope, accompanied by positive-valued peaks in the energy derivative $\gamma(E) = d\beta(E)/dE$. Similarly, a second-order transition occurs when $\beta(E)$ exhibits an inflection point with a negative slope and $\gamma(E)$ attains a negative-valued peak. Examples of microcanonical pseudophase transition signals are shown in Fig. 2.1. The formalism can be naturally extended to higher-order transitions. Inflection point in the $(2n)$ th-derivative of entropy, accompanied by a positive-valued valley in the $(2n + 1)$ th-derivative, indicates a $(2n + 1)$ th-order transition. Similarly, a $(2n)$ th-order transition is marked by an inflection point in the $(2n - 1)$ th-derivative of entropy and a negative-valued peak in the $(2n)$ th-order derivative.

Alternatively, in the case of first-order transitions, the transition temperature β_{tr} can be obtained by the means of the Maxwell construction which was originally introduced to repair the unphysical back-bending in the pressure versus volume isotherms for the van der Waals gas. In mesoscopic systems, the finite-size effects lead to the entropic suppression of transition states, which is manifested in the backbending of $\beta(E)$ and the convex intruder in $S(E)$. The position of the Maxwell construction is determined by the equality of the areas s_o and s_d [Fig.2.2]. Commonly referred to as *surface entropies*, s_o and s_d are defined as the integrals

$$s_o = \int_{E_o}^{E_{\text{tr}}} dE (\beta_{\text{tr}} - \beta(E)), \quad (2.13)$$

$$s_d = \int_{E_{\text{tr}}}^{E_d} dE (\beta(E) - \beta_{\text{tr}}). \quad (2.14)$$

The Maxwell line intersects the inverse temperature at the energies E_o , E_{tr} , and E_d . The latent heat $\Delta Q = E_d - E_o$ corresponds to the energetic separation between the ordered and the disordered pseudophases. The transition energy E_{tr} indicates the location where intermediate states experience the maximal entropic suppression [1].

The slope of the double-tangent Gibbs construction, also shown in Figure 2.2, provides yet another definition of β_{tr} . As a function of energy, the Gibbs hull is defined as

$$\mathcal{H}(E) = S(E_o) + \beta_{\text{tr}}[E - E_o], \quad (2.15)$$

where β_{tr} can be expressed in terms of the energy and entropy differences between the ordered and disordered pseudophases as

$$\beta_{\text{tr}} = \frac{S_d - S_o}{E_d - E_o} = \frac{\Delta S}{\Delta Q}. \quad (2.16)$$

With the exception of composite multi-step transitions, characterized by additional oscilla-

tions in the back-bending region of $\beta(E)$, the transition temperatures obtained by the means of the Maxwell and Gibbs constructions are identical.

The formalism of the microcanonical inflection-point analysis makes no reference to the thermodynamic limit. In fact, it is equally suitable for analysis of macroscopic and mesoscopic systems alike. This is in stark contrast to the more traditional canonical analysis which is defined under the assumption of the thermodynamic limit and has to be modified for the treatment of finite systems.

2.2 The canonical ensemble

The canonical ensemble describes the behavior of a closed system which is in thermal equilibrium with a large external heat bath at a fixed temperature T . In analogy to the density of states in the microcanonical ensemble, the partition function $Z(T)$ contains all the essential information about the thermodynamic properties of the system under consideration [9]. It can be defined directly as a Laplace transform⁶ of the microcanonical density of states $g(E)$

$$Z(T) = \sum_i g(E_i) e^{-\frac{E_i}{k_B T}}, \quad (2.17)$$

where T is the canonical temperature and k_B is the Boltzmann constant. The condition of thermal equilibrium prohibits any net average energy transfer between the system and the heat bath. However, the system can temporarily gain or lose energy through constant fluctuations and dissipations. The probability for a given microstate μ at a temperature T

⁶Here we assume that the system under investigation has discrete energy levels, which is always true in the context of computational studies. In the case of a continuous energy spectrum, the discrete sum is replaced by the integral $Z(T) = \int dE g(E) e^{-\frac{E}{k_B T}}$.

is given by the Boltzmann distribution

$$p(\mu) = \frac{1}{Z(T)} e^{-\frac{\mathcal{H}(\mu)}{k_B T}}, \quad (2.18)$$

where \mathcal{H} is the Hamiltonian of the system. The appropriate thermodynamic potential in the canonical ensemble is the Helmholtz free energy

$$F(T) = -k_B T \ln Z(T). \quad (2.19)$$

This quantity represents the energy available to perform work and can be used to obtain all other thermodynamic quantities by differentiation [4, 5]. The temperature derivative of the free energy defines the canonical entropy

$$S(T) = -\frac{\partial}{\partial T} F(T) \Big|_{N,V}, \quad (2.20)$$

which measures the amount of disorder in the system. The internal energy U , defined as a sum over all microstate energies weighted by the Boltzmann distribution

$$U(T) = \frac{\sum_{\mu} \mathcal{H}(\mu) e^{-\frac{\mathcal{H}(\mu)}{k_B T}}}{Z(T)} = \frac{\sum_E E g(E) e^{-\frac{E}{k_B T}}}{Z(T)}, \quad (2.21)$$

represents the average energy of the system. Alternatively, the internal energy can be obtained by the differentiation of the free energy

$$U(T) = k_B T^2 \frac{\partial}{\partial T} \ln Z(T) \Big|_{N,V} = -T^2 \frac{\partial}{\partial T} \left(\frac{F}{T} \right) \Big|_{N,V}. \quad (2.22)$$

The amount of energy needed to increase the temperature of the system by one unit is given by the specific heat C_V , defined as a temperature derivative of the internal energy

$$C_V(T) = \left. \frac{\partial}{\partial T} U(T) \right|_{N,V} = -T \left. \frac{\partial^2}{\partial T^2} F(T) \right|_{N,V}. \quad (2.23)$$

On the other hand, starting with the third term in equation 2.21 we obtain the following expression

$$\begin{aligned} C_V(T) &= \frac{\partial}{\partial T} \frac{\sum_E E g(E) e^{-\frac{E}{k_B T}}}{Z(T)} = -\frac{1}{k_B T^2} \frac{\partial}{\partial \beta} \frac{\sum_E E g(E) e^{-\beta E}}{\sum_E g(E) e^{-\beta E}} \\ &= \frac{1}{k_B T^2} \left[\left(\frac{\sum_E E^2 g(E) e^{-\beta E}}{Z(T)} \right) - \left(\frac{\sum_E E g(E) e^{-\beta E}}{Z(T)} \right)^2 \right] \\ &= \frac{1}{k_B T^2} (\langle E^2 \rangle - \langle E \rangle^2), \end{aligned} \quad (2.24)$$

where the last expression corresponds to the variance of the Boltzmann distribution. This result is of a profound physical importance, establishing the connection between the macroscopic response quantity C_V , and microscopic fluctuations.

2.2.1 Canonical analysis of phase transitions

Sudden dramatic changes of macroscopic properties, in response to small variations of an external control parameter, indicate that the system under investigation is undergoing a phase transition. Here we consider temperature-driven transitions and describe a classification scheme similar to Ehrenfest's.

In the thermodynamic limit, it is generally possible to identify some property of the system which is non-zero in the ordered phase and zero in the disordered phase, i.e. the order parameter [1, 9]. A standard example is the magnetization m in a ferromagnetic system, where $m = 1$ in the ordered ferromagnetic phase and $m = 0$ in the disordered

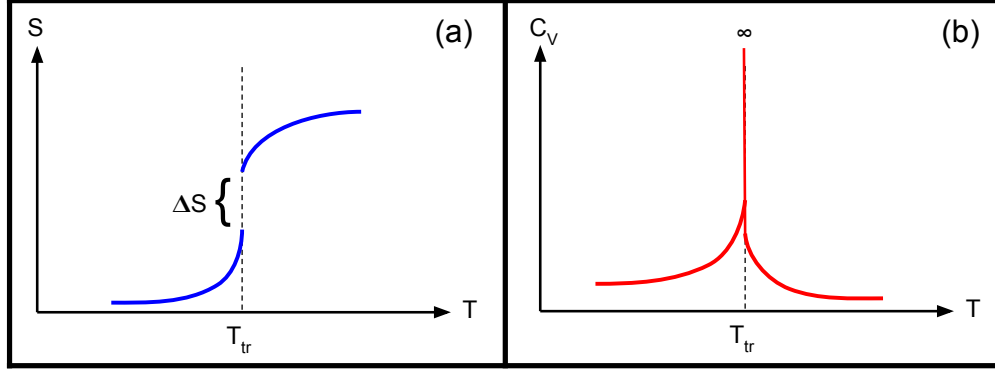


Figure 2.3: (a) The jump discontinuity in the canonical entropy S , (b) and the delta peak in the specific heat C_V , are characteristic of a first order phase transition.

paramagnetic phase. The derivative of the order parameter with respect to its conjugate variable defines a response quantity⁷ which is discontinuous at the transition point. Order parameters also play a central role in the formulation of the Landau theory, where they serve as a basis for the expansion of the free energy around the transition point [10].

First order transitions are characterized by a jump discontinuity ΔS in entropy and the coexistence of two distinct phases⁸ at the transition temperature. The energetic separation between the two phases corresponds to the latent heat

$$\Delta Q = T_{\text{trans}} \Delta S, \quad (2.25)$$

where ΔS is the height of the discontinuity and T_{trans} is the transition temperature. The specific heat C_V exhibits a delta peak at T_{trans} , as shown in Fig. 2.3 (b).

⁷In the case of the magnetization m , the appropriate conjugate thermodynamic variable is the external field H , and the corresponding response quantity is the magnetic susceptibility χ .

⁸As a familiar example, consider the coexistence of gas bubbles and liquid at the boiling point of water.

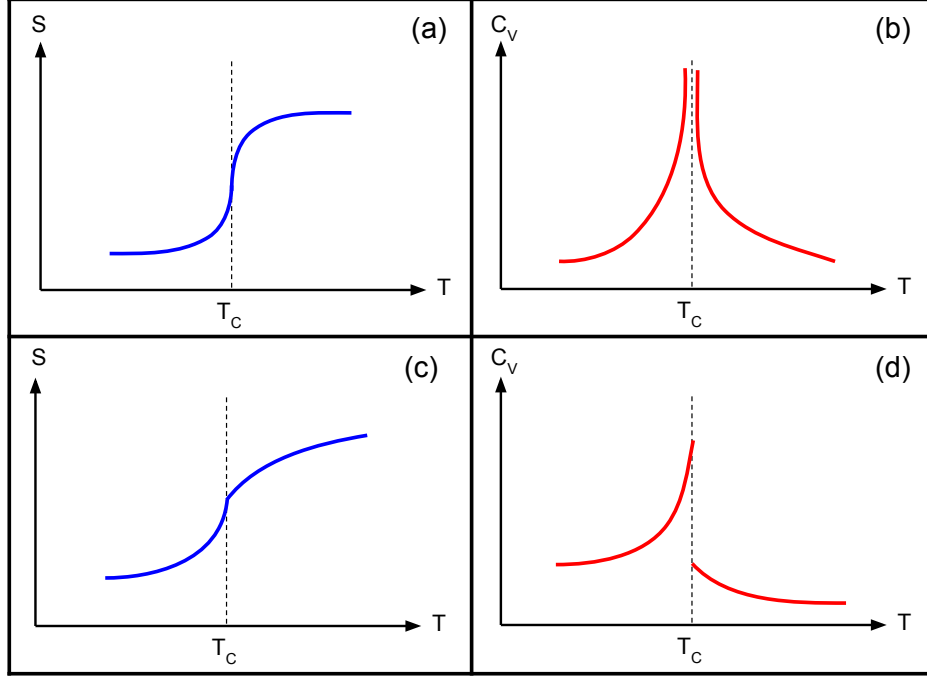


Figure 2.4: Second order transitions are characterized by discontinuities in response quantities, such as the specific heat. (a,b) In the case of a **critical** second order transition, the entropy S attains an infinite slope at T_c accompanied by a divergence in the specific heat C_V . (c,d) So called *lambda* transitions are characterized by a jump discontinuity in C_V and a cusp singularity in entropy.

Second order transitions do not possess discontinuities in entropy, and for that reason are often called *continuous* transitions. Instead, discontinuities are found in the second derivatives of the free energy with respect to temperature. It is customary to make use of equation 2.23, and consider the specific heat C_V which also contains the same discontinuities. In the vicinity of the transition point T_c , the specific heat exhibits a power law behavior $C_V(\tau) \propto |\tau|^{-\alpha}$, where $\tau = (T - T_c)/T_c$ and α is the associated critical exponent. Examples of common types of discontinuities of C_V are shown in Fig. 2.4. Other important quantities such as the magnetic susceptibility χ and the correlation length ξ also exhibit a power law behavior near the transition point, governed by the critical exponents γ and ν respectively.

The striking observation, that in the vicinity of the critical temperature T_c , the behavior of physical systems with diverse microscopic properties can be described in terms of the same critical exponents, is formalized in the theory of Universality [10].

Canonical analysis in mesoscopic systems

The description of phase transitions in the terms of discontinuities and divergences is valid only in the thermodynamic limit. In situations where the thermodynamic behavior of a system is affected by finite size effects, this idealized description no longer applies. Nevertheless, the numerous examples of abrupt changes of macroscopic properties in finite systems necessitate the generalization of the theory. In order to avoid possible confusion, we shall refer to significant conformational changes in finite systems as *pseudophase transitions*. Similarly, sets of macrostates with sufficiently similar macroscopic properties will be denoted *pseudophases*.

In the generalized formalism, peaks in the specific heat and other response quantities indicate regions of increased thermodynamic activity, i.e. pseudophase transitions. The order of the transition is determined from the shape of the canonical energy distribution in the transition region. Bimodal distributions reveal the coexistence of two pseudophases and indicate a first-order transition [11]. The associated latent heat of the transition is given by the energetic separation between the two peaks in the distribution. Second-order transitions correspond to unimodal energy distributions. The power law behavior of response quantities contains significant finite-size corrections and in some cases is altogether not applicable [9]. An example of canonical analysis, applied to first- and second-order pseudophase transitions, is illustrated in Fig. 2.5.

It should be mentioned that second-order pseudophase transitions do not always produce peaks in the specific heat. In general, it is necessary to investigate the behavior of several response quantities in order to obtain an accurate picture of the transition properties of

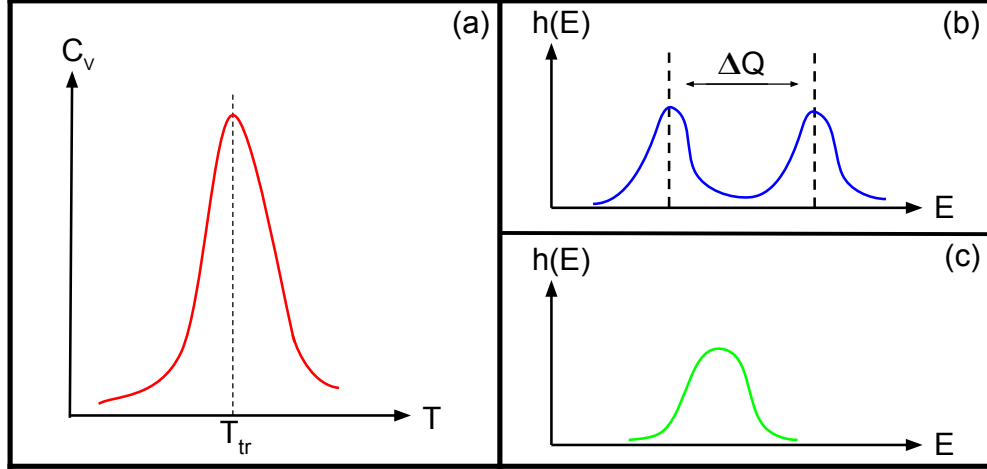


Figure 2.5: (a) The peak in the specific heat C_V indicates a region of heightened thermodynamic activity. (b) The two peaks in the bimodal canonical energy distribution correspond to the ordered and disordered pseudophases, energetically separated by the latent heat ΔQ . Pseudophase coexistence and latent heat are reliable indicators of a first-order pseudophase transition. (c) Second-order transitions are marked by wide unimodal energy distributions at the transition point.

the system under investigation. However, due to finite size effects, the signals obtained from different quantities will in general not coincide at a single transition temperature. This reality further fortifies the argument that the microcanonical inflection-point analysis⁹, which defines a unique transition temperature in mesoscopic and macroscopic systems alike, is the preferred formalism for the analysis of finite systems.

⁹Introduced in Sec. 2.1.2

2.3 Alternative definitions of the density of states

In section 2.1 we have defined the microcanonical density of states $g(E)$ as an integral over the surface of constant energy in the $6N$ -dimensional phase space. We have argued that $g(E)$ contains all the essential information about the thermodynamic properties of the system under consideration, and introduced the formalism of the microcanonical inflection-point analysis which uses the logarithm of $g(E)$ as its starting point. In section 2.2 we have shown that the canonical partition function $Z(T)$ can be obtained by performing a Laplace transform of $g(E)$. Clearly, the microcanonical density of states plays a fundamental role in equilibrium statistical mechanics, and as such needs to be carefully defined.

Two distinct definitions of the density of states arise from certain ambiguity in the exact meaning of the microcanonical ensemble in computational studies. The density of states can be defined in the context of the conformational microcanonical ensemble (N, V, E_p) as a function of the potential energy only

$$g_c(E_p) = \int \mathcal{D}\mathcal{Q} \, \delta(E_p - \mathcal{H}(\mathcal{Q})) \quad (2.26)$$

This definition is commonly used in Monte Carlo simulations of magnetic systems where the kinetic energy contributions have little physical significance and the sampling can be restricted to the conformational space. However, in systems where the transfer between potential and kinetic energy has important physical interpretation, the sampling of the full phase space becomes necessary. The standard definition of the microcanonical ensemble (N, V, E) is applied and the measured density of states becomes a function of the total system energy, which can be written as the sum of the potential and kinetic energies

$$E = E_p + E_k. \quad (2.27)$$

In order to distinguish between the two definitions, we shall use the symbol $\Gamma(E)$ to represent the latter definition of the density of states. The connection between the conformational density of states and $\Gamma(E)$ is expressed as a convolution [12]

$$\Gamma(E) = \int dE_k g_c(E - E_k) g_k(E_k), \quad (2.28)$$

where

$$g_k(E_k) = \int \mathcal{DP} \delta(E_k - \mathcal{H}(\mathcal{P})) \quad (2.29)$$

is the kinetic density of states obtained by integrating over the momentum space.

We shall now turn our attention to the consequence of choosing either the conformational or the full density of states as the starting point for a systematic analysis of the thermodynamic properties of a system under consideration. In the following we will discuss the impact of ignoring the momentum degrees of freedom on the results of both the canonical and microcanonical analysis. As an illustration, we will provide results from Monte Carlo simulations of two short flexible homopolymers.

2.3.1 Consequences for canonical analysis

The canonical partition function $Z(T)$ and the microcanonical density of states are connected via a Laplace transform. We begin with the full density of states $\Gamma(E)$ and using the definition from Eq. 2.28 write

$$Z(T) = \mathcal{L}\{\Gamma(E)\} = \mathcal{L}\{g_c * g_k\} = \mathcal{L}\{g_c\}\mathcal{L}\{g_k\}, \quad (2.30)$$

where the last step follows from the convolution theorem [13].

The partition function of the system can hence be conveniently written as a product of two independent partition functions

$$Z(T) = Z_c(T)Z_k(T), \quad (2.31)$$

which depend on the potential and kinetic energies respectively. It follows that the average ensemble energy can be expressed as the sum of the average potential and kinetic energies

$$\begin{aligned} U(T) &= k_B T^2 \frac{\partial}{\partial T} \ln Z \Big|_{N,V} \\ &= k_B T^2 \frac{\partial}{\partial T} \ln Z_c \Big|_{N,V} + k_B T^2 \frac{\partial}{\partial T} \ln Z_k \Big|_{N,V} \\ &= \langle E_c \rangle + \langle E_k \rangle. \end{aligned} \quad (2.32)$$

With the exception of systems with rigid constraints, the average kinetic energy is given by the equipartition theorem

$$\langle E_k \rangle = \frac{3Nk_B T}{2}, \quad (2.33)$$

where N is the number of particles in the system. It follows that the specific heat C_V obtains only a trivial additive constant from the kinetic energy term

$$\begin{aligned} C_V(T) &= \frac{\partial}{\partial T} U(T) \Big|_{N,V} \\ &= \frac{\partial}{\partial T} \langle E_c \rangle \Big|_{N,V} + \frac{\partial}{\partial T} \frac{3Nk_B T}{2} \\ &= C_{V,\text{conf.}} + \frac{3Nk_B}{2}. \end{aligned} \quad (2.34)$$

In conclusion, the locations and shapes of signals for pseudophase transitions are not affected by the inclusion of the momentum space into a sampling scheme. To substantiate this assertion, in Fig. 2.6 we present the results from a Monte Carlo study of a short

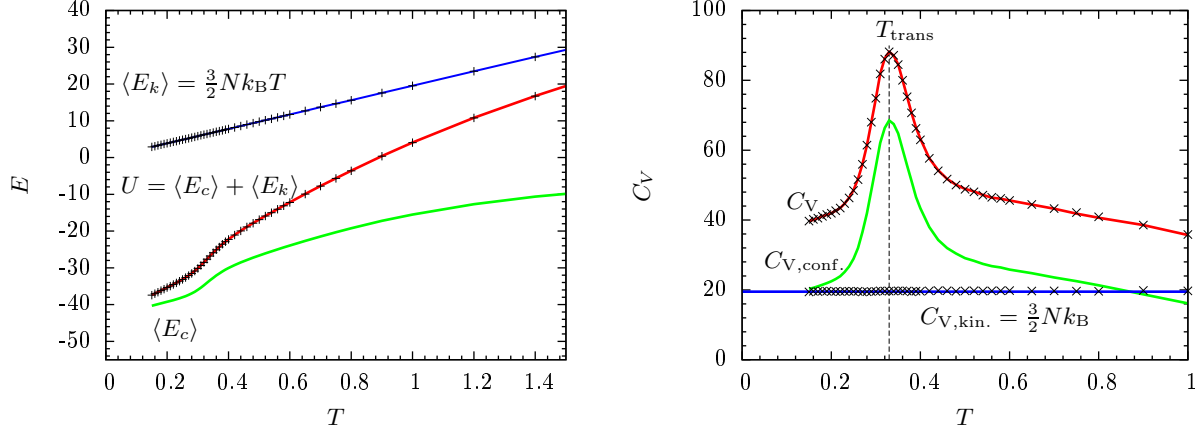


Figure 2.6: Results of a Monte Carlo simulation of a short flexible homopolymer of length $N = 13$. The average kinetic energy $\langle E_k \rangle$ and the kinetic contributions $C_{V,\text{kin.}}$ towards the specific heat are plotted as points on top of their respective theoretical curves (blue). The average potential energy $\langle E_c \rangle$ and the configurational specific heat $C_{V,\text{conf.}}$ (green) were obtained by sampling of the configurational space. Sampling of the full phase space was performed to obtain the total average energy U and the combined specific heat C_V (red). As expected, the combined specific heat is identical to $C_{V,\text{conf.}}$, except for a trivial additive constant.

flexible homopolymer. The average kinetic energy $\langle E_k \rangle$ and the kinetic contributions $C_{V,\text{kin.}}$ towards the specific heat are plotted as points on top of their respective theoretical curves (blue), showing good agreement with the predicted values. The average potential energy $\langle E_c \rangle$ and the configurational specific heat $C_{V,\text{conf.}}$ (green) were obtained by the sampling of the configurational space only. Sampling of the full phase space was performed to obtain the total average energy U and the combined specific heat C_V (red). As expected, the combined specific heat is identical to $C_{V,\text{conf.}}$, except for a trivial additive constant. The estimate of the transition temperature is independent of the choice of either definition of the density of states.

2.3.2 Consequences for microcanonical analysis

The application of the Laplace transform to the total density of states $\Gamma(E)$, allowed us to conveniently disentangle the convolution in Eq. 2.28 into separate kinetic and conformational contributions [Eq. 2.30]. Unfortunately, in the microcanonical ensemble no such simplification is readily available. Let us however consider a class of physical systems whose momenta and positional degrees of freedom are independent. Explicit integration over the momentum space yields a simple expression for the kinetic density of states

$$g_k(E_k) = \int \mathcal{D}\mathcal{P} \delta(E_k - \mathcal{H}(\mathcal{P})) = E_k^{\frac{3N-2}{2}}. \quad (2.35)$$

Combining the result with Eq. 2.28 we obtain

$$\Gamma(E) = \int dE_k g_c(E - E_k) E_k^{\frac{3N-2}{2}}. \quad (2.36)$$

Next, taking a derivative with respect to the total energy E and dividing both sides by $\Gamma(E)$ we get two equivalent expressions for the microcanonical inverse temperature

$$\beta(E) = \int dE_k \frac{3N-2}{2E_k} \left[\frac{g_c(E - E_k) E_k^{\frac{3N-2}{2}}}{\Gamma(E)} \right] \quad (2.37)$$

$$= \int dE_p \beta_c(E_p) \left[\frac{g_c(E_p) (E - E_p)^{\frac{3N-2}{2}}}{\Gamma(E)} \right]. \quad (2.38)$$

Recognizing the two terms enclosed in square brackets as the microcanonical probability densities for the kinetic and potential energies, we can rewrite equations 2.37 and 2.38 as

$$\beta(E) = \int dE_k \frac{3N-2}{2E_k} \rho(E_k)_E = \frac{3N-2}{2} \left\langle \frac{1}{E_k} \right\rangle, \quad (2.39)$$

and

$$\beta(E) = \int dE_p \beta_c(E_p) \rho(E_p)_E = \langle \beta_c \rangle. \quad (2.40)$$

The microcanonical inverse temperature, obtained by the differentiation of the total density of states, can therefore be interpreted as an average of the conformational and kinetic analogs weighted by their respective microcanonical probability distributions.

When the number of particles in the system is large, the probability densities $\rho(E_k)_E$ and $\rho(E_p)_E$ are expected to be sharply peaked around the most probable kinetic \bar{E}_k and potential \bar{E}_p energies respectively. We can therefore apply the saddle point approximation to the integrals in equations [2.39, 2.40] and obtain the following first order approximations for the inverse temperature

$$\beta(E) \approx \beta_c(\bar{E}_p), \quad (2.41)$$

and

$$\beta(E) \approx \frac{3N-2}{2} \left(\frac{1}{\bar{E}_k} \right). \quad (2.42)$$

The first expression suggests that it is possible to reconstruct $\beta(E)$ from the conformational inverse temperature β_c , and that the two quantities contain essentially the same information. We test the validity of this hypothesis by comparing the microcanonical results of Monte Carlo simulations of a flexible elastic 55-mer, which were carried out in both the conformational space and the full phase space.

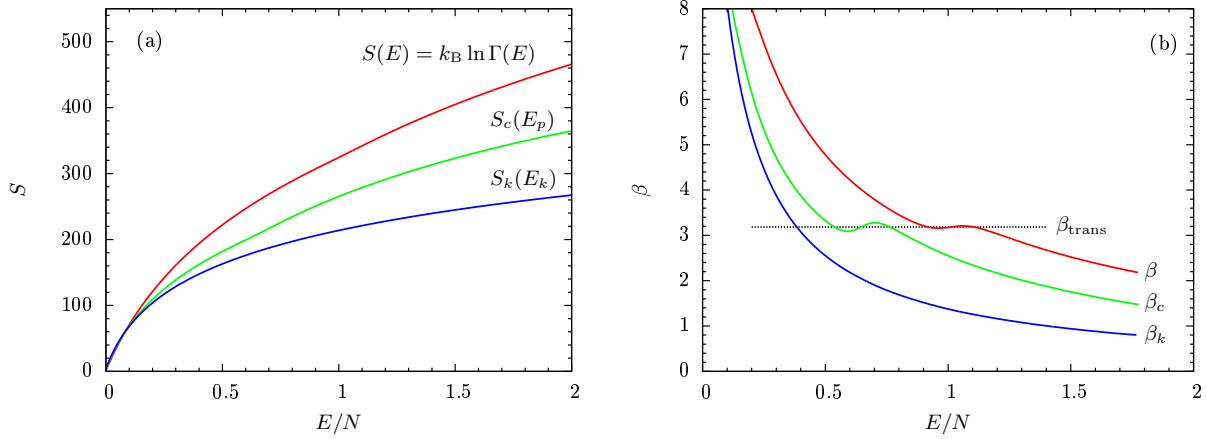


Figure 2.7: Comparison of microcanonical results from a Monte Carlo simulation of a flexible homopolymer of length $N = 55$. (a) The combined S , conformational S_c , and kinetic S_k entropy curves. (b) The kinetic inverse temperature β_k is a strictly convex function and the application of the inflection-point analysis reveals no transition signals. The conformational inverse temperature β_c clearly differs from $\beta(E)$, however both indicate a first-order pseudophase transition at virtually the same temperature.

The kinetic entropy in Fig. 2.7 is a strictly concave function and the application of the inflection-point analysis to the corresponding inverse temperature β_k reveals no transition signals. The conformational inverse temperature clearly differs from $\beta(E)$, however both indicate a first-order pseudophase transition at virtually the same temperature. In Fig. 2.8 we show the comparison between the true $\beta(E)$ and the reconstruction obtained from the conformational inverse temperature according to equations 2.41 and 2.42. It is evident that the approximation is valid, except in the back-bending region of the first-order transition due to the bimodality of the probability densities $\rho(E_k)_E$ and $\rho(E_p)_E$.

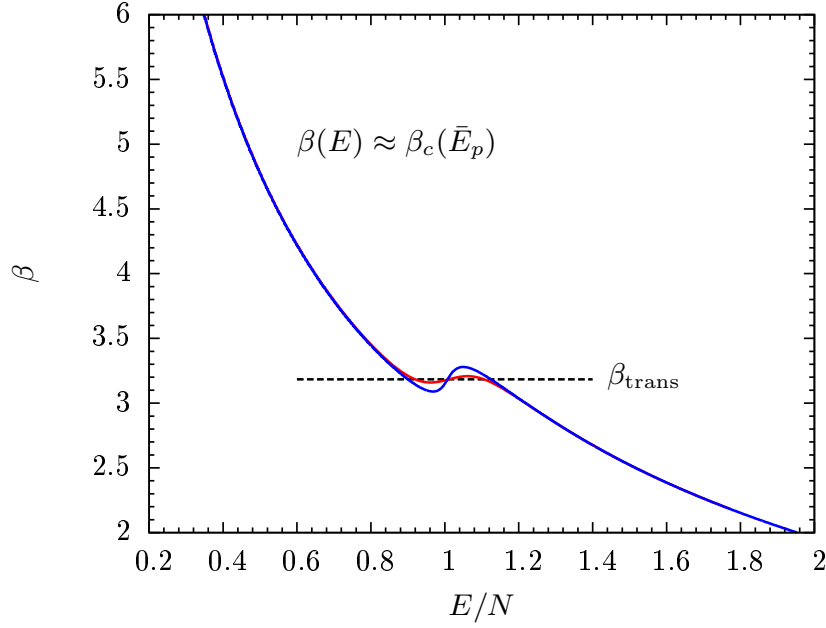


Figure 2.8: Comparison of the inverse microcanonical temperature $\beta(E)$ (red) and the conformational inverse temperature $\beta_c(\bar{E}_p)$ (blue) evaluated at the most probable potential energy \bar{E}_p . The approximation introduced in equation 2.41 holds except in the back-bending region of the first-order pseudophase transition. The inverse transition temperature β_{trans} obtained from the two quantities is virtually identical.

The expression in equation 2.42 can be rewritten as

$$k_{\text{B}}T(E) \approx \frac{2}{3N-2} \left(\frac{1}{\bar{E}_k} \right)^{-1}, \quad (2.43)$$

which clearly resembles the well known relationship between the canonical temperature and the average kinetic energy. In the thermodynamic limit, this approximation becomes exact and the equivalency of the microcanonical and canonical ensembles is restored.

Chapter 3

Computational Methods

3.1 Markov chain Monte Carlo

3.1.1 Master equation and detailed balance

3.1.2 Metropolis sampling

3.2 Generalized ensemble Monte Carlo

3.2.1 Parallel tempering

3.2.2 Multiple Gaussian modified ensemble

3.2.3 Histogram reweighting methods

3.2.4 Multicanonical sampling

3.3 Simple Monte Carlo updates

Chapter 4

Coarse-grained Homopolymer Model

4.1 Flexible elastic homopolymer

4.2 Interacting homopolymers

Chapter 5

Confinement Effects on Structural Transitions in Flexible Homopolymers

5.1 Introduction

5.2 Canonical analysis

5.3 Inflection-point analysis

5.4 Hyper-phase diagrams

Chapter 6

Impact of Bonded Interactions on the Ground-State Geometries of Flexible Homopolymers

6.1 Structural order parameters

6.2 15-mer

6.3 55-mer

Chapter 7

Aggregation of Flexible Elastic Homopolymers

7.1 Introduction

7.2 Microcanonical analysis

7.2.1 Subphases and subphase transitions

7.2.2 Missing subphases and translational entropy

7.2.3 Density effects on the latent heat

Chapter 8

Summary and Outlook

[You could put a picture here.]

Figure 8.1: Example of a figure.

Table 8.1: Example of a table.
[The contents of the table would go here.]

Bibliography

- [1] M. Bachmann, *Thermodynamics and Statistical Mechanics of Macromolecular Systems*, (Cambridge University Press, Cambridge, 2014).
- [2] H. H. Rugh , Phys. Rev. E **64**, 055101 (2001).
- [3] M. Kardar, *Statistical Physics of Particles*, (Cambridge University Press, New York, 2007).
- [4] R. K. Pathria, and P. D. Beale, *Statistical Mechanics*, (Elsevier, Oxford, 2011).
- [5] J. P. Sethna, *Statistical Mechanics: Entropy, Order Parameters, and Complexity*, (Oxford University Press, New York, 2006).
- [6] D. H. E. Gross, *Microcanonical Thermodynamics*, (World Scientific, Singapore, 2001).
- [7] P. M. Stevenson, Phys. Rev. D **23**, 2916 (1981).
- [8] S. Schnabel, D. T. Seaton, D. P. Landau, and M. Bachmann, Phys. Rev. E **84**, 011127 (2011).
- [9] D. P. Landau, and K. Binder, *A Guide to Monte Carlo Simulations in Statistical Physics*, (Cambridge University Press, Cambridge, 2000).
- [10] M. Kardar, *Statistical Physics of Fields*, (Cambridge University Press, New York, 2009).

- [11] W. Janke, Nuc Phys. B **63** A-C (1998).
- [12] F. Calvo, and P. Labastie, Chem. Phys. Lett. **247**, 395 (1995).
- [13] G. B. Arfken, *Mathematical Methods for Physicists*, (Elsevier, Oxford, 2013).