
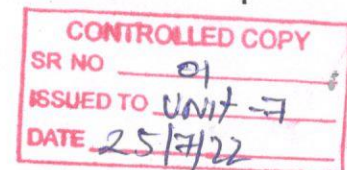


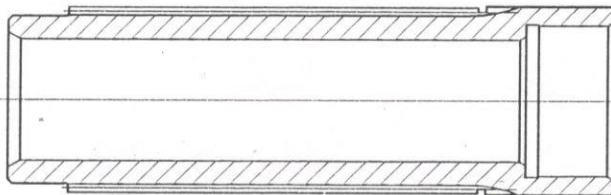

INSPECTION STANDARD (HT LAB)

☐ Prototype	☒ Pre-Launch	☐ Production	Date (Original)		11/12/18		
Part Name:- Lay Shaft -2		Part No.:- 93650625		Inspection Standard Number		SIP/4289/160	
Customer :- TMTL		Change Level:-00		Part Stage		HT Lab.	
Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	*	58-62 HRC	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
2.	ECD Measured To 550HV	*	0.60-0.90 mm	Micro Vicker / Vicker Hardness Tester	1Pc/Lot	FMT-HT-39	A
3.	Core Hardness at PCD	*	42 HRC (Max)	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
4.	Core Hardness at RCD	*	30 HRC (Min)	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
5.	Micro Case	*	Tempered Martensite + RA<12%, Carbide (Globular) Upto 2% Max.	Microscope	1Pc/Lot	FMT-HT-39	A
6.	Core Micro	*	LCM+Bainitic Structure, Ferrite Upto 5% Max.	Microscope	1Pc/Lot	FMT-HT-39	A
7.	IGO / NMTP	*	20 Micron Max.	Microscope	1Pc/Lot	FMT-HT-39	A

OPEN SKTCH

Material- 20MnCr5

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ☒ Special Characteristics as Per Drawing * Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change

Prepared By: *Mandak*

Checked By:

Approved By: *[Signature]*