







INSPECTION STANDARD (HT LAB)

☐ Prototype	☐ Pre-Launch	☒ Production	Date (Original)		30/08/2020		
Part Name:- SHAFT,GEAR(11-14,PTO)		Part No.:- KTE12279133		Inspection Standard Number		SIP/4379/200	
Customer :- ESCORTS (KUBOTA)		Change Level:- 00		Part Stage		HT Lab.	
Sr.No	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness check at Dia D1,D2,	*	57~61 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
2.	Effective case depth at 550 HV 300gf. & 10sec	*	0.70~1.0 mm	Micro Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
3.	Effective case depth at 550 HV 300gf. & 10sec	*	0.70~1.0 mm	Micro Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
4.	Effective case depth at 550 HV 300gf. & 10sec	*	0.70~1.0 mm	Micro Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
5.	Surface Carbon concentration Tooth Bottom	*	0.77~0.95 %	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A
6.	Internal Oxidation Layer Depth at Tooth Bottom	*	Layer Depth Shall be 25 Microns (um) or less	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A
7.	Core Hardness check at A1,A2,A3,A4(d/4)		----	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
8.	Case Micro at PCD	*	Tempered Martensite + Retained austenite 30% max.	Microscope (400x or more Magnification) see std KS-013-0003	1Pc/Lot	HT Lab Report	A
9.	Austenite Grain Size	*	The grain size number shall be 6 or more	Microscope (Three or more visual field shall be check) see std KS-013-0035	1Pc/Lot	HT Lab Report	A
10.	Microstructure	*	Fine pearlite shall have no precipitation within $\frac{1}{2}$ of the lower limit of effective hardened layer depth	Microscope (Three or more visual field shall be check) see std KS-013-0035	1Pc/Lot	HT Lab Report	A
11.	Core Micro check at core hardness location	*	LCTM + Baintic	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A
12.	Precipitation of Fe ₃ C (cementite) on surface at Tooth top & PCD	*	Granular form is allowable Note that the grain size shall be 5 micron or less	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A

OPEN. SKETCH:-

Material:- SCM420(H)

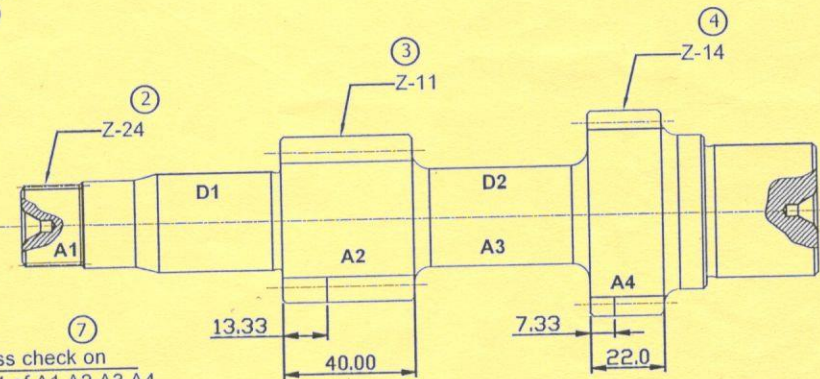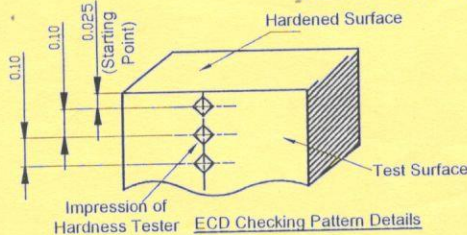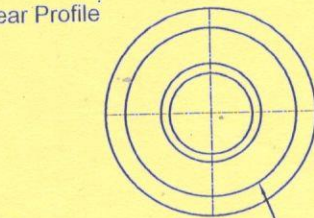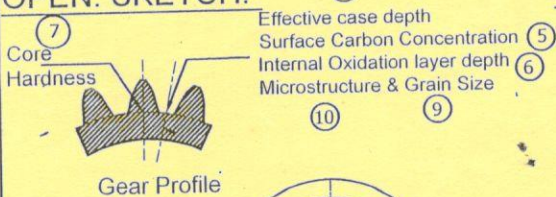

CONTROLLED COPY
 SR. NO. 01
 ISSUED TO Unit-7
 DATED 25/07/22

Note:-
 1st Measurement point at 0.025mm from the Surface, and after each indent 0.10mm interval

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें।

Legends: ☒ Special Characteristics as Per Drawing ☒ Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change