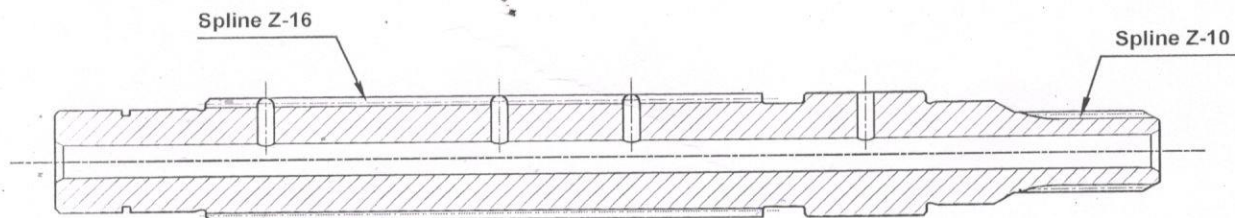
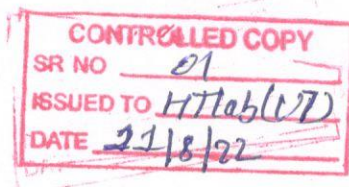


INSPECTION STANDARD (HT LAB)

☐ Prototype	☒ Pre-Launch	☐ Production	Date (Original)	11/March/2022			
Part Name:- Shaft Speed Driven		Part No.:- P80001280A		Inspection Standard Number		SIP/4480/170	
Customer :- M & M SWARAJ		Change Level.:-00		Part Stage		HT Lab.	
Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	*	58~63 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
2.	ECD Measured To 513HV	*	0.5~0.8 mm	Micro Vicker Hardness Tester/ Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
3.	Core Hardness	*	34~42 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
4.	Micro Case	*	Tempered Martensite+RA<20%	Microscope	1Pc/Lot	HT Lab Report	A
5.	Micro Core	*	Bainite+Sorbide Free Ferrite<5%	Microscope	1Pc/Lot	HT Lab Report	A

OPEN SKETCH

Material- 20MnCr5

#ECD to be measured from below spline root.

#Core Hardness to be measured from mid radius of the hollow shaft (approx. :-4.5 mm from the surface of this particular shaft.

Reaction Plan: A-यदि Inspection करते समय कम्पोंन्ट खराब मिले तो खराब कम्पोंन्ट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ☒ Special Characteristics as Per Drawing * Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change