

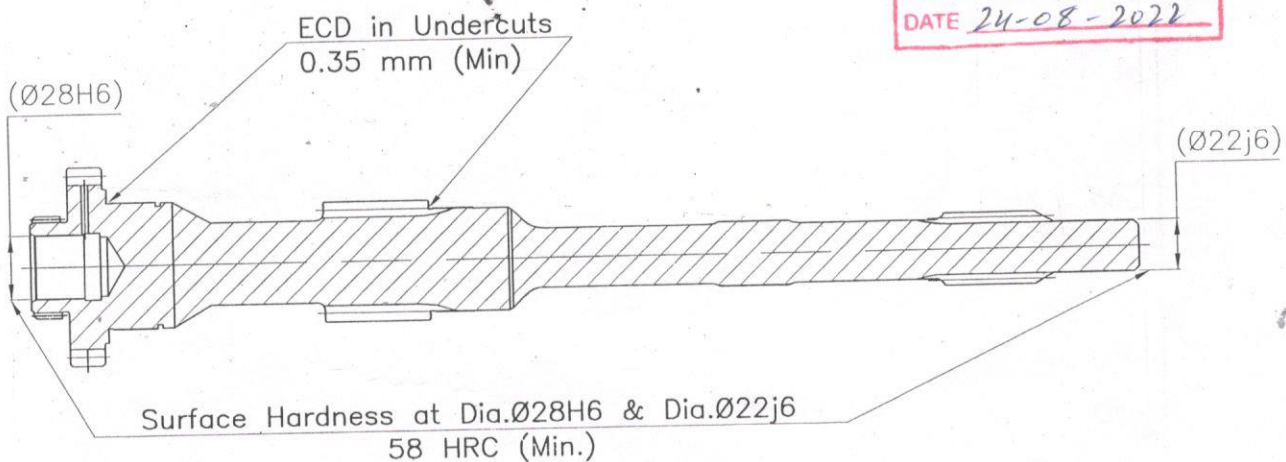
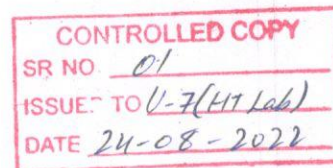


INSPECTION STANDARD (HT LAB)

☐ Prototype	☒ Pre-Launch	☐ Production	Date (Original)	28/01/2019			
Part Name:- Primary Shaft		Part No.:- 93624560		Inspection Standard Number		SIP/4281/250	
Customer :- TMTL		Change Level.:-00		Part Stage		HT Lab.	

Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	*	59-63 HRC	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
2.	ECD Measured To 550HV	*	0.60-0.90 mm	Vicker Hardness Tester/Micro Vicker Hardness Tester	1Pc/Lot	FMT-HT-39	A
3.	ECD in Undercuts	*	0.35 mm (Min.)	Vicker Hardness Tester/Micro Vicker Hardness Tester	1Pc/Lot	FMT-HT-39	A
4.	Surface Hardness at Dia.Ø22j6 & Dia.Ø28H6	*	58 HRC Min.	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
5.	Core Hardness at PCD	*	42 HRC Max.	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
6.	Core Hardness at RCD	*	30 HRC Min.	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
7.	Micro Case	*	Tempered Martensite+ RA<12%, Carbide (Globular) Upto 2% Max.	Microscope	1Pc/Lot	FMT-HT-39	A
8.	Core Micro	*	LCM+Bainitic Structure, Ferrite Upto 5%	Microscope	1Pc/Lot	FMT-HT-39	A
9.	IGO / NMTP	*	20 Micron Max.	Microscope	1Pc/Lot	FMT-HT-39	A

OPEN SKTCH

Material- 20MnCr5

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें।

Legends: ☒ Special Characteristics as Per Drawing ☒ Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change