


Standard Operating Procedure				OPTN. NO.	200	MACHINE NO.	---
				REVISION NO.	01	REVISION DATE	17/04/10
OPERATION :-- Metallurgical Testing				CHD. BY: <i>[Signature]</i>		DATE OF ENACTMENT	
CUST. NAME				APPD. BY: <i>[Signature]</i>		01 - 10 - 2009	
MATERIAL				SAE 8620H			
Sleeve Carrier				2212P01601			
MS/SOP/3012/200							
SECTION INSTRUMENTS DETAIL :							
For Well Tester, Vicker H. Tester, Microscope							
MACHINE / EQUIPMENT PARAMETERS				VALUE			
JIG / FIX. / CTG. TOOL PARAMETERS				VALUE			
CONTROLLING OF DIEMENSION							
Dimension	Specifications	Instrument	Freq.				
Surface Hardness	58~63 HRC	Rockwell Tester	1pc / heat				
Core Hardness	28~40HRC	--do--					
E.C.D. Cut off Point 50 HRC	0.70~1.0	Vicker H Tester					
Micro - Case	Tempered Martensite R.A. Less than 10%	Microscope					
Micro - Core	LCM+ Banite	Microscope					
Surface Carbon Content	0.8 ~ 1.1%						
CASE OF ABNORMALITY / NON CONFORMANCE OF THE PRODUCT							
ACTION PLAN :							
Reset the Dimension as per resetting limit in case of abnormality.							
In case of non conformity , enter in the SPOT Analysis Register.							
GG. CHANGES.							
A. ECD 0.7~1.0 was 0.76~1.14		B.					
C.		D.					

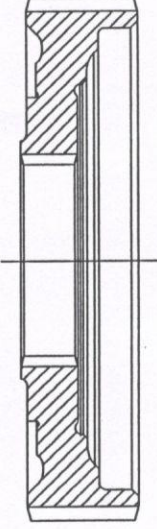

OPTN. SKETCH

CONTROLLED COPY

SR NO. ISSUED TO 127 (HT Lab)

DATE 25/08/22

WORKING INSTRUCTIONS